



Mg-induced increase of band gap in Zn $1 - x$ Mg x O nanorods revealed by x-ray absorption and emission spectroscopy

J. W. Chiou, H. M. Tsai, C. W. Pao, F. Z. Chien, W. F. Pong, C. W. Chen, M.-H. Tsai, J. J. Wu, C. H. Ko, H. H. Chiang, H.-J. Lin, J. F. Lee, and J.-H. Guo

Citation: *Journal of Applied Physics* **104**, 013709 (2008); doi: 10.1063/1.2951939

View online: <http://dx.doi.org/10.1063/1.2951939>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/jap/104/1?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Electronic structure of Al-doped ZnO transparent conductive thin films studied by x-ray absorption and emission spectroscopies](#)

J. Appl. Phys. **110**, 103705 (2011); 10.1063/1.3662202

[Comparison of the electronic structures of Zn \$1 - x\$ Co \$x\$ O and Zn \$1 - x\$ Mg \$x\$ O nanorods using x-ray absorption and scanning photoelectron microscopies](#)

Appl. Phys. Lett. **89**, 043121 (2006); 10.1063/1.2240108

[Electronic structures of group-III–nitride nanorods studied by x-ray absorption, x-ray emission, and Raman spectroscopy](#)

Appl. Phys. Lett. **88**, 223113 (2006); 10.1063/1.2207836

[Diameter dependence of the electronic structure of ZnO nanorods determined by x-ray absorption spectroscopy and scanning photoelectron microscopy](#)

Appl. Phys. Lett. **85**, 3220 (2004); 10.1063/1.1802373

[Electronic structure of ZnO nanorods studied by angle-dependent x-ray absorption spectroscopy and scanning photoelectron microscopy](#)

Appl. Phys. Lett. **84**, 3462 (2004); 10.1063/1.1737075

A horizontal banner with an orange-to-red gradient background. At the top center, the text '2014 Special Topics' is written in a large, white, sans-serif font. Below this text, five circular icons are arranged horizontally, each containing a different material structure and a label. From left to right: 1. A red and black lattice structure labeled 'PEROVSKITES'. 2. A blue and red lattice structure labeled '2D MATERIALS'. 3. A green and black porous structure labeled 'MESOPOROUS MATERIALS'. 4. A yellow and black structure labeled 'BIOMATERIALS/ BIOELECTRONICS'. 5. A brown and black porous structure labeled 'METAL-ORGANIC FRAMEWORK MATERIALS'. At the bottom left, the 'AIP | APL Materials' logo is displayed. At the bottom right, a red ribbon contains the text 'Submit Today!' in white.

Mg-induced increase of band gap in $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods revealed by x-ray absorption and emission spectroscopy

J. W. Chiou,^{1,a)} H. M. Tsai,² C. W. Pao,² F. Z. Chien,² W. F. Pong,^{2,b)} C. W. Chen,³ M.-H. Tsai,⁴ J. J. Wu,⁵ C. H. Ko,⁵ H. H. Chiang,⁵ H.-J. Lin,⁶ J. F. Lee,⁶ and J.-H. Guo⁷

¹Department of Applied Physics, National University of Kaohsiung, Kaohsiung 811, Taiwan

²Department of Physics, Tamkang University, Tamsui 251, Taiwan

³Department of Materials Science and Engineering, National Taiwan University, Taipei 106, Taiwan

⁴Department of Physics, National Sun Yat-Sen University, Kaohsiung 804, Taiwan

⁵Department of Chemical Engineering, National Cheng Kung University, Tainan 701, Taiwan

⁶National Synchrotron Radiation Research Center, Hsinchu 300, Taiwan

⁷Advanced Light Source, Lawrence Berkeley National Laboratory, Berkeley, California 94720, USA

(Received 12 February 2008; accepted 25 April 2008; published online 10 July 2008)

X-ray absorption near-edge structure (XANES) and x-ray emission spectroscopy (XES) measurements were used to investigate the effect of Mg doping in ZnO nanorods. The intensities of the features in the O K -edge XANES spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods are lower than those of pure ZnO nanorods, suggesting that Mg doping increases the negative effective charge of O ions. XES and XANES spectra of O $2p$ states indicate that Mg doping raises (lowers) the conduction-band-minimum (valence-band-maximum) and increases the band gap. The band gap is found to increase linearly with the Mg content, as revealed by photoluminescence and combined XANES and XES measurements. © 2008 American Institute of Physics. [DOI: 10.1063/1.2951939]

I. INTRODUCTION

The wide band gap II–VI semiconductor alloy, ZnMgO , has attracted extensive interest in recent years because of its fundamental and technological importance in ZnMgO/ZnO -based superlattice structures.^{1–3} The photoluminescence (PL) measurements of Mg doped ZnO nanowires/nanorods revealed a blueshift in near-band-edge (NBE) emission as the Mg content is increased,^{4–6} suggesting that this material may be suitable for use in tunable electronic and optical nanodevices. Raman spectra indicated that the disorder associated with the incorporation of Mg dopants enhanced exciton localization and asymmetrically broadened the phonon line-shapes of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanocrystals.⁷ The extended x-ray absorption fine structure (EXAFS) also demonstrated that the blueshift of the band gap (E_g) of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ thin films was associated with the increase of the structural distortion/disorder.⁸ Although PL measurements have revealed the blueshift in E_g in the $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ alloys, the engineering of E_g by altering the electronic density of states (DOSs) at/near conduction-band-minimum (CBM) and valence-band-maximum (VBM) by doping Mg to ZnO nanomaterials has not been extensively investigated.^{9–11} Knowledge of the dependence of the electronic structures of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanomaterials on Mg doping is crucial to understanding the basic physics that underlie their nanotechnological applications. Chang *et al.* attempted to elucidate the correlation between the electronic structures and the optical properties of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods.¹⁰ Here, a combination of PL, EXAFS, x-ray absorption near-edge structure (XANES),

and x-ray emission spectroscopy (XES) was used to investigate the increase of E_g by the doping of Mg in ZnO nanorods.

II. EXPERIMENTAL DETAILS

O and Mg K -edge, Zn L_3 -edge XANES, and Zn K -edge EXAFS spectra were obtained in the fluorescence mode, using the high-energy spherical grating monochromator-20A, Dragon-11A, and wiggler-17C beamlines, respectively, at the National Synchrotron Radiation Research Center in Hsinchu, Taiwan. The XES and corresponding XANES measurements at the O K -edge were carried out at beamline-7.0.1 at the Advanced Light Source, Lawrence Berkeley National Laboratory. The angle of incidence of the incoming photon with respect to the normal direction of the sample's surface was approximately 37° . The resolutions were set to 0.1–0.2 eV at a photon energy of 530–1300 eV during XANES measurements, while the resolution of the XES measurement was set to ~ 0.35 eV. The well-aligned $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ ($x=0, 0.03, 0.07, 0.10, \text{ and } 0.12$) nanorods were prepared on the Si(100) substrate using catalyst-free metalorganic chemical vapor deposition. Room-temperature PL spectra were obtained using the emission of the Xe lamp with a wavelength of 325 nm. The size of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods was measured using high-resolution transmission electron microscopy (HR-TEM). The nanorods had a diameter of $\sim 50 \pm 10$ nm and a length of $\sim 450 \pm 10$ nm. Heo *et al.* reported that due to the limited solubility of Mg in ZnO, ZnMgO nanostructures may grow in a core-shell structure with a low Mg core surrounded by a shell with a higher Mg content.¹² Therefore, $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods were also characterized using HR-TEM. Analyses of the bottom, middle, and top regions of the nanorods show an absence of segregated structures of the impurity phase, indicating that $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods have mainly a single-phase

^{a)}Electronic mail: jwchiou@nuk.edu.tw.

^{b)}Author to whom correspondence should be addressed. Electronic mail: wfpong@mail.tku.edu.tw. On leave at Advanced Light Source, LBNL, Berkeley, CA 94720.

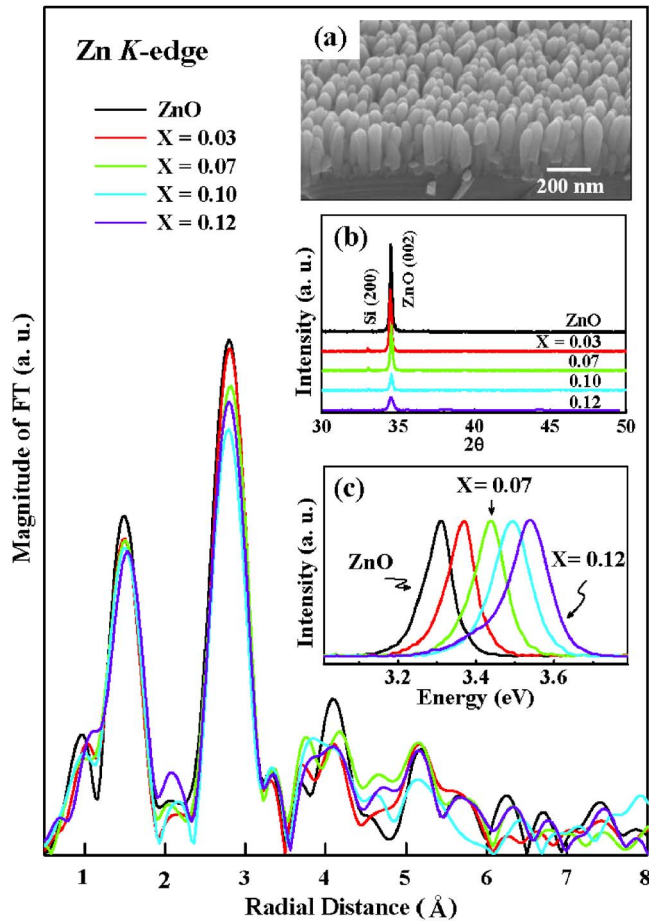


FIG. 1. (Color online) Magnitude of FT of EXAFS $k^3\chi$ data at the Zn K-edge of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods. Insets (a)–(c) present SEM image ($x=0.03$), XRD patterns, and PL spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods, respectively.

structure. Details of the preparation and characterization of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods have been presented elsewhere.⁵

III. RESULTS AND DISCUSSION

The inset (a) in Fig. 1 presents the scanning electron microscopic (SEM) image of $\text{Zn}_{0.97}\text{Mg}_{0.03}\text{O}$ nanorods. X-ray diffraction (XRD) patterns in inset (b) reveal that the doping of Mg does not change the wurtzite structure of host ZnO nanorods. $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods show a predominant (002) reflection at $\sim 34.5^\circ$, indicating that the nanorods are preferentially oriented along the c -axis. Evidently, the XRD spectra of the $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods do not exhibit any Bragg peak of MgO or Mg metal, further supporting the HR-TEM observation that $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods have mainly a single-phase structure, without MgO phase segregation or the formation of a Mg core-shell structure in $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods, as proposed by Heo *et al.*¹² Inset (c) shows the NBE emission in the PL spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods, clearly indicating the shifts of the PL-maximum position from ~ 3.3 ($x=0$) to 3.5 eV ($x=0.12$). This blueshift in the NBE emission cannot be caused by the quantum confinement effect, because the sizes of the $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods in all of the samples are almost the same and are far beyond the quantum confinement regime. Figure 1 also presents the Fourier transform (FT) of EXAFS $k^3\chi$ data at the Zn K-edge. The general

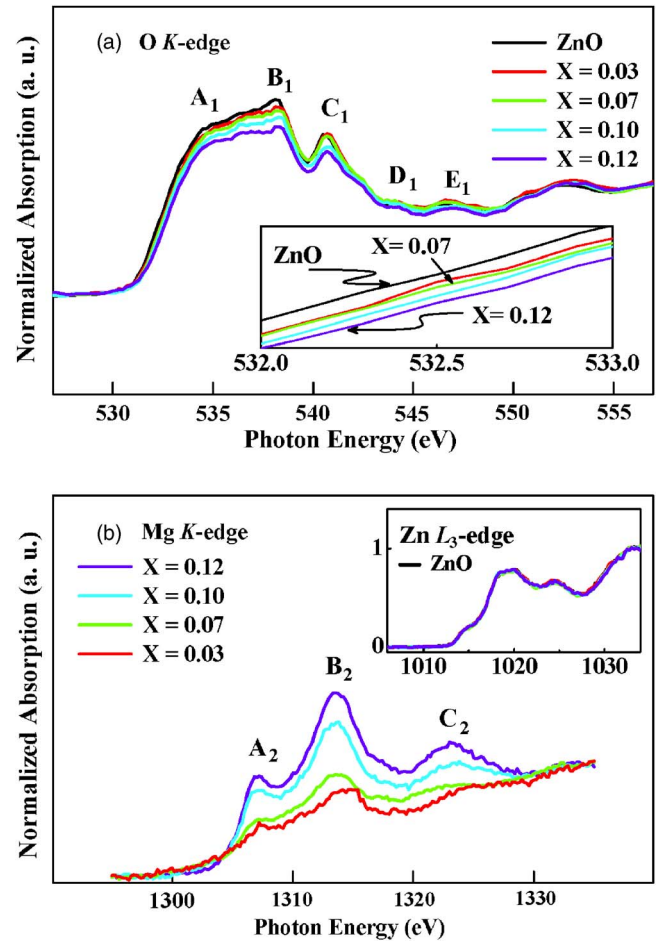


FIG. 2. (Color online) (a) Normalized O K-edge XANES spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods. The inset shows a magnified view of edge features of O K-edge XANES spectra. (b) Normalized Mg K-edge XANES spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods. The inset presents normalized Zn L_3 -edge spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods.

line-shapes and radial distribution of the FT spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods are similar to those of pure ZnO nanorods, suggesting Mg is substituted at the Zn sites. The first two main peaks in the FT spectra correspond to the nearest-neighbor Zn–O and the next-nearest-neighbor Zn–Zn/Zn–Mg bond lengths,⁸ respectively. Their overall intensities decrease as the Mg content in the $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods increases, which can be due to the increase of the structural disorder/distortion at the Zn sites in the $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods. Park *et al.* observed a similar trend for $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ thin films.⁸

Figure 2(a) presents the normalized O K-edge XANES spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods. Features A_1 – E_1 of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods are attributable to electron transitions from O $1s$ to unoccupied O $2p_\pi$ (along the c -axis) and O $2p_\sigma$ (in the bi-layer) states.^{9,13,14} The line-shapes of the O K-edge XANES spectra of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods are very similar to those of ZnO nanorods ($x=0$). However, the overall intensities of the features of $\text{Zn}_{1-x}\text{Mg}_x\text{O}$ nanorods are lower than those of ZnO nanorods, reflecting the reduction in the number of unoccupied O $2p$ -derived states. The decrease in the O K-edge XANES intensity suggests an increase in the occupation of the O $2p$ -orbitals or the number of electrons in O ions. The increase in the number of electrons in O ions by

Mg doping is understandable, because Mg has a significantly smaller electronegativity (1.31) than that of Zn (1.65),¹⁵ such that more electrons are transferred from Mg to the O 2*p* states, and the ionic character of the Zn_{1-x}Mg_xO alloys is increased.^{10,11} Previous studies of Zn_{1-x}Co_xO nanorods indicated that the intensity of the O *K*-edge XANES feature decreases as the Co content increases,⁹ despite the fact that Co has an electronegativity that is larger than that of Zn. This can be understood by the fact that Co has additional 3*d* states, which are absent from Mg. The decrease in intensity due to Co doping can be interpreted as being caused by O 2*p*-Co 3*d* hybridization, which lowers the energies of O 2*p* orbitals, enhancing the occupation of O 2*p* orbitals. The higher O 2*p* occupation associated with smaller electronegativity of Mg is consistent with the higher the intensity of the valence-band photoemission spectra in Fig. 4 of Ref. 9. The inset in Fig. 2(a) shows that the threshold in the O *K*-edge XANES spectra moves slightly toward higher energy as the Mg content in the Zn_{1-x}Mg_xO nanorods increases. Figure 2(b) presents the normalized Mg *K*-edge XANES spectra of Zn_{1-x}Mg_xO. The partial DOSs calculated using the CASTEP code,¹⁶ based on the plane-wave pseudopotential method with the local density approximation for Zn_{1-x}Mg_xO,¹⁰ indicates that the three main features, A₂-C₂, are associated primarily with Mg 3*p*-O 2*p* hybridized states. The intensities of features A₂-C₂ clearly increase with the Mg content, suggesting that the increase in the number of unoccupied Mg 3*p*-derived states is associated with the transfer of electrons from Mg to O atoms as the Mg content increases, in a manner consistent with the O *K*-edge XANES measurements. The inset in Fig. 2(b) also presents the normalized Zn *L*₃-edge XANES spectra of Zn_{1-x}Mg_xO nanorods, which reveal electron transitions from Zn 2*p* states to unoccupied Zn 4*sd* states.^{9,13,17} Figure 2(b) shows that the unoccupied Zn 4*sd* states are insensitive to Mg doping. Indeed, the calculated unoccupied partial DOSs of Zn 4*s* states in Ref. 10 for Zn_{1-x}Mg_xO are similar to that for ZnO.

Figure 3 displays XES and corresponding XANES spectra of O 2*p* states of Zn_{1-x}Mg_xO nanorods. The maximum intensities of the features in the XES and XANES spectra were arbitrarily normalized to unity. The O *K*_α-emission spectra reflect O 2*p* occupied (valence-band) states and O *K*-edge XANES spectra reflect O 2*p* unoccupied (conduction-band) states of Zn_{1-x}Mg_xO nanorods. The spectra in Fig. 3 are similar to those of ZnO nanoparticles reported elsewhere.¹⁸ A well-defined band gap, *E*_g, indicated by the dotted lines is obtained by extrapolating the leading edges in the XANES and XES spectra to the baselines, which correspond to the CBM and VBM,^{18,19} respectively. Apparently, the threshold in the O *K*-edge XANES (O *K*_α XES) spectra overall moves slightly toward higher (lower) energy as the Mg content is increased, as can be seen on the magnified scale in inset (a) [inset (b)]. This result is consistent with the measurements shown in Fig. 2(a). Nevertheless, the combined emission and absorption spectra demonstrate that *E*_g is ~3.3 eV for pure ZnO nanorods and systematically increases with the Mg content in the Zn_{1-x}Mg_xO nanorods, as plotted in inset (c). These results are consistent with the general trend of NBE emission that was revealed by PL

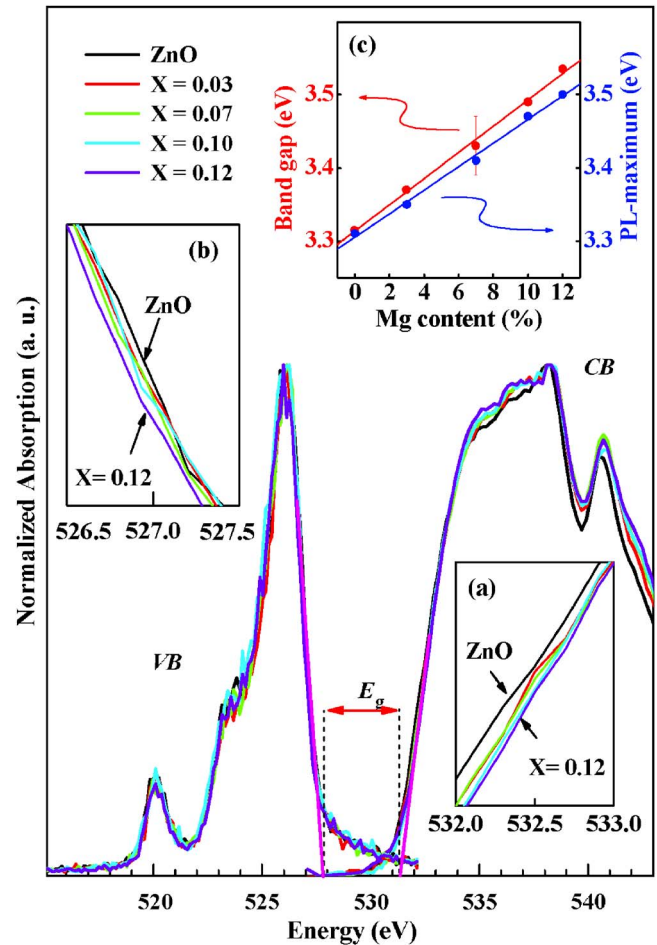


FIG. 3. (Color online) XES and corresponding XANES of O 2*p* states of Zn_{1-x}Mg_xO nanorods. Insets (a) and (b) show magnified views of edge features of O *K*-edge XANES and O *K*_α XES spectra, respectively. Inset (c) plots *E*_g and NBE emission data [inset (c) in Fig. 1] for various Mg content.

measurements [data obtained from inset (c) in Fig. 1]. The *E*_g values that were determined from the combined XES and XANES measurements were slightly larger than those determined from the NBE emission data. Since NBE emission is the result of free exciton emission,¹⁰ the difference between *E*_g values and emission data, Δ*E*_g, can be attributed to the difference between the energy of CBM and the exciton level, which is approximately tens of meV in Zn_{1-x}Mg_xO nanorods. The Δ*E*_g of ~40 meV for *x*=12% is the largest for any Zn_{1-x}Mg_xO nanorods. Recently, temperature-dependent PL studies have found that the exciton was bound by an energy of 50–60 meV (depending on Mg doping) in Zn_{1-x}Mg_xO nanorods,²⁰ suggesting that Δ*E*_g ~ 50–60 meV. The discrepancy may be due to the limit of the energy resolutions of the XES and XANES measurements ~0.35 and 0.1 eV, respectively.

Several factors are believed to affect the shifts of NBE emission in the PL spectra of Zn_{1-x}Mg_xO alloys upon the doping of ZnO with Mg. Excitonic transitions (exciton-related recombination), alloy-induced structural disorder/distortion effects, quantum confinement, surface effects/defects, and bulk defects, such as oxygen vacancies, are present.^{6–8,21,22} The FT analysis of EXAFS results suggests Mg-induced structural disorder/distortion at the Zn sites in

Zn_{1-x}Mg_xO nanorods. Structural disorder/distortion typically is responsible for potential fluctuation in the alloy, enhancing excitonic transition.⁷ This phenomenon may be related to native defects in the ZnMgO alloy, since Mg doping shifts CBM toward higher energy, away from the intrinsic shallow donor states, and increases the activation energy of defect donors, increasing the emission-energy in the PL spectra.^{23,24} Importantly, combining O *K*_α XES and the corresponding O *K*-edge XANES spectra in Fig. 3 demonstrates that the increase in *E*_g is associated with the shifts in CBM (VBM) toward higher (lower) energy upon the doping of host ZnO nanorods with Mg. Previous theoretical calculations have indicated that the widths of both O *2p* and Zn *3d* bands become narrower and their partial DOSs near the top of valence bands increase with the increase of *x* in Zn_{1-x}Mg_xO,¹⁰ suggesting Mg-induced enhancement of the localization of O *2p* and Zn *3d* states as well as the ionic character of Zn_{1-x}Mg_xO. As a result, the screening effect is reduced and the exciton energy is increased, which may explain the linear increase of Δ*E*_g in the inset of Fig. 3.

IV. CONCLUSION

O *K*-edge XANES measurements suggest that Mg doping increased the negative effective charge of oxygen ions. O *K*-edge XES and XANES spectra demonstrate that Mg doping raises and lowers conduction- and valence-band edges, respectively, thus increasing *E*_g. Both PL and combined XES and XANES measurements show that *E*_g increases linearly with Mg content.

ACKNOWLEDGMENTS

One of the authors (W.F.P.) would like to thank the National Science Council of Taiwan for financially supporting this research under Contract No. NSC96-2112-M032-012-MY3. The Advanced Light Source is supported by the Director, Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231.

¹A. Tsukazaki, A. Ohtomo, T. Kita, Y. Ohno, H. Ohno, and M. Kawasaki, *Science* **315**, 1388 (2007).

- ²V. A. Fonoberov and A. A. Balandin, *J. Phys.: Condens. Matter* **17**, 1085 (2005).
- ³A. Malashevich and D. Vanderbilt, *Phys. Rev. B* **75**, 045106 (2007).
- ⁴T. Makino, Y. Segawa, M. Kawasaki, A. Ohtomo, R. Shiroki, K. Tamura, T. Yasuda, and H. Koinuma, *Appl. Phys. Lett.* **78**, 1237 (2001).
- ⁵C. H. Ku, H. H. Chiang, and J. J. Wu, *Chem. Phys. Lett.* **404**, 132 (2005).
- ⁶H. C. Hsu, C. Y. Wu, H. M. Cheng, and W. F. Hsieh, *Appl. Phys. Lett.* **89**, 013101 (2006).
- ⁷J. D. Ye, K. W. Teoh, X. W. Sun, G. Q. Lo, D. L. Kwong, H. Zhao, S. L. Gu, R. Zhang, Y. D. Zheng, S. A. Oh, X. H. Zhang, and S. Tripathy, *Appl. Phys. Lett.* **91**, 091901 (2007).
- ⁸S.-H. Park, K.-B. Kim, S.-Y. Seo, S.-H. Kim, and S.-W. Han, *J. Electron. Mater.* **35**, 1680 (2006).
- ⁹J. W. Chiou, H. M. Tsai, C. W. Pao, K. P. Krishna Kumar, S. C. Ray, F. Z. Chien, W. F. Pong, M.-H. Tsai, C.-H. Chen, H.-J. Lin, J. J. Wu, M.-H. Yang, S. C. Liu, H. H. Chiang, and C. W. Chen, *Appl. Phys. Lett.* **89**, 043121 (2006).
- ¹⁰Y. S. Chang, C. T. Chien, C. W. Chen, T. Y. Chu, H. H. Chiang, C. H. Ku, J. J. Wu, C. S. Lin, L. C. Chen, and K. H. Chen, *J. Appl. Phys.* **101**, 033502 (2007).
- ¹¹M. K. Yadav, M. Ghosh, R. Biswas, A. K. Raychaudhuri, A. Mookerjee, and S. Datta, *Phys. Rev. B* **76**, 195450 (2007).
- ¹²Y. W. Heo, D. P. Norton, L. C. Tien, Y. Kwon, B. S. Kang, F. Ren, S. J. Pearton, and J. R. LaRoche, *Mater. Sci. Eng., R* **47**, 1 (2004).
- ¹³J. W. Chiou, K. P. Krishna Kumar, J. C. Jan, H. M. Tsai, C. W. Bao, W. F. Pong, F. Z. Chien, M.-H. Tsai, I.-H. Hong, R. Klausner, J. F. Lee, J. J. Wu, and S. C. Liu, *Appl. Phys. Lett.* **85**, 3220 (2004).
- ¹⁴J. W. Chiou, J. C. Jan, H. M. Tsai, C. W. Bao, W. F. Pong, M.-H. Tsai, I.-H. Hong, R. Klausner, J. F. Lee, J. J. Wu, and S. C. Liu, *Appl. Phys. Lett.* **84**, 3462 (2004).
- ¹⁵*Table of Periodic Properties of the Elements* (Sargent-Welch Scientific, Skokie, IL, 1980).
- ¹⁶T. Mizoguchi, A. Seko, M. Yoshiya, H. Yoshida, T. Yoshida, W. Y. Ching, and I. Tanaka, *Phys. Rev. B* **76**, 195125 (2007).
- ¹⁷M. C. Payne, M. P. Teter, D. C. Allan, T. A. Arias, and J. D. Joannopoulos, *Rev. Mod. Phys.* **64**, 1045 (1992).
- ¹⁸C. L. Dong, C. Persson, L. Vayssieres, A. Augustsson, T. Schmitt, M. Mattesini, R. Ahuja, C. L. Chang, and J.-H. Guo, *Phys. Rev. B* **70**, 195325 (2004).
- ¹⁹J. W. Chiou, S. C. Ray, H. M. Tsai, C. W. Pao, F. Z. Chien, W. F. Pong, M.-H. Tsai, J. J. Wu, C. H. Tseng, C.-H. Chen, J. F. Lee, and J.-H. Guo, *Appl. Phys. Lett.* **90**, 192112 (2007).
- ²⁰J. G. Lu, Y. Z. Zhang, Z. Z. Ye, Y. J. Zeng, J. Y. Huang, and L. Wang, *Appl. Phys. Lett.* **91**, 193108 (2007).
- ²¹Ü. Özgür, Ya. I. Alivov, C. Liu, A. Teke, M. A. Reshchikov, S. Doğan, V. Avrutin, S.-J. Cho, and H. Morkoç, *J. Appl. Phys.* **98**, 041301 (2005).
- ²²V. A. Fonoberov and A. A. Balandin, *J. Nanoelectron. Optoelectron.* **1**, 19 (2006).
- ²³Y. W. Heo, Y. W. Kwon, Y. Li, S. J. Pearton, and D. P. Norton, *Appl. Phys. Lett.* **84**, 3474 (2004).
- ²⁴Y. J. Zeng, Z. Z. Ye, Y. F. Lu, J. G. Lu, L. Sun, W. Z. Xu, L. P. Zhu, B. H. Zhao, and Y. Che, *Appl. Phys. Lett.* **90**, 012111 (2007).