

Accepted Article

Title: SSZ-27: a small pore zeolite with large heart-shaped cavities determined using multi-crystal electron diffraction

Authors: Stef Smeets, Stacey I. Zones, Dan Xie, Lukáš Palatinus, Jesus C. Pascual, Son-Jong Hwang, Joel E. Schmidt, and Lynne B. McCusker

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: *Angew. Chem. Int. Ed.* 10.1002/anie.201905049
Angew. Chem. 10.1002/ange.201905049

Link to VoR: <http://dx.doi.org/10.1002/anie.201905049>
<http://dx.doi.org/10.1002/ange.201905049>

RESEARCH ARTICLE

SSZ-27: a small pore zeolite with large heart-shaped cavities determined using multi-crystal electron diffraction

Stef Smeets,^[a,b] Stacey I. Zones,^{*,[c]} Dan Xie,^[c] Lukáš Palatinus,^[d] Jesus Pascual,^[c] Son-Jong Hwang,^[e] Joel E. Schmidt,^[c] Lynne B. McCusker^[f,g]

Abstract: The high-silica zeolite SSZ-27 was synthesized using one of the isomers of the organic structure-directing agent that is known to produce the large-pore zeolite SSZ-26 (**CON**). The structure of the as-synthesized form was solved using multi-crystal electron diffraction data. Data were collected on eighteen crystals, and to obtain a high-quality and complete data set for structure refinement, hierarchical cluster analysis was employed to select the data sets most suitable for merging. The framework structure of SSZ-27 can be described as a combination of two types of cavities, one of which is shaped like a heart. The cavities are connected through shared 8-ring windows to create straight channels that are linked together in pairs to form a one-dimensional channel system. Once the framework structure was known, molecular modeling was used to find the best fitting isomer, and this, in turn, was isolated to improve the synthesis conditions for SSZ-27.

Introduction

A number of novel high-silica zeolite structures have been found through exploratory synthesis trials that combine an organic guest molecule, usually a quaternary ammonium compound, with a variety of synthetic conditions. We have recently described how the inorganic conditions chosen in the hydrothermal reaction can bias the crystalline product in terms of the sub-units likely to occur in the zeolite structure.^[1] For example, syntheses can be tuned or modified to produce zeolites with relatively moderate SiO₂/Al₂O₃ ratios (SAR) and small pores running multi-dimensionally between cages (where the organic guest is found in the as-synthesized zeolite). This is particularly relevant in the search for

materials with high performance in DeNO_x reactions in the SCR (selective catalytic reduction) components in diesel emission systems,^[2] where there is high interest in novel small-pore zeolites. High hydroxide levels and the presence of one of a number of alicyclic ring derivatives produce zeolites yielding an optimum DeNO_x catalyst once the counter ions have been exchanged with copper or iron cations. In the various zeolite framework types discovered over the last few decades,^[3] there is a wide range of channel and cage architectures to choose from. A description of various unique zeolitic features with examples are given in Table S1 (Supporting Information).

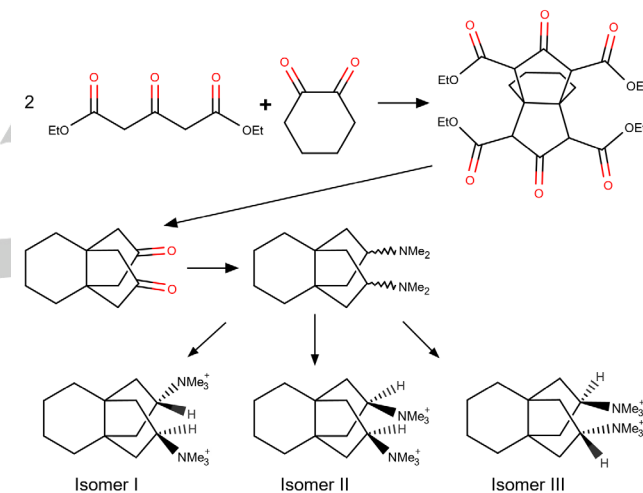


Figure 1. Synthesis scheme to make the diquaternary ammonium isomers used in SSZ-26 (**CON**) and their labeling. Isomer III is used in the synthesis of SSZ-27.

In the present study we explore how the synthesis of a diquaternary organic structure-directing agent (SDA) results in different isomeric versions of the SDA, and how a small difference can lead to the formation of a different zeolite framework. Figure 1 shows the synthesis path that produces the isomers and their labeling from an earlier work.^[4] Initially, we focused on the production of zeolite SSZ-26 (**CON**) and showed that it could be made from two well-described isomers (isomers I and III).^[4] The concept for developing these isomers was to break the fit of an SDA into either (1) a cage accessed by smaller portals, or (2) a single large pore. A past study, juxtaposing the size of the SDA and the SAR conditions, shows a breakdown into 5 types of zeolite products.^[5] At the time, we succeeded in creating a material with intersecting pores. In fact, this was the first discovery of a zeolite (SSZ-26) with both large- and medium-sized pores.^[6] During the course of the synthesis explorations for SSZ-26, we occasionally encountered a different product. Early microporosity studies on the impurity phase, which we termed SSZ-27, indicated

- [a, b] Dr. S. Smeets
Department of Materials and Environmental Chemistry, Stockholm University, SE-106 91 Stockholm, Sweden; Kavli Institute of Nanoscience, Delft University of Technology, 2629 HZ Delft, The Netherlands
E-mail: s.smeets@tudelft.nl
- [c] Dr. S. I. Zones, Dr. D. Xie, J. C. Pascual, Dr. J. E. Schmidt
Chevron Energy Technology Company, Richmond, California 94802, United States
E-Mail: sizo@chevron.com
- [d] Dr. L. Palatinus
Institute of Physics of the Czech Academy of Sciences, Na Slovance 2, Prague, Czechia
- [e] Dr. S.-J. Hwang
Division of Chemistry and Chemical Engineering, California Institute of Technology, Pasadena, California 91125, United States
- [f, g] Dr. L. B. McCusker
Department of Materials, ETH Zurich, Vladimir-Prelog-Weg 5, CH-8093 Zurich, Switzerland; Department of Chemical Engineering, University of California, Santa Barbara, California 93106, United States

Supporting information for this article is given via a link at the end of the document.

RESEARCH ARTICLE

that it had only small pores and selective hydrocarbon uptake. At the time, these materials were not of much developmental interest for catalysis or for separations, so further characterization of SSZ-27 was not pursued. However, interest in small pore zeolites has recently taken a dramatic upward turn. We therefore revisited the synthesis of SSZ-27, and show here that the conformation of one of the isolated isomers of the diquateryary SDA (isomer III) is such that it fits particularly well into one of the cavities of SSZ-27. Here we present the reaction conditions and modeling results that led to the synthesis of SSZ-27 and to an understanding of how it forms, and its structure determination from electron diffraction data.

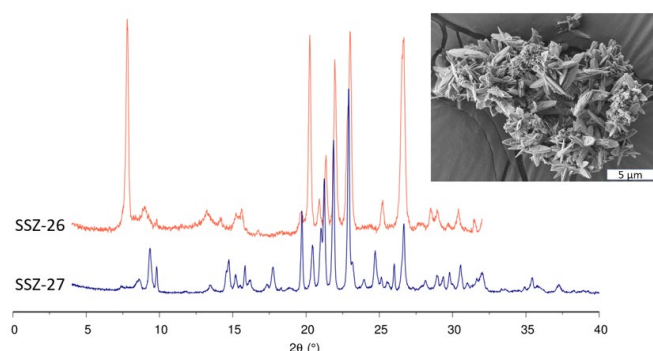


Figure 2. XRPD pattern for SSZ-26 (CON) and SSZ-27, both as-synthesized. The inset shows an SEM image of as-synthesized SSZ-27. Note that the SSZ-27 sample shown here may contain an SSZ-26 impurity (see text).

Results and Discussion

Synthesis

Our point of departure was the synthesis of the diquateryary SDA, shown in Figure 1. The concept was to build on the established organic synthesis chemistry of Ginsberg and others^[7,8] to build fused molecules called propellanes. In this way we could make derivatives that might promote the construction of channels in the zeolite framework that would extend in more than one direction. We could convert the resulting dione to a di-tertiary amine in one step using the Leuckart reaction.^[9] These diamines can then be quaternized using methyl iodide. Note that in the formation of the diamine, the isomeric possibilities (there are 3 at this step) are fixed. Individual isomers were recovered by selective recrystallization methods and their structures determined using single-crystal X-ray diffraction data.^[4]

For the zeolite synthesis, we used a set of inorganic component ratios consistent with earlier work on high silica zeolites like ZSM-5 (MFI), where a reduced hydroxide to silica ratio was needed to create structures rich in 5-ring sub-units. An important finding proved to be the need to reduce the alkali content while retaining the amount of hydroxide, and this was achieved by replacing the alkali cations with the quaternary ammonium centers. This change reduces the intrusion of high-silica zeolite competitors like

Mordenite and Magadiite, which require sodium in the synthesis.^[10] As we were exploring the synthesis conditions for SSZ-26, we occasionally encountered SSZ-27 as a by-product. SSZ-27 formed well-defined homogenous crystals (Figure 2). A comparison of the X-ray powder diffraction patterns for SSZ-26 and SSZ-27 is shown in Figure 2.

Structure determination using electron diffraction data

Preliminary characterizations of SSZ-27 using XRPD revealed several unindexed peaks, which were identified as coming from quartz and SSZ-26 (CON) impurity phases (Supporting Information). In view of the fact that obtaining a pure sample of SSZ-27 was proving to be difficult (more on this later), we opted to collect ED data using the continuous rotation method,^[11] which offers a combination of fast acquisition times and high data completeness, because all of reciprocal space is sampled. We used a recently developed crystal tracking routine to ensure that the crystal stayed in the electron beam during rotation.^[12] This makes it easier to collect data with high rotation ranges, and at the same time enables more accurate integration of the reflection intensities for structure refinement. Diffraction data were collected on eighteen isolated crystals between 200 and 1000 nm in size over three sessions (Supporting information Table S2 and Figure S2). Unit cell determination, indexing, and intensity integration were performed using XDS^[13] (Supporting information Tables S4 and S5). The patterns of fourteen crystals could be indexed with very similar unit cells, with mean lattice parameters of $a=24.12(14)$ Å, $b=13.81(6)$ Å, $c=25.07(10)$ Å, $\beta=115.19(18)^\circ$ in space group $C2/m$, matching the unit cell found for SSZ-27 in our preliminary XRPD assessment (Supporting Information). The cell parameters of SSZ-27 were optimized using the synchrotron XRPD data and the Pawley^[14] profile-fitting routine in TOPAS 5,^[15] yielding a good profile fit with $a=23.29$ Å, $b=13.37$ Å, $c=24.38$ Å, $\beta=114.23^\circ$. Several of the fourteen ED data sets could be used for structure determination using the programs FOCUS^[16,17] and SHELXT,^[18] revealing the framework structure of SSZ-27 (Figure 3a). The remaining four crystals had a unit cell matching SSZ-26 (CON). A detailed characterization of the SSZ-26 crystals can be found in the Supporting Information.

Because the crystal system of SSZ-27 is monoclinic, none of the ED data sets had a completeness of more than 90%, which is required for a good structure refinement. Therefore, to improve data completeness and redundancy, several data sets were merged. We performed hierarchical cluster analysis (HCA) on the fourteen data sets using the algorithm described by Giordano and coworkers^[19] to find the optimal selection of data sets for merging. We have found this approach to be useful for dealing with large multi-crystal ED data sets.^[20] The distance metric t , which defines the similarity between the data sets, is derived from the correlation coefficients of the common reflection intensities (CC_t) in pairs of data sets, and the 'average' linkage method is used. The clusters can be visualized in a dendrogram (Figure 4a), which facilitates finding a suitable cut distance, although finding the right value

RESEARCH ARTICLE

involved some trial and error. Finally, a cut distance $t=0.32$, equivalent to $CC_t = 0.95$, was used. In our experience with HCA, clusters with $t < 0.40$ usually result in useful data sets. Here, two clusters were obtained, where the largest cluster, consisting of 10 data sets (shown in red), comprised the highest data quality (assessed via $CC_{1/2}$ ^[21] and completeness (Supporting Information Table S6). The scripts for cluster analysis are available online from <https://github.com/stefsmets/edtools>.

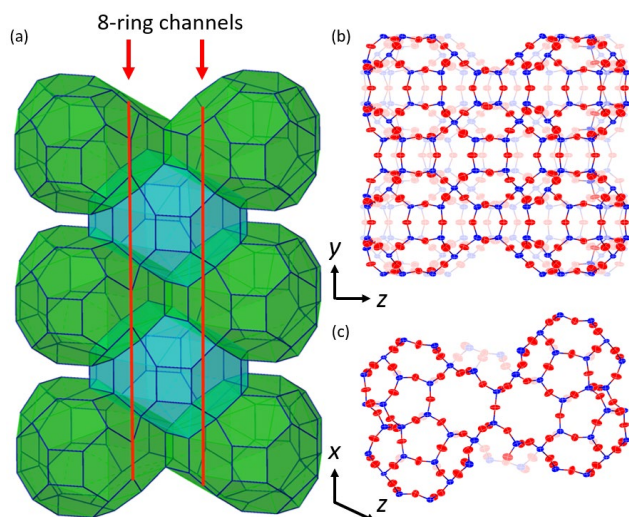


Figure 3. (a) Schematic representation of the crystal structure of SSZ-27 with the heart-shaped cavities (50T) in green, and the 42T cavities in blue. Each 42T cavity connects four heart-shaped cavities through 8-ring windows, forming 1-dimensional channels along the y-axis. Red lines indicate the direction of a pair of 8-ring straight channels. The 8-ring channels are linked through the 42T cavities. The heart-shaped cavities can be viewed as large side pockets. Views of the framework structure along the (b) x- and (c) z-axes showing the ADPs at 50% probability.

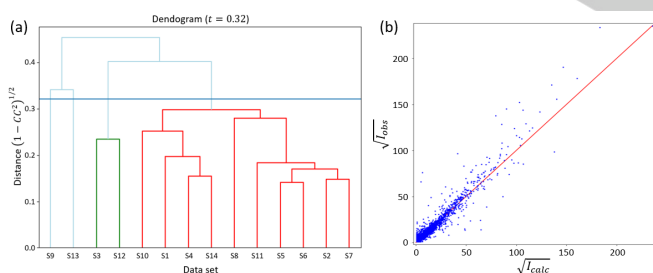


Figure 4. (a) Dendrogram showing the correlation between the SSZ-27 data sets (crystals S1-S14) corresponding to the data shown in Table S4 (Supporting Information). The cut distance set at 0.32 is represented by the horizontal line. Two clusters (green, red) can be identified. (b) $\sqrt{I_{obs}}$ vs. $\sqrt{I_{calc}}$ plot for the refinement of SSZ-27. The refinement details can be found in Table S7 (Supporting Information).

The ten data sets belonging to the largest cluster were merged using XSCALE^[13] and structure refinement was initiated using the lattice parameters obtained from the XRPD data, reasoning that these would be more accurate than those obtained from ED data. Indeed, this immediately resulted in more reasonable average

Si—O bond distances. Restraints on the Si—O distances and O—Si—O angles were not necessary. The atomic displacement parameters (ADPs) for all framework atoms were refined anisotropically. In the final stages of the refinement, the SWAT instruction was introduced to model the diffuse species in the channels (such as the SDA, residual water, Na⁺). This instruction suppresses the contribution from the strong, low-angle reflections where the contribution of extra-framework species is strongest. This significantly reduced the R1 value, and resulted in more meaningful shapes for the ADPs (Figure 3b,c). The refinement of the framework structure of SSZ-27 converged with R1 = 0.178, wR2 = 0.486, and S = 1.47 (Figure 4b). Crystallographic details and the geometry of the zeolite framework are summarized in the Supporting information (Tables S6–S8).

In a recent publication, we showed that physically meaningful anisotropic ADPs can be obtained from ED data, provided these are of sufficiently high quality.^[12] ADPs are known to act as a fudge factor for poor quality data. For this reason, they are often refined isotropically or their physical meaning is ignored. In the case of SSZ-27, the anisotropic refinement of the ADPs was stable without the addition of restraints and their values are physically sensible (Figure 3b,c). They are slightly elongated along the z-direction, which we attribute to lower data redundancy along this direction. The ADPs of the O atoms are slightly larger than those for Si, and elongated in the direction perpendicular to the plane formed by the Si—O—Si bond. The fact that reliable ADPs can be obtained for submicron-sized crystals from ED data may open up new possibilities for studying the atomic vibrations or static disorder in zeolites that do not grow large enough for X-ray single-crystal analysis. Finally, we attempted to find the position of the SDA from the ED data. To do so, the SWAT instruction was removed, and a difference map generated. Although the difference map clearly revealed two large clouds of residual electrostatic potential (Supporting Information Figure S3), refinement of the SDA in the heart-shaped cavity was not stable, so we had to conclude that the data do not support refinement of the SDA at this stage (see also the Supporting information).

Framework structure

The structure analysis confirmed that SSZ-27 is indeed a small pore zeolite. As mentioned earlier, the data also revealed the presence of a small, but noticeable amount of SSZ-26. The framework structure of SSZ-27 is characterized by two types of cavities (Figure 5a-b). The larger, heart-shaped cavity consists of 50 T-atoms ($[8^26^{10}5^{10}4^6]$), and has two 8-ring windows with free dimensions of 3.6×5.5 Å (Supporting Information Figure S4), which are shared with a smaller cavity of 42 T-atoms ($[8^46^84^6]$). Each 42T cavity, delimited by a 14-ring perpendicular to the z-axis, connects four heart-shaped cavities together. Figure 6 shows the orientation of the heart-shaped cavities with respect to the 42T cavities and the layer they form in the xz-plane. Each layer is shifted by $(\frac{1}{2}, \frac{1}{2}, 0)$ with respect to the adjacent one. SSZ-27 has a one-dimensional channel system. A pair of linked straight 8-ring

RESEARCH ARTICLE

channels runs along the y -axis, alternating between single 42T and two heart-shaped cavities. The heart-shaped cavities can be viewed as large side-pockets. This means that despite this being a small-pore zeolite, the internal volume is relatively large (Figure 3).

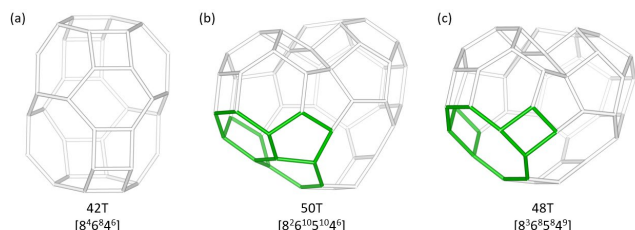


Figure 5. Schematic representation of (a) the small 42T cavity, (b) the heart-shaped cavity observed in SSZ-27, and (c) the heart-shaped cavity observed in ITQ-55. The differences between the heart-shaped cavities are highlighted in green.

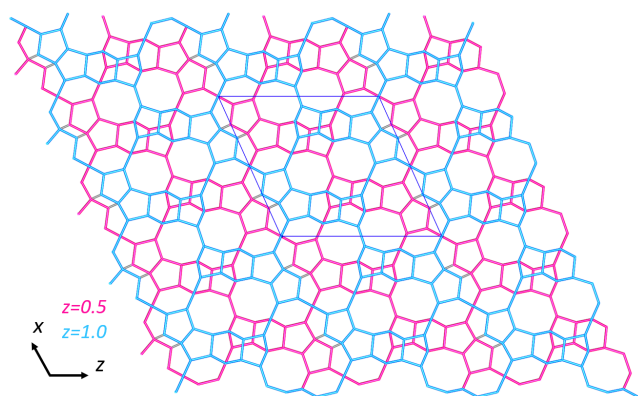


Figure 6. Schematic representation of the framework structure of SSZ-27 along the y -axis showing the arrangement of the heart-shaped and 42T cavities in the xz -plane. The structure can be described in terms of layers that stack along the y -axis, where pink depicts the $y=0.50\pm 0.25$ layer and blue the $y=1.00\pm 0.25$ layer. The layers are connected via 8-rings that connect each 42T cavity with 4 heart-shaped cavities in the adjacent layers, forming 1D channels running parallel to the y -axis. O atoms are omitted for clarity.

Another small-pore zeolite with a slightly different heart-shaped cavity was reported recently by Bereciartua and coworkers.^[22] The framework structure of this zeolite, ITQ-55, consists of heart-shaped cavities exclusively. These 48 T-atom cavities ($[8^3 6^8 5^4 4^9]$) are interconnected via three shared 8-ring windows forming a 2-dimensional channel system. The difference between the ITQ-55 and SSZ-27 heart-shaped cavities is that two 4-rings and one 8-ring in the ITQ-55 cavity are replaced by two 6-rings and two 5-rings in SSZ-27 (Figure 5b-c). Furthermore, the 8-ring openings in ITQ-55 appear to be more restricted (free dimensions: $2.1 \times 5.8 \text{ \AA}$ and $3.4 \times 5.3 \text{ \AA}$) than those in SSZ-27 ($3.6 \times 5.5 \text{ \AA}$; Supporting Information Figure S5).

To the best of our knowledge, the **EEI**^[23,24] framework type is the only one besides that of SSZ-27 with small pores, a one-

dimensional channel system, and large side pockets. In our previous experiments, SSZ-45 (**EEI**) showed a surprisingly low N_2 microporosity ($0.056 \text{ cm}^3/\text{g}$),^[24] which appeared to be limited by the fact that the connection between the cavities involves two 8-rings (i.e. forms a short channel) and is relatively rigid. In contrast, the micropore volume of $0.14 \text{ cm}^3/\text{g}$ found for SSZ-27 is much more in line with what is expected for a zeolite (Supporting Information Figure S1). We suspect that the pore configuration consisting of only a single 8-ring window connecting the large cavities allows for much more efficient diffusion.

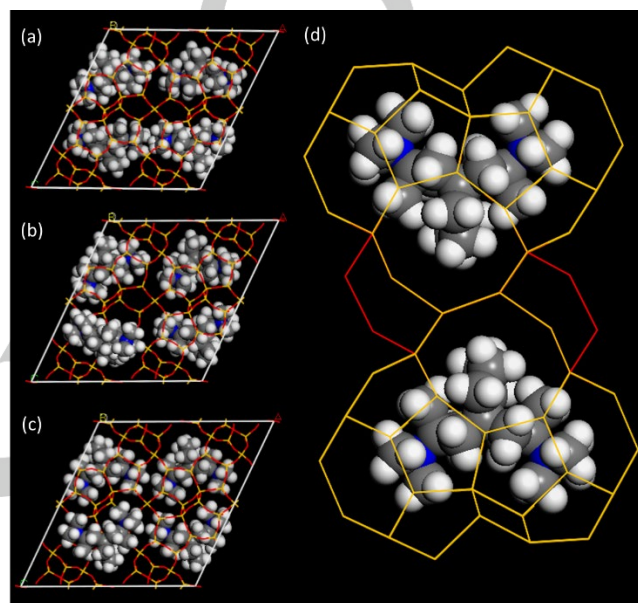


Figure 7. Modeling fit and energetics for (a) isomer I (-3.66 kJ/Mol), (b) isomer II (-3.31 kJ/Mol), and (c) isomer III (-8.95 kJ/Mol) in the heart-shaped cavities of SSZ-27. (d) close-up view of isomer III.

Molecular modeling and the location of the SDA

The molecular modelling results show that the SDA is located exclusively in the heart-shaped cavity, which fits around the SDA (isomer III) like a glove (Figure 7). At a maximum occupancy of 0.5 on a position of mirror symmetry, there is one SDA (with two possible orientations) per heart-shaped cavity, or four ($8 N^+$) per unit cell. Based on elemental analyses (Supplementary Information Table S12), the SAR of the framework was estimated to be 14.5, which translates to 7.5 Al per unit cell, so the charge from the SDA balances that of the framework nicely. This would indicate that there are no additional organic cations in the 42T cavity, where the second cloud of residual electrostatic potential was found, and that is consistent with the fact that the cavity is too small to accommodate an SDA cation. On the other hand, the elemental analysis also indicate the presence of a small amount of residual Na^+ (approximately 1.0 per cell), which could be located in the 42T cavity with an occupancy of 0.5. This may indicate that the SDA is not fully occupied, which we have

RESEARCH ARTICLE

observed before [25–27]. The rest of the 42T cavity is probably filled with residual water.

It has been observed experimentally,^[28] and predicted computationally^[29] that the SDA can direct the location of Al in aluminosilicates. We have previously observed this for borosilicates, in which B atoms are preferentially located in close proximity to the N⁺ center in the SDA.^[25,30] In SSZ-27, the SDA appears to be located exclusively in the heart-shaped cavity, which suggests that the Al is likely to be at the surface of this cavity too. We hypothesize that this means that all the active sites are accessible in the side pockets created by the heart-shaped cavities, whereas the main straight channels are relatively free of active sites, and this might reduce the potential for blockage.

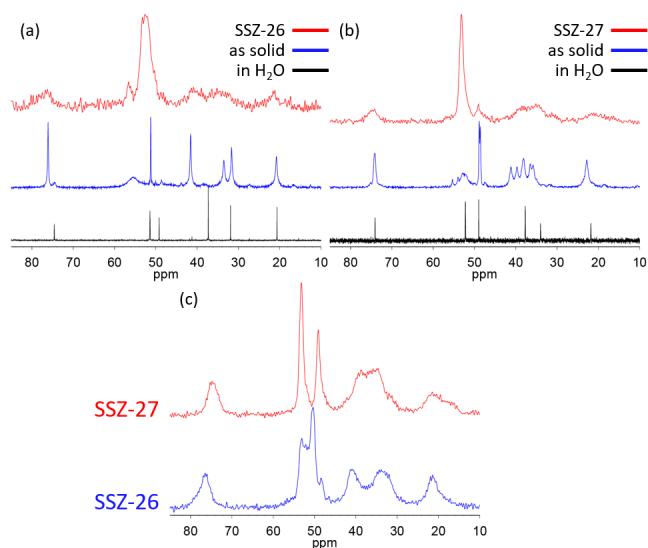


Figure 8. ¹³C MAS NMR spectra for (a) SSZ-26 (red), isomer I in the solid state (blue) and in water (black), (b) SSZ-27 (red), isomer III in the solid state (blue) and in water (black). (c) ¹³C CPMAS-NMR (0.5 ms cross-polarization contact time) spectra for SSZ-26 and SSZ-27.

NMR

Figure 8 shows a comparison of the ¹³C MAS NMR spectra for the as-made products in runs to make SSZ-26 (with isomer I) and SSZ-27 (with isomer III). Also shown are the spectra for the two separate isomers (I and III) in the crystalline solid state and in solution. There are clear differences in the ¹³C MAS NMR spectra of the two isomers, but the lines become broader and less distinctive in when they are entrapped in the SSZ-26 and SSZ-27 framework structures. Note that ¹³C resonances in the crystalline solid are more complicated than those in solution phase,^[4] especially for peaks in the 35–45 ppm region for Isomer I and the 45–65 ppm region for Isomer III. The change may be attributed to the generation of less symmetric crystalline stacking of molecules during solidification. Therefore, the ¹³C NMR spectra of the two zeolites do not provide a clear view of the structural difference between the isomers. However, ¹³C cross-polarization MAS

(CPMAS) spectra in Figure 8c differentiate resonances of methylene carbons in the 5-membered rings (30–45 ppm) as well as the methyl groups.

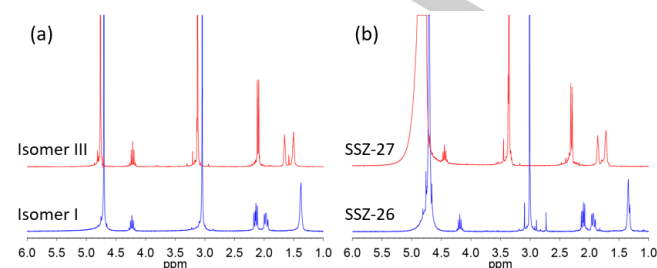


Figure 9. Liquid phase ¹H NMR spectra for (a) pure isomers I and III, and (b) organic compounds extracted after dissolution of SSZ-26 and SSZ-27.

To unambiguously show which isomer was occluded inside the two frameworks we dissolved the crystalline samples of SSZ-26 and SSZ-27 with HF and extracted the organic material for ¹H NMR analysis. Besides a slight shift because of the acidic condition after dissolution with HF, the ¹H NMR spectra (Figure 9) clearly demonstrate that the isomers recovered from SSZ-26 and SSZ-27 identify as I and III, respectively. This proves that both samples contain only a single isomer, and that no interconversion occurred during zeolite synthesis and crystallization.

On the other hand, the ED structure analysis clearly showed that SSZ-26 is a minor component in the SSZ-27 sample studied. Additional modeling studies (Supporting information Table S13 and Figure S9) show that while Isomer I significantly favors the formation of SSZ-26 (-7.6 kJ/mol Si) over SSZ-27 (-3.66 kJ/mol Si), Isomer III only favors SSZ-27 slightly (-8.95 kJ/mol Si) over SSZ-26 (-8.18 kJ/mol Si). Then it is perhaps not surprising that some SSZ-26 formed in the presence of Isomer III, albeit more slowly than SSZ-27. Of course, the chemical environment of Isomer III in SSZ-26 will be slightly different from that in SSZ-27 and this will contribute to the breadth of the ¹³C NMR signals, making a definitive interpretation of the NMR spectra difficult. Additional NMR studies using nuclear Overhauser effect spectroscopy (NOESY) to better probe the details of the SDA within the zeolite are planned.

Additional synthesis studies

In an attempt to confirm the indications of the energy calculations that isomer I favors the formation of SSZ-26 and isomer III SSZ-27 experimentally, we performed a set of synthesis experiments where the two isomers (I and III) were used individually with and without seeding (Table 1). It can be seen that in the case of isomer III, which shows the favorable space-filling (Figure 7), SSZ-27 crystallizes. The formation is even faster if there is seeding with SSZ-27. In contrast, the other two experiments yield no SSZ-27 and eventually form SSZ-26 after a much longer run period (4–5 times longer). In the process of determining the crystallization

RESEARCH ARTICLE

requisites for reproducing the synthesis of SSZ-27, we found that higher temperatures (170°C) favored SSZ-27 over SSZ-26. The latter is typically made at 160°C. While the zeolite synthesis literature does describe some examples of crystallization of relatively open structures at higher temperatures, the general trend in crystallization is to produce open, metastable structures at short reaction times and lower temperatures and then zeolites with progressively higher framework density (sometimes through structure transformation^[31]) at longer reaction times and higher temperatures. The void volumes in zeolite structures have an inverse relationship to framework density, and the framework structure of SSZ-26, which crystallizes at the lower temperature, is in fact more open than that of SSZ-27.

Returning to the theme advanced in the introduction, alicyclic derivatized ring structures provide good guest molecules for the formation of cage-based zeolites under the right synthetic conditions. The zeolite SSZ-13 (**CHA**) was first discovered with a derivative of the polycyclic hydrocarbon, adamantane.^[32] Similarly, a very large number of piperidine ring derivatives will make SSZ-35 (**STF**).^[33] The underlying aim in the synthesis was to produce guest molecules that have axes long enough to extend along the channels of a zeolite. This is true for the *anti,anti* isomeric derivative (Isomer I) and, in fact, SSZ-26 is the only zeolite made with this SDA. However, once both trimethyl ammonium groups have *syn,syn* configurations (Isomer III), it is as though the molecule is beginning to fold in on itself to produce more of a cage structure. This was well-illustrated in our previous work to produce a triquatery ammonium derivative off a central benzene ring, where the imidazolium charged groups folded in on themselves to stabilize the sizable cage of the small pore zeolite **LTA**.^[34]

Table 1. Crystallization selectivity for the use of 2 SDA isomers.

Run #	Isomer #	Seeded?	Result
1	III	Yes	Good (SSZ-27 formed)
2	III	No	Slower crystallization of SSZ-27
3	I	Yes	No SSZ-27, eventually SSZ-26
4	I	No	No SSZ-27, eventually SSZ-26 (slower than in 3)

Conclusion

Synthesis highlights in this work are that subtle changes in the rigid organo-cation (SDA) stereochemistry can lead to entirely different zeolite (host lattice) structures as the framework develops around the guest molecule. In turn, as we continue to increase our database of known zeolite structures, and understand the spatial orientation of the guest SDA molecules in the lattice, our ability to create new pairings improves. That is, we can predict what type of host environment can accommodate the guest and in which orientation. Molecular modeling of the type seen here can be used effectively to check on the feasibility of the

orientation of the SDA in a prospective lattice. In addition, our understanding of how the inorganic conditions of a zeolite synthesis bias the potential for specific sub-units in the developing structure provide another parameter in model building for creating space for a guest. The resurgence of discoveries related to ABC-6 zeolites, small pore products with larger cages that host the organo-cations, are a good example. Here, the SSZ-27 zeolite, rich in 5 and 6 ring subunits (which typically requires a higher Si/Al synthesis regime) is found to have a good spatial consistency with one particular SDA isomer, and then yields a highly unusual framework structure.

At the same time, developments in electron diffraction methodology, both hardware and software, have reached a point where high-quality data can be collected routinely on a large number of crystals. As the XRPD data were insufficient for structure refinement, ED data were collected on eighteen crystals, four of which belonged to an SSZ-26 impurity phase, corroborating our conclusions from the molecular modelling studies that SSZ-26 forms equally well using all three isomers. The other fourteen crystals belonged to the SSZ-27 phase. Key to this study is the application of hierarchical cluster analysis that leads to an optimal selection of data sets for structure refinement. This, in turn, helps to obtain more reliable and precise atomic coordinates of the framework, but also to get a handle on the atomic displacements of the atoms. The fact that physically meaningful atomic displacement parameters can be obtained from submicron-sized crystals opens up new possibilities for studying atomic motion (e.g. internal vibrations) and disorder (static or dynamic). The framework structure that emerged for SSZ-27 is that of a small-pore zeolite with a one-dimensional channel system connecting heart-shaped cavities with smaller cavities through 8-rings. Through molecular modeling, we were able to establish that the SDA is located exclusively in the heart-shaped cavity. It is assumed that the other cavity contains water.

Experimental Section

Synthesis of the SDA. The [4.3.3.0] propellane-8,11-dione is prepared as described previously (see also Supporting Information).^[7] The initial mixture of tertiary amine isomers (Figure 1) is obtained by using the Leuckart reaction^[9] to convert the propellane dione to the dimethylamine terminus and then reacting the diamine with methyl iodide. 33 g of the propellane dione was mixed with 33 g of dimethylformamide and 27 g of formic acid (88%) and then heated in a closed system at 180°C for 16 hours. The product is collected and dissolved in 100 mL of water. The pH of the solution is raised to above 13 by addition of 50% NaOH solution. Then, 5 extractions are carried out with 100 mL diethyl ether each time to recover the free amines from the aqueous phase. The extracts are dried over sodium sulfate overnight, combined and stripped down to leave an oil of the mixed amine isomers. The mixture of amines is dissolved in 100 mL chloroform and 21 g of methyl iodide (a molar excess) are added dropwise with the solution in an ice bath. Solids will precipitate out as the diquatery ammonium product forms. The product can be collected after 2 days of stirring at room temperature by vacuum filtration and washing with diethyl ether. Isomers I or III can be collected by separate recrystallization approaches. For isomer I, 1.2 g of the mixed diquatery ammonium salts were heated up in 10 mL of 100% ethanol (78°C) until some of the material has dissolved. Then water is added dropwise while at that temperature. At the point where the solution becomes clear, 0.60 mL of water is added. Cooling to room temperature in a freezer will

RESEARCH ARTICLE

eventually produce a crystalline product. A similar recrystallization but using acetonitrile will produce isomer III instead. 1 g of the reaction mixture is mixed with 13 mL acetonitrile and brought to reflux. Then 1 mL water is added to eventually produce a clear solution. Crystals of isomer III are obtained upon cooling in the freezer. The NMR spectra of isomer I and III are shown in Figure 8 (and also in ref [4] where the crystal structures are given).

Zeolite synthesis. 1 mmole of the SDA (Isomer III) in the OH form, in 2.5 g of water, was added into a Teflon liner for a 23 mL Parr reactor. Next, 2 g of 1 N NaOH solution was added, followed by 1 g of water, and NaY Zeolite (CBV 100, Zeolyst International, SiO/Al₂O mole ratio=5.1) as the aluminum source. Finally, 0.60 g of CAB-O-SIL(R) M5 fumed silica (Cabot Corporation) was added. The liner was capped and placed within a Parr steel autoclave reactor. The autoclave was then fixed in a rotating Spit (43 rpm) within an oven and heated at 170°C for 7-10 days. The solid products were recovered, washed thoroughly with deionized water and dried.^[35]

Scanning electron microscopy. Scanning electron micrographs (Figure 2) were obtained using a JEOL JSM 6700F instrument.

Micropore. The porosity features of the zeolite were characterized with nitrogen adsorption at 77 K on a Micromeritics Tristar 3030 apparatus. The sample was degassed at 400°C in nitrogen flow overnight before adsorption analysis. The specific surface area was calculated according to the Brunauer-Emmett-Teller (BET) model in $p/p_0 = 0.05$ -0.2 pressure range. Micropore volume was obtained by the t -plot method, using adsorption data collected in $p/p_0 = 0.015$ -0.4 pressure range. The total pore volume of the sample is measured at $p/p_0 = 0.99$ pressure point. The micropore volume of SSZ-27 is 0.136 cm³/g, with a total pore volume of 0.229 cm³/g, and a surface area of 347 m²/g.

X-ray powder diffraction. Lab X-ray powder diffraction (XRPD) data were collected on a PANalytical X'pert Pro MRD diffractometer with Cu K α radiation (wavelength = 1.5418 Å; Figure 2). Synchrotron X-ray powder diffraction (XRPD) data were collected on as-synthesized samples of SSZ-27 (non-seeded) in 0.3 mm capillaries on the Materials Science beamline at the Swiss Light Source in Villigen, Switzerland^[36] using a wavelength of 0.70872 Å and a Mythen II detector.

Electron diffraction. ED data suitable for structure refinement were collected using the continuous rotation method^[37] on a JEOL JEM-2100 with a LaB₆ filament at 200 kV using the software *Instamatic*^[38] following the crystal tracking procedure described in ref. [12]. Samples were prepared by crushing a powder of SSZ-27 (non-seeded), which was then dispersed in ethanol, and ultrasonicated for 1 to 5 minutes. A drop of the dispersion was deposited onto a 3 mm copper TEM grid with continuous carbon film (CF400-Cu-UL from Electron Microscopy Sciences) or lacey carbon film (Cu150P from Okenshoji Co., Ltd), and the ethanol was allowed to evaporate. The raw ED data from all 18 crystals and processing files are available from <https://dx.doi.org/10.5281/zenodo.2633052>.

Molecular modeling. To gain more knowledge as to which isomer might best promote the formation of SSZ-27, molecular modeling on the location and the van der Waals (vdW) interaction energy for each of the three SDA isomers with the SSZ-27 framework were carried out using the Materials Studio software.^[39] The CVFF forcefield^[40] was selected for the calculation and the most stable locations of the molecules were obtained by simulated annealing. The host framework was assumed to be all silica, and the unit cell was fixed during the calculation. The best fit was achieved with isomer III (Figure 7), giving the interaction energy of -8.95 kJ/mol per T atom. The other two isomers provided a much poorer fit, the interaction energy was -3.66 kJ/mol per T atom for isomer I and -3.31 kJ/mol per T atom for isomer II. These results were then used to guide further syntheses of SSZ-27.

NMR. ¹³C solid state NMR experiments were performed using a Bruker DSX-500 spectrometer and a 4 mm Bruker MAS probe. Solid powders of isomers I and III and zeolite powders SSZ-26 and SSZ-27 were each packed into 4 mm rotors and spun at 8 kHz to record the ¹³C signal after a single pulse (direct polarization) or ¹H cross-polarization (CP). Typical rf power for the ¹³C channel was 62.5 kHz while that for the ¹H channel was adjusted to satisfy CP conditions under sample spinning or to perform high power decoupling. Isomers were dissolved into DDI water and ¹³C spectra of the solutions were collected under MAS conditions. All ¹³C spectra reported are referenced to TMS at 0 ppm. ¹H liquid phase NMR experiments were performed using a Bruker UltraShield™ 400 Plus and all spectra were recorded in D₂O. For the HF dissolution experiments, 100 mg of as-made zeolite was suspended in water and then HF was added to dissolve the zeolite framework. **Caution: Take all appropriate safety measures when working with HF.** Then the HF was neutralized with an excess of 1N NaOH. The water was evaporated under a stream of nitrogen and then the SDA was extracted from the remaining solids using D₂O for NMR analysis.

Acknowledgements

The authors thank Chevron Energy Technology Company for support and the continued interest in new zeolite materials from Dr. Robert Saxton and Dr. Georgie Scheuerman. We thank Dr. Ana Pinar and Dr. Antonio Cervellino for the powder diffraction measurements on the Materials Science Beamline at the SLS in Villigen, Switzerland and Dr. Kelvin Stone for help with measurements at the 2-1 Powder Diffraction Beamline at the SSRL in Stanford (CA), US. We thank Kaustav Chaudhuri for the SEM images. This work was supported by the Swiss National Science Foundation (award numbers 165282 & 177761). The electron diffraction experiments were supported by the Knut and Alice Wallenberg Foundation (3DEM-NATUR). The NMR facility at the California Institute of Technology was supported by the National Science Foundation (NSF) under Grant Number 9724240 and partially supported by the MRSEC Program of the NSF under Award Number DMR-520565.

Keywords: SSZ-27 • aluminosilicate zeolite • synthesis • electron diffraction • structure determination

- [1] S. I. Zones, *Micropor. Mesopor. Mat.* **2011**, *144*, 1–8.
- [2] F. Gao, J. H. Kwak, J. Szanyi, C. H. F. Peden, *Top. Catal.* **2013**, *56*, 1441–1459.
- [3] C. Baerlocher, L. B. McCusker, D. H. Olson, *Atlas of Zeolite Framework Types*, Elsevier, **2007**.
- [4] S. I. Zones, M. M. Olmstead, D. S. Santilli, *J. Am. Chem. Soc.* **1992**, *114*, 4195–4201.
- [5] S. I. Zones, *Microporous Mater.* **1994**, *2*, 281–287.
- [6] R. F. Lobo, M. Pan, I. Chan, H.-X. Li, R. C. Medrud, S. I. Zones, P. A. Crozier, M. E. Davis, *Science* **1993**, *262*, 1543–1546.
- [7] S. Bhanumati, P. Ashkenazi, S. Migdal, D. Ginsburg, *Helv. Chim. Acta* **1983**, *66*, 2703–2706.
- [8] G. Kubiak, J. M. Cook, U. Weiss, *J. Org. Chem.* **1984**, *49*, 561–564.
- [9] R. D. Bach, *J. Org. Chem.* **1968**, *33*, 1647–1649.
- [10] M. E. Davis, S. I. Zones, in *Synthesis of Porous Materials: Zeolites, Clays and Nanostructures*, Marcel Dekker, **1997**, pp. 1–34.
- [11] U. W. Arndt, A. J. Wonacott, *Rotation Method in Crystallography*, North-Holland Pub. Co., **1977**.
- [12] M. O. Cichocka, J. Ångström, B. Wang, X. Zou, S. Smeets, *J. Appl. Crystallogr.* **2018**, *51*, 1652–1661.

RESEARCH ARTICLE

- [13] W. Kabsch, *Acta Cryst. D* **2010**, *66*, 125–132.
- [14] G. S. Pawley, *J. Appl. Crystallogr.* **1981**, *14*, 357–361.
- [15] A. A. Coelho, *J. Appl. Crystallogr.* **2018**, *51*, 210–218.
- [16] R. W. Grosse-Kunstleve, L. B. McCusker, C. Baerlocher, *J. Appl. Crystallogr.* **1999**, *32*, 536–542.
- [17] S. Smeets, L. B. McCusker, C. Baerlocher, E. Mugnaioli, U. Kolb, *J. Appl. Crystallogr.* **2013**, *46*, 1017–1023.
- [18] G. M. Sheldrick, *Acta Cryst. A* **2015**, *71*, 3–8.
- [19] R. Giordano, R. M. F. Leal, G. P. Bourenkov, S. McSweeney, A. N. Popov, *Acta Cryst D* **2012**, *68*, 649–658.
- [20] B. Wang, X. Zou, S. Smeets, *IUCrJ* **2019**, *6*, <https://doi.org/10.1107/S2052252519007681>.
- [21] P. A. Karplus, K. Diederichs, *Science* **2012**, *336*, 1030–1033.
- [22] P. J. Bereciartua, Á. Cantín, A. Corma, J. L. Jordá, M. Palomino, F. Rey, S. Valencia, E. W. Corcoran, P. Kortunov, P. I. Ravikovitch, et al., *Science* **2017**, *358*, 1068–1071.
- [23] S. Zanardi, R. Millini, F. Frigerio, A. Belloni, G. Cruciani, G. Bellussi, A. Carati, C. Rizzo, E. Montanari, *Micropor. Mesopor. Mat.* **2011**, *143*, 6–13.
- [24] S. Smeets, D. Xie, L. B. McCusker, C. Baerlocher, S. I. Zones, J. A. Thompson, H. S. Lacheen, H.-M. Huang, *Chem. Mater.* **2014**, *26*, 3909–3913.
- [25] S. Smeets, L. B. McCusker, C. Baerlocher, S. Elomari, D. Xie, S. I. Zones, *J. Am. Chem. Soc.* **2016**, *138*, 7099–7106.
- [26] J. H. Kang, D. Xie, S. I. Zones, S. Smeets, L. B. McCusker, M. E. Davis, *Chem. Mater.* **2016**, *28*, 6250–6259.
- [27] M. O. Cichocka, Y. Lorgouilloux, S. Smeets, J. Su, W. Wan, P. Caullet, N. Bats, L. B. McCusker, J.-L. Paillaud, X. Zou, *Cryst. Growth Des.* **2018**, *18*, 2441–2451.
- [28] A. B. Pinar, L. Gómez-Hortigüela, L. B. McCusker, J. Pérez-Pariente, *Chem. Mater.* **2013**, *25*, 3654–3661.
- [29] K. Muraoka, W. Chaikittisilp, Y. Yanaba, T. Yoshikawa, T. Okubo, *Angew. Chem. Int. Ed.* **2018**, *57*, 3742–3746.
- [30] S. Smeets, L. B. McCusker, C. Baerlocher, D. Xie, C.-Y. Chen, S. I. Zones, *J. Am. Chem. Soc.* **2015**, *137*, 2015–2020.
- [31] S. Goel, S. I. Zones, E. Iglesia, *Chem. Mater.* **2015**, *27*, 2056–2066.
- [32] S. I. Zones, *Zeolite SSZ-13 and Its Method of Preparation*, **1985**, U.S. Patent 4,544,538 A.
- [33] P. Wagner, Y. Nakagawa, G. S. Lee, M. E. Davis, S. Elomari, R. C. Medrud, S. I. Zones, *J. Am. Chem. Soc.* **2000**, *122*, 263–273.
- [34] J. E. Schmidt, S. I. Zones, D. Xie, M. E. Davis, *Micropor. Mesopor. Mat.* **2014**, *200*, 132–139.
- [35] S. I. Zones, D. Xie, R. J. Saxton, *Method for Making Molecular Sieve SSZ-27*, **2017**, U.S. Patent 9,586,830 B2.
- [36] A. Bergamaschi, A. Cervellino, R. Dinapoli, F. Gozzo, B. Henrich, I. Johnson, P. Kraft, A. Mozzanica, B. Schmitt, X. Shi, *J. Synchrotron Radiat.* **2010**, *17*, 653–668.
- [37] I. Nederlof, E. van Genderen, Y.-W. Li, J. P. Abrahams, *Acta Cryst. D* **2013**, *69*, 1223–1230.
- [38] S. Smeets, B. Wang, M. O. Cichocka, J. Ångström, W. Wan, *Instamatic 1.0*, Zenodo, <https://dx.doi.org/10.5281/zenodo.1090388>, **2018**.
- [39] *Materials Studio 6.0*, Accelrys, Inc., San Diego, **2012**.
- [40] P. Dauber-Osguthorpe, V. A. Roberts, D. J. Osguthorpe, J. Wolff, M. Genest, A. T. Hagler, *Proteins: Struct., Funct., Bioinf.* **1988**, *4*, 31–47.


RESEARCH ARTICLE

Entry for the Table of Contents

Layout 1:

RESEARCH ARTICLE

An aluminosilicate zeolite containing heart-shaped cavities was synthesized. The isomer favouring its formation was identified using molecular modelling and NMR to optimize the synthesis conditions.

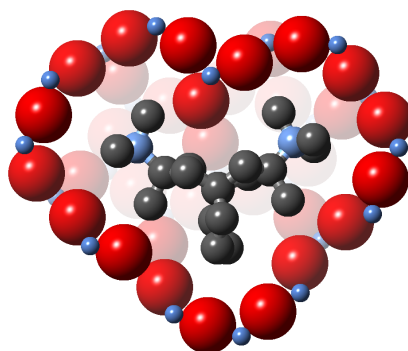

Stef Smeets, Stacey I. Zones,* Dan Xie, Lukáš Palatinus, Jesus Pascual, Son-Jong Hwang, Joel E. Schmidt, Lynne B. McCusker*

Page No. – Page No.

SSZ-27: a small pore zeolite with large heart-shaped cavities determined using multi-crystal electron diffraction