

Anisotropic Self-Diffusion of Guest Molecules in $\text{Zn}_2(\text{bdc})_2\text{dabco}$

Markus Wehring¹, Saeed Amirjalayer², Rochus Schmid², Frank Stallmach¹

¹Universität Leipzig, Fakultät für Physik und Geowissenschaften, Linnéstr. 5, 04103 Leipzig, Germany, E-Mail: wehring@physik.uni-leipzig.de

²Ruhr-University Bochum, Faculty of Chemistry and Biochemistry, Germany

1. Introduction

Non-invasive pulsed field gradient (PFG) NMR self-diffusion studies [1] are a powerful tool to elucidate host-guest interactions in MOFs [2,3]. Experimental (PFG) NMR self-diffusion studies on benzene adsorbed in the well-known Zinc-based metal organic framework MOF-5 show for relatively low loading (less than 20 molecules per unit cell) good agreement with data obtained by MD simulations [2,4,6]. Zinc-based MOFs provide good conditions for further studies of host-guest interactions based on the comparison of data obtained by experimental PFG NMR methods on one side and theoretical MD Simulation on the other. Therefore, zinc-based MOF $\text{Zn}_2(\text{bdc})_2\text{dabco}$ [6] is a promising candidate to investigate host-guest interactions in microporous materials. $\text{Zn}_2(\text{bdc})_2\text{dabco}$ consists of zincoxide-clusters in a paddlewheel configuration and two different linkers (Terephthalic acid, dabco). This build-up forms channels with a size of 7.5 Å, which are interlinked by windows of 4 Å. In a first step we measured self-diffusion coefficients of benzene and CO_2 via PFG NMR.

2. Results

PFG NMR experiments of benzene adsorbed in $\text{Zn}_2(\text{bdc})_2\text{dabco}$ (see Fig. 1) do not show a simple mono-exponential behaviour of the spin-echo attenuation curve. These are in the case of $\text{Zn}_2(\text{bdc})_2\text{dabco}$ most likely caused by an anisotropic diffusion behaviour due to the pore channels in the $\text{Zn}_2(\text{bdc})_2\text{dabco}$ crystals. The analysis of the spin-echo attenuation using a model of Callaghan et al. [7] for anisotropic self-diffusion yields self-diffusion coefficients of $1 \cdot 10^{-11} \text{ m}^2/\text{s}$ along the channels and $3 \cdot 10^{-13} \text{ m}^2/\text{s}$ perpendicular to the channels.

Self-diffusion studies on CO_2 adsorbed in $\text{Zn}_2(\text{bdc})_2\text{dabco}$ show a strictly mono-exponential behaviour of the spin-echo attenuation curve. The corresponding self-diffusion coefficient is $6 \cdot 10^{-9} \text{ m}^2/\text{s}$.

The different diffusion behaviour of the two species of guest molecules may be attributed to the different hydrodynamic radii of benzene and CO_2 . The smaller CO_2

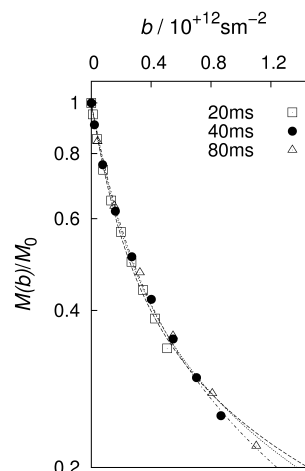


Fig. 1: Spin-echo attenuation curve of benzene in $\text{Zn}_2(\text{bdc})_2\text{dabco}$ for 20, 40 and 80 ms Diffusion time.

molecules are able to pass the windows between the channels without obstructions, but the benzene molecules are restricted during a jump from one channel to the other.

The next step will be the implementation of MD simulations of benzene and CO₂ in Zn₂(bdc)₂dabco to verify the conclusions of the experimental (PFG) NMR studies.

References

- [1] F. Stallmach, P. Galvosas, *Annu. Rep. NMR Spectrosc.*, 61 (2007) 51-131
- [2] S. Hertel, M. Wehring, S. Amirjalayer, M. Gratz, J. Lincke, H. Krautscheid, R. Schmid, F. Stallmach, *European Physical Journal -- Applied Physics*. in press.
- [3] M. Wehring, J. Gascon, D. Dubbeldam, F. Kapteijn, R. Q. Snurr, F. Stallmach, *J. Phys. Chem. C*, 114 (2010) 10527-10534
- [4] F. Stallmach, S. Gröger, V. Künzel, J. Kärger, O. M. Yaghi, M. Hesse, U. Müller, *Angew. Chem.-Int. Edit.*, 45 (2006) 2123-2126
- [5] S. Amirjalayer, M. Tafipolsky, R. Schmid, *Angew. Chem.-Int. Edit.*, 46 (2007) 463-466
- [6] D. N. Dybtsev, H. Chun, K. Kim, *Angew. Chem. Int. Ed.*, 43 (2004) 5033-5036
- [7] P. T. Callaghan, K. W. Jolley, J. Lelievre, *Biophysical Journal*, Biophysical Society, 28 (1979) 133-141