

## Phase stability and stress evolution of nano-multilayered coatings upon thermal treatment

**C. Cancellieri\***, E. Klyatskina, M. Chiodi, V. Araullo-Peters, J. Janczak-Rusch,  
L.P.H. Jeurgens

Empa, Swiss Federal Laboratories for Materials Science and Technology, Überlandstrasse 129, 8600  
Dübendorf, Switzerland

\*claudia.cancellieri@empa.ch

The functionality, reliability and service lifetime of nano-multilayered (NML) devices and components are largely affected by the stress evolution during fabrication, processing and operation. Hence a comprehensive experimental assessment of their structural integrity, including stress state evolution, during thermal loading is a crucial step to evaluate their applicability. This contribution addresses recent advances in the experimental investigation of the phase stability, microstructural integrity and stress evolution of metal/metal (Cu/W) [1] and metal/ceramic (Ag/AlN, Ag60wt.%Cu40at%/AlN, AgGe10at% /AlN) NML coatings during heating by advanced in-situ diffraction methods in combination with XPS, SEM and TEM analysis: see Fig.1. Such NML systems, as prepared by conventional magnetron sputtering, are envisaged as novel nano-structured brazing filler materials for advanced joining applications [2].

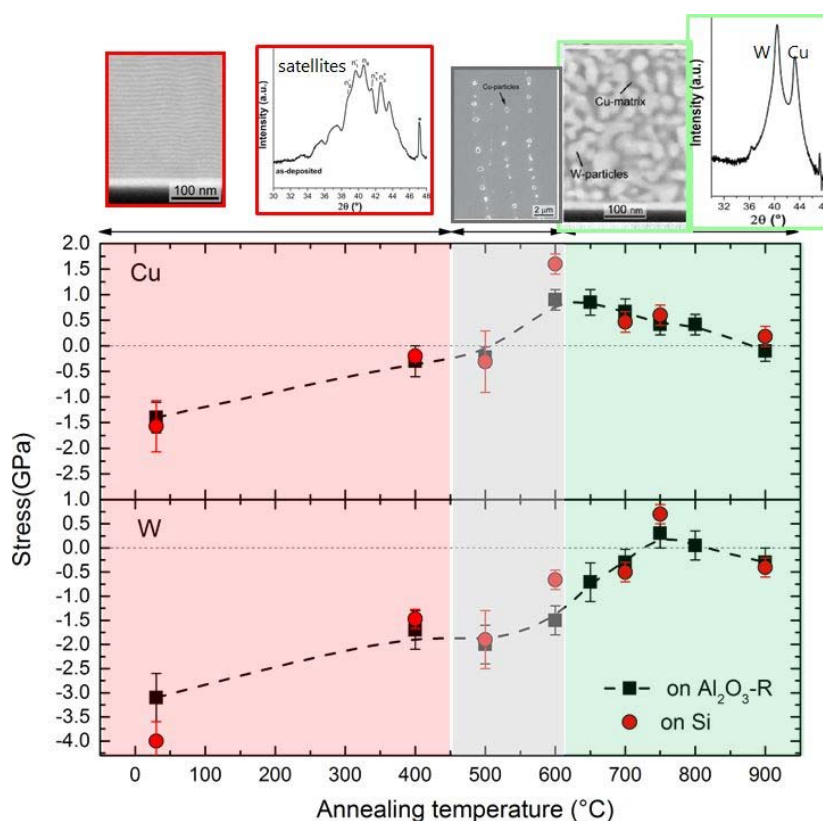


Figure 2: Stress evolution of Cu, W layers combined with SEM morphologic analysis

It is shown that the Cu/W NMLs gradually transform from a nano-laminated into a nano-composite structure upon heating at  $T > 750^{\circ}\text{C}$ , as accompanied by a complete relaxation of the compressive growth stresses in the confined Cu and W nanolayers. On the contrary, fast heating of the Ag/AlN NMLs in air invokes massive mass transport of Ag from the NML interior to the coating surface at temperatures as low as  $200^{\circ}\text{C}$  (i.e. much below the Ag bulk melting point), as accompanied by a fast relaxation of thermally-induced compressive stresses [3]. The crucial role of the processing atmosphere and of co-alloying elements like Cu and Ge on the phase stability and compressive/tensile stress determination of the Ag-based NMLs is rationalized.

### **Acknowledgment**

The authors acknowledge the financial support of FP7-PEOPLE-2013-IRSES Project EXMONAN

### **References**

- [1] C. Cancellieri, F. Moszner, M. Chiodi; S. Yoon, J. Janczak-Rusch, L.P.H. Jeurgens, *The effect of thermal treatment on the stress state and evolving microstructure of Cu/W nanomultilayers*, J. Appl. Phys. **120**, 195107 (2016).
- [2] F. Moszner, C. Cancellieri, C. Becker, M. Chiodi, J. Janczak-Rusch, L.P.H. Jeurgens, *Nano-structured Cu/W brazing fillers for advanced joining applications*, J. of Mater. Science and Engineering B **6** (9-10) 226-230 (2016).
- [3] M. Chiodi, C. Cancellieri, F. Moszner, M. Andrzejczuk, J. Janczak-Ruscha and L.P. H. Jeurgens, *Massive Ag migration through metal/ceramic nano-multilayers: an interplay between temperature, stress-relaxation and oxygen-enhanced mass transport*, J. Mater. Chem. C **4**, 4927 (2016).