

Microwave assisted synthesis of polynuclear Ni(II) complexes

Lidia Rosado Piquer,^{a,b} E. Carolina Sañudo^{a,b*}

Published in 2019, please cite as: Rosado Piquer, L.; Sañudo, E. C. Microwave Assisted Synthesis of Polynuclear Ni(II) Complexes. *Polyhedron* **2019**, *169*, 195–201

DOI: <https://doi.org/10.1016/j.poly.2019.05.011>

^a *Secció de Química Inorgànica, Departament de Química Inorgànica i orgànica, Facultat de Química, Universitat de Barcelona. C/Martí i Franqués 1-11, Barcelona 08028 Spain;* ^b *Institut de Nanociència i Nanotecnologia (IN2UB), Universitat de Barcelona. C/Martí i Franqués 1-11, Barcelona 08028 Spain*

Abstract

In this paper we test a solvent-free microwave assisted synthesis method with a known Ni₇ complex, [Ni₇(chp)₁₂(OH)₂(CH₃OH)₆] (**2**), and then extended the method to a more complex ligand system. We prepare two new trinuclear Ni(II) complexes ([Ni₃(chp)₄(tBuSALOH)₂(MeOH)₅] (**4**) and [Ni₃(chp)₄(iPrSALOH)₂(MeOH)₆] (**5**)) and report here their characterization and magnetic properties.

Introduction

The synthesis of high nuclearity coordination complexes is an area where design and serendipity struggle. Serendipitous self-assembly^{1,2} is at the heart of the mechanism of formation of most high nuclearity transition metal complexes. It is often impossible to predict the outcome of a reaction and single-crystal X-ray characterization is key in order to ascertain the nature of the product. In solution it is often the case that several species may form and one or more than one might precipitate or crystallize. There are few examples when complex molecules co-crystallize like the iron clusters reported by Aromí et al, where a dimer of Fe₄ butterfly type complexes co-crystallizes with a dimer of Fe₃ complexes. Carefully controlling the system allows the crystallization of either the Fe₄ butterfly dimer or the dimer of Fe₃ complexes.³

In a world where waste management is very important and the chemical industries are subject to strict waste management policies (for EU: <http://ec.europa.eu/environment/waste/index.htm>), synthetic methods that reduce waste generation should be key. In particular this is even more important for the possible technological application of coordination complexes, in the so-called molecular spintronics approach to information storage and processing.⁴⁻⁶ Syntheses without solvents, in a melt state⁷⁻¹¹ or forcing sublimation of a species¹² have been a good route to high nuclearity complexes. Of particular relevance to spintronics is the archetypical mononuclear single molecule magnet (SMM) TbPc_2 ,¹³ synthesized by conventional heating over long periods of time and that often produce mixtures of products and require tedious purification methods.^{14,15} In general, for these synthesis yields are usually poor and reproducibility might be problematic in some cases. On the other hand, these kind of reactions are effective in providing access to high nuclearity complexes. Single ion anisotropy for Ni(II) in an axial coordination environment can be large.^{16,17} In some cases, this might lead to slow relaxation of the magnetization and SMM behavior. The first Ni(II) SMM was reported in 1994, it was a dodecanuclear species of formula $[\text{Ni}_{12}(\text{chp})_{12}(\text{O}_2\text{CMe})_{12}(\text{thf})_6(\text{H}_2\text{O})_6]$.¹⁸ The molecule has a large spin ground state ($S=12$) and small axial magnetic anisotropy ($D=-0.05 \text{ cm}^{-1}$) setting the standard for Ni(II) SMMs, which are usually characterized by very low blocking temperatures.^{19,20}

In order to tackle the lack of reproducibility observed in the particular case of a Ni_7 complex reported by Winpenny^{8,21} we decided to undertake such 'melt' reactions in the microwave reactor. There is already a report of TbPc_2 ²² prepared using microwaves to improve yield and avoid mixtures. Microwave assisted synthesis has been used with quite a lot of success to prepare high-nuclearity complexes by Brechin and co-workers^{23,24} and by us,²⁵⁻²⁸ among others.²⁹⁻³¹

In this paper we report the use of solvent free microwave assisted synthesis to prepare Ni(II) complexes with a simple ligand system.

Experimental

All solvents and reagents were acquired from commercial sources and used as received. Microwave assisted reactions were performed in a CEM Discover reactor. chp is

deprotonated 6-chloro-2-hydroxypyridine (C_5H_3ClNO), tBuSALOH is monodeprotonated 3,5-di-tert-butylsalicylic acid ($tBuSALOH_2$, $C_{15}H_{21}O_3$) and iPrSALOH is monodeprotonated 3,5-di-isopropyl-salicylic acid ($iPrSALOH_2$, $C_{13}H_{17}O_3$).

[Ni(OH)₂] \cdot xH₂O (1): NiCl₂ \cdot 6H₂O (2.59 g, 10.88 mmol) and NaOH are mixed in 50 ml of water. The reaction is stirred for 10 minutes. A green precipitate is filtered and dried under vacuum for at least 8 hours. Yield is quantitative. IR (KBr, cm⁻¹): 3488 (s, broad), 1645 (m), 1462 (m), 1369 (m), 655 (s, broad), 416 (s).

[Ni₇(chp)₁₂(OH)₂(CH₃OH)₆] (2) (Ni₇)

Fresh **1** (0.4 g, 4.3 mmol) and chp (0.562 g, 4.3 mmol) are mixed in a microwave reactor cavity. A microwave pulse of 150 W is applied and the reaction kept at 150°C for 10 minutes. The solid obtained is dried in vacuum for 2 hours. The dried solid is extracted with 10 mL of MeOH/MeCN (1:1 en volum) while heating is applied. The suspension is filtered while hot and the solid discarded. Slow evaporation of the liquor results in green crystals of complex **2** after circa. 15 days.

Yield: 8% (52 mg). Elemental analyses calculated for C₆₆H₆₂Cl₁₂N₁₂Ni₇O₂₀: C, 36.54%; N, 7.75%; H, 2.88%. Experimental elemental analyses: C, 35.82%; N, 7.76%; H, 2.68%. IR (KBr, cm⁻¹): 3092 (m, broad), 2791 (m, broad), 1596 (s), 1539 (s), 1447 (s), 1341 (s), 1248 (m), 1172 (m), 1002 (s), 937 (m), 788 (s), 731 (m), 701 (m).

[Ni(H₂O)₂(chp)₂] (3) (Ni₁)

Fresh **1** (1.1 g, 8.4 mmol) and chp (1.088 g, 8.4 mmol) are mixed in a Schlenck flask and heated under N₂ at 130°C for 2 hours. The green solid is extracted with MeCN/MeOH (1:1) while heating is applied. The suspension is filtered while hot and the solid discarded. Slow evaporation of the liquor results in deep green crystals of complex **3** after circa. 25 days.

Yield <5% (55 mg). Elemental analyses calculated for C₁₀H₁₀Cl₂N₂NiO₄: C, 34.3%; N, 8.0%; H, 2.8%. Experimental elemental analyses: C, 34.6%; N, 7.9%; H, 2.8%. IR (KBr, cm⁻¹): 3214 (s, broad), 1602 (s), 1537 (s), 1453 (s), 1345 (s), 1241 (m), 1167 (s), 1003 (s), 936 (s), 856 (m), 789 (s), 734 (s), 702 (m), 667 (m), 608 (m).

[Ni₃(chp)₄(tBuSALOH)₂(MeOH)₅] (4) (Ni₃tBu)

Fresh **1** (0.203 g, 2.176 mmol), chp (0.281 g, 2.176 mmol) and tBuSALOH₂ (181.7 mg, 0.726 mmol) are mixed in the microwave reactor cavity. A microwave pulse of 150 W is applied and the reaction kept at 170°C for 10 minutes. The solid is extracted with 10 mL of MeOH/MeCN (1:1 volume) while heating is applied. The suspension is filtered while hot and the solid discarded. Slow evaporation of the liquor results in green crystals of complex **4** after circa. 3 days.

Yield: 44% (0.214 g). Calculated elemental analyses for C₅₅H₇₄Cl₄N₄Ni₃O₁₅: C, 49.0%; N, 4.2%; H, 5.6%. Experimental elemental analyses: C, 49.1%; N, 4.2%; H, 5.6%. IR (KBr, cm⁻¹): 3339 (m, broad), 2956 (s), 2522 (m, broad), 1596 (s), 1539 (s), 1435 (s), 1386 (s), 1331 (s), 1292 (s), 1244 (s), 1219 (m), 1202 (m), 1170 (s), 1151 (m), 1023 (s), 998 (s), 923 (s), 814 (m), 784 (s), 748 (m), 727 (m), 704 (m).

[Ni₃(chp)₄(iPrSALOH)₂(MeOH)₆] (5) (Ni₃iPr)

Fresh **1** (0.203 g, 2.176 mmol), chp (0.281 g, 2.176 mmol) and iPrSALOH₂ (161.38 mg, 0.726 mmol) are mixed in the microwave reactor cavity. A microwave pulse of 150 W is applied and the reaction kept at 150°C for 10 minutes. The solid is extracted with 10 mL of MeOH/MeCN (1:1 volume) while heating is applied. The suspension is filtered while hot and the solid discarded. Slow evaporation of the liquor results in green crystals of complex **5** after circa. 4 days.

Yield: 27% (0.130 g). Calculated elemental analyses for C₅₂H₇₀Cl₄N₄Ni₃O₁₆: C, 47.1%; N, 4.2%; H, 5.3%. Experimental elemental analyses: C, 47.1%; N, 4.2%; H, 5.0%. IR (KBr, cm⁻¹): 3332 (m, broad), 2956 (s), 2522 (m, broad), 1596 (s), 1538 (s), 1437 (s), 1392 (s), 1330 (s), 1243 (s), 1169 (s), 1072 (m), 1022 (s), 998 (s), 923 (s), 872 (w), 813 (s), 785 (s), 753 (m), 704 (m), 638 (w), 617 (m), 478 (m), 424 (m).

X-Ray diffraction data for complexes **3**, **4**, **5** were collected on a Bruker APEXII SMART diffractometer using Molybdenum K α microfocus ($\lambda=0.71073\text{\AA}$) radiation source. Single crystal diffraction data for **2** were collected at the Advanced Light Source station, at Berkeley (USA) (T=173 K, $\lambda=0.71073\text{\AA}$). The structures were solved by Patterson or intrinsic phasing methods (SHELXS2013 and SHELXT) and refined on F² (SHELXL-2013). Hydrogen atoms were included on calculated positions, riding on their carrier atoms.

Elemental analyses (CHN) were performed at Servei de Microanàlisi in CSIC (Consell Superior d'Investigacions Científiques). Infrared spectra were collected on KBr pellets on an AVATAR 330 FT-IR at Departament de Química Inorgànica, Universitat de Barcelona.

Magnetic measurements were performed at the Unitat de Mesures Magnètiques of the Universitat de Barcelona on a Quantum Design SQUID MPMS-XL magnetometer equipped with a 5 T magnet. Diamagnetic corrections for the sample holder and for the sample using Pascal's constants were applied. Hysteresis measurements were performed with an array of micro-SQUIDs. This magnetometer works in the temperature range of 0.04 to 5 K and in fields up to 1.4 T with sweeping rates as high as 0.28 T s⁻¹.

Results

We reproduced the synthesis reported by Brechin and Winpenny⁸ for complex **2**, [Ni₇(chp)₁₂(OH)₂(CH₃OH)₆], with various results: complex **2**:Ni₇ was obtained with very low yield and often contaminated by a Ni(II) monomer that was identified as complex **3**, [Ni(H₂O)₂(chp)₂], a monomer of Ni(II) with two chp ligands and two aqua ligands. The starting material for this reaction was nickel hydroxide, freshly prepared. In fact, an infra-red analysis of the discarded precipitate showed broad intense bands in the 400 and 600 cm⁻¹ region, in accord with metal oxides. Taking the reaction to the microwave cavity resulted in a green paste that was then treated with MeOH/MeCN and crystals of complex **2**:Ni₇ were obtained in a reproducible manner. The choice of the chp ligand is not trivial, since its easily attainable melting point makes it ideal for this kind of synthesis: the melted ligand or ligands are the medium where diffusion happens and reaction takes place. Figure 1 shows the structure of the ligands and their melting points. Introduction of a carboxylato ligand, in the form of the corresponding acid in the reaction medium, was checked by using two derivatives of salicylic acid, with tert-butyl and iso-propyl substituents. These carboxylic acids have easily attainable melting points and are good ligands for high-nuclearity complexes. The treatment of the solid obtained from the microwave assisted reaction resulted in green solutions and some solid that did not dissolve. This solid was discarded. Slow evaporation of the green solutions gave nice single crystals of [Ni₃(chp)₄(tBuSALOH)₂(MeOH)₅] (**4**) and [Ni₃(chp)₄(iPrSALOH)₂(MeOH)₆] (**5**). The two species differ in the number of coordinated

MeOH molecules and in the coordination of the chp ligands (vide infra). The reactions were very reproducible and no other byproducts were obtained. Microwave assisted synthesis has proven a fast reaction method that allows access to high-nuclearity species in a reproducible manner.

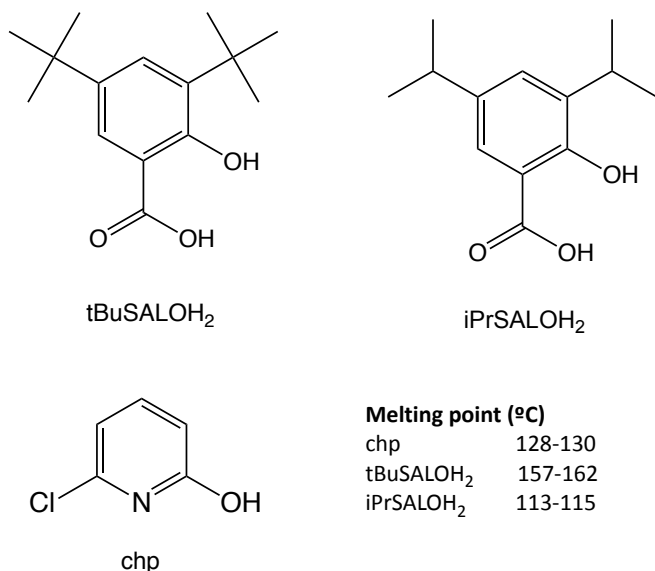


Figure 1. Structure of the ligands and their melting points.


Description of crystal structures

Table 1 shows the data collection and crystallographic parameters for **2**: Ni₇, **3**: Ni₁, **4**: Ni₃tBu and **5**: Ni₃iPr.

Table 1. Data collection and crystallographic parameters for complexes **2**: Ni₇, **3**: Ni₁, **4**: Ni₃tBu and **5**: Ni₃iPr.

	2	3	4	5
	Ni ₇	Ni ₁	Ni ₃ tBu	Ni ₃ iPr
Formula	C ₆₆ H ₆₂ Cl ₁₂ N ₁₂ Ni ₇ O ₂₀	C ₁₀ H ₆ Cl ₂ N ₂ NiO ₄	C ₅₅ H ₇₄ Cl ₄ N ₄ Ni ₃ O ₁₅	C ₅₂ H ₇₀ Cl ₄ N ₄ Ni ₃ O ₁₆
MW	2179.64	347.78	1344.20	1325.05
Crystal system	monoclinic	monoclinic	triclinic	triclinic
Space group	P2 ₁ /n	P2 ₁ /c	P-1	P-1
a/Å	12.4654 (13)	11.7180(13)	11.4853(2)	11.458(4)
b/Å	19.813(2)	5.3087(6)	12.9875(3)	11.463(3)

c/Å	17.5510(19)	10.6786(11)	22.2963(5)	12.721(4)
α/°	90	90	75.6450(10)	91.78(2)
β/°	106.4440(14)	106.874(7)	89.8420(10)	109.585(18)
γ/°	90	90	88.5890(10)	91.551(17)
Volume/Å³	4157.3(8)	635.69(12)	3221.00(12)	1572.0(8)
Z	2	2	2	1
Reflections	45744	5860	64470	14033
μ/mm⁻¹	2.011	1.955	1.097	1.124
R(int)	0.0439	0.0430	0.0410	0.0726
R indexes	R ₁ = 0.0367	R ₁ = 0.0372	R ₁ = 0.0447	R ₁ = 0.0793 wR ₂ =
[I≥2σ (I)]	wR ₂ = 0.1021	wR ₂ = 0.1104	wR ₂ = 0.1099	0.2159
R indexes (all data)	R ₁ = 0.0398	R ₁ = 0.0494	R ₁ = 0.0872	R ₁ = 0.1271 wR ₂ =
	wR ₂ = 0.1041	wR ₂ = 0.1229	wR ₂ = 0.1277	0.2523
T/K	173	100	293	293

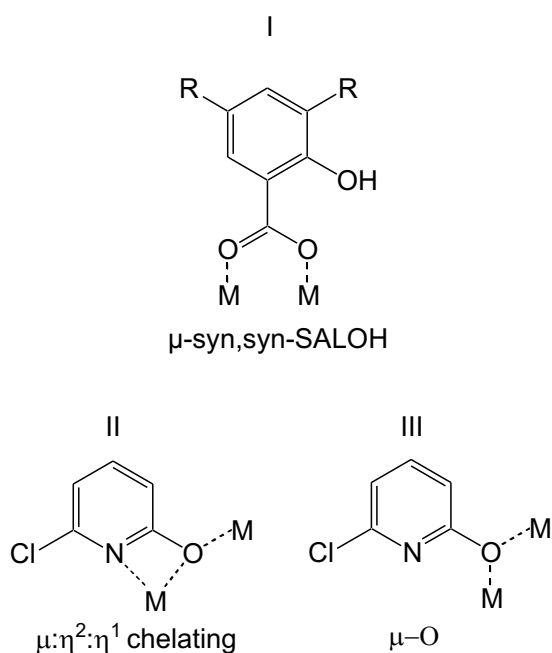

Scheme 1. Binding modes of the chp and carboxylato ligands.

As mentioned in the synthesis section, complex **2**:Ni₇ was usually obtained contaminated with a Ni(II) monomer, complex **3**:Ni₁, or unreacted oxides. For the microwave assisted reactions we studied several crystals from each batch both at our in-house diffractometer and at Berkeley ALS synchrotron radiation source. In all cases

the unit cell and the structure obtained were those of complex **2**:Ni₇. The structure of complex **2**:Ni₇ is shown in Figure 2. This is a known structure previously reported by Winpenny et al⁸, so it will not be described in detail here. All Ni are Ni(II) in complex **2**:Ni₇, hexacoordinated in a distorted octahedral fashion. The core can be described as two distorted tetrahedral Ni₄ units sharing one vertex, as shown in Figure 2. The Ni₃ units are bridged by OH⁻ groups, the protonation level is established calculating the bond valence sum (BVS).³² The same reaction performed in normal bench-top conditions results in mixtures of complex **2**:Ni₇ and complex **3**:Ni₁. Complex **3**:Ni₁ is a mononuclear Ni(II) complex with two chelating chp ligands and two coordinated water molecules that are involved in hydrogen bonding with the terminal oxygen atoms (

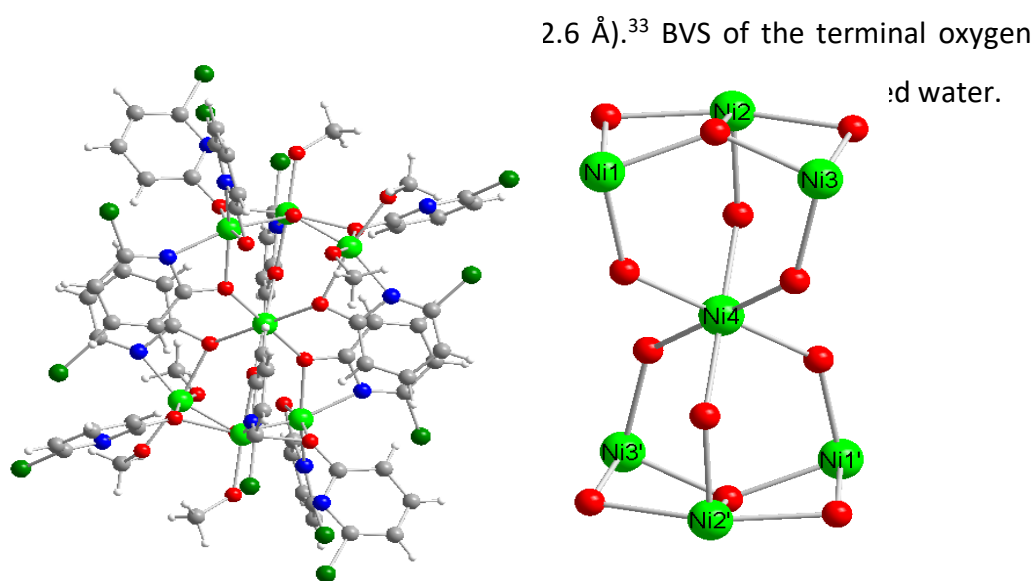


Figure 2. Crystal structure and core of complex **2**:Ni₇.

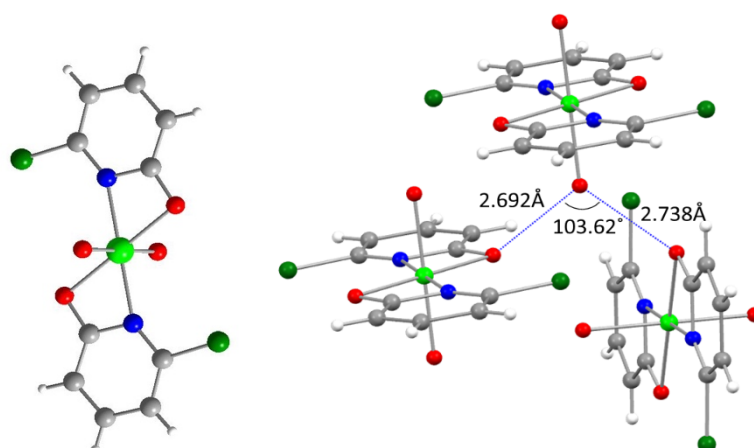


Figure 3. Crystal structure and packing of complex **3**:Ni₁, showing the intermolecular interaction via H-bonding of one chp oxygen and the coordinated water.

When a carboxylic acid is introduced in the reaction mixture, a linear Ni₃ complex is formed. The coordination modes of chp found in complexes **4**: Ni₃tBu and **5**: Ni₃iPr are found in Scheme 1. They are the same as those found in complex **2**. Complexes **4**: Ni₃tBu and **5** consist of a linear arrangement of three Ni(II) ions, as shown in Figure 4. All metal centers are hexacoordinated in a distorted octahedral fashion. Each pair of Ni(II) ions are bridged by one *syn,syn*-carboxylato groups from tBuSALOH in **4**: Ni₃tBu and iPrSALOH in **5**: Ni₃iPr. The hydroxyl group of the ligand does not participate in metal bonding in either **4**: Ni₃tBu or **5**: Ni₃iPr. There are four chp ligands in **4**: Ni₃tBu, three of them using the oxygen atom to bridge two Ni(II) ions in coordination mode III (Scheme 1), and one in coordination mode II (Scheme 1) that uses the pyridine nitrogen to chelate one Ni(II) ion. In complex **5**: Ni₃iPr the four chp ligands are in the same binding mode: bridging two Ni(II) ions using the oxygen atom, coordination mode III (Scheme 1). The two external Ni(II) ions in the Ni₃ unit complete their coordination sphere with coordinated MeOH. For complex **4**: Ni₃tBu the two Ni(II) Ni(2) and Ni(3) are crystallographically distinct, Ni(2) coordinates to the chelating chp (coordination mode II in Scheme 1) and to two MeOH ligands while Ni(3) completes the octahedral coordination with three MeOH ligands. For complex **5**: Ni₃iPr, the central Ni(II) ion Ni(1) is sitting in a crystallographic inversion center and the two terminal Ni(II) ions are Ni(2) and Ni(2'), related by symmetry. Both Ni(2) and Ni(2') complete their coordination sphere with three MeOH ligands.

Table 2. Bond Valence Sum (BVS) for complexes **2-5**

	2: Ni₇	3: Ni₁	4: Ni₃tBu	5: Ni₃iPr
Ni1	1.93	1.95	2.03	2.03
Ni2	2.00		2.10	2.04
Ni3	2.00		2.06	
Ni4	2.06			

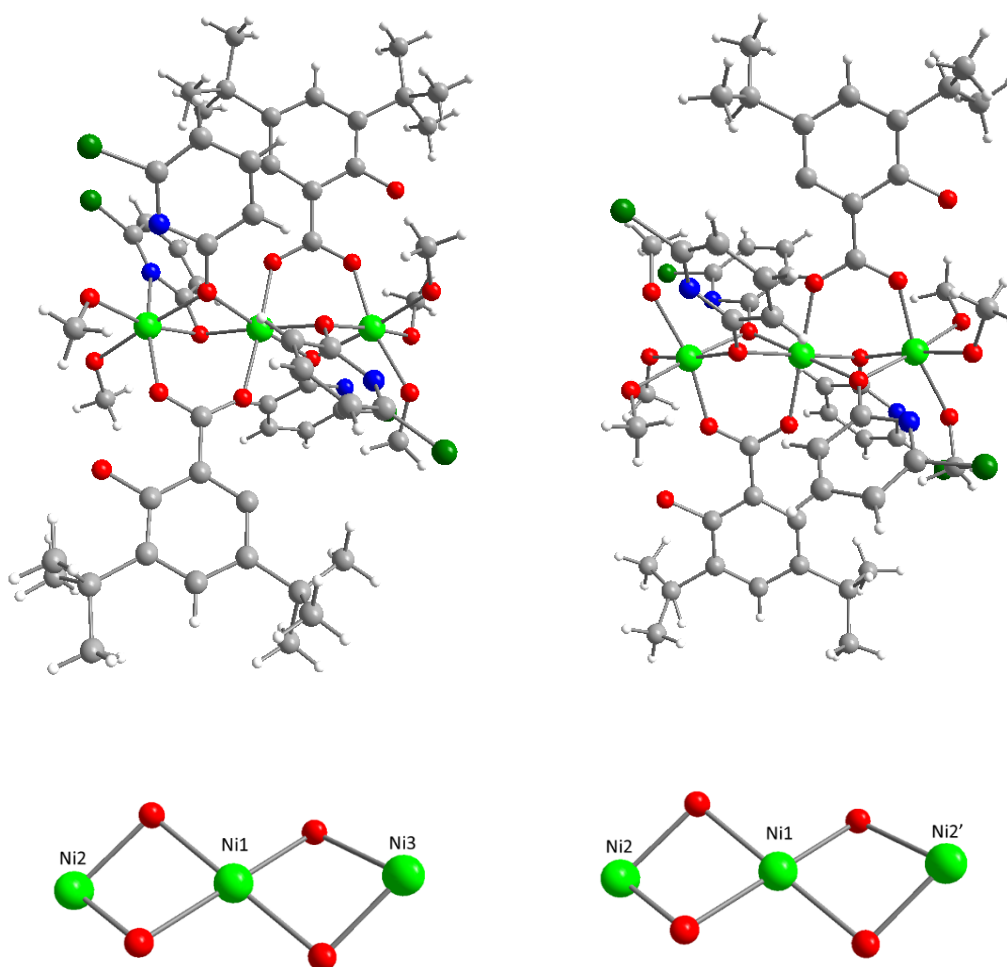


Figure 4. Crystal structures of **4**: Ni₃tBu (left) and **5**: Ni₃iPr (right).

Magnetic properties

The magnetic susceptibility of complex **2**: Ni₇ was measured at two different applied fields (300 and 5000 Oe) and is shown in Figure 5 as χT vs. T plot. Between 2-300 K data were collected with an applied field of 5000 Oe and below 25 K data were collected with an applied field of 300 Oe. The susceptibility is clearly field dependent. The χT product at 300 K has a value of 8.47 cm³ K mol⁻¹, in agreement for seven isolated Ni(II) ions with $S = 1$ and $g = 2.2$. The susceptibility decreases steadily down to 30 K, as expected for dominant antiferromagnetic interactions. There is a small plateau at a χT product value

of $4.5 \text{ cm}^3 \text{ K mol}^{-1}$ and then the χT product drops sharply to a non-zero value of $2 \text{ cm}^3 \text{ K mol}^{-1}$.

The magnetization vs. field plot at 2 K is shown in Figure 6. Clearly, saturation is not reached even at the highest field of 5 T. The shape of the curve is typical of Zeeman population of a large number of excited states with larger S than the ground state.

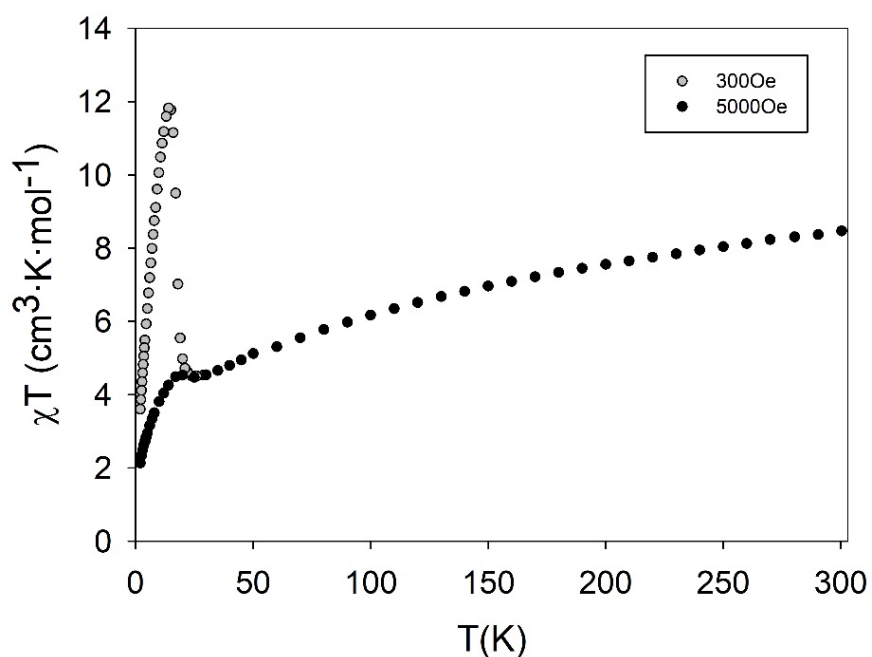


Figure 5. Magnetic susceptibility for complex **2**:Ni₇ shown as a χT vs. T plot at the indicated magnetic fields.

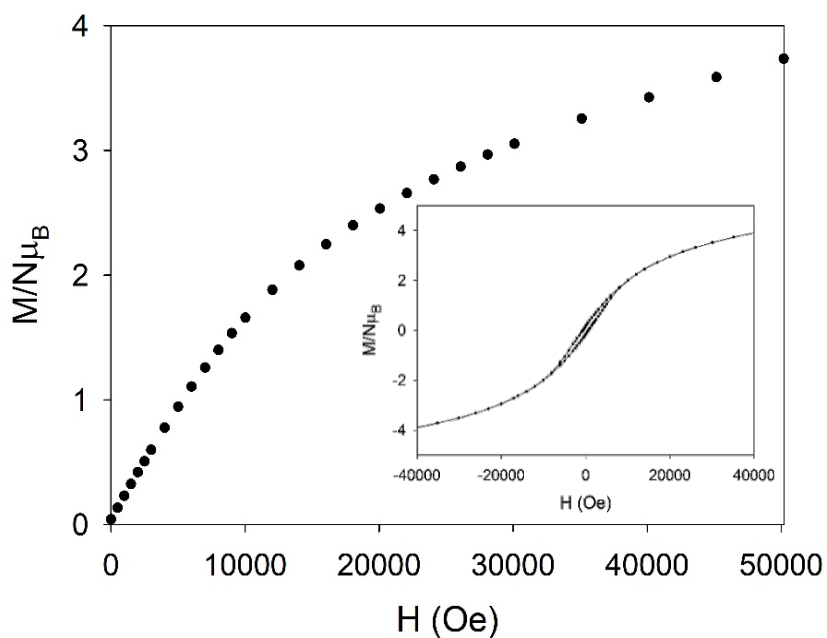


Figure 6. Magnetization vs field plot at 2 K for complex **2**: Ni₇. The inset shows a hysteresis loop at the same temperature for complex **2**: Ni₇.

The disposition of the seven Ni(II) ions in complex **2**: Ni₇ as two tetrahedra sharing a vertex results in a spin frustrated system if all pairwise magnetic exchange interactions are antiferromagnetic as expected for the observed Ni-OH-Ni angles (98.92°, 108.89° and 130.12°) and the Ni-O-Ni angles (133.80°, 134.90° and 136.14°). Garlatti *et al.* studied the magnetic properties of this complex and used a simple model with two antiferromagnetic exchange constants. This results in the ground state $S = 1$ that includes nine distinct multiplets, for a total degeneracy of 27, resulting in a spin manifold.²¹ We observed a narrow hysteresis of the magnetization vs. field for a pure, crushed, crystalline sample of complex **2**: Ni₇ at 2 K (Figure 6) and out-of-phase ac magnetic susceptibility frequency dependent peaks (Figure 7).

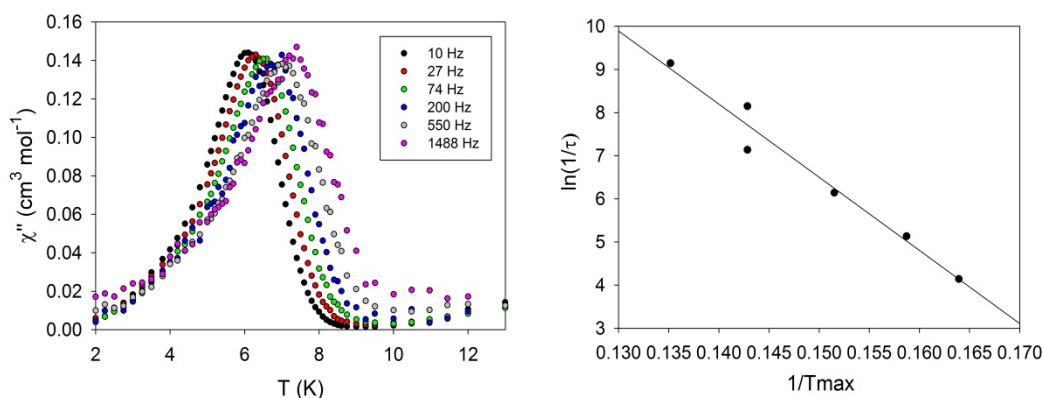


Figure 7. Out-of-phase ac magnetic susceptibility for complex **2**: Ni₇ at the indicated frequencies and Arrhenius plot for the ac data.

Clearly, the out-of-phase signal is not the typical of a transition metal SMM like Mn₁₂.^{34,35} When the relaxation process is studied using the Arrhenius equation, $\tau = \tau_0 e^{-U_{eff}/kT}$

the values obtained are $U_{\text{eff}} = 169.6 \text{ K}$ and $\tau_0 = 1.3 \cdot 10^{-14} \text{ s}^{-1}$. The value for the pre-exponential factor is not that of an SMM and it is better suited for the relaxation of the free electron. Similar values are found for spin-glasses, where frustration and disorder play a key role.^{36,37} Similar systems with Ni(II) that show AC peaks due to spin frustration have been reported for Ni₁₀ supertetrahedral complexes.^{38,39} The Mydosh parameter^{37,40} was calculated. Using the formula $F = (\Delta T_M / T_M) / (\Delta \log f)$ a value of $F = 0.07$ is obtained. This value is as expected for a spin glass or a cluster glass, but it is too small for an SMM, thus complex **2**: Ni₇ is not an SMM. Spin glasses are systems for which spins freeze at random orientations below certain temperature, cluster glasses are systems where instead of single spins, clusters of spins follow this random freezing. The key factors are disorder and frustration, complex **2**: Ni₇ clearly complies the frustration but also, it lacks important intermolecular interactions that can lead to long range ordering of the Ni₇ molecules. In order to rule out Ni(OH)₂ impurities in the crushed crystalline sample of **2**: Ni₇ we studied the magnetic properties of the prepared hydroxide. An out-of-phase ac peak characteristic of Ni(OH)₂ appears at 17 K and shows no frequency dependence. Several samples of **2**: Ni₇ that were obtained with higher yields contained some precipitate along with the crystals, large amounts of oxide, and that was reflected in two ac peaks, one centered at 5 K for **2**: Ni₇ with strong frequency dependence and one at 17 K for the Ni(OH)₂ impurity.

Magnetic susceptibility data for **4**: Ni₃tBu and **5**: Ni₃iPr are shown in Figure 8 as χT vs T plots. The χT product values at 300 K are $4.19 \text{ cm}^3 \text{ K mol}^{-1}$ for **4**: Ni₃tBu and $2.0 \text{ cm}^3 \text{ K mol}^{-1}$ for **5**: Ni₃iPr. Both values are in agreement with the expected value for three independent Ni(II) ions with $S = 1$ and $g = 2.3$. Maxima are observed for both complexes below 25 K, due to Zeeman effects and magnetic anisotropy. Ferromagnetic coupling is to be expected in these Ni₃ linear species, each pair of Ni(II) ions are bridged by one carboxylato group (mode I in Scheme 1) and two oxygen atoms of chp ligands (mode V of Scheme 1). The Ni-O-Ni angles, where O is the oxygen from chp ligand, are between 92° and 94° .⁴¹ Magnetization vs. field plots at 2K, shown in Figure 9 are in agreement with an anisotropic non-zero spin ground state.

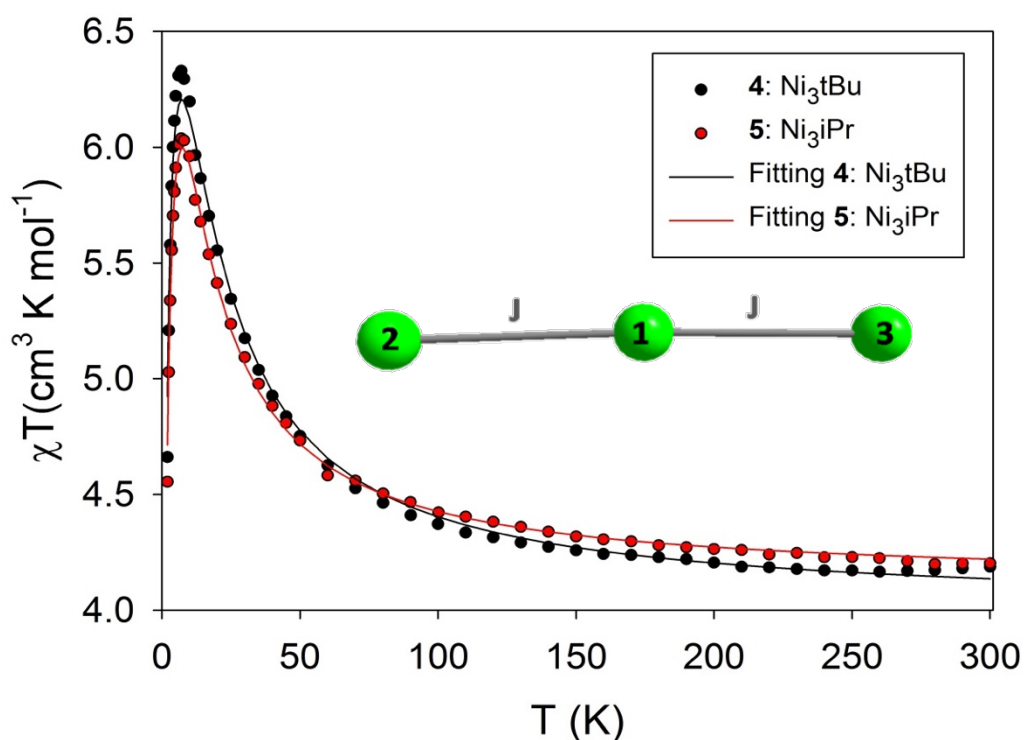


Figure 8. Magnetic susceptibility for complexes **4**: Ni₃tBu and **5**: Ni₃iPr. The solid lines are the best fitting to the experimental data (see text for fitting parameters).

The software PHI⁴² was used to fit simultaneously the susceptibility and the magnetization vs. field data. The susceptibility data can be modelled using a simple spin Hamiltonian with only one exchange constant and including the Zeeman effect and the crystal field on the single ions, as shown in equations 1 and 2.

$$\text{Eq. 1} \quad \hat{H} = \hat{H}_{EX} + \hat{H}_{CF} + \hat{H}_{Zeeman}$$

$$\text{Eq. 2} \quad \hat{H}_{EX} = -J[\hat{S}Ni_1\hat{S}Ni_2 + \hat{S}Ni_2\hat{S}Ni_3]$$

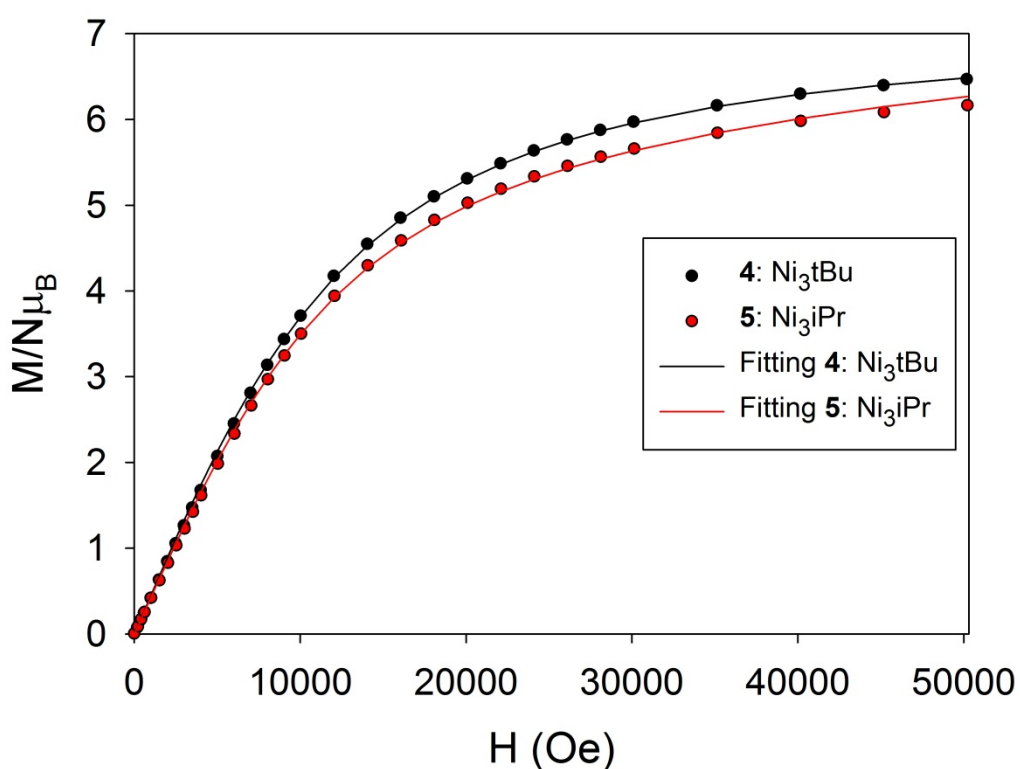


Figure 9. Magnetization vs. field plots for **4**: Ni₃tBu and **5**: Ni₃iPr. The solid lines are the best fitting to the experimental data (see text for fitting parameters).

The best fitting is shown in Figure 8 and 9 as solid lines. The *g* value was fixed as 2.3 for both complexes. The fitting parameters were $J = 3.7 \text{ cm}^{-1}$, $D_2 = D_3 = 8.02 \text{ cm}^{-1}$ and $D_1 = -14.53 \text{ cm}^{-1}$ for **4**: Ni₃tBu and $J = 3.8 \text{ cm}^{-1}$, $D_2 = D_3 = 9.38 \text{ cm}^{-1}$ and $D_1 = -11.45 \text{ cm}^{-1}$ for **5**: Ni₃iPr. D_1 is the *D* value for the central Ni(II) ion, while $D_2 = D_3$ are the *D* values for the two external Ni(II) ions. Even though they are not crystallographically equivalent in

complex **4**: Ni₃tBu, the approximation has been accepted to avoid overparametrization of the fitting. For both complexes, the ground state is S = 3 resulting from ferromagnetic coupling of the three Ni(II) ions. Magnetization and susceptibility fittings are not optimal to obtain the sign of D. the values reported here are those that afford the best agreement with experimental data. Neither **4**: Ni₃tBu nor **5**: Ni₃iPr displayed out-of-phase ac magnetic susceptibility signals, as could be expected for a relatively small spin ground state and all mostly positive single-ion anisotropy parameters.

Conclusions

Microwave assisted synthesis is a great tool for the coordination chemistry laboratory. We show here that it can be used to prepare polynuclear coordination complexes with good yields and purities. Waste generation in the research laboratory can be minimized using this synthetic method, where only small amounts of solvents are used to extract the solid obtained from the solvent-free microwave reaction.

We tested the solvent-free microwave assisted synthesis with the known complex [Ni₇(chp)₁₂(OH)₂(CH₃OH)₆] (**2**), and then extended the method to a more complex ligand system. We prepared two new trinuclear Ni(II) complexes [Ni₃(chp)₄(tBuSALOH)₂(MeOH)₅] (**4**) and [Ni₃(chp)₄(iPrSALOH)₂(MeOH)₆] (**5**) using solvent-free microwave assisted synthesis. The two Ni₃ complexes contain a linear arrangement of Ni(II) ions that are ferromagnetically coupled.

Acknowledgements

ECS, LRP acknowledge the financial support from the Spanish Government, (Grant CTQ2015-68370-P). We acknowledge Dr. Simon S. Teat for data collection of complex **2** at Berkeley ALS.

References

- (1) Winpenny, R. E. P. *Dalt. Trans.* **2002**, 1–10.
- (2) Ledezma-gairaud, M.; Grangel, L.; Aromí, G.; Fujisawa, T.; Yamaguchi, A.; Sumiyama, A.; Sañudo, E. C. *Inorg. Chem.* **2014**, *53*, 5878–5880.
- (3) Sañudo, E. C.; Uber, J. S.; Pons Balagué, A.; Roubeau, O.; Aromí, G. *Inorg. Chem.*

- 2012**, *51*, 8441–8446.
- (4) Coronado, E.; Yamashita, M. *Dalt. Trans.* **2016**, *80*, 1517.
 - (5) Transport, M.; Balestro, F.; Bendiab, N.; Bonet, E.; Bouchiat, V.; Marty, L.; Wernsdorfer, W. **2008**.
 - (6) Sanvito, S. *Chem. Soc. Rev.* **2011**, *40*, 3336.
 - (7) Blake, A. J.; Brechin, E. K.; Codron, A.; Gould, R. O.; Grant, C. M.; Parsons, S.; Rawson, J. M.; Winpenny, R. E. P. *J. Chem. Soc. Chem. Commun.* **1995**, *3*, 1983.
 - (8) Brechin, E. K.; Harris, S. G.; Parsons, S.; Winpenny, R. E. P. *Angew. Chemie Int. Ed. English* **1997**, *36*, 1967–1969.
 - (9) Sanudo, E. C.; Smith, A. A.; Mason, P. V.; Helliwell, M.; Aromi, G.; Winpenny, R. E. P. *Dalt. Trans.* **2006**, 1981–1987.
 - (10) Sañudo, E. C.; Muryn, C. a; Helliwell, M. a; Timco, G. a; Wernsdorfer, W.; Winpenny, R. E. P. *Chem. Commun.* **2007**, 801–803.
 - (11) Laye, R. H.; Larsen, F. K.; Overgaard, J.; Muryn, C. a; McInnes, E. J. L.; Rentschler, E.; Sanchez, V.; Teat, S. J.; Güdel, H. U.; Waldmann, O.; Timco, G. a; Winpenny, R. E. P. *Chem. Commun. (Camb)*. **2005**, *8*, 1125–1127.
 - (12) Sanudo, E. C.; Ribas, J.; Winpenny, R. E. P. *New J. Chem.* **2007**, *31*, 1421–1423.
 - (13) Ishikawa, N.; Sugita, M.; Ishikawa, T.; Koshihara, S.-Y.; Kaizu, Y. *J. Am. Chem. Soc.* **2003**, *125*, 8694–8695.
 - (14) Horii, Y.; Katoh, K.; Cosquer, G.; Breedlove, B. K.; Yamashita, M. *Inorg. Chem.* **2016**, *55*, 11782–11790.
 - (15) Yong, Y. F.; Kowalski, J. a.; Lipton, M. a. *J. Org. Chem.* **1997**, *62*, 1540–1542.
 - (16) Marriott, K. E. R.; Bhaskaran, L.; Wilson, C.; Medarde, M.; Ochsenein, S. T.; Murrie, M.; Hill, S. *Chem. Sci.* **2015**, *6*, 6823–6828.
 - (17) Kahn, O. *Molecular magnetism*; VCH Publishers: New York, 1993; Vol. 103.
 - (18) Blake, A. J.; Grant, C. M.; Parsons, S.; Rawson, J. M.; Winpenny, R. E. P. *J. Chem. Soc., Chem. Commun.* **1994**, *0*, 2363–2364.
 - (19) Andres, H.; Basler, R.; Blake, A. J.; Cadiou, C.; Chaboussant, G.; Grant, C. M.; Güdel, H.-U.; Murrie, M.; Parsons, S.; Paulsen, C.; Semadini, F.; Villar, V.; Wernsdorfer, W.; Winpenny, R. E. P. *Chemistry* **2002**, *8*, 4867–4876.
 - (20) Cadiou, C.; Murrie, M.; Paulsen, C.; Villar, V.; Winpenny, R. E. P. *Chem. Commun.* **2001**, 2666–2667.

- (21) Garlatti, E.; Carretta, S.; Affronte, M.; Sanudo, E. C.; Amoretti, G.; Santini, P. J. *Phys. Condens. Matter* **2012**, *24*, 104006/1-104006/9.
- (22) Branzoli, F.; Carretta, P.; Filibian, M.; Zoppellaro, G.; Graf, M. J.; Galan-Mascaros, J. R.; Fuhr, O.; Brink, S.; Ruben, M. J. *Am. Chem. Soc.* **2009**, *131*, 4387–4396.
- (23) Milios, C. J.; Vinslava, A.; Whittaker, a G.; Parsons, S.; Wernsdorfer, W.; Christou, G.; Perlepes, S. P.; Brechin, E. K. *Inorg. Chem.* **2006**, *45*, 5272–5274.
- (24) Gass, I. a; Milios, C. J.; Whittaker, a G.; Fabiani, F. P. a; Parsons, S.; Murrie, M.; Perlepes, S. P.; Brechin, E. K. *Inorg. Chem.* **2006**, *45*, 5281–5283.
- (25) Pons-Balagué, A.; Piligkos, S.; Teat, S. J.; Sánchez Costa, J.; Shiddiq, M.; Hill, S.; Castro, G. R.; Ferrer-Escorihuela, P.; Sañudo, E. C. *Chemistry* **2013**, *19*, 9064–9071.
- (26) Ledezma-Gairaud, M.; Pineda, L. W.; Aromí, G.; Sañudo, E. C. *Polyhedron* **2013**, *64*, 45–51.
- (27) Pons-Balague, A.; Ioanidis, N.; Wernsdorfer, W.; Yamaguchi, A.; Sanudo, E. C. *Dalt. Trans.* **2011**, *40*, 11765–11769.
- (28) Pons-Balagué, A.; Heras Ojea, M. J.; Ledezma-Gairaud, M.; Reta Mañeru, D.; Teat, S. J.; Sánchez, J.; Aromí, G.; Sañudo, E. C. *Polyhedron* **2013**, *52*, 781–787.
- (29) Shi, S.; Hwang, J. **2003**, *2*, 101–110.
- (30) Díaz-Torres, R.; Menelaou, M.; Roubeau, O.; Sorrenti, A.; Brandariz-De-Pedro, G.; Sañudo, E. C.; Teat, S. J.; Fraxedas, J.; Ruiz, E.; Aliaga-Alcalde, N. *Chem. Sci.* **2016**, *7*, 2793–2803.
- (31) Kharisov, B. I.; Dias, H. V. R.; Kharissova, O. V.; Vázquez, A.; Peña, Y.; Gómez, I. *RSC Adv.* **2014**, *4*, 45354–45381.
- (32) Brown, I. D.; Wu, K. K. *Acta Crystallogr. Sect. B Struct. Crystallogr. Cryst. Chem.* **1976**, *32*, 1957–1959.
- (33) Petrenko, V. F. *Structure of Ordinary Ice Ih - Part I: Ideal Structure of Ice*; 1993.
- (34) Bagai, R.; Christou, G. *Chem. Soc. Rev.* **2009**, *38*, 1011–1026.
- (35) Sessoli, R.; Tsai, H.-L.; Schake, A. R.; Wang, S.; Vincent, J. B.; Folting, K.; Gatteschi, D.; Christou, G.; Hendrickson, D. N. *J. Am. Chem. Soc.* **1993**, *115*, 1804–1816.
- (36) Physik, I.; Mainz, U.; Mainz, D.-; Germany, W.; Young, A. P. **1986**.
- (37) Mydosh, J. A. *Reports Prog. Phys.* **2015**, *78*, 052501–052526.

- (38) Shaw, R.; Tidmarsh, I. S.; Laye, R. H.; Breeze, B.; Helliwell, M.; Brechin, E. K.; Heath, S. L.; Murrie, M.; Ochsenein, S.; Güdel, H. U.; McInnes, E. J. L. *Chem. Commun.* **2004**, *4*, 1418–1419.
- (39) Carretta, S.; Santini, P.; Amoretti, G.; Affronte, M.; Candini, A.; Ghirri, A.; Tidmarsh, I. S.; Laye, R. H.; Shaw, R.; McInnes, E. J. L. *Phys. Rev. Lett.* **2006**, *97*, 1–4.
- (40) Goremychkin, E. a.; Osborn, R.; Rainford, B. D.; Macaluso, R. T.; Adroja, D. T.; Koza, M. *Nat. Phys.* **2008**, *4*, 766–770.
- (41) Halcrow, M. A.; Sun, J.; Huffman, J. C.; Christou, G. *Inorg. Chem.* **1995**, *4*, 4167–4177.
- (42) Chilton, N. F.; Anderson, R. P.; Turner, L. D.; Soncini, A.; Murray, K. S. *J. Comput. Chem.* **2013**, *34*, 1164–1175.