

Controlled periodic illumination in semiconductor photocatalysis

Tokode, O. , Prabhu, Radhakrishna , Lawton, Linda A. and Robertson, Peter K.J.

Author post-print (accepted) deposited by Coventry University's Repository

Original citation & hyperlink:

Tokode, O. , Prabhu, Radhakrishna , Lawton, Linda A. and Robertson, Peter K.J. (2015) Controlled periodic illumination in semiconductor photocatalysis. *Journal of Photochemistry and Photobiology A: Chemistry*, volume 319-320 : 96-106
<http://dx.doi.org/10.1016/j.jphotochem.2015.12.002>

DOI 10.1016/j.jphotochem.2015.12.002

ISSN 1010-6030

Publisher: Elsevier

NOTICE: this is the author's version of a work that was accepted for publication in Journal of Photochemistry and Photobiology A: Chemistry. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Journal of Photochemistry and Photobiology A: Chemistry, [VOL 319-320, (2015)] DOI: 10.1016/j.jphotochem.2015.12.002

© 2015, Elsevier. Licensed under the Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International

<http://creativecommons.org/licenses/by-nc-nd/4.0/>


Copyright © and Moral Rights are retained by the author(s) and/ or other copyright owners. A copy can be downloaded for personal non-commercial research or study, without prior permission or charge. This item cannot be reproduced or quoted extensively from without first obtaining permission in writing from the copyright holder(s). The content must not be changed in any way or sold commercially in any format or medium without the formal permission of the copyright holders.

This document is the author's post-print version, incorporating any revisions agreed during the peer-review process. Some differences between the published version and this version may remain and you are advised to consult the published version if you wish to cite from it.

Accepted Manuscript

Title: Controlled periodic illumination in semiconductor photocatalysis

Author: Oluwatosin Tokode Radhakrishna Prabhu Linda Lawton Peter K.J. Robertson

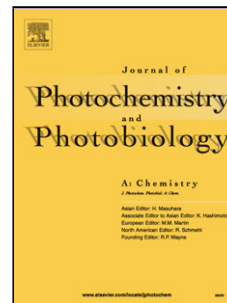

PII: S1010-6030(15)30245-8
DOI: <http://dx.doi.org/doi:10.1016/j.jphotochem.2015.12.002>
Reference: JPC 10077

To appear in: *Journal of Photochemistry and Photobiology A: Chemistry*

Received date: 13-11-2015
Accepted date: 5-12-2015

Please cite this article as: Oluwatosin Tokode, Radhakrishna Prabhu, Linda Lawton, Peter K.J. Robertson, Controlled periodic illumination in semiconductor photocatalysis, *Journal of Photochemistry and Photobiology A: Chemistry* <http://dx.doi.org/10.1016/j.jphotochem.2015.12.002>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Controlled periodic illumination in semiconductor photocatalysis

Oluwatosin Tokode^{1*}, Radhakrishna Prabhu², Linda Lawton³, Peter K. J. Robertson^{4*}.

¹Department of Engineering, Coventry University College, Priory Street, Coventry CV1 5FB, UK.

²School of Engineering, Robert Gordon University, Garthdee Road, Aberdeen, AB10 7GJ, UK.


³School of Pharmacy and Life Sciences, Robert Gordon University, Garthdee Road, Aberdeen, AB10 7GJ, UK.

⁴Centre for the Theory and Application of Catalysis (CenTACat), School of Chemistry and Chemical Engineering, Queen's University Belfast, Stranmillis Road, Belfast, BT9 5AG, UK.

^{1, 4} Corresponding authors

Email: ¹Oluwatosin.Tokode@cuc.coventry.ac.uk; ⁴p.robertson@qub.ac.uk

Graphical Abstract

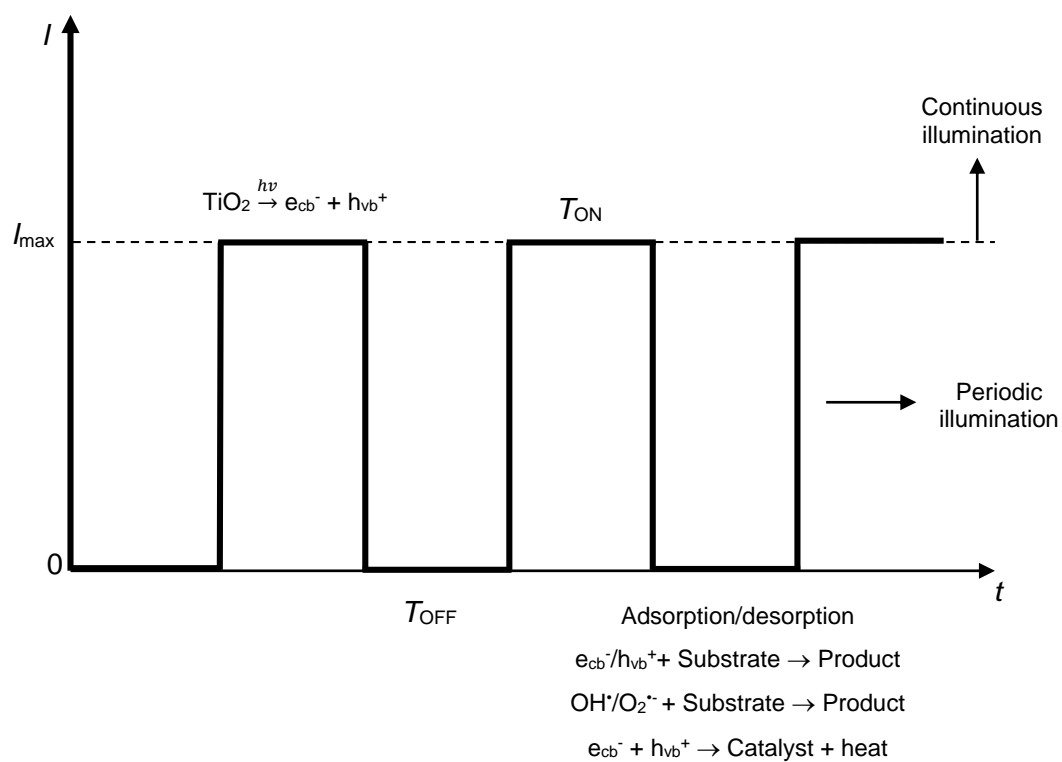

Highlights

- ◆ Use of controlled periodic illumination (CPI) for photocatalysis is critically reviewed.
- ◆ Experimental and theoretical studies are examined with emphasis on two theoretical models.
- ◆ A Langmuir-Hinshelwood model for incorporating CPI failed to predict photocatalytic rates.
- ◆ A quantum yield model showed good agreement with experimental data.
- ◆ Recent research in CPI have shown new applications of CPI that differ from the original hypothesis.

Abstract

Controlled periodic illumination is a hypothesis postulated in the early 1990s for enhancing the efficiency of semiconductor photocatalytic reactions. This technique has been proposed to improve photocatalytic efficiency by the nature of photon introduction alone. Before its application in semiconductor photocatalysis, controlled periodic illumination had been investigated in other fields including photosynthesis. This paper presents a detailed review of the state of the art research undertaken on the application of controlled periodic illumination in semiconductor photocatalysis. The review briefly introduces semiconductor photocatalysis, and then presents a detailed explanation of this technique, its importance to photocatalytic efficiency, an overview of previous results of its application in significant studies and present knowledge. Results from previous as well as some of the most recent studies indicate potential applications of controlled periodic illumination in areas other than just the improvement of the efficiency of the photocatalytic process.


Keywords

Controlled periodic illumination, Semiconductor photocatalysis, UV LEDs, Langmuir-Hinshelwood, Photonic efficiency

1. Introduction

Over the years, it has been observed that certain pollutants cannot be treated by biological and conventional treatment methods because of their high chemical stability or strong resistance to mineralization. In such cases, it has been necessary to adopt a more reactive and efficient chemical treatment processes. A group of oxidation processes defined as advanced oxidation processes which operate at ambient temperature and pressure have gained prominence as alternative treatment methods. Advanced oxidation processes (AOPs) [1,2] are characterized by a unique chemical feature common to them: the in-situ generation of highly reactive hydroxyl radicals (OH^{\bullet}) which drive the oxidation process by reacting with target molecules leading to the degradation and complete mineralisation of organic (and inorganic) pollutants in the environment [3]. They are also characterized by the selectivity of attack and versatility in the variety of ways OH^{\bullet} are produced. The advanced oxidation processes for generation of OH radicals include; $\text{H}_2\text{O}_2/\text{Fe}^{2+}$, TiO_2/UV , $\text{O}_3/\text{UV}/\text{H}_2\text{O}_2$ and $\text{H}_2\text{O}_2/\text{UV}$ processes.

TiO_2/UV is a heterogeneous photocatalytic process, which is an AOP employing TiO_2 catalysts however, several other semiconductors such as ZnO [4], SnO_2 and CdS have demonstrated capability as potential alternative materials to TiO_2 [5]. Research on semiconductor photocatalysis has received significant attention after the electrochemical photolysis of water at a TiO_2 electrode was reported in 1972 by Fujishima and Honda [6]. Water molecules were decomposed by visible light into oxygen and hydrogen using TiO_2 and platinum electrodes without any externally applied voltage. The water splitting was sustained by keeping the TiO_2 and platinum electrodes apart according to the following schemes:



The overall reaction was



The fundamental principles, mechanisms and applications of semiconductor photocatalysis have now been widely studied and reported in the scientific literature [7-10]. Furthermore, this field continues to receive a significant amount of interest and research including industrial applications following the demonstration of the Honda-Fujishima effect.

2. Semiconductor photocatalysis


The band structure of a semiconductor exists as a series of energetic, tightly packed energy levels associated with atoms exhibiting covalent bonding which make up the valence band. Another series of similar energetic levels which are spatially diffuse and at a higher energy, associated with conduction make up the conduction band. The size of the energy gap (E_{bg}) (fig. 1) between the valence and the conduction band is responsible for the electrical conductivity of the semiconductor and its wavelength sensitivity to irradiance while in its undoped state [11].

Figure 1.

1.1. Mechanism of semiconductor photocatalysis

When photons having energy greater than or equal to the band gap are incident on the semiconductor, the photons may be absorbed by the material. This leads to photo-excitation resulting in promotion of an electron from the valence to the conduction band leaving behind a hole (h_{vb}^+) i.e. an electron vacancy. If the initial photo-excitation takes place in the semiconductor catalyst which then transfers energy or an electron to the adsorbed ground state molecule (substrate), a sensitized photo-reaction is said to have taken place. When the reverse takes place, the process is referred to as a catalyzed photo-reaction [12]. Upon band gap excitation, charge separation due to the promotion of an electron (e_{cb}^-) from the valence to the conduction band takes place, generating a hole (h_{vb}^+) at the valence band in the process. The photogenerated charge carriers (e_{cb}^- and h_{vb}^+) can follow several pathways which include recombination hence dissipating energy as heat, become trapped in a metastable state or take part in reduction and oxidation reactions on the catalyst surface. For productive photocatalysis to occur, trapping of the e_{cb}^-/h_{vb}^+ or both is necessary. The trapping dynamics of photogenerated holes and electrons has been studied extensively by various authors and reviewed by Schneider *et al.* [13]. The primary steps after photon absorption by TiO_2 ; a widely used photocatalyst in semiconductor photocatalysis are shown in reactions (5-11) [14].





These reactions take place on the surface of the photocatalyst in traps located below the edge of the conduction band [15,16]. The highly reactive photogenerated h_{vb^+} and e_{cb^-} are directly involved in the oxidation and reduction reactions respectively or indirectly through intermediate such as OH^* and O_2^- which are equally highly oxidizing and reducing species with high standard redox potentials [17,18]. Characteristic times for the primary processes based on measurements of laser flash photolysis have been investigated [7]. Schneider *et al.* have also recently compiled a similar table and separated the primary process into processes on the catalyst surface and inside the catalyst particle [13]. The characteristic times for the primary processes are shown in Table 1.

Table 1.

In Table 1, $Ti^{IV}OH$ is the hydrated surface TiO_2 , e_{cb^-} is the conduction-band electron, e_{tr^-} is the trapped conduction-band electron, h_{vb^+} is the valence-band hole, Red is the reductant (electron donor), Ox is the oxidant (electron acceptor), $\{>Ti^{III}OH\}$ is a surface-trapped conduction-band electron and $\{>Ti^{IV}OH^*\}^+$ is the valence-band hole trapped at the surface or surface-bound hydroxyl radical. The photogenerated h_{vb^+} have a high quantum yield of 5.7×10^{-2} for ordinary photocatalytic reactions [19]. They are readily trapped at the hydrated TiO_2 surface during the oxidation of surface-bound OH^- ion groups to OH^* because of their small effective mass [20]. The yield of OH^* is dependent on competition between oxidation of surface water by the h_{vb^+} and the rate of charge carrier recombination [21]. Furthermore, OH^* adsorbed on the surface of the hydroxylated TiO_2 particle are easily assimilated and are indistinguishable from

surface-trapped holes [10]. The resulting $\{\text{Ti}^{\text{IV}}\text{OH}^*\}^+_{\text{ads}}$ is readily available for oxidative reactions with substrates adsorbed on the surface.

1.2. Efficiency of semiconductor photocatalysis

In semiconductor photocatalysis, the efficiency of the photocatalytic process is referred to as the quantum yield, which can be defined as the number of molecules changed divided by the number of absorbed photons, assuming all photons are absorbed by the catalyst and losses due to light scattering are negligible [7]. For a species i , the quantum yield Φ is given by equation 12.

$$\Phi_X = \frac{\pm(d[X]/dt)}{d[h\nu]_{\text{abs}}/dt} \quad (12)$$

Φ_X is the quantum yield for X , $d[X]/dt$ is the initial rate of formation or degradation of X and $d[h\nu]/dt$ is the rate of photon absorption by the catalyst.

Generally, photo-driven processes such as photography, photosynthesis and photocatalysis are preceded by photo-induced charge separation (5). The incident photons that initiate this process in photocatalysis are however, not efficiently used since charge carrier recombination (10 and 11) is a faster primary process than interfacial charge transfer (8 and 9). Hence, most electron-hole pairs recombine therefore limiting charge transfer which is necessary for initiating the desired redox reactions, ultimately this leads to low efficiencies [22]. When determining the quantum yield or efficiency, a combination of the total pathway probabilities for the hole and electron must be considered. This quantum yield is directly proportional to the electron

transfer rate constant (k_t) and inversely proportional to the charge carrier recombination rate constant (k_r) (13).

$$\Phi \propto \frac{k_t}{k_r} \quad (13)$$

For an ideal system, the quantum yield is directly proportional to the rate of charge transfer processes (k_{CT}) and inversely proportional to the sum of both bulk and surface electron-hole recombination rate (k_R) and the charge transfer rate (k_{CT}) (14):

$$\Phi \propto \frac{k_{CT}}{k_{CT} + k_R} \quad (14)$$

Diffusion of the products into the solution is assumed to be rapid without the reverse reaction of reduction by electrons and oxidation by holes. In the absence of recombination, quantum yield will have an ideal value of 1 [12] for photocatalytic processes. In real systems, however, recombination occurs and the concentration of holes and electrons at the surface is not equal [23].

1.1.1. Measures of photocatalytic efficiency

A variety of measures of efficiency are used in the literature on semiconductor photocatalysis. The quantum yield, Φ which takes into account the actual number of photons absorbed by the semiconductor catalyst has been sometimes referred to as the quantum efficiency, η or photonic efficiency, ζ and determined using the number of photons incident on the catalyst. This latter definition is an accurate approximation of the efficiency and is a lower limit of the actual quantum yield. While determining quantum yields in semiconductor photocatalysis is feasible and has been demonstrated in several studies [22,24-27], it is experimentally difficult due to the

significant amount of scattering, reflection, absorption and transmission of photons. As a result, most studies on semiconductor photocatalysis determine the rate of incident photons hence, employing photonic efficiency as a measure of efficiency. Differences in reactor geometry, light sources, reaction conditions and difficulties inherent in the determination of photon absorption by the catalyst have led to a proposed standardization of efficiencies. Relative photonic efficiency, ζ_r [16] has been suggested as a protocol which affords comparisons of efficiencies from different studies and eliminates the confusion associated with quantum yield determination in the literature. Other suggested measures of efficiency include Electric energy per order/mass (E_{EO}/E_{EM}) [28] which are based on electric energy consumption and mostly useful in economic analysis.

1.1.2. Enhancement of photocatalytic efficiency

A lot of effort has been directed at understanding the fundamental and engineering aspects of semiconductor photocatalysis with the primary aim of improving its efficiency [23]. Previous studies have shown that quantum yields in dilute aqueous suspensions are usually below ~10% while quantum yields of oxidation of organic species in the gas phase exceed 50% under weak UV illumination [7,12,29]. Various methods of improving efficiency have been studied, for example doping of catalysts to enhance efficiency by inhibiting charge carrier recombination or improving light absorption is well reported in the literature [30-34]. The introduction of an extra electric field across the semiconductor photocatalyst to enhance the photocatalytic efficiency has been demonstrated [35]. The electric field promoted the separation of e_{cb^-}/h_{vb^+} pairs and prevented their recombination. These two examples employ the principles

of band offsetting, defect introduction and electric force field that overcome the binding Coulombic forces and cause the dissociation of the electron-hole pair initially. In 1993 Sczechowski *et al.* [36] reported an impressive 500% increase in the photonic efficiency of formate decomposition in TiO₂ suspension through the technique of controlled periodic illumination (CPI).

3. Controlled periodic illumination

Controlled periodic illumination (CPI) in semiconductor photocatalysis is a hypothesis which was first investigated in 1993 by Sczechowski and co-workers. Prior to this report, it was known that information on the lifetimes of reactive intermediates in photochemical reactions could be obtained through periodic illumination [37-39]. The hypothesis suggests that upon illumination of a catalyst, there is a critical illumination time during which absorbed photons generate oxidizing species (h_{vb}^+) on the surface of the catalyst. The generated species or their intermediates (OH^*) go on to react with substrates on the surface or in the bulk. Photons are not required for this latter step which also includes adsorption, desorption and diffusion hence, it can take place in the dark. After a critical recovery period in the dark, the photocatalyst can efficiently use photons again thus photons are reintroduced. CPI is therefore based on a series of alternate light and dark (T_{ON}/T_{OFF}) periods (fig.2) which prevent the continuous introduction of photons that will result in the build-up of charges (e_{cb}^-/h_{vb}^+) and photogenerated intermediates (OH^*/O_2^*). These charges and intermediate species are required for the desired photocatalytic reactions but their build-up can favour undesirable reactions resulting in a low efficiency of the photocatalytic process.

Figure 2.

The application of CPI will allow for the variation of T_{ON}/T_{OFF} and calculation of the optimal amount of photons a photocatalyst can utilize in a given T_{ON} period or under continuous illumination before saturation. It also makes determination of the specific light intensity required for photonic efficiency improvement possible. It was also suggested that CPI may influence selectivity of photocatalysis through changes in initial oxidation or relative rates of the remaining steps in the proposed pathways during reaction. Ultimately, an understanding of the mechanism of CPI will lead to design and synthesis of photocatalysts that can accommodate longer T_{ON} and minimal T_{OFF} . An optimal photocatalyst in this hypothesis will require no T_{OFF} but will be highly efficient under continuous illumination.

Generally for CPI studies, the period of illumination is the time taken for a complete light time and dark time cycle and is the sum $T_{ON} + T_{OFF}$ while the duty cycle, γ is the percentage of the period equivalent to a light time (15).

$$\gamma = \frac{T_{on}}{T_{on} + T_{off}} \times 100\% \quad (15)$$

At light times, the intensity of illumination is maximum hence, for a given reaction time under CPI, the average intensity of illumination, is calculated as:

$$I_{avg} = \gamma + I_{max} \quad (16)$$

While the photonic efficiency, ζ is determined as:

$$\zeta_X = \frac{\pm(d[X]/dt)}{d[h\nu]_{inc}/dt} \quad (17)$$


Where ζ_X is the photonic efficiency for X , $d[X]/dt$ is the initial rate of formation or disappearance of X and $d[h\nu]/dt$ is the incident photon rate on the catalyst.

1.3. Controlled periodic illumination in other fields

The concept of periodic illumination has been applied in other fields for various purposes. It has been demonstrated to be a powerful tool in photolysis for studying the individual steps and mechanisms of chain reactions [37]. It has also been applied in the control of the formation of concentration patterns formed from instability of chemical reaction-diffusion systems; these patterns are known as Turing structures [40]. Of particular interest here is the demonstration of the efficient suppression of Turing structures using periodic illumination and the removal of defects in pre-existing Turing structures. Its investigation in the field of photosynthesis research which is characterised by photon saturation during T_{ON} precedes photocatalysis and is also concerned with enhancement of efficiency. Earlier results in this area of research indicate an improved quantum yield under CPI [41] however, there are reports of equivalent yields under continuous and periodic illumination from other studies [42,43]. It is now well established that under periodic illumination, the photosynthetic apparatus being a very complex system, elicits various acclimatisation responses in plants leading to conflicting results on the effects of CPI on photosynthesis [44,45].

1.4. Experimental CPI studies in semiconductor photocatalysis

The experimental studies by Sczechowski *et al.* provided preliminary results on the CPI hypothesis and its effects on photonic efficiency of photocatalytic reactions. Their pioneering study [36] reported a 500% increase in photonic efficiency during formate ion oxidation (18) in TiO_2 slurries. The oxidation of formate to CO_2 was an appropriate reaction for testing this hypothesis due to the lack of competing intermediates.



Periodic illumination of the TiO₂ slurry was simulated by wrapping sections of the bulb in aluminium foil (T_{OFF}) with some sections exposed (T_{ON}) while the TiO₂ suspension flowed underneath the light bulb in the channel reactor. The 5-fold increase in photonic efficiency which was due to CPI and the inadequacies of the channel reactor prompted the need for photoreactors which as a singular unit can periodically illuminate the semiconductor photocatalyst. Due to the inability of turning fluorescent bulbs on and off on a millisecond timescale, subsequent studies employed a Taylor vortex reactor (TVR) to simulate CPI [46]. Vortices formed in the TVR, transport catalyst particles into and out of the illuminated portion of the reactor. Creating vortices fast enough for the frequencies optimal for the CPI effect was, however, a significant design challenge.

Figure 3.

The results of the CPI effects were also investigated by Stewart and Fox [47], who studied the effect of varying the dark recovery time on the photonic efficiency of the photocatalytic oxidation of 1-octanol and photocatalytic reduction of *p*-nitroacetophenone in a non-aqueous media, using Degussa P25 TiO₂. They reported a 1.8 fold improvement in the net photonic efficiency of 1-octanol oxidation to octanal but no improvement in the reduction of *p*-nitroacetophenone to *p*-aminoacetophenone. They suggested that a dark recovery time between intermittent excitation lowered the steady state concentration of the adsorbed intermediates and helped prevent charge carrier recombination which decreased efficiency. Foster *et al.* [48] investigated the mechanism of CPI effects using rotating ring disk photoelectrochemistry (RRDE). Their results suggested ordinary photoreactors at low light intensities could exhibit high photonic efficiencies but high photonic efficiencies at high light intensities would

require photoreactors capable of periodically illuminating the photocatalyst. Buechler *et al.* investigated the CPI effect in the aqueous [49] and gaseous [50] phases using novel photoreactors capable of CPI. A 15% increase in photonic efficiency due to CPI was reported at light intensities above 0.5 mW/cm² for formate oxidation in the aqueous phase while photonic efficiency of trichloroethylene (TCE) oxidation in the diffusion-limited regime approached ~100%. All studies on CPI after Sczechowski *et al.* first demonstrated photonic efficiency enhancement using this technique corroborate the original hypothesis. This hypothesis, however, was later challenged by Cornu *et al.* [51] who demonstrated with formate oxidation that quantum yields under CPI did not exceed those under continuous illumination at equivalent photon absorption rates. Their results gave the first indication Φ values under CPI were always less than Φ under continuous illumination but equivalent at high frequency CPI. A subsequent study by Buechler *et al.* in formate photocatalytic oxidation reached a similar conclusion [52]; they attributed the previously reported CPI effect to be due to mass transport limitations and slow or weak adsorption/reaction steps.

In addition to their study on quantum yields under CPI, Cornu *et al.* [53] also studied CPI in the stochastic regime and reported two rate-determining intermediates whose lifetimes and oxidizing/reducing potentials are dependent on the pH of the media. Their results also showed two transitions between low-frequency and high-frequency Φ values, the two transitions had characteristic times which were shown to be exponential functions of the pH of the media. For chain reactions in the stochastic regime, Φ will depend on the average concentration of the rate-determining intermediates. Further research into the understanding of the CPI effect was carried out by Wang *et al.* [54], where periodic illumination was created using laser pulse illumination having light-to-dark time ratio of 20 ns to 2 s. They studied quantum yield

of formaldehyde formation in aqueous methanolic TiO₂ suspensions without mass transport limitations. They explained the increase in quantum yield of formaldehyde formation to be due to laser pulse-induced deaggregation of agglomerated TiO₂ particles. Their results suggested deaggregation results in the exposure of additional sites for reactant adsorption hence, optimising catalyst surface area leading to increased reaction rates and quantum yields. The deaggregation concept was further developed with a novel mechanism proposed by Wang *et al.* to explain the CPI effect. The antenna mechanism [55] suggests that a long chain of agglomerated TiO₂ particles not only increase catalyst surface area upon deaggregation but also acts as an antenna for transferring photon energy from the site of absorption to the site of reaction. The claim that no advantage accrued from the use of CPI over continuous illumination was further investigated by Chen *et al.* [56] who first studied CPI using UV LED sources [57] which were more suitable for the series of light and dark times required by CPI (fig. 4).

Figure 4.

UV LEDs were also employed by Tokode *et al.* [58] who used a controlled experiment design to study the CPI effect (Table 2). Both studies reported no photonic efficiency enhancement due to CPI at I_{avg} equivalent to I under continuous illumination. These studies provide overwhelming experimental data which show that CPI alone is not sufficient to enhance the photonic efficiency of semiconductor photocatalysis.

Table 2.

1.5. Theoretical CPI studies in semiconductor photocatalysis

The vast majority of studies investigating CPI have relied on the experimental approach; these studies provided initial data for the development of mathematical models to simulate the observable phenomena on the semiconductor catalyst during CPI. Two CPI models have been formulated and reported in the literature for determining quantum yields and photocatalytic rates of reaction under CPI.

1.1.3. Quantum yield CPI model

A transient kinetic model to simulate the initial experimental evidence of the CPI hypothesis tested by Sczechowski *et al.* in terms of the fundamental steps was proposed by Upadhyaya and Ollis [59]. They identified factors which affect quantum yield and arrived at a kinetic scheme of four reactions leading to the equation development. A model for the quantum yield Φ , (19, 20) as opposed to photonic efficiency was developed due to availability of data on photon absorption by the TiO₂ catalyst. This model calculated quantum yield of the organic substrate was as an integral of the instantaneous quantum yield over time;

$$\Phi_{\text{periodic}} = \frac{\int^{T_{\text{ON}}+T_{\text{OFF}}} k_1 n_A (h^+(t)) \Omega_A(t) dt}{\int^{T_{\text{ON}}} k_g I dt} \quad (19)$$

$$\Phi_{\text{continuous}} = \frac{\int^{T_{\text{ON}}} k_1 n_A (h^+)_{ss} \Omega_{Ass} dt}{\int^{T_{\text{ON}}} k_g I dt} \quad (20)$$

Where k_1 is the oxidation reaction rate constant, h^+ is the hole concentration, Ω_A is the surface fractional coverage of organic substrate, k_g is the light absorption rate constant, n_A is the number of surface sites for organic substrate, T_{ON} is the light time,

T_{OFF} is the dark time and I is the incident light intensity. Their results at the time, corroborated the quantum yield enhancement result of Sczechowski and co-workers but more importantly, it provided knowledge of dioxygen and net charge concentration dynamics as a function of $T_{\text{ON}}/T_{\text{OFF}}$ during CPI (fig. 5).

Figure 5.

1.1.4. The Langmuir-Hinshelwood CPI rate model

For reactions on surfaces such as occur in semiconductor photocatalysis, the Langmuir-Hinshelwood (L-H) rate equation (24) is the simplest model consistent with Langmuir's equilibrium isotherm. The L-H rate model has a dependence upon concentration and is widely applied in determining rates of photocatalytic reactions in the literature with a close agreement when compared with experimental rate data [60-62]. The photocatalytic rate, r is calculated by the L-H model as the product of the reaction rate constant, k_r of surface species (photogenerated and substrate) and the extent of substrate adsorption, K_{ads} . Competition for adsorption by other species is represented by adding the terms $K_{\text{ads}}C$ to the denominator.

$$-\frac{dC}{dt} = r = k_r \frac{K_{\text{ads}}C}{(1 + K_{\text{ads}}C)} \quad (24)$$

Previous studies have established the dependence of photocatalytic rates on light intensity [63] leading to studies incorporating intensity into the L-H model [64]. With the intensity incorporated into equation 24, the L-H model is unsuitable for modelling reaction rates when the photocatalyst is under CPI. The illumination intensity, its order

and periodicity have to be accounted for in any rate model under CPI. Chen *et al.* [56] modified the L-H model by incorporating these parameters which account for the CPI effect (25) with the reaction assumed to take place on the outer surface of the photocatalyst particle.

$$-\frac{dC}{dt} = r = k_r(\gamma I_{max})^m \frac{K_{ads}C}{(1+K_{ads}C)} \quad (25)$$

Where γ is the duty cycle of UV illumination, I_{max} is the light intensity ($I_{avg} = \gamma I_{max}$) and m is the order of light intensity. The L-H CPI model produced photocatalytic rate trends at varying concentration and constant γ in close agreement with the experimental data (fig. 6).

Figure 6.

In a recent study [65], the quantum yield CPI model and the L-H CPI model were employed in the photocatalytic degradation of methyl orange under CPI. The calculated values of Φ and ζ from the quantum yield CPI model and photonic efficiency experimental data respectively had different magnitudes but followed a similar trend (fig. 7). The L-H CPI model however, failed to predict the experimental rates due to the varying γ at constant concentration. The accuracy of the L-H CPI model is sensitive to I_{avg} while the quantum yield CPI model accurately simulates quantum yield enhancement due to the CPI effect.

Figure 7.

1.6. Recent results from CPI studies

The body of work on CPI in semiconductor photocatalysis has disproved the original hypothesis by Sczechowski *et al.* The photonic efficiency enhancement due to CPI can be attained under continuous illumination at very weak illumination intensity. This technique, however, still receives attention from studies involving and investigating its effect on semiconductor photocatalysis as detailed in Table 3, which summarises the work that has been reported on CPI to date.

Table 3.

The mechanism for the hypothesis of residual disinfection effect which describes a further decrease of bacterial concentration long after photocatalyst illumination and photo-excitation has ceased was studied by Xiong and Hu [66]. They reported higher log-removal and inactivation of bacteria at high frequency CPI compared to continuous illumination at equivalent UV dosage. This result in semiconductor photocatalysis mediated inactivation of bacteria is significant because it mirrors the initial results of increase in photonic efficiency by pioneering studies in CPI. Tokode *et al.* [67] recently described a triple effect of pH, γ and oxidizing species on the photonic efficiency of semiconductor photocatalysis. They describe how to optimize CPI and increase photonic efficiency without making any comparisons with continuous illumination. Two efficiency regimes were proposed under the experimental conditions of the study (fig.8).

Figure 8.

A recent study by Korovin *et al.* [68] has shown that frequency of periodic illumination is equally important as γ in CPI. They employed UV LEDs in the photocatalytic

oxidation of acetone vapour at very high frequency CPI. The results of Korovin and co-workers shows photonic efficiency, ζ under high frequency CPI is always lower than that of the continuous regime at equivalent average UV light intensities (fig. 9) but equals it at the maximum photonic efficiency value reached when the reaction becomes photon-limited [29]. This result is at variance with previous studies [51,58] which report comparable efficiencies at equivalent average UV light intensities and further illustrates the need for more investigations into CPI for more understanding of its effects in semiconductor photocatalysis.

Figure 9.

4. Conclusion

The initial hypothesis put forward by Sczechowski *et al.* for improving the photonic efficiency of semiconductor photocatalysis through controlled periodic illumination has been a controversial subject having been both proved by initial studies [36,47,59] and disproved by subsequent studies [51,65,68]. Research investigating the mechanism of CPI has spanned two decades and is still ongoing [66,67] despite not achieving its original purpose. This technique appears to only restore catalyst activity which is lost due to limitations in diffusion in large catalyst aggregates and is therefore a kinetic disguise because of the omitted rate-influencing reaction step. The mechanistic concept of the antenna mechanism and deaggregation proposed by Wang *et al.* [55] is currently employed by researchers in interpreting CPI data. Furthermore, the gains in photonic efficiency achieved under CPI alone can be achieved under low intensity continuous illumination. Photocatalytic experiments under CPI can, however be applied in providing kinetic information on the lifetimes of reactive intermediates on the

photocatalyst surface, which determine the efficiency of the photocatalytic reaction. Its proposed contribution in determining the specific light intensity required by a semiconductor catalyst for improving photonic efficiency as well as the design and synthesis of an optimal catalyst still remain an objective of semiconductor photocatalysis research activity.

5. References

- [1] K. Topudurtir, S. Tay, E. Monschein, *Advanced Photochemical Oxidation Processes. Handbook*, (1998).
- [2] R. Andreatti, V. Caprio, A. Insola, R. Marotta, *Advanced oxidation processes (AOP) for water purification and recovery*, *Catalysis today*. 53 (1999) 51-59.
- [3] O. Tokode, *Photocatalytic destruction of volatile organic compounds from the oil and gas industry*. (2014).
- [4] A. McLaren, T. Valdes-Solis, G. Li, S.C. Tsang, *Shape and size effects of ZnO nanocrystals on photocatalytic activity*, *J. Am. Chem. Soc.* 131 (2009) 12540-12541.
- [5] M. Miyauchi, A. Nakajima, T. Watanabe, K. Hashimoto, *Photocatalysis and photoinduced hydrophilicity of various metal oxide thin films*, *Chemistry of Materials*. 14 (2002) 2812-2816.
- [6] A. Fujishima, K. Honda, *Photolysis-decomposition of water at the surface of an irradiated semiconductor*, *Nature*. 238 (1972) 37-38.
- [7] M.R. Hoffmann, S.T. Martin, W. Choi, D.W. Bahnemann, *Environmental applications of semiconductor photocatalysis*, *Chem. Rev.* 95 (1995) 69-96.
- [8] A. Mills, S. Le Hunte, *An overview of semiconductor photocatalysis*, *J. Photochem. Photobiol. A*. 108 (1997) 1-35.
- [9] M.A. Fox, M.T. Dulay, *Heterogeneous photocatalysis*, *Chem. Rev.* 93 (1993) 341-357.

- [10] D. Lawless, N. Serpone, D. Meisel, Role of hydroxyl radicals and trapped holes in photocatalysis. A pulse radiolysis study, *J. Phys. Chem.* 95 (1991) 5166-5170.
- [11] A.J. Nozik, Photoelectrochemistry: Applications to solar energy conversion, *Annu. Rev. Phys. Chem.* 29 (1978) 189-222.
- [12] A.L. Linsebigler, G. Lu, J.T. Yates Jr, Photocatalysis on TiO₂ surfaces: principles, mechanisms, and selected results, *Chem. Rev.* 95 (1995) 735-758.
- [13] J. Schneider, M. Matsuoka, M. Takeuchi, J. Zhang, Y. Horiuchi, M. Anpo, D.W. Bahnemann, Understanding TiO₂ photocatalysis: mechanisms and materials, *Chem. Rev.* 114 (2014) 9919-9986.
- [14] S. Goldstein, D. Behar, J. Rabani, Nature of the oxidizing species formed upon UV photolysis of C-TiO₂ aqueous suspensions, *The Journal of Physical Chemistry C.* 113 (2009) 12489-12494.
- [15] S.H. Szczepankiewicz, J.A. Moss, M.R. Hoffmann, Slow surface charge trapping kinetics on irradiated TiO₂, *The Journal of Physical Chemistry B.* 106 (2002) 2922-2927.
- [16] H. Wang, J. He, G. Boschloo, H. Lindström, A. Hagfeldt, S. Lindquist, Electrochemical investigation of traps in a nanostructured TiO₂ film, *The Journal of Physical Chemistry B.* 105 (2001) 2529-2533.
- [17] D.T. Sawyer, J.S. Valentine, How super is superoxide? *Acc. Chem. Res.* 14 (1981) 393-400.
- [18] P.M. Wood, The potential diagram for oxygen at pH 7, *Biochem. J.* 253 (1988) 287-289.

- [19] K. Ishibashi, A. Fujishima, T. Watanabe, K. Hashimoto, Quantum yields of active oxidative species formed on TiO₂ photocatalyst, *J. Photochem. Photobiol. A.* 134 (2000) 139-142.
- [20] S.H. Szczepankiewicz, J.A. Moss, M.R. Hoffmann, Electron traps and the stark effect on hydroxylated titania photocatalysts, *The Journal of Physical Chemistry B.* 106 (2002) 7654-7658.
- [21] R. Gao, J. Stark, D.W. Bahnemann, J. Rabani, Quantum yields of hydroxyl radicals in illuminated TiO₂ nanocrystallite layers, *J. Photochem. Photobiol. A.* 148 (2002) 387-391.
- [22] M.A. Grela, A.J. Colussi, Kinetics of stochastic charge transfer and recombination events in semiconductor colloids. Relevance to photocatalysis efficiency, *J. Phys. Chem.* 100 (1996) 18214-18221.
- [23] D.F. Ollis, H. Al-Ekabi, Photocatalytic Purification and Treatment of Water and Air: Proceedings of the 1st International Conference on TiO₂ Photocatalytic Purification and Treatment of Water and Air, London, Ontario, Canada, 8-13 November, 1992, Elsevier Science Ltd, 1993.
- [24] A. Salinaro, A.V. Emeline, J. Zhao, H. Hidaka, V.K. Ryabchuk, N. Serpone, Terminology, relative photonic efficiencies and quantum yields in heterogeneous

photocatalysis. Part II: Experimental determination of quantum yields, *Pure and applied chemistry*. 71 (1999) 321-335.

[25] M.L. Satuf, R.J. Brandi, A.E. Cassano, O.M. Alfano, Experimental method to evaluate the optical properties of aqueous titanium dioxide suspensions, *Ind Eng Chem Res*. 44 (2005) 6643-6649.

[26] Y. Du, J. Rabani, Determination of quantum yields in two-dimensional scattering systems, *J. Photochem. Photobiol. A*. 162 (2004) 575-578.

[27] C. Wang, J. Rabani, D.W. Bahnemann, J.K. Dohrmann, Photonic efficiency and quantum yield of formaldehyde formation from methanol in the presence of various TiO₂ photocatalysts, *J. Photochem. Photobiol. A*. 148 (2002) 169-176.

[28] J.R. Bolton, K.G. Bircher, W. Tumas, C.A. Tolman, Figures-of-merit for the technical development and application of advanced oxidation technologies for both electric-and solar-driven systems (IUPAC Technical Report), *Pure and Applied Chemistry*. 73 (2001) 627-637.

[29] Y. Ohko, K. Hashimoto, A. Fujishima, Kinetics of photocatalytic reactions under extremely low-intensity UV illumination on titanium dioxide thin films, *The Journal of Physical Chemistry A*. 101 (1997) 8057-8062.

[30] J. Disidier, J. Herrmann, P. Pichat, A Photoconductivity study of electron transfer from the ultraviolet-illuminated support to the metal and of the influence of hydrogen, *J.Chem.Soc.Faraday Trans.I*. 79 (1983) 651-660.

[31] S. Sakthivel, M. Shankar, M. Palanichamy, B. Arabindoo, D. Bahnemann, V. Murugesan, Enhancement of photocatalytic activity by metal deposition:

characterisation and photonic efficiency of Pt, Au and Pd deposited on TiO₂ catalyst, Water Res. 38 (2004) 3001-3008.

[32] M.K. Seery, R. George, P. Floris, S.C. Pillai, Silver doped titanium dioxide nanomaterials for enhanced visible light photocatalysis, J. Photochem. Photobiol. A. 189 (2007) 258-263.

[33] T. Xu, L. Zhang, H. Cheng, Y. Zhu, Significantly enhanced photocatalytic performance of ZnO via graphene hybridization and the mechanism study, Applied Catalysis B: Environmental. 101 (2011) 382-387.

[34] X. Zong, H. Yan, G. Wu, G. Ma, F. Wen, L. Wang, C. Li, Enhancement of photocatalytic H₂ evolution on CdS by loading MoS₂ as cocatalyst under visible light irradiation, J. Am. Chem. Soc. 130 (2008) 7176-7177.

[35] Z. Jiang, H. Wang, H. Huang, C. Cao, Photocatalysis enhancement by electric field: TiO₂ thin film for degradation of dye X-3B, Chemosphere. 56 (2004) 503-508.

[36] J.G. Sczechowski, C.A. Koval, R.D. Noble, Evidence of critical illumination and dark recovery times for increasing the photoefficiency of aqueous heterogeneous photocatalysis, J. Photochem. Photobiol. A. 74 (1993) 273-278.

[37] W. Haden Jr, O. Rice, The Chain Photolysis of Acetaldehyde in Intermittent Light, J. Chem. Phys. 10 (1942) 445-460.

[38] W.A. Noyes, P.A. Leighton, Photochemistry of gases, (1966).

[39] G. Burnett, H. Melville, Propagation and Termination Coefficients for Vinyl Acetate Photopolymerization, Nature. 156 (1945) 661.

[40] A.K. Horváth, M. Dolnik, A.P. Munuzuri, A.M. Zhabotinsky, I.R. Epstein, Control of Turing structures by periodic illumination, *Phys. Rev. Lett.* 83 (1999) 2950.

[41] R. Emerson, W. Arnold, A Separation of the Reactions in Photosynthesis by Means of Intermittent Light, *J. Gen. Physiol.* 15 (1932) 391-420.

[42] J.P. Gaudillère, Effect of periodic oscillations of artificial light emission on photosynthetic activity, *Physiol. Plantarum.* 41 (1977) 95-98.

[43] J. Gaudillere, J. Drevon, J. Bernoud, F. Jardinnet, M. Euvrard, Effects of periodic fluctuations of photon flux density on anatomical and photosynthetic characteristics of soybean leaves, *Photosynthesis Res.* 13 (1987) 81-89.

[44] M. Kono, I. Terashima, Long-term and short-term responses of the photosynthetic electron transport to fluctuating light, *Journal of Photochemistry and Photobiology B: Biology.* 137 (2014) 89-99.

[45] J.U. Grobbelaar, L. Nedbal, V. Tichý, Influence of high frequency light/dark fluctuations on photosynthetic characteristics of microalgae photoacclimated to

different light intensities and implications for mass algal cultivation, *J. Appl. Phycol.* 8 (1996) 335-343.

[46] J.G. Sczechowski, C.A. Koval, R.D. Noble, A Taylor vortex reactor for heterogeneous photocatalysis, *Chemical Engineering Science.* 50 (1995) 3163-3173.

[47] G. Stewart, M.A. Fox, The effect of dark recovery time on the photoefficiency of heterogeneous photocatalysis by TiO_2 suspended in non-aqueous media, *Research on chemical intermediates.* 21 (1995) 933-938.

[48] N.S. Foster, C.A. Koval, J.G. Sczechowski, R.D. Noble, Investigation of controlled periodic illumination effects on photo-oxidation processes at titanium dioxide films

using rotating ring disk photoelectrochemistry, *J Electroanal Chem.* 406 (1996) 213-217.

[49] K.J. Buechler, C.H. Nam, T.M. Zawistowski, R.D. Noble, C.A. Koval, Design and evaluation of a novel-controlled periodic illumination reactor to study photocatalysis, *Ind Eng Chem Res.* 38 (1999) 1258-1263.

[50] K.J. Buechler, R.D. Noble, C.A. Koval, W.A. Jacoby, Investigation of the effects of controlled periodic illumination on the oxidation of gaseous trichloroethylene using a thin film of TiO_2 , *Ind Eng Chem Res.* 38 (1999) 892-896.

[51] C.J. Cornu, A. Colussi, M.R. Hoffmann, Quantum yields of the photocatalytic oxidation of formate in aqueous TiO_2 suspensions under continuous and periodic illumination, *The Journal of Physical Chemistry B.* 105 (2001) 1351-1354.

[52] K.J. Buechler, T.M. Zawistowski, R.D. Noble, C.A. Koval, Investigation of the mechanism for the controlled periodic illumination effect in TiO_2 photocatalysis, *Ind Eng Chem Res.* 40 (2001) 1097-1102.

[53] C. Cornu, A. Colussi, M. Hoffmann, Time scales and pH dependences of the redox processes determining the photocatalytic efficiency of TiO_2 nanoparticles from periodic illumination experiments in the stochastic regime, *The Journal of Physical Chemistry B.* 107 (2003) 3156-3160.

[54] C. Wang, R. Pagel, D.W. Bahnemann, J.K. Dohrmann, Quantum yield of formaldehyde formation in the presence of colloidal TiO_2 -based photocatalysts: effect

of intermittent illumination, platinization, and deoxygenation, *The Journal of Physical Chemistry B*. 108 (2004) 14082-14092.

[55] C. Wang, R. Pagel, J.K. Dohrmann, D.W. Bahnemann, Antenna mechanism and deaggregation concept: novel mechanistic principles for photocatalysis, *Comptes Rendus Chimie*. 9 (2006) 761-773.

[56] H. Chen, Y. Ku, A. Irawan, Photodecomposition of o-cresol by UV-LED/TiO₂ process with controlled periodic illumination, *Chemosphere*. 69 (2007) 184-190.

[57] O. Tokode, R. Prabhu, L.A. Lawton, P.K.J Robertson, UV LED Sources for Heterogeneous Photocatalysis, in "Environmental Photochemistry Part III", eds. D. W. Bahnemann and P.K.J Robertson, Springer-Verlag Berlin Heidelberg. 2015, 159-180

[58] O.I. Tokode, R. Prabhu, L.A. Lawton, P.K.J Robertson, Effect of controlled periodic-based illumination on the photonic efficiency of photocatalytic degradation of methyl orange, *Journal of Catalysis*. 290 (2012) 138-142.


[59] S. Upadhya, D.F. Ollis, Simple photocatalysis model for photoefficiency enhancement via controlled, periodic illumination, *The Journal of Physical Chemistry B*. 101 (1997) 2625-2631.

[60] K.V. Kumar, K. Porkodi, F. Rocha, Langmuir–Hinshelwood kinetics—a theoretical study, *Catalysis Communications*. 9 (2008) 82-84.

[61] A. Mills, J. Wang, D.F. Ollis, Dependence of the kinetics of liquid-phase photocatalyzed reactions on oxygen concentration and light intensity, *Journal of Catalysis*. 243 (2006) 1-6.

- [62] D.F. Ollis, Kinetic disguises in heterogeneous photocatalysis, *Topics in catalysis*. 35 (2005) 217-223.
- [63] D.F. Ollis, E. Pelizzetti, N. Serpone, Photocatalyzed destruction of water contaminants, *Environ. Sci. Technol.* 25 (1991) 1522-1529.
- [64] M. Behnajady, N. Modirshahla, R. Hamzavi, Kinetic study on photocatalytic degradation of CI Acid Yellow 23 by ZnO photocatalyst, *J. Hazard. Mater.* 133 (2006) 226-232.
- [65] O. Tokode, R. Prabhu, L.A. Lawton, P.K.J. Robertson, Mathematical modelling of quantum yield enhancements of methyl orange photooxidation in aqueous TiO₂ suspensions under controlled periodic UV LED illumination, *Applied Catalysis B: Environmental*. 156 (2014) 398-403.
- [66] P. Xiong, J. Hu, Inactivation/reactivation of antibiotic-resistant bacteria by a novel UVA/LED/TiO₂ system, *Water Res.* 47 (2013) 4547-4555.
- [67] O. Tokode, R. Prabhu, L.A. Lawton, P.K. Robertson, The effect of pH on the photonic efficiency of the destruction of methyl orange under controlled periodic illumination with UV-LED sources, *Chem. Eng. J.* 246 (2014) 337-342.
- [68] E. Korovin, D. Selishchev, A. Besov, D. Kozlov, UV-LED TiO₂ photocatalytic oxidation of acetone vapor: Effect of high frequency controlled periodic illumination, *Applied Catalysis B: Environmental*. 163 (2015) 143-149.
- [69] X. Zhang, Y.L. Chen, R. Liu, D.P. Tsai, Plasmonic photocatalysis, *Reports on Progress in Physics*. 76 (2013) 046401.

(a)

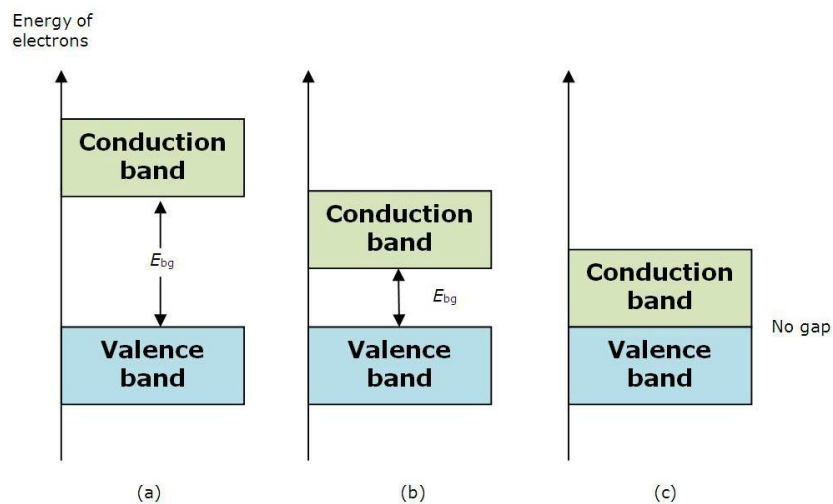

(b)

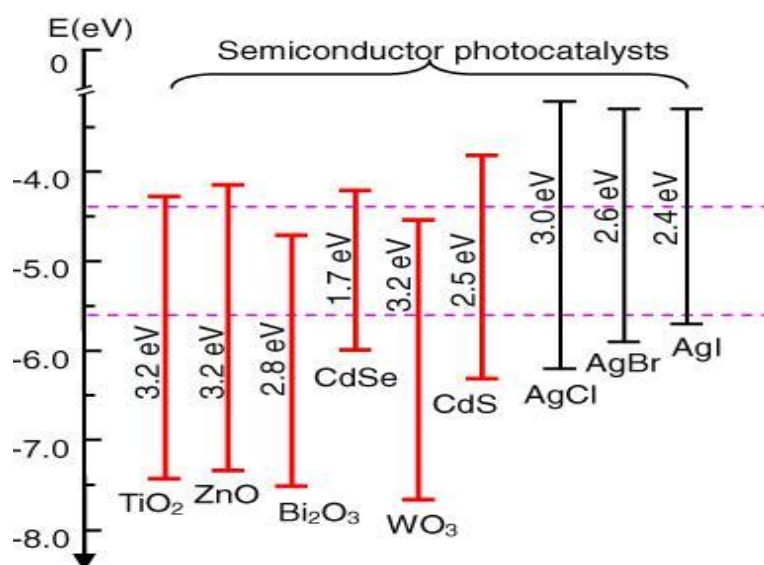


Figure 1: (a) Energy bands in solids: (a) insulator, (b) semiconductor, (c) conductor; (b) band gaps of common semiconductor photocatalysts [Reprinted with permission from [69]. Copyright 2013, IOP publishing].

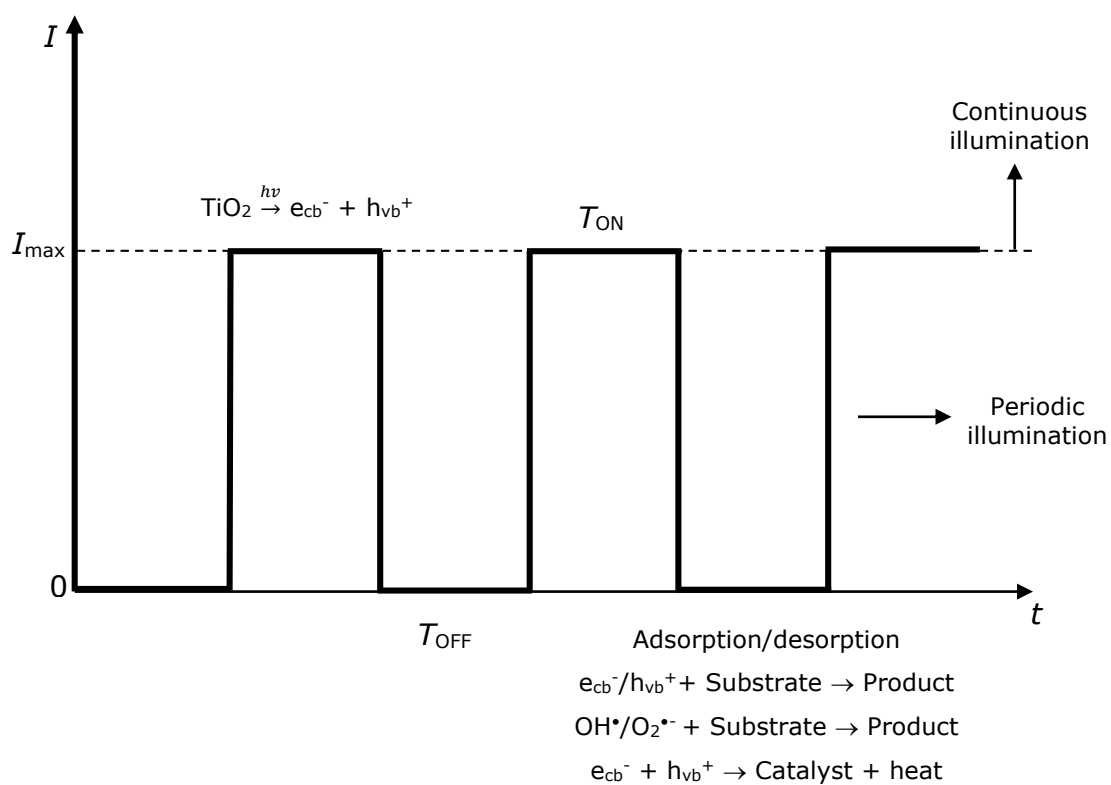


Figure 2: Schematic of CPI according to the original hypothesis by Sczechowski and co-workers.

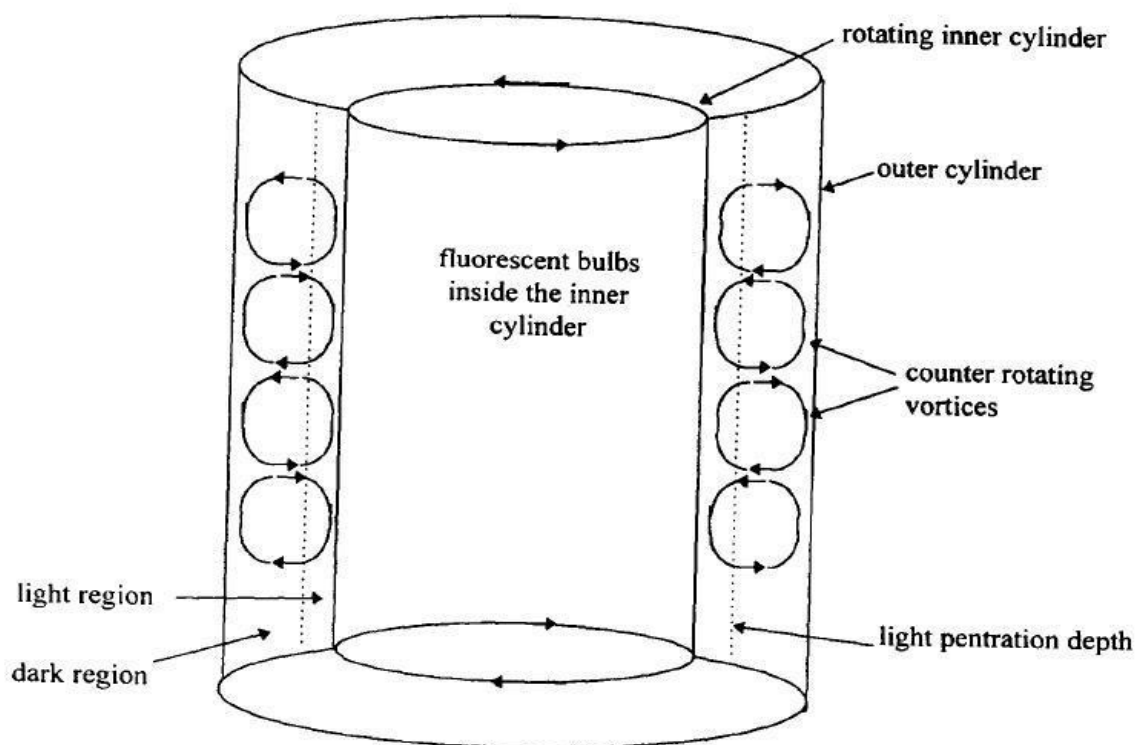


Figure 3: A section through a TVR during operation [Reprinted with permission from [46]. Copyright 1995, Elsevier].

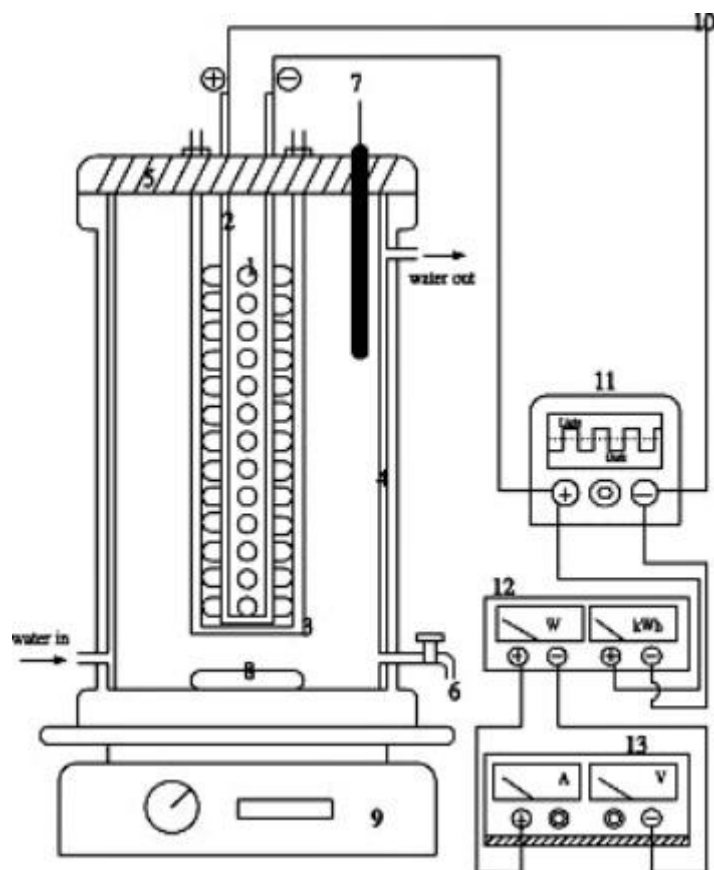


Figure 4: UV LED illuminated photoreactor designed by Chen *et al.* [Reprinted with permission from [56]. Copyright 2007, Elsevier].

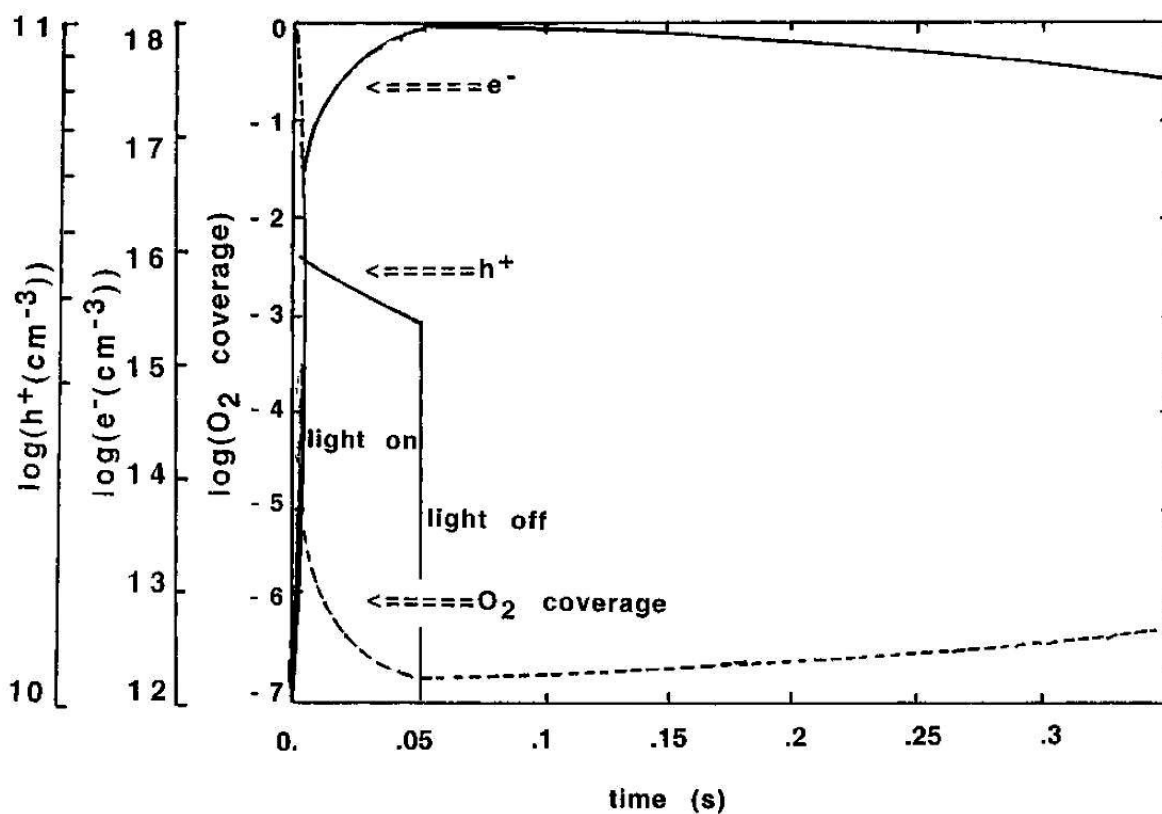


Figure 5: Calculation of dioxygen and net charge concentration as a function of time by Upadhyaya and Ollis. [Reprinted with permission from [59]. Copyright 1997, American Chemical Society].



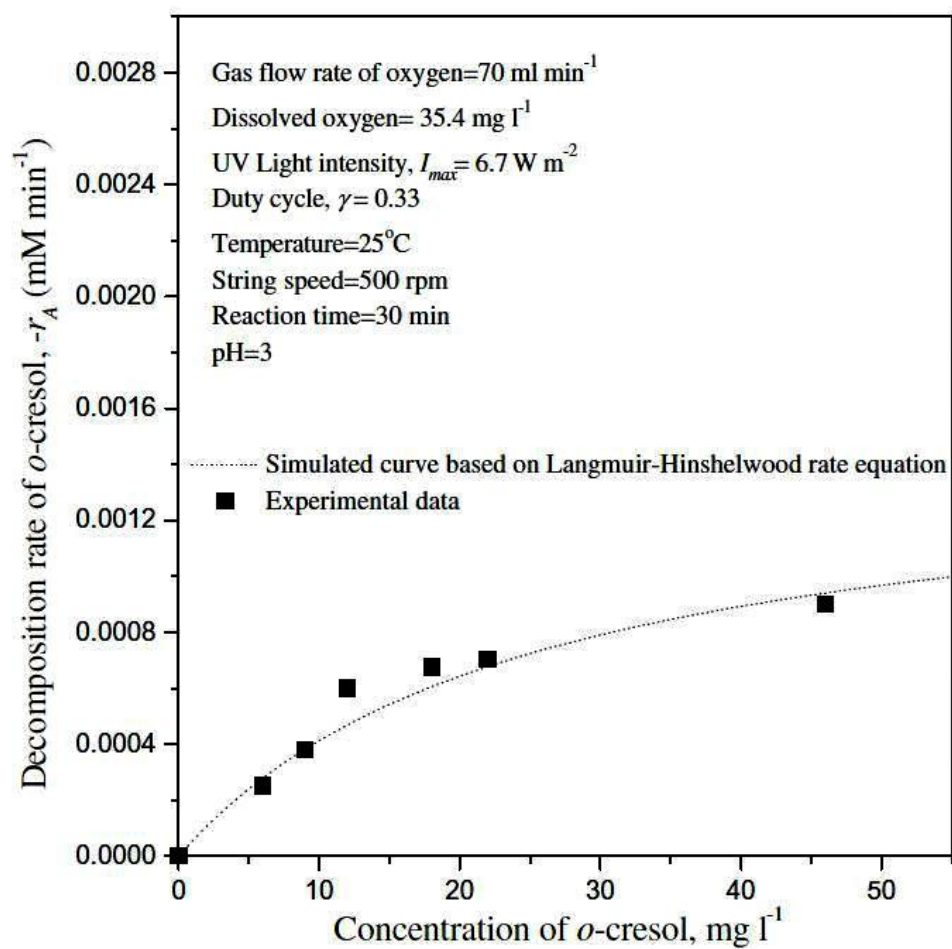


Figure 6: Rate comparison between experimental data and L-H CPI model by Chen *et al.* [Reprinted with permission from [56]. Copyright 2007, Elsevier].

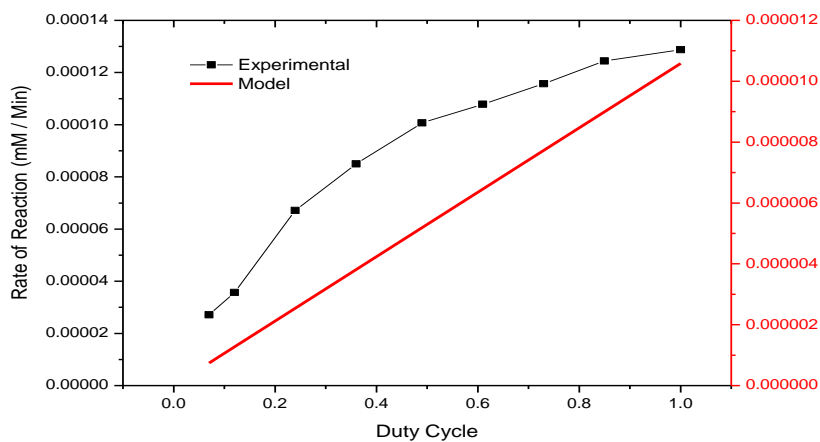

(a)

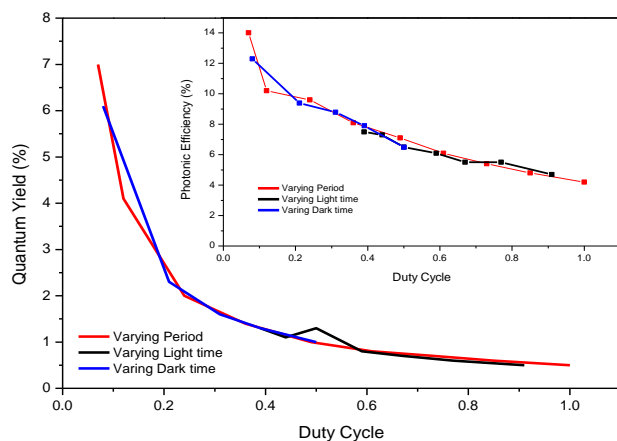

(b)

Figure 7: Comparison between experimental and model data for (a) L-H CPI rate model, (b) quantum yield CPI model. [Reprinted with permission from [65]. Copyright 2014, Elsevier].

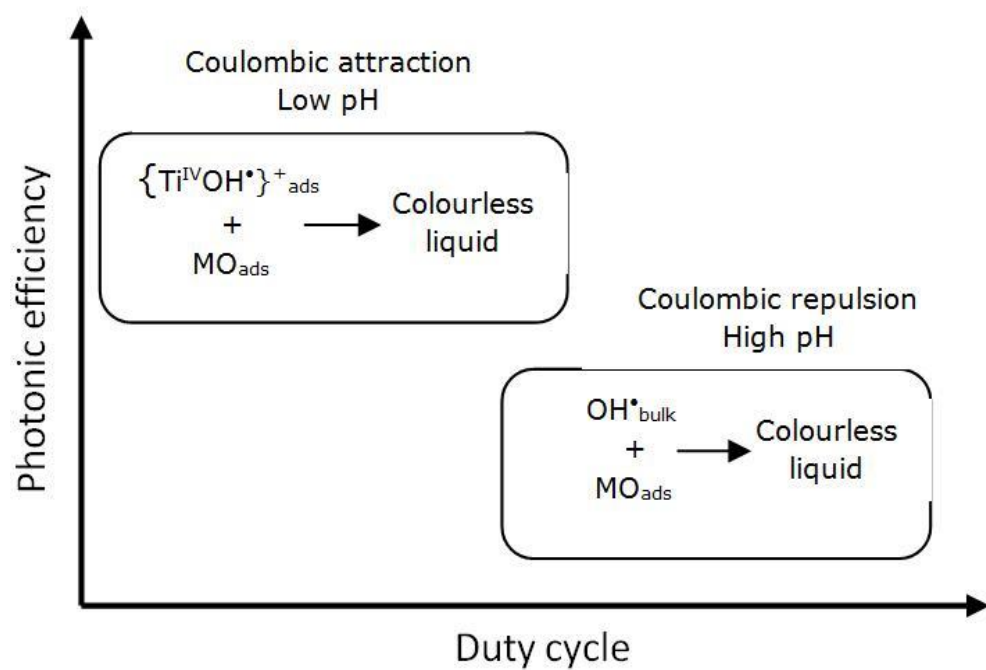


Figure 8: Photonic efficiency regimes due to the triple effect of pH, γ and oxidizing species.

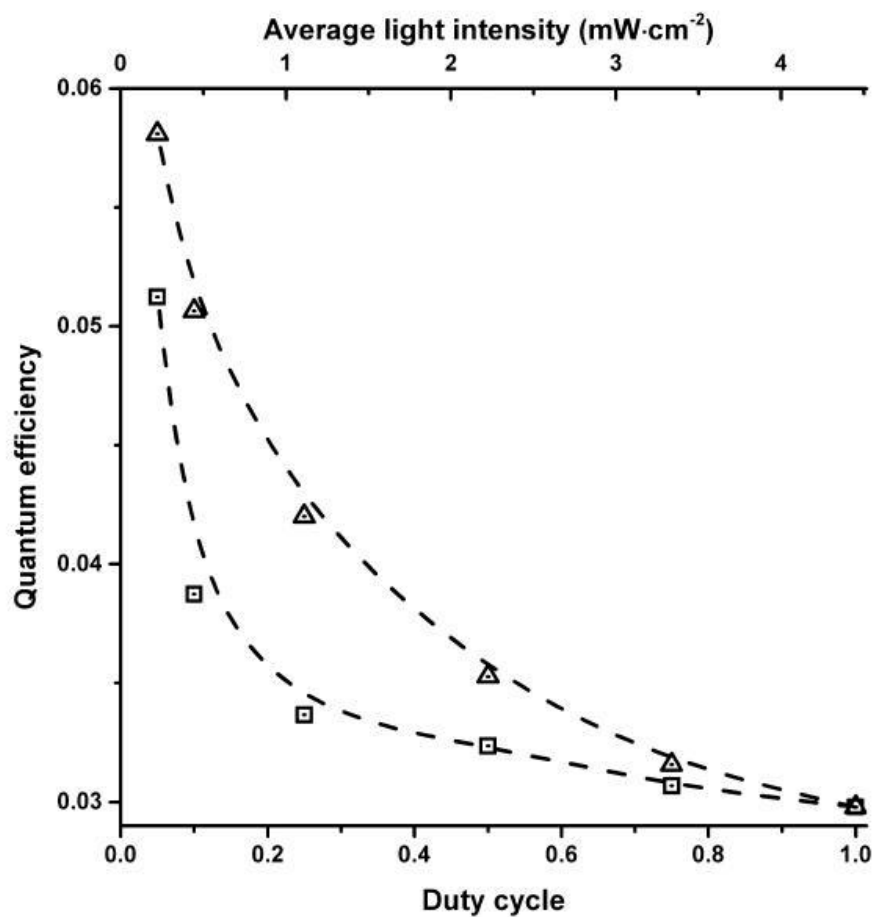


Figure 9: Comparison between photonic efficiencies under CPI (box) and continuous illumination (triangle) at equivalent average light intensities by Korovin *et al.*

[Reprinted with permission from [68]. Copyright 2015, Elsevier].

Table 1: Characteristic times of primary processes in semiconductor photocatalysis of TiO₂.

PRIMARY PROCESS	CHARACTERISTIC TIMES
Charge-carrier generation	
$\text{TiO}_2 + h\nu \rightarrow \text{h}_{\text{vb}}^+ + \text{e}_{\text{cb}}^-$	Very fast (fs)
Charge-carrier trapping	
$\text{h}_{\text{vb}}^+ + \text{Ti}^{\text{IV}}\text{OH} \rightarrow \{\text{Ti}^{\text{IV}}\text{OH}^*\}^+$	Fast (10 ns)
$\text{e}_{\text{cb}}^- + \text{Ti}^{\text{IV}}\text{OH} \leftrightarrow \{\text{Ti}^{\text{III}}\text{OH}\}$	Shallow trap (100 ps)(dynamic equilibrium)
$\text{e}_{\text{cb}}^- + \text{Ti}^{\text{IV}} \rightarrow \text{Ti}^{\text{III}}$	Deep trap (10 ns) (irreversible)
Charge-carrier recombination	
$\text{e}_{\text{cb}}^- + \{\text{Ti}^{\text{IV}}\text{OH}^*\}^+ \rightarrow \text{Ti}^{\text{IV}}\text{OH}$	Slow (100 ns)
$\text{h}_{\text{vb}}^+ + \{\text{Ti}^{\text{III}}\text{OH}\} \rightarrow \text{Ti}^{\text{IV}}\text{OH}$	Fast (10 ns)
Interfacial charge transfer	
$\{\text{Ti}^{\text{IV}}\text{OH}^*\}^+ + \text{Red} \rightarrow$	Slow (100 ns)
$\text{Ti}^{\text{IV}}\text{OH} + \text{Red}^{\bullet+}$	Very slow (ms)
$\text{e}_{\text{tr}}^- + \text{Ox} \rightarrow \text{Ti}^{\text{IV}}\text{OH} + \text{Ox}^{\bullet-}$	

Table 2: Controlled experiment design used by Tokode *et al.* for studying the CPI effect.

EXPERIMENT	DEPENDENT VARIABLE	INDEPENDENT VARIABLE	CONTROLLED VARIABLE
1	ζ	T_{ON}/T_{OFF}	Period
2	ζ	T_{OFF} / Period	T_{ON}
3	ζ	T_{ON} / Period	T_{OFF}

Table 3: Bibliography of work involving CPI in semiconductor photocatalysis in chronological order

Author	Type/Phase of study	Study	Year
Sczechowski <i>et al.</i>	Experimental/Liquid	CPI hypothesis	1993
Sczechowski <i>et al.</i>	Experimental/Liquid	Photonic efficiency	1993
Sczechowski <i>et al.</i>	Experimental/Liquid	Taylor vortex reactor (TVR)	1995
Stewart and Fox	Experimental/Liquid	Effect of T_{off}	1995
Foster <i>et al.</i>	Experimental/Liquid	Rotating Ring Disk Electrochemistry (RRDE)/ Effect of CPI	1996
Upadhyya and Ollis	Theoretical	Transient kinetic model	1997
Buechler <i>et al.</i>	Experimental/Gaseous	Effect of CPI	1999
Buechler <i>et al.</i>	Experimental/Gaseous	Rotating Disk Reactor (RDR)	1999
Cornu <i>et al.</i>	Experimental/Liquid	Effect of CPI on quantum yield	2001
Buechler <i>et al.</i>	Experimental/Liquid	Mechanism of CPI	2001
Cornu <i>et al.</i>	Experimental/Liquid	Effect of pH on CPI	2003
Wang and Ku	Experimental/Liquid	Effect of CPI	2006
Wang <i>et al.</i>	Experimental/Liquid	Deaggregation concept	2004
Chen <i>et al.</i>	Experimental/Liquid	Effect of CPI on photonic efficiency	2007
Chen <i>et al.</i>	Experimental/Liquid	Effect of CPI	2007
Tokode <i>et al.</i>	Experimental/Liquid	Effect of CPI on photonic efficiency	2012
Xiong and Hu	Experimental/Liquid	Residual disinfection effect	2013
Tokode <i>et al.</i>	Experimental/Liquid	Effect of pH on photonic efficiency	2014
Tokode <i>et al.</i>	Theoretical	CPI modelling	2014
Rasoulifard <i>et al.</i>	Experimental/Liquid	Effect of CPI	2014
Korovin <i>et al.</i>	Experimental/Gaseous	High frequency CPI	2015