



Missouri University of Science and Technology
Scholars' Mine

Materials Science and Engineering Faculty
Research & Creative Works

Materials Science and Engineering

01 Sep 2013

Comment on "Giant Plasticity of a Quantum Crystal"

Caizhi Zhou

Missouri University of Science and Technology, zhouc@mst.edu

Charles J. Olson Reichhardt

Matthias J. Graf

Jungjung Su

et. al. For a complete list of authors, see https://scholarsmine.mst.edu/matsci_eng_facwork/2126

Follow this and additional works at: https://scholarsmine.mst.edu/matsci_eng_facwork

 Part of the [Materials Science and Engineering Commons](#)

Recommended Citation

C. Zhou et al., "Comment on "Giant Plasticity of a Quantum Crystal"," *Physical Review Letters*, vol. 111, no. 11, American Physical Society (APS), Sep 2013.

The definitive version is available at <https://doi.org/10.1103/PhysRevLett.111.119601>

This Article - Journal is brought to you for free and open access by Scholars' Mine. It has been accepted for inclusion in Materials Science and Engineering Faculty Research & Creative Works by an authorized administrator of Scholars' Mine. This work is protected by U. S. Copyright Law. Unauthorized use including reproduction for redistribution requires the permission of the copyright holder. For more information, please contact scholarsmine@mst.edu.

Comment on “Giant Plasticity of a Quantum Crystal”

In their Letter, Haziot *et al.* [1] report a novel phenomenon of giant plasticity for hcp ^4He quantum crystals. They assert that ^4He exhibits mechanical properties not found in classical plasticity theory. Specifically, they examine high-quality crystals as a function of temperature T and applied strain ϵ_{app} , where the shear modulus $\mu = \tau_{\text{app}}/\epsilon_{\text{app}}$ reaches a plateau and dissipation $1/Q$ becomes close to zero; both quantities are reported to be independent of applied stress τ_{app} and strain ϵ_{app} , implying a reversible dissipation process and suggesting dislocation motion by quantum tunneling. At lower T , an increase in μ and $1/Q$ is found, which is argued to be caused by ^3He atoms binding to dislocations, thus pinning them and stiffening the solid.

In this Comment, we show that these signatures can be explained with a classical model of thermally activated dislocation glide without the need to invoke quantum tunneling or dissipationless motion. Recently, we proposed a dislocation glide model in solid ^4He containing the dissipation contribution in the presence of other dislocations with qualitatively similar behavior [2].

In Fig. 1(a), we plot our results for both effective shear modulus $\mu = \tau_{\text{app}}/\epsilon_{\text{app}}$ and the work hardening rate (WHR) $d\tau_{\text{app}}/d\epsilon_{\text{app}}$ at low (2.65×10^{-8}) and high strain (1.0×10^{-7}). The yield strain at 20 mK is 2.72×10^{-8} . In Fig. 1(b), we show the corresponding dissipated plastic energy density dW_p/dt , which is proportional to $1/Q$ in periodic shear-strain measurements. Notably, μ and WHR exhibit the key features observed in Ref. [1]; namely, they decrease at high T . In addition, our model describes the corresponding dissipation at low strain [see Fig. 1(b)], which drops at high T , whereas the dissipation remains small and independent of T at high strain. This low dissipation arises due to the low Peierls stress that permits dislocations to glide freely. However, even in the dislocation freely glide regime, the plastic flow is viscous with finite dissipation. In Fig. 1(c), we plot τ_{app} vs ϵ_{app} at 20 mK to demonstrate that $\tau_{\text{app}}/\epsilon_{\text{app}}$ is nearly independent of ϵ_{app} above the yield point, just as is reported in Ref. [1], which implies a reversible process. Clearly, the presented results contradict the conclusion of Ref. [1], namely, that motion in the giant plasticity regime is dissipationless. Note that recent torsional oscillator studies no longer show evidence for motion without friction or supersolidity [3].

Additional concerns exist with the interpretation of the results of Ref. [1]: (a) anisotropy in the dislocation glide does not prove any kind of quantum effect but can arise classically in perfect crystals with specific glide planes and directions of high atomic density. (b) Reversible plastic flow can exist in clean systems with no cross glide [4] or in ac driven systems [5,6]. (c) The low- T dissipation peak is not sufficient evidence for the process of ^3He

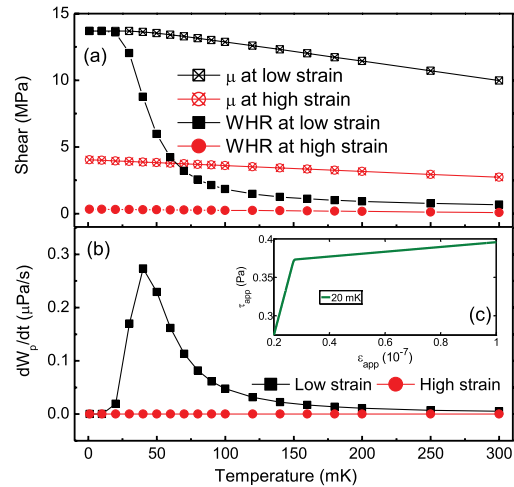


FIG. 1 (color online). (a) Shear modulus and WHR of solid ^4He , (b) dissipated plastic energy density, and (c) stress-strain curve at 20 mK. The model parameters of Ref. [7] were used.

atoms binding to dislocations as T is lowered, as our model results show in Fig. 1(b) for a scenario without ^3He atoms.

In summary, the results in Ref. [1] can be explained with a classical model of dislocation glide and without requiring quantum tunneling or dissipationless motion of dislocations or other exotic processes.

This work was supported by the U.S. DOE at LANL under Award No. DE-AC52-06NA25396 through the LDRD program (C.Z., C.R., and I.J.B.) and the Office of Basic Energy Sciences, Division of Materials Sciences and Engineering (M.J.G. and A.V.B.). C.Z. also received partial support from MRC at MS&T.

C. Zhou,^{1,*} C. Reichhardt,² M. J. Graf,² J.-J. Su,³
A. V. Balatsky,^{2,4} and I. J. Beyerlein²

¹Department of Materials Science and Engineering
Missouri University of Science and Technology
Rolla, Missouri 65409, USA

²Los Alamos National Laboratory
Theoretical Division
Los Alamos, New Mexico 87545, USA

³Department of Electrophysics
National Chiao Tung University
Hsinchu 300, Taiwan

⁴NORDITA
Roslagstullsbacken 23, 106 91 Stockholm, Sweden

Received 11 March 2013; published 13 September 2013

DOI: 10.1103/PhysRevLett.111.119601

PACS numbers: 67.80.de, 62.20.de, 62.20.fq, 67.80.dj

*zhouc@mst.edu

[1] A. Haziot, X. Rojas, A. D. Fefferman, J. R. Beamish, and S. Balibar, *Phys. Rev. Lett.* **110**, 035301 (2013).

[2] C. Zhou, J.-J. Su, M. J. Graf, C. Reichhardt, A. V. Balatsky, and I. J. Beyerlein, *Philos. Mag. Lett.* **92**, 608 (2012).

-
- [3] D. Y. Kim and M. H. W. Chan, *Phys. Rev. Lett.* **109**, 155301 (2012).
- [4] G. Ziegenhain and H. M. Urbassek, *Philos. Mag. Lett.* **89**, 717 (2009).
- [5] D. J. Pine, J. P. Gollub, J. F. Brady, and A. M. Leshansky, *Nature (London)* **438**, 997 (2005).
- [6] M. Lundberg, K. Krishan, N. Xu, C. S. O'Hern, and M. Dennin, *Phys. Rev. E* **77**, 041505 (2008).
- [7] C. Zhou, J.-J. Su, M. J. Graf, C. Reichhardt, A. V. Balatsky, and I. J. Beyerlein, *Phys. Rev. B* **88**, 024513 (2013).