

University of Massachusetts Boston ScholarWorks at UMass Boston

Physics Faculty Publications

Physics

3-9-2009

Practical enhancement of photoluminescence by metal nanoparticles

Greg Sun

University of Massachusetts Boston, greg.sun@umb.edu

Jacob B. Khurgin

Johns Hopkins University

R. A. Soref

Air Force Research Laboratory, Hanscom Air Force Base

Follow this and additional works at: http://scholarworks.umb.edu/physics_faculty_pubs

 Part of the [Physics Commons](#)

Recommended Citation

Sun, Greg; Khurgin, Jacob B.; and Soref, R. A., "Practical enhancement of photoluminescence by metal nanoparticles" (2009). *Physics Faculty Publications*. Paper 15.

http://scholarworks.umb.edu/physics_faculty_pubs/15

This Article is brought to you for free and open access by the Physics at ScholarWorks at UMass Boston. It has been accepted for inclusion in Physics Faculty Publications by an authorized administrator of ScholarWorks at UMass Boston. For more information, please contact library.uasc@umb.edu.

Practical enhancement of photoluminescence by metal nanoparticles

G. Sun, J. B. Khurgin, and R. A. Soref

Citation: *Appl. Phys. Lett.* **94**, 101103 (2009); doi: 10.1063/1.3097025

View online: <http://dx.doi.org/10.1063/1.3097025>

View Table of Contents: <http://apl.aip.org/resource/1/APPLAB/v94/i10>

Published by the [American Institute of Physics](#).

Related Articles

Influence of non-radiative recombination on photoluminescence decay time in GaInNAs quantum wells with Ga- and In-rich environments of nitrogen atoms

J. Appl. Phys. **111**, 063514 (2012)

Spontaneous emission control of single quantum dots in bottom-up nanowire waveguides

Appl. Phys. Lett. **100**, 121106 (2012)

Europium location in the AlN: Eu green phosphor prepared by a gas-reduction-nitridation route

J. Appl. Phys. **111**, 053534 (2012)

Extremely long carrier lifetime over 200ns in GaAs wall-inserted type II InAs quantum dots

Appl. Phys. Lett. **100**, 113105 (2012)

Optical observation of single-carrier charging in type-II quantum ring ensembles

Appl. Phys. Lett. **100**, 082104 (2012)

Additional information on *Appl. Phys. Lett.*

Journal Homepage: <http://apl.aip.org/>

Journal Information: http://apl.aip.org/about/about_the_journal

Top downloads: http://apl.aip.org/features/most_downloaded

Information for Authors: <http://apl.aip.org/authors>

ADVERTISEMENT

NEW!

iPeerReview
AIP's Newest App



**Authors...
Reviewers...
Check the status of
submitted papers remotely!**

AIP | Publishing

Practical enhancement of photoluminescence by metal nanoparticles

G. Sun,^{1,a)} J. B. Khurgin,² and R. A. Soref³

¹Department of Physics, University of Massachusetts Boston, Boston, Massachusetts 02125, USA

²Department of Electrical and Computer Engineering, Johns Hopkins University, Baltimore, Maryland 21218, USA

³Sensors Directorate, Air Force Research Laboratory, Hanscom AFB, Massachusetts 01731, USA

(Received 22 January 2009; accepted 12 February 2009; published online 9 March 2009)

We develop a simple yet rigorous theory of the photoluminescence (PL) enhancement in the vicinity of metal nanoparticles. The enhancement takes place during both optical excitation and emission. The strong dependence on the nanoparticle size enables optimization for maximum PL efficiency. Using the example of InGaN quantum dots (QDs) positioned near Ag nanospheres embedded in GaN, we show that strong enhancement can be obtained only for those QDs, atoms, or molecules that are originally inefficient in absorbing as well as in emitting optical energy. We then discuss practical implications for sensor technology. © 2009 American Institute of Physics. [DOI: 10.1063/1.3097025]

The enhancement of luminescence from various optically active objects of nanoscale dimensions such as atoms, molecules, and quantum dots (QDs) (here we shall use the generic term "molecule" to denote them all) when placed in close proximity to metal nanoparticles¹⁻¹⁰ is a phenomenon that has been conceptually well understood as a product of strong localized electric field induced by the surface plasmons (SPs).¹¹ This enhancement with important applications in sensing has been attributed primarily to the increase in radiative decay rate caused by the Purcell¹² effect associated with the tightly confined high-density SP modes. That treatment is adequate in estimating the enhancement factor for electroluminescence where the excitation energy in the form of an electric dipole gets coupled directly into the SP modes. But for photoluminescence (PL), the situation is more complicated. There are two enhancement mechanisms at work. One takes place during the optical excitation stage and the other during the stage of light emission. In the absence of metal nanoparticles, the optical excitation typically in the form of a focused laser beam is being absorbed by the molecules. With a metal nanoparticle placed in the vicinity of the molecules, the beam can now get coupled first into the tightly confined SP mode enhancing the optical energy density near the molecule field, which enhances the absorption rate. The same SP modes (albeit at different frequencies) can also enhance the energy-emission efficiency of the excited molecules through the Purcell¹² effect. A proper estimate of PL enhancement by metal nanoparticles therefore has to include both energy absorption and emission processes that are enhanced simultaneously by the associated SP modes. To make the matter even more complicated, all of these processes depend on the wavelength relationships between the optical excitation, the molecule emission, and the SP mode. A clear understanding of the enhancement mechanism is obviously important for improving the performance of sensors relying upon PL. Based on the "effective mode volume" approach,¹³ we have previously developed analytical models that rigorously treated the enhancement effects of light emission by molecules in the presence of a metal sheet¹⁴ and metal nanoparticles,¹⁵ as well as light absorption by mol-

ecules in the proximity of metal nanoparticles.¹⁶ Combining the models for light absorption¹⁶ and emission by metal nanoparticles,¹⁵ we are now in position to calculate how much total enhancement one can realistically obtain in measured PL for a given metal embedded in a given dielectric medium. We can also provide an analytical approach for optimizing the metal nanostructure in order to achieve maximum enhancement. The salient feature of our approach is that it shows the attainable PL enhancement that can be optimized for each particular molecule—characterized by the absorption cross section at the excitation frequency $\sigma_a(\omega_{ex})$, the radiative efficiency $\eta_{rad}(\omega_{PL})$, and their product—the PL cross section $\sigma_{PL}(\omega_{ex}, \omega_{PL}) = \sigma_a(\omega_{ex}) \eta_{rad}(\omega_{PL})$.

The enhancement of a PL process is illustrated in Fig. 1. Optical excitation at the frequency of ω_{ex} in the form of a laser beam is focused into the region where a metal nanosphere with a radius r and a molecule separated by a distance d are located. The excitation beam couples into the highly confined SP mode around the metal sphere with an in-coupling coefficient κ_{in} . Energy inside the SP mode is then absorbed by the active molecule with an absorption cross section σ_a . This process competes with radiative (γ_{rad}) and nonradiative decays (γ_{nrad}) of the SP mode. The excited mol-

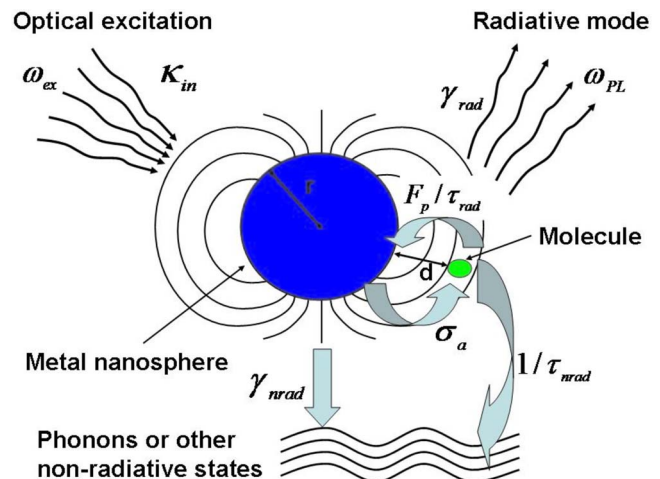


FIG. 1. (Color online) Illustration of the enhancement of a PL process by the incoupling of the optical excitation into the SP mode surrounding a metal sphere and by the outcoupling of the SP mode into the radiative mode.

^{a)}Electronic mail: greg.sun@umb.edu.

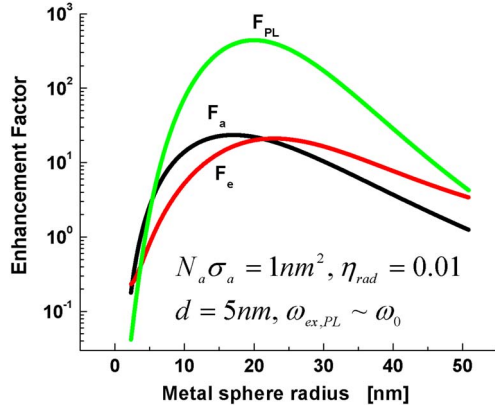


FIG. 2. (Color online) Absorption F_a , emission F_e , and total enhancement factors F_{PL} vs metal sphere radius for Ag/GaN.

ecule with the original radiative decay rate $1/\tau_{rad}$ subsequently relaxes by emitting energy at the frequency ω_{PL} into the SP mode at the rate of F_p/τ_{rad} , which is enhanced by the Purcell¹² factor F_p . Simultaneously, the molecule also relaxes into nonradiative modes at its original nonradiative rate of $1/\tau_{nrad}$. The observed PL power depends on the outcoupling efficiency of the SP mode $\eta_{pr} = \gamma_{rad}/(\gamma_{rad} + \gamma_{nrad})$. It is clear that strong PL enhancement occurs when the frequencies of both optical excitation and emission are close to the SP resonance. It is thus optimal to have the frequency relationship $\omega_{ex} \geq \omega_0 \geq \omega_{PL}$ for PL measurement.

Following our previous work,¹⁶ we first treat the enhancement of absorption by a metal nanosphere. In the absence of the metal nanosphere, the optical excitation will simply be focused onto a diffraction limited spot at the apex of the cone characterized by a far field half angle θ with a spot radius at the waist $w_0 = \lambda_{ex}/\pi\theta$, where λ_{ex} is the excitation wavelength in the dielectric medium. The electric field in the focal spot E_{foc} is related to the power $|s_+|^2$ carried by the incident wave as $|s_+|^2 = \pi n w_0^2 E_{foc}^2 / 4Z_0$, where Z_0 is the impedance of free space and n is the index of refraction. In the presence of a metal sphere with radius r , the incident light gets coupled into the SP mode with an incoupling coefficient $\kappa_{in} \approx \theta\sqrt{3}\gamma_{rad}/8$.¹⁷ The SP mode has a maximum field E_{max} at the surface of the sphere that is related to its energy $|a|^2 = \frac{1}{2}\epsilon_0\epsilon_D E_{max}^2 V_{eff}$, where ϵ_0 is the permittivity of free space, ϵ_D is the dielectric constant of the medium, and $V_{eff} = (4\pi r^3/3)[1 + (2\epsilon_D)^{-1}]$ is the effective mode volume at the resonant frequency ω_0 (wavelength λ_D in the dielectric).¹⁵ The field enhancement is then found from the steady-state solution of the rate equation for the amplitude a of the SP mode that describes the incoupling of the incident wave at the excitation frequency ω_{ex} and the various decay mechanisms,¹³

$$\frac{da}{dt} = j(\omega_{ex} - \omega_0)a - \frac{1}{2}(\gamma_{rad} + \gamma_{nrad} + \gamma_{abs})a + \kappa_{in}s_+, \quad (1)$$

where γ_{nrad} is the rate due to the Ohmic loss in the Drude model approximation, $\gamma_{rad} = [\omega_0/(1+2\epsilon_D)](2\pi r/\lambda_D)^3$ is the radiative decay rate in the dipole approximation,¹⁵ and $\gamma_{abs} = (cN_a\sigma_a/nV_{eff})[r/(r+d)]^6$ is the decay rate due to energy absorption by N_a molecules placed near the sphere. Introducing the Q -factors for the nonradiative decay as $Q_n = \omega_0/[(1+2\epsilon_D)\gamma_{nrad}]$, for absorption as $Q_a = \omega_0/[(1+2\epsilon_D)\gamma_{abs}]$, and the normalized excitation detuning as $\delta_{ex} = 2(1+2\epsilon_D)|\omega_{ex} - \omega_0|/\omega_0$, and taking into account that molecules are situated

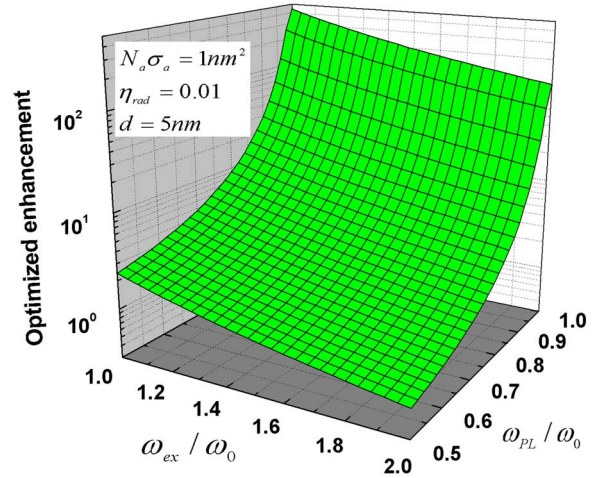


FIG. 3. (Color online) Optimized PL enhancement factor vs frequency detuning ratio of the optical excitation ω_{ex}/ω_0 and PL emission ω_{PL}/ω_0 .

at a distance d away from the metal sphere, we arrive at the energy density (and thus absorption) enhancement factor

$$F_a = \frac{9\epsilon_D}{2} \left(\frac{\omega_0}{\omega_{ex}} \right)^2 \frac{1}{\delta_{ex}^2 + (\chi^3 + Q_n^{-1} + Q_a^{-1})^2} \left(\frac{\chi}{\chi + \chi_d} \right)^6, \quad (2)$$

where we have used the normalized radius $\chi = 2\pi r/\lambda_D$ and distance $\chi_d = 2\pi d/\lambda_D$.

Let us now turn our attention to the enhancement of the emission process. The energy in a molecule with an original radiative efficiency $\eta_{rad} = \tau_{rad}^{-1}/(\tau_{rad}^{-1} + \tau_{nrad}^{-1})$ can be coupled into the SP mode at the PL frequency ω_{PL} into the SP mode according to the rate $F_p(\omega_{PL})/\tau_{rad}$ where the Purcell factor $F_p(\omega_{PL})$ as the ratio of the SP effective density of SP modes $\rho_{SP} = [L(\omega_{PL})/V_{eff}][\chi/(\chi + \chi_d)]^6$ to that of the radiation continuum $\rho_{rad} = 8\pi/(3\lambda_{PL}^3\omega_{PL})$ with the Lorentzian linewidth factor $L(\omega) = [(\gamma_{rad} + \gamma_{nrad})/2\pi]/[(\omega - \omega_0)^2 + (\gamma_{rad} + \gamma_{nrad})^2/4]$ is given as¹⁵

$$F_p(\omega_{PL}) = \frac{9\epsilon_D}{\chi^3} \left(\frac{\omega_0}{\omega_{PL}} \right)^2 \frac{\chi^3 + Q_n^{-1}}{\delta_{PL}^2 + (\chi^3 + Q_n^{-1})^2} \left(\frac{\chi}{\chi + \chi_d} \right)^6, \quad (3)$$

in which the normalized PL detuning $\delta_{PL} = 2(1+2\epsilon_D)|\omega_{PL} - \omega_0|/\omega_0$. The enhancement factor can now be evaluated as

$$F_e = \frac{1 + F_p\eta_{pr}}{1 + F_p\eta_{rad}}, \quad (4)$$

where the radiative outcoupling efficiency of the SP mode $\eta_{pr} = Q_n\chi^3/(1+Q_n\chi^3)$. Finally, combining the two sequential enhancement processes given by Eqs. (2) and (4), we arrive at the total PL enhancement factor $F_{PL} = F_a F_e$ that shows a rather complicated dependence on one adjustable parameter—the size of nanoparticle χ . This dependence can be traced to the fact that nanoparticles play two mutually exclusive roles—that of antenna for efficient in- and outcoupling of energy and that of a nanocavity for energy concentration. An efficient antenna requires a large dipole, while a high concentration of energy calls for a small nanocavity. Therefore, for each combination of χ_d , N_a , σ_a , and η_{rad} , there exists an optimum size χ that maximizes PL enhancement.

It is not difficult to see that the largest enhancement can be obtained only for a small number of molecules placed very close to the metal sphere, $\chi_d \ll \chi$, with a small absorption cross section, $Q_a \gg Q_n$, and a small original radiative

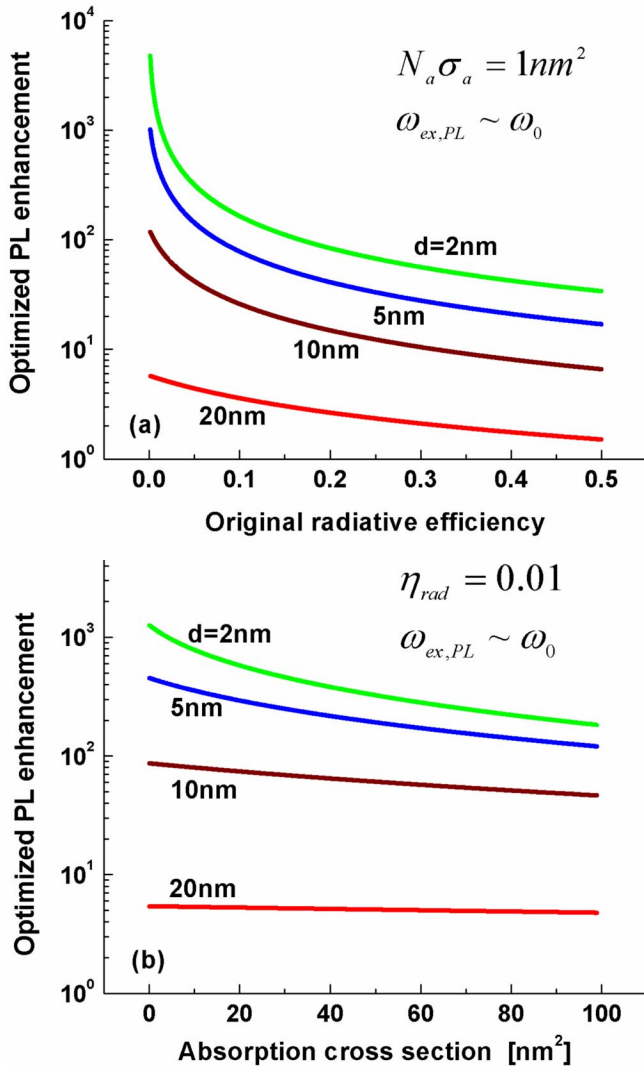


FIG. 4. (Color online) Optimized PL enhancement as a function of (a) original radiative efficiency η_{rad} at fixed $N_a \sigma_a = 1 \text{ nm}^2$ and (b) absorption cross section $N_a \sigma_a$ at fixed $\eta_{\text{rad}} = 0.01$ for several values of the molecule-metal spacing d and near resonance optical excitation and PL emission.

efficiency, $F_P \eta_{\text{rad}} \ll 1$, when both excitation and PL frequencies are close to SP resonance, $\omega_{\text{ex,PL}} \sim \omega_0$. Under these favorable conditions, we obtain $F_{\text{PL}} \approx 81 \varepsilon_D^2 / [2(\chi^3 + Q_n^{-1})^4]$, indicating that for a small metal sphere, $\chi^3 Q_n \ll 1$, the maximum enhancement factor $F_{\text{PL,max}} \approx 81 \varepsilon_D^2 Q_n^4 / 2$ in line with what a simple electrostatic analysis predicts. For a Ag nanoparticle embedded in GaN ($Q_n = 2.77$, $\varepsilon_D = 5.81$, and $\hbar \omega_0 = 2.344 \text{ eV}$), $F_{\text{PL,max}} \approx 8.0 \times 10^4$. This is a huge enhancement, but in reality, the PL enhancement is not nearly as significant when the finite absorption cross section and original radiative efficiency of the molecules that are spaced a finite distance away from the metal sphere are taken into account.

Consider the example of InGaN QDs situated at $d = 5 \text{ nm}$ away from a Ag sphere in GaN with $N_a \sigma_a = 1 \text{ nm}^2$ and $\eta_{\text{rad}} = 0.01$. The resulting PL enhancement factor F_{PL} , along with its enhancement contributions from absorption F_a and emission F_e , is shown in Fig. 2, where the optical excitation and emission frequencies are very close to the resonance of SP mode, $\omega_{\text{ex,PL}} \sim \omega_0$. There exists an optimized size of the metal sphere for which maximum enhancement is achieved. Also, as one can see, the two contributions are

roughly of the same order. Figure 3 shows the optimized PL enhancement factor as a function of the detuning of optical excitation $\omega_{\text{ex}}/\omega_0$ and that of PL emission $\omega_{\text{PL}}/\omega_0$ for the same example—which clearly indicates that it is more critical to have the PL emission frequency near resonance with the SP mode. This is because, as shown in Fig. 4, the dependence of PL enhancement on the original radiative efficiency η_{rad} [Fig. 4(a)] is more sensitive than that on the total absorption cross section $N_a \sigma_a$ [Fig. 4(b)]. It is clear that PL enhancement is strong only if the active molecules are both weak absorbers and inefficient emitters being positioned in close proximity to the metal nanoparticles. Note that the condition $\sigma_a \eta_{\text{rad}} \rightarrow 0$ under which the maximum enhancement is achieved is always satisfied for Raman scattering, which can be seen as nothing but PL with a negligibly small cross section; hence $F_{\text{Raman}} \approx F_{\text{PL,max}}$. Indeed the experimentally verified enhancement of Raman scattering is always significantly larger than that for PL.

In summary, we have analytically treated the PL enhancement as a product of two equally important factors—one on the absorption stage and another on the emission stage—and for a given metal-dielectric combination there exists an optimal nanoparticle size that maximizes the combined enhancement. The key conclusion is that metal nanoparticles provide large PL enhancement only for small quantities of the atoms, molecules, or QDs with originally low PL cross section, hence metal nanoparticles can be indispensable in improving sensors but are of limited use in other applications, where PL is already reasonably (a few percent) efficient.

- ¹P. J. Schuck, D. P. Fromm, A. Sundaramurthy, G. S. Kino, and W. E. Moerner, *Phys. Rev. Lett.* **94**, 017402 (2005).
- ²J.-Y. Wang, Y.-W. Kiang, and C. C. Yang, *Appl. Phys. Lett.* **91**, 233104 (2007).
- ³S. Kühn, U. Håkanson, L. Rogobete, and V. Sandoghdar, *Phys. Rev. Lett.* **97**, 017402 (2006).
- ⁴R. Carminati, J.-J. Greffet, C. Henkel, and J. M. Vigoureux, *Opt. Commun.* **261**, 368 (2006).
- ⁵L. Rogobete, H. Schniepp, V. Sandoghdar, and C. Henkel, *Opt. Lett.* **28**, 1736 (2003).
- ⁶C. Girard, O. J. F. Martin, and A. Dereux, *Phys. Rev. Lett.* **75**, 3098 (1995).
- ⁷L. Novotny, *Appl. Phys. Lett.* **69**, 3806 (1996).
- ⁸M. Thomas, J.-J. Greffet, R. Carminati, and J. R. Arias-Gonzalez, *Appl. Phys. Lett.* **85**, 3863 (2004).
- ⁹G. Baffou, C. Girard, E. Dujardin, G. C. des Francs, and O. J. F. Martin, *Phys. Rev. B* **77**, 121101(R) (2008); G. Colas des Francs, C. Girard, T. Laroche, G. Leveque, and O. J. F. Martin, *J. Chem. Phys.* **127**, 034701 (2007).
- ¹⁰R. M. Bakker, V. P. Drachev, Z. Liu, H.-K. Yuan, R. H. Pedersen, A. Boltasseva, J. Chen, J. Irudayaraj, A. V. Kildishev, and V. M. Shalaev, *New J. Phys.* **10**, 125022 (2008).
- ¹¹D. Maystre, in *Electromagnetic Surface Modes*, edited by A. D. Boardman (Wiley, New York, 1982), Chap. 17.
- ¹²M. Purcell, H. C. Torrey, and R. V. Pound, *Phys. Rev.* **69**, 37 (1946).
- ¹³S. Maier, *Opt. Express* **14**, 1957 (2006).
- ¹⁴J. B. Khurgin, G. Sun, and R. A. Soref, *J. Opt. Soc. Am. B* **24**, 1968 (2007); G. Sun, J. B. Khurgin, and R. A. Soref, *Appl. Phys. Lett.* **90**, 111107 (2007).
- ¹⁵J. B. Khurgin, G. Sun, and R. A. Soref, *Appl. Phys. Lett.* **93**, 021120 (2008); G. Sun, J. B. Khurgin, and R. A. Soref, *J. Opt. Soc. Am. B* **25**, 1748 (2008).
- ¹⁶J. B. Khurgin, G. Sun, and R. A. Soref, *Appl. Phys. Lett.* **94**, 071103 (2009).
- ¹⁷H. A. Haus, *Waves and Fields in Optoelectronics*, 1st ed. (Prentice-Hall, Englewood Cliffs, NJ, 1984).