

Liposomal delivery of 5 Fluorouracil and Tretinoin: An Aspect of Topical treatment of skin warts

Entrega liposomal de 5 fluorouracilo y tretinoína: un aspecto del tratamiento tópico de las verrugas cutáneas

Ruchi Tiwari¹, Gaurav Tiwari^{1*}, Ankita Wal¹ and Chitranshu Gupta¹

¹ Department of Pharmaceutical Sciences, Pranveer Singh Institute of Technology, Kalpi road, Bhauti, Kanpur, Uttar Pradesh, India.

<http://dx.doi.org/10.30827/ars.v60i3.7966>

Artículo Original Original Article

Correspondencia Correspondence

Dr. Gaurav Tiwari,
Pranveer Singh Institute of Technology,
Kalpi Road, Bhauti,
Kanpur-208020,
Uttar Pradesh, India.
e-mail: drgauravtiwari81@gmail.com,

Conflicto de interés Competing interest

There is no conflict of interest

Received: 27.09.2018
Accepted: 04.05.2019

ABSTRACT

Background: Tretinoin and 5-fluorouracil are indicated for treatment of various skin disorders and actinic keratosis respectively.

Objective: Present study was focused to design liposomes containing 5- fluorouracil and tretinoin. Design was further optimized by 3² full factorial design.

Methods: Liposomes were prepared by ethanol injection method and evaluated by Transmission Electron Microscopy, percentage entrapment efficiency, zeta potential and *in vitro* drug release. Optimized formulation was subjected to histopathological and stability studies at 4°C, 25°C and 60°C temperatures.

Results: No drug crystals were visible in transmission electron microscopy, regardless of the preparation technique or the loaded drug. Formulation F9 showed maximum drug entrapment of 72.86% and 69.70% for 5-fluorouracil and tretinoin respectively. When phospholipid concentration was increased from 40 to 60 mg/ml, encapsulation efficiencies of formulation increased. Zeta potential and particle size were maintained within range of -19.14 to -25.61 and 100 to 200 nm respectively which facilitated good stability and penetration of liposomes. Dissolution profiles of formulations F1 to F6 showed high amount of drug release (30.6 to 67.42%) at 2 h. Liposomes were not stable at high temperature but formulations were most stable when stored at lower temperature i.e. 4°C.

Conclusion: So, in liposomes both 5-fluorouracil and tretinoin were successfully incorporated and it can be further used for formulation development.

Keywords: 5-fluorouracil; Tretinoin; Liposomes; *in vitro* drug release; 3² experimental design.

RESUMEN

Objetivo: El presente estudio se centró en el diseño de liposomas que contenían 5-fluorouracilo y tretinoína. El diseño fue optimizado por 3² diseño factorial completo.

Metodos: Los liposomas se prepararon mediante el método de inyección de etanol y se evaluaron mediante Microscopía Electrónica de Transmisión, % de eficiencia de encapsulación, potencial zeta y liberación de fármaco *in vitro*. La formulación optimizada se sometió a estudios histopatológicos y de estabilidad a temperaturas de 4°C, 25°C y 60°C.

Resultados: Ningún cristal de los fármacos era visibles en el Microscopía Electrónica de Transmisión, sin importar la técnica de la preparación o el fármaco cargado. La formulación F9 demostró el atrapamiento máximo del fármaco del 72,86% y del 69,70% para 5-fluorouracilo y tretinoína respectivamente. Cuando la concentración del fosfolípido fue aumentada a partir de 40 a 60 mg/ml, las eficiencias de encapsulación de la formulación aumentaron. El potencial de zeta y el tamaño de partícula fueron mantenidos dentro de la gama de -19,14 a -25,61 y 100 a 200 nanómetros respectivamente, que facilitó la buena estabilidad y la penetración de liposomas. Los perfiles de disolución de las formulaciones F1 a F6 mostraron una alta cantidad de liberación de fármaco (30,6 a 67,42%) a las 2h. Los liposomas no eran estables a alta

temperatura, pero las formulaciones eran más estables cuando se almacenaban a una temperatura más baja, es decir, 4 °C.

Conclusiones: Así, en los liposomas, tanto los fármacos 5-fluorouracilo como los tretinoína se incorporaron con éxito y se pueden utilizar para el desarrollo de la formulación.

Palabras clave: 5 fluorouracilo; tretinoína; liposomas; liberación de fármaco in vitro; 3² diseño experimental.

INTRODUCTION

Liposomes are utilized as transporters for both lipophilic and water solvent molecules. Hydrophilic substances are encapsulated in the interior aqueous portions whereas lipophilic substances are entrapped within lipid bilayers. Liposomes as drug delivery frameworks plays a vital role to enhance their therapeutic effect, decrease adverse effects and improve the viability of medications for the treatment of illnesses.⁽¹⁾ Liposomes are as of now increasingly involved in the dermatology, antibody adjuvant, infective ailment, immunology, eye issue, and in tumor treatment. Various improvements have been utilized to target liposomes which lead to drug accumulation at disease sites and reduced distribution to sensitive tissues. Liposomes with enhanced drug delivery to disease locations, by the ability of long circulation residence times, are now achieving clinical acceptance.⁽²⁾ Release rate of different types of drug molecules from liposomes is dependent on the type of drug applied.⁽²⁾ Cholesterol may be included to improve bilayer characteristics of vesicles, increase microviscosity of the bilayers, reduce the permeability of the membrane to water-soluble molecules, stabilize the membrane and increase the rigidity of the vesicles.⁽³⁾ 5-FU is most often prescribed for actinic keratoses and skin warts.^(2,3) It destroys sun-damaged skin cells so the skin appears smoother and more youthful. It works best on face and scalp, and is less

effective on other areas. TTN enhances the effect of 5-FU by peeling off the top layer of skin. It reduces the time required for the course of 5-FU treatment.⁽³⁾

The present study was planned to formulate and evaluate a new combination of 5-FU and TTN for topical administration. The main aim of the study is to attain effective drug concentration at the intended site of action for a sufficient period of time to elicit the response.

MATERIALS

TTN and 5-FU were kindly provided by Curetech Skincare [Baddi, Himachal Pradesh] and Shalaks pharmaceuticals [New Delhi] respectively. Cholesterol and Soy Lecithin were purchased from the Central drug house [New Delhi]. Cellophane membrane (molecular weight cut off 12,000-14,000) was purchased from Qualigens Fine Chemicals [Mumbai, India]. Ethanol and all other chemicals used were of analytical grade.

METHODS

Experimental design

A 3² randomized full factorial design was adopted to optimize the variables. In the design two factors were evaluated, each at 3 levels and experimental trials were at all nine possible combinations using Design Expert Software 10 (State-Ease, inc., Minneapolis, USA). In the present investigation, the concentration of TTN (X1) and concentration of phospholipid (X2) were selected as independent variables. The entrapment efficiency (EE; R1), and cumulative drug release (% CDR; R2) were selected as dependent variables (Table 1). The polynomial equation was generated for the dependent variables. The value of p<0.05 was considered to be significant.^(4,5)

Table 1: 3² Factorial design for preparation of liposomal formulations

Formulation Code#	Independent Variables		Dependent Variables	Zeta Potential (mV)	Particle size (nm)
	X1*	X2\$			
F1	-1	-1	%EE (R1) %DR (R2)	-19.14±2.12	112±2.76
F2	0	-1		-19.99±1.98	100±2.34
F3	+1	-1		-20.10±2.01	148±2.10
F4	-1	0		-24.34±1.87	198±1.99
F5	0	0		-19.89±2.87	200±1.59
F6	+1	0		-21.42 ±1.34	167±2.37
F7	-1	+1		-24.32±1.23	196±2.02
F8	0	+1		-23.99±1.87	182±2.88
F9	+1	+1		-25.61±2.03	191±2.98

*Concentration of TTN, \$Concentration of phospholipid, #All batches contained 500 mg of 5-FU, 4mg/ml cholesterol. Coded values (-1, 0, +1); Actual values (mg/ml) (X1= 0.25, 0.75, 1.0, X2= 20, 40, 60)

Formulation of drug loaded liposomes

Drug loaded liposomes were prepared by a modified ethanol injection method.⁽⁴⁾ Required amounts of phospholipids (20, 40, 60 mg/ml) and cholesterol (4 mg/ml) were dissolved in ethanol and different concentrations of TTN (0.25, 0.75 and 1.0 % w/v) was added to the organic phase individually. Resulting organic phase was injected by means of a syringe pump to aqueous phase (500 mg of 5-FU was added to the aqueous phase) under magnetic stirring at 45 ± 2 °C. Spontaneous liposome formation occurred as soon as the ethanolic solution was in contact with the aqueous phase. Liposome suspension was then kept under stirring for 1h at room temperature to remove the traces of solvent. The unloaded drug was removed by ultracentrifugation of liposome suspension (Beckman, Miami, Florida, USA) at 60,000 rpm for 1 hour and stored at 4°C.^(4,5)

Evaluation of liposomes

Morphological study by transmission electron microscopy (TEM)

Liposome suspensions were imaged by using TEM (Philips CM120; Eindhoven, The Netherlands). A drop of the liposome suspension was placed onto a carbon-coated copper grid, forming a thin liquid film. The films were negatively stained with 2% phosphotungstic acid solution for 1 minute. The excess of phosphotungstic solution was removed with a filter paper and stained samples were characterized by using an accelerating voltage of 80 kV.^(6,7)

Zeta potential study

The particle size and the zeta potential of liposomes were determined by dynamic light scattering (DLS), using the Zetasizer (Malvern instruments, UK). Each sample was measured three times, after which the mean of the values was calculated. The measurement was performed at 25°C after an appropriate dilution with distilled water.⁽¹⁰⁻¹¹⁾

Entrapment efficiency

5ml of liposome formulation was taken and transferred to a 100 ml volumetric flask containing 25 ml of phosphate buffer (skin pH 6.8), then sonicated using an ultrasound bath for few minutes and filtered through a 0.45µm membrane filter. The filtrate was finally diluted with phosphate buffer (pH 6.8) and absorbance was recorded by Shimadzu 1700 UV visible spectrophotometer at 266 and 340 nm respectively for 5-FU and TTN.⁽⁷⁾

In vitro drug release

In-vitro drug release study of liposomal formulations was performed using Franz diffusion cells with diffusional

area of 0.75 cm². An egg membrane was placed between donor and receptor compartments. The receptor compartment contained phosphate buffer pH 6.8 was continuously stirred by magnetic bead and maintained at temperature of 37 ± 1 °C. One ml liposomal suspension was loaded on the donor compartment. The drug concentrations in aliquot were withdrawn at different time intervals and analyzed at 266 nm and 340 nm against appropriate blank for 5-FU and TTN respectively, using UV-Vis spectrophotometer.^(3,5) The kinetics of drug release from liposomes was determined by fitting the appropriate drug release data to zero order, first order, Higuchi equation, Hixson-Crowell equation and the Korsmeyer-Peppas model.⁽⁹⁾

Optimization of liposome using experimental design

Constraints, like maximizing entrapment efficiency and % drug release at the end of 8 hours as well as minimizing the particle size, were set as a goal to select the optimized formulation using Design expert software version 10 (Stat-Ease, Inc., Minneapolis, USA).

Histopathological evaluation of optimized liposome

A section of goatskin was harvested from local commercial supplier to evaluate histopathological condition in the presence of F9 liposomes. Harvested skin was shaved and placed on a Franz diffusion cell filled with phosphate buffer (pH 6.8 ± 0.10). Test group was treated with F9, while control group was treated with blank liposome for about eight hours. Exposed test and control tissues were fixed in 10% v/v neutral buffered formalin (pH 6.6) and were routinely processed in paraffin. Tissue sections of ~ 7 µm were cut on a glass slide and stained with hematoxylin-eosin. These sections were examined under light microscope to detect tissue damage caused by the formulations during the permeation studies.

RESULTS AND DISCUSSION

Evaluation of prepared liposomes

Negative-strain TEM images showed that liposomes obtained were spherical shaped, which could have an impact on drug-release. The particle size of drug-loaded liposomes was found to be 100 – 200 nm (Table 1). No drug crystals were visible in TEM-images, regardless of the preparation technique or the loaded drug (Figure 1).⁽¹²⁾ All liposomes were negatively charged and zeta-potential values varied between -19.14 and -25.61 mV (Table 1), which is considered as an optimal potential for assuring particle stability. It was observed that zeta potential of prepared liposomes has sufficient charge to inhibit aggregation of vesicles.⁽¹³⁾ The average percent drug entrapment efficiency of the nine for-

mulations ranges from 28.57 to 72.86% and 37.88 to 69.70% of 5- FU and TTN respectively, where the Formulation

F9 showed a maximum drug entrapment of 72.86% and 69.70% for 5- FU and TTN respectively.


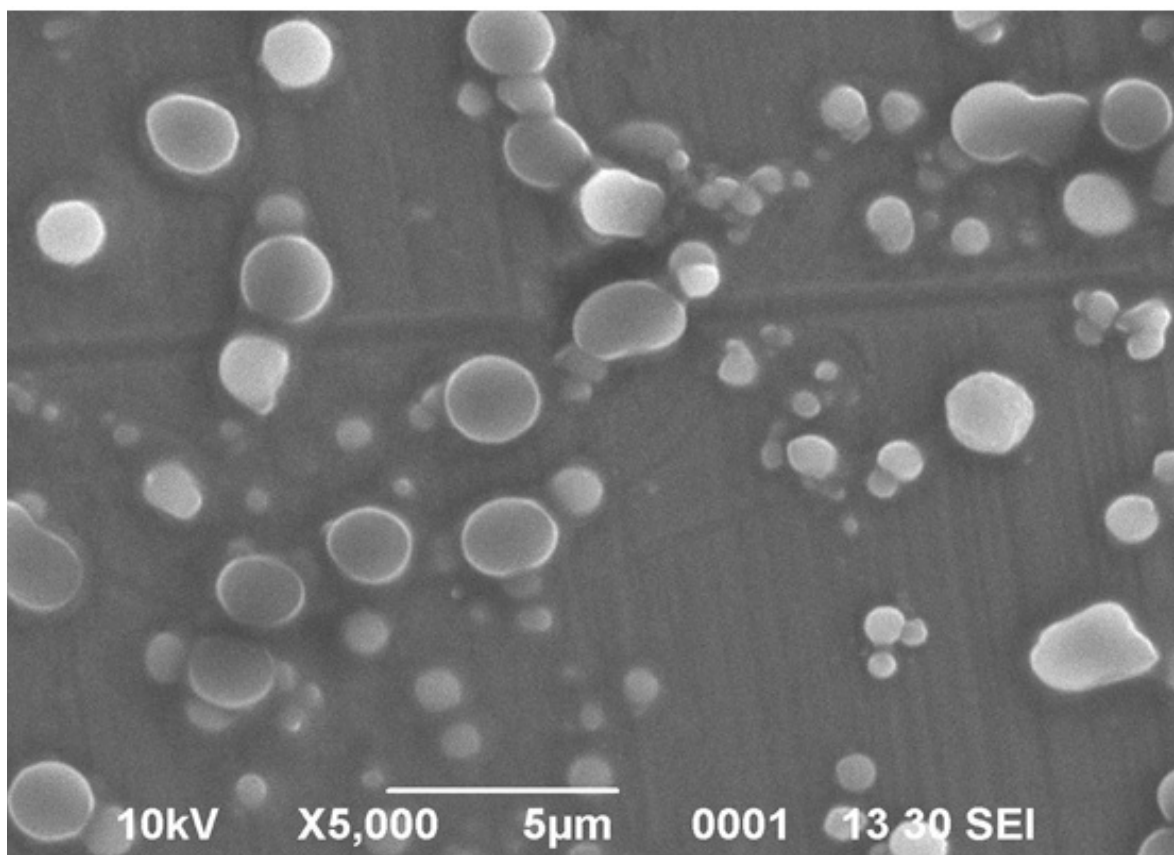


Figure 1: TEM image of formulation F9 at 10 kv, X5,000


In vitro Release Study of Liposomes

The release profiles of liposomes of entire formulations were shown in Figure 2. As the concentration of phospholipid was increased from 20 to 60 mg/ml (Figure 2), using the same cholesterol percentage with respect to phospholipid amount, the cumulative released amount of drugs decreased. It has been stated that the release of lipophilic agents from liposomes is delayed because of their location within the lipid bilayers.⁽¹⁰⁾ From the drug release profile of formulations F2, F5, F8 it was observed that drug release was found to be increased within 2 hrs and very less amount of drug was left for further release. Release profile of formulation F9 showed that almost entire drug was released within 7hrs. The higher amount of phospholipid in F9 leads to a time-dependent increase in diffusion coefficient is a highly lipophilic drug, should be entrapped within the phospholipid bilayers. Hence, the release mechanism involves slow diffusion through the liposome wall. No sudden release occurred during the release study, indicating that no liposome disintegration had taken place.

In vitro dissolution studies showed that as the concentration of phospholipid was increased, drug release rate was decreased. Dissolution profiles of formulations F1 to F6 were not good because high amount of drug release (30.6 to 67.42%) at 2 h. The results of drug release profile of the F9 showed the release of 32.48% of drug during initial 2hrs. While within the first 4 h 61.1% of drug was released and the remaining drug was released during last 4 hrs. Model with the highest correlation coefficient (r^2) was judged to be a more appropriate model for the dissolution data. According to the result obtained by release kinetics in case of 5- FU formulations F1, F3, F4, F5, F7, and F8 followed the korsmeyer- peppas model, F2&F6 Hixson model, and F9 zero order kinetics. In case of TTN F1, F3, F5,F6, F8&F9 followed korsmeyer- peppas model, F2&F7 zero and F4 Higuchi kinetics.⁽¹⁶⁾

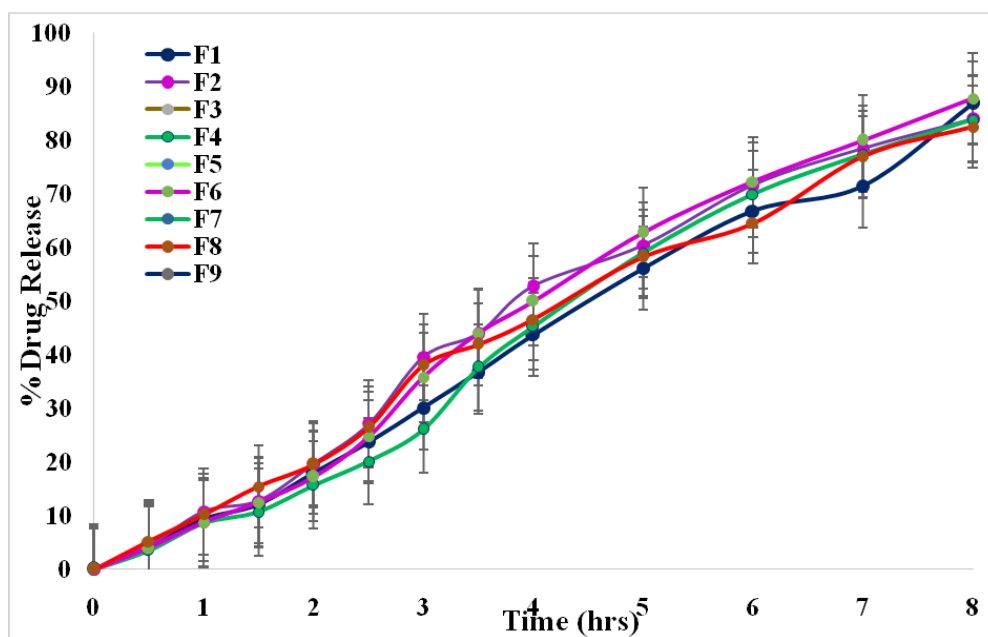

(A)

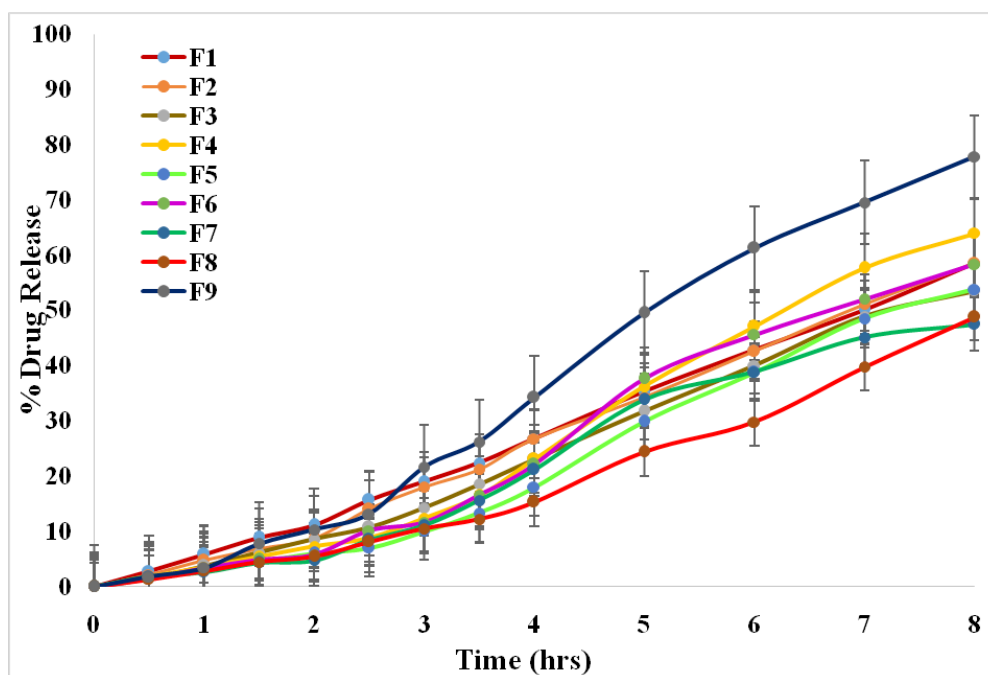

(B)

Figures 2: Drug Release profiles of (A) 5- FU and (B) TTN

Optimization of Liposome Formulation Using 3² Full Factorial Design

A 3² full factorial design was constructed to study the effect of TTN concentration (X₁) and phospholipid concentration (X₂) on the drug release from liposomal preparations. The percentage entrapment efficiency at pH 6.8 (R₁) and percentage drug release (R₂) was selected as dependent variables. The main effects (X₁ and X₂) represent the average result of changing one factor at a time from its low to high

value. The statistical model incorporating interactive and polynomial terms was utilized to evaluate the responses. The interaction terms (X₁, X₂) showed how the response changes when 2 factors are changed simultaneously. The full Equation (equation containing only statistically significant terms) is then used for drawing plots to visualize the impact of changing variables at a glance. The optimum point may be identified from the plot.

The factorial equation for R1 (Eq 1) and R2 (Eq2) was found to be:

$$R1 = 7.87 + 0.47x1 + 0.47x2 + 0.67x1x2 + 0.67x1 + 0.67x2^2$$

..... Eq 1

$$R2 = 51.07 + 0.47x1 + 0.47x2 + 0.67x1x2 + 0.67x1 + 0.67x2^2$$

..... Eq 2

The coefficient of X1 and X2 was found to be positive indicated that predicted values could be obtained when the concentration of TTN and phospholipid increased. The p value for variable X1 and X2 was 0.0231 and 0.0112 respectively (P<0.0500) indicated that both independent variables showed a significant effect on dependent variable i.e. R1 and R2. The prediction error in the response parameters ranged between 0.47 and 0.79% to the value of the absolute error of 0.90±0.70%. The low values of error indicate the high prognostic ability of factorial equation and counter plot methodology. "Adeq Precision" measures the signal to noise ratio. A ratio greater than 4 is desirable. The ratio of 7.56 indicates an adequate signal. Thus, this model

can be used to navigate the design space⁽⁶⁾. From the plot, the spread of points on the right side of the graph (where X1 is low) is larger than the spread between the points at the left side of the graph where X1 is high. In other words, the effect of X2 is less significant where X1 is high (Figure 3(A)).^(17,18) Therefore, at a very high X1 value, the effect of phospholipid concentration can be significantly reduced, thus reducing the R1 and R2. Ramps (Figure 3(B)) indicated that response R1 increases with a decrease in X1 and X2.⁽¹⁹⁾ Higher X1 and X2 reduced response R1. Ramps report clearly supported optimized formulation. After generating the polynomial equation for the dependent and independent variables, the combination was optimized for responses.⁽²⁰⁾ Formulations with high X1 and X2 showed highest desirability factor of 1.00 with highest R1 and R2 was selected as optimized formulation (Figure 3(C)). The Response Surface linear model generated for X1 and X2 was found to be significant with an F-value of 2.50 and 6.80 (P<0.0500) respectively.

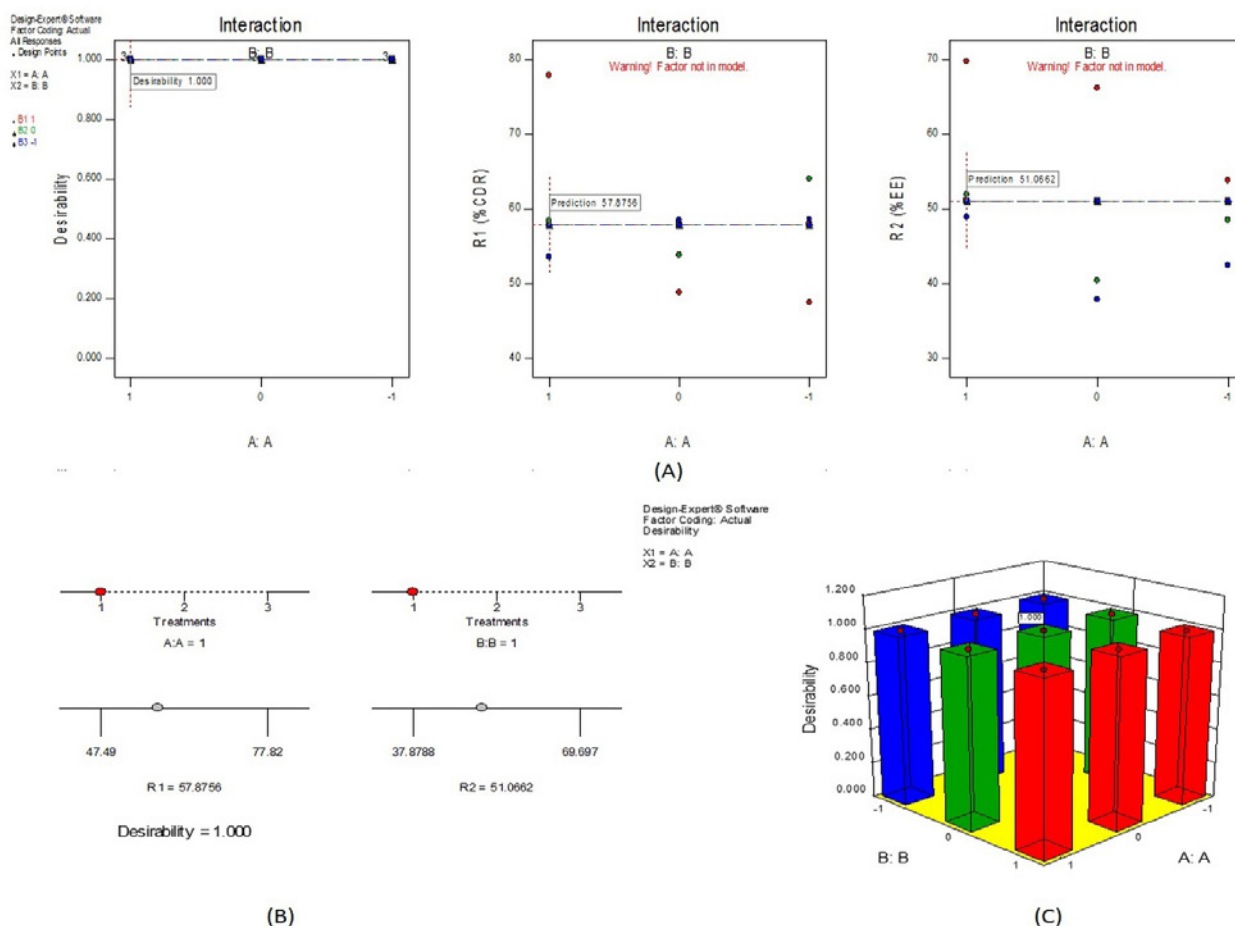


Figure 3: Graphs showing experimental design (A) Interaction of R1 and R2; (B) Ramps for Desirability; (C) 3D graph for optimization of independent variables

The histopathology results demonstrated the safety profile of developed F9 liposomes (Figure 4). The developed liposome F9 revealed no signs of damage to epithelial cells of goatskin.

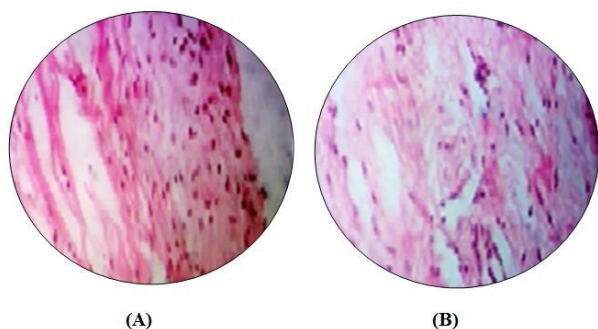


Figure 4: Histopathology of goatskin treated with (A) control and; (B) F9 liposome formulation

CONCLUSION

In this study, liposomes containing 5- FU and TTN were prepared with different proportions of TTN and phospholipid using modified injection method. Liposomes composed of 1.0 mg/ml of TTN and 60 mg/ml phospholipid presented higher % entrapment efficiency and 30 days stability. Particle size of liposomes remained smaller than 200 nm, making them suitable for topical application. Results suggested that liposomes gradually release 5- FU and TTN and found to be topically safe as tested by histological evaluation. Prepared liposomes containing 5-FU and TTN may be successfully used for treatment of skin warts with high patient compliance.

REFERENCES

- Akhtar N. Vesicles: A Recently Developed Novel Carrier for Enhanced Topical Drug Delivery. *Current Drug Del.* 2014;11:87-97. DOI: 10.2174/15672018113106660064
- Nguyen TL, Nguyen TH and Nguyen DH. Development and In Vitro Evaluation of Liposomes Using Soy Lecithin to Encapsulate Paclitaxel. *Int J Biomat.* 2017;7. DOI:10.1155/2017/8234712
- Yadav D, Sandeep K, Pandey D and Dutta RK. Liposomes for Drug Delivery. *J Biotechnol Biomater.* 2017;7:276. DOI: 10.4172/2155-952X.1000276
- Tiwari R, Tiwari G, Wal P, Wal A and Gupta C. Treatment of warts by topical Retinoids: An Exploration and Meticulosity. *Pharma Times.*2018;9:9-12.
- Akhtar N, Pathak K. Cavamax W7 Composite Ethosomal Gel of Clotrimazole for Improved Topical Delivery: Development and Comparison with Ethosomal Gel. *AAPS pharm Sci Tech.*, 2012; 13(1): 344-355. DOI: 10.1208/s12249-012-9754-y
- Cevc G. *Phospholipids Handbook*, Marcel Dekker, New York, 1992.
- Egbaria K and Weiner N. Liposomes as a topical drug delivery system. *Advanced Drug Delivery Reviews.* 1990;5:287-300. DOI:10.1016/0169-409X(90)90021-J
- Prabhakar P, Samip Sand Shankar G. Formulation development and investigation of domperidone transdermal patches. *Int J Pharm Investig.* 2011;1:240-246. DOI: 10.4103/2230-973X.93008
- Acharya A, Dhakal P and Khadka D. Formulation and Evaluation of Transdermal Gel of Lornoxicam and its Delivery by Passive and Inotophoresis Method: A Comparative Study. *Int J Pharm Sci Res.* 2016;7:810-18. DOI: 10.13040/IJPSR.0975-8232
- Epstein H, Gutman D, Cohen-Sela E, Haber E, Elmalak O, Koroukhov N. Preparation of alendronate liposomes for enhanced stability and bioactivity: *in vitro* and *in vivo* characterization. *AAPS J.*2008;10:505-515. DOI: 10.1208/s12248-008-9060-5
- Mayer LD, Bally MB, Hope MJ, Cullis PR. Techniques for encapsulating bioactive agents in to liposomes. *Chem Phys Lipids.*1986;40:333-345.DOI:10.1016/0009-3084(86)90077-0
- Tiwari R, Tiwari G, Wal P, Wal A and Maurya P. Understanding the Impact of Polymer Ratio and its Concentration on Omeprazole Release from Matrix Tablets: Response Optimization Study. *Int J Drug Del Tech.*2017;7:13-21.
- Batzri S and Korn ED. Single bilayer liposomes prepared without sonication. *BiochimBiophysActa.*1973;16:1015-9. DOI:10.1016/0005-2736(73)90408-2
- Tiwari R, Tiwari G, Wal P, Wal A and Maurya P. Development, Characterization and Transdermal Delivery of Dapsone and an Antibiotic Entrapped in Ethanolic Liposomal Gel for the Treatment of *Lapromatous Leprosy*. *The Open Nanomed J.*2018;5:1-15. DOI: 10.2174/1875933501805010001
- Fang JY, Hong CT, Chiu WT, Wang YY. Effect of liposomes and niosomes on skin permeation of enoxacin. *Int J Pharm.* 2001;219:61-72. DOI:10.1016/S0378-5173(01)00627-5
- Hitzman CJ, Elmquist WF, Wattenberg LW, Wiedmann TS. Development of a respirable, sustained release microcarrier for 5- FU: *in vitro* assessment of liposomes, microspheres, and lipid coated nanoparticles. *J Pharm Sci.* 2006;95:1114-1126. DOI:10.1002/jps.20591
- Juliano RL, Stamp D, McCullogh N. Pharmacokinetics of liposomes encapsulated antitumor drugs and implications for therapy. *Ann N Y Acad Sci.* 1998;308:411-423. DOI:10.1111/j.1749-6632.1978.tb22038.x
- Kesisoglou F, Zhou SY, Niemiec S, Lee JW, Zimmermann EM, Fleisher D. Liposomal formulations of inflammatory bowel disease drugs: local versus systemic drug delivery in a rat

model. Pharm Res. 2005;22:1320-1330. DOI:10.1007/s11095-005-5376-3

19. Ali DS, Fatih H, Erdal C, Zeki O, Ahmet LB and Jülide A. Chitosan film containing fucoidan as a wound dressing for dermal burn healing: Preparation and *in vitro*/*in vivo* evaluation. AAPS Pharm Sci Tech.2007;8:E94-E101. DOI: 10.1208/pt0802039
20. Chiranjeevi C, Muthukumaran M, Krishnamoorthy B. A review on potency of vesicular systems in targeting drug delivery. Res. J. Pharm. Bio. Chem. Sci. 2013;4:156-170.
21. Gregoriadis G, Davis C. Stability of liposomes *in vivo* and *in vitro* is promoted by their cholesterol content and the presence of blood cells. Biochem Bioph Res Co.1979;89:1287-1293. DOI:10.1016/0006-291X(79)92148-X