

## Engineering Conferences International ECI Digital Archives

Electric Field Enhanced Processing of Advanced  
Materials II: Complexities and Opportunities

Proceedings

3-10-2019

# Tensile strength of materials obtained by electric pulse consolidation of powders

Evgeny Grigoryev  
*ISMAN, Russia*

Vladimir Goltsev  
*ISMAN, gvy587@gmail.com*

Andrey Osintsev  
*NRNU MEPhI*

Aleksandr Plotnikov  
*NRNU MEPhI*

Follow this and additional works at: [http://dc.engconfintl.org/efe\\_advancedmaterials\\_ii](http://dc.engconfintl.org/efe_advancedmaterials_ii)

 Part of the [Materials Science and Engineering Commons](#)

### Recommended Citation

Evgeny Grigoryev, Vladimir Goltsev, Andrey Osintsev, and Aleksandr Plotnikov, "Tensile strength of materials obtained by electric pulse consolidation of powders" in "Electric Field Enhanced Processing of Advanced Materials II: Complexities and Opportunities", Rishi Raj, University of Colorado, USA Olivier Guillon, Forschungszentrum Jülich, Germany Hidehiro Yoshida, National Institute for Materials Science, Japan Eds, ECI Symposium Series, (2019). [http://dc.engconfintl.org/efe\\_advancedmaterials\\_ii/29](http://dc.engconfintl.org/efe_advancedmaterials_ii/29)

This Abstract and Presentation is brought to you for free and open access by the Proceedings at ECI Digital Archives. It has been accepted for inclusion in Electric Field Enhanced Processing of Advanced Materials II: Complexities and Opportunities by an authorized administrator of ECI Digital Archives. For more information, please contact [franco@bepress.com](mailto:franco@bepress.com).

## Abstract

For materials obtained by electro pulse consolidation, two methods for determining fracture resistance of thin brittle disks—bend testing on pivot rings and so-called Brazilian test — are comparatively analyzed on the example of such brittle materials as gray cast iron, graphite, SiAlON and alumina. In most cases, good agreement between the results obtained by the above techniques was observed.

**Keywords:** electric pulse consolidation, strength of materials, small specimens, Brazilian test, bending of thin disks on pivot ring

## Bending of thin disks for on the ring support

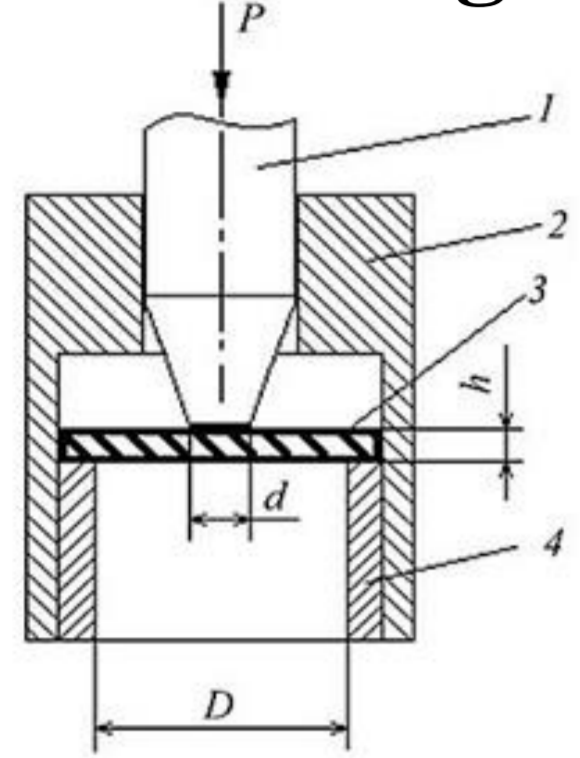


Figure 1. Schematic of bend testing: 1 indenter, 2 ferrule, 3 specimen, 4 pivot ring

$$\sigma_B = \frac{3P_{max}}{8\pi h^2} \left[ 4 - (1-\mu) \left(\frac{d}{D}\right)^2 + 4(1+\mu) \ln \frac{D}{d} \right] \quad (1)$$

In equation (1)  $h$  is the thickness of the disk;  $d$  and  $D$  are the diameters of the punch and support, respectively;  $\mu$  is the Poisson's ratio [1].

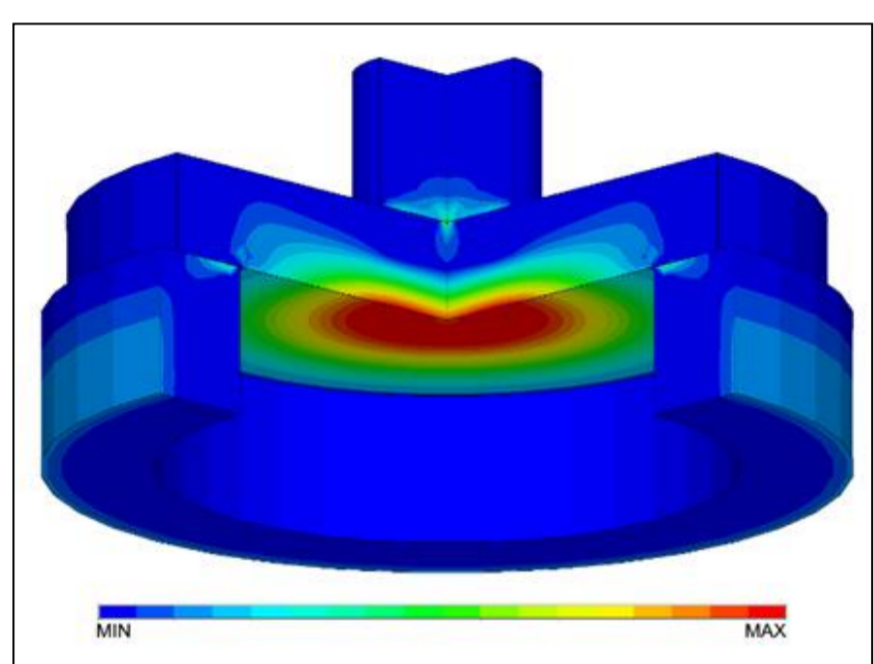


Figure 2. Distribution of main strains during bend testing.

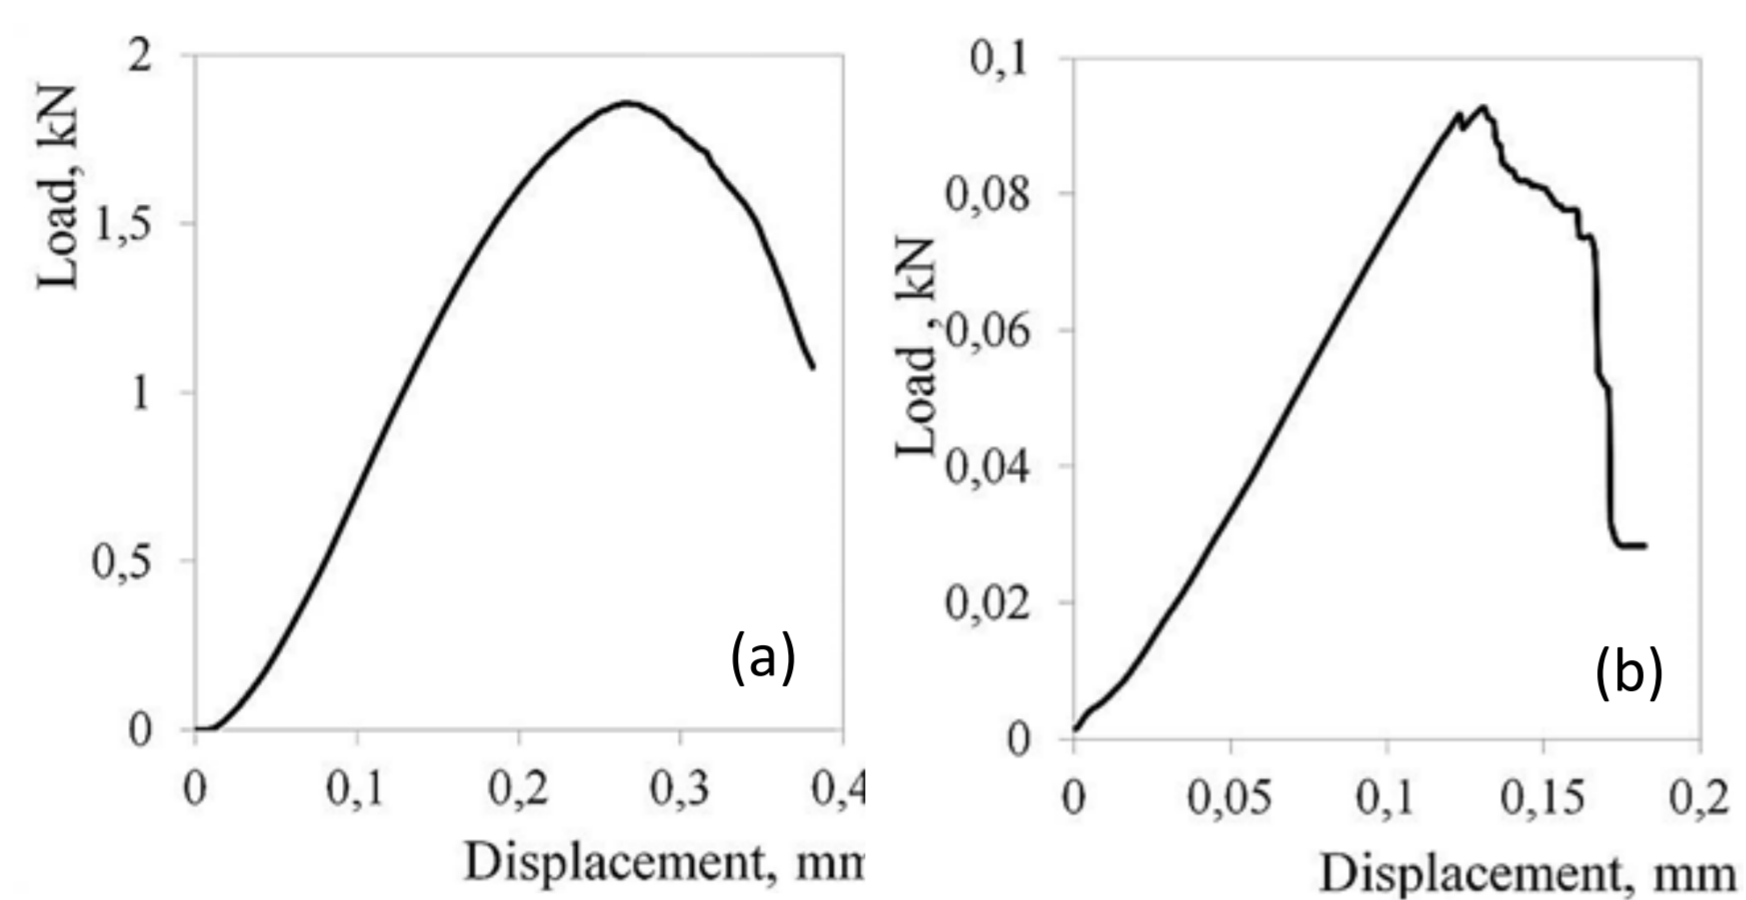


Figure 3. The P- $\delta$  diagrams for bend testing of disks  $D = 10$  mm,  $h = 1.5$  mm of cast iron (a) and graphite (b).

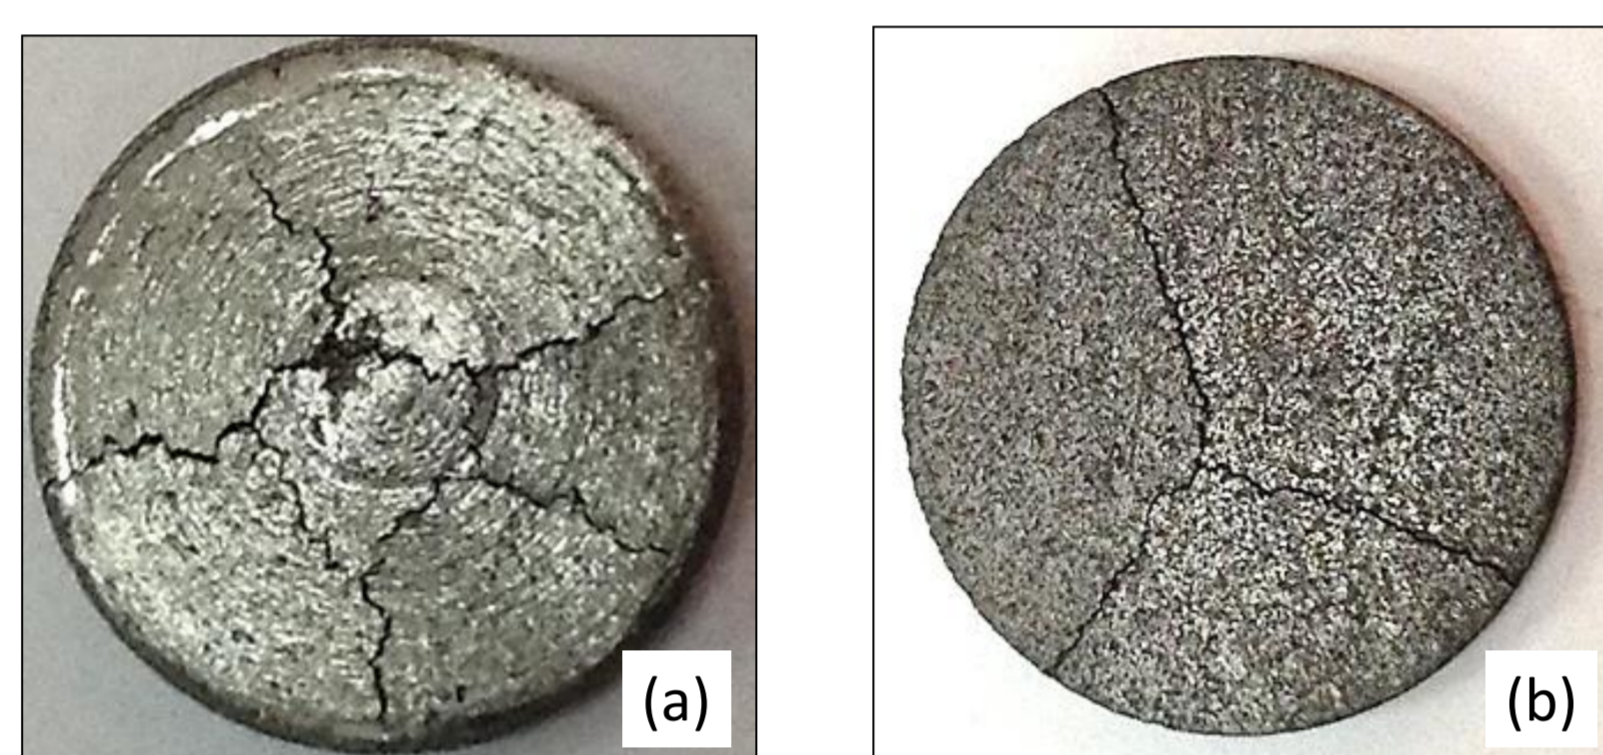


Figure 4. Overall view of plastic cracked cast iron (a) and brittle graphite (b) for disks  $D = 15$  mm.

## Brazilian testing of short cylinders

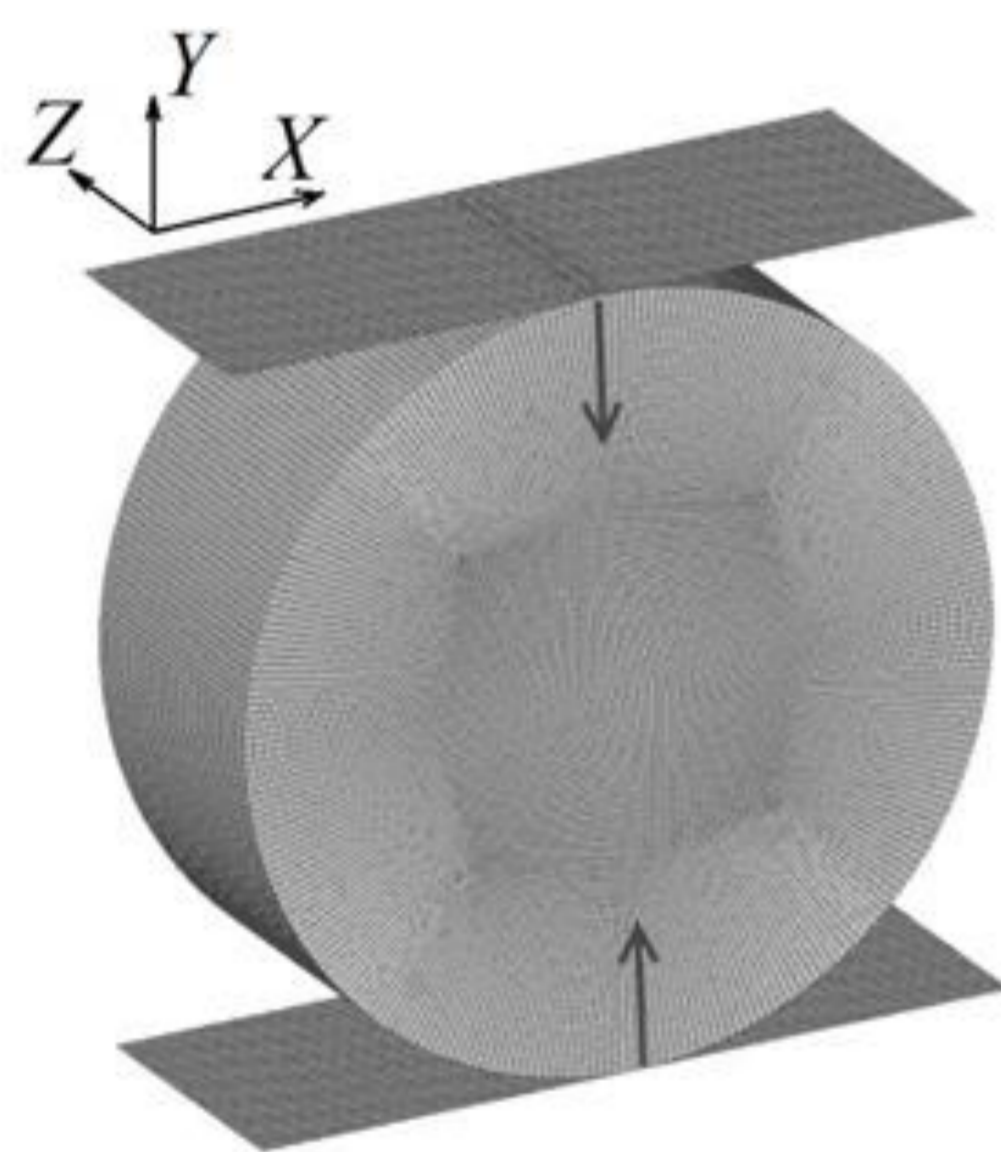


Figure 8. Schematic of Brazilian test.

$$\sigma_t = \frac{2P}{\pi t D} \quad (2)$$

In equation (2)  $P$  is the maximum load sustained by the specimen,  $t$  is the thickness of the specimen,  $D$  is its diameter [2].


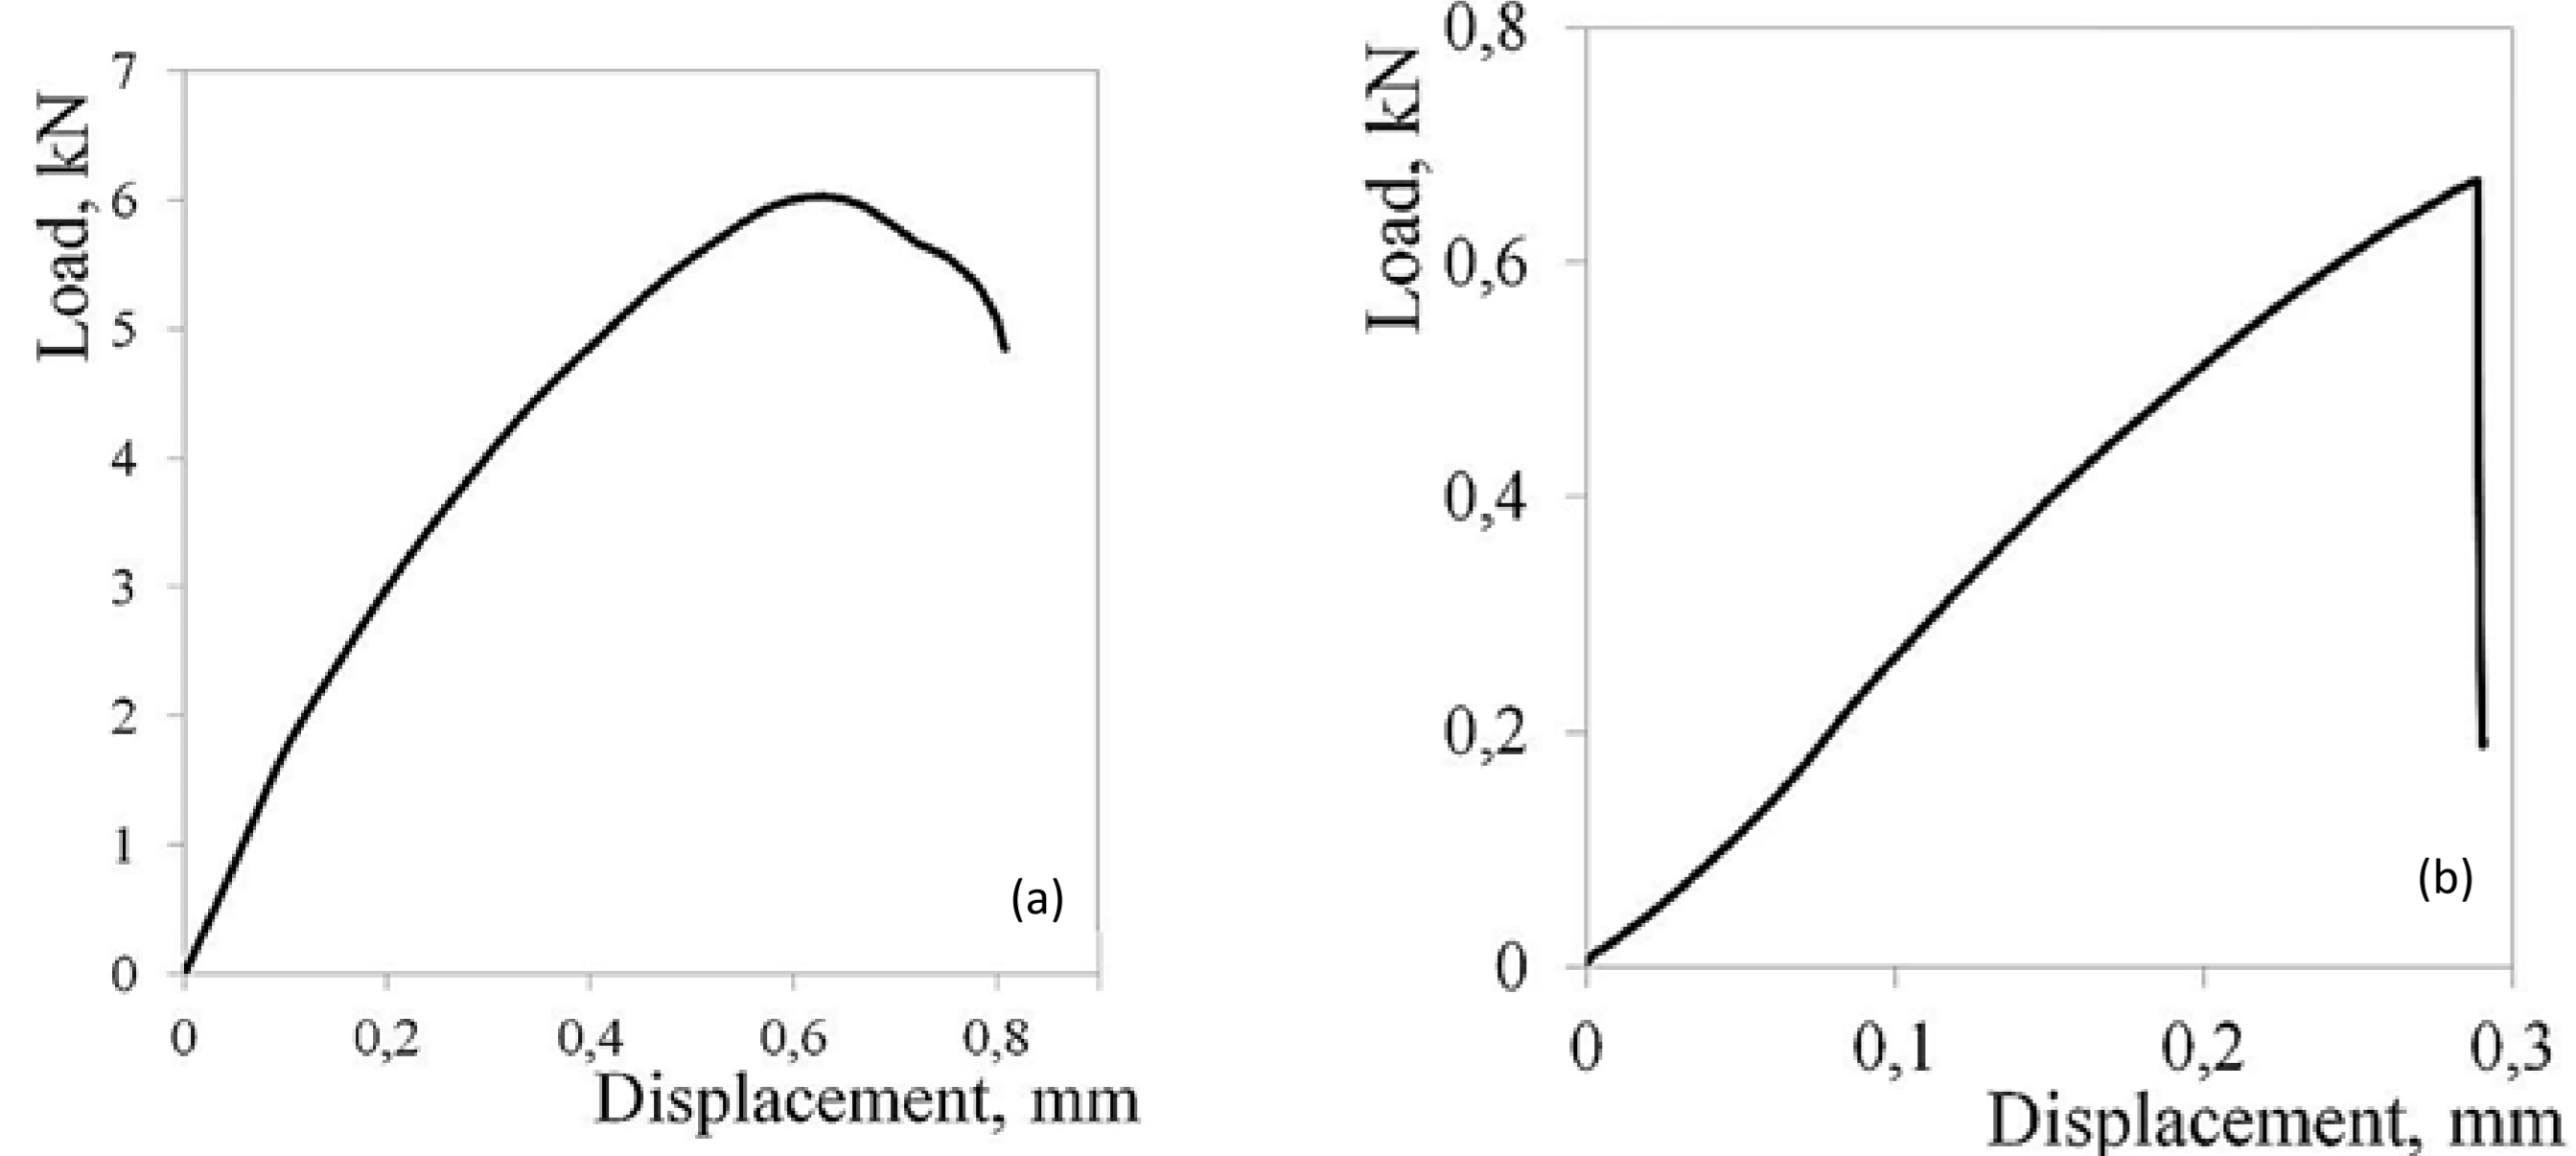


Figure 10. Compression diagrams in Brazilian testing of cast iron 10x4 mm (a) and ARV-1 graphite 8x8 mm (b) disks.

Figure 9. Distribution of compression strain  $\epsilon_x$  (a) and first main stresses (gray areas with  $\sigma_1 < 0$ ) (b) in disk-shaped specimens.

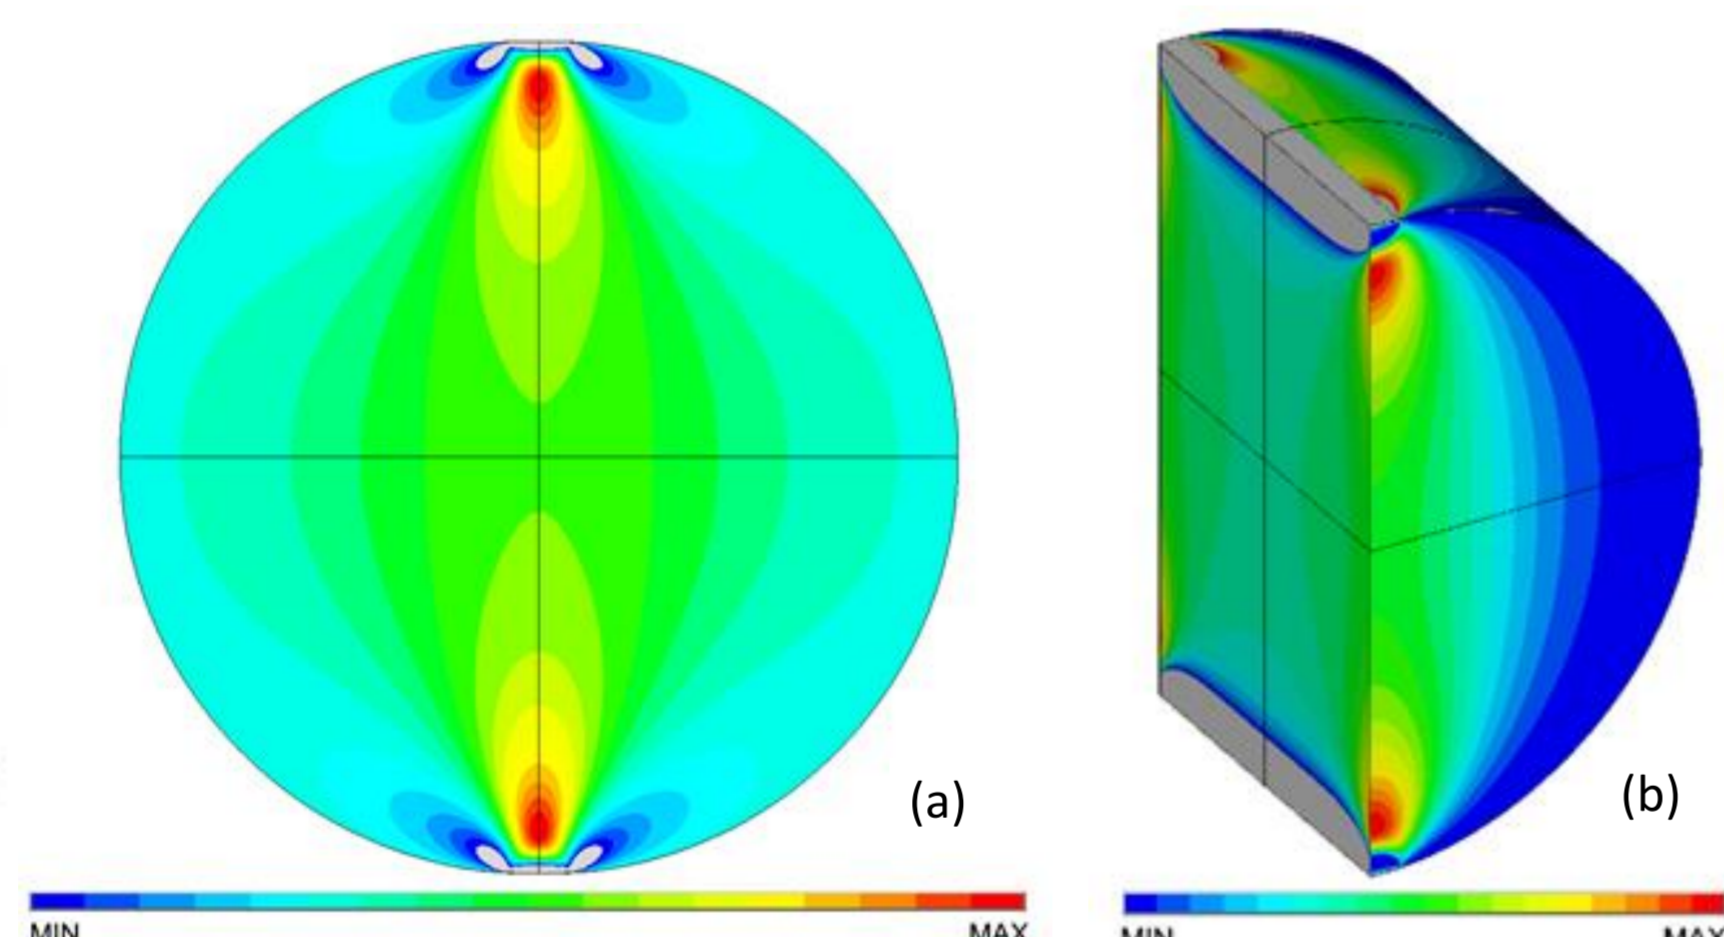

## Samples of heavy alloy WNiFe (90W-7Ni-3Fe) obtained by high-voltage consolidation

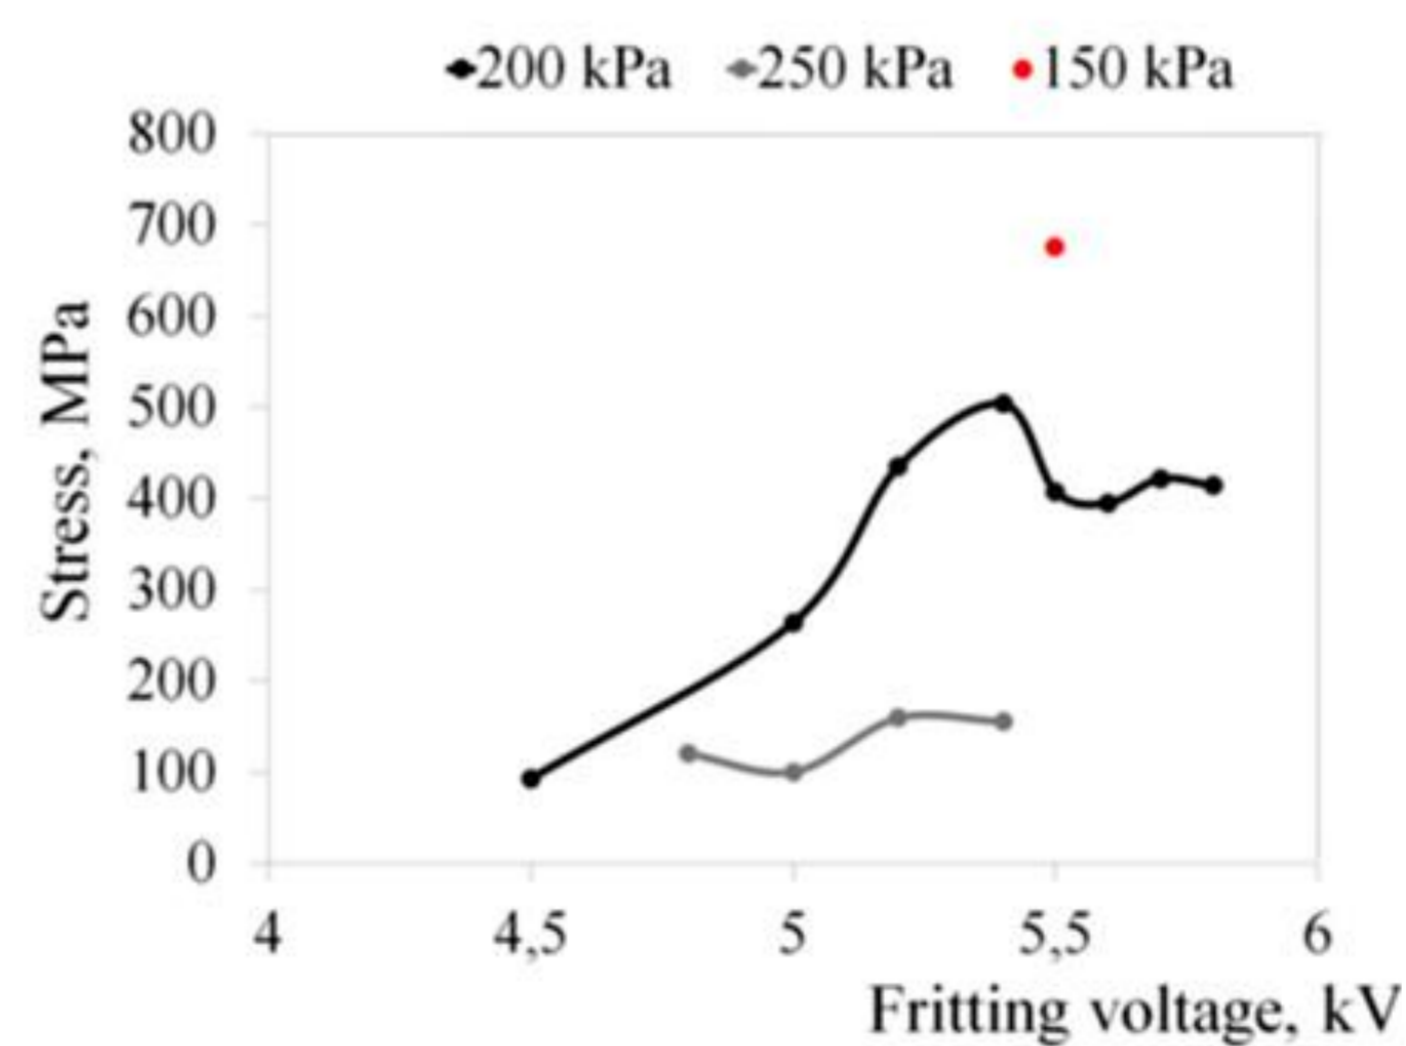


Figure 11. Breaking stress of WNiFe alloys consolidated at 150, 200, and 250 kPa as a function of fritting voltage.

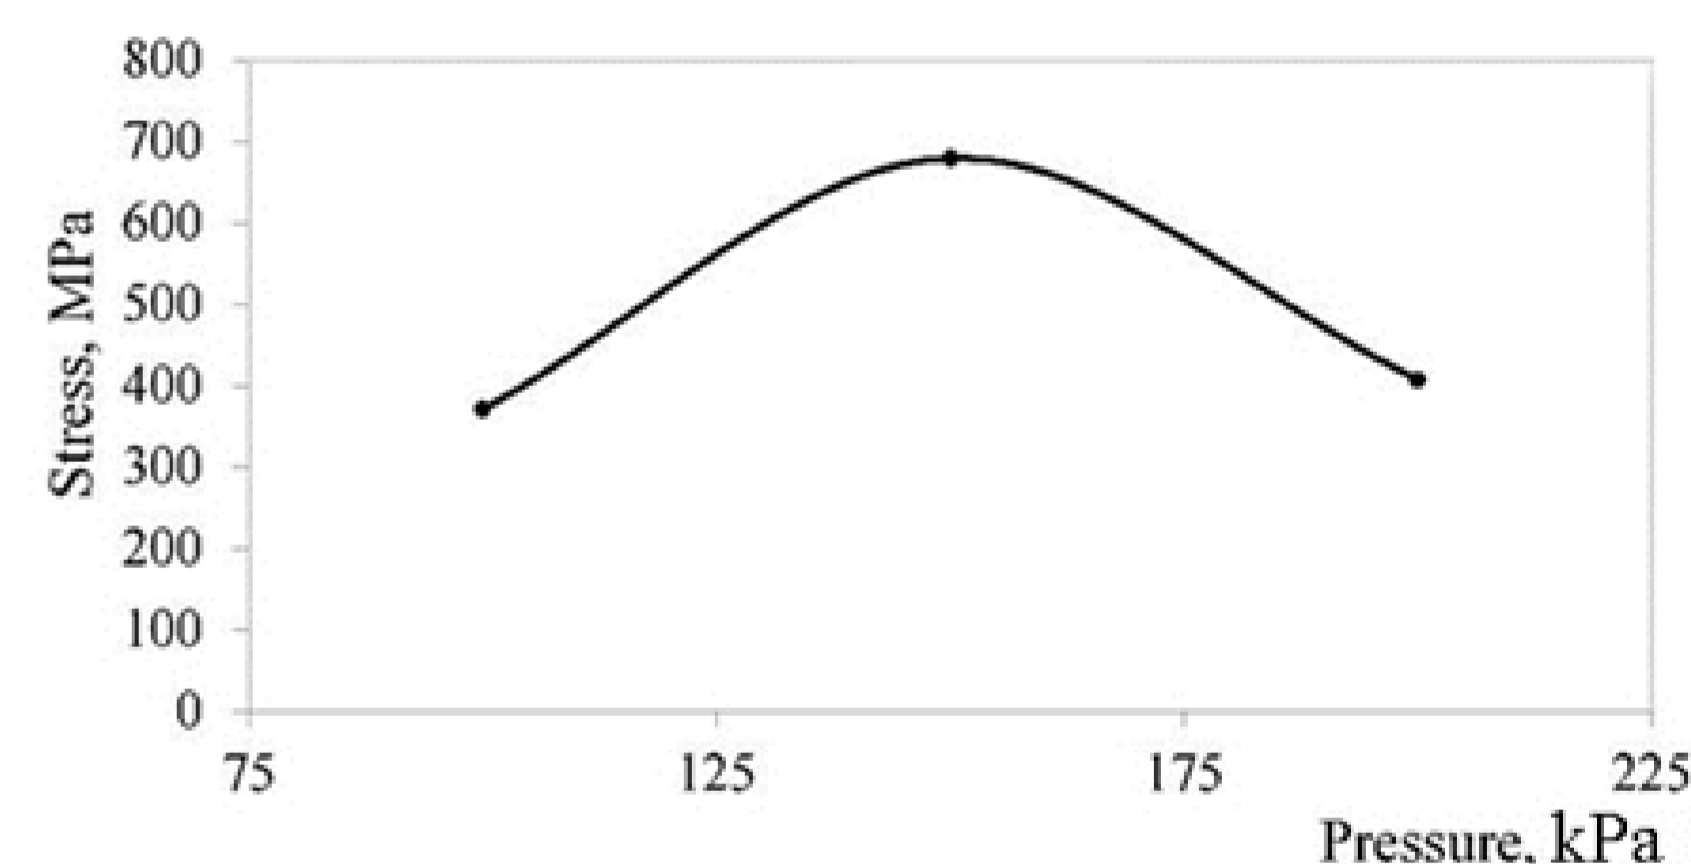


Figure 12. Fracture stress as a function of fritting pressure.

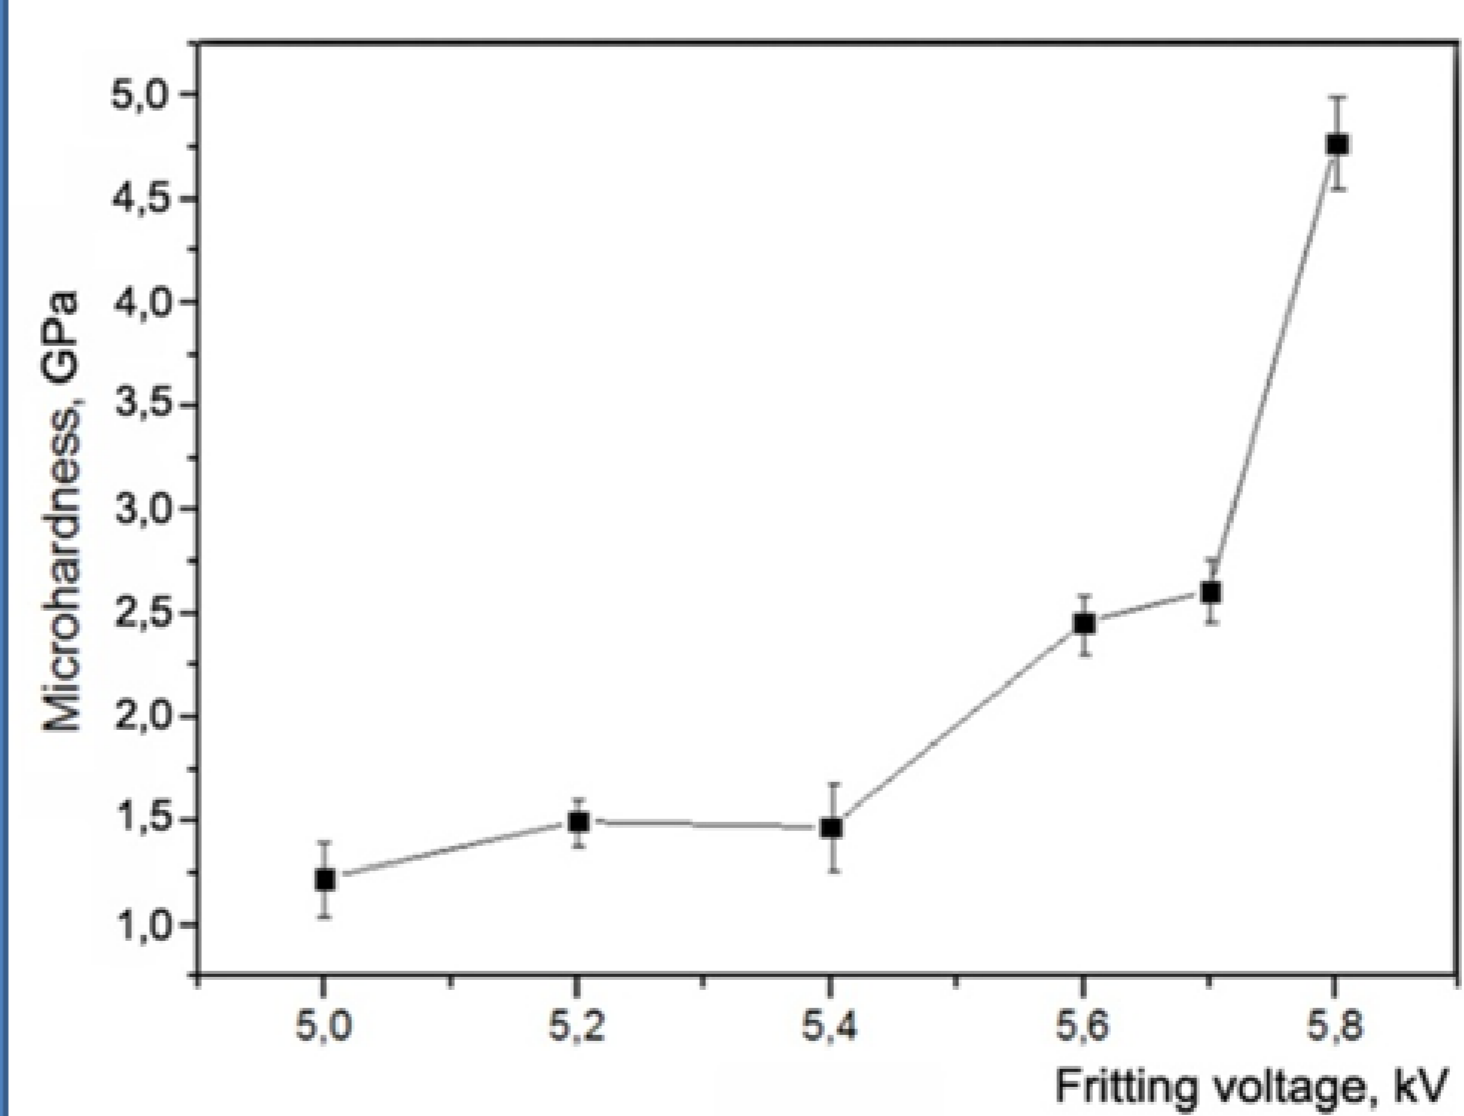


Figure 13. The sample microhardness as a function of fritting voltage

## Samples of aluminum oxide obtained by SPS

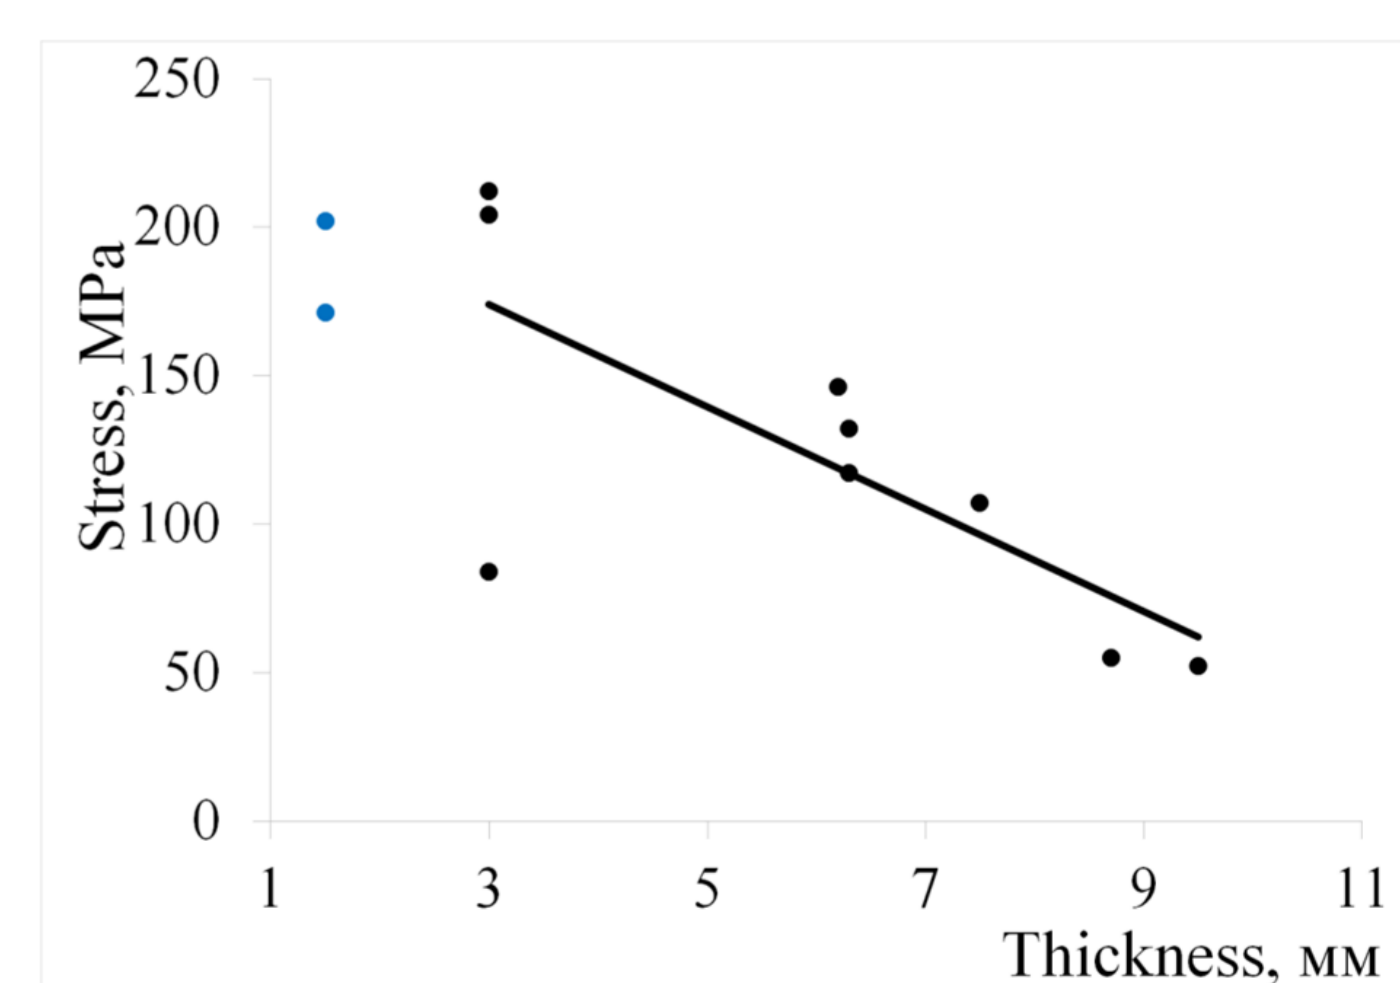


Figure 14. Breaking stress of alumina disk 10 mm in diameter as a function of disk thickness.

The blue points show the bending of the disks with a diameter of 15 mm and a thickness of 1.5 mm on the pivot support.

## Conclusions

For materials obtained by electro pulse consolidation, two methods for determining fracture resistance of thin brittle disks — bend testing on pivot ring and Brazilian test — have been comparatively analyzed using cast iron, graphite, SiAlON and alumina as reference samples. In most cases, good agreement between the results of the above testing procedures is observed, especially if material failure is preceded by plastic deformation (as in case of cast iron). In case of brittle failure (graphite), the results of testing by the above methods are by 20 and 50% lower than true values, respectively. The strength of consolidated materials depends on sintering temperature/pressure and presence/absence of dopants.

## References

- [1] Tumanov AT, editor, Methods for Strength Testing of Metals. Moscow: Mashinostroenie; 1974. 320 p.
- [2] ASTM D3967-95a Standard. Test Method for Splitting Tensile Strength of Intact Rock Core Specimens.