

Experimental Evaluation of Steel–Concrete bond Strength in Low-cost Self-compacting Concrete

M. M. Kamal¹, M. A. Safan^{*1} and M. A. Al-Gazzar²
¹Civil Engineering Dept., Faculty of Engineering, Menoufia University, Egypt
²Water Research Center, Ministry of Irrigation, Al-Kanater, Egypt

Abstract

The main objective of this research was to evaluate the potentials of self-compacting concrete (SCC) mixes to develop bond strength. The investigated mixes incorporated relatively high contents of dolomite powder replacing Portland cement. Either silica fume or fly ash was used along with the dolomite powder in some mixes. Seven mixes were proportioned and cast without vibration in long beams with 10 mm and 16 mm steel dowels fixed vertically along the concrete flow path. The beams were then broken into discrete test specimens. A push-out configuration was adopted for conducting the bond test. The variation of the bond strength along the flowing path for the different mixes was evaluated. The steel-concrete bond adequacy was evaluated based on normalized bond strength. The results showed that the bond strength was reduced due to Portland cement replacement with dolomite powder. The addition of either silica fume or fly ash positively hindered further degradation as the dolomite powder content increased. However, all SCC mixes containing up to 30% dolomite powder still yielded bond strengths that were adequate for design purpose. The test results demonstrated inconsistent normalized bond strength in the case of the larger bar diameter compared to the smaller one.

Keywords: Self-compacting concrete; bond; pull-out, push-out, filler, dolomite powder.

1. Introduction

Self-compacting concrete (SCC) refers to a normal or high strength concrete that is flowable enough to be placed without need for compaction due to the ability of filling the forms under gravity. Despite the high flowability of SCC, the mixes are sufficiently stable to resist segregation. Japanese researchers began to develop SCC mixes in the 1980s to ensure high quality in concrete construction [1]. The availability of this type of concrete provided unique merits including faster construction rates since the concrete places so quickly, reduced labor since no vibration is needed, the quality of compaction is no longer relevant, good finished surface quality and design flexibility in detailing congested steel reinforcement with regard to the limited size of coarse aggregates and the passing ability of SCC [2]. Compared to conventional vibrated concrete (VC), SCC mixes typically require higher contents of fine materials and less coarse aggregate content. The maximum nominal size of the coarse aggregate is typically no more than 19 mm. Also, the use of a high range water reducer is a must to make the mix flowable at a reasonable water/cement ratio. Viscosity agents are sometimes used to make the mix robust and less sensitive to accidental variations in the proportions and/or the quality of the used materials. Increasing the content of fine materials is

* Corresponding Author: Dr. Mohamed A. Safan, Associate Professor
e-mail: msafan2000@yahoo.com Telephone: +20100 4919 623

typically achieved by the increased content of sand and other by-product materials that have specific potentials for being implemented in concrete manufacturing. Silica fume, fly ash, granulated blast furnace slag and limestone powders have been successfully used in VC and SCC mixes. Pozzolanic activity, cementitious properties, smooth surface texture and fineness are appealing features that can be provided by these materials to improve the workability, strength and durability [3-5]. Also, the consumption of by-product materials has a positive environmental impact and reduces the energy consumption in cement factories.

The authors have conducted extensive experimental testing to explore the potentials of low-cost SCC incorporating relatively high contents of dolomite powder. Early research was devoted to explore the productions aspects, the rheological properties and short term strength for single, binary and ternary systems of silica fume, fly ash and dolomite powders replacing Portland cement [6, 7]. Later, SCC mixes selected on compressive strength criterion were used to study the flexure and shear strength of reinforced concrete beams [8]. Also, these mixes were used to prepare reinforced concrete beams that were subjected to severe corrosive environment and tested in flexure [9]. The results obtained that far were very encouraging for implementing binary systems of dolomite powder and either silica fume or fly ash to replace Portland cement in SCC mixes.

In the authors' previous works, dolomite powder (DP) rather limestone powder was used to replace Portland cement for two reasons. The first was the availability of the fine DP in local plants for ready-mix asphalt concrete and the second was the restrictions of the Egyptian Code of Practice [10] that did not allow the use of Portland limestone cements in reinforced concrete. A survey on the subject showed that the consulted international specifications and reported research works were concerned about some durability considerations [11-15].

The current work was devoted to study the bond strength between steel bars and concrete utilizing test specimens prepared using the SCC mixes tested in previous research work by the authors. Steel-concrete bond is a fundamental property to ensure the integrity of reinforced concrete structural elements because efficient bond ensures reliable force transfer between reinforcement and the surrounding concrete. In case of a deformed steel bar, the following mechanisms contribute to force transfer: (1) Chemical adhesion between the bar and the concrete, (2) Frictional forces arising from the roughness of the interface and (3) Mechanical anchorage or bearing of the ribs against the concrete surface. It has been demonstrated that the bond strength is governed by the mechanical properties of the concrete, the volume of the concrete around the bars in terms of the concrete cover and bar spacing parameters; the presence of confinement in the form of transverse reinforcement, which can delay and control crack propagation; and the diameter and geometry of the bar (deformation height, spacing and face angle) [16, 17].

There were only limited researches on bond strength in SCC providing conclusions that were not comparable. In the bond tests carried out using pull-out specimens, De Almeida et al. [18] obtained similar bond strengths with SCC and VC, Chan et al. [19] and Daoud et al. [20] obtained 5% higher strengths with SCC, while Zhu et al. [21] reported strengths that were up to 25% higher with SCC, with lower bond stresses as the bar size increased. Turk et al. [22] studied the effect of using different types and contents of fly ash and silica fume on the bond strength by testing splice specimens for different SCC and VC mixes. The results showed that SCC mixes demonstrated higher bond strengths compared to VC due to superior filling and covering capability. Moreover, the beam specimens produced from SCC containing 5% replacement of silica fume had the greatest stiffness as a result of the pore structure improvement due to the pozzolanic activity of silica fume.

A variety of test specimen configurations have been used to study the bond between reinforcing bars and concrete. The details of the specimen affect both the measured bond strength as well as the nature of the bond response. According to ACI 408R-03 [16], the four most common configurations are the pull-out specimen, beam end specimen, beam anchorage specimen and splice specimen. Pull-out specimens are widely used because of ease of fabrication. However, they are considered to be less realistic because the stress fields within the specimen simulate only a few cases in actual construction. As the bar is placed in tension, the concrete is placed in compression.

Further, compressive struts form between the support points for the concrete and the surface of the reinforcing bar, placing the bar surface in compression. On the other hand, beam anchorage and splice specimens represent larger-scale specimens designed to directly measure development and splice strengths in full-size members. The anchorage specimen simulates a member with a flexural crack and a known bonded length. The splice specimen, normally fabricated with the splice in a constant moment region, is easier to fabricate and produces similar bond strengths to those obtained from the anchorage specimen.

2. Aim and significance of the current work

This research was a part of an extensive program to explore the potentials of low-cost self-compacting concrete. Earlier, the production aspects, rheology and short-term compressive strength were investigated for SCC mixes incorporating different systems of by-product fillers. Also, the shear strength in RC beams and the performance of RC beams in an aggressive environment were investigated for selected mixes that demonstrated relatively superior strength performance. The current work was devoted to explore the bond strength between steel bars and SCC. The main parameters were the diameter of the steel bars, composition of the filler material and variation of compressive strength along the concrete flow path. The research presents correlations between the experimental bond strength and compressive strength to assess the capability of the different mixes to develop adequate levels of bond strength. Actually, the bond strength is strongly influenced by the adhesion characteristics and the mechanical prosperities of the surrounding concrete. The current research results are expected to provide some necessary answers concerning the bond strength as an essential prosperity for the integrity of structural elements with regard to the variable composition of SCC among the other mentioned test parameters.

3. Experimental study

3.1. Materials

Cement and fillers: cement type CEM I 32.5 N meeting the requirements of BS EN 197-1:2000 [23] was used. The specific gravity of cement was 3.13 and the initial setting time was 90 min. at 27.5 percent water for standard consistency. Locally produced densified silica fume was delivered in 20-kg sacks. According to the manufacturer, the light-gray powder had a specific gravity of 2.2, specific surface area of 17 m²/gm, loss on ignition of 1.5, and 93 percent SiO₂ content. Imported class F fly ash meeting the requirements of ASTM C618 [24] was used. According to the manufacturer, the average sum of SiO₂, Al₂O₃ and Fe₂O₃ is 85 percent by weight with a specific gravity of 2.1, and loss on ignition of 1.25 percent.

The particle size distribution curve in Fig. (1) shows that 90 percent by weight of ash passes through the 45- μ m sieve. The dolomite powder was obtained as a by-product from a local plant for ready-mix asphalt concrete. The production processes include drying the crushed dolomite used as a coarse aggregate by heating at a degree of 120 °C and sieving the aggregates to separate the different sizes. A small fraction of the powder that passes through sieve No. 50 (300 μ m) is used in the mix, while most of the powder is a by-product. This powder had a light brownish color, specific gravity of 2.72. Sieving six random samples of the powder showed that the average passing percentage through the 45- μ m sieve was 63 percent. The chemical analysis results of the fine materials are reported in Table (1). Fig. (1) shows the grading of the used materials.

TABLE 1. CHEMICAL ANALYSIS OF FINE MATERIALS (% BY MASS)

	Cement	Silica fume	Fly ash (F)	Dolomite Powder
SiO ₂	24.3	93.2	49.0	0.83
Fe ₂ O ₃	3.67	1.58	4.10	0.52
Al ₂ O ₃	4.10	0.51	32.3	0.77
CaO	58.3	0.20	5.33	28.5
MgO	2.35	0.57	1.56	19.3
K ₂ O	0.98	0.53	0.54	nd
Na ₂ O	0.35	0.45	0.28	nd
SO ₃	3.40	0.22	0.16	nd
CO ₂	nd	nd	0.80	46.8
L.O.I	2.10	2.62	1.25	43.2

nd: not detected

Aggregates: natural siliceous sand having a fineness modulus of 2.54 and a specific gravity of 2.65 was used. Crushed dolomite with a maximum nominal size of 16 mm was used as coarse aggregate. The aggregate had a specific gravity of 2.65 and a crushing modulus of 23 percent. About half of the particles were flaky and elongated. The grading of the used aggregates is shown in Fig. (1).

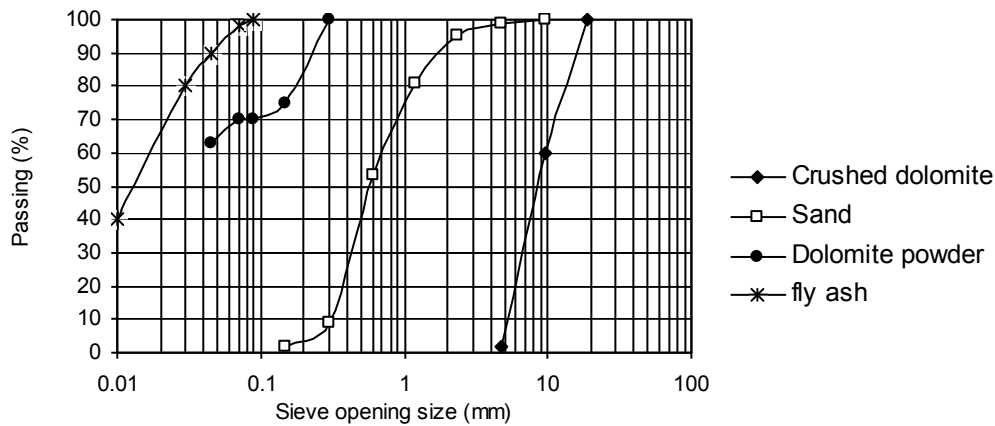


Fig. 1. Particle size distribution for concrete materials

Admixtures: a traditional sulfonated naphthalene formaldehyde condensate HRWR admixture conforming to ASTM C494 (types A and F) [25] was used. The admixture is a brown liquid with a specific gravity of 1.18.

Steel dowels: high tensile ribbed steel bars of 10 mm and 16 mm diameter were cut into 180 mm and 240 mm long dowels, respectively. The geometry of the bars and measured dimensions are shown in Table (2) and Fig. (2).

TABLE 2: DIMENSIONS OF THE STEEL BAR PROFILE

Nominal diameter (mm)	Dimensions (mm)					
	d_1	d_2	t	r_s	r_l	r_h
10	9.9	10.4	2.0	4.2	2.2	0.75
16	15.9	17.3	1.7	6.9	3.1	1.25

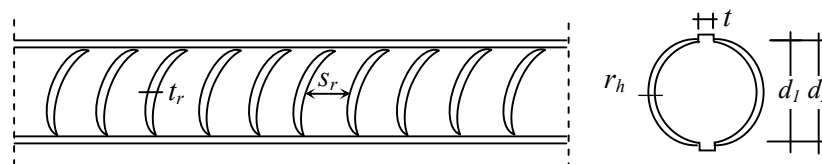


Fig. 2. Geometry of the steel bars

3.2. Concrete mix proportions

Based on the results reported in an initial phase of research [6], seven mixes were selected to produce SCC based on compressive strength criterion. The selected mixes incorporated dolomite powder (DP) replacing up to 30% of cement along with either silica fume (SF) or fly ash (FA) that replaced 10% of cement. The constituents of the selected SCC mixes are given in Table (3). In these mixes, the fine-to-coarse aggregate ratio was 1.13, the total content of powders (cement and fillers) was 500 kg/m^3 , the HRWR dosage was fixed at 10 kg/m^3 (2% by weight of powders). The water content was determined by trail and error procedure to obtain consistent mixes with the required fresh rheological properties. Table (4) shows the mechanical properties at 28 days, and the measured rheological properties.

TABLE 3. CONCRETE MIX MATERIALS AND PROPORTIONS

Mix	Mix Constituents *, kg/m^3							w/p
	cement	sand	dolomite	water	dolomite powder	silica fume	fly ash	
M1	500	945	840	160	-	--	--	0.32
M2	450	935	830	165	50	--	--	0.33
M3	400	925	820	170	100	--	--	0.34
M4	350	915	810	170	100	50	--	0.34
M5	300	900	800	175	150	50	--	0.35
M6	350	915	810	170	100	--	50	0.34
M7	300	900	800	175	150	--	50	0.35

* Superplasticizer dosage in all mixes = 10 kg/m^3 (2% by weight of powders).

TABLE 4. RHEOLOGICAL AND HARDENED PROPERTIES OF SSC MIXES

Mix	mechanical properties			rheological properties	
	f_{cu} (MPa)	f_r (MPa)	$f_r/f_{cu}^{0.5}$	slump flow (mm)	V-funnel t_o (sec.)
M1	34.0	3.8	0.65	700	6.0
M2	33.0	4.0	0.69	665	6.4
M3	29.5	3.8	0.70	655	5.5
M4	35.0	4.1	0.69	600	5.5
M5	31.5	3.9	0.69	580	5.2
M6	30.5	4.0	0.72	650	5.0
M7	28.5	3.9	0.73	640	5.1

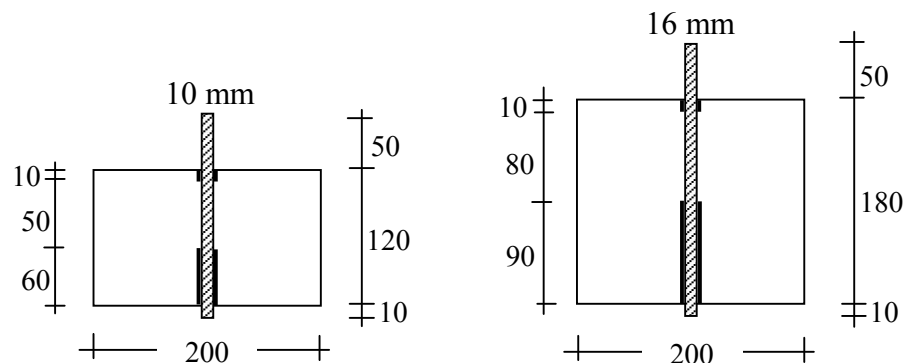


Fig. 3: Configuration of push-out bond test specimens

3.3. Configuration of push-out specimens

Push-out test specimens were used in the current work. Generally, the weak points of push-out test specimens, similar to pull-out test specimens, were the friction between the specimen and the bearing plate, and the arch-effect in the region close to the bearing plate. For these reasons, the bonded length was moved away from the bearing plate by providing a broken-bond zone next to the bearing plate as can be seen in Fig. (3). The procedure adopted by Foroughi et al. [26] to introduce a broken-bond zone and to avoid an unplanned force transfer between the bar and the concrete in this area was followed by encasing the bar with a plastic tube and sealing with a highly elastic silicone material. Also, 10 mm broken-bond zone was provided at the loading end so that the bonded length was five times the bar diameter.



Fig. 4. Preparation and testing of push-out test specimens

3.4. Casting forms

Casting forms were needed to manufacture concrete beams by casting the SCC mixes at one end and allowing concrete to flow to the other end without any compaction or vibration. The forms were designed to make it possible to split each beam into seven bond specimens with a steel dowel inserted at the center of each specimen. Specially designed wooden forms were manufactured for this purpose. The wooden forms had net internal dimensions of 120 mm depth, 150 mm width and 1400 mm length for the 10 mm steel bar diameter specimens. The corresponding dimensions for the 16 mm steel bar diameter specimens were 180 mm, 150 mm and 1400 mm. A separate plate was laid along the bottom of the form. The bottom plate was provided with seven holes at 200 mm center-to-center spacing to accommodate the lower end of the steel dowel. Vertical 25x25 mm polyurethane strips were adhered along the depth of the two sides of the form at 200 mm center-to-center

spacing. The soft polyurethane strips were intended to provide notches along the beam specimens to facilitate its splitting into discrete test specimens. After sampling the forms, a thin layer of grease was applied to the internal faces to prevent water absorption and ensure easy stripping of the forms. Upper horizontal plywood strips provided with holes were used to confine the upper portion of the steel dowel and thus the dowels were held in a vertical position during casting. Fig. (4-a) shows the wooden forms with the steel dowels inserted and confined.

Two 40-liter batches were used to cast two beams of 120 mm and 180 mm depth along with one 100 mm cube to determine the compressive strength, f_{cu} , and one 100x100x500 mm prism to determine the tensile strength in terms of the fracture modulus, f_r . Each concrete mix was used to fill the forms and molds three times, so that each reported test result was the average of three test results. After mixing, the concrete was poured in a wide vessel and successively hand-poured in the forms and molds, Fig. (4-a). The forms were stripped 24-hours after casting. Fig. (4-b) shows the beam specimens after stripping and sequentially numbering the bond test specimens. After that, each beam was carefully poisoned in a hydraulic flexure machine to split it at the notched sections and obtain the bond test specimens, Fig. (4-c). All specimens were cured under continuously wet cloth that was moistened twice a day until testing at 28-day age.

3.5. Testing Procedure

A total number of 147 bond test specimens, 21 cubes and 21 prisms were tested. Fig. (4-d) shows the test set up and loading configuration of the push-out test. The bond test specimen was tested under a compression force driving down the steel dowel. A 500 kN universal testing machine was used to apply the compression force at a loading rate of 50 kN/min. The machine provided an automatic control of the loading range to ensure precise load measurements. A 20 mm thick bearing plate provided with a central hole was used to support the test specimen. The plate was supported on the edges of a rigid base allowing the penetration of the dowel. A packing plywood plate was used to ensure even contact between the bottom surface of the concrete specimen and the bearing plate. To prevent buckling of the 50-mm long upper free part of the dowel under the applied load and to ensure eccentric loading, a special steel punched head was fixed in the upper platen of the testing machine. The punched head confined 30 mm of the free loaded part and thus a bar length of 20 mm was available for the dowel to penetrate through the concrete block. The 20 mm maximum penetration value was more than sufficient to achieve the ultimate bond strength knowing that the rib spacing was 4.2 mm in the 10 mm dowels and 6.9-mm in the 16 mm dowels. The test was ended once the ultimate load was recorded.

4. Test results and discussion

While the configuration of the push-out test specimen adopted in this work is not a standard one, some measures were considered to make the obtained results more realistic. The bonded length was shifted away from the bearing plate to avoid confinement effect due to the lateral compression stress induced in the concrete. Also, a relatively limited bond length of five times the steel bar size was adopted. These factors were expected to yield favorable bond failures due to the slip of the bar rather than due to splitting of concrete. However, splitting failures could still occur if the tensile strength is exhausted given that no radial steel reinforcement was provided to resist splitting.

The test results were evaluated based on normalized bond strength obtained by dividing the average bond strength of a given mix to the square root of the corresponding compressive strength. The bond strength was calculated by dividing the ultimate load by the bonded area ($\pi.d.l$). Given

that the bonded length (l) was five times the bar diameter (d), the ultimate bond strength can be expressed as:

$$f_b = P_u / 5 \pi d^2 \quad (1)$$

Due to the variation of the concrete compressive strength, the bond strength was expressed in terms of normalized bond strength f_{bn} , where:

$$f_{bn} = f_b / f_{cy}^{0.5} \quad (2)$$

To examine the adequacy of the obtained levels of bond strength, two approaches were adopted. The first was to check out the design bond strength requirements in the ACI 318-08 design code [27] and the second was to compare the obtained results with the results available in the literature for similar SCC mixes and bar diameters. For this purpose, the bond strength was related to the square root of the cylinder compressive strength. The cylinder compressive strength f_{cy} was taken equal to 80% of the corresponding cube compressive strength according to the data collected by Domone [28]. The average bond strength along the flowing path, the total average and the normalized bond strength are reported in Tables 5 and 6.

TABLE 5: BOND STRENGTH OF THE 10 MM BAR SPECIMENS

Specimen serial number	Mix No.						
	1	2	3	4	5	6	7
1	13.14	9.40	5.3	6.75	5.49	5.56	4.90
2	15.42	9.80	5.51	6.90	6.04	5.96	6.22
3	15.90	12.38	6.94	7.76	6.36	6.76	6.62
4	17.75	10.18	6.57	7.50	7.42	7.15	7.28
5	18.70	10.15	5.99	7.18	8.05	6.63	6.12
6	17.10	9.67	5.99	6.92	6.76	6.36	4.90
7	16.80	9.15	5.00	6.47	6.33	6.30	4.50
<i>Average f_b</i> (MPa)	16.40	10.10	5.90	7.07	6.64	6.39	5.80
$f_{bn} (f_b / f_{cy}^{0.5})$	3.14	1.97	1.21	1.34	1.32	1.29	1.21

TABLE 6: BOND STRENGTH OF THE 16 MM BAR SPECIMENS

Specimen serial number	Mix No.						
	1	2	3	4	5	6	7
1	11.32	8.66	5.55	7.55	6.44	6.44	9.99
2	11.10	9.32	5.77	7.70	6.88	6.66	9.32
3	12.88	9.77	6.88	7.90	6.66	7.33	9.32
4	12.43	9.10	5.99	7.77	7.10	7.55	10.44
5	13.10	8.44	5.99	7.99	6.66	7.99	8.66
6	11.99	8.44	5.77	7.99	6.22	7.55	8.44
7	11.77	8.21	5.33	7.55	6.22	6.66	8.44
<i>Average f_b</i> (MPa)	12.1	8.85	5.90	7.78	6.60	7.17	9.20
$f_{bn} (f_b / f_{cy}^{0.5})$	2.32	1.72	1.21	1.47	1.31	1.45	1.93

The current ACI 318-08 code [27] does not provide an explicit expression linking the bond strength to the concrete compressive strength. Rather, the bond strength was implicitly applied in the calculation of the development length. The development length concept is based on the average bond stress over the length of embedment of the reinforcement. For some favorable conditions concerning the spacing between developed or spliced bars, clear cover and confinement, the

following equation is used to calculate the development or splice length (l) associated with relatively higher bond strengths for 19 mm and smaller steel bars:

$$l = f_y d / 2.1 f_{cy}^{0.5} \quad (3)$$

Setting the ultimate force in the push-out bond test equal to $f_y A_b$, then the bond strength (f_b) can be expressed as:

$$f_b = f_y A_b / \pi d l \quad (4)$$

where: f_y is the yield stress of steel and A_b is the area of the steel bar. Equation (4) yields:

$$l = f_y d / 4 f_b \quad (5)$$

The analogy between equations (3) and (5) yields:

$$f_b = 0.53 f_{cy}^{0.5} \quad (6)$$

Equation (6) shows that the normalized bond strength for design purposes is taken 0.53 in favorable design conditions that require the development of satisfactory bond strength levels. The normalized bond strength values in Tables 5 and 6 ranged from 1.21 to 1.97 for the SCC mixes incorporating dolomite powder. These values are 2.3 to 3.7 times the design value with an average of 2.6 and 2.9 for the 10 mm and 16 mm bars, respectively.

Fig. (5) shows a plot of the normalized bond strength obtained from pull-out tests against the corresponding compressive strength (f_{cy}). The data were collected for different SCC mixes that had comparable compressive strength in the range of 26 to 36 MPa and steel bar diameters of 10, 14 and 16 mm [26, 28, 29]. In this range, the normalized bond strength varied from 1.07 to 2.6. It can be seen that the obtained normalized bond strengths are within this range.

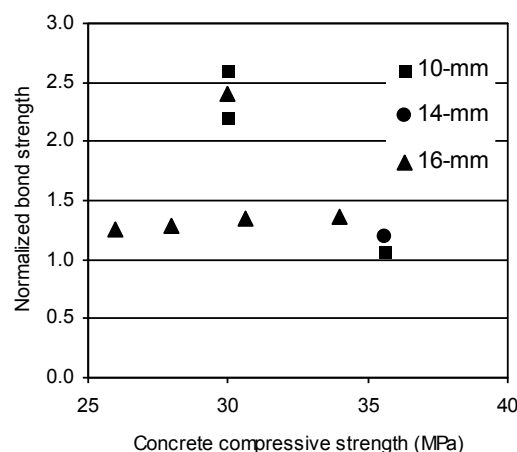


Fig. 5. Normalized bond strength and corresponding compressive strength

The 10 mm and 16 mm test specimens cast using mixes 1 and 2 failed due to splitting as the tensile stresses reached its ultimate values. The average normalized bond strength was higher in the 10 mm bar diameter specimens compared to the 16 mm diameter specimens. The decrease of the bond strength for a given concrete strength as the steel bar diameter increased has been traditionally reported in the literature. The rest of the test specimens failed favorably due to the penetration of the steel bar through the concrete without concrete cracking. This behavior can be attributed partially

due to the relative improvement of the tensile strength expressed in terms of the normalized values of the fracture modulus as indicated in Table (4). On the other hand, SCC mixes incorporating finely divided minerals were reported to demonstrate improved interfacial transition zones between the paste and the steel bars. Zhu et al. [21] investigated the steel-concrete interfacial transition zone with a nano-indentation technique, and found that the increased bond strength with the SCC mixes compared to vibrated concrete could be attributed to a greater uniformity in the ITZ around the bars. The relative improvement of the tensile strength and uniformity of the ITZ associated with better adhesion can rationally explain the penetration of the steel bar extracting a uniform layer of mortar between the ribs as observed after the test. This failure mode was associated with two distinct observations. First, the reduction of the both the bond and normalized bond strength due to cement replacement in all mixes. Second, the normalized bond strength was higher for the 16 mm bars in mixes 4, 6 and 7 compared to the 10 mm bars, while the normalized bond strength was the same for the two diameters in mixes 3 and 5. The reduction of the bond strength in SCC mixes seemed to increase as the percentage replacement with dolomite powder (DP) increased in mix 3 compared to mix 2.

The addition of either silica fume or fly ash seemed to have a positive effect even when the DP ratios increased. The reduction of the bond strength due to the incorporation of the DP can be explained by recalling that load transfer between concrete and steel occurs through the action of three mechanisms: chemical adhesion, friction and mechanical interaction of the lugs of the deformed reinforcement bearing on the surrounding concrete. For deformed reinforcement, mechanical interaction is the dominant mechanism of response according to Zhu et al. [21]. The use of the DP as cement replacement seemed to have a softening effect on the matrix, while keeping an adequate chemical adhesion due to the improvement in the ITS as mentioned before. This behavior hindered the development of the mechanical interaction and the bond strength was dominated by the friction resistance. Another parameter contributing to the reduction of the bond strength is the reduced shrinkage of concrete upon cement replacement and consequently the reduced gripping force exert by the concrete as reported by Sonebi et al. [30]. The observed occasional increase in the bond strength for a bigger diameter was reported by Khan et al. [31]. The increase was attributed to the increase in the friction bond component as the bar diameter increased. Also, the inconsistency of bond strength results in SCC mixes has been reported by Zhu et Al. [32] and Domone [28] and it was recommended that each concrete mix with a specified composition of the fillers should be tested to evaluate the bond behavior.

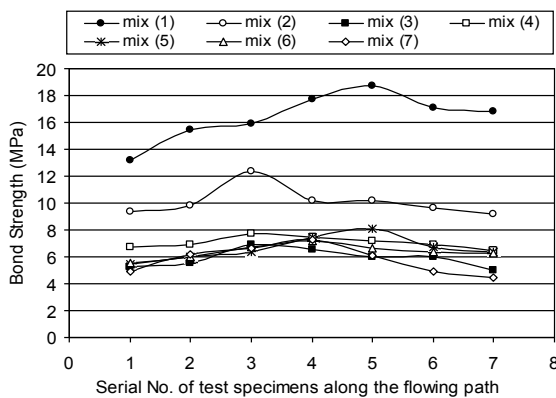


Fig. 6. Bond strength along the flow path (10 mm bar diameter specimens)

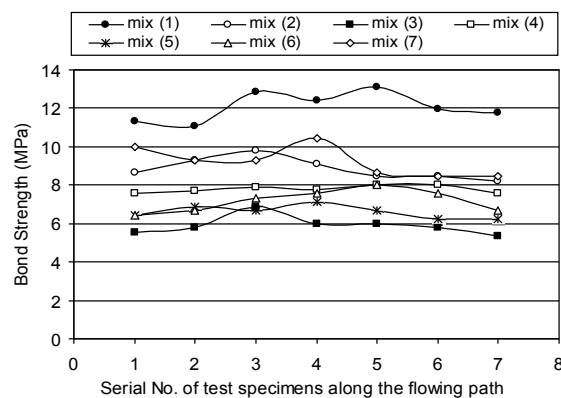


Fig. 7. Bond strength along the flow path (16 mm bar diameter specimens)

Figs. 6 and 7 show a plot of the average bond strength for the test specimens along the flow path for the 10 mm and 16 mm bars. The specimens were numbered sequentially beginning with the first

specimen at the casting end and ending with the seventh specimen at the end of the flow path. It can be seen that the bond strength tended to be higher about the middle of the flow path compared to the strength evaluated at the casting and end points. This trend needs to be further examined in actual size concrete elements being related to size effect and flow characteristics.

5. Conclusions

The current work investigated the potentials of the SCC mixes incorporating dolomite powder along with either silica fume or fly ash to develop bond strength. The variability of bond strength along a flowing path was evaluated, based on the available test results; the following conclusions could be drawn:

1. The bond strength was reduced due to Portland cement replacement with dolomite powder. While the chemical adhesion component was improved, the mechanical interaction was hindered and the bond strength was dominated by the friction resistance.
2. The addition of either silica fume or fly ash positively hindered further degradation of bond strength as the dolomite powder content increased.
3. SCC mixes containing up to 30% dolomite powder yielded bond strengths that were adequate for design purpose according to the requirements of the ACI 318-08 code.
4. The test results demonstrated inconsistent normalized bond strength in case of the larger steel bar diameter of 16 mm compared to the 10 mm steel bar diameter.
5. The bond strength tended to increase about the middle of the flowing path. This trend needs to be further examined in actual size concrete elements being related to size effect and flow characteristics.

References

- [1] Ozawa K, Maekawa K, Kunishima M, and Okamura H, *High performance concrete based on the durability design of concrete structures*. Proceedings East Asia Pacific conference on Structural Engineering (EASEC 2), Chiang Mai, Thailand: 1989.
- [2] Chan KD, Ong KCG and Tam CT, *Passing ability of SCC – improved method based on the P-Ring*. Proceedings of the 35th conference on Our World in Concrete and Structures, Singapore, August, (2010): 9 p.
- [3] ACI Committee 232, *Use of fly ash in concrete*. ACI 232.2R-03 (2003): 41 p.
- [4] ACI Committee 234, *Guide for the use of silica fume in concrete*. ACI 234R-06: 63 p.
- [5] Dunster A, *Silica fume in concrete*. BRE Press, Watford, UK (2009): 12 p.
- [6] Kamal MM, Safan MA, and Al-Gazzar MA, *Blended Portland cements for low-cost self-compacting concrete*. Proceedings of the 1st International Conference "New Cements and their Effects on Concrete Performance" National Housing and Building and Research Center (HBRC) and Helwan University, Cairo, Egypt, (2008): 14 p.
- [7] Al-Gazzar M A, *Low-cost self-compacting Concrete*. PhD Thesis, Menoufia University, Egypt (2009): 243 p.
- [8] Safan MA, *Shear strength of concrete beams cast with self-compacting concrete containing different fillers and coarse aggregates*. Canadian Journal of Civil Engineering, 2012, 38(7): in press.
- [9] Safan MA, *Performance of beams cast with low-cost self-compacting concrete in aggressive environment*. Acta Polytechnica, 2011, 51(5): 120-130.
- [10] ECP 203-2007, *Egyptian code for the design and construction of reinforced concrete structures*. National Building and Research Center (HBRC), Cairo, Egypt, 2007: 352 p.
- [11] Assié S, Escadeillas G, and Waller V, *Estimates of self-compacting concrete potential durability*. Construction and Building Materials, 2007, 21: 1909-1917.

- [12] BS 5328-1, *Concrete: Guide to specifying concrete*. British Standard Institution, 389 Chiswick High Road, London, W4- 4Al, UK, 1997: 32p.
- [13] BS 8500, *Concrete: Complementary British Standard to BS EN 206-1, Part 1: method of specifying and guidance for the specifier, 66p., and Part 2: Specifications for constituent materials and concrete*. British Standards Institution, 389 Chiswick High Road, London, W4-4Al, UK, 2002, 2006.
- [14] BRE Special Digest-1, *Concrete in aggressive ground*. Building Research Establishment (BRE), Watford, UK. Publisher: HIS Rapidoc, Willoughby, Bracknall, Berks, RG12-8DW, 2005.
- [15] CSA A23.1, *Concrete materials and methods of concrete construction*. Canadian Standards Association, Canada, 2009: 420 p.
- [16] ACI Committee 408, *Bond and development of straight reinforcing bars in tension*. ACI 408R-03, 2003: 49 p.
- [17] FIB Bulletin 10, *Bond of reinforcement in concrete*. State-of-the-art Report, FIB Bulletin 10, Switzerland, 2000: 427p.
- [18] De Almeida FM, De Nardin S, and El-Debs ALHC, *Evaluation of the bond strength of self-compacting concrete in pull-out tests*. Proceedings of the 2nd North American conference on the Design and Use of Self-Consolidating Concrete and 4th International RILEM Symposium on Self-Compacting Concrete. Chicago, 2005: 44-55.
- [19] Chan YW, Chen YS, and Liu YS, *Development of bond strength of reinforcing steel in self-consolidation concrete*. ACI Structure Journal, 2003, 100(4): 490–498.
- [20] Daoud A, Lorrain M, and Laborderie C, *Anchorage and cracking behavior of self-compacting concrete*. Proceedings of third RILEM International Symposium on Self-Compacting Concrete, Wallevik O, and Nielsson I Editors, Reykjavik Iceland, RILEM Publications, PRO 33, Bagneux, France, 2003.
- [21] Zhu W, Sonebi M, and Bartos PJM, *Bond and interfacial properties of reinforcement in self-compacting concrete*. Materials and Structures, 2004, 37: 442–448.
- [22] Turk K, Karatas M, and Ulucan Z, *Effect of the use of different types and dosages of mineral additions on the bond strength of lap-spliced bars in self-compacting concrete*. Materials and Structures, 2010, 43: 557-570.
- [23] BS-EN 197-1, *Cement: composition, specifications, and conformity criteria for common cements*. British Standard Institution, 389 Chiswick High Road, London, W4- 4Al, UK, 2000: 52 p.
- [24] ASTM C618, *Specification for fly ash and raw calcined natural pozzolan for use as a mineral admixture in Portland cement concrete*. Annual Book for ASTM Standards, 2000, 4: 4 p.
- [25] ASTM C494, *Standard specification for chemical admixtures for concrete*. 1999: 9 p.
- [26] Foroughi-Asl A, Dilmaghani S, and Famili H, *Bond strength of reinforcement steel in self-compacting concrete*. International Journal of Civil Engineering, 2008, 6(1): 24-33.
- [27] ACI 318R-08, *Building code requirements for structural concrete (318-08) and commentary*. ACI Committee 318, 2008: 471p.
- [28] Domone PL, *A Review of the hardened mechanical properties of self-compacting concrete*. Cement and Concrete Composites, 2007, 29: 1-12.
- [29] Menezes F, El Debs MK, and El Debs AL, *Bond-slip behavior of self-compacting concrete and vibrated concrete using pull-out and beam tests*. Materials and Structures, 2008, 41: 1073-1089.
- [30] Sonebi M, and Bartos PJM, *Hardened SCC and its bond with reinforcement*. Proceedings of the First International RILEM Symposium on "Self-compacting concrete", Skarendahl, A. and Petersson, O. Editors, 1999.
- [30] Khan MS, Reddy AR, Shariq M, and Prasad J, *Studies in bond strength in RC flexural members*. Asian Journal of Civil Engineering (Building and Housing), 2007, 8(1): 89-96

- [32] Zhu W, Gibbs JC, and Bartos PJM, *Uniformity of in situ properties of self-compacting concrete in full-scale structural elements*. Cement and Concrete Composites, 2001, 23(1): 57–64.