

# Green nanotechnology: Anticancer Activity of Silver Nanoparticles using *Citrullus colocynthis* aqueous extracts

Alaa M. Shawkey<sup>1</sup>, Mohamed A. Rabeh<sup>2,\*</sup>, Abeer K. Abdulall<sup>3</sup> and Ashraf O. Abdellatif<sup>4</sup>

<sup>1</sup>Department of microbiology and immunology, Faculty of Pharmacy, Cairo University, Cairo, Egypt.

<sup>2</sup>Department of pharmacognosy, Faculty of Pharmacy, Cairo University, Cairo, Egypt.

<sup>3</sup>Department of microbiology and immunology, Faculty of Pharmacy (Girls), Al-Azhar University, Cairo, Egypt

<sup>4</sup>Department of microbiology and immunology, Faculty of Pharmacy, Karary University, Khartoum, Sudan.

\* Corresponding author: E-mail: [mohamedabdelatty68@yahoo.com](mailto:mohamedabdelatty68@yahoo.com) Tele: +20223639307, Fax: +2023628426

## Abstract:

Green synthesis of metal nanoparticles is a growing research area because of their potential applications in nanomedicines. The green synthesis of silver nanoparticles (SNPs) is a convenient, cheap and environmentally safe approach compared to chemical synthesis. In the present study, we synthesized SNPs from AgNO<sub>3</sub> using aqueous extracts (AEs) of fruits, leaves, roots and seeds of *Citrullus colocynthis* as reducing and capping agents. The SNPs were early detected in the aqueous extracts by color change to the reddish brown, and further were confirmed by Transmission Electron Microscope (TEM) analysis. The TEM analysis of SNPs showed spherical nanoparticles with mean size between 7 to 19nm. The anticancer activity of SNPs has been assessed *in vitro*. MTT assay on human cancer cell lines of colon (HCT-116), breast (MCF-7), liver (Hep-G2) and intestine (Caco-2) showed good anticancer activity which was negligible for the aqueous plant extracts. Regarding to the tested cell lines the Hep-G2 cell line and HCT-116 were the most sensitive cell line towards the cytotoxic activities of the tested SNPs, while the Caco-2 was the most resistant cell line towards the cytotoxic activities.

**Keywords:** green synthesis, silver nanoparticles, *Citrullus colocynthis*, anticancer.

## 1. Introduction

Nanoparticles of free metals have been extensively studied because of their unique physical properties, chemical reactivity and potential applications in catalysis, biological labeling, biosensing, drug delivery, antibacterial activity, antiviral activity, detection of genetic disorders, gene therapy and DNA sequencing (Thirumurgan *et al.*, 2010).

Nanoparticles are particles with a maximum size of 100 nm. These particles have unique properties, which are quite different than those of larger particles. These new properties have been attributed to variation in specific characteristics such as size, shape and distribution (Nalwa, 2005).

Silver (Ag), as a noble metal, has potential applications in medicine due to its unique properties (Gurunathan *et al.*, 2009). There are various methods for SNPs preparation, for example; sol-gel process, chemical precipitation, reverse micelle method, hydrothermal method, microwave, chemical vapor deposition and biological methods, etc (Murthy *et al.*, 2010; Panáček *et al.*, 2006; Sharma *et al.*, 2009). However, biological methods are preferred for being eco-friendly, cost effective, and don't involve the use of toxic chemicals.

Nanoparticles green synthesis is not time consuming compared to other biological processes (Chandran *et al.*, 2006). Synthesis of SNPs using different medicinal plants for pharmaceutical and biological applications have been reported (Gardea-Torresdey *et al.*, 2003; Huang *et al.*, 2007; Leela and Vivekanandan, 2008; Li *et al.*, 2007; Shankar *et al.*, 2004; Song and Kim, 2009).

Cancer is an abnormal type of tissue growth in which the cells exhibit an uncontrolled division, relatively in an autonomous fashion, leading to a progressive increase in the number of dividing cell (Kanchana and Balakrishna, 2011). There is increasing demands for anticancer therapy (Unno *et al.*, 2005). *In vitro* cytotoxicity testing procedures reduces the use of laboratory animals (Abraham *et al.*, 2004) and hence use of cultured tissues and cells have increased (Byrd *et al.*, 2003).

The discovery and identification of new antitumor drug with low side effects on immune system has become an essential goal in many studies of immuno-therapies (Xu *et al.*, 2009). Despite many efforts, multi drug resistance is still considered as a major drawback in chemotherapy of cancer which has been the subject of exhaustive experiments recently (Gottesman *et al.*, 2002). With this aim, many attentions have been paid to

natural compounds in plants, marine organism and microorganisms. Many medically relevant nanoparticles such as AgNPs were investigated for their cytotoxicity aspect. AgNPs showed different degrees of in vitro cytotoxicity (Hsin *et al.*, 2008).

*Citrullus colocynthis* belongs to Family *Cucurbitaceae*. It grows widely in Sudan and Egypt and it has been used in folk medicine of Sudan and many other African countries for its anti-inflammatory, anti-diabetic, and antioxidant activities (Gurudeeban and Ramanathan, 2010; Kumar *et al.*, 2008).

In the current study, we are showing the synthesis of SNPs using AEs of *C. colocynthis* in a cheap simple method. Additionally, we are verifying the possible upgrading of cytotoxic action of SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 human cancer cell lines relative to normal AEs of *C. colocynthis*.

## 2. Materials and methods

### 2.1 Plant material:

*C. colocynthis* fruits, seeds, leaves and roots were collected from Omdurman, Sudan (15°39'N 32°29'E). The plants were authenticated by Dr. Mohammed El-Gibali; senior botanist for plant identification at El-Orman botanical garden, Giza, Egypt. Voucher specimens have been deposited in the herbarium of the El-Orman botanical garden and were used to prepare the AEs.

### 2.2 Cancer Cell lines:

Colon adenocarcinoma (HCT-116), breast adenocarcinoma (MCF-7), liver carcinoma (Hep-G2) and intestinal adenocarcinoma (Caco-2) cell lines were obtained from National Institute of Cancer, Cairo University, Cancer biology department, pharmacology unit, Cairo, Egypt. Cells were routinely cultured in DMEM (Dulbecco's Modified Eagle's Medium), which was supplemented with 10% fetal bovine serum (FBS), 2 mM L-glutamine, containing 100 units/ml penicillin G sodium, 100 units/ml streptomycin sulphate, and 250 mg/ml Amphotericin B.

### 2.3 Preparation of plant aqueous extracts:

50grams of each plant organ (fruits, leaves, seeds and roots) were thoroughly washed in distilled water, cut into fine pieces, soaked in 200 ml distilled water for 24 hours at 40°C. The decoction obtained was then filtered through Whatman No.1 filter paper. The same procedure was repeated twice. The aqueous extracts of two successive extractions were pooled, concentrated under vacuum, and lyophilized.

### 2.4 Synthesis of silver nanoparticles using *C. colocynthis* AEs:

90 ml of 5.0 mM aqueous solution of silver nitrate (Sigma Aldrich, Egypt) were added to 10 ml of *C. colocynthis* AEs of concentration 2 mg/ml and kept at room temperature for 24 hours. Silver nanoparticles were gradually formed during the incubation period.

### 2.5 Characterization of SNPs by TEM analysis:

A drop of the silver nanoparticles solution was placed on a copper grid and coated with carbon support film. After drying, the shape and size of SNPs were analyzed using Transmission Electron Microscope (TEM) JEOL model JEM-2000EX (100 keV).

### 2.6 Evaluation of invitro cytotoxic activity of the SNPs on tested cell lines:

MTT assay was performed to determine the cytotoxic property of synthesized SNPs against HCT-116, MCF-7, Hep-G2 and Caco-2 cell lines. Briefly cell lines were seeded in 96-well tissue culture plates. Appropriate concentrations of stock solution were added and incubated for 48 hours at 37°C. Non-treated cells were used as control. Incubated cultured cell was then subjected to MTT (3-(4,5 Dimethylthiazol-2-yl)-2,5diphenyltetrazolium bromide, a tetrazole) colorimetric assay. The tetrazolium salt 3-[4,5-dimethylthiazol-2-yl]-2,5 diphenyltetrazolium bromide (MTT) is used to determine cell viability in assays of cell proliferation and cytotoxicity. MTT is reduced in metabolically active cells to yield an insoluble purple formazan product. Cells were harvested from maintenance cultures in the exponential phase and counted by a hemocytometer using trypan blue solution. The cell suspensions were dispensed (100µl) in triplicate into 96-well culture plates at optimized concentrations of  $1 \times 10^5$ /well for each cell lines, after a 24 hours recovery period. Assay plates were

read using a spectrophotometer at 520 nm. The spectrophotometrical absorbance of the samples was measured using a microplate (ELISA) reader. The cytotoxicity data was standardized by determining absorbance and calculating the correspondent SNPs concentrations. Data generated were used to plot a dose-response curve of which the concentration of extract required to kill 50% of cell population ( $IC_{50}$ ) was determined.

$$\text{Cell viability (\%)} = \text{Mean OD/ control OD} \times 100$$

### 3. Data analysis

The  $IC_{50}$  values (concentration at which 50% of cells were death) against colon adenocarcinoma (HCT-116), breast adenocarcinoma (MCF-7), liver carcinoma (Hep-G2) and intestinal adenocarcinoma (Caco-2) cell lines are reported as mean  $\pm$  standard deviation of three independent experiments.  $IC_{50}$  values that were greater than 30  $\mu\text{g/ml}$  considered insignificant, and vice versa.

The experimental work can be summarized in the following chart (Figure 1).

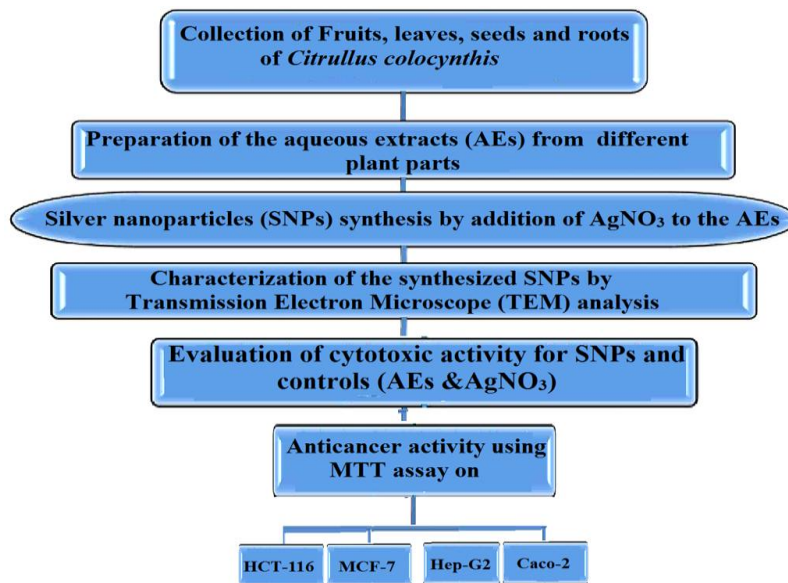


Figure 1: Experiment flowchart

## 4. Results

### 4.1 Synthesis and characterization of SNPs/*C. colocynthis*:

We treated the AEs of different organs of *C. colocynthis* with  $\text{AgNO}_3$  which resulted in changing the color of AEs to reddish brown which is the early sign for SNPs formation as shown in figure 2, due to the excitation of surface plasmon vibrations in SNPs (Thirumurgan *et al.*, 2010). Further confirmation for SNPs synthesis was carried out using TEM analysis. The  $\text{AgNO}_3$  solution and the AEs were used as a negative control throughout the study.



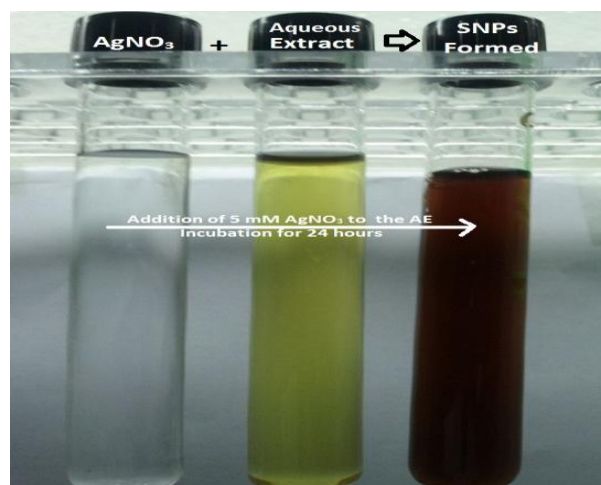


Figure 2: Early sign for SNPs formation observed as color change of *C. colocynthis* /AEs to reddish brown after 24 hours incubation with 5mM  $\text{AgNO}_3$

Figure 3 shows (TEM) picture of 5 mM AgNO<sub>3</sub> solution, 5 mM AgNO<sub>3</sub> solution , particles exhibited irregular shapes with an average size 562.4 nm; whereas Figure 4 shows TEM images of the AEs from different parts of *C. colocynthis* before and after treatment with AgNO<sub>3</sub> formation; fruits AE (A1), fruits SNPs (A2), seeds AE (B1), Seeds SNPs (B2), leaves AE (C1), leaves SNPs (C2), roots AE (D1) and roots SNPs (D2). The average mean sizes of silver nanoparticles were 19.267 nm, 16.578 nm, 13.376 nm and 7.398 nm for fruits, seeds, leaves and roots SNPs respectively. All produced nanoparticles seem to be spherical in their morphology.

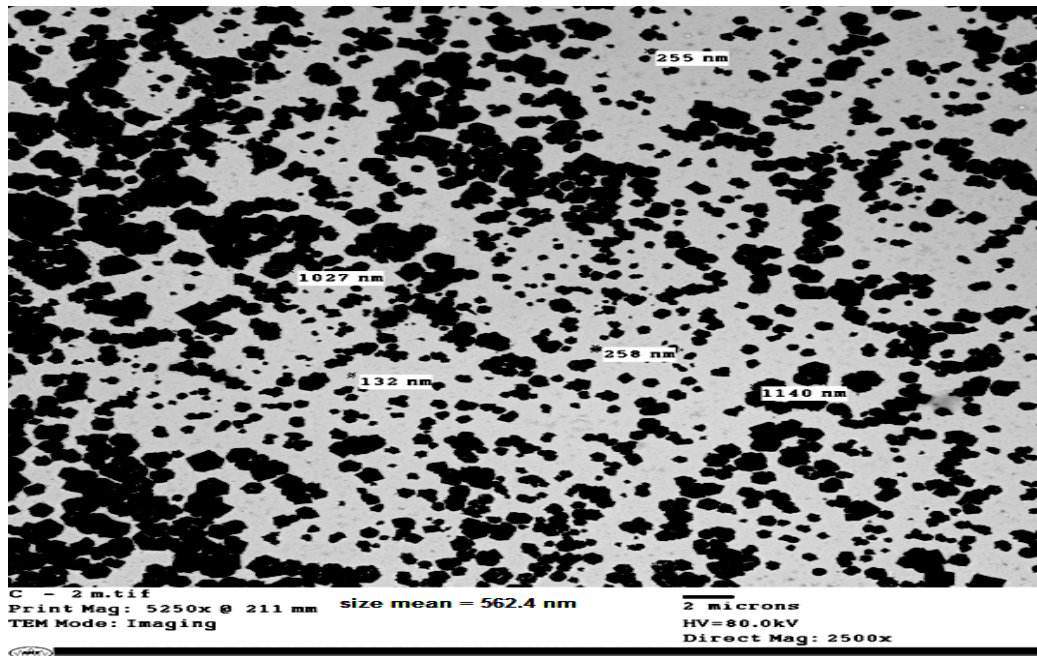

**Figure 3:** TEM photo showing 5 mM AgNO<sub>3</sub> solution . Particles exhibits irregular shapes with an average size 562.4 nm

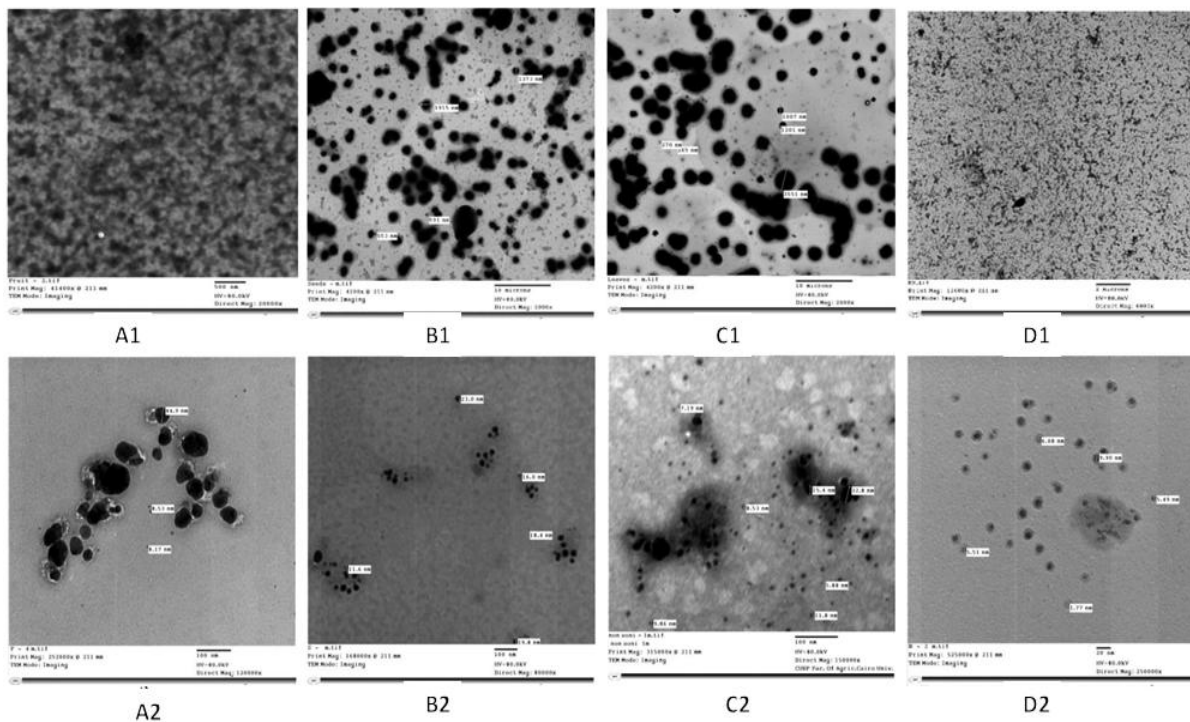

**Figure 4:** TEM photos for the aqueous extracts (AEs) from different parts of *C. colocynthis* before and after treatment with AgNO<sub>3</sub>, showing the shape and size of produced SNPs after treatment process : fruits AE (A1), fruits SNPs (A2), seeds AE (B1), Seeds SNPs (B2), leaves AE (C1), leaves SNPs (C2), roots AE (D1), roots SNPs (D2 ).

#### 4.2 *Citrullus colocynthis* /SNPs anticancer activity:

The cytotoxicity of the SNPs and AEs were studied invitro against HCT-116, MCF-7, Hep-G2 and Caco-2 cancer cell lines at different concentration (0, 5, 12.5, 25, 50 µg/ml).

The results obtained from MTT assay after 48hrs of incubation showed that fruits/SNPs showed significant effect on Hep-G2 and MCF-7 with  $IC_{50} = 17.2$  and  $22.4$  µg respectively. Fruits/ SNPs cytotoxic effect on HCT-116 and Caco-2 showed insignificant anticancer activity with  $IC_{50} > 30$ µg/ml (Table 1, Figure 5).

Leaves/SNPs was effective only against Hep-G2 cancer cell line, as it led to inhibition in cell growth as concluded from  $IC_{50}$  values  $10.2$ µg/ml as shown in (Table 1 , Figure 6).

Treatment of tested cell cancer cell lines with seeds/SNPs led to insignificant cytotoxic effect with  $IC_{50}$  values above  $30$  µg (Table 1, Figure 7).


At the same time treatment of HCT-116 and Hep-G2 cancer cell lines with roots/SNPs led to significant cytotoxic effects with  $IC_{50}$   $21.2$  µg for HCT-116 and  $IC_{50} = 22.4$  µg for Hep-G2 . Insignificant cytotoxic effect was observed on MCF-7 and Caco-2 cell lines as shown in (Table 1, Figure 8).

**Table 1:** *Invitro* cytotoxicity effect of silver nanoparticles (SNPs) from the fruits, leaves, seeds and roots of *C. colocynthis* on colon adenocarcinoma (HCT-116), breast adenocarcinoma (MCF-7), liver carcinoma (Hep-G2) and intestinal adenocarcinoma (Caco-2) cell lines represented as cell viability percentage ± standard deviation:


	Conc. (µg/ml)	Cell Viability % ± SD				
		0	5	12.5	25	50
<b>Fruits SNPs</b>	HCT-116	100	83.1±0.41	82.3±0.18	66.8±0.56	41.3±0.73
	MCF-7	100	88.8±0.22	64.9±0.85	43.6±0.31	41.1±0.26
	Hep-G2	100	90.4±0.73	59.1±0.82	34.7±0.16	46.1±0.91
	Caco-2	100	84.1±0.26	80±0.35	55.2±0.11	61.6±0.56
<b>Leaves SNPs</b>	HCT-116	100	54.3±0.11	50.5±0.96	52.7±0.42	58.5±0.23
	MCF-7	100	95.5±0.12	95.5±0.68	98.6±0.22	99.6±0.35
	Hep-G2	100	52.4±0.55	48.4±0.41	51.2±0.15	53.2±0.35
	Caco-2	100	66.4±0.34	63.1±0.53	68.6±0.60	61.1±0.87
<b>Seeds SNPs</b>	HCT-116	100	91.6±0.13	77.4±0.27	51.5±0.17	48.1±0.45
	MCF-7	100	82.3±0.44	80±0.21	83.2±0.15	91.6±0.82
	Hep-G2	100	77±0.41	79.1±0.35	67.5±0.41	49.1±0.91
	Caco-2	100	70.4±0.25	63.8±0.17	52.3±0.35	67.6±0.46
<b>Roots SNPs</b>	HCT-116	100	87.7±0.47	62.6±0.29	43.6±0.36	41±0.84
	MCF-7	100	94.1±0.73	100±0.33	97.6±0.19	100±0.14
	Hep-G2	100	76.6±0.23	62.8±0.57	44.4±0.62	42.3±0.33
	Caco-2	100	95.7±0.45	77.9±0.63	74.9±0.45	71.4±0.25

**Conc.** = concentration (W. /V. mg/ml H<sub>2</sub>O), **SNPs** = Silver Nanoparticles, **SD** = Standard deviation, **HCT-116**= Colon adenocarcinoma cell line, **MCF-7**= Breast adenocarcinoma cell line, **Hep-G2**= Liver carcinoma cell line, **Caco-2**= Intestinal adenocarcinoma cell line.


From the obtained data no significant cytotoxic activities were observed against Caco-2 cancer cell line and with exception of fruits/SNPs, other SNPs didn't show any significant activity against MCF-7 cancer cell line. Fruits/SNPs showed good cytotoxic properties comparing to other SNPs and to less degree roots/SNPs whereas leaves/ SNPs were only active against Hep-G2 while seeds/SNPs cytotoxicity is the weakest one. Regarding to the tested cell lines the HCT-116 and Hep-G2 cell lines were the most sensitive cell lines towards the cytotoxic activities of the tested SNPs, while the Caco-2 was the most resistant cell line towards the cytotoxic activities.

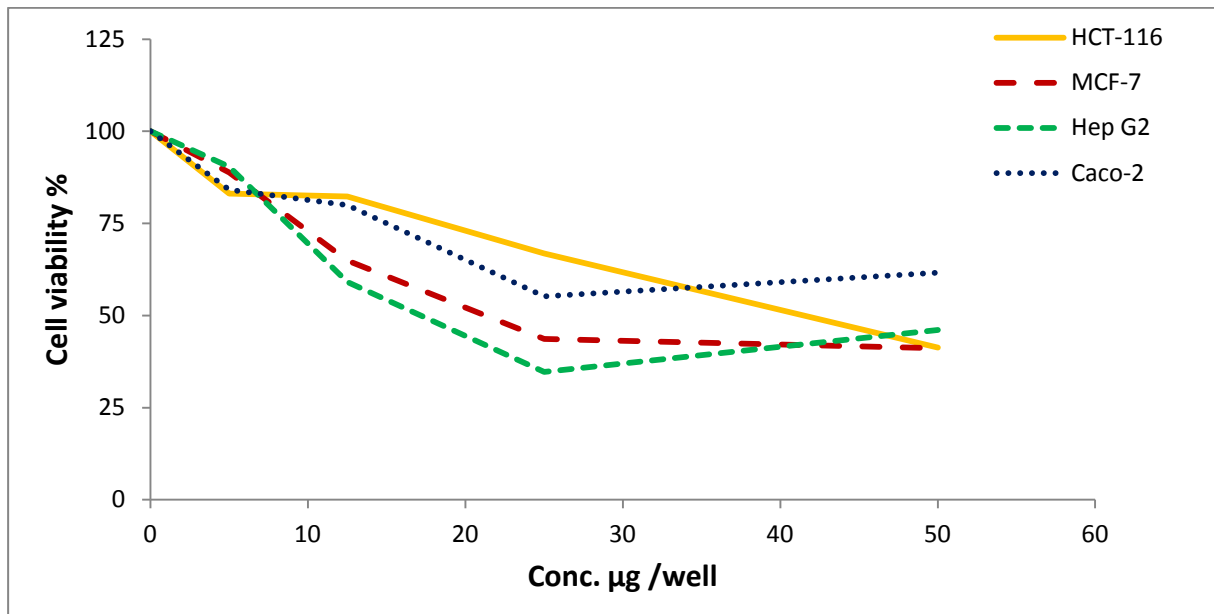


**Figure 5: Cytotoxicity effect of fruits/SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 cancer cell lines using MTT assay;** Fruits/SNPs showed significant effects on Hep-G2 and MCF-7 with  $IC_{50} = 17.2 \mu\text{g}$   $22.4 \mu\text{g}$  respectively . Fruits/SNPs Cytotoxic activity on HCT-116 and Caco-2 cell lines was non-significant ( $IC_{50} > 30 \mu\text{g}$ )

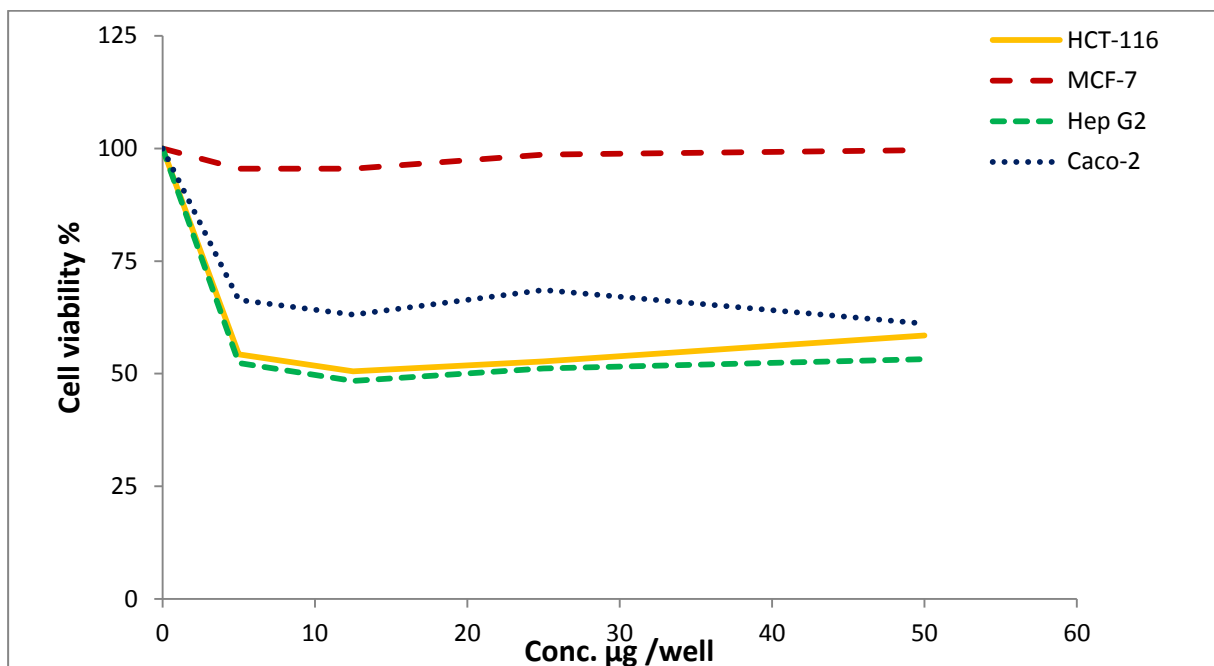

**Figure (6): Cytotoxicity effect of leaves/SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 cancer cell lines using MTT assay;** Leaves/SNPs showed significant effects only on Hep-G2 with  $IC_{50} = 10.2 \mu\text{g}$ . Leaves /SNPs anticancer activity on HCT-116, Cytotoxic activity on MCF-7 and Caco-2 cell lines was non-significant ( $IC_{50} > 30 \mu\text{g}$ )

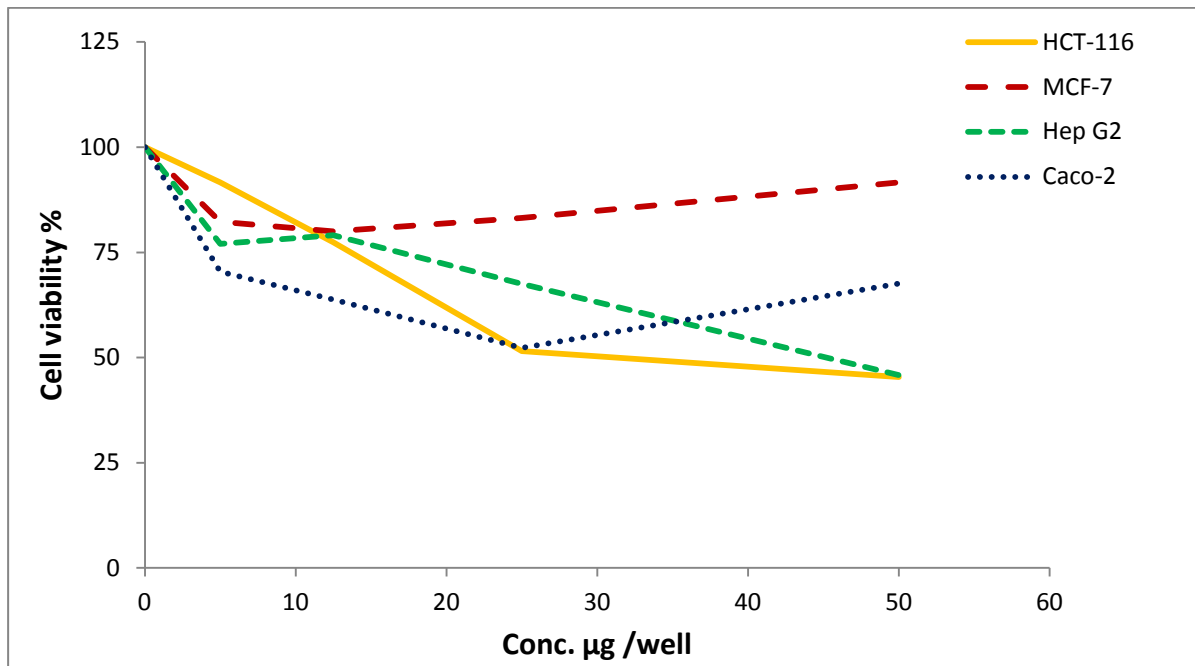

**Figure 7:** Cytotoxicity effect of seeds/SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 cancer cell lines using MTT assay; Seeds/SNPs showed non-significant cytotoxic activity on tested cell lines ( $IC_{50} > 30 \mu g$ )

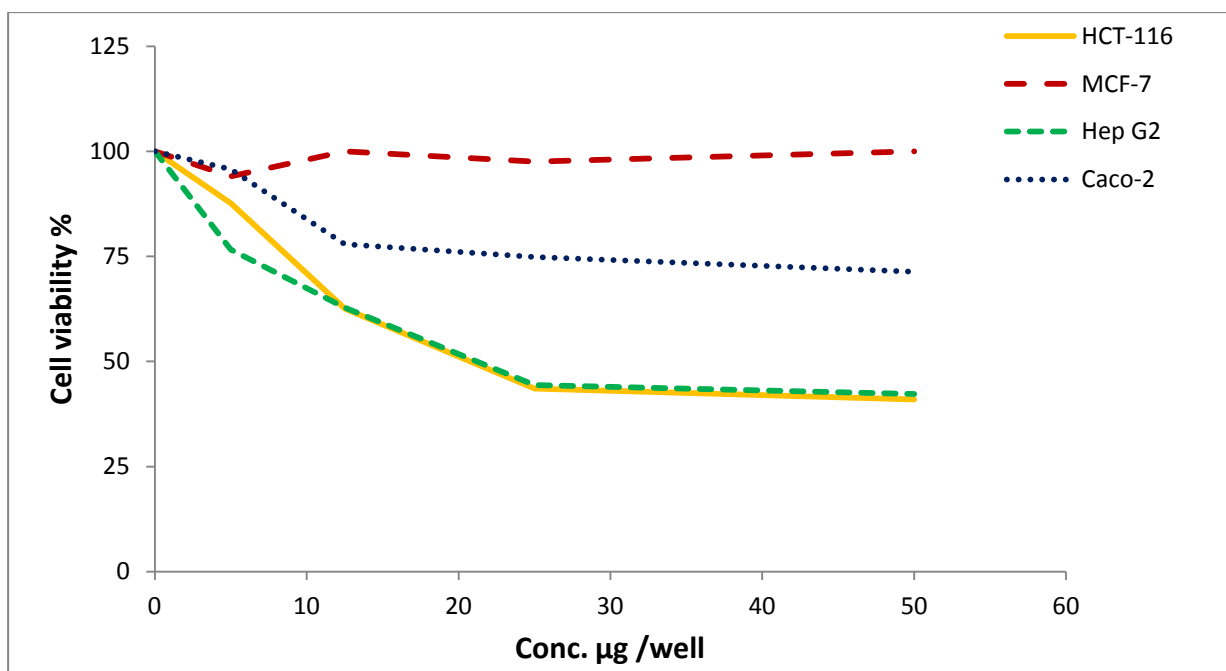

**Figure 8:** Cytotoxicity effect of roots/SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 cancer cell lines using MTT assay; Roots/SNPs led to significant cytotoxic effects on HCT-116 and for Hep-G2 with  $IC_{50}$  21.2  $\mu g$  and 22.4  $\mu g$  respectively. Cytotoxic activity on MCF-7 and Caco-2 cell lines was non significant ( $IC_{50} > 30 \mu g$ )

## 5. Discussion

It is well known that Ag ions and Ag-based compounds have strong biological activities (Furno *et al.*, 2004), However, Ag ions or salts has only limited usefulness for several reasons, including the interfering effects of salts and the continuous release of enough concentration of Ag ion from the metal form. In contrast, these kinds of limitations can be overcome by the use of SNPs.

However, to use SNPs in various fields, it is essential to prepare the SNPs with a cost effective method. In this study we were able to prepare SNPs eco-friendly and cost effectively by using the aqueous extracts from different parts of *C. colocynthis*, and these SNPs were homogeneous (Figures 4).

Owing to their small size, SNPs impair the sulfur and phosphorus containing essential macromolecules such as proteins and DNA (Wei *et al.*, 2009), Thus, action of SNPs appears to be a consequence of adherence to and penetration inside the cell of the target cells.

The anti-proliferative effect of SNPs and Ag<sup>+</sup> was reported (Ahamed *et al.*, 2008; Rahman *et al.*, 2009). Furthermore, the interaction of SNPs and Ag<sup>+</sup> with certain proteins has been the subject of extensive studies in recent years. In this study, anti-proliferative effect of SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 was investigated. Cells were observed to exhibit different responses after treatment with SNPs. The associate IC<sub>50</sub> values as indicated in table 1 reason for

The enhanced cytotoxicity of SNPs may be due to their size which facilitates their subsequent penetration in tumor cells.

The cytotoxic effects of SNPs, probably due to the fact that SNPs may interfere with the proper functioning of cellular proteins and induce subsequent changes in cellular chemistry (Rogers *et al.*, 2008). Zolghadri and coworkers demonstrated that SNPs provide a relatively high hydrophobicity inside bovine hemoglobin which causes a transition from alpha helices to beta sheets and leads to partial unfolding and aggregation of the protein (Zolghadri *et al.*, 2009), other researchers suggest that SNPs are likely to interact with thiol rich enzymes (Morones *et al.*, 2005); Therefore, it is possible that once penetrated into cells, SNPs may attack functional proteins of cells which results in partial unfolding and aggregation of proteins as it is the case in the bovine hemoglobin.

Toxicity of silver nanoparticles is concentration-size-shape dependent; In green synthesis process these factors are affected by chemical compositions of plant parts extracts, accordingly this will lead to variability in the biological activities of such extracts (Elechiguerra *et al.*, 2005; Morones *et al.*, 2005; Savithramma *et al.*, 2011).

Based on the present study, the action model of SNPs may be described as SNPs making a breakthrough in the permeability of outer membrane firstly, resulting in the leakage of cellular materials. Secondly, SNPs enter the inner membrane and inactivate respiratory chain dehydrogenases, thus inhibiting respiration and growth of cells. Simultaneously, SNPs could affect some proteins and phosphate lipids and induce collapse of membrane, resulting in cell decomposition and death eventually.

These results are potentially promising because they suggest that, by using non-cytotoxic amounts of silver salt with a convenient, eco-friendly and cheap method using *C. colocynthis* aqueous extract; we can synthesize SNPs with good anticancer activities. This opens the door to prepare a suitable pharmaceutical formulation using these nanoparticles. Taking into account the mobility of SNPs into cells and their fate in a bioprocess or even in the environment, the risk aspects for the application in larger scales and in the environment as well as studies on different biological activities in different fields should be strengthened in future studies.

## 6. Conclusion

Silver nanoparticles with an average size between 7 to 19 nm and spherical shapes were successfully synthesized using aqueous extract of fruits, seeds, leaves and roots of *C. colocynthis*. Green synthesis of SNPs using green resources like *C. colocynthis* is a better alternative to chemical synthesis, since this green synthesis has many advantages such as, ease of applicability for large scale production, economically feasible, and eco-friendly. The anticancer studies showed great improvement in the biological activity of the extracts after SNPs synthesis.

The present study explores the potential antitumor activity of green synthesized SNPs on HCT-116, MCF-7, Hep-G2 and Caco-2 tumor cell lines. Our results suggest that with the aid of metal based nanoparticles,



conditional chemotherapeutic agents may have even broader range of applications in future such as direct targeting to tumor cells. Thus, a study of the exact mechanism by which SNPs inhibit signaling cascades responsible for the development and progression of the disease would be a tremendous breakthrough in the field of nanomedicines and make these agents an effective alternative in tumor and angiogenesis-related diseases.

The use of plant extracts for making SNPs is an inexpensive, easily scaled up and environmentally benign. It is especially suited for making nanoparticles that must be free of toxic contaminants as required in therapeutic applications. The plant extract based synthesis can provide nanoparticles of a controlled size and morphology. Applications in targeted drug delivery and clinical diagnostics are developing.

## References

- Abraham, S.A., McKenzie, C., Masin, D., Ng, R., Harasym, T.O., Mayer, L.D., Bally, M.B., 2004. In vitro and in vivo characterization of doxorubicin and vincristine coencapsulated within liposomes through use of transition metal ion complexation and pH gradient loading. *Clinical cancer research* 10, 728-738.
- Ahamed, M., Karns, M., Goodson, M., Rowe, J., Hussain, S.M., Schlager, J.J., Hong, Y., 2008. DNA damage response to different surface chemistry of silver nanoparticles in mammalian cells. *Toxicology and Applied Pharmacology* 233, 404-410.
- Byrd, J.C., Lucas, D.M., Mone, A.P., Kitner, J.B., Drabick, J.J., Grever, M.R., 2003. KRN5500: a novel therapeutic agent with in vitro activity against human B-cell chronic lymphocytic leukemia cells mediates cytotoxicity via the intrinsic pathway of apoptosis. *Blood* 101, 4547-4550.
- Chandran, S.P., Chaudhary, M., Pasricha, R., Ahmad, A., Sastry, M., 2006. Synthesis of gold nanotriangles and silver nanoparticles using *Aloe vera* plant extract. *Biotechnology progress* 22, 577-583.
- Furno, F., Morley, K.S., Wong, B., Sharp, B.L., Arnold, P.L., Howdle, S.M., Bayston, R., Brown, P.D., Winship, P.D., Reid, H.J., 2004. Silver nanoparticles and polymeric medical devices: a new approach to prevention of infection? *Journal of Antimicrobial Chemotherapy* 54, 1019-1024.
- Gardea-Torresdey, J.L., Gomez, E., Peralta-Videa, J.R., Parsons, J.G., Troiani, H., Jose-Yacamán, M., 2003. Alfalfa sprouts: a natural source for the synthesis of silver nanoparticles. *Langmuir* 19, 1357-1361.
- Gottesman, M.M., Fojo, T., Bates, S.E., 2002. Multidrug resistance in cancer: role of ATP-dependent transporters. *Nature Reviews Cancer* 2, 48-58.
- Gurudeeban, S., Ramanathan, T., 2010. Antidiabetic effect of *Citrullus colocynthis* in alloxan-induced diabetic rats. *Inventi Rapid: Ethnopharmacology*.
- Gurunathan, S., Kalishwaralal, K., Vaidyanathan, R., Venkataraman, D., Pandian, S.R.K., Muniyandi, J., Hariharan, N., Eom, S.H., 2009. Biosynthesis, purification and characterization of silver nanoparticles using *Escherichia coli*. *Colloids and Surfaces B: Biointerfaces* 74, 328-335.
- Hsin, Y.-H., Chen, C.-F., Huang, S., Shih, T.-S., Lai, P.-S., Chueh, P.J., 2008. The apoptotic effect of nanosilver is mediated by a ROS-and JNK-dependent mechanism involving the mitochondrial pathway in NIH3T3 cells. *Toxicology letters* 179, 130-139.
- Huang, J., Li, Q., Sun, D., Lu, Y., Su, Y., Yang, X., Wang, H., Wang, Y., Shao, W., He, N., 2007. Biosynthesis of silver and gold nanoparticles by novel sundried *Cinnamomum camphora* leaf. *Nanotechnology* 18, 105104.
- Kanchana, A., Balakrishna, M., 2011. Anti-cancer effect of saponins isolated from solanum trilobatum leaf extract and induction of apoptosis in human larynx cancer cell lines. *International journal of pharmacy and pharmaceutical sciences* 3, 356-364.
- Kumar, S., Kumar, D., Jusha, M., Saroha, K., Singh, N., Vashishta, B., 2008. Antioxidant and free radical scavenging potential of *Citrullus colocynthis* (L.) Schrad. methanolic fruit extract.

- Leela, A., Vivekanandan, M., 2008. Tapping the unexploited plant resources for the synthesis of silver nanoparticles. *African Journal of Biotechnology* 7.
- Li, S., Shen, Y., Xie, A., Yu, X., Qiu, L., Zhang, L., Zhang, Q., 2007. Green synthesis of silver nanoparticles using *Capsicum annuum* L. extract. *Green Chem.* 9, 852-858.
- Li, W.-R., Xie, X.-B., Shi, Q.-S., Zeng, H.-Y., You-Sheng, O.-Y., Chen, Y.-B., 2010. Antibacterial activity and mechanism of silver nanoparticles on *Escherichia coli*. *Applied microbiology and biotechnology* 85, 1115-1122.
- Lok, C.-N., Ho, C.-M., Chen, R., He, Q.-Y., Yu, W.-Y., Sun, H., Tam, P.K.-H., Chiu, J.-F., Che, C.-M., 2006. Proteomic analysis of the mode of antibacterial action of silver nanoparticles. *Journal of Proteome research* 5, 916-924.
- Morones, J.R., Elechiguerra, J.L., Camacho, A., Holt, K., Kouri, J.B., Ramírez, J.T., Yacaman, M.J., 2005. The bactericidal effect of silver nanoparticles. *Nanotechnology* 16, 2346.
- Murthy, Y., Kondala Rao, T., Singh, R., 2010. Synthesis and characterization of nano silver ferrite composite. *Journal of Magnetism and Magnetic Materials* 322, 2071-2074.
- Nalwa, H.S., 2005. Handbook of nanostructured biomaterials and their applications in nanobiotechnology. American Scientific Publishers Valencia, CA.
- Panáček, A., Kvitek, L., Prucek, R., Kolar, M., Vecerova, R., Pizurova, N., Sharma, V.K., Nevečná, T.j., Zboril, R., 2006. Silver colloid nanoparticles: synthesis, characterization, and their antibacterial activity. *The Journal of Physical Chemistry B* 110, 16248-16253.
- Rahman, M., Wang, J., Patterson, T., Saini, U., Robinson, B., Newport, G., Murdock, R., Schlager, J., Hussain, S., Ali, S., 2009. Expression of genes related to oxidative stress in the mouse brain after exposure to silver-25 nanoparticles. *Toxicology letters* 187, 15-21.
- Rai, M., Yadav, A., Gade, A., 2009. Silver nanoparticles as a new generation of antimicrobials. *Biotechnology advances* 27, 76-83.
- Rogers, J.V., Parkinson, C.V., Choi, Y.W., Speshock, J.L., Hussain, S.M., 2008. A preliminary assessment of silver nanoparticle inhibition of monkeypox virus plaque formation. *Nanoscale Research Letters* 3, 129-133.
- Shankar, S.S., Rai, A., Ahmad, A., Sastry, M., 2004. Rapid synthesis of Au, Ag, and bimetallic Au core–Ag shell nanoparticles using Neem (*Azadirachta indica*) leaf broth. *Journal of colloid and interface science* 275, 496-502.
- Sharma, V.K., Yngard, R.A., Lin, Y., 2009. Silver nanoparticles: green synthesis and their antimicrobial activities. *Advances in Colloid and Interface Science* 145, 83-96.
- Song, J.Y., Kim, B.S., 2009. Rapid biological synthesis of silver nanoparticles using plant leaf extracts. *Bioprocess and biosystems engineering* 32, 79-84.
- Thirumurgan, A., Tomy, N., Jai Ganesh, R., Gobikrishnan, S., 2010. Biological reduction of silver nanoparticles using plant leaf extracts and its effect an increased antimicrobial activity against clinically isolated organism. *De. Phar. Chem* 2, 279-284.
- Unno, Y., Shino, Y., Kondo, F., Igarashi, N., Wang, G., Shimura, R., Yamaguchi, T., Asano, T., Saisho, H., Sekiya, S., 2005. Oncolytic viral therapy for cervical and ovarian cancer cells by Sindbis virus AR339 strain. *Clinical cancer research* 11, 4553-4560.
- Wei, D., Sun, W., Qian, W., Ye, Y., Ma, X., 2009. The synthesis of chitosan-based silver nanoparticles and their antibacterial activity. *Carbohydrate research* 344, 2375-2382.

Xu, H., Yao, L., Sun, H., Wu, Y., 2009. Chemical composition and antitumor activity of different polysaccharides from the roots of *Actinidia eriantha*. Carbohydrate polymers 78, 316-322.

Zolghadri, S., Saboury, A., Golestani, A., Divsalar, A., Rezaei-Zarchi, S., Moosavi-Movahedi, A., 2009. Interaction between silver nanoparticle and bovine hemoglobin at different temperatures. Journal of Nanoparticle Research 11, 1751-1758.

#### LIST OF ABBREVIATIONS

<b>TEM</b>	Transmitted Electron Microscope
<b>nm</b>	nanometer
<b>mM</b>	millimolar
<b>SNPs</b>	Silver Nanoparticles
<b>AE</b>	Aqueous extract
<b>DMEM</b>	Dulbecco's Modified Eagle's Medium
<b>ml</b>	Milliliter
<b>IC<sub>50</sub></b>	50% Inhibitory concentration
<b>Conc.</b>	Concentration

This academic article was published by The International Institute for Science, Technology and Education (IISTE). The IISTE is a pioneer in the Open Access Publishing service based in the U.S. and Europe. The aim of the institute is Accelerating Global Knowledge Sharing.

More information about the publisher can be found in the IISTE's homepage:

<http://www.iiste.org>

## CALL FOR JOURNAL PAPERS

The IISTE is currently hosting more than 30 peer-reviewed academic journals and collaborating with academic institutions around the world. There's no deadline for submission. **Prospective authors of IISTE journals can find the submission instruction on the following page:** <http://www.iiste.org/journals/> The IISTE editorial team promises to review and publish all the qualified submissions in a **fast** manner. All the journals articles are available online to the readers all over the world without financial, legal, or technical barriers other than those inseparable from gaining access to the internet itself. Printed version of the journals is also available upon request of readers and authors.

## MORE RESOURCES

Book publication information: <http://www.iiste.org/book/>

Recent conferences: <http://www.iiste.org/conference/>

## IISTE Knowledge Sharing Partners

EBSCO, Index Copernicus, Ulrich's Periodicals Directory, Journal TOCS, PKP Open Archives Harvester, Bielefeld Academic Search Engine, Elektronische Zeitschriftenbibliothek EZB, Open J-Gate, OCLC WorldCat, Universe Digital Library, NewJour, Google Scholar

