

The Photovoltaic Performance of CdS/Cu₂S (QD) Co-Sensitized Solar Cell

A. Khalid^{a*}, K. Easawi^b, S. Abdallah^c, M. G. El-Shaarawy^d, S. Negm^e, H. Talaat^f

^{a,b,c,e}Mathematical and Physical Engineering Department, Faculty of Engineering (Shoubra), Banha University, Cairo, Egypt

^dPhysics Department, Faculty of Science, Benha University, Cairo, Egypt

^fPhysics Department, Faculty of Science, Ain Shams University, Cairo, Egypt

^aEmail: akh_ghalia@yahoo.com

^bEmail: dr_easawi@yahoo.com

^cEmail: dr.saiedabdallah@yahoo.com

^dEmail: merfat.alsharawy@fsc.bu.edu.eg

^eEmail: drnegm@hotmail.com

^fEmail: hassantalaat@hotmail.com

Abstract

The performance of CdS/Cu₂S co-sensitized quantum dot solar cell (QDSSCs) is studied. CdS quantum dots (QDs) were adsorbed onto TiO₂ using Successive Ionic Layer Adsorption and Reaction (SILAR) method for different cycles (2, 4, 6, 8 and 10). The Cu₂S QDs were deposited onto TiO₂/CdS10 cycle photoanodes using the same method. The FTO counter electrodes were coated with platinum, while the electrolyte containing polysulfide redox species was sandwiched between the two electrodes. The current density- voltage (J-V) characteristic curves of the assembled QDSSCs were measured at different cycles and AM 1.5 simulated sunlight. The value of current density (J_{sc}) and conversion efficiency (η) of TiO₂/CdS/Cu₂S are 252% larger than the TiO₂/CdS values. The maximum values of J_{sc} and η are 3.56 mA/cm² and 1.21% respectively corresponding to CdS10/Cu₂S for 6 cycles of Cu₂S.

Keywords: Quantum dot sensitized solar cell (QDSSCs); CdS QD; SILAR; photovoltaic parameters.

* Corresponding author.

1. Introduction

In the last two decades, a great effort has been indicated to improve the performance of the third generation solar cells, especially that of quantum dots sensitized solar cells (QDSSCs)[1]. In this kind of solar cells, quantum dots (QDs) are adsorbed onto a large band gap metal oxides such as TiO₂ nanoparticles (NPs)[2-7], ZnO NPs[7-11], and SnO₂ NPs[7] to act as light harvesting sensitizers [12]. These QDs possess many attractive properties such as the ability to tune band gaps, high absorption coefficients due to quantum confinement, large dipole moment leading to rapid charge separation and as well low manufacturing cost [13]. CdS has become a very attractive promising material for many specific applications in solar energy conversion and Cu₂S is highlighted because of its non-toxic, low cost and earth-abundant properties. The band-gap of bulk Cu₂S is 1.20 eV, which can make Cu₂S become a widely used photosensitizer for various wide band-gap semiconductor photoanodes [14]. The adsorption of Cu₂S QDs onto TiO₂/CdS can make TiO₂/CdS/Cu₂S which would be more efficient for solar energy utilization than single semiconductor doped one. Their band gap matching for solar light absorption along wide band gap tunability and high absorption coefficient [15]. Synthesizing QDs techniques may involve different scientific processes, such as chemical, physical, biological, or some combination of these processes [16]. In some chemical methods, QDs are synthesized either by chemical bath deposition (CBD) technique or successive ionic layer adsorption and reaction (SILAR) method [16]. In our study we use SILAR, since it is simply adjusted by controlling the number of deposition cycles. A. Badawi and his colleagues employed CdSe QD sensitized TiO₂ using the direct adsorption technique (DA) to anchor CdSe QD onto TiO₂ substrate and the efficiency for energy conversion η has been increased from 0.11 % to 0.29 % [9]. N. Al-Hosiny and his colleagues studied CdTe_xS_{1-x} QDs to deposit TiO₂ mesoporous, they tuned the efficiency via molar ratio control of CdTe_xS_{1-x} QD and reported the maximum value of η was 0.31 % for x=0.6 of CdTe_xS_{1-x} [10]. In our work CdS QDs and CdS/Cu₂S QDs were adsorbed onto the surface of the TiO₂ electrode by (SILAR) method. The effect of the CdS QDs and CdS/Cu₂S QDs number SILAR cycle on the QDSSCs photovoltaic parameter (short circuit current density J_{sc} , open circuit voltage V_{oc} , fill factor FF, efficiency for energy conversion η) has been investigated.

2. Experimental

2.1. Deposition of the CdS QDs onto TiO₂ NPs photoanode

The nano TiO₂ paste was prepared by the following procedure of G. Syrokostas et al [17]. The CdS QDs were sensitized onto TiO₂ nanoparticles using SILAR method [18]. The photoanode is immersed for one min in 0.1 M (Cd(NO₃)₂·H₂O) in methanol as a cation source (Cd²⁺) and to be adsorbed on the TiO₂ electrode. The TiO₂ electrode was then rinsed with methanol to remove the excess Cd²⁺ cations. Then the photoanode is immersed in 0.1 M Na₂S methanolic solution as the anion source (S²⁻) for one min in order to react with Cd²⁺ cations followed by methanol rinsing. This procedure was referred to as one SILAR cycle. Five samples obtained at increasing number of cycles labeled a, b, c, d and e for 2, 4, 6, 8 and 10 cycles, respectively. The counter electrodes were prepared by coating another Fluorine-doped Tin Oxide (FTO) substrate of resistance of 7 Ω /sq

with platinum (Pt).

2.2. Deposition of the Cu₂S QDs onto TiO₂/CdS10 QDs photoanode

In this part, the Cu₂S QDs were deposited onto TiO₂/CdS10 (sample e which has high efficiency) by the same method (SILAR technique). The photoanode is immersed for 1 min in 0.1 M (CuNO₃)₂·4H₂O in methanol as a cation source (Cu⁺²) and to be adsorbed on the TiO₂ electrode. The TiO₂ electrode was then rinsed with methanol to remove the excess Cu⁺² cations. Then the photoanode is immersed in 0.1 M Na₂S methanolic solution as the anion source (S⁻²) for 1 min in order to react with Cu⁺² cations followed by methanol rinsing. We get also five samples at different cycles labeled a, b, c, d and e for 2, 4, 6, 8 and 10 cycles respectively.

2.3. Assembly of QDSSCs

QDSSCs were built by assembling the TiO₂ photoanodes sensitized with (CdS and CdS/Cu₂S), aqueous polysulfide electrolyte and the counter electrodes. Parafilm was used as spacer between the two electrodes and also as a sealing to prevent the evaporation of the electrolyte. The space between the two electrodes was filled by polysulfide electrolyte which was prepared by dissolving 1.1M Na₂S, 1.2 M S, and 0.12 M KCl in deionized water [19].

2.4. Characterizations and measurements

The UV-Vis absorption spectra were recorded using (Jasco 670 with 1cm quartz cuvettes) spectrophotometer. The size and morphology was determined using high resolution transmission electron microscopy (HRTEM, JEOL JEM-2100 operated at 200KV with high resolution Gatan CCD bottom camera, Orius SC200). Photovoltaic solar cell measurements were performed using a solar simulator device (San-Ei Electric XES-40S1) at AM 1.5 with 1 sun illumination intensity (100 mW/cm²), and current density–voltage (J–V) data were recorded using a source meter unit (Keithley SMU 2600).

3. Results and Discussion

3.1. Optical measurements of CdS QD

For TEM measurement, TiO₂/CdS layer in ethanol was scratched from FTO coated substrate without disturbing FTO layer and placed on Cu-coated carbon grid. Figure 1 shows the TEM image of TiO₂/CdS for sample (e). The average particle size for CdS QD were estimated to be approximately 5.4 nm and average particle size for TiO₂ is 22 nm.

Figure 2 show UV-visible absorption spectra for (TiO₂ and TiO₂ / CdS layer with increasing number of cycles by SILAR method). It can be seen that the TiO₂ layer shows an absorbance edge at 400 nm corresponding to 3.1 eV band gap. Also, there is a blue shift of absorbance edge with decreasing number of cycle. These are 401 nm, 414 nm, 431 nm, 451nm and 465 nm for samples (a, b, c, d and e) respectively. This blue shift is due to quantum confinement effect [20].

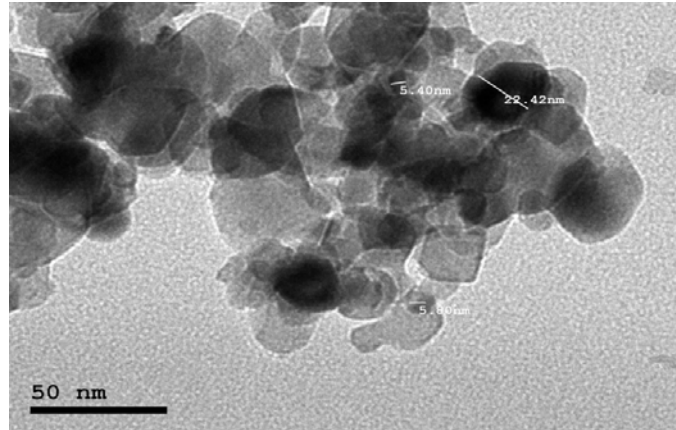


Figure 1: TEM image of TiO₂ / CdS QD for sample (e)

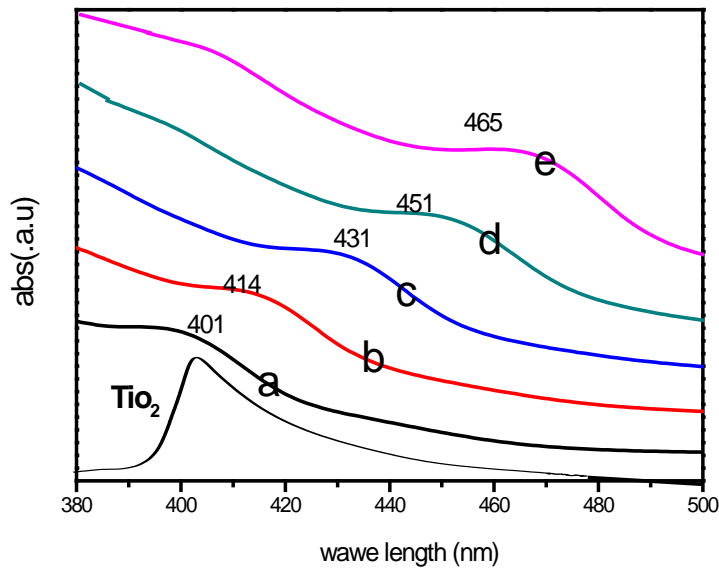


Figure 2: show UV-vis. absorption of TO₂/CdS QD electrode with different number of cycles by SILAR method

The particle size of CdS QD is calculated using the effective mass approximation (EMA) model [21-23].

$$E_{gn}(R) = E_{gb} + \frac{h^2}{8m^*R^2} - \frac{1.8e^2}{4\pi\epsilon\epsilon_0R} \tag{1}$$

where E_{gb} (2.4 ev) is the bulk band gap [21], E_{gn} is the nano band gap, R is the radius of the CdS quantum dots, m^* (7.62×10^{-32} kg) is the reduced mass [21], and ϵ (7.1) is the dielectric constant for CdS [21]. The average particle sizes of CdS QDs are obtained from UV.spectra and applied equation 1. The obtained values of CdS particle sizes ranged from 3.2 nm for sample (a) to 4.4 nm for sample (e) in close agreement with that

obtained by TEM measurements. The elemental analyses of the CdS QDs sensitized TiO₂ working electrode was measured using (EDX) (model JEOL JED-2300). Figure 3 shows the EDX spectra of TiO₂/CdS QDs sensitized working electrode where Cd, S, Ti and O atoms are indicated. This result ensures the adsorption of CdS QDs onto the TiO₂ electrode.

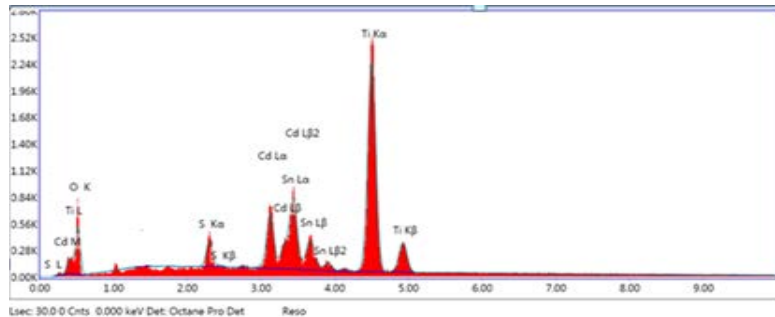


Figure 3: EDX of TiO₂/ CdS QD working electrode for sample e

3.2. Photovoltaic performance of CdS QDSSCs

Figure 4.a shows the J-V characteristics curves of CdS QDSSCs measured under a simulated sunlight with an intensity of 100 mW/cm² (AM 1.5G). The value of J_{sc} vs number of SILAR cycle of CdS QD are shown in Figure 4.b. The photovoltaic parameters V_{oc}, J_{sc}, FF and η for produced CdS QDSSCs are given in Table 1. It is clearly seen that as CdS QDs size increases, the values of J_{sc} and η increase. The maximum values of J_{sc} and η are 2.24 mA/cm² and 0.48% respectively for 10 cycles (sample e) of CdS QD. S.Abdallah et. al [24,25] has made measurement on CdS QD sensitized TiO₂ using the direct adsorption technique (DA) to anchor CdS QD onto TiO₂ substrate . They reported that, there are an increase of J_{sc} (from 0.31 mA/cm² to 0.67 mA/cm²) and η (from 0.05% to 0.18%) as the CdS particle size increase. Our results shows that an increase of J_{sc} (from 1.18 mA/cm² to 2.24 mA/cm²) and η increase (from 0.15 to 0.48) with increasing particle size of CdS QDs in agreement with their work .They attributed the increase in J_{sc} with increase particle size in a red shift and thus causes relativity high absorption of the incident photon from solar spectrum .Therefore, particle size of CdS QD 4.4 nm (correspond to 465 nm) harvest more visible photon than the other particle. However , our results show an improvement of the J_{sc} and (η) than their work by 266 % which may be ,due to the SILAR technique is being better method than DA technique to give high-quality surface spread, lower aggregation ,higher photocurrents, longer lifetimes of electron and solve problem of surface chemistry which lead to improve QDSSCs [26].

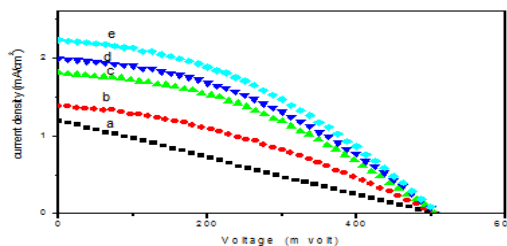


Figure 4.a: J-V characteristic curve of QDSSCs of CdS QDs with different size (different cycle)

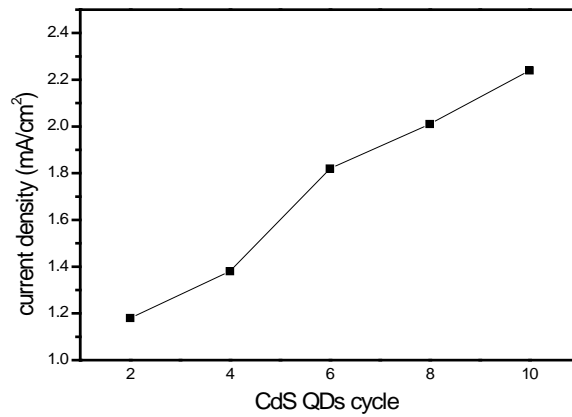


Figure 4.b: Variation of the current density as a function of SILAR cycles of CdS QD

Table 1: J -V characteristics parameters of a CdS QDSSCs for different QDs sizes, under 1 sun illumination.

Sample	V _{oc} (m Volt)	J _{sc} (mA/cm ²)	FF	η(%)
TiO ₂ /CdS	± 0.01			± 0.01
a	508	1.18± 0.01	0.24	0.15
b	505	1.38± 0.02	0.35	0.24
c	504	1.82± 0.01	0.39	0.37
d	509	2.01± 0.01	0.38	0.42
e	510	2.24± 0.01	0.40	0.48

3.3. Optical measurements of CdS10/Cu₂S QD

In this part, the Cu₂S QDs were deposited onto TiO₂/CdS(10) photoanodes by SILAR method (which has higher J_{sc} and η). Figure 5 shows the UV spectra of TiO₂/CdS10/Cu₂S photoanode for different number of cycle. The absorption edges varies between 487 nm for sample a with a corresponding band gap of 2.55 eV to 553 nm for sample e with a corresponding band gap of 2.24 eV which should be ascribed to the contribution of Cu₂S, since its band gap was reported to be 1.2 eV [15].It was also noted that, the absorption intensity of this band gradually increased with the increasing amount of Cu₂S in CdS.

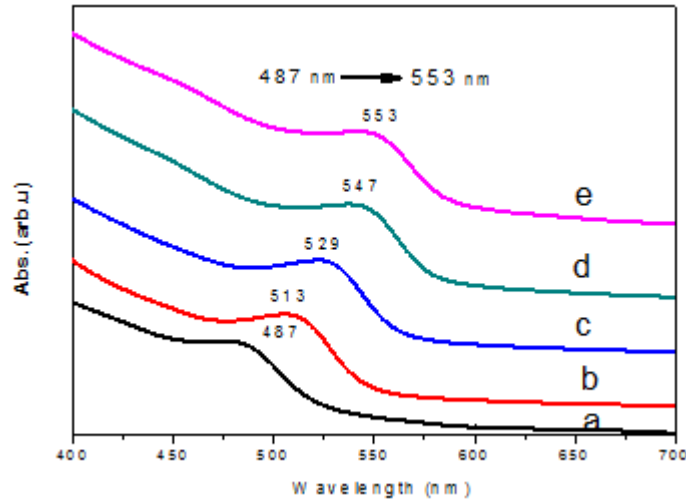


Figure 5: show UV-vis. absorption of $\text{TO}_2/\text{CdS10}/\text{Cu}_2\text{S}$ QD electrode with different number of cycles by SILAR method

3.4. Photovoltaic performance of $\text{Cu}_2\text{S}/\text{CdS}$ QDSSCs

Cu_2S Figure 6 shows the J-V characteristics curves of $(\text{CdS10}/\text{Cu}_2\text{S})$ QDSSCs measured under a simulated sunlight with an intensity of $100 \text{ mW}/\text{cm}^2$ (AM 1.5G). The photovoltaic parameters (V_{oc} , I_{sc} , FF and η) for all the sample are obtained and given in Table 2.

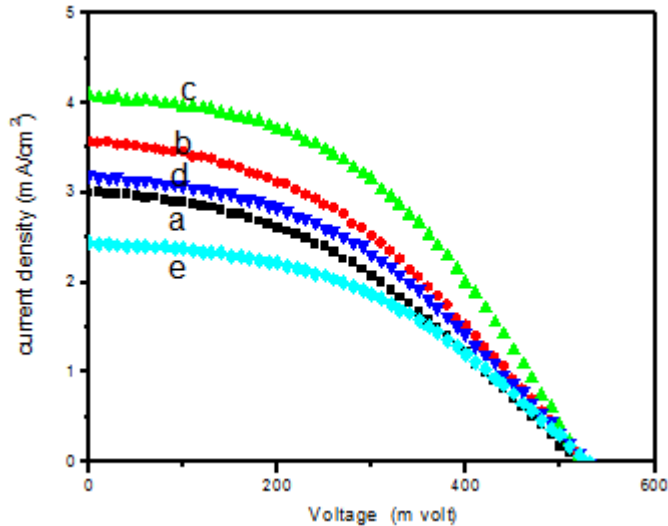


Figure 6: J-V characteristic curve of QDSSCs of $\text{CdS10}/\text{Cu}_2\text{S}$ QDs with different cycle

It is clearly seen that as Cu_2S QDs SILAR cycles increases, the values of J_{sc} and η increases peaking at $4.01 \text{ mA}/\text{cm}^2$ and 1.21% respectively for 6 cycles (sample c) which about 252% larger than TiO_2/CdS . These values decrease for sample d ($3.56 \text{ mA}/\text{cm}^2$ and 0.96%) and sample e ($2.60 \text{ mA}/\text{cm}^2$ and 0.73%). The increase of J_{sc} and η can be explained by two effect .First effect , due to the relative narrow band gap of Cu_2S (1.2 ev) [15] , Cu_2S can increase the utilization efficiency of the incident light , and result in the more efficient charge

separation in CdS QD , which can improve the transportation of the photosensitized electron and reduce the recombination of the photosensitized electron and hole , so the performance of the whole efficiency will be promoted in turn [27].

Table 2: J -V characteristics parameters of CdS10/ Cu₂S QDSSCs for different QDs cycles, under 1 sun illumination.

sample	V _{oc} (mV)) ± 0.01	J _{sc} (mA/cm ²)	FF	η(%) ± 0.01
a	520	3.01± 0.01	0.41	0.52
b	531	3.72± 0.02	0.40	1.06
c	527	4.01± 0.03	0.49	1.21
d	525	3.56± 0.01	0.48	0.96
e	527	2.60± 0.01	0.41	0.73
CdS10	510	2.24	0.42	0.48

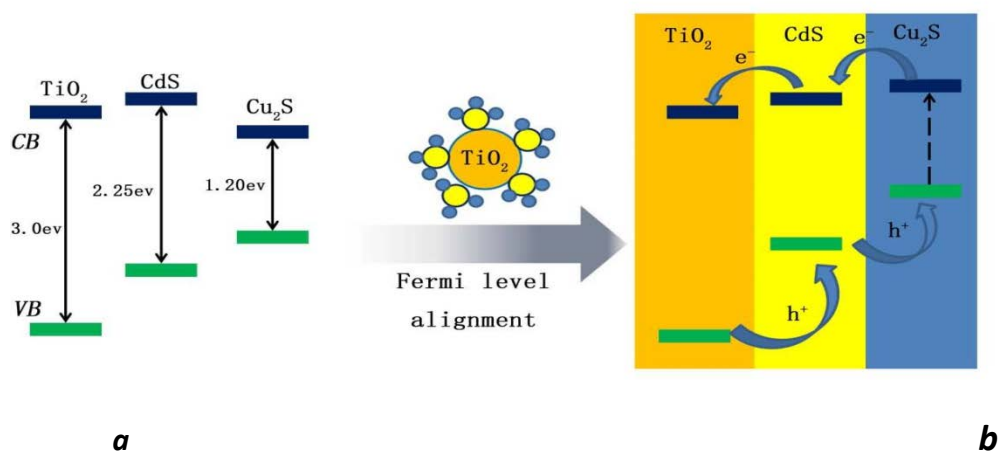


Figure 7.a: Relative band positions of TiO₂, CdS and Cu₂S in bulk and ideal stepwise structure

Figure 7.b: band edges for the efficient transport of the excited electrons and holes in TiO₂/CdS/Cu₂S photoelectrode

Second effect, when TiO₂, CdS and Cu₂S are in bulk. Their band gap are 3.2 eV, 2.25 eV and 1.20 eV, respectively can be seen in Figure 7.a. Therefore, their band gap cannot match well to provide a good path for the transportation of the electrons due to that the conduction band of Cu₂S is lower than that of CdS, which inhibit the photosensitized electrons transport from the Cu₂S to CdS [27]. When Cu₂S nanoparticles were coated on the CdS QDs a great number of nanoscale heterostructure between the two semiconductors could be produced. The band gap alignment of TiO₂ CdS/ Cu₂S has been reported by Y.Chen and his colleagues [15], as shown in Figure 7.b. It is easily observed that the conduction band (CB) of CdS is lower than (CB) of Cu₂S lead to the electron transfer occurred from Cu₂S to CdS, and eventually to TiO₂ [27]. While the hole transfer occurred from TiO₂ to CdS and then from CdS to Cu₂S due to the different Fermi levels alignment when the system reached equilibration state. And when the Cu₂S SILAR reached 6 cycles, the interaction between Cu₂S and CdS achieved the best effect. Our result show the increase of J_{sc} from 2 cycle (Sample a) 3.01 mA cm⁻² to 6 cycle (sample c) 4.01 mA cm⁻² support this argument. The decrease of J_{sc} for sample d and e are attributed to beyond 6 cycle CdS QD nearly covered by Cu₂S nanoparticles, which would reduce the formation of more heterostructure and affect the efficient utilization of light by CdS nanoparticles. Additionally, the increase of Cu₂S cycles led to an increase in the thickness which takes a longer time for the electron to reach the TiO₂. Therefore, the probability of recombination or trapping of the generated holes would be higher, causing the photocurrent to decrease [28].

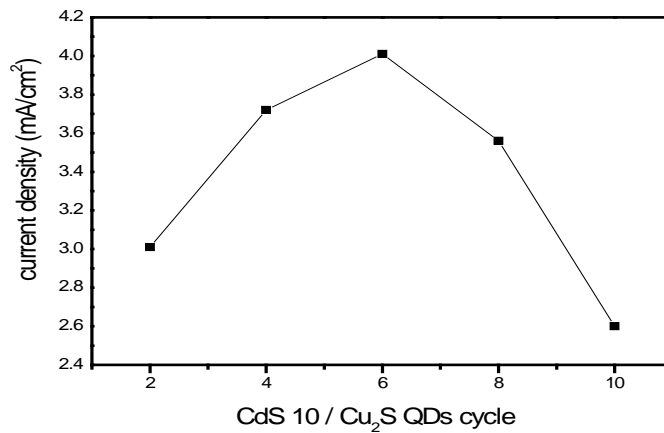


Figure 8: Variation of the current density as function of SILAR cycles of Cu₂S QD

The value of J_{sc} vs number of SILAR cycle of Cu₂S QD is shown in Figure 8.

4. Conclusions

CdS QDs were adsorbed onto TiO₂ nanoparticle electrode using SILAR method to act as sensitizer for QDSSCs. The absorption edges of TiO₂/CdS photoanode are red shift as the number of cycle increases from 2 to 10. EDX measurements ensures the success of adsorption of CdS QDs onto the TiO₂ electrode. The values of J_{sc} and η for CdS QDs solar cell increase as the number of cycle increase. Such an increase may be result from the

improving of photo-absorption efficiency and charge separation of TiO₂/CdS solar cell. Furthermore, Cu₂S were adsorbed onto TiO₂ / CdS (10) cycles (which has higher efficiency) with different cycles. The absorption edges of TiO₂/CdS10/Cu₂S photoanode are red shift from 487 nm to 553 nm as the number of cycle increases from 2 to 10 which should be ascribed to the contribution of Cu₂S. The maximum values of J_{sc} (3.56 mA/cm²) and η (1.21%) are obtained for sample CdS10/Cu₂S for 6 cycles of Cu₂S which about 252% larger than TiO₂/CdS. The improvement of J_{sc} and η are due to the formation of heterostructure between CdS and Cu₂S which causes the conduction band (CB) of CdS is lower than (CB) of Cu₂S . Thus more electrons can be transfer from Cu₂S to CdS and injected to TiO₂ nanoparticle electrode.

Acknowledgements

The authors would like to express their sincere gratitude to Ain Shams University and the Physics Department at Ain Shams University for their financial and technical support in performing and finishing this work.

References

- [1] A.Badawi , N.Y. Mostafa , N.M. Al-Hosiny , A.Merazga , A.M. Albaradi , F. Abdel- Wahab and A. A. Atta. " The photovoltaic performance of Ag₂S quantum dots- sensitized solar cells using plasmonic Au nanoparticles/TiO₂ working electrodes" Modern Physics Letters B, 1850172 (2018): 1-17.
- [2] S.K. Kokate, A.T. Supekar, P.K. Baviskar, B.M. Palve, S.R. Jadkar, K.C. Mohite, H.M. Pathan, "CdS sensitized pristine and Cd doped ZnO solar cells: Effect of SILAR cycles on optical properties and efficiency, Materials Science in Semiconductor Processing, 80 (2018)p. 179-183.
- [3] P.Yu, , et al., "Nanocrystalline TiO₂ Solar Cells Sensitized with InAs Quantum Dots". J. Phys. Chem. B, 110(2006) p. 25451-25454.
- [4] N.Guijarro, et al., "CdSe Quantum Dot-Sensitized TiO₂ Electrodes: Effect of Quantum Dot Coverage and Mode of Attachment". J. Phys. Chem. C, 113(2009) p. 4208-4214.
- [5] J.H.Bang and P.V. Kamat, "Quantum Dot Sensitized Solar Cells. A Tale of Two Semiconductor Nanocrystals: CdSe and CdTe". ACS NANO, 3(2009) p. 1467–1476.
- [6] P.Sudhagar, et al., "The performance of coupled (CdS:CdSe) quantum dot-sensitized TiO₂ nanofibrous solar cells". Electrochemistry Communications. 11(2009) p. 2220-2224.
- [7] K.Tvrđy , P.A. Frantsuzov, and P.V. Kamat, "Photoinduced electron transfer from semiconductor quantum dots to metal oxide nanoparticles". PNAS, 108(1)(2011) p. 29-34.
- [8] I.Barceló, T. Lana-Villarreal, and R. Gómez, "Efficient sensitization of ZnO nanoporous films with CdSe QDs grown by Successive Ionic Layer Adsorption and Reaction (SILAR) ". Journal of Photochemistry

and Photobiology A: Chemistry, 220(1)(2011) p. 47-53.

- [9] A.Badawi , N.Al-Hosiny , S.Abdallah and H.Talaat, "Tuning photocurrent response through size control of CdSe quantum dots sensitized solar cell".Material Science and Semiconductor Processing ,31 (2013)p. 6-13 .
- [10] N.Al-Hosiny , S.Abdallah , A.Badawi , K.Easawi and H.Talaat, "The photovoltaic performance o alloy CdTe_xS_{1-x} quantum dot sensitized solar cells " Material Science and Semiconductor Processing ,26 (2014)p. 238-243. .
- [11] A.Badawi , N.Al-Hosiny , S.Abdallah , S.Negm and H.Talaat, "Tuning photocurrent response through size control of CdTe quantum dots sensitized solar cell". Solar energy ,88 (2013)p. 137-143 .
- [12] Kokate, Sunita K., Chaitali V. Jagtap, Prashant K. Baviskar, Sandesh R. Jadkar, Habib M. Pathan, and Kakasaheb C. Mohite. "CdS sensitized cadmium doped ZnO solar cell: Fabrication and characterizations" .Optik-International Journal for Light and Electron Optics 157 (2018): 628-634.
- [13] A.Badawi, N. Al-Hosiny, Amar Merazga, Ateyyah M. Albaradi, S. Abdallah, and H. Talaat. "Study of the back recombination processes of PbS quantum dots sensitized solar cells." Superlattices and Microstructures" 100 (2016).p 694-702.
- [14] Yang, Peizhi, Q.Tang, Chenming Ji, and H.Wang. "A strategy of combining SILAR with solvothermal process for In₂S₃ sensitized quantum dot-sensitized solar cells." Applied Surface Science.357 (2015)p. 666-671.
- [15] Y. Chen, Z. Qin, X. Wang, X. Guo, L. Guo, "Noble-metal-free Cu₂S-modified photocatalysts for enhanced photocatalytic hydrogen production by forming nanoscale p–n junction structure" RSC Adv., 5 (2015) p.18159-18166.
- [16] A.Badawi, "Photoacoustic study of alloyed Cd_{1-x}Pb_xS quantum dots sensitized solar cells electrodes"2016 DOI 10.1007/s10854-016-4781-1.2016.
- [17] G.Syrrokostas, M.Giannouli and P.Yianoulis. "effects of paste storage on the properties of nanostructured thin films for the development of dye-sensitized solar cell." Renewable Energy ,34 (2009)p.1759-1764.
- [18] A Hessein, A. Abd El-Moneim, "Synthesis of copper sulfide/reduced graphene oxide nanocomposites for use as the counter electrodes of high-performance CdS-sensitized solar cells", New Carbon Materials , 33(2018)p.26-35.
- [19] H.Thanh, Tung, D.Huynh Thanh, and V.Quang Lam. "The CdS/CdSe/ZnS photoanode cosensitized solar cells basedon Pt, CuS, Cu₂S, and PbS counter electrodes." Advances in OptoElectronics" 9

(2014)p.23-37.

- [20] A. Badawi "Tunable energy band gap of $Pb_{1-x}Co_xS$ quantum dots for optoelectronic application" Superlattices and Microstructures , <https://doi.org/10.1016/j.spmi.2018.11.012>.
- [21] A. Badawi, N. Al-Hosiny, S. Abdallah, "The photovoltaic performance of CdS quantum dots sensitized solar cell using graphene/TiO₂ working electrode", Superlattices and Microstructures 81 (2015) p.88–96.
- [22] Heba Hassan, T. Abdallah, S. Negm, and H. Talaat. "Rabi like angular splitting in Surface Plasmon Polariton–Exciton interaction in ATR configuration." Applied Surface Science " 441(2018).p. 341-346.
- [23] M. Nabil, K. Easawi, T. Abdallah, S. Abdallah, M. K. Elmancye, S. Negm, H.Talaat, "Performance Enhancement of TBAI Capped CdSeQuantum Dot Sensitized Solar Cells by an Interlayer Gold Nanoparticle", American Scientific Research Journal for Engineering, Technology and Science(ASRJETS) 53(2019)p. 27-42.
- [24] S. Abdallah, N. Al-Hosiny, A. Badawi, "Photoacoustic Study of CdS Semiconductor Nanoparticles For Solar Cell Applications" Journal of Nanomaterial,1(2012)p.1-6.
- [25] S. Abdallah, N. Al-Hosiny, A. Badawi, "Photoacoustic Study of CdS Semiconductor Nanoparticles For Solar Cell Applications" MSTI-Nanoteck,1(2012)p.55-60.
- [26] W.Li , X,Zhong "Capping Ligand-Induced Self-Assembly For Quantum Dot Sensitized Solar Cell ", Journal physical chemistry letters , 6(2015)p.796-806.
- [27] L.Tang, Y. Deng, G. Zeng, W. Hu, J.Wang, Y.Zhou, J. Wang, J. Tang , "CdS/Cu₂S co-sensitized TiO₂ branched nanorod arrays of enhanced photoelectrochemical properties by forming nanoscale heterostructure "Journal of alloys and compound , 662(2016)p.516-527.
- [28] S.Abdallah " The Performance of Alloyed ($CdS_{0.33}Se_{1.67}$) Quantum Dots –Sensitized TiO₂ solar cell "physics of semiconductor devices,48(2014)p.1385-1390.