

# ENGINEERING JOURNAL

*Article*

## Metathesis of Ethylene and *Trans*-2-Butene over MgO Admixed WO<sub>3</sub>/SiO<sub>2</sub> Catalysts

Prinyanee Suttibut, Piyasan Prasertthdam, and Joongjai Panpranot\*

Center of Excellence on Catalysis and Catalytic Reaction Engineering, Department of Chemical Engineering, Faculty of Engineering, Chulalongkorn University, Bangkok 10330, Thailand

\*E-mail: [joongjai.p@chula.ac.th](mailto:joongjai.p@chula.ac.th) (Corresponding author)

**Abstract.** The performances of MgO admixed WO<sub>3</sub>/SiO<sub>2</sub> catalysts were investigated in the cross metathesis of ethylene and 2-butene to propylene at 450°C atmospheric pressure. Compared to the WO<sub>3</sub>/SiO<sub>2</sub> + silica gel, the conversion of 2-butene and the propylene selectivity were much higher on all the WO<sub>3</sub>/SiO<sub>2</sub> + MgO catalysts. An increased propylene yield corresponded to the decrease in 1-butene and *cis*-2-butene by products. The results in this study also suggest suitable method to prepare highly stable MgO catalysts in order to maximize the propylene yield.

**Keywords:** Metathesis, 2-butene, propylene production, MgO, WO<sub>3</sub>/SiO<sub>2</sub>.

**ENGINEERING JOURNAL** Volume 21 Issue 1

Received 25 February 2016

Accepted 10 May 2016

Published 31 January 2017

Online at <http://www.engj.org/>

DOI:10.4186/ej.2017.21.1.1

## 1. Introduction

Due to the highly demanded propylene in the market, the cross metathesis of ethylene and 2-butene to propylene is of a great interest for both academia and industry [1, 2]. Among the most successful heterogeneous olefin metathesis catalysts including Mo, W, and Re in oxide form supported on high surface area inorganic oxides such as silica and alumina, the W-based catalysts receive much more attention for commercial use due to their long lifetime, considerable resistance to poisoning and low price [3, 4]. However, because they are active at relatively high reaction temperature, side reactions and lower selectivity are inevitable. In addition, the catalyst performances are often dependent on the metal precursor, the preparation method, and modification of the supports [4, 5].

During the metathesis of ethylene and 2-butene, 1-butene in feedstock can interfere ethylene and 2-butene metathesis by competitively metathesizing with 2-butene resulting in higher molecular weight hydrocarbon formation as a by-product. In order to avoid this by-product formation, double-bond isomerization catalysts, such as magnesium oxide (MgO), may be used to isomerize 1-butene to 2-butene as 2-butene is consumed in the reaction [6]. According to the US patent number 8,586,813 (2013) [6], MgO catalysts may be mixed with metathesis catalysts for performing both double-bond isomerization and metathesis in the same reactor. MgO is a particularly preferred basic isomerization catalyst. It is expected that a double-bond isomerization catalyst can convert 1-butene to 2-butenes during the metathesis reaction, thus increase the propylene yield of the metathesis reaction [7].

Typically, MgO contains numerous basic sites of various strength (strong: low coordination  $O^{2-}$  anions, medium: oxygen in  $Mg^{2+}-O^{2-}$  pairs, and weak: surface  $OH^-$  groups). The isomerization activity of MgO, however, has often been found to be related to the presence of some specific low coordinated sites such as step, edge, and corner sites. A recent study from our group showed that rearrangement of the MgO structure occurred upon  $N_2$  pretreatment at 325°C followed by isomerization reaction at 125°C [8]. Thus, it is interesting to investigate how the restructuring of MgO catalysts may affect the performances of the MgO admixed with W-based catalysts in the metathesis reaction.

In the present work, MgO catalysts, which were prepared by co-precipitation, solvothermal, and sol-gel methods, were physically mixed with the 9 wt%  $WO_3/SiO_2$  catalysts and tested in the cross metathesis of ethylene and 2-butene for propylene production in a single catalyst bed reactor. The physicochemical properties of MgO were characterized by means of X-ray diffraction (XRD),  $N_2$  physisorption, Fourier-transformed infrared spectroscopy (FT-IR), scanning electron microscopy (SEM), thermogravimetric analysis (TGA), and basicity titration. The catalytic activity, propylene yield, and product distribution of metathesis reaction were correlated to the reactivity and characteristics of the MgO co-catalysts, which depended on the preparation protocols used.

## 2. Experimental

### 2.1. Synthesis of MgO Catalysts

The MgO catalysts were prepared by three different routes namely co-precipitation (CP), sol-gel (SG), and solvothermal (SV) using magnesium nitrate hexahydrate ( $Mg(NO_3)_2 \cdot 6H_2O$ ) (Ajax Finechem) and potassium hydroxide (KOH) (AnalaR) as the starting materials. For the CP method, firstly, 0.8 M of  $Mg(NO_3)_2 \cdot 6H_2O$  and 0.9 M of KOH solutions were prepared in de-ionized water. These two solutions were added dropwise into 200  $cm^3$  of deionized water under vigorous stirring. The pH was controlled at 11-12. The complete solution was separated by centrifuging and washed in de-ionized water. The wet white solid was dried in ambient air overnight at 80°C and then calcined at 500°C for 4 h in air.

The MgO catalysts were prepared by SG according to the procedure described in Tamilselvi et al. [9]. Firstly, 0.2 M  $Mg(NO_3)_2 \cdot 6H_2O$  was dissolved in de-ionized water then 0.4 M NaOH was added dropwise under sonication and mixed at room temperature for 2 h. The precipitation formed was washed by de-ionized water and followed by ethanol. After that the wet solid was dried at 110°C for 24 h. Finally, the white solid was calcined at 500°C for 4 h in air. The procedure described by Hadia et al. [10] was employed for the preparation of MgO catalysts by the SV method. The solvent containing ethanol and water was firstly prepared in equal volume ratio. Then 6 g of NaOH were added to 70  $cm^3$  of the mixed solvent and stirred until completely mixed. 3.446 g of  $Mg(NO_3)_2 \cdot 6H_2O$  were added to the solution and stirred vigorously. Then the white precipitate was transferred to an autoclave chamber and placed inside a

pretreated oven at 180°C for 10 h. The precipitation formed was filtered and washed by de-ionized water and followed by ethanol. After that the wet solid was dried at 80°C for 2 h. Finally, the white solid was calcined at 500°C for 4 h in air. The MgO catalysts prepared by CP, SG, and SV methods are denoted as MgO(CP), MgO(SG), and MgO(SV), respectively.

## 2.2. Synthesis of WO<sub>3</sub>/SiO<sub>2</sub> Catalysts

The WO<sub>3</sub>/SiO<sub>2</sub> catalysts with 9 wt% tungsten loading were prepared by the incipient wetness impregnation of an aqueous solution of ammonium metatungstate hydrate (Aldrich) over silica gel (Aldrich, Davisil grade 646). The catalysts were dried at room temperature for 2 h and 110°C for overnight. Finally, the white solid was calcined in a tubular furnace at 500°C for 4 h in air to remove any residue.

## 2.3. Catalyst Characterization

The XRD patterns of catalysts were obtained using a Bruker D8 Advance X-ray diffractometer, with CuK<sub>α</sub> radiation and a Ni filter in 10-80° 2θ angular region. The BET surface area, pore size, and pore volume of the catalysts were calculated by N<sub>2</sub> physisorption using a Quadrasorb evo (QDS-30) automated system. The functional groups on catalyst surface were identified by FT-IR using a Nicolet 6700™ spectrometer in the range of 400-1000 cm<sup>-1</sup> and 3200-3800 cm<sup>-1</sup>. The weight loss of catalysts was measured by thermal gravimetric analysis (TGA) using a SDT Q6000. SEM micrographs of catalysts were obtained with a Hitachi S3400N scanning electron microscope. The amounts of basic sites were measured by titration technique according to the procedure explained by Pokrovsky et al. [11].

## 2.4. Reaction Study

The isomerization of 1-butene was carried out in a stainless steel flow reactor at 325°C and atmospheric pressure. Feed gas was composed of 10% 1-butene in nitrogen (Linde PLC, Thailand). Approximately 1.5 g of the MgO catalyst was packed in the reactor. The feed gas flowrate was 12 cm<sup>3</sup>min<sup>-1</sup> with the gas hourly space velocity (GHSV) 231 h<sup>-1</sup>. Before the reaction tests, the MgO catalysts were pretreated at 325°C under continuous flow of N<sub>2</sub> (ultra-high purity from Linde (Thailand) PLC) with flow rate 30 cm<sup>3</sup>/min for 1 h. The products were analyzed by Agilent 7820A online gas chromatography equipped with FID detector.

The metathesis of *trans*-2-butene and ethylene was carried out in the same reactor at 450°C and atmospheric pressure. The reaction was conducted for 5 h. Feed gas was composed of 2% *trans*-2-butene and excess of ethylene in nitrogen provided by Linde (Thailand) PLC. Approximately 1.5 g of the MgO catalyst and 1.5 g of WO<sub>3</sub>/SiO<sub>2</sub> were physical mixed and then were packed in the reactor. The feed gas flow rate was 12 cm<sup>3</sup>/min with the gas hourly space velocity (GHSV) 257 h<sup>-1</sup>. Before the reaction tests, the WO<sub>3</sub>/SiO<sub>2</sub> + MgO mixed catalysts were pretreated at 450°C under continuous flow of N<sub>2</sub> (ultra-high purity from Linde (Thailand) PLC) with flow rate 30 cm<sup>3</sup>/min for 1 h. The products were analyzed by Agilent 7820A online gas chromatography equipped with FID detector.

## 3. Results and Discussion

### 3.1. Physicochemical Properties of the As-Prepared MgO Catalysts

The physicochemical properties of the as-prepared MgO catalysts are shown in Table 1. Among the different preparation methods used in this study, the SV method produced nanocrystalline MgO with the largest BET surface area (102 m<sup>2</sup>/g). The surface area of the MgO obtained from the CP and SG methods were ranged between 72-88 m<sup>2</sup>/g. Despite their lower surface area, the MgO(SG) exhibited higher amount of basicity as measured by the titration technique. The XRD patterns of the prepared MgO catalysts are shown in Fig. 1. All the prepared catalysts exhibited only the MgO phase, which were apparent at 2θ degrees = 36.8°, 42.6°, 62.1°, 74.6°, and 78.4°. However, the average crystallite size of the MgO(SG) was much larger (23 nm) than those prepared by CP and SV methods (average crystallite size ~ 9 nm). The adsorption-desorption isotherms of the MgO catalysts are shown in Fig. 2. The MgO(CP) and MgO(SV) catalysts exhibited type IV isotherm with a hysteresis loop that associated with the mesoporous

characteristics whereas most of the pores in the MgO(SG) were macropores. The catalyst morphology is shown by the SEM micrographs in Fig. 3 as agglomeration of irregular aggregates.

The TGA measurements were carried out on the fresh catalysts after exposed in air at room temperature for 3 days and the results are shown Fig. 4. The weight loss of catalysts was found to be in the order: MgO(CP) 34.3% > MgO(SV) 24.3% > MgO(SG) 21.3%. The first region of weight loss occurred at 40°C - 250°C was attributed to the removal of the physisorbed water molecules. The major weight loss at around 250°C - 450°C was attributed to the decomposition of magnesium hydroxide to magnesium oxide. The decomposition of Mg(OH)<sub>2</sub> to form MgO was suggested to complete in the temperature region 500°C - 680°C [12].

Table 1. The BET surface area, pore volume, average pore size, average crystallite size, and basicity of MgO catalysts (based on XRD patterns and titration technique).

Catalyst	BET (m <sup>2</sup> /g)	Pore volume (cm <sup>3</sup> /g)	XRD crystallite size (nm)	Basicity titration (μmol/g)
Fresh Catalyst				
Fresh-MgO(CP)	88.1	0.6	MgO (8.6)	2000
Fresh-MgO(SV)	102	0.3	MgO (9.2)	2000
Fresh-MgO(SG)	71.6	1.7	MgO (22.9)	3000

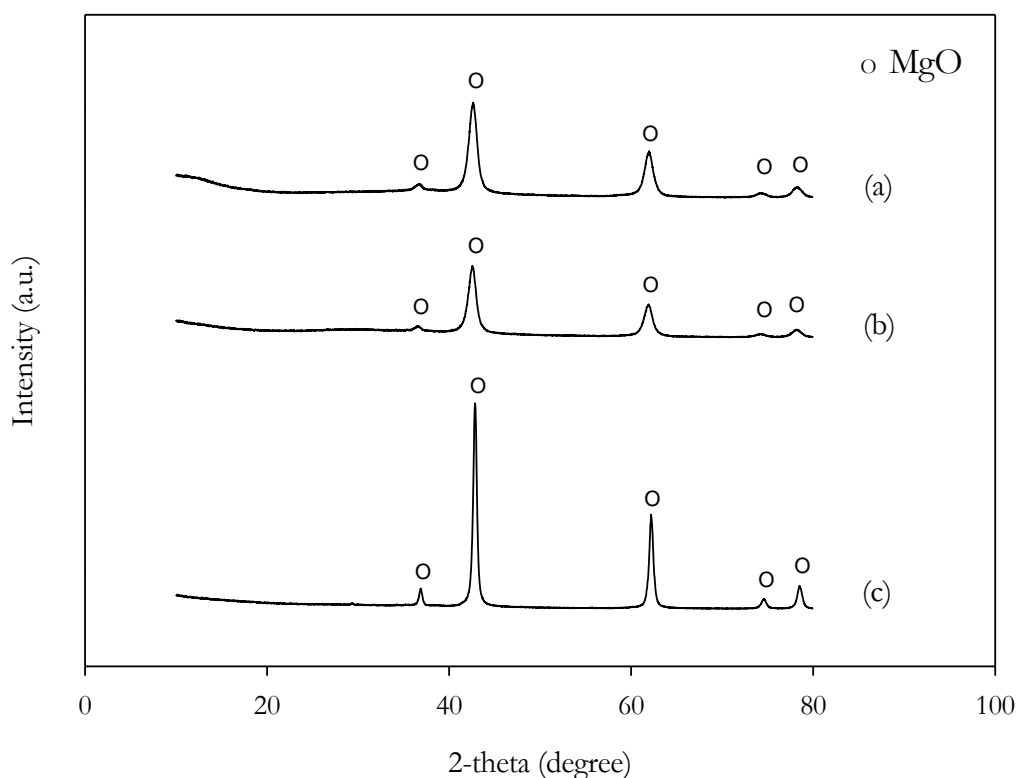
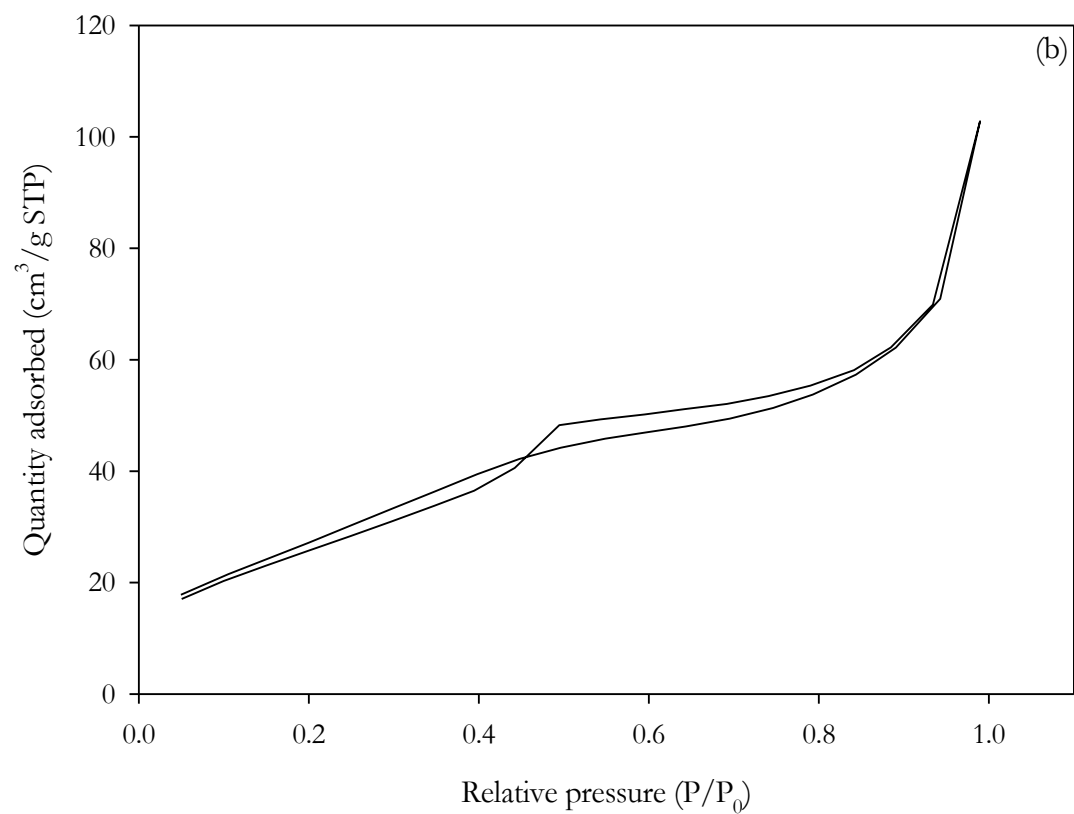
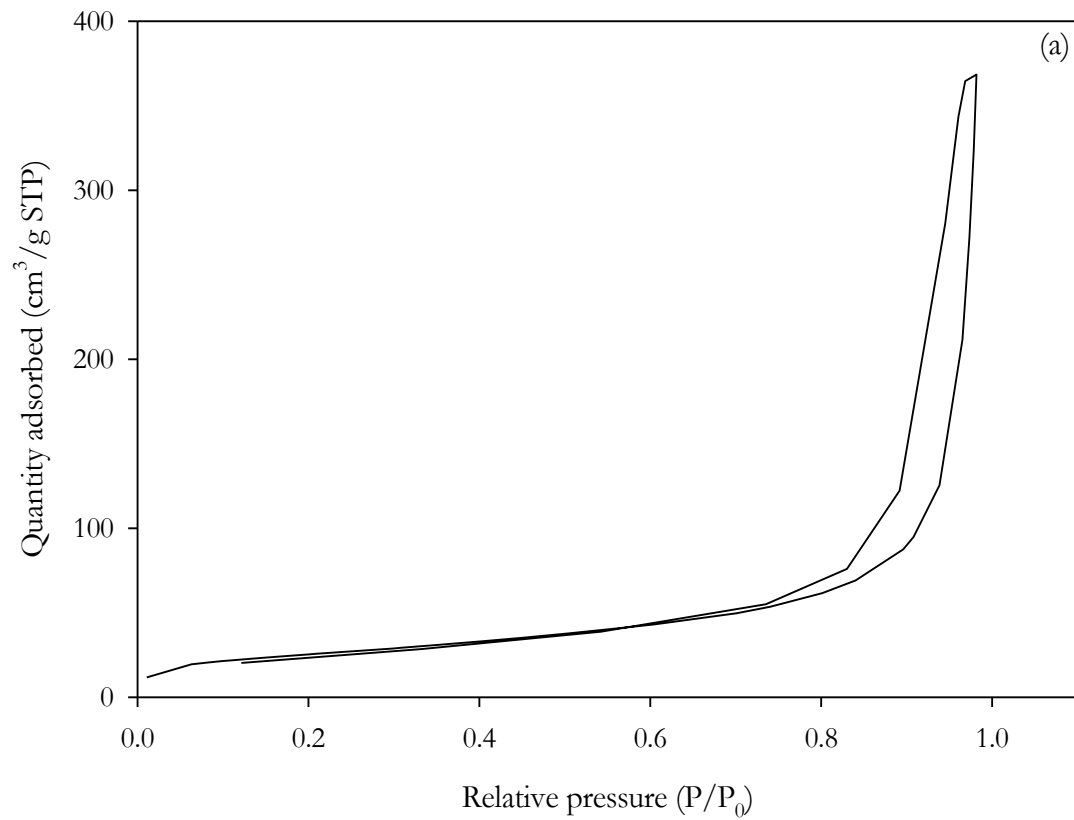


Fig. 1. The XRD patterns of the as-prepared MgO catalysts: (a) MgO(CP); (b) MgO(SV); (c) MgO(SG).



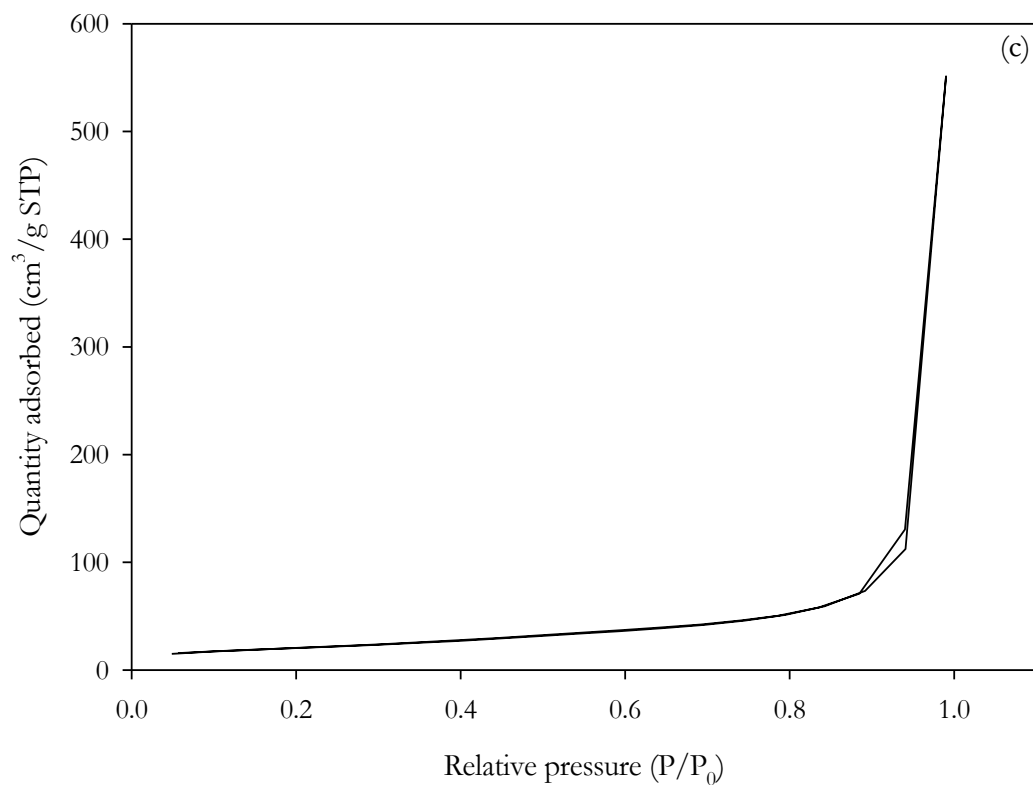


Fig. 2. The N<sub>2</sub> adsorption–desorption isotherm of the as-prepared MgO catalysts: (a) MgO(CP); (b) MgO(SV); (c) MgO(SG).

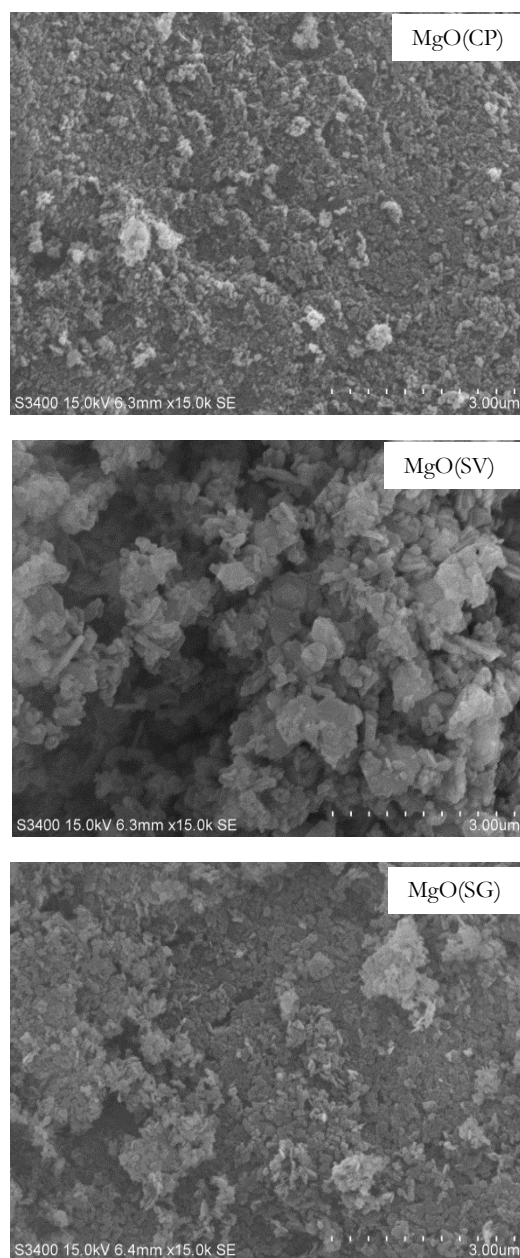


Fig. 3. The SEM micrographs of the as-prepared MgO catalysts.

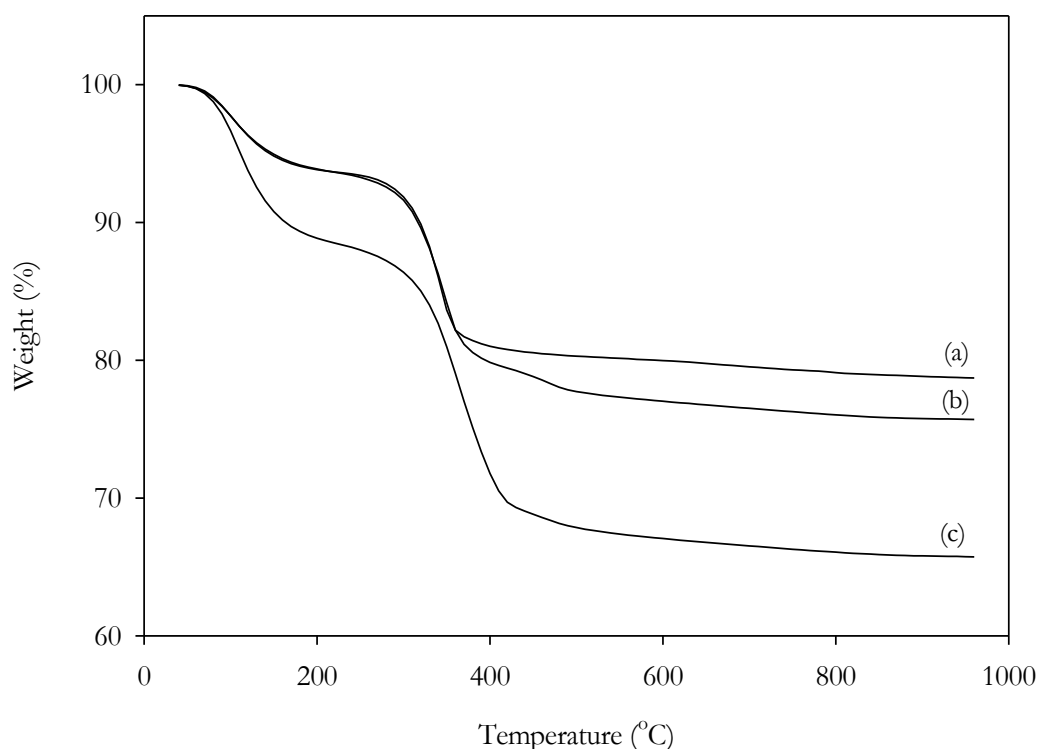


Fig. 4. The TGA of fresh MgO catalysts after exposed in air at room temperature for 3 days: (a) fresh-MgO(SG)- RT 3 days; (b) fresh-MgO(SV)-RT 3 days; (c) fresh-MgO(CP)-RT 3 days.

### 3.2. Isomerization of 1-Butene on MgO Catalysts

All the prepared MgO catalysts were tested in the isomerization of 1-butene to 2-butene at 325°C and atmospheric pressure. The conversions of 1-butene and 2-butene selectivity as a function of reaction time obtained on the various MgO catalysts are shown in Fig. 5. All the MgO catalysts exhibited relatively high isomerization activity (1-butene conversion 77-79%) with 2-butene selectivity > 99%. From the characterization results, the isomerization activity may be correlated to the reactivity of the catalysts for OH adsorption (the TGA results). Such findings follow the more recent trend showing the dependence of MgO reactivity on the presence of specific low coordinated sites such as step, edge, and corner sites rather than on the total number of basic sites [13]. A correlation between the catalytic activity of MgO and the amount of OH groups has been reported by Chizallet et al. [14]. The catalytically active sites were identified as  $O_{1C}H$  and  $O_{2C}H$  formed by hydroxylation of the steps, corners and  $O^{2-}_{3C}$ -terminated kinks. A recent study by Petitjean et al. [15] also showed that the partial hydroxylated MgO catalyzed basic MBOH conversion better than the dehydroxylated MgO.



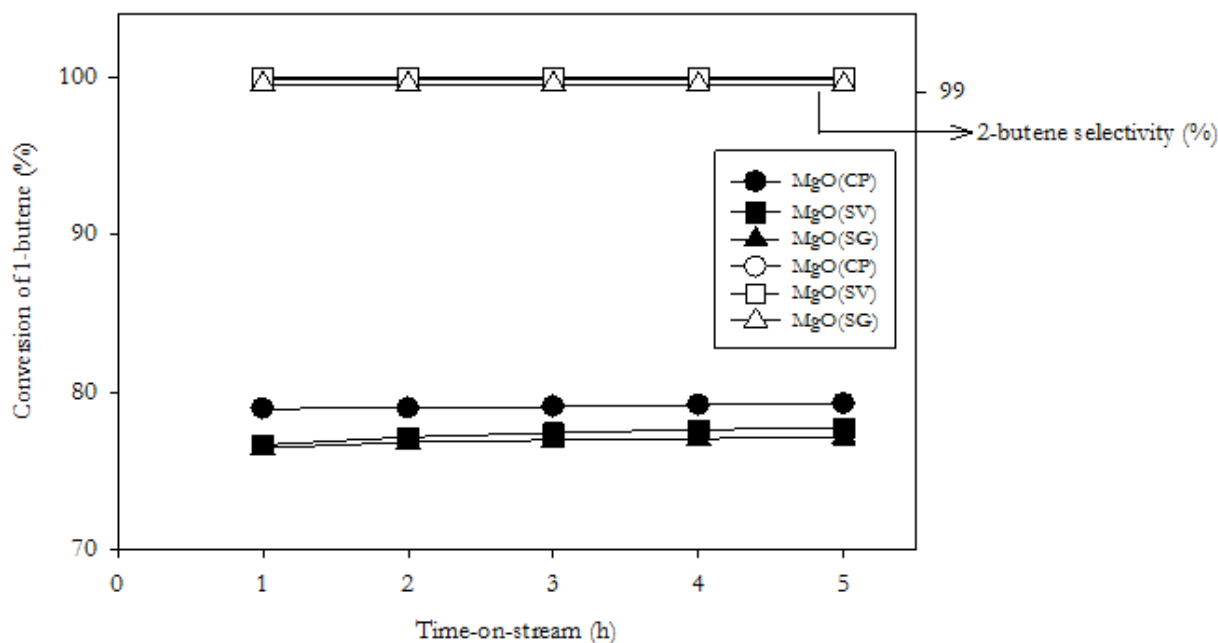


Fig. 5. The results of 1-butene isomerization over MgO catalysts.

### 3.3. Restructuring of MgO Catalysts after 1-Butene Isomerization

The XRD patterns of the spent MgO catalysts after 1-butene isomerization at 325°C in comparison to the fresh ones are shown in Fig. 6. All the fresh catalysts contained only single phase MgO. There were no changes of the MgO phase on the fresh catalysts upon contact with moisture for 3 days. After the reaction tests, the spent catalysts were also left in air for 3 days. Additional peaks corresponding to the Mg(OH)<sub>2</sub> phase were observed at 2θ degrees = 18.3°, 37.8°, 50.8°, and 58.5° for the MgO(CP) and MgO(SV) whereas the MgO(SG) still exhibited only the single phase MgO. The OH groups of the Mg(OH)<sub>2</sub> structure were confirmed by the FT-IR results of the spent catalysts and the results are shown in Fig. 7. The peaks at wavenumber 3618, 3646, 3696, 3698, 3723 and 3726 cm<sup>-1</sup> corresponded to OH groups of the Mg(OH)<sub>2</sub> structure [8]. For the MgO(CP) and MgO(SV), these OH peaks were higher for the spent catalysts compared to the fresh ones. This change was not observed for the MgO(SG) in which the spent catalysts showed relatively small OH peaks. There were no significant differences in the morphology between fresh and spent catalysts (not shown). Based on the characterization results from XRD, and FT-IR, it can be summarized that the MgO(CP) and MgO(SV) possessed strong OH adsorption sites whereas MgO(SG) contained weak adsorbed OH sites. According to Higashimoto et al. and Chizallet et al. [16, 17], OH formed on monoatomic steps, kinks, or divacancies are much more stable than those formed on higher steps and those formed on corners. It is also noted that the Mg(OH)<sub>2</sub> phase could not be reverse back to the single MgO phase by the same pretreatment used (N<sub>2</sub>, 325°C, 1h).

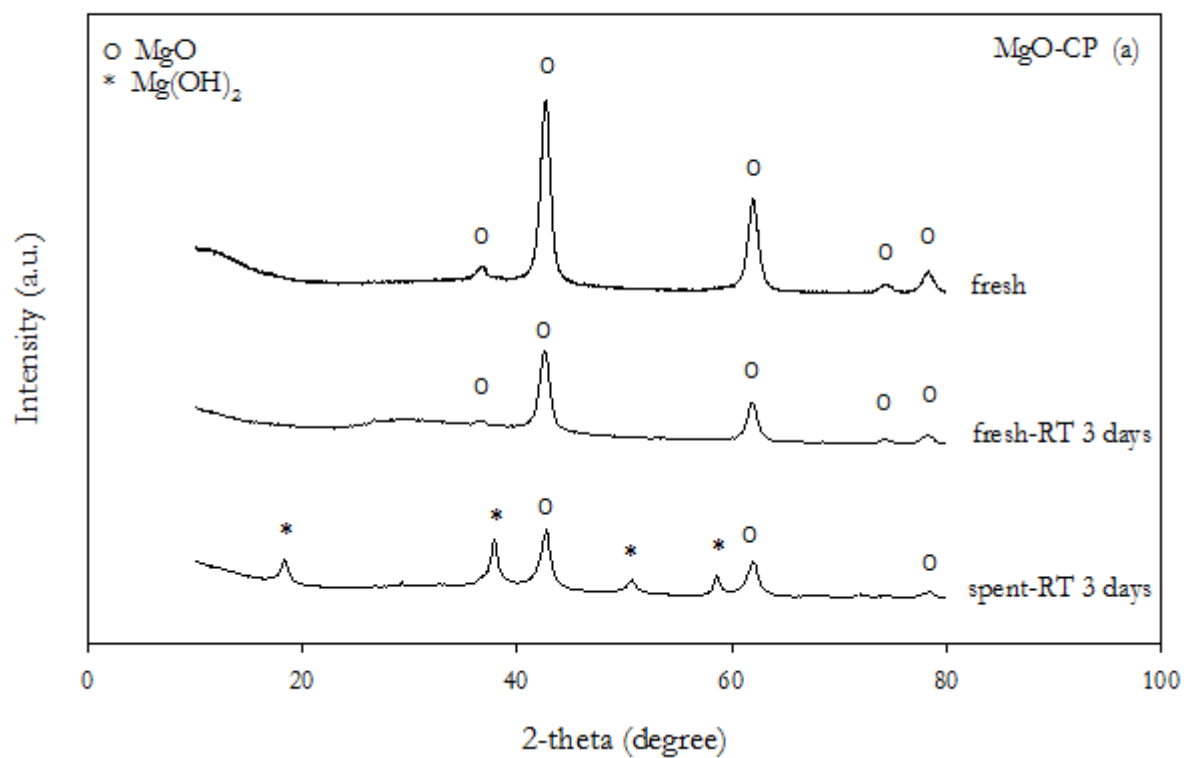


Fig. 6(a) The XRD patterns of fresh and spent MgO(CP) catalysts.

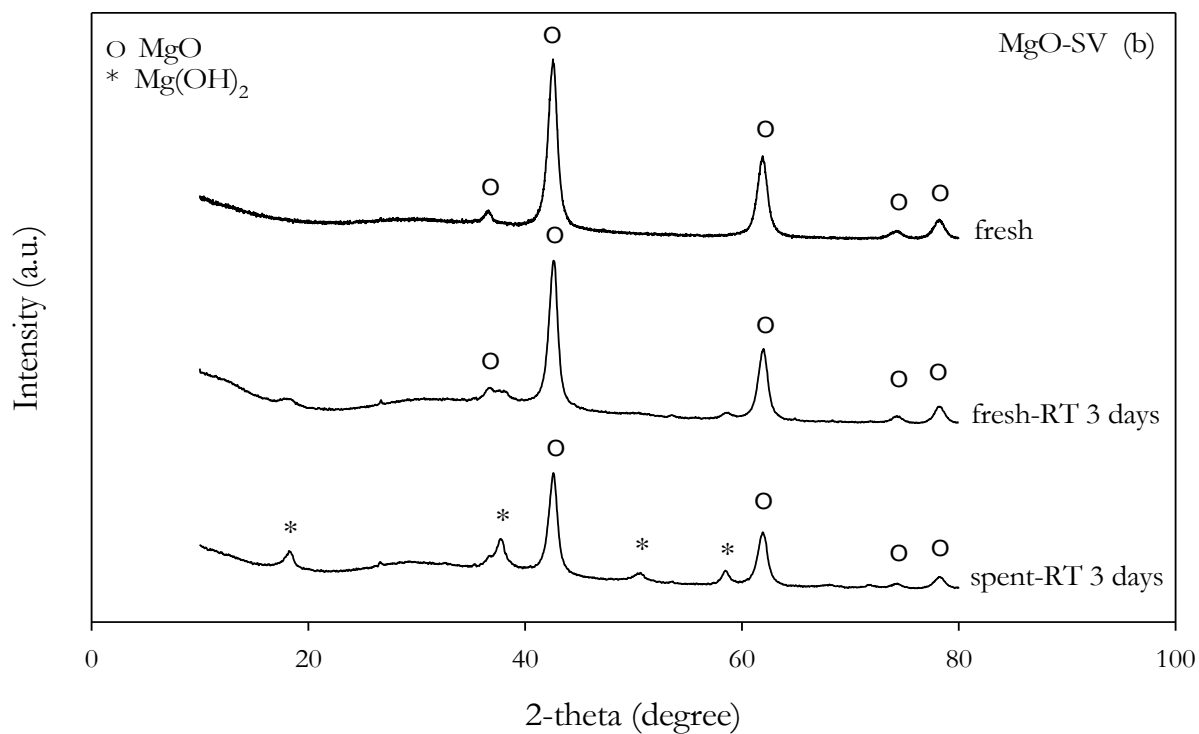


Fig. 6(b) The XRD patterns of fresh and spent MgO(SV) catalysts.

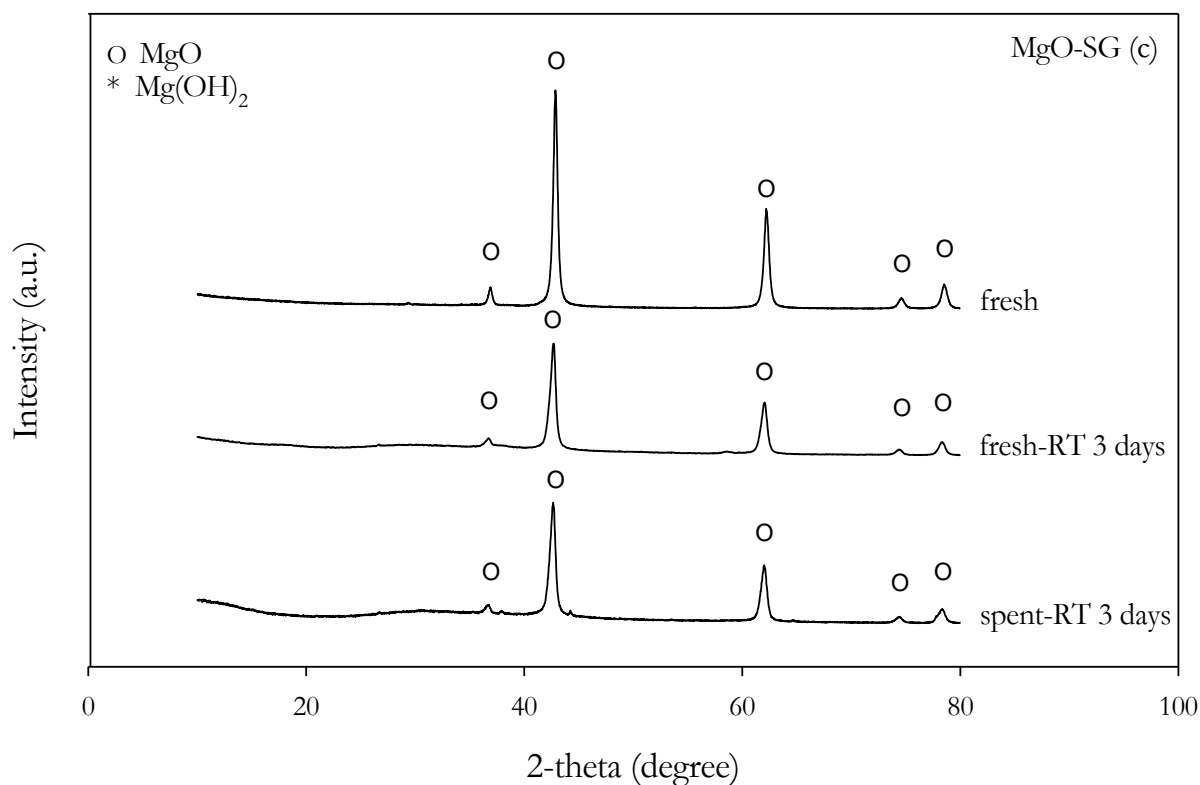


Fig. 6(c) The XRD patterns of fresh and spent MgO(SG) catalysts.

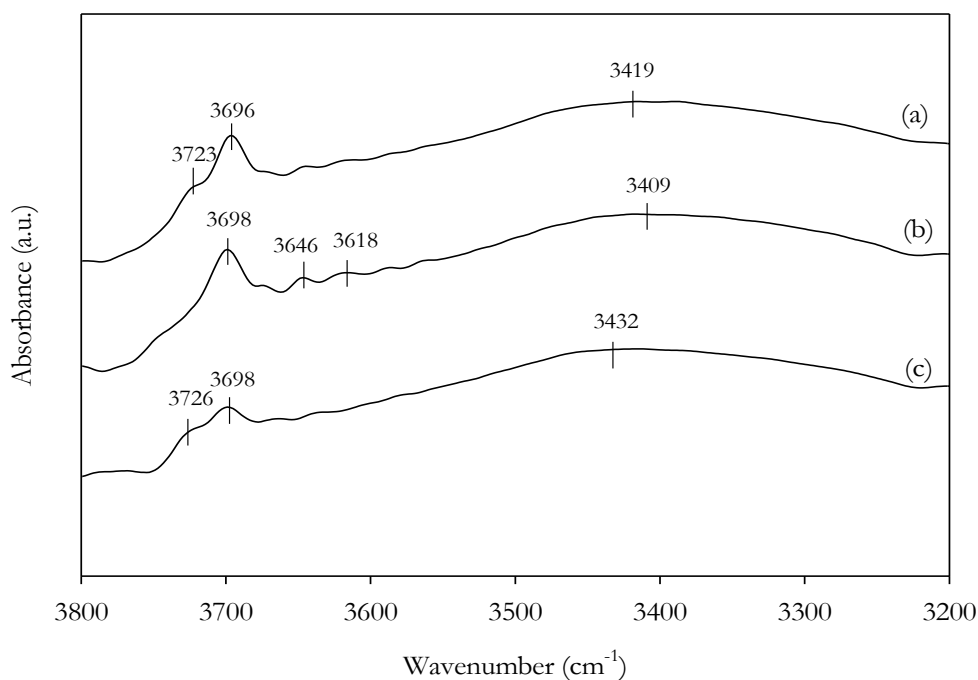


Fig. 7. The FT-IR spectra of spent MgO catalysts (after isomerization tests) in the region 3200 - 3800 cm<sup>-1</sup>: (a) spent-MgO(CP); (b) spent-MgO(SV); (c) spent-MgO(SG).

### 3.4. Metathesis of Ethylene and *Trans*-2-Butene on the Mixed $\text{WO}_3/\text{SiO}_2 + \text{MgO}$ Catalysts

The activity of the  $\text{WO}_3/\text{SiO}_2$  physically mixed with MgO in the cross metathesis of ethylene and *trans*-2-butene are shown in Fig. 8. The  $\text{WO}_3/\text{SiO}_2$  mixed with silica gel was employed for comparison purposes. It is clearly seen that the admixed MgO with the  $\text{WO}_3/\text{SiO}_2$  (weight ratio 1:1) resulted in much higher conversion of *trans*-2-butene compared to the one physically mixed with silica gel along the 5 h reaction time. The *trans*-2-butene conversion was found to be varied in the order:  $\text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{SG}) > \text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{SV}) > \text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{CP}) > \text{WO}_3/\text{SiO}_2 + \text{silica gel}$ . Despite their similar activity in 1-butene isomerization reaction, the  $\text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{CP})$  showed the lowest metathesis activity among the MgO admixed  $\text{WO}_3/\text{SiO}_2$  catalysts. It is postulated that restructuring of the MgO during the reaction affected the catalyst performances in the metathesis of ethylene and 2-butene over the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  catalysts.




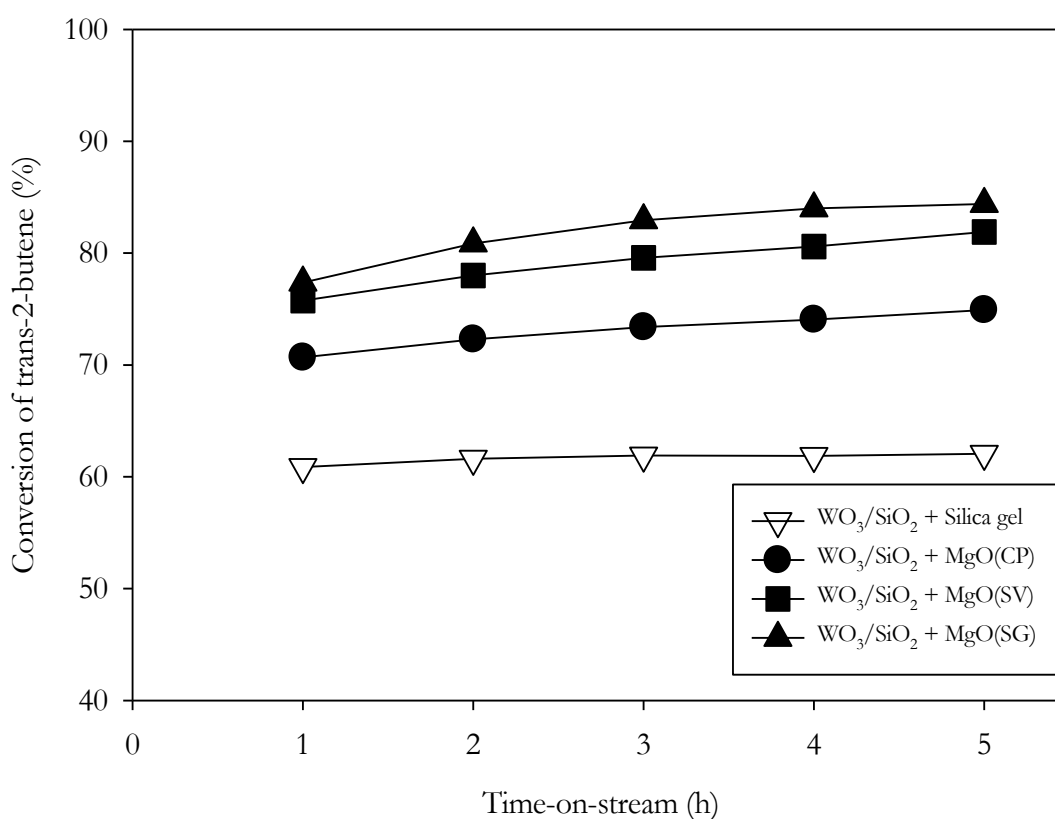


Fig. 8. The catalytic activity of the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (or silica gel) catalysts in the cross metathesis of ethylene and *trans*-2-butene.

Generally, the performances of W-based catalysts in metathesis reaction depend on many factors such as the amount and the nature of active sites, the active site concentration and dispersion [4, 18]. Addition of extra supports including silica [19],  $\text{TiO}_2$  and  $\text{ZrO}_2$  [20] could provide more space for tungsten migration, resulting in a better dispersion of the tungsten oxide species so that the catalytic activity was enhanced. Nevertheless, the surface and bulk structures of the  $\text{WO}_3/\text{SiO}_2$  catalysts in the present work were not altered when physically mixed with the MgO catalysts and tested in the metathesis of ethylene and 2-butene as confirmed in our previous work by the XRD, Raman, and UV-Vis spectroscopy [21]. Hu et al. also studied the metathesis of 1-butene and ethylene to propylene on the W-contained catalysts mixed with MgO [22]. It was confirmed that MgO did not catalyze the reaction of 2-butene and ethylene for propylene. The only role of MgO was to convert 1-butene to 2-butene.

However, in this study, pure *trans*-2-butene was used as the limiting reactant in addition to the excess ethylene. The main reactions involved are shown in the reactions (i) to (iv):



Besides the metathesis products, the products from isomerization reactions were observed including 1-butene, *cis*-2-butene, and iso-butene. The product distribution obtained from the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (or silica gel) catalysts in terms of %selectivity and %yield after 5 h reaction time are summarized in Table 2 and Fig. 9, respectively. Compared to the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$ , the  $\text{WO}_3/\text{SiO}_2 + \text{silica gel}$  exhibited lower conversion of *trans*-2-butene and much lower propylene selectivity with higher amounts of 1-butene and *cis*-2-butene. Therefore, the isomerization of *trans*-2-butene occurred as the side reactions without MgO catalysts on the isomerization sites of the  $\text{WO}_3/\text{SiO}_2$  catalysts. The higher yields of these products after 5 h reaction suggests that the cross metathesis reactions between 1-butene and 2-butene or 1-butene self metathesis for additional propylene production proceeded much slower as compared to the main metathesis reaction between ethylene and 2-butene. It is also noticed that the isomerization sites on the  $\text{WO}_3/\text{SiO}_2$  were not strong enough to convert 1-butene and *cis*-2-butene to *trans*-2-butene. However, in the presence of MgO co-catalysts, these by-products were converted back to *trans*-2-butene and additional propylene was mainly produced by the main metathesis reaction between *trans*-2-butene and excess ethylene (reaction (i)). The effect of *cis/trans*-2-butene isomers on the metathesis activity of  $\text{WO}_3/\text{SiO}_2$  has been reported by Poovarawan et al. [23]. The conversion of 2-butene was found to be lower when the reactant feed contained the mixture of *cis/trans*-2-butene isomers, compared to the ones using pure *trans*-2-butene as the reactant feed. Furthermore, the metathesis reaction of 1-butene with ethylene is considered to be a non-productive reaction as the products of this metathesis reaction are essentially the same as reactants. Therefore, it is advantageous to convert as much of 1-butene to 2-butene, simultaneously during metathesis to maximize the production of propylene. Nevertheless, as revealed by the characterization results, there were strong and weak OH adsorption sites on the MgO catalysts. The superior performances of the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  catalysts in the metathesis of ethylene and 2-butene for propylene production suggest that MgO containing weak OH adsorption sites is more appropriate to use as the co-catalyst under the reaction conditions used.

Table 2. Catalytic performances of  $\text{WO}_3/\text{SiO}_2$  physically mixed with MgO catalysts in the metathesis of ethylene and *trans*-2-butene.

Catalysts	<i>trans</i> -2-butene conversion (%)	Selectivity (%)				
		propylene	1-butene	<i>cis</i> -2-butene	isobutene	C <sub>5+</sub>
$\text{WO}_3/\text{SiO}_2 + \text{Silica gel}$	62.0	16.1	39.6	41.7	2.6	-
$\text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{CP})$	74.9	46.4	22.9	24.7	3.3	2.7
$\text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{SV})$	81.9	59.6	16.2	16.5	4.7	3.0
$\text{WO}_3/\text{SiO}_2 + \text{MgO}(\text{SG})$	84.4	68.5	12.4	13.4	2.4	3.3

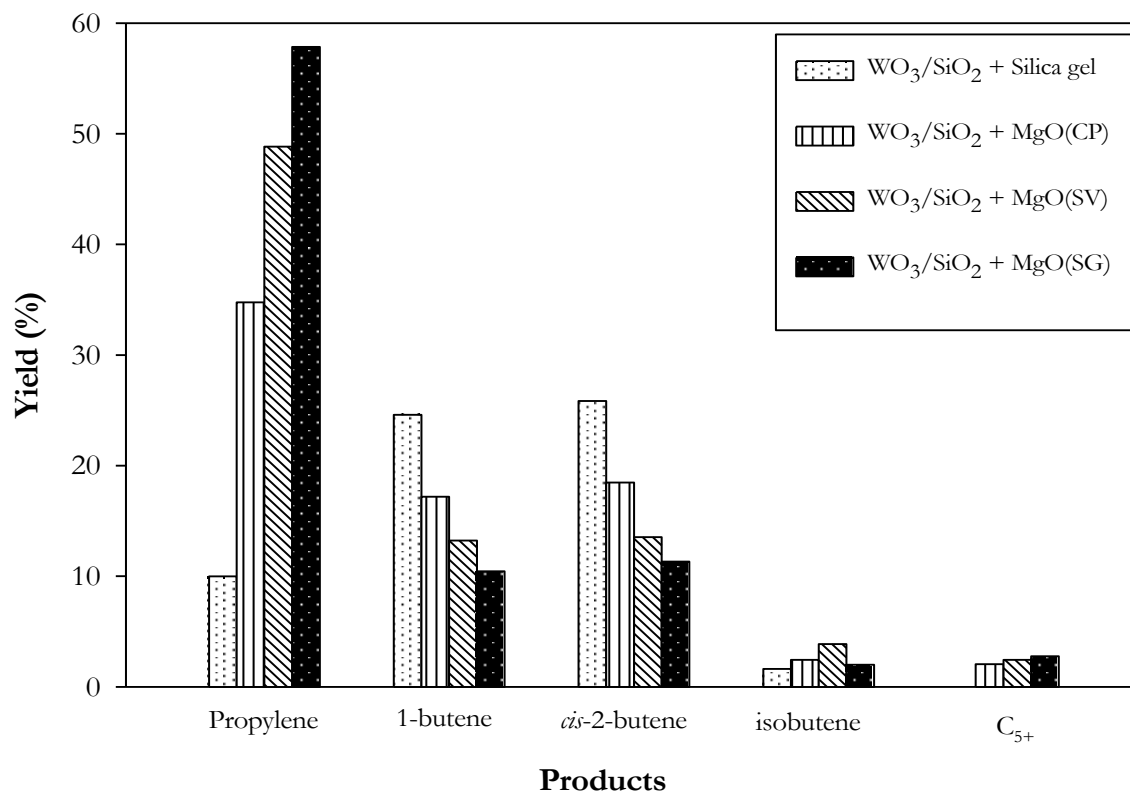


Fig. 9. Product distribution (%yield) after 5 h reaction time of the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (or silica gel) catalysts in the cross metathesis of ethylene and *trans*-2-butene.

#### 4. Conclusions

The metathesis of ethylene and *trans*-2-butene was investigated over the physical mixed  $\text{WO}_3/\text{SiO}_2$  and MgO (1:1 weight ratio) at 450°C in a single catalyst bed. Compared to the  $\text{WO}_3/\text{SiO}_2 + \text{silica gel}$ , the use of MgO admixed  $\text{WO}_3/\text{SiO}_2$  showed much higher 2-butene conversion and propylene selectivity. The major role of the MgO co-catalysts was to convert 1-butene and *cis*-2-butene by-products to *trans*-2-butene, which could further react with excess ethylene, resulting in higher propylene being produced. However, it was noticed that the MgO catalysts containing weak OH adsorption sites showed better performances during the metathesis reaction. Much higher propylene yield can be obtained over the mixed  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (SG) catalysts than  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (SV) or  $\text{WO}_3/\text{SiO}_2 + \text{MgO}$  (CP). The preparation method used may affect the formation of different OH adsorption sites on MgO (i.e., steps, kinks, divacancies, corners).

#### Acknowledgments

The financial support from the Ratchadaphiseksomphot Endowment Fund for International Research Integration: Chula Research Scholar (GCRS\_58\_02\_21\_01) is gratefully acknowledged.

#### References

- [1] N. Gholampour, M. Yusubov, and F. Verpoort, "Investigation of the preparation and catalytic activity of supported Mo, W, and Re oxides as heterogeneous catalysts in olefin metathesis," *Catalysis Reviews Science and Engineering*, pp. 1-44, Jan., 2016. DOI: 10.1080/01614940.2015.1100871

- [2] W. Phongsawat, B. Netiworaruksa, K. Suriye, P. Prasertthdam, and J. Panpranot, "Influence of preparation method on the catalytic performances of  $\text{Re}_2\text{O}_7/\text{SiO}_2\text{-Al}_2\text{O}_3$  catalysts in the metathesis of ethylene and 2-pentene," *J. Ind. Eng. Chem.*, vol. 20, pp. 145–152, Apr. 2014.
- [3] A. Spamer, T. I. Dube, D. J. Moodley, C. V. Schalkwyk, and J. M. Botha, "Application of a  $\text{WO}_3/\text{SiO}_2$  catalyst in an industrial environment: part II," *Appl. Catal. A.*, vol. 255, pp. 133–142, Jun. 2003.
- [4] S. Huang, S. Liu, W. Xin, J. Bai, S. Xie, Q. Wang, and L. Xu, "Metathesis of ethene and 2-butene to propene on  $\text{W}/\text{Al}_2\text{O}_3\text{-HY}$  catalysts with different HY contents," *J. Mol. Catal. A.*, vol. 226, pp. 61–68, Nov. 2005.
- [5] D. Hua, S.L. Chen, G. Yuan, Y. Wang, and L. Zhang, "Metathesis of butene to propene on  $\text{WO}_3$  supported on MTS-9 titanium-silica: Effect of loading on selectivity of product and yield of propene," *Trans. Met. Chem.*, vol. 36, pp. 245–248, Feb. 2011.
- [6] B. Ramachandran, S. Choi, R. J. Gartside, and M. I. Greene, "Catalyst for metathesis of ethylene and 2-butene and/or double bond isomerization," US Patent, No. 8,586,813, 2013.
- [7] G. A. Sawyer and M. G. Axelrod, "Propylene production," US Patent, No. 8,119,849, 2012.
- [8] P. Suttibut, K. Suriye, S. Kunjara Na Ayudhya, P. Prasertthdam, and J. Panpranot, "Effect of  $\text{N}_2$  pretreatment on the basicity, structural change, and isomerization activity of  $\text{MgO}/\text{Mg}(\text{OH})_2$  catalysts," *Asia-Pac. J. Chem. Eng.*, vol. 10, pp. 248–258, Mar. 2015.
- [9] P. Tamilselvi, A. Yelilarasi, M. Hema, and R. Anbarasan, "Synthesis of hierarchical structured  $\text{MgO}$  by sol-gel method," *Nano Bulletin.*, vol. 2, no. 1, pp. 1–5, Apr. 2013.
- [10] N. M. A. Hadia and H. A. H. Mohamed, "Characteristics and optical properties of  $\text{MgO}$  nanowires synthesized by solvothermal method," *Mat. Sci. Semicon. Proc.*, vol. 29, pp. 238–244, 2015.
- [11] O. S. Pokrovsky, J. Schott, and F. Thomas, "Processes at the magnesium-bearing carbonates/solution interface. I. A surface speciation model for magnesite," *Geochim. Cosmochim. Ac.*, vol. 63, pp. 863–880, 1999.
- [12] A. R. Yacob, M. K. A. A. Mustajab, and N. S. Samadi, "Calcination temperature of nano  $\text{MgO}$  effect on base transesterification of palm oil," *World Academy of Science, Engineering and Technology.*, vol. 56, pp. 408–412, 2009.
- [13] F. Wang, N. Ta, and W. Shen, " $\text{MgO}$  nanosheets, nanodisks, and nanofibers for the Meerwein–Ponndorf–Verley reaction," *Appl. Catal. A.*, vol. 475, pp. 76–81, Jan. 2014.
- [14] C. Chizallet, H. Petitjean, G. Costentin, H. L. Pernot, J. Maquet, C. Bonhomme, and M. Che, "Identification of the OH groups responsible for kinetic basicity on  $\text{MgO}$  surfaces by H MAS NMR," *J. Catal.*, vol. 268, pp. 175–179, Oct. 2009.
- [15] H. Petitjean, H. Guesmi, H. L. Pernot, G. Costentin, D. Loffreda, P. Sautet, and F. Delbecq, "How surface hydroxyl enhance," *ACS. Catal.*, vol. 4, pp. 4004–4014, Oct. 2014.
- [16] S. Higashimoto, G. Costentin, B. Morin, and M. Che, "An EPR study of physi- and chemisorption of  $\text{NO}$  on  $\text{MgO}$ : Effect of outgassing temperature and nature of surface sites," *Appl. Catal. B.*, vol. 84, pp. 58–64, Mar. 2008.
- [17] C. Chizallet, G. Costentin, M. Che, F. Delbecq, and P. Sautet, "Revisiting acido-basicity of the  $\text{MgO}$  surface by periodic density functional theory calculation: Role of surface topology and ion coordination on water dissociation," *J. Phys. Chem. B.*, vol. 110, pp. 15878–15886, Jun. 2006.
- [18] S. Huang, F. Chen, S. Liu, Q. Zhu, X. Zhu, W. Xin, Z. Feng, C. Li, Q. Wang, and L. Xu, "The influence of preparation procedures and tungsten loading on the metathesis activity of ethene and 2-butene over supported  $\text{WO}_3$  catalysts," *J. Mol. Catal. A.*, vol. 267, pp. 224–233, 2007.
- [19] W. Limsangkass, P. Prasertthdam, S. Phatanasri, J. Panpranot, S. Chaemchuen, W. Jareewatchara, S. Kunjara Na Ayudhya, and K. Suriye, "Influence of micro- and nano-sized  $\text{SiO}_2$  excess support on the metathesis of ethylene and *trans*-2-butene to propylene over silica-supported tungsten catalysts," *Reac. Kinet. Mech. Cat.*, vol. 113, pp. 225–240, Jun. 2014.
- [20] W. Limsangkass, P. Prasertthdam, S. Phatanasri, J. Panpranot, N. Poovarawan, W. Jareewatchara, S. Kunjara Na Ayudhya, and K. Suriye, "Comparative effect of nano-sized  $\text{ZrO}_2$  and  $\text{TiO}_2$  additional supports in silica-supported tungsten catalysts on performance in metathesis of ethylene and 2-butene to propylene," *Catal. Lett.*, vol. 144, pp. 1524–1529, Jul. 2014.
- [21] T. Thitiapichart and P. Prasertthdam, "Influence of  $\text{MgO}$  physically mixed with tungsten oxide support silica catalyst on coke formation," *Inte. J. Environ. Chem. Eco. Geolog. Geophy. Eng.*, vol. 9, no. 5, pp. 551–554, 2015.

- [22] B. Hu, H. Liu, K. Tao, C. Xiong, and S. Zhou, "Highly active doped mesoporous KIT-6 catalysts for metathesis of 1-butene and ethene to propene: the influence of neighboring environment of W species," *J. Phys. Chem. C.*, vol. 117, pp. 26385–26395, Nov. 2013.
- [23] N. Poovarawan, K. Suriye, S. Kunjara Na Ayudhya, J. Punpranot, F. J. C. S. Aires, and P. Praserttham, "Effect of 2-butene *cis/trans* isomers in the metathesis of ethylene and 2-butene over  $WO_3/SiO_2$  catalysts," *Catal. Lett.*, vol. 144, pp. 920–927, Mar. 2014.