

# Se atom incorporation in fullerenes by using nuclear recoil and ab initio molecular dynamics simulation

著者	大槻 勤
journal or publication title	Physical review. B
volume	65
number	7
page range	073402-1-073402-4
year	2002
URL	<a href="http://hdl.handle.net/10097/35726">http://hdl.handle.net/10097/35726</a>

doi: 10.1103/PhysRevB.65.073402

## Se atom incorporation in fullerenes by using nuclear recoil and *ab initio* molecular dynamics simulation

T. Ohtsuki,<sup>1</sup> K. Ohno,<sup>2</sup> K. Shiga,<sup>3</sup> Y. Kawazoe,<sup>3</sup> and H. Yuki<sup>1</sup>

<sup>1</sup>Laboratory of Nuclear Science, Tohoku University, Taihaku, Sendai 982-0826, Japan

<sup>2</sup>Department of Physics, Yokohama National University, Yokohama, 240-8501, Japan

<sup>3</sup>Institute for Materials Research, Tohoku University, Aoba-ku, Sendai 980-8577, Japan

(Received 28 June 2001; published 10 January 2002)

The formation of Se-atom-incorporated fullerenes has been investigated by using radionuclides produced by nuclear reactions. From the trace of radioactivities of <sup>75</sup>Se after high-performance liquid chromatography, it was found that the formation of endohedral fullerenes or heterofullerenes is possible by a recoil process following the nuclear reactions. To confirm the produced materials, *ab initio* molecular-dynamics simulations based on an all-electron mixed-basis approach were carried out. We found that the insertion of a Se atom into C<sub>60</sub> cage is much easier than that of As and Ge atoms. The result indicates that an electron affinity of doping atoms seems to be important in the formation of foreign-atom-doped fullerenes.

DOI: 10.1103/PhysRevB.65.073402

PACS number(s): 61.48.+c, 81.05.Tp

Fullerenes have been presented a new type of carbon compounds and show very interesting physical and chemical properties since the discovery and the synthesis of a large amount of fullerenes.<sup>1,2</sup> Especially, the chemical interaction between C<sub>60</sub> and a variety of atoms is becoming a very new field of cluster research. So far, numerous experimental studies for endohedrally doped<sup>3-13</sup> or exohedrally doped<sup>14-16</sup> fullerenes with foreign atoms have been undertaken by resorting to arc-desorption or laser-vaporization techniques. On the other hand, it has become possible to synthesize the heterofullerenes, where the foreign atom is incorporated into the carbon cage. Experimentally, heterofullerenes doped with foreign atoms, such as boron<sup>17,18</sup> (B), nitrogen<sup>19,20</sup> (N), and silicon<sup>21,22</sup> (Si) have been reported. In our previous studies, we have studied not only the endohedral doping of Be (Ref. 23), Kr, and Xe (Ref. 24) but also the substitutional doping of <sup>11</sup>C (Ref. 25), <sup>13</sup>N (Ref. 26), <sup>69</sup>Ge, and <sup>72</sup>As (Ref. 27) by a recoil-implantation process following nuclear reactions. In spite of the intense research, only partial facts for the formation process and the produced materials have been unveiled on the nature of the chemical interaction between a foreign atom and a fullerene cage. Therefore, it is important and intriguing to synthesize new complexes, such as several foreign-atom-incorporated fullerenes, and to investigate their properties so that knowledge about how to produce a large amount of these complexes is gained.

In this paper, we show evidence of Se-atom-incorporated fullerenes on the collision between a C<sub>60</sub> cage and an Se atom, which was generated from a recoil process following nuclear reactions. We performed *ab initio* molecular-dynamics (MD) simulations to see whether the Se atom can be incorporated in the fullerene with the endohedral doping: Se@C<sub>60</sub>. Furthermore, the chemical nature of the Se atom in a fullerene is compared with that of the Ge and As atoms.

In order to produce Se atom-incorporated fullerenes, about 10 mg of C<sub>60</sub> fullerene powder was mixed homogeneously with 10 mg of As<sub>2</sub>S<sub>3</sub> (200 meshes) and used to the target material. Deuteron irradiation with beam energy of 16 MeV was performed at the Cyclotron Radio-Isotope Center

(CYRIC), Tohoku University. Radioisotopes of <sup>75</sup>Se can be produced by <sup>75</sup>As(*d,2n*)<sup>75</sup>Se reactions. The beam current was typically 5 μA and the irradiation time was about 1 h. The sample was cooled with He gas during irradiation. After the irradiation, the samples were left for 1 day to cool down the several kinds of short-lived radioactivities of by-products. After the 1-day cooling, radioactivities, such as <sup>11</sup>C or <sup>13</sup>N, e.g., <sup>11</sup>C decays to <sup>11</sup>B with *T*<sub>1/2</sub>=20 min, the radioactivities of <sup>75</sup>Se could be measured with its characteristic γ rays. The typical γ ray and the half-life (*T*<sub>1/2</sub>) of <sup>75</sup>Se are 136 keV (and 265 keV), 120 days,<sup>28</sup> respectively.

The fullerene samples were dissolved in *o*-dichlorobenzene after being filtrated to remove insoluble materials through a membrane filter (pore size=0.2 μm). The soluble fraction was injected into a high-performance liquid chromatograph (HPLC) equipped with a 5PBB (silica bonded with the pentabromobenzyl group) column of 10 mm (inner diameter)×250 mm (length), at a flow rate of 3 ml/min. The eluted solution was passed through a UV detector, the wavelength of which was adjusted to 290 nm in order to measure the amount of fullerenes and their derivatives. The fraction was collected at 30-sec intervals, and the γ-ray activities of each fraction were measured with a Ge detector. Therefore, the existence of <sup>75</sup>Se could be confirmed by their characteristic γ rays.

The elution curve shown by solid line in Fig. 1 indicates the absorbances monitored continuously by a UV detector for the irradiated samples of C<sub>60</sub>+As<sub>2</sub>S<sub>3</sub>. The horizontal axis indicates the retention time after injection into the HPLC, and vertical one indicates the absorption intensity of the UV and the γ counting rate of the <sup>75</sup>Se radionuclide produced by the <sup>75</sup>As(*d,2n*)<sup>75</sup>Se reaction. A strong absorption peak was observed at the retention time of 4.2–5.2 min in the elution curve (solid line) which was measured by the UV detector. This peak position corresponds to the retention time of C<sub>60</sub> which was confirmed by the calibration run using the C<sub>60</sub> sample before the irradiation. Following the first peak, two peaks at around 6.5–7.2 min and 10–15 min were consecu-

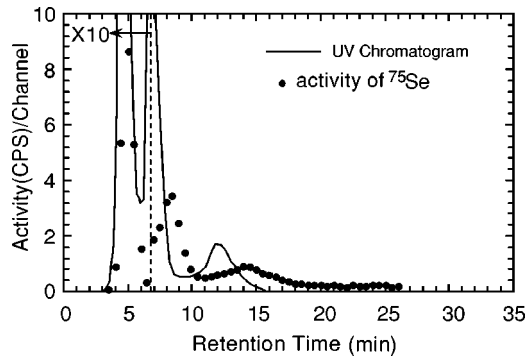


FIG. 1. HPLC elution curves of the soluble portion of the crude extracted in the deuteron-irradiated sample of  $C_{60}$  mixed with  $As_2S_3$ . The horizontal axis indicates retention time, while the vertical axis represents the counting rate of the radioactivities of  $^{75}Se$  (solid circles) measured with a Ge detector and the absorbance of a UV chromatogram of  $C_{60}$  (solid line).

tively observed in the UV chromatogram. This fact indicates that the second and smaller third peaks can be assigned to  $C_{60}$  dimers and  $C_{60}$  trimers, respectively, with resorting to TOFMS measurements. These materials can be produced by the interaction between  $C_{60}$ 's in coalescence reactions after ionization by the incident or produced charged particles. Three peaks appeared in the curve of the  $^{75}Se$  radioactivities in the radiochromatogram. Aside from a slight delay, the first peak (5.0 min) corresponds to the  $C_{60}$  UV absorption peak. The second and the relatively broad third peaks were observed at the retention time of 7–10 min and 11–18 min, respectively. Though there is a delay in the elution peaks of the radioactivities against that of the UV absorption peaks, it seems that the elution behavior is similar. This result indicates that the radioactive fullerene monomers and their polymers (dimers and trimers) labeled with  $^{75}Se$  possibly exist in the final fractions.

In order to understand the present experimental results, *ab initio* molecular-dynamics simulations were carried out. The method, which is used here, is based on the all-electron mixed-basis approach<sup>29–31</sup> using both plane waves (PW's) and atomic orbitals (AO's) as a basis set within the framework of the local density approximation (LDA). In the present study, all the core atomic orbitals are determined numerically by a standard atomic calculation based on the Herman-Skillman framework with logarithmic radial meshes. We use the Ceperley-Alder fitting form for the LDA.<sup>32</sup> For the present system, we use 318 numerical AO's and 4169 PW's corresponding to a 7-Ry cutoff energy. For dynamics, we assume the adiabatic approximation where the electronic structure is always in the ground state. We utilize a supercell composed of  $64 \times 64 \times 64$  meshes, where one mesh corresponds to  $0.196 \text{ \AA}$ . We set the basic time step as  $\Delta t = 0.1 \text{ fs}$  and perform five steepest descent (SD) iterations after each updation of atomic positions. We do not impose any velocity control, so that the system is almost microcanonical with a little energy dissipation from the SD algorithm.

First, we show the results of the following simulation: an Se atom with a kinetic energies (KE) 40 eV hits vertically the

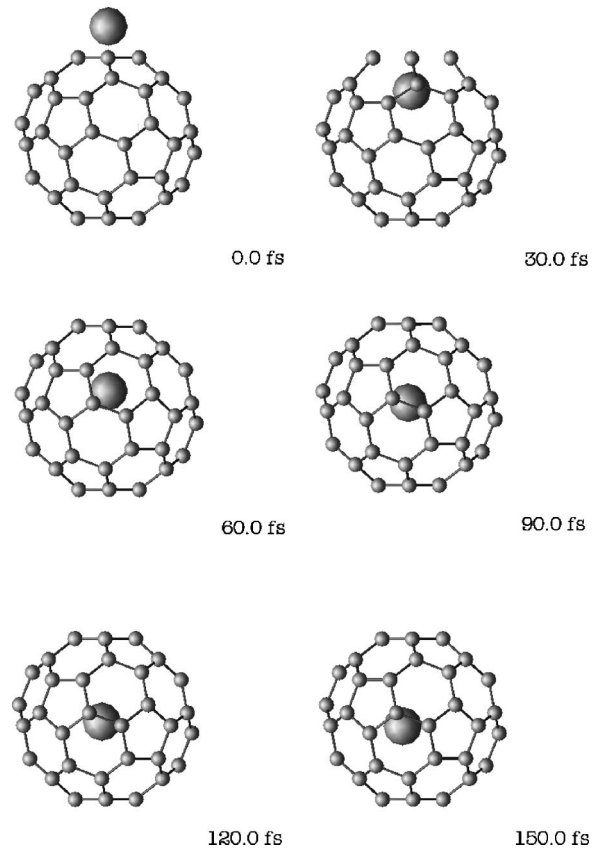


FIG. 2. Simulation of Se hitting the center of the uppermost six-membered ring ( $u-C_6$ ) of  $C_{60}$  with a kinetic energy of 40 eV. Here, the local skeleton disappears from the figure when the bond length is elongated to more than by  $1.5 \text{ \AA}$ .

center of the uppermost six-membered ring (hereafter we call it  $u-C_6$ ) of  $C_{60}$ . From the simulation, we found that an Se atom can penetrate into  $C_{60}$  easily when its initial speed is 40 eV and stop at the inside of the  $C_{60}$  cage (see Fig. 2), although an Se atom goes out again from the opposite side of the cage when its initial speed is greater than 100 eV. For an interaction with the KE lower than 40 eV, the Se atom first touches  $u-C_6$  and carbon atoms are pushed to open  $u-C_6$ , but the  $u-C_6$  soon recovers its initial configuration. Similar simulations were performed for the case of As.<sup>27</sup> In this case, we found that an As atom can penetrate into  $C_{60}$  if its KE is greater than 70 eV, although an As atom goes out again from the opposite side of the cage when its initial energy is greater than 160 eV. Comparing Se and As, we found that the formation of  $Se@C_{60}$  seems to be easier than that of  $As@C_{60}$ , because the energy range of the insertion for the Se atom is relatively lower than that for the As atom.

Second, we put additionally one Se atom on the radial axis by  $1.39 \text{ \AA}$  inward from the original C position of  $C_{60}$ , and then start the simulation with zero initial velocity. Then we found that there is a force acting on the Se atom to accelerate it inward, and finally the Se atom stops at around the center of  $C_{60}$ . Thus the Se-encapsulated fullerene,  $Se@C_{60}$ , is reproduced. Similarly, when we put additionally one As atom on the same radial axis by  $1.39 \text{ \AA}$  inward from the original C position of  $C_{60}$ , on the contrary, there is a strong

force acting on the As atom to accelerate it outward and, as a result, to repel the outward C atom. Finally, the As atom<sup>27</sup> stops at 0.50 Å from the cage sphere. Thus, it seems that the As atom put inside the cage is relatively unstable and has a strong tendency to repel the closest C atom of C<sub>60</sub>, and is stabilized slightly outside the cage sphere after the removal (emission) of the closest C atom. Therefore, a heterofullerene, such as AsC<sub>59</sub>, may exist stably under realistic conditions. It should be noted that similar results for the case of a Si atom have been reported by Pellarin and co-workers<sup>21,22</sup> (however, the possibility for endohedral doping, As@C<sub>60</sub>, cannot be completely ruled out at present; there seems to be a local stable point inside the cage).

Radiochromatograms of <sup>69</sup>Ge, <sup>72</sup>As and <sup>75</sup>Se are shown in Figs. 3(a) and 3(b), respectively. The area ratios, the peak area assigned by A and B in Figs. 3(a) and 3(b), are shown in Fig. 3(c) for Ge, As and Se atoms, respectively. It is interesting and important to note that the area ratio A/B (monomer/dimer) in the radiochromatogram of <sup>75</sup>Se is much larger than that in the radiochromatogram of <sup>72</sup>As (and further much larger than that in the radiochromatogram of <sup>69</sup>Ge). This trend indicates that the shock caused by a collision with higher KE (e.g., ~70 eV, for an As atom) most probably induced the cage to create dimers with a higher rate.

The difference can be due mainly to the nature of the covalent bonding between the C atom and the 4B–6B (Ge–Se) atoms. An electron affinity of the Se atom is greater than that of Ge and As atoms. It seems that a hall of *u*-C<sub>6</sub> at the collision between Se and C<sub>60</sub> comes to be larger due to the occurrence of a few-electron transfer from the *u*-C<sub>6</sub> to Se atom. Therefore, the penetrability of the Se atom into C<sub>60</sub> may increase, compared with that of Ge and As atoms.

In this study, the formation of atom-incorporated fullerenes has been investigated by the trace of radioactivities of <sup>75</sup>Se produced by nuclear reactions. It was found that a 6B element, like Se, remained in the final C<sub>60</sub> portion after a HPLC process. This fact suggests that the formation of <sup>75</sup>Se atom-incorporated fullerenes can be possible by a recoil process following nuclear reactions. Carrying out *ab initio* MD simulations on the basis of the all-electron mixed-basis approach, we showed possibility of the formation of endohedral fullerenes for Se atoms. In comparison with 4B–6B (Ge–Se) atoms, we found that the insertion of a Se atom into a C<sub>60</sub> cage is much easier than that of As and Ge atoms.

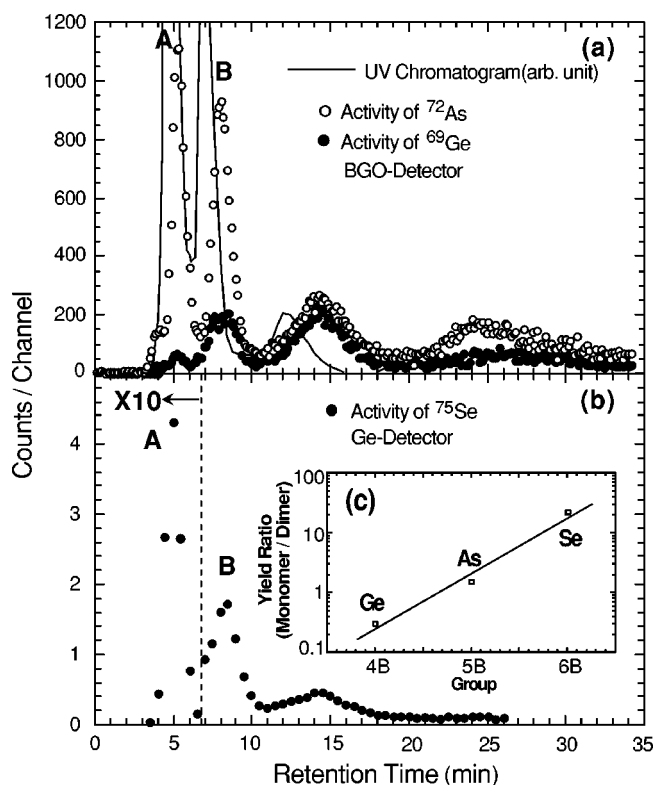


FIG. 3. (a) HPLC elution curves of the soluble portion of the crude extracted in the deuteron-irradiated sample for the production of <sup>69</sup>Ge and <sup>72</sup>As taken from Ref. 24. The horizontal and vertical axes are same as Fig. 1, but for <sup>69</sup>Ge and <sup>72</sup>As. (b) Same as (a), but for <sup>75</sup>Se for comparison with the <sup>69</sup>Ge and <sup>72</sup>As cases. The difference in vertical scale between (a) and (b) is due to the efficiency of the BGO and Ge detectors. (c) Area ratio, monomer/dimer indicated by peaks A and B in (a) and (b), in the radiochromatogram of 4B–6B (Ge–Se) atoms.

The authors are grateful to the staff of the Cyclotron Radio-Isotope Center (CYRIC) for handling the beam and are grateful to the technical staffs, working at IMR, Tohoku University, for their continuous support, for the supercomputing facilities of HITAC S3800. This work was supported by a Grant-in-Aid for Cooperative Research No. 12640532 from the Ministry of Education, Science and Culture of Japan.

- <sup>1</sup>H. Kroto, J. R. Heath, S. C. O'Brien, R. F. Curl, and R. E. Smalley, *Nature (London)* **318**, 162 (1985).
- <sup>2</sup>W. Krätschmer, L. D. Lamb, K. Fostiropoulos, and D. R. Huffman, *Nature (London)* **347**, 354 (1990).
- <sup>3</sup>J. R. Heath, S. C. O'Brien, Q. Zhang, Y. Liu, R. F. Curl, H. W. Kroto, F. K. Tittel, and R. E. Smalley, *J. Am. Chem. Soc.* **107**, 7779 (1985).
- <sup>4</sup>Y. Chai, T. Guo, C. Jin, R. E. Haufler, L. P. F. Chibante, J. Fune, L. Wang, J. M. Alford, and R. E. Smalley, *J. Phys. Chem.* **95**, 7564 (1991).
- <sup>5</sup>R. D. Johnson, M. S. de Vries, J. Salem, D. S. Bethune, and C.

Yannoni, *Nature (London)* **355**, 239 (1992).

- <sup>6</sup>J. H. Weaver, Y. Chai, G. H. Kroll, C. Jin, T. R. Ohno, R. E. Haufler, T. Guo, J. M. Alford, J. Conceicao, L. P. F. Chibante, A. Jain, G. Palmer, and R. E. Smalley, *Chem. Phys. Lett.* **190**, 460 (1992).
- <sup>7</sup>H. Shinohara, H. Sato, Y. Saito, M. Ohkohchi, and Y. Ando, *Nature (London)* **357**, 52 (1992).
- <sup>8</sup>M. Takata, B. Umeda, E. Nishibori, M. Sakata, Y. Saito, M. Ohno, and H. Shinohara, *Nature (London)* **377**, 46 (1995).
- <sup>9</sup>W. Sato, K. Sueki, K. Kikuchi, K. Kobayashi, S. Suzuki, Y. Achiba, H. Nakahara, Y. Ohkubo, F. Ambe, and K. Asai, *Phys.*

- Rev. Lett. **80**, 133 (1998).
- <sup>10</sup>M. Saunders, R. J. Cross, H. A. Jimenez-Vazquez, R. Shimshi, and A. Khong, *Science* **271**, 1693 (1996).
- <sup>11</sup>T. Braun and H. Rausch, *Chem. Phys. Lett.* **288**, 179 (1998).
- <sup>12</sup>T. Braun and H. Rausch, *Chem. Phys. Lett.* **237**, 443 (1995).
- <sup>13</sup>G. E. Gadd, P. Schmidt, C. Bowles, G. McOrist, P. J. Evans, J. Wood, L. Smith, A. Dixon, and J. Easey, *J. Am. Chem. Soc.* **120**, 10 322 (1998).
- <sup>14</sup>L. M. Roth, Y. Huang, J. T. Schwedker, C. J. Cassady, D. Ben-Amotz, B. Kahr, and B. S. Freiser, *J. Am. Chem. Soc.* **113**, 6298 (1991).
- <sup>15</sup>Y. Huang and B. S. Freiser, *J. Am. Chem. Soc.* **113**, 9418 (1991).
- <sup>16</sup>S. W. McElvany, *J. Phys. Chem.* **96**, 4935 (1992).
- <sup>17</sup>T. Guo, C. Jin, and R. E. Smalley, *J. Phys. Chem.* **95**, 4948 (1991).
- <sup>18</sup>H. J. Muhr, R. Nesper, B. Schnyder, and R. Kotz, *Chem. Phys. Lett.* **249**, 399 (1996).
- <sup>19</sup>T. Pradeep, V. Vijayakrishnan, A. K. Santra, and C. N. R. Rao, *J. Phys. Chem.* **95**, 10 564 (1991).
- <sup>20</sup>J. F. Christian, Z. Wan, and S. Anderson, *J. Phys. Chem.* **96**, 10 597 (1992).
- <sup>21</sup>M. Pellarin, C. Ray, P. Mélinon, J. L. Lerm'e, J. L. Vialle, P. Kéghélian, A. Perez, and M. Broyer, *Chem. Phys. Lett.* **277**, 96 (1997).
- <sup>22</sup>C. Ray, M. Pellarin, J. L. Lermé, J. L. Vialle, M. Broyer, X. Blase, P. Mélinon, P. Kéghélian, and A. Perez, *Phys. Rev. Lett.* **80**, 5365 (1998).
- <sup>23</sup>T. Ohtsuki, K. Masumoto, K. Ohno, Y. Maruyama, Y. Kawazoe, K. Sueki, and K. Kikuchi, *Phys. Rev. Lett.* **77**, 3522 (1996).
- <sup>24</sup>T. Ohtsuki, K. Ohno, K. Shiga, Y. Kawazoe, Y. Maruyama, and K. Masumoto, *Phys. Rev. Lett.* **81**, 967 (1998).
- <sup>25</sup>T. Ohtsuki, K. Masumoto, K. Sueki, K. Kobayashi, and K. Kikuchi, *J. Am. Chem. Soc.* **117**, 12 869 (1995).
- <sup>26</sup>T. Ohtsuki, K. Masumoto, K. Sueki, K. Shikano, and T. Shigematsu, *J. Radioanal. Nucl. Chem.* **239**, 365 (1999).
- <sup>27</sup>T. Ohtsuki, K. Ohno, K. Shiga, Y. Kawazoe, Y. Maruyama, and K. Masumoto, *Phys. Rev. B* **60**, 1531 (1999).
- <sup>28</sup>*Table of Isotopes*, 8th ed., edited by R. B. Firestone and V. S. Shirley (Wiley, New York, 1996), Vol. I.
- <sup>29</sup>K. Ohno, Y. Maruyama, K. Esfarjani, Y. Kawazoe, N. Sato, R. Hatakeyama, T. Hirata, and M. Niwano, *Phys. Rev. Lett.* **76**, 3590 (1996).
- <sup>30</sup>K. Ohno, Y. Maruyama, and Y. Kawazoe, *Phys. Rev. B* **56**, 1009 (1997).
- <sup>31</sup>K. Shiga, K. Ohno, Y. Maruyama, Y. Kawazoe, and T. Ohtsuki, *Modell. Simul. Mater. Sci. Eng.* **7**, 621 (1999).
- <sup>32</sup>D. M. Ceperley and B. J. Alder, *Phys. Rev. Lett.* **45**, 566 (1980).