

# Single-step novel biosynthesis of silver nanoparticles: A potent and eco-friendly mosquitocides

Kaliyan Veerakumar<sup>1</sup>, Marimuthu Govindarajan<sup>1\*</sup>, Kadarkarai Murugan<sup>2</sup>

<sup>1</sup>Department of Zoology, Unit of Vector Control, Phytochemistry and Nanotechnology, Annamalai University, Annamalainagar - 608 002, Cuddalore, Tamil Nadu, India, <sup>2</sup>Department of Zoology, Division of Entomology, School life Sciences, Bharathiar University, Coimbatore - 641 046, Tamil Nadu, India

Received: 20.11.2014

Revised: 09.12.2014

Accepted: 10.12.2014

**\*Address for correspondence:**

M. Govindarajan,  
Department of Zoology,  
Unit of Vector Control,  
Phytochemistry and  
Nanotechnology,  
Annamalai University,  
Annamalainagar - 608 002,  
Cuddalore,  
Tamil Nadu, India.  
E-mail: [drgovind1979@gmail.com](mailto:drgovind1979@gmail.com)

## ABSTRACT

Mosquito-borne diseases such as malaria, dengue, chikungunya, filariasis, and Japanese encephalitis cause thousands of deaths per year. Mosquito control is to enhance the health and quality of life of county residents and visitors through the reduction of mosquito populations. Mosquito control is of serious concern in developing countries like India due to the lack of general awareness, development of resistance, and socioeconomic reasons. Insecticides of botanical origin may serve as suitable alternative biocontrol techniques in the future. In view of the recently increased interest in developing plant origin insecticides as an alternative to chemical insecticide, in this research, we biosynthesized silver nanoparticles (AgNPs) using the *Sida acuta* leaf extract as reducing and stabilizing agent. The biosynthesis of AgNP was confirmed analyzing the excitation of surface plasmon resonance using ultraviolet-visible spectrophotometry. Scanning electron microscopy and transmission electron microscopy showed the clustered and irregular shapes of AgNP. The presence of silver was confirmed by energy-dispersive X-ray spectroscopy. Fourier transform infrared spectroscopy investigated the identity of secondary metabolites, which may also act as AgNP capping agents. The acute toxicity of *S. acuta* leaf extract and biosynthesized AgNP was evaluated against larvae of *Aedes aegypti*, *Anopheles stephensi*, and *Culex quinquefasciatus*. Compared to the leaf aqueous extract, biosynthesized AgNP showed higher toxicity against *A. aegypti*, *A. stephensi*, and *C. quinquefasciatus* with the LD<sub>50</sub> values of 35.12, 39.53, and 41.44 µg/mL, respectively. This result suggests that the leaf extract has the potential to be used as an ideal eco-friendly approach for the control of vector mosquitoes.

**KEY WORDS:** Green synthesis, Mosquito adulticide, nanoparticles, scanning electron microscopy, *Sida acuta*, transmission electron microscopy

## INTRODUCTION

Mosquitoes constitute a major public health problem as vectors of serious human diseases malaria, filariasis, Japanese encephalitis, dengue fever, chikungunya, and yellow fever that cause substantial mortality and morbidity among people living in tropical and subtropical zones (Jang *et al.*, 2002). Essential oil, nanoparticles, and aqueous extracts from plants may be alternative sources of mosquito control agents because they constitute a rich source of bioactive compounds that are biodegradable into nontoxic products and potentially suitable for use to control mosquitoes. Insecticides of botanical origin may serve as suitable alternative bio control techniques in the future. Mosquito control is being strengthened in

many areas, but there are significant challenges, including an increasing mosquito resistance to insecticides and a lack of alternative, cost-effective, and safe insecticides. Increasing insecticide resistance requires the development of strategies for prolonging the use of highly effective vector control compounds (Govindarajan *et al.*, 2008). The use of combinations of multiple insecticides and phytochemicals is one such strategy that may be suitable for mosquito control. Thus, attempts to develop novel materials as mosquitocides are still necessary. With the progress of nanotechnology, many laboratories around the world have investigated silver nanoparticle (AgNP) production (Murugan *et al.*, 2012).

Among 53 anopheline species present in India, 9 are vectors of malaria. In India, malaria is still the most important

cause of morbidity and mortality with approximately two to three million new cases arising every year (Sharma *et al.*, 2009). Malaria mortality rates have fallen by 47% globally since 2000 and by 54% in the African region. Most deaths occur among children living in Africa, where a child dies every minute from malaria. Malaria is caused by *Plasmodium* parasites, vectored to people through the bites of infected *Anopheles* mosquitoes, which bite mainly between dusk and dawn (Jensen and Mehlhorn, 2009).

*Aedes* mosquitoes are painful and persistent biters. *Aedes aegypti* is responsible for spreading dengue and chikungunya. Dengue is prevalent throughout the tropics and subtropics. The World Health Organization estimates that around 2.5 billion people are at risk of dengue. Infections have dramatically increased in recent decades due to increased urbanization, trade, and travel (WHO, 2014). *Culex* is a genus of mosquito which serves as vectors of important diseases, such as West Nile virus, filariasis, Japanese encephalitis, St. Louis encephalitis, and avian malaria. *Culex quinquefasciatus* is responsible for transmitting the filarial nematode, *Wuchereria bancrofti*. More than 1.3 billion people in 72 countries worldwide are threatened by lymphatic filariasis, commonly known as elephantiasis. Over 120 million people are currently infected, with about 40 million disfigured and incapacitated by the disease (WHO, 2012).

Recently, a growing number of plant-borne compounds have been reported as excellent toxics against mosquitoes, acting as adulticidal, larvicidal, ovicidal, growth and/or reproduction inhibitors, and/or adult repellents (e.g., Govindarajan and Sivakumar, 2014; Veerakumar *et al.*, 2013; 2014a). In recent years, the biosynthesis method using plant extracts has received more attention than chemical and physical methods and even more than the use of microbes, for the nanoscale metal synthesis, due to the absence of any requirement to maintain an aseptic environment. Nanoparticles have attracted considerable attention because of their various applications. Use of plant extract for the synthesis of nanoparticles could be advantageous over other environmentally benign biological processes because it eliminates the elaborate process of maintaining cell cultures. Recently, green AgNPs have been synthesized using various natural products like *Feronia elephantum* (Veerakumar *et al.*, 2014b).

The larvicidal and repellent properties of essential oils from various parts of four plant species *Cymbopogon citrates*, *Cinnamomum zeylanicum*, *Rosmarinus officinalis*, and *Zingiber officinale* against *Culex tritaeniorhynchus* and *Anopheles subpictus* (Govindarajan *et al.*, 2011). The larvicidal

activities of myco synthesized AgNPs against vectors and responsible for diseases of public health importance have been evaluated (Salunkhe *et al.*, 2011). The toxicity of mosquito larvicidal activity of leaf essential oil and their major chemical constituents from *Ocimum basilicum* were evaluated against *C. tritaeniorhynchus*, *Aedes albopictus*, and *An. subpictus* (Govindarajan *et al.*, 2013).

The larvicidal activity of AgNPs synthesized using *F. elephantum* plant leaf extract against late third instar larvae of *Anopheles stephensi*, *A. aegypti*, and *C. quinquefasciatus* (Veerakumar *et al.*, 2014b). The adulticidal and repellent activities of crude hexane, ethyl acetate, benzene, chloroform, and methanol extracts of leaf of *Eclipta alba* and *Acalypha paniculata* were assayed for their toxicity against two important vector mosquitoes, viz., *C. quinquefasciatus* and *A. aegypti* (Govindarajan and Sivakumar 2012). The larvicidal efficacy of the crude leaf extracts of *Ficus benghalensis*, with three different solvents such as methanol, benzene, and acetone, were tested against the early second, third, and fourth instar larvae of *C. quinquefasciatus*, *A. aegypti*, and *A. stephensi* (Govindarajan, 2010).

The adulticidal activity of AgNPs synthesized using *Heliotropium indicum* plant leaf extract against adults of *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus* (Veerakumar *et al.*, 2014c). *Sida* is an erect perennial shrub found throughout the hotter parts of India and Nepal. The genus name *Sida* is from the Greek for “pomegranate or water lily,” Tamil name Vatta thiruthi. Carl Linnaeus adopted the name from the writings of Theophrastus. Many *Sida* are attractive to butterflies and moths. Arrow leaf *sida*, for example, is a larval host for the Tropical Checkered Skipper (*Pyrgus oileus*). These are annual or perennial herbs or shrubs growing 20 cm (7.9 in) to two meters (6 ft 7 in) tall. Most species have hairy herbage. The leaf blades are usually unlobed with serrated edges, but may be divided into lobes.

They are borne on petioles and have stipules. Flowers are solitary or arranged in inflorescences of various forms. There are many stamens and a style divided into several branches. The fruit is a disc-shaped schizocarp up to two centimeters (0.79 in) wide which is divided into five to 12 sections, each containing a seed. It is used for various medicinal purposes such as liver disorders, diuretic and abortifacient, in ayurvedic preparations, asthma, fever, headache (migraine), cough, cold, ulcer, anthelmintic, snake bite, urinary diseases, female disorders, antifertility agents, and sedative (Kirtikar *et al.*, 1993). In this research, we reported a method to biosynthesize AgNPs using the

aqueous leaf extract of the *Sida acuta*, a cheap and eco-friendly material acting as reducing and stabilizing agent. AgNPs were characterized by ultraviolet-visible (UV-Vis) spectrophotometry, Fourier transform infrared (FT-IR) spectroscopy, scanning electron microscopy (SEM), energy-dispersive X-ray analysis (EDX), and transmission electron microscopy (TEM). In the research evaluated, the aqueous extract of *S. acuta* and the biosynthesized AgNPs were tested for their adulticidal potential against the malaria vector *A. stephensi*, the dengue vector *A. aegypti* and the Japanese encephalitis vector *C. quinquefasciatus*.

## MATERIALS AND METHODS

### Materials

Silver nitrate was procured from Merck, India. The glassware was acid-washed thoroughly and then rinsed with Millipore Milli-Q water. Healthy and fresh leaves of *S. acuta* (Figure 1) were collected from Annamalai Nagar area, Tamil Nadu State, India. The identity was confirmed at the Department of Botany, Annamalai University, Annamalai Nagar, Tamil Nadu. Voucher specimens were numbered and kept in our laboratory and were available on request.

### Preparation of Plant Extract

Leaves of *S. acuta* were dried in the shade and ground to fine powder in an electric grinder. The aqueous extract was prepared by mixing 50 g of dried leaf powder with 500 mL of water (boiled and cooled distilled water) with constant stirring on a magnetic stirrer. The suspension of dried leaf powder in water was left for 3 h and filtered through Whatman No. 1 filter paper, and the filtrate was stored in an amber-colored airtight bottle at 10°C temperature until testing (Veerakumar et al., 2013).



Figure 1: *Sida acuta*

### Biosynthesis and Characterization of AgNPs

The broth solution of fresh leaves was prepared by taking 10 g of thoroughly washed and finely cut leaves in a 300 mL Erlenmeyer flask along with 100 mL of sterilized double-distilled water and then boiling the mixture for 5 min before finally decanting it. The extract was filtered with Whatman filter paper No. 1, stored at -15°C and tested within a week. The filtrate was treated with aqueous 1 mM AgNO<sub>3</sub> (21.2 mg of AgNO<sub>3</sub> in 125 mL of Milli-Q water) solution in an Erlenmeyer flask and incubated at room temperature. 88 mm of an aqueous solution of 1 mM silver nitrate was reduced using 12 mL of leaf extract at room temperature for 10 min, resulting in a brown-yellow solution indicating the formation of AgNP.

The bioreduction of Ag<sup>+</sup> ions was monitored using UV-visible spectrophotometer (UV-160v, Shimadzu, Japan). Analysis of size, morphology, and composition of AgNP was performed by SEM (Hitachi S3000 H SEM), TEM (TEM Technite 10 Philips) and EDX. The purified AgNP was examined for the presence of biomolecules using FT-IR spectrum (Thermo Scientific Nicolet 380 FT-IR Spectrometer) KBr pellets.

### Mosquito Rearing

Laboratory-bred pathogen-free strains of mosquitoes were reared in the vector control laboratory, Department of Zoology, Annamalai University. At the time of adult feeding, these mosquitoes were 3-4 days old after emergences (maintained on raisins and water) and were starved for 12 h before feeding. Each time, 500 mosquitoes per cage were fed on blood using a feeding unit fitted with Parafilm as membrane for 4 h. *A. aegypti* feeding was done from 12 noon to 4.00 p.m. and *A. stephensi* and *C. quinquefasciatus* were fed during 6.00 p.m. to 10.00 p.m. A membrane feeder with the bottom end fitted with Parafilm was placed with 2.0 ml of the blood sample (obtained from a slaughter house by collecting in a heparinized vial and stored at 4°C) and kept over a netted cage of mosquitoes. The blood was stirred continuously using an automated stirring device, and a constant temperature of 37°C were maintained using a water jacket circulating system. After feeding, the fully engorged females were separated and maintained on raisins. Mosquitoes were held at 28°C ± 2°C, 70-85% relative humidity, with a photoperiod of 12 h light and 12 h dark.

### Adulticidal Experiment

Adulticidal bioassay was performed by the WHO method (1981). Based on the wide range and narrow range tests,

the aqueous crude extract was tested at 40, 80, 120, 160, and 200  $\mu\text{g}/\text{mL}$  concentrations and AgNPs were tested at 8, 16, 24, 32, and 40  $\mu\text{g}/\text{mL}$  concentrations. Aqueous crude extract and AgNPs were applied on Whatman no. 1 filter papers (size 12 cm  $\times$  15 cm). Control papers were treated with silver nitrate and distilled water. Twenty female mosquitoes were collected and gently transferred into a plastic holding tube. The mosquitoes were allowed to acclimatize in the holding tube for 1 h and then exposed to test paper for 1 h. At the end of the exposure period, the mosquitoes were transferred back to the holding tube and kept 24 h for the recovery period. A pad of cotton soaked with 10% glucose solution was placed on the mesh screen. Each test included a set control groups (silver nitrate and distilled water) with five replicates for each individual concentration.


### Data Analysis

Mortality data were subjected to probit analysis.  $\text{LD}_{50}$  and  $\text{LD}_{90}$  were calculated using the method by Finney (1971). All data were analyzed using the SPSS Statistical Software Package version 16.0. A probability level of  $P < 0.05$  was used for the significance of differences between values.


## RESULTS AND DISCUSSION

### Biosynthesis and Characterization of AgNPs

While silver nitrate was added to the *S. acuta* leaf extract, the formation of AgNP occurred and color changed from yellowish to dark brown (Figure 2a). The intensity of color was directly proportional to the formation of AgNP. The color change was rapid, and as soon as the two solutions were mixed, the solution turned brown within 10 min. This color change was due to the reduction of  $\text{Ag}^+$  to  $\text{Ag}^0$  by various biomolecules present in the leaf extract. The UV-Vis absorption spectrum was reported in Figure 2b; an intense, broad absorption peak was observed at 449 nm because of surface plasmon resonance (SPR). SPR peak is sensitive to the size and shape of the nanoparticles, amount of extract, silver nitrate concentration, and the type of biomolecules present in the leaf extract (Singh *et al.*, 2010; Zargar *et al.*, 2011). The AgNP was observed as stable in solution and also showed little aggregation. Besides, the plasmon bands were broadened with an absorption tail in longer wavelengths; this could be related to the size distribution of nanoparticles (Ahmad *et al.*, 2003). The FT-IR spectrum of biosynthesized AgNP by using *S. acuta* leaf extract is shown in Figure 3. It showed main bands at O-H group (1269.92/cm), C=N stretch (1486.57),  $-\text{NH}_2$  (1636.98), =NH (2332.25), -H stretch (2358.27), and O-H stretch (3345.57).

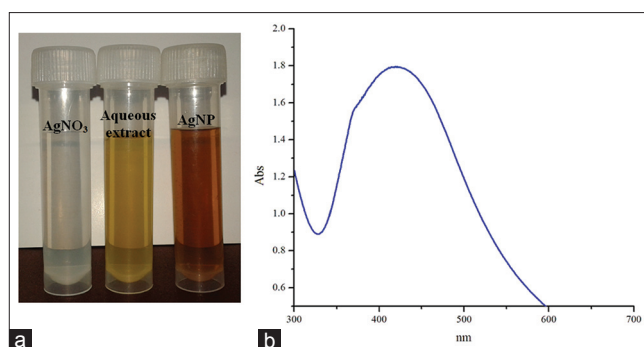

**Figure 2:** (a) Color intensity of *Sida acuta* aqueous extract before and after the reaction with silver nitrate aqueous solution (1 mM). The color change indicates  $\text{Ag}^+$  reduction to elemental nanosilver. (b) Ultraviolet-visible spectrum of silver nanoparticles after 180 min from the reaction

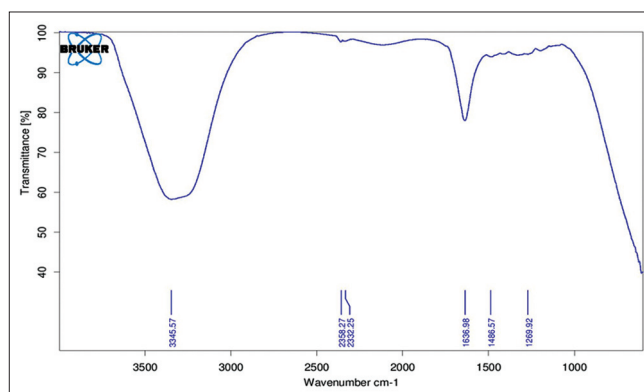

**Figure 3:** Fourier transform infrared spectrum of silver nanoparticles biosynthesized using the *Sida acuta* aqueous leaf extract

In particular, the band at 3345/cm corresponded to O-H, as also the H-bonded alcohols and phenols. Shanmugam *et al.* (2014) suggested that these bonds could be due to the stretching of -OH in proteins, enzymes or polysaccharides present in the extract. The peak at 2358/cm indicated carboxylic acid (Li *et al.*, 2007). Shoulder peaks at 1636/cm indicated that the amide I and amide II arise due to carbonyl and -NH stretch vibrations in the amide linkages of the proteins. The band at 1269/cm corresponded to C,C stretching of the aromatic amine. Overall, the immediate reduction of silver ions in the present investigation seems linked with the presence of water-soluble phytochemicals such as flavones, quinones, and organic acids present in the leaves of *S. acuta*.

A representative SEM micrograph (Figure 4a) of AgNP showed that nanoparticles were mostly spherical or with cubic structures. We also noted that “capped” AgNPs were stable in solution for at least 8 weeks. The EDX analysis provided information on the chemical analysis of the fields being investigated or the composition at specific locations (spot EDX). Figure 4b shows a representative profile of

the spot EDX analysis, obtained by focusing on AgNP. As a general trend, the particle shape of plant-mediated AgNP was spherical, with the exception of some neem-synthesized AgNP. They are polydisperse, with spherical or flat, plate-like, morphology, and mean size range of 5-35 nm in size (Shankar *et al.*, 2004). Furthermore, SEM images of AgNP fabricated using *Emblica officinalis* were also predominantly spherical with an average size of 16.8 nm ranging from 7.5 to 25 nm (Ankamwar *et al.*, 2005).

Moreover, Figure 5 shows the TEM of AgNP synthesized using *S. acuta* leaf extract. Among shapes, spheres, triangle, truncated triangles, and decahedral morphologies dominated and ranged from 32 to 45 nm with an average size of 38 nm. Most of the AgNP was roughly circular in shape with smooth edges. In agreement with these findings, AgNP from *Annona*

*squamosa* leaf extract were spherical in shape with an average size ranging from 20 to 100 nm (Vivek *et al.*, 2012) while Thirunavokkarasu *et al.* (2013) reported spherical nanoparticles with size ranging from 8 to 90 nm using *Desmodium gangeticum* as reducing agent. Our TEM images also showed that the surfaces of the AgNPs were surrounded by a black thin layer of some material, which might be due to the capping organic constituents of the plant broth as previously highlighted by Rafiuddin (2013).


### Adulticidal Potential against Mosquito Vectors

In laboratory conditions, the *S. acuta* aqueous leaf extract showed adulticidal properties against *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus*; LC<sub>50</sub> values were 157.88, 164.89 and 177.48 µg/ml, for *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus*, respectively (Table 1). Recently, a growing number of plant extracts have been found effective against *C. quinquefasciatus* larvae (e.g. Govindarajan *et al.*, 2013; Veerakumar *et al.*, 2014; 2013; Sivakumar and Govindarajan, 2013).


Furthermore, the *S. acuta*-synthesized AgNPs were highly toxic against *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus* adults; LC<sub>50</sub> values were 35.12, 39.53, and 41.44 µg/ml, *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus*, respectively (Table 2). In latest years, a growing number of plant-synthesized AgNP has been studied for their excellent adulticidal activity against important mosquito vectors (Veerakumar *et al.*, 2014c). For instance, the larvicidal activity of AgNP biosynthesized using *S. acuta* plant leaf extract was tested against III instar larvae of *C. quinquefasciatus* (LC<sub>50</sub> = 26.13 µg/mL), *A. stephensi* (LC<sub>50</sub> = 21.92 µg/mL), and *A. aegypti* (LC<sub>50</sub> = 23.96 µg/mL) (Veerakumar *et al.*, 2013). The mortality effect evoked by AgNP on mosquito larvae and pupae may be due by the small size of the AgNP, which allows their passage through the insect cuticle and into individual cells, where they interfere with molting and other physiological processes.

### CONCLUSIONS

Overall, we biosynthesized AgNPs using a cheap aqueous extract of *S. acuta* leaves as reducing and stabilizing agent. Our AgNPs were mostly spherical in shape, crystalline in nature, with face-centered cubic geometry, and their mean size was 28-35 nm. This research highlighted that *S. acuta* -synthesized AgNPs are easy to produce, stable over time, and can be employed at low dosages to strongly reduce populations of vectors mosquitoes.

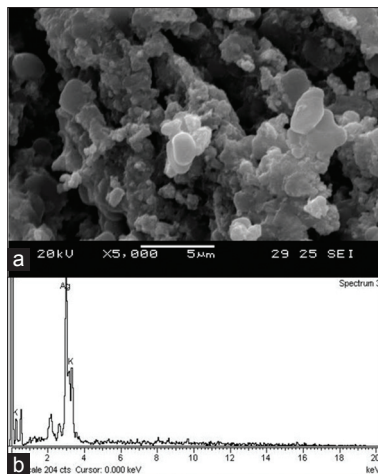

**Figure 4:** Silver nanoparticles biosynthesized using the *Sida acuta* leaf extract: (a) Scanning electron micrograph (5000×); (b) EDX spectrum showing chemical composition

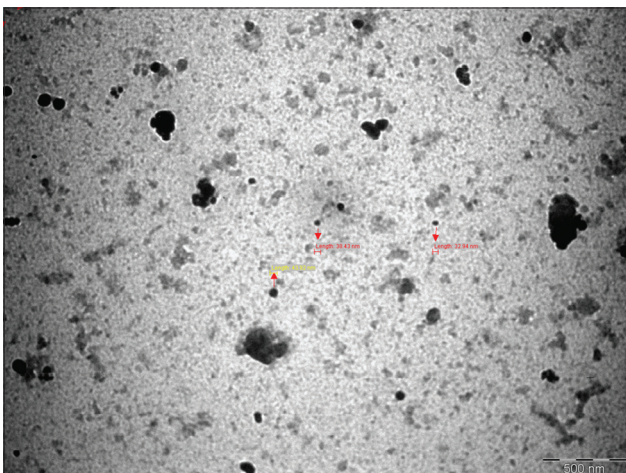

**Figure 5:** Transmission electron microscopy micrograph of silver nanoparticles biosynthesized using the *Sida acuta* aqueous extract

**Table 1: Adulticidal activity of *S. acuta* aqueous leaf extract against the mosquito vectors *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus***

Mosquitoes	Concentration	24 h mortality (%)±SD <sup>a</sup>	LD <sub>50</sub> (µg/mL) (LCL-UCL)	LD <sub>90</sub> (µg/mL) (LCL-UCL)	χ <sup>2</sup>
<i>A. stephensi</i>	Control	0.0±0.0	157.88 (109.89-203.33)	287.44 (234.84-401.57)	21.933*
	70	31.7±2.0			
	140	42.3±1.4			
	210	65.6±1.8			
	280	84.3±0.6			
	350	100.0±0.0			
<i>A. aegypti</i>	Control	0.0±0.0	164.89 (121.20-207.16)	299.01 (248.05-402.42)	18.493*
	70	29.7±0.4			
	140	40.3±1.6			
	210	63.2±1.9			
	280	82.4±0.8			
	350	98.6±1.2			
<i>C. quinquefasciatus</i>	Control	0.0±0.0	177.48 (135.60-220.02)	321.05 (268.06-427.43)	16.743*
	70	26.4±0.8			
	140	39.2±1.9			
	210	58.6±1.3			
	280	76.2±0.4			
	350	96.7±1.5			

<sup>a</sup>Values are mean±SD of five replicates. No mortality was observed in the control, SD: Standard deviation, LD<sub>50</sub>: Lethal concentration that kills 50% of the exposed organisms, LD<sub>90</sub>: Lethal concentration that kills 90% of the exposed organisms, UCL: 95% upper confidence limit, LCL: 95% lower confidence limit, χ<sup>2</sup>: Chi-square, \*Significant at *P*<0.05 level, *A. stephensi*: *Anopheles stephensi*, *A. aegypti*: *Aedes aegypti*, *C. quinquefasciatus*: *Culex quinquefasciatus*, *S. acuta*: *Sida acuta*

**Table 2: Adulticidal activity of silver nanoparticles biosynthesized using the *S. acuta* leaf extract against the mosquito vectors *A. stephensi*, *A. aegypti*, and *C. quinquefasciatus***

Mosquitoes	Concentration	24 h mortality (%)±SD <sup>a</sup>	LD <sub>50</sub> (µg/mL) (LCL-UCL)	LD <sub>90</sub> (µg/mL) (LCL-UCL)	χ <sup>2</sup>
<i>A. stephensi</i>	Control	0.0±0.0	35.12 (25.94-44.94)	62.60 (51.99-84.17)	18.945*
	15	27.1±0.2			
	30	43.4±1.3			
	45	61.7±1.6			
	60	83.3±0.8			
	75	100.0±0.0			
<i>A. aegypti</i>	Control	0.0±0.0	39.53 (30.08-49.27)	70.94 (58.92-95.98)	17.763*
	15	25.4±0.6			
	30	36.0±1.6			
	45	57.3±0.2			
	60	72.6±1.3			
	75	96.2±0.2			
<i>C. quinquefasciatus</i>	Control	0.0±0.0	41.44 (32.25-51.26)	73.94 (61.62-99.46)	16.597*
	15	24.1±0.8			
	30	33.4±1.9			
	45	54.2±0.5			
	60	69.7±1.5			
	75	94.3±0.6			

<sup>a</sup>Values are mean±SD of five replicates. No mortality was observed in the control, SD: Standard deviation, LD<sub>50</sub>: Lethal concentration that kills 50% of the exposed organisms, LD<sub>90</sub>: Lethal concentration that kills 90% of the exposed organisms, UCL: 95% upper confidence limit, LCL: 95% lower confidence limit, χ<sup>2</sup>: Chi-square, \*Significant at *P*<0.05 level, *A. stephensi*: *Anopheles stephensi*, *A. aegypti*: *Aedes aegypti*, *C. quinquefasciatus*: *Culex quinquefasciatus*, *S. acuta*: *Sida acuta*

## ACKNOWLEDGMENTS

The authors would like to thank the Professor and Head of the Department of Zoology, Annamalai University, for the laboratory facilities provided. The authors would also like to acknowledge the cooperation of staff members of the VCRC (ICMR), Pondicherry and thankful to Dr. S. Ramesh, Professor and Head, Veterinary College, Vepery, Chennai for TEM analysis.

## REFERENCES

- Ahmad A, Mukherjee M, Mandal D, Senapati S, Khan MI, Kumar R, et al. Extracellular biosynthesis of silver nanoparticles using the fungus *Fusarium oxysporum*. *Colloid Surf B* 2003;28:313-8.
- Ankamwar B, Chaudhary M, Sastry M. Gold nanotriangles biologically synthesized using tamarind leaf extract and potential application in vapor sensing. *Synth React Inorg Metal Org Nano Metal Chem* 2005;35:19-26.

- Finney DJ. Probit Analysis. London: Cambridge University Press; 1971. p. 68-78.
- Govindarajan M, Jebanesan A, Pushpanathan T. Larvicidal and ovicidal activity of *Cassia fistula* Linn. Leaf extract against filarial and malarial vector mosquitoes. Parasitol Res 2008;102:289-92.
- Govindarajan M, Mathivanan T, Elumalai K, Krishnappa K, Anandan A. Mosquito larvicidal, ovicidal and repellent properties of botanical extracts against *Culex quinquefasciatus*, *Aedes aegypti* and *Anopheles stephensi* (Diptera: Culicidae). Asian Pac J Trop Biomed 2011;1:43-8.
- Govindarajan M, Sivakumar R, Rajeswary M, Yogalakshmi K. Chemical composition and larvicidal activity of essential oil from *Ocimum basilicum* (L.) against *Culex tritaeniorhynchus*, *Aedes albopictus* and *Anopheles subpictus* (Diptera: Culicidae). Exp Parasitol 2013;134:7-11.
- Govindarajan M, Sivakumar R. Adulticidal and repellent properties of indigenous plant extracts against *Culex quinquefasciatus* and *Aedes aegypti* (Diptera: Culicidae). Parasitol Res 2012;110:1607-20.
- Govindarajan M, Sivakumar R. Larvicidal, ovicidal, and adulticidal efficacy of *Erythrina indica* (Lam.) (Family: Fabaceae) against *Anopheles stephensi*, *Aedes aegypti*, and *Culex quinquefasciatus* (Diptera: Culicidae). Parasitol Res 2013;113:777-91.
- Govindarajan M, Sivakumar R. Ovicidal, larvicidal and adulticidal properties of *Asparagus racemosus* (Willd.) (Family: Asparagaceae) root extracts against filariasis (*Culex quinquefasciatus*), dengue (*Aedes aegypti*) and malaria (*Anopheles stephensi*) vector mosquitoes. Diptera: Culicidae). Parasitol Res 2014;113:1435-49.
- Govindarajan M. Larvicidal efficacy of *Ficus benghalensis* L. plant leaf extracts against *Culex quinquefasciatus* Say, *Aedes aegypti* L. and *Anopheles stephensi* L. (Diptera: Culicidae). Eur Rev Med Pharmacol Sci 2010;14:107-11.
- JangYS, Kim MK, AhnYS, Lee HS. Larvicidal activity of Brazilian plant against *Aedes aegypti* and *Culex pipiens* (Diptera: Culicidae). Agric Chem Biotechnol 2002;4:131-4.
- Jensen M, Mehlhorn H. Seventy-five years of Resochin® in the fight against malaria. Parasitol Res 2009;105:609-27.
- Kirtikar KR, Basu BD, Blatter E, Caius JF, Mhaskar KS. Indian Medicinal Plants. 2<sup>nd</sup> ed., Vol. II. Allahabad, India: Lalit Mohan Basu; 1993. p. 1182.
- Li S, ShenY, Xie A, Yu X, Qiu L, Zhang L, et al. Green synthesis of silver nanoparticles using *Capsicum annuum* L. extract. Green Chem 2007;9:852-8.
- Murugan K, Mahesh Kumar P, Kovendan K, Amerasan D, Subramaniam J. Larvicidal, pupicidal, repellent and adulticidal activity of *Citrus sinensis* orange peel extract against *Anopheles stephensi*, *Aedes aegypti* and *Culex quinquefasciatus* (Diptera: Culicidae). Parasitol Res 2012;111:1757-69.
- Rafiuddin ZZ. Bio-conjugated silver nanoparticles from *Ocimum sanctum* and role of cetyltrimethyl ammonium bromide. Colloid Surf B 2007;108:90-4.
- Salunkhe RB, Patil SV, Patil CD, Salunke BK. Larvicidal potential of silver nanoparticles synthesized using fungus *Cochliobolus lunatus* against *Aedes aegypti* (Linnaeus, 1762) and *Anopheles stephensi* Liston (Diptera; Culicidae). Parasitol Res 2011;109:823-83.
- Shankar SS, Rai A, Ahmad A, Sastry M. Biosynthesis of silver and gold nanoparticles from extracts of different parts of the *Geranium* plant. Appl Nanotechnol 2004;1:69-77.
- Shanmugam N, Rajkamal P, Cholan S, Kannadasan N, Sathishkumar K, Viruthagiri G, et al. Biosynthesis of silver nanoparticles from the marine seaweed *Sargassum wightii* and their antibacterial activity against some human pathogens. Appl Nanosci 2014;4:881-8.
- Sharma P, Mohan L, Srivastava CN. *Amaranthus oleracea* and *Euphorbia hirta*: Natural potential larvicidal agents against the urban Indian malaria vector, *Anopheles stephensi* Liston (Diptera: Culicidae). Parasitol Res 2009;106:171-6.
- Singh BP, Hatton BJ, Singh B, Cowie AL, Kathuria A. Influence of biochars on nitrous oxide emission and nitrogen leaching from two contrasting oils. J Environ Q 2010;39:1-12.
- Sivakumar R, Govindarajan M. Mosquito adulticidal activity of *Coccinia indica* wight and arn. (Family: Cucurbitaceae) against *Culex quinquefasciatus* say (Diptera: Culicidae). Int J Curr Sci Technol 2013;2:004-8.
- Thirunavokkarasu M, Balaji U, Behera S, Panda PK, Mishra BK. Biosynthesis of silver nanoparticles from extract of *Desmodium gangeticum* (L.) DC. and its biomedical potential. Spectrochim. Acta Part A Mol Biomol Spectrosc 2013;116:424-7.
- Veerakumar A, Govindarajan M, Rajeswary M, Muthukumaran U. Low-cost and eco-friendly green synthesis of silver nanoparticles using *Feronia elephantum* (Rutaceae) against *Culex quinquefasciatus*, *Anopheles stephensi* and *Aedes aegypti* (Diptera: Culicidae). Parasitol Res 2014;113:1775-85.
- Veerakumar K, Govindarajan M, Hoti LS. Evaluation of plant-mediated synthesized silver nanoparticles against vector mosquitoes. Parasitol Res 2014;113:4567-77.
- Veerakumar K, Govindarajan M, Rajeswary M, Muthukumaran U. Mosquito larvicidal properties of silver nanoparticles synthesized using *Heliotropium indicum* (Boraginaceae) against *Aedes aegypti*, *Anopheles stephensi*, and *Culex quinquefasciatus* (Diptera: Culicidae). Parasitol Res 2014;113:2363-73.
- Veerakumar K, Govindarajan M, Rajeswary M. Green synthesis of silver nanoparticles using *Sida acuta* (Malvaceae) leaf extract against *Culex quinquefasciatus*, *Anopheles stephensi*, and *Aedes aegypti* (Diptera: Culicidae). Parasitol Res 2013;112:4073-85.
- Vivek R, Thangam R, Muthuchelian K, Gunasekaran P, Kaveri K,

- Kannan S. Green biosynthesis of silver nanoparticles from *Annona squamosa* leaf extract and its *in vitro* cytotoxic effect on MCF-7 cells. *Process Biochem* 2012;47:2405-10.
- World Health Organization. Dengue and Serbe Dengue. Fact Sheet No. 117. 2014.
- World Health Organization. Instructions for Determining the Susceptibility or Resistance of Adult Mosquitoes to Organochlorine, Organophosphate and Carbamate Insecticides: Diagnostic Test. Geneva: WHO/VBC; 1981. p. 81-807.
- World Health Organization. Lymphatic Filariasis. Fact Sheet No. 102. 2012.
- Zargar M, Hamid AA, Bakar FA, Shamsudin MN, Shameli K, Jahanshiri F, *et al.* Green synthesis and antibacterial effect of silver nanoparticles using *Vitex negundo* L. *Molecules* 2010;6:6667-6.