

STARS

University of Central Florida
STARS

Faculty Bibliography 1990s

Faculty Bibliography

1-1-1995

Neodymium-Doped Sr-5(Po4)(3)F And Sr-5(Vo4)(3)F

Deborah L. Corker

Bruce H. T. Chai

University of Central Florida

John Nicholls

University of Central Florida

George B. Loutts

University of Central Florida

Find similar works at: <https://stars.library.ucf.edu/facultybib1990>

University of Central Florida Libraries <http://library.ucf.edu>

This Article is brought to you for free and open access by the Faculty Bibliography at STARS. It has been accepted for inclusion in Faculty Bibliography 1990s by an authorized administrator of STARS. For more information, please contact STARS@ucf.edu.

Recommended Citation

Corker, Deborah L.; Chai, Bruce H. T.; Nicholls, John; and Loutts, George B., "Neodymium-Doped Sr-5(Po4)(3)F And Sr-5(Vo4)(3)F" (1995). *Faculty Bibliography 1990s*. 1317.

<https://stars.library.ucf.edu/facultybib1990/1317>



Table 2. Selected geometric parameters (Å, °)

Cs(1)—O(2 ⁱ)	2.975 (7)	Ga(1)—O(3 ^{iv})	1.824 (7)
Cs(1)—O(2 ^h)	3.456 (8)	Ga(1)—O(4 ^{ix})	1.842 (7)
Cs(1)—O(4)	3.316 (8)	Ga(1)—O(6)	1.830 (8)
Cs(1)—O(4 ⁱⁱⁱ)	3.337 (8)	Ga(1)—O(7 ^{viii})	1.822 (7)
Cs(1)—O(4 ^{iv})	3.210 (8)	Ga(2)—O(1)	1.827 (7)
Cs(1)—O(5)	3.410 (7)	Ga(2)—O(2 ^{viii})	1.847 (8)
Cs(1)—O(7 ^{iv})	3.063 (8)	Ga(2)—O(5 ^{vii})	1.836 (8)
Cs(1)—O(7 ^v)	3.204 (8)	Ga(2)—O(7)	1.794 (7)
Cs(2)—O(1)	3.173 (7)	B(1)—O(1)	1.39 (1)
Cs(2)—O(1 ^{vi})	3.178 (8)	B(1)—O(2 ^s)	1.37 (1)
Cs(2)—O(2 ^{vii})	3.439 (8)	B(1)—O(3)	1.35 (1)
Cs(2)—O(3)	2.885 (7)	B(2)—O(4)	1.38 (1)
Cs(2)—O(5)	3.102 (7)	B(2)—O(5)	1.37 (1)
Cs(2)—O(5 ^{viii})	3.221 (8)	B(2)—O(6 ^{viii})	1.36 (1)
Cs(2)—O(6)	3.241 (8)		
Cs(2)—O(6 ^{viii})	3.321 (8)		
O(3 ^{iv})—Ga(1)—O(4 ^{ix})	106.2 (4)	O(2 ^{viii})—Ga(2)—O(5 ^{vii})	109.6 (3)
O(3 ^{iv})—Ga(1)—O(6)	104.4 (4)	O(2 ^{viii})—Ga(2)—O(7)	110.4 (3)
O(3 ^{iv})—Ga(1)—O(7 ^{viii})	108.4 (3)	O(5 ^{vii})—Ga(2)—O(7)	108.6 (3)
O(4 ^{ix})—Ga(1)—O(6)	114.4 (3)	O(1)—B(1)—O(2 ^s)	121 (1)
O(4 ^{ix})—Ga(1)—O(7 ^{viii})	110.5 (3)	O(2 ^s)—B(1)—O(3)	121 (1)
O(6)—Ga(1)—O(7 ^{viii})	112.4 (4)	O(3)—B(1)—O(1)	118 (1)
O(1)—Ga(2)—O(2 ^{viii})	104.9 (3)	O(4)—B(2)—O(5)	119 (1)
O(1)—Ga(2)—O(5 ^{vii})	109.4 (3)	O(5)—B(2)—O(6 ^{viii})	118 (1)
O(1)—Ga(2)—O(7)	113.8 (3)	O(6 ^{viii})—B(2)—O(4)	123 (1)

Symmetry codes: (i) $x - 1, y, z$; (ii) $1 - x, -y, -z$; (iii) $-x, y - \frac{1}{2}, \frac{1}{2} - z$; (iv) $x, \frac{1}{2} - y, z - \frac{1}{2}$; (v) $-x, -y, 1 - z$; (vi) $1 - x, \frac{1}{2} + y, \frac{3}{2} - z$; (vii) $x, \frac{1}{2} - y, \frac{1}{2} + z$; (viii) $1 - x, -y, 1 - z$; (ix) $1 + x, y, z$; (x) $x, y, 1 + z$.

A clear, colorless, plate-shaped crystal was mounted on a glass fiber with epoxy for X-ray structure analysis. Data were collected with a scan speed of $16.0^\circ \text{ min}^{-1}$ in ω and a scan width of $(1.5 + 0.3 \tan \theta)^\circ$.

The TEXSAN crystallographic software package (Molecular Structure Corporation, 1989) was used to solve the crystal structure. The Laue symmetry $2/m$ and the systematic absences $h0l$ ($l = 2n + 1$) and $0k0$ ($k = 2n + 1$) unambiguously indicated space group $P2_1/c$. The positions of the Cs atoms were determined by a Patterson vector map and the remaining atoms were found by examination of the difference electron density maps. After isotropic refinement, the data were averaged and corrected for absorption.

Lists of structure factors, anisotropic displacement parameters and complete geometry have been deposited with the IUCr (Reference: BR1078). Copies may be obtained through The Managing Editor, International Union of Crystallography, 5 Abbey Square, Chester CH1 2HU, England.

References

- Heller, G. (1986). *Topics Curr. Chem.* **131**, 39–98.
 Molecular Structure Corporation (1989). *TEXSAN. TEXRAY Structure Analysis Package*. MSC, 3200 Research Forest Drive, The Woodlands, TX 77381, USA.
 Shannon, R. D. (1976). *Acta Cryst.* **A32**, 751–767.
 Walker, N. & Stuart, D. (1983). *Acta Cryst.* **A39**, 158–166.

Acta Cryst. (1995). **C51**, 549–551

Neodymium-Doped $\text{Sr}_5(\text{PO}_4)_3\text{F}$ and $\text{Sr}_5(\text{VO}_4)_3\text{F}$

DEBORAH L. CORKER

Clarendon Laboratory, University of Oxford, Parks Road, Oxford OX1 3PU, England

BRUCE H. T. CHAI, JOHN NICHOLLS AND GEORGE B. LOUITS

CREOL, University of Central Florida, 12424 Research Parkway, Orlando, USA

(Received 22 February 1994; accepted 15 June 1994)

Abstract

Neodymium-doped $\text{Sr}_5(\text{PO}_4)_3\text{F}$ [neodymium strontium fluoride phosphate, $(\text{Nd},\text{Sr})_5(\text{PO}_4)_3\text{F}$] and neodymium-doped $\text{Sr}_5(\text{VO}_4)_3\text{F}$ [neodymium strontium fluoride vanadate, $(\text{Nd},\text{Sr})_5(\text{VO}_4)_3\text{F}$] crystallize in space group $P6_3/m$ and are isostructural with calcium fluorophosphate, $\text{Ca}_5(\text{PO}_4)_3\text{F}$. There are two different Sr sites in $\text{Sr}_5(\text{XO}_4)_3\text{F}$, denoted Sr(1) and Sr(2). Using single-crystal X-ray diffraction the two structures were refined to R factors of 2.3 and 2.2%, respectively, showing that Nd is present at both Sr sites in $(\text{Sr},\text{Nd})_5(\text{VO}_4)_3\text{F}$ but only at the Sr(2) site in $(\text{Sr},\text{Nd})_5(\text{PO}_4)_3\text{F}$.

Comment

Calcium fluorophosphate (FAP) crystals have been investigated previously as laser hosts, and lasing characteristics of rare-earth-doped FAP were reported as early as 1968 (Ohlmann, Steinbruegge & Mazelsky, 1968). Recent developments have reopened investigations into FAP and the whole calcium–strontium fluorophosphate system for use as laser hosts. This paper presents the detailed crystal structure refinements that followed the recent successful crystal growth of neodymium-doped $\text{Sr}_5(\text{PO}_4)_3\text{F}$ (SFAP) and neodymium-doped $\text{Sr}_5(\text{VO}_4)_3\text{F}$ (SVAP).

Both crystals were grown by the Czochralski method. SVAP and SFAP are isostructural and belong to the hexagonal space group $P6_3/m$. The structure contains layers of XO_4 tetrahedra ($X = \text{P}, \text{V}$) centred at two levels along [001] and F^- ions lying along the c axis, as can be seen in Fig. 1. V—O and P—O bond lengths are given in Tables 2 and 4, respectively, and show that the VO_4 tetrahedra are distorted [average/(deviation) for P—O and V—O bond distances are $1.541 \text{ \AA}/(0.004 \text{ \AA})$ and $1.711 \text{ \AA}/(0.01 \text{ \AA})$, respectively].

There are two independent Sr sites in the structures, the first of which, Sr(1), contains 40% of the Sr^{2+}

ions when fully occupied and has threefold symmetry. The remaining 60% of the Sr^{2+} ions are found at the Sr(2) sites, which have reflection symmetry in the plane perpendicular to the c axis. Each Sr(2) site has an F^- ion as its nearest neighbour. Nd substitutes for Sr in both SVAP and SFAP, but the location of the dopant in the two compounds is different to within the precision of the X-ray structure refinement. Nd^{3+} was found to be present on the Sr(2) site in both SVAP and SFAP, but only in SVAP was Nd^{3+} present on the Sr(1) site as well.

A charge-compensation mechanism is required for the 1:1 substitution of Nd^{3+} for Sr^{2+} . This has been discussed previously by Mackie & Young (1973) for the similar structure of neodymium-doped FAP, where the substitution of O^{2-} for F^- and the creation of Ca^{2+} (in this case Sr^{2+}) vacancies were considered. For this reason, all site occupancies in the present work were refined. In both SVAP and SFAP all the O-site occupancies converged to a value slightly greater than unity, and so were fixed at unity for the final cycles of refinement. Likewise, the occupancy of the F sites refined to a value greater than or within experimental error of unity. However, a reduction in the site occupancy factors for the V and P sites in SVAP and SFAP, respectively, was observed, which could be the mechanism for charge balance in these compounds.

Further evidence supporting the location of the Nd dopant was obtained by investigation of the absorption and fluorescence spectra of Nd in SVAP and SFAP. This work, carried out at CREOL, suggested that essentially all the Nd in SFAP is on the Sr(2) site, while Nd was

seen on both Sr sites in SVAP. However, the results indicated a preference for the Sr(2) site which could not be seen from the X-ray analysis. The preference for substitution at the Sr(2) site, which is smaller than the Sr(1) site, can be explained by the fact that the ionic radius of Nd^{3+} is much smaller than that of Sr^{2+} .

Experimental

SVAP

Crystal data

$(\text{Sr}_{0.982}\text{Nd}_{0.012})_5(\text{VO}_4)_3\text{F}$

$M_r = 798.02$

Hexagonal

$P6_3/m$

$a = 10.0077$ (6) Å

$c = 7.4342$ (8) Å

$V = 644.82$ Å³

$Z = 2$

$D_x = 4.11$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71069$ Å

Cell parameters from 36 reflections

$\theta = 18\text{--}20^\circ$

$\mu = 23.66$ mm⁻¹

Room temperature

Irregular

$0.15 \times 0.11 \times 0.07$ mm

Blue

Data collection

Stoe Stadi-4 diffractometer

ω - 2θ scans

Absorption correction:

ψ scans of five reflections

$T_{\min} = 0.0825$, $T_{\max} =$

0.1860

3146 measured reflections

831 independent reflections

421 observed reflections

$[I > 3\sigma(I)]$

$R_{\text{int}} = 0.078$

$\theta_{\text{max}} = 32.5^\circ$

$h = -13 \rightarrow 13$

$k = -15 \rightarrow 15$

$l = -11 \rightarrow 11$

3 standard reflections

frequency: 60 min

intensity decay: 1.5%

Refinement

Refinement on F

$R = 0.022$

$wR = 0.027$

$S = 0.87$

421 reflections

51 parameters

Weighting scheme:

Chebyshev polynomial

with parameters 16.3,

20.5, 7.19

$(\Delta/\sigma)_{\text{max}} = 0.002$

$\Delta\rho_{\text{max}} = 0.620$ e Å⁻³

$\Delta\rho_{\text{min}} = -0.677$ e Å⁻³

Extinction correction:

secondary (Larson, 1970)

Extinction coefficient: 99 (4)

Atomic scattering factors

from *International Tables*

for *X-ray Crystallography*

(1974, Vol. IV)

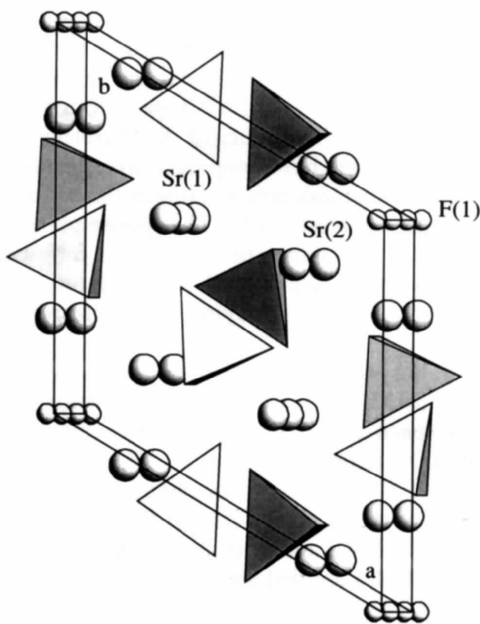


Fig. 1. The structure of $\text{Sr}_5(\text{PO}_4)_3\text{F}$ projected along $[001]$ and then rotated 6° around the y axis, showing the two Sr sites and the PO_4 tetrahedra.

Table 1. Fractional atomic coordinates and equivalent isotropic displacement parameters (Å²) for SVAP

$$U_{\text{eq}} = (1/3)\sum_i\sum_j U_{ij}a_i^*a_j^*a_i\cdot a_j.$$

	Occupancy	x	y	z	U_{eq}
Sr(1)	0.980 (3)	1/3	2/3	0.0004 (1)	0.0123 (3)
Nd(1)	0.014 (3)	1/3	2/3	0.0004 (1)	0.0123 (3)
Sr(2)	0.983 (3)	0.23884 (7)	-0.01060 (8)	1/4	0.0114 (3)
Nd(2)	0.011 (2)	0.23884 (7)	-0.01060 (8)	1/4	0.0114 (3)
O(1)	1.0	0.3159 (7)	0.4835 (6)	1/4	0.014 (3)
O(2)	1.0	0.5962 (6)	0.4705 (6)	1/4	0.016 (3)
O(3)	1.0	0.3405 (5)	0.2498 (4)	0.0671 (6)	0.018 (2)
V(1)	0.972 (4)	0.3982 (1)	0.3682 (1)	1/4	0.0080 (5)
F(1)	0.98 (2)	0	0	1/4	0.023 (6)

Table 2. Selected geometric parameters (Å) for SVAP

Sr(1)—O(1 ⁱ)	2.552 (3)	Sr(2)—O(3 ^{vii})	2.510 (4)
Sr(1)—O(1 ⁱⁱ)	2.552 (3)	Sr(2)—O(2 ^{viii})	2.521 (5)
Sr(1)—O(1)	2.552 (3)	Sr(2)—O(3 ^{ix})	2.651 (4)
Sr(1)—O(2 ⁱⁱⁱ)	2.611 (4)	Sr(2)—O(3)	2.651 (4)
Sr(1)—O(2 ^{iv})	2.611 (4)	Sr(2)—O(1 ^x)	2.768 (6)
Sr(1)—O(2 ^v)	2.611 (4)	Sr(2)—O(3 ^x)	3.569 (4)
Sr(1)—O(3 ^{vi})	2.980 (4)	Sr(2)—O(3 ^{xi})	3.569 (4)
Sr(1)—O(3 ^{vii})	2.980 (4)	V(1)—O(1)	1.721 (5)
Sr(1)—O(3 ^{viii})	2.980 (4)	V(1)—O(2)	1.716 (5)
Sr(2)—F(1)	2.445 (1)	V(1)—O(3)	1.703 (4)
Sr(2)—O(3 ^{xii})	2.510 (4)	V(1)—O(3 ^{ix})	1.703 (4)

Symmetry codes: (i) $y - x, 1 - x, \frac{1}{2} - z$; (ii) $1 - y, 1 + x - y, \frac{1}{2} - z$; (iii) $x - y, x, -z$; (iv) $y, 1 + y - x, -z$; (v) $1 - x, 1 - y, -z$; (vi) $y, -x + y, \frac{1}{2} + z$; (vii) $y, y - x, -z$; (viii) $1 - y, -y + x, z$; (ix) $x, y, \frac{1}{2} - z$; (x) $-x + y, -x, z$; (xi) $y - x, -x, \frac{1}{2} - z$.

SFAP

Crystal data

(Sr_{0.992}Nd_{0.005})₅(PO₄)₃F $M_r = 739.79$

Hexagonal

 $P6_3/m$ $a = 9.7156$ (4) Å $c = 7.2810$ (3) Å $V = 595.19$ Å³ $Z = 2$ $D_x = 4.13$ Mg m⁻³Mo $K\alpha$ radiation $\lambda = 0.71069$ Å

Cell parameters from 46 reflections

 $\theta = 17-19^\circ$ $\mu = 23.73$ mm⁻¹

Room temperature

Irregular

 $0.14 \times 0.10 \times 0.06$ mm

Blue-purple

Data collection

Stoe Stadi-4 diffractometer

 $\omega-2\theta$ scans

Absorption correction:

 ψ scans of five reflections $T_{\min} = 0.0817, T_{\max} = 0.2043$

3682 measured reflections

942 independent reflections

460 observed reflections

 $[I > 3\sigma(I)]$ $R_{\text{int}} = 0.075$ $\theta_{\max} = 35^\circ$ $h = -13 \rightarrow 13$ $k = -15 \rightarrow 15$ $l = -11 \rightarrow 11$

3 standard reflections

frequency: 60 min

intensity decay: 1%

Refinement

Refinement on F $R = 0.023$ $wR = 0.029$ $S = 0.84$

460 reflections

51 parameters

Weighting scheme:

Chebychev polynomial
with parameters 7.0, 8.44,
3.09 $(\Delta/\sigma)_{\max} = 0.002$ $\Delta\rho_{\max} = 0.881$ e Å⁻³ $\Delta\rho_{\min} = -0.741$ e Å⁻³

Extinction correction:

secondary (Larson, 1970)

Extinction coefficient: 67 (3)

Atomic scattering factors

from *International Tables*
for *X-ray Crystallography*
(1974, Vol. IV)Table 3. Fractional atomic coordinates and equivalent isotropic displacement parameters (Å²) for SFAP

$$U_{\text{eq}} = (1/3)\sum_i\sum_j U_{ij}a_i^*a_j^*a_i \cdot a_j$$

	Occupancy	x	y	z	U_{eq}
Sr(1)	0.996 (3)	1/3	2/3	-0.0002 (1)	0.0098 (3)
Sr(2)	0.989 (3)	0.23910 (7)	-0.01445 (7)	1/4	0.0092 (3)
Nd(2)	0.009 (2)	0.23910 (7)	-0.01445 (7)	1/4	0.0092 (3)

O(1)	1.0	0.3306 (6)	0.4810 (6)	1/4	0.011 (2)
O(2)	1.0	0.5827 (5)	0.4644 (6)	1/4	0.010 (3)
O(3)	1.0	0.3441 (4)	0.2612 (4)	0.0788 (5)	0.013 (2)
P(1)	0.975 (5)	0.3992 (2)	0.3685 (2)	1/4	0.0066 (6)
F(1)	1.0	0	0	1/4	0.021 (6)

Table 4. Selected geometric parameters (Å) for SFAP

Sr(1)—O(1 ⁱ)	2.554 (3)	Sr(2)—O(3 ^{vii})	2.522 (3)
Sr(1)—O(1 ⁱⁱ)	2.554 (3)	Sr(2)—O(1 ^{viii})	2.744 (5)
Sr(1)—O(1)	2.554 (3)	Sr(2)—O(3)	2.652 (3)
Sr(1)—O(2 ⁱⁱⁱ)	2.576 (3)	Sr(2)—O(3 ^{ix})	2.652 (3)
Sr(1)—O(2 ^{iv})	2.576 (3)	Sr(2)—O(2 ^v)	2.499 (4)
Sr(1)—O(2 ^v)	2.576 (3)	Sr(2)—O(3 ^{viii})	3.403 (4)
Sr(1)—O(3 ^{vi})	2.906 (4)	Sr(2)—O(3 ^{xii})	3.403 (4)
Sr(1)—O(3 ^{vii})	2.906 (4)	P(1)—O(1)	1.539 (4)
Sr(1)—O(3 ^{viii})	2.906 (4)	P(1)—O(2)	1.545 (5)
Sr(2)—F(1)	2.396 (1)	P(1)—O(3)	1.539 (3)
Sr(2)—O(3 ^{ix})	2.522 (3)	P(1)—O(3 ^{ix})	1.539 (3)

Symmetry codes: (i) $y - x, 1 - x, \frac{1}{2} - z$; (ii) $1 - y, 1 + x - y, \frac{1}{2} - z$; (iii) $x - y, x, -z$; (iv) $y, 1 + y - x, -z$; (v) $1 - x, 1 - y, -z$; (vi) $y, -x + y, \frac{1}{2} + z$; (vii) $y, y - x, -z$; (viii) $-x + y, -x, z$; (ix) $x, y, \frac{1}{2} - z$; (x) $1 - y, -y + x, z$; (xi) $y - x, -x, \frac{1}{2} - z$.

Data were collected using a learnt-profile method (Clegg, 1981). Data collection and reduction were performed using *DIF4* (Stoe & Cie, 1988a) and *REDU4* (Stoe & Cie, 1988b). Cell constants were refined using high 2θ reflections extracted from the data collection and measured with double stepscans. Refinement of both structures was carried out using *CRYSTALS* (Watkin, Carruthers & Betteridge, 1985). The atomic coordinates for Ca₅(PO₄)₃F (Mackie & Young, 1973) were used as an initial model for both refinements. The positional and displacement parameters for Nd rode with the corresponding Sr parameters. Their occupancies were refined separately so that a vacancy on an Sr site would not give rise to an increase in Nd occupancy.

DLC wishes to thank Dr A. M. Glazer for producing the diagram of Sr₅(PO₄)₃F shown in this paper and also wishes to express gratitude to the Science and Engineering Research Council for a studentship.

Lists of structure factors and anisotropic displacement parameters have been deposited with the IUCr (Reference: DU1084). Copies may be obtained through The Managing Editor, International Union of Crystallography, 5 Abbey Square, Chester CH1 2HU, England.

References

- Clegg, W. (1981). *Acta Cryst.* **A37**, 22–28.
 Larson, A. C. (1970). *Crystallographic Computing*, edited by F. R. Ahmed, S. R. Hall & C. P. Huber, pp. 291–294. Copenhagen: Munksgaard.
 Mackie, P. E. & Young, R. A. (1973). *J. Appl. Cryst.* **6**, 26–31.
 Ohlmann, R. C., Steinbruegge, K. B. & Mazelsky, R. (1968). *Appl. Opt.* **7**, 905–914.
 Stoe & Cie (1988a). *DIF4. Diffractometer Control Program*. Version 6.2. Stoe & Cie, Darmstadt, Germany.
 Stoe & Cie (1988b). *REDU4. Data Reduction Program*. Version 6.2. Stoe & Cie, Darmstadt, Germany.
 Watkin, D. J., Carruthers, J. R. & Betteridge, P. W. (1985). *CRYSTALS User Guide*. Chemical Crystallography Laboratory, Univ. of Oxford, England.