



Citation for published version:

Pesce, GL, Ball, RJ, Bowen, CR, Kurchania, R & Bhalla, S 2012, Monitoring hydration in lime - metakaolin composites. in M Russell (ed.), *32nd Cement & Concrete Science Conference, 17-18 September 2012, Queens University Belfast, Belfast*. pp. 116-121, 32nd Cement & Concrete Science Conference, Belfast, UK United Kingdom, 16/09/12.

Publication date:
2012

Document Version
Publisher's PDF, also known as Version of record

[Link to publication](#)

University of Bath

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

32nd Cement and Concrete Science Conference 2012



The Queen's University of Belfast, UK

17-18 September 2012

Editor:

Mark Russell

Supported by:



The Institute of Materials, Minerals & Mining

Monitoring hydration in lime - metakaolin composites

G.L. Pesce, R.J. Ball

Department of Architecture and Civil Engineering, University of Bath, Bath, BA2 7AY, United Kingdom

C. R. Bowen

Department of Mechanical Engineering, University of Bath, BA2 7AY, United Kingdom

R. Kurchania

Department of Physics, Maulana Azad National Institute of Technology (MANIT), Bhopal, India

S. Bhalla

Department of Civil Engineering, Indian Institute of Technology (IIT) Delhi, Hauz Khas, New Delhi, India

ABSTRACT

This paper describes a study of the micro-macro property relationships relating to hydraulic setting reactions in air lime - metakaolin mixtures. The application of electrochemical impedance spectroscopy (EIS) to monitor the on-going hardening processes is discussed together with the recorded changes in the chemical, physical and mechanical properties. Scanning electron microscopy (SEM) and bulk characterisation techniques including thermal analyses (TGA/DSC), mercury intrusion porosimetry (MIP) and mechanical property measurements were applied to evaluate structure and composition. Electro-mechanical impedance (EMI) measurements were taken on samples and used to monitor changes in the mechanical properties of the paste. Results showed a clear relationship between the chemical and structural development of the paste while electro-mechanical impedance was sensitive to hydration. Changes in electrical-chemical and mechanical impedance show potential for the development of in-situ sensors for monitoring of lime based composite materials.

1. INTRODUCTION

Impedance spectroscopy (or electro-chemical impedance spectroscopy, EIS) is a non-destructive technique commonly used to study processes in a range of materials including ceramics, polymers and composites. Over the past 30 years its use in the construction industry has been mostly confined to cement hydration and rebar corrosion in concrete (McCarter *et al.*, 1988; McCarter *et al.*, 2002). Only limited work has been carried out in applying this technique to lime binders (Ball *et al.*, 2010; Ball *et al.*, 2011; Ball *et al.*, 2012). The ability of impedance spectroscopy to monitor setting reactions in lime based materials would allow the construction industry to estimate strength development based on quantitative data. This is particularly important in the early days and weeks after mixing when strengths are low and environmental vulnerability to processes such as frost damage is high. Data obtained from EIS is mainly related to the chemical and physical characteristics of the material and does not directly measure mechanical characteristics.

In addition to EIS, electro-mechanical impedance (EMI) is a non-destructive technique whose potential has been shown in the construction

industry for both, structural health monitoring (SHM) and strength development monitoring in concrete (Soh and Bhalla, 2005). EMI applications are of great interest to the construction industry because, unlike other techniques, the sensors used are inexpensive and simple to use. Furthermore, these sensors have excellent mechanical strength, flat response over a wide frequency range and broad dynamic response (Tawie and Lee, 2011). Research on SHM dates back to the 1990's (Bhalla and Soh, 2004) while research on strength development monitoring has only begun in recent years (Shin and Oh, 2009; Tawie and Lee, 2010a, 2010b).

2. EXPERIMENTAL

The hydraulic reactions between calcium hydroxide, amorphous silica and aluminum hydroxide were followed using a paste of lime and metakaolin. A commercially available hydrated lime classified as a CL 90 according to BS-EN 459-1 (2001) and a metakaolin manufactured by Imerys Minerals Ltd was used (Ball *et al.*, 2012). According to previous research (Edwards, 2009; Aggelakopoulou *et al.*, 2011), optimum mechanical properties were obtained from a 10:1 mixture of lime to metakaolin by weight ratio, therefore a similar mix ratio has been adopted in this study with no added water. Due to the small

quantities of material, the required mixing was performed by hand in a plastic container. A mixing time of approximately eight minutes was adequate to obtain a homogeneous mixture (water-lime ratio of 1.2:1). After mixing, the paste was immediately cast into stainless steel moulds. Evaporation of water and carbonation were minimized by covering the top surface of the moulds that were open to air with a thin layer of plastic. In order to reduce the above mentioned processes during the curing time, the moulds were inserted into a polystyrene box where the temperature was controlled by a thermal bath at $20^{\circ}\text{C}\pm 1$. Inside the box a beaker containing water was left to maintain humidity at near 100% along with a Petri dish containing lime putty to adsorb excess carbon dioxide contained in the atmosphere. Before sealing the boxes, the cell was connected to the impedance analyser and the EIS test was started. The first measurement was recorded one hour after the initial mixing. Throughout a three week period when EIS measurements were acquired, chemical, physical and mechanical tests were performed on the paste after 1, 2 and 3 weeks. In order to evaluate the response of impedance spectroscopy to the hydraulic reactions, a similar test with only lime was also performed. Impedance spectroscopy was performed using a Solartron SI 1260 Impedance/Gain-Phase Analyzer. Measurement acquisition was controlled with SMaRT (Solartron Materials Research and Test; Solartron Mobrey Ltd) software version 2.7.0. Impedance sweeps were taken over a 4 week period in the frequency range 1MHz to 10Hz. During impedance measurements, the sample was housed in an open top polycarbonate reaction cell of internal dimensions 50 x 50 x 50 mm containing two 50 x 50 x 3mm stainless steel electrodes on opposing faces. The sample impedance, $Z(f)$ at a frequency, f , is described in Ball *et al.*, (2011) along with calculation of the relative permittivity (ϵ'_r) and ac conductivity (σ) of the sample at a given frequency. Compressive strengths of the samples were determined using a Instron 'Fastrack' 8800 digitally controlled servo hydraulic system with 100 kN load cell at a loading speed of 0.2 mm/min. Microstructural information relating to phases within the hardened samples was obtained from fresh surface fractures using a Scanning Electron Microscope JEOL JSM6480LV. Thermal analysis was performed using a SETARAM thermo gravimetric - differential scanning calorimetry (TG-DSC) model TGA 92-1750 thermal balance with a 1600°C module. Analysis was made using a dynamic regime, with a temperature rate of $10^{\circ}\text{C}/\text{min}$ up to 950°C , starting from 20°C . During testing, nitrogen gas was flowed inside the furnace in order to avoid any reaction between the samples and atmospheric oxygen or carbon dioxide. In order to have a sample with an average content of moisture, fragments from the inner and the outer regions of the sample were crushed with a pestle

and mortar prior to particles greater than 250 μm being removed with a sieve. Mercury intrusion porosimetry was performed using a Micrometrics AutoPore III utilizing ports for both low and high pressure. Penetrometers (pen and stem) for solid samples with 5 ml volume from Micrometrics were also used. EMI tests were carried out on two lime-metakaolin specimens, each sealed in plastic tubes of diameter 46 mm and height 50 mm. In order to reduce water evaporation and exclude carbon dioxide, and thus carbonation, the two moulds were closed at each ends with plastic. The specimens were de-moulded after one week curing and stored at 30°C . A piezo-concrete composite sensor (Bhalla and Gupta, 2011) was embedded at the mid height of each specimen. EMI measurements were performed with an Agilent 4980A Precision LCR meter in the frequency range between 50 and 350kHz, recording 2500 readings at 1 Volt tension. At each frequency within this range, the values of the real part (conductance) and the imaginary part (susceptance) of admittance were recorded together with the related frequency. Measurements were acquired for the paste at ages between 6 and 19 days.

3. RESULTS AND DISCUSSION

3.1 Electrochemical Impedance Spectroscopy (EIS)

A decrease in dielectric constant (that describes the electric polarizability) and a relatively small increase in ac conductivity with frequency was observed and is shown in Figure 1. The sum of all polarization processes operating within the lime-metakaolin structure contribute to this value at a given frequency of applied field. These processes, which may be superimposed, each have a characteristic relaxation frequency defining the polarisation behaviour. The permittivity across the entire frequency range under study is indicative of a spread of relaxation frequencies. At the lower frequencies the dielectric constant rises to anomalously high values of around 10^8 . This behaviour is attributed to the dominating influence of electrode polarization below this frequency. Previous work suggests polarisation is a combination of electric double-layer polarization and an interfacial polarization processes (Ball *et al.*, 2011). The presence of conductive species, such as water can also lead to very high relative permittivity (Almond and Bowen, 2004). With hardening time, a decrease is recorded in both conductivity and in relative permittivity.

3.2 Compression test

Results from the compression test performed on a one week old sample are shown in Figure 2, which clearly demonstrates a maximum resistance of about 0.30 MPa and a low slope of

curve ($E=557$ MPa). After two weeks the above mentioned slope increases up to about 800 MPa and the maximum load reaches 0.40 MPa. At the end of the third week maximum load rises again, 0.44 MPa, but little change is recorded in the slope of the curve ($E=845$ MPa). At the end of fourth week maximum load rises again, 0.55 MPa and the slope of the curve remains almost constant. In all samples the peak load is followed by a gradually reduction of resistance without breaking of sample.

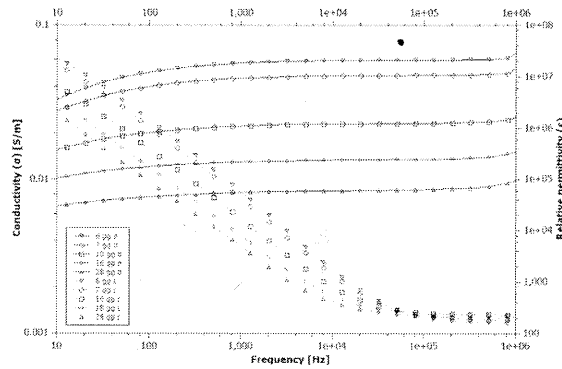


Figure 1. Conductivity and relative permittivity as function of frequency (6, 7, 10, 18 and 28 days).

3.3 Scanning electron microscopy (SEM)

The microstructure of a fresh fracture surface is characterised by the presence of metakaolin plates randomly scattered in a porous matrix, mainly made of non-crystalline compounds. Plates can be single or grouped in packs of 2-8 plates and it is often possible to recognise plate fragments intimately mixed and incorporated into the lime matrix. In a one week old sample it is possible to observe bridges of amorphous phases between two plates and the growth of amorphous structures on the edge of the plates as shown in Figure 3. Metakaolin plates were readily identifiable in the one week old paste. However, it is worth noting that due to the progress of the reaction of metakaolin with lime the plates became covered and harder to identify in the two and three week old pastes. In fact, the SEM microstructure of the four week old sample showed a higher compactness compared with the microstructure at one week.

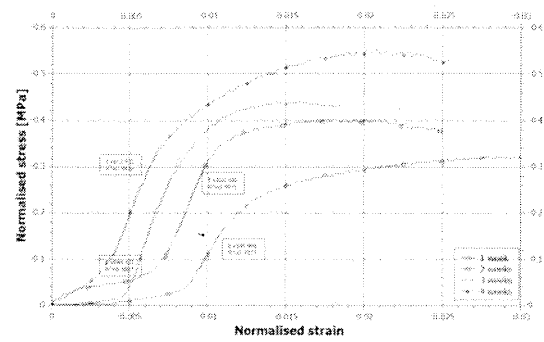


Figure 2. Stress-strain plot for lime-metakaolin paste for one to four weeks.

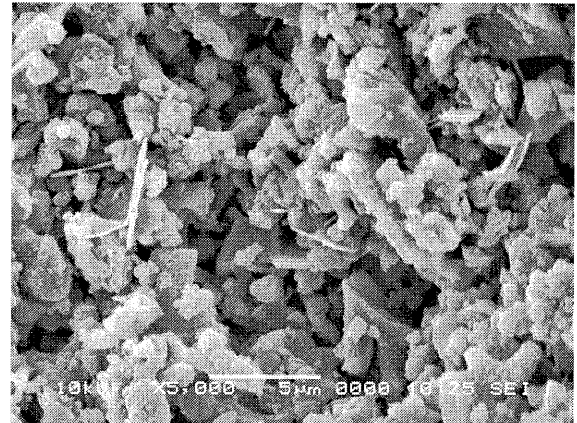


Figure 3. SEM image of lime-metakaolin paste at one week.

3.4 Thermal analyses

The endothermic reaction and weight loss due to dehydration of CSH occurs in the temperature range 110-140°C (Moropoulou *et al.*, 2004; Frias Rojas and Sanchez, 2001; Bakolas *et al.*, 2006) however this is not perfectly clear due to the water evaporation from the pores. Calculations demonstrate a decrease of these compounds between the first and the second week, while their amount remains almost the same between the second and the fourth week. The DSC curves in Figure 4 show a peak between 140-200°C attributed to the dehydration of the hydraulic compound stratlingite (C_2ASH_6). A second less pronounced peak which is visible by close inspection of the one week old sample between 200-270°C, is attributed to hydrogarnet C_4AH_{13} (Moropoulou *et al.*, 2004; Bakolas *et al.*, 2006). A large endothermic peak at about 500°C is due to the dehydration of calcium hydroxide. In all the samples this peak consists of two overlapping peaks attributed to the presence of calcium hydroxide of different crystallinities. According to the test set up, a very small amount of calcium carbonate was detected by the thermal analysis.

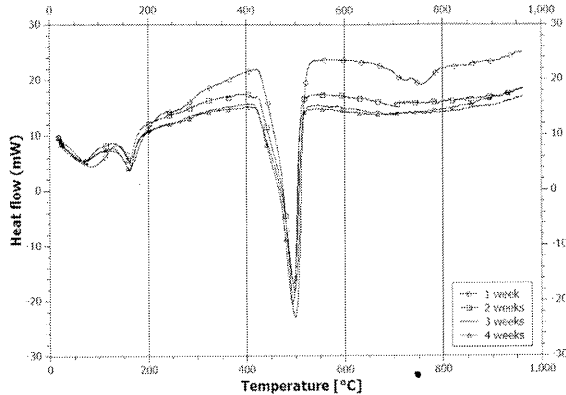


Figure 4. DSC of lime-metakaolin paste up to four weeks.

3.5 Mercury Intrusion Porosimetry (MIP)

Mercury intrusion porosimetry of lime-metakaolin paste aged up to four weeks is shown in Figure 5.

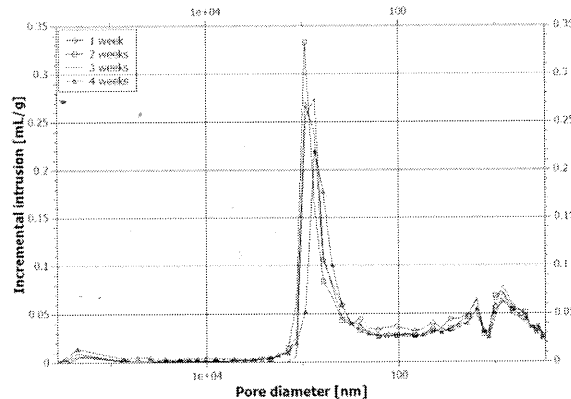


Figure 5. Mercury intrusion porosimetry plot of lime-metakaolin paste aged up to four weeks.

Results of the one week old sample show that pores are mainly in the 400-1200 nm diameter range but a small quantity of smaller pores in the 20 nm and 6 nm range are also present. Results on the two week old samples show that after one week porosity remains constant but a slight increase is noticeable in the 9 nm diameter pores. This small increase is shown also in the total intrusion volume of mercury and the reduction in volume of median pore diameter.

In contrast to the week one and three, a significant pore reduction in the porosity is apparent in the fourth week (Khatib and Wild, 1996; Frias and Cabrera, 2000).

3.6 Electro Mechanical Impedance (EMI)

The PZT patches mounted in both samples exhibited uniform behaviour with hydration in the lime-metakaolin pastes tested. The real and imaginary components of the extracted mechanical impedance were found to exhibit a

response similar to that of a parallel spring damper (Kelvin-Voigt) combination (Bhalla and Soh, 2004; Soh and Bhalla, 2005) in the frequency range 70-120 kHz. The variation of spring stiffness, k and damping coefficient, c was monitored with progression of hydration. The system parameters k and c both showed a decrease with time with the exception of a small initial increase in the beginning. A typical response from one of the samples is shown in Figure 6. The variation of c is similar to that observed for concrete curing (Soh and Bhalla, 2005) however, k exhibited a somewhat opposite trend. More experiments are underway to verify the observation in this particular case. Nevertheless, there is no doubt that both parameters are sensitive to hydration of lime.

4. DISCUSSION

Results of thermal analysis suggest that samples contain a certain amount of water after three weeks and that negligible carbonation had taken place.

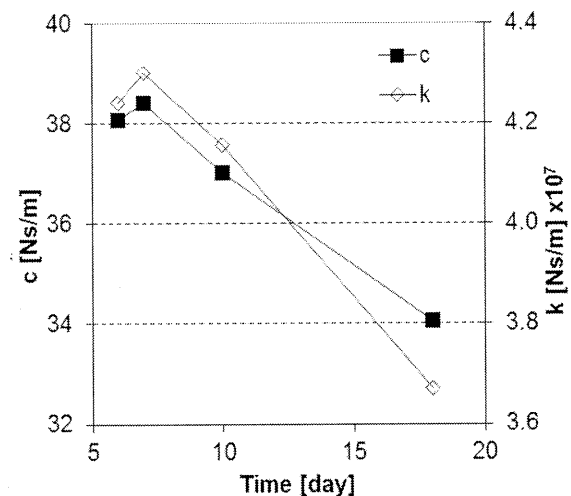


Figure 6. Variation in electromechanical impedance system parameters k and c as a function of hydration time.

This observation is also supported by the absence of angular calcium carbonate crystals in the SEM micrograph. Consequently, the only reaction that can be taken into consideration for the mechanical and physical properties of hardened samples is the hydration process of silica and alumina. Furthermore, according to previous research, thermal analysis suggests a specific sequence in the silica and aluminum hydrated compounds. By the end of the first week mainly the C-S-H, the stratingite and the hydrogarnet (C_4AH_{13}) are formed. As these compounds are not stable (Moropoulou *et al.*, 2004) they begin to transform into hydrogarnet (C_3ASH_6) over the longer term (Ball *et al.*, 2012). The noticeable difference from the thermal calorimetry, attributed to the degree of crystallisation in $Ca(OH)_2$ phases, may be a consequence of calcium hydroxide

recrystallization during the experiment. However, the constant proportion of calcium hydroxide detected in all of the samples suggests that all the calcium needed by the reaction with the metakaolin is acquired during the first week. Consequently, changes visible in the hydraulic phases are mainly due to the modifications of the hydraulic compounds developed during the first week, rather than formation of new phases. Results from the MIP support the theory that the recrystallisation and hydration reactions modify the pore size distribution and structure. These can also be attributed to the changes in the electrical response identified by impedance spectroscopy. A reduction in freely rotational water molecules associated with the formation of the hydraulic phases is consistent with the results. Changes in the mechanical properties of the mixes, attributable to hydration, were detected by the electro mechanical impedance technique.

5. CONCLUSIONS

This paper demonstrates the potential of impedance spectroscopy to study and monitor the reaction between lime and metakaolin. Changes of impedance response with time are believed to be associated with reaction kinetics. Impedance behaviour with time was consistent with results obtained from the complementary techniques. The EMI technique is sensitive to changes in extent of hydration in a lime-metakaolin paste. This study highlights the importance of impedance spectroscopy (both EIS and EMI) as potential tools for the non-destructive monitoring and evaluation of lime based hydraulic binders.

ACKNOWLEDGEMENTS

The authors would like to thank the UK India Education and Research Initiative (UKIERI project Reference No. UKUTP20110031) and the Engineering and Physical Sciences Research Council (EPSRC).

REFERENCES

- Aggelakopoulou, E., Bakolas, A., Moropoulou, A., 2011. Properties of lime-metakaolin for the restoration of historic masonry, *Applied Clay Science*, 53(1):15-19.
- Almond, D.P., Bowen, C.R., 2004. Anomalous power law dispersion in AC conductivity and permittivity shown to be characteristics of microstructural electrical networks, *Physical Review Letters*, 92(15):1-4.
- Bakolas, A., Aggelakopoulou, E., Moropoulou, A., Anagnostopoulou, S., 2006. Evaluation of pozzolanic activity and physico-mechanical characteristics in metakaolin-lime pastes, *Journal of Thermal Analysis and Calorimetry*, 84:157-163.
- Ball, R.J., Allen, G.C., 2010. The measurement of water transport in porous materials using impedance spectroscopy, *Journal of Physics D: Applied Physics*, 43:105503.
- Ball R. J., G. C. Allen, G. Starrs, W. J. McCarter, 2011. Impedance spectroscopy measurements to study physio-chemical processes in lime-based composites, *Applied Physics: A Materials Science and Processing*, 105:739-751.
- Ball, R.J., Pesce, G.L.A, Bowen, C.R., Allen, G.C., 2012. Characterisation of lime/metakaolin paste using Impedance Spectroscopy, *Key Engineering Materials*, 517:487-494.
- Bhalla, S., Gupta A. A Piezo-Composite Vibration Sensor for Monitoring Health of Concrete Structures, *Patent application 1011/Del/2011*.
- Bhalla, S., Soh, C.K., 2004. Structural Health Monitoring by Piezo-Impedance Transducers. I: Modelling, *Journal of Aerospace and Engineering*, October, 154-165.
- BS-EN 459-1, Building lime - Part 1: Definitions, specifications and conformity criteria, British Standard, (2001).
- Edwards, D. D., 2009, Sustainable Lime Mortars, thesis submitted to the University of Bristol for award of degree of Doctor of Philosophy at the Faculty of Science. Interface Analysis Centre.
- Frias, M., Cabrera, J., 2000. Pore size distribution and degree of hydration of metakaolin-cement paste, *Cement and Concrete Research*. 30:561-569.
- Frias Rojas, M., Sanchez de Rojas, M.I., 2001. The effect of high curing temperature on the reaction kinetics in MK/lime and MK-blended cement matrices at 60°C, *Cement and Concrete Research*, 33, 643-649.
- Khatib, J.M., Wild, S., 1996. Pore size distribution of metakaolin paste, *Cement and Concrete Research*, 26, 10, 1545-1553.
- McCarter, W. J., Garvin, S., Bouzid, N., 1998. Impedance measurements on cement pastes, *Journal of Material Science Letters*, 7:1056-1057.
- McCarter, W. J., Starrs, G., Chrisp, T.M., 2002. Electrical monitoring methods in cement science, Structure and Performance of Cements, SPON, London.
- Moropoulou, A., Bakolas, A., Aggelakopoulou, E., 2004. Evaluation of pozzolanic activity of natural and artificial pozzolans by thermal analysis, *Thermochimica Acta*, 420:135-140.
- Shin, S.W., Oh T.K., 2009. Application of electro-mechanical impedance sensing technique for online monitoring of strength development in concrete using smart PZT patches, *Construction and Building Materials*, 23(2):1185-1188.

Soh, C.K., Bhalla, S., 2005. Calibration of piezo-impedance transducers for strength prediction and damage assessment of concrete, *Smart Materials and Structures*, 14:671-684.

Tawie, R., Lee, H.K., 2010a. Piezoelectric-based non-destructive monitoring of hydration of reinforced concrete as an indicator of bond development at the steel-concrete interface, *Cement and Concrete Research*, 40:1697-1703.

Tawie, R., Lee, H.K., 2010b. Monitoring the strength development in concrete by EMI sensing technique, *Construction and Building Materials*, 24:1746-1753.

Tawie, R., Lee, H.K., 2011. Characterization of cement-based materials using a reusable piezoelectric impedance-based sensor, *Smart Materials and Structures*, 20:085023.