

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. S. Romanov, S. T. E. Jones, Q. Gu, P. Conaghan, B. Drummond, J. Feng, F. Chotard, L. Buizza, M. Foley, M. Linnolahti, D. Credgington and M. Bochmann, *Chem. Sci.*, 2019, DOI: 10.1039/C9SC04589A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Carbene Metal Amide Photoemitters: Tailoring Conformationally Flexible Amides for Full Color Range Emissions Including White-Emitting OLED

Alexander S. Romanov,^{*†} Saul T. E. Jones,[‡] Qinying Gu,[‡] Patrick J. Conaghan,[‡] Bluebell H. Drummond,[‡] Jiale Feng,[‡] Florian Chotard,[‡] Leonardo Buizza,[‡] Morgan Foley,[‡] Mikko Linnolahti,^{*§} Dan Credgington^{*‡} and Manfred Bochmann^{*†}

[†] School of Chemistry, University of East Anglia, Norwich Research Park, Norwich, NR4 7TJ, UK;

E-mail: A.Romanov@uea.ac.uk; m.bochmann@uea.ac.uk

[‡] Department of Physics, Cavendish Laboratory, Cambridge University, Cambridge CB3 0HF, UK;

E-mail: djnc3@cam.ac.uk

[§] Department of Chemistry, University of Eastern Finland, Joensuu Campus, FI-80101 Joensuu, Finland;

E-mail: mikko.linnolahti@uef.fi

ORCID:

A. S. Romanov: <https://orcid.org/0000-0003-2617-6402>

M. Bochmann: <https://orcid.org/0000-0001-7736-5428>

S. T. E. Jones <https://orcid.org/0000-0001-6007-2530>

D. Credgington <https://orcid.org/0000-0003-4246-2118>

M. Linnolahti <https://orcid.org/0000-0003-0056-2698>

B. H. Drummond <https://orcid.org/0000-0001-5940-8631>

P. J. Conaghan: <https://0000-0001-9199-5805>

F. Chotard: <https://0000-0002-4791-5270>

J. Feng: <https://0000-0002-4729-9404>

ABSTRACT:

Conformationally flexible “Carbene-Metal-Amide” (CMA) complexes of copper and gold have been developed based on a combination of sterically hindered cyclic (alkyl)(amino)carbene (CAAC) and 6- and 7-ring heterocyclic amide ligands. These complexes show photoemissions across the visible spectrum with PL quantum yields of up to 89% in solution and 83% in host-guest films. Single crystal X-ray diffraction and photoluminescence (PL) studies combined with



DFT calculations indicate the important role of ring structure and conformational flexibility of the amide ligands. Time-resolved PL shows efficient delayed emission with sub-microsecond to microsecond excited state lifetimes at room temperature, with radiative rates exceeding 10^6 s^{-1} . Yellow organic light-emitting diodes (OLEDs) based on a 7-ring gold amide were fabricated by thermal vapor deposition, while the sky-blue to warm-white mechanochromic behavior of the gold phenothiazin-5,5-dioxide complex enabled fabrication of the first CMA-based white light-emitting OLED.

■ INTRODUCTION

Two-coordinate coinage metal complexes with linear geometry (L)MX (L = carbene; M = Cu, Ag or Au; X = anionic ligand) have recently emerged as a new class of strongly photoemissive materials.¹⁻⁴ Their effectiveness is based on a combination of ligands with complementary donor and acceptor properties: on the one hand, a carbene ligand capable of acting as both a strong electron donor and effective π -acceptor, and, on the other hand, an anionic ligand X that on photochemical or electrical excitation enables charge transfer to the acceptor orbital of the carbene. Cyclic (alkyl)(amino)carbene (CAAC) ligands⁵⁻⁹ were found to be particularly suitable on the basis of their balance between donor and acceptor properties.¹⁰ CAAC complexes of copper,¹ silver¹¹ and gold^{1,7,12} are thermally very stable and resistant to ligand rearrangements. Even simple CAAC copper halide adducts give photoluminescence quantum yields (PLQY) as high as 96%.¹ Combining CAAC carbene ligands with anions X = arylamide and especially carbazolate proved a particularly effective design strategy for bright phosphors, to give “carbene-metal-amides” (CMAs). The incorporation of such CMA-type copper and gold complexes into the emissive layer of organic light-emitting diodes (OLEDs) enabled the construction of devices with near-100% internal and >25% external quantum efficiency (EQE) by both solution-processing and thermal vapor deposition techniques.^{13,14} OLEDs based on mononuclear silver complexes as emitters were obtained similarly.¹⁵


The emission mechanism of CMAs has been the subject of several theoretical and spectroscopic investigations.¹⁶⁻¹⁹ Theoretical calculations revealed that the highest occupied molecular orbital (HOMO) is located mostly on the carbazole, while the lowest unoccupied molecular orbital (LUMO) comprises mainly the C_{carbene} p-orbital.^{13,15} Excitation is a ligand-to-ligand charge transfer process (LLCT) from the carbazole to the carbene ligand involving mainly



a HOMO→LUMO transition, with only a minor ($\leq 5\%$ to HOMO, 7 – 15% to LUMO) contribution of the metal orbitals. For gold carbazolate complexes we reported earlier that inter-system crossing to triplets occurs within 4 ps after photoexcitation.¹³ The emission process from CMAs is associated with strong dipole moment changes between ground (μ_{gs}) and excited states (μ_{es}) (Scheme 1). This process differs therefore from that operative in most metal-based phosphors where metal-to-ligand charge transfer (MLCT) is dominant.²⁰⁻²⁸

The emissions from CMA complexes appear to follow predominantly a thermally activated delayed-fluorescence (TADF) mechanism. However, whereas the classical TADF process shows a characteristic blue-shift on warming,²¹⁻²⁴ CMAs display a temperature-dependent red-shift. Current models suggest that given the rotational flexibility of linear L-M-X complexes, intramolecular twisting of the carbene relative to the amide ligand planes affects both the ground and excited state energy levels. The exchange energy, ΔE_{ST} , is small and at high twist angles approaches zero.¹⁴⁻¹⁸ This enables efficient mixing of singlet and triplet excited states and results in short (sub-microsecond to microsecond) excited state lifetimes. Radiative rates exceeding 10^6 s⁻¹ and near unity PLQY values have been realized.¹³⁻¹⁵ The principle of carbene-metal-amide photoemitters has recently been extended to dendritic systems²⁹ and to a range of related carbazolate-based CMA systems.³⁰⁻³²



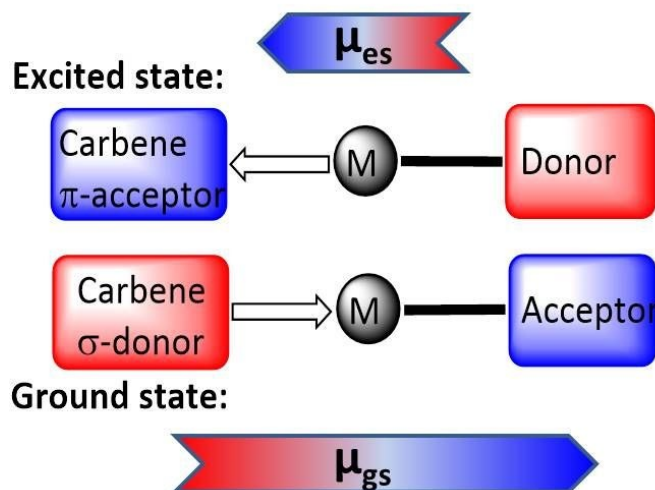

$$S_1 \text{ and } T_1 \text{ mixing} \propto H_{SO}/\Delta E_{ST}$$

- Flexible geometry for $\Delta E_{ST} \approx 0$
- Cu or Au for high spin-orbit coupling H_{SO}

Scheme 1. Principle of the CMA structure in the ground and excited states, with arrows indicating direction of molecular ground state (μ_{gs}) and excited state dipoles (μ_{es}).

Whereas the studies so far have concentrated on the carbazole ligands, where the amide N-atom is locked into a rigid 5-membered ring, we report here a series of CMA complexes carrying amide ligands based on various phenoxazine, phenothiazine, di- and tribenzazepine and sulfone derivatives in which the N-atoms are part of conformationally flexible 6- or 7-membered rings. The electron-donor capacity of these amido ligands varies significantly, so that the luminescence wavelengths can be tuned to cover the visible spectrum from blue to deep red.³³ We report the use of these emitters in OLEDs, including the first case of a device based on a mechanochromic CMA material, an application enabled by the conformational flexibility of the amide ligand.


■ RESULTS AND DISCUSSION

Synthesis and structure

Copper and gold CMA complexes of adamantyl-substituted CAAC ligands (^{Ad}L) were prepared in high yields as shown in Scheme 2, following previously established procedures.^{2,12,13} The color of the complexes in the solid state or in solutions varies significantly and depends on



the donor strength of the amide ligand (colorless **Au1**, yellow **Au2–Au4**, orange **Au5**, red **Au6** and deep-purple **Au7/Au8**; the copper analogues show very similar colors). The complexes possess good solubility in aromatic and polar non-protic solvents like dichloromethane, THF, and acetone, and moderate solubility in acetonitrile. Gold CMA complexes are stable in air for several months and indefinitely stable under argon. The stability of the copper complexes is reduced to several hours in air as the electron donor strength of the amide ligand increases. According to thermogravimetric analysis (TGA, under nitrogen) the decomposition temperature (T_d) for gold complexes is 15–30 °C higher than for copper compounds (see SI, Figure S1). In the series of gold complexes **Au1–Au8** thermal stability decreases with increasing electron donor properties of the amide ligand, for instance, T_d is 322 °C for **Au1** vs 250 °C for **Au8**.

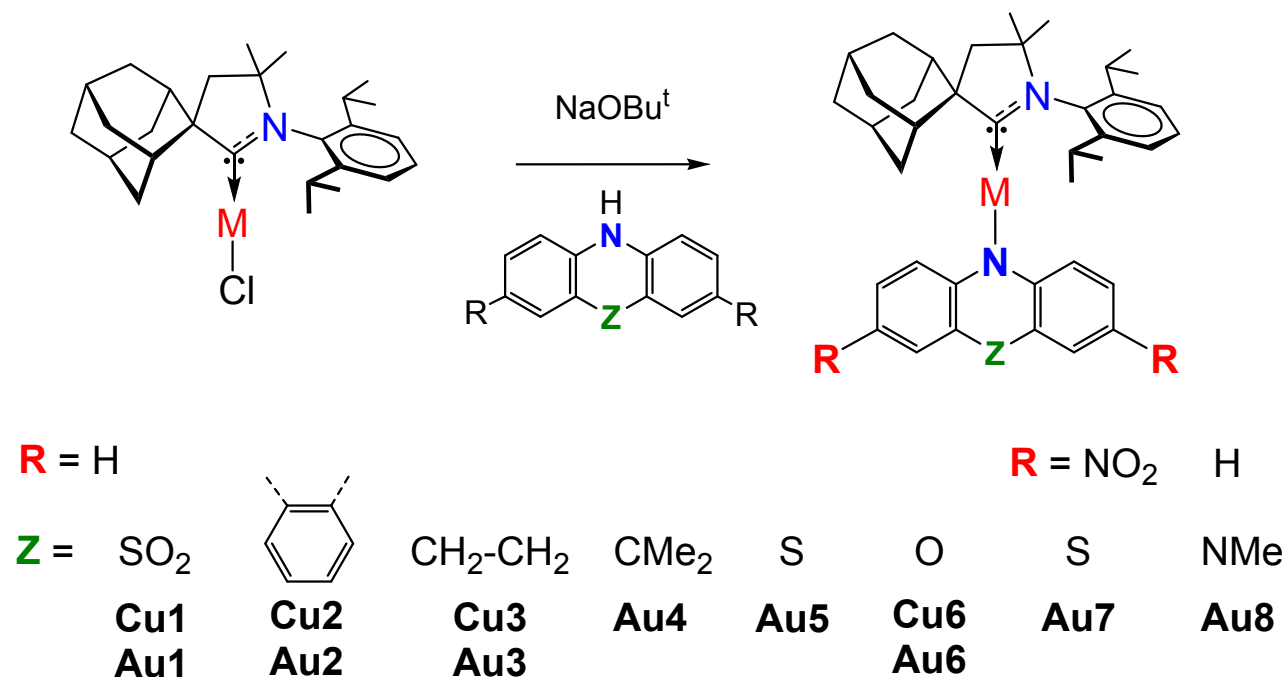

Scheme 2. Synthesis and structures of carbene metal amide complexes.

Crystals of the copper and gold complexes suitable for X-ray diffraction were obtained by layering of CH₂Cl₂ or toluene solutions with hexane. Key structural parameters for the crystal structures are defined in Figure 1 and collected in Table 1. The crystal structures are shown in Figure S2 (see SI).



6

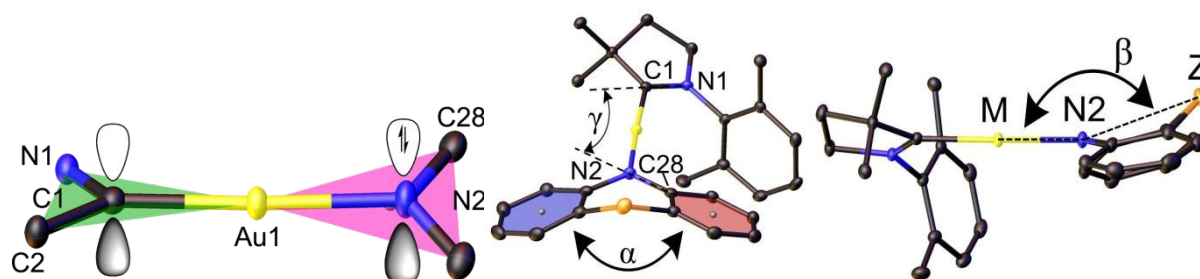


Figure 1. Structural definitions of the dihedral (butterfly) angle α between the two best planes of the aromatic 6-rings and deviation of the bridgehead (Z) from the linear CMA unit, angle β .



Table 1. Selected bond lengths [\AA] and angles [$^\circ$] of copper and gold amide complexes. The values for the monoclinic form of **Au1** are the average for the two independent molecules in the unit cell.

	M–C1, \AA	M–N2, \AA	C1 \cdots N2, \AA	angle, $^\circ$ C1–M–N2	torsion angle, $^\circ$ N1–C1–N2–C28	N2 deviation from M1 \cdots C28 \cdots C39, \AA	angles, $^\circ$ α/β
Au1	1.994(6)	2.055(5)	4.049(6)	176.5(2)	17.4(5)	0.037(6)	154.5(1)/153.7(2)
Au2	1.973(3)	2.015(2)	3.988(3)	172.4(1)	23.3(2)	0.074(3)	124.3(1)/138.0(1)
Au4	1.984(4)	2.053(3)	4.037(4)	178.73(14)	16.6(5)	0.005(4)	174.8(1)/173.6(1)
Au5	1.983(2)	2.043(2)	4.026(2)	177.05(8)	12.9(4)	0.098(2)	144.8(2)/160.3(1)
Au6	1.989(6)	2.033(6)	4.021(6)	176.5(3)	21.1(4)	0.070(7)	167.6(2)/160.5(3)
Au7	1.992(3)	2.055(3)	4.047(3)	173.6(1)	17.3(3)	0.052(3)	162.1(2)/152.5(1)
Au8	1.991(3)	2.032(3)	4.022(6)	177.2(1)	15.6(3)	0.003(3)	161.7(1)/159.1(1)

All compounds are monomeric, with the molecules arranged into three-dimensional networks by weak C–H \cdots X hydrogen bonds (X = Cl, O, N, and S). There are no close metal-metal contacts. Complexes with six-membered amide ligands (**Au1**, **Au4–Au8**) exhibit C(1)_{CAAC}–Au bond lengths that are very similar to the carbazolate complex (^{Ad}CAAC)Au(carbazolate) (**CMA1**), while the Au–N(2) bond lengths are longer by 0.01–0.03 Å (Table 1). The carbene-carbon C(1) lies in the N(1)–Au–C(2) plane for all complexes. The amide N-atom N(2) can tend towards a pyramidal geometry (deviation from the M1 \cdots C28 \cdots C39 plane), as found in phenothiazine-based **Au1**, **Au5**, **Au7**, and in the oxazine **Au6** complexes (Figure S1).

Complex **Au2**, which bears a seven-membered amide, shows both C(1)_{CAAC}–Au and Au–N(2) bond lengths shorter by 0.01 Å than **CMA1**. Such deviations in bond lengths lead to the C(1)_{CAAC} \cdots N(2) distance being longer for six-membered amide complexes (0.01–0.04 Å) and shorter by 0.03 Å for **Au2** compared with **CMA1** (4.117 Å, see Table 1). The shortest C(1)_{CAAC} \cdots N(2) distance for complex **Au2** is accompanied by significant deviation from linear geometry around gold atom and shows the smallest C(1)–Au–N(2) angle (172.4(1)°) in the gold series. The distance between donor and acceptor (C1 \cdots N2) plays an important role in the charge transfer step and, together with the carbene/amide twist angle, can be used as a molecular design tool to control the HOMO–LUMO overlap.

The six- and seven-membered amide ligands in **Au1** to **Au8** are non-planar (“butterfly” conformation) and conformationally flexible. To evaluate the deviations from planarity we introduce the folding angle α as the angle between best planes through the two benzo-rings of the amide ligand (Figure 1). The angle β is defined as the angle between the M–N(2) vector and Z, where Z is a bridgehead or the centroid of the C34–C39 bond of **Au2**, see Fig. 1. Complex **Au4** exhibits the largest angle α and displays an almost planar geometry of the amide ligand (Z = CMe₂). A bent geometry with smaller α angles (154–167°) has been found for Z = S, SO₂, NMe (Table 1), while the smallest values of α and β are found for **Au2** due to the sterically demanding *o*-phenylene bridge.

Crystals of **Au1** were obtained in two forms, a monoclinic and an orthorhombic phase. Monoclinic crystals were grown by layering a dichloromethane solution with hexane and are obtained as the solvate, **Au1**·0.5CH₂Cl₂. They contain two independent **Au1** molecules in the unit cell, which differ by 10° in the β angle, indicating the flexibility of the sulfone bridge in six-



membered amide *vs.* the rigid five membered carbazolate ligand in **CMA1** (Figure S3). Layering a toluene solution of **Au1** with hexane leads to a solvent-free orthorhombic phase which exhibits a more flattened conformation of the amide ligand ($\alpha/\beta = 159.7(3)/164.6(6)^\circ$ for the orthorhombic *vs.* $154.5(1)/153.7(2)^\circ$ for the monoclinic form, Table 1). These structural variations appear to exercise a strong influence on the photo- and electroluminescence properties of **Au1** (*vide infra*). Unfortunately, systematic twinning prevents a detailed discussion of bond lengths and angles of the orthorhombic **Au1** complex.

Electrochemistry

Cyclic voltammetry (CV) was used to analyze the redox behavior of the new copper and gold complexes in MeCN solution, using [ⁿBu₄N]PF₆ as the supporting electrolyte (Table S1, and SI, Figures S4–S10). All gold complexes show a quasi-reversible, carbene ligand-centered reduction process similar to our previous reports.^{2,13,29} The peak-to-peak separation ΔE_p varies within a small range of 77–91 mV for gold complexes; this is higher than the expected value of 59 mV for a theoretical reversible one-electron process. The oxazine complex **Cu6** shows quasi-reversible reduction with a peak-to-peak separation ΔE_p of 79 mV, whereas other copper complexes **Cu1–Cu3** showed irreversible reduction processes. The lowest reduction potential was found for **M1** (M = Cu and Au) and **Au7** due to the strongly electron-withdrawing nature of the SO₂ and NO₂ groups, which results in a stabilization of the LUMO by 0.2 eV for **M1** and 1 eV for **Au7**, respectively (Figure 2). Unlike **M1** and **Au7**, the reduction potentials of all other complexes are largely insensitive to the nature of the amide ligands and show very similar LUMO energy levels (Table S1, Figure 2). Such a marked difference in a first reduction potential for complex **Au7** indicates that it is likely localized on the amide ligand rather than on the carbene (see Fig. S9 in SI).

The copper and gold complexes **Cu1–Cu3** and **Au1–Au4** undergo multiple irreversible amide ligand-centered oxidation processes at all scan rates. The phenothiazine-based (**Au5** and **Au7**), oxazine (**Cu6** and **Au6**) and N-methylphenazine (**Au8**) show multiple and quasi-reversible oxidation waves with a well-defined back-peak (see SI, Figures S5 and S6). The first quasi-reversible oxidation process shows a peak-to-peak separation ΔE_p in the range 66–84 mV for copper and gold compounds, whereas larger variations in ΔE_p values (59–106 mV) were observed for the second or third quasi-reversible processes (Table S1). The quasi-reversibility of



the reduction and oxidation peaks is witnessed by a small shift of 10–20 mV in the peak position E_p on increasing the scan rate and the peak-to-peak separation ΔE_p of 77–91 mV (at 100 mV/s), which is close to the ideal value of 59 mV for a one-electron reversible couple. For instance, complex **Au1** shows an increase of the i_{pa}/i_{pc} ratio for the reduction process from 0.74 (at 0.05 Vs^{-1}) towards unity (0.85 at 2 Vs^{-1}) which is the ideal value for a reversible couple (Fig. S5, see SI for a varied scan rate study for gold and copper complexes showing quasi-reversible redox processes).

On the basis of the electrochemistry data of the free amine ligands³⁴ and theoretical calculations all oxidation waves can be assigned to amide-centered processes. The band gap value (ΔE , eV see Table S1) decreases in the series **Au1**–**Au8** from 2.93 eV for **Au1** to 1.64 V for **Au8** as a result of the decrease in the first oxidation potential and destabilization of the HOMO energy from –5.85 eV for **Au1** to –4.56 eV for **Au8**.³⁵ Such trends are in line with the increasing electron-donor strength of the amide ligand. The exception is complex **Au7** which shows a small band gap value of 1.9 eV since in this case both reduction and oxidation processes are centered on the amide ligand, as can be seen by comparison with the free amine ligand 10-H-3,7-dinitrophenothiazine (Fig. S9 in SI).

Computational results

The electronic structure of copper and gold complexes was investigated by density-functional theory (DFT) for the ground state and time-dependent DFT (TD-DFT)³⁶ calculations for the excited states, using the MN15 functional by Truhlar³⁷ in combination with def2-TZVP basis set by Ahlrichs.^{38–40} For complexes where X = SO₂, or S (R = NO₂) the optimized structures for the S₁ and T₁ excited states show twist angles between CAAC carbene and amide ligand planes of only 20°. Excitation of the molecules is accompanied by a flattening of the six- or seven-amide ligands; the α/β angles are larger by 5–10° compared with the ground state geometries determined by X-ray diffraction.

The LUMO is aligned along the metal–carbene bond, whereas the HOMO is localized on the amide ligand. The contribution of the metal orbitals is \approx 3–5% for the HOMO and 7–16% for the LUMO (SI, Table S3). The calculated HOMO-LUMO energy gaps are consistent the values obtained by electrochemistry for copper and gold complexes (Figure 2 and Table S4). The



charge transfer process is predominantly HOMO→LUMO in character (>96%). The copper and gold complexes are characterized by small exchange energies ΔE_{ST} of <0.3 eV (Table S5).

All molecules possess a high ground state dipole moment (μ_{gs}) in the range of 8–17 D (see SI, Table S6) oriented along the metal- C_{carbene} vector. The dipole moments in the excited states (μ_{es}) is reduced to 1–4 D and in most cases changes direction, commensurate with significant charge transfer from the amide to the carbene ligand.

The exception to this is **Au7** where an intraligand HOMO→LUMO+1 charge transfer (ILCT) process for the amide ligand dominates, while the contribution by the HOMO(amide)→LUMO(carbene) transition is low (see SI, Table S5). **Au7** possesses the highest oscillator strength ($f = 0.2634$) and by far the largest exchange energy ΔE_{ST} of >0.5 eV, indicative of a potential competing mechanism of ligand-based fluorescence. In agreement with this analysis, **Au7** shows no change in dipole moment since the $S_0 \rightarrow S_1$ transition is localized on the amide ligand. Evidently, the nitro substituents outcompete the carbene as π -acceptors and stabilize local excited states.



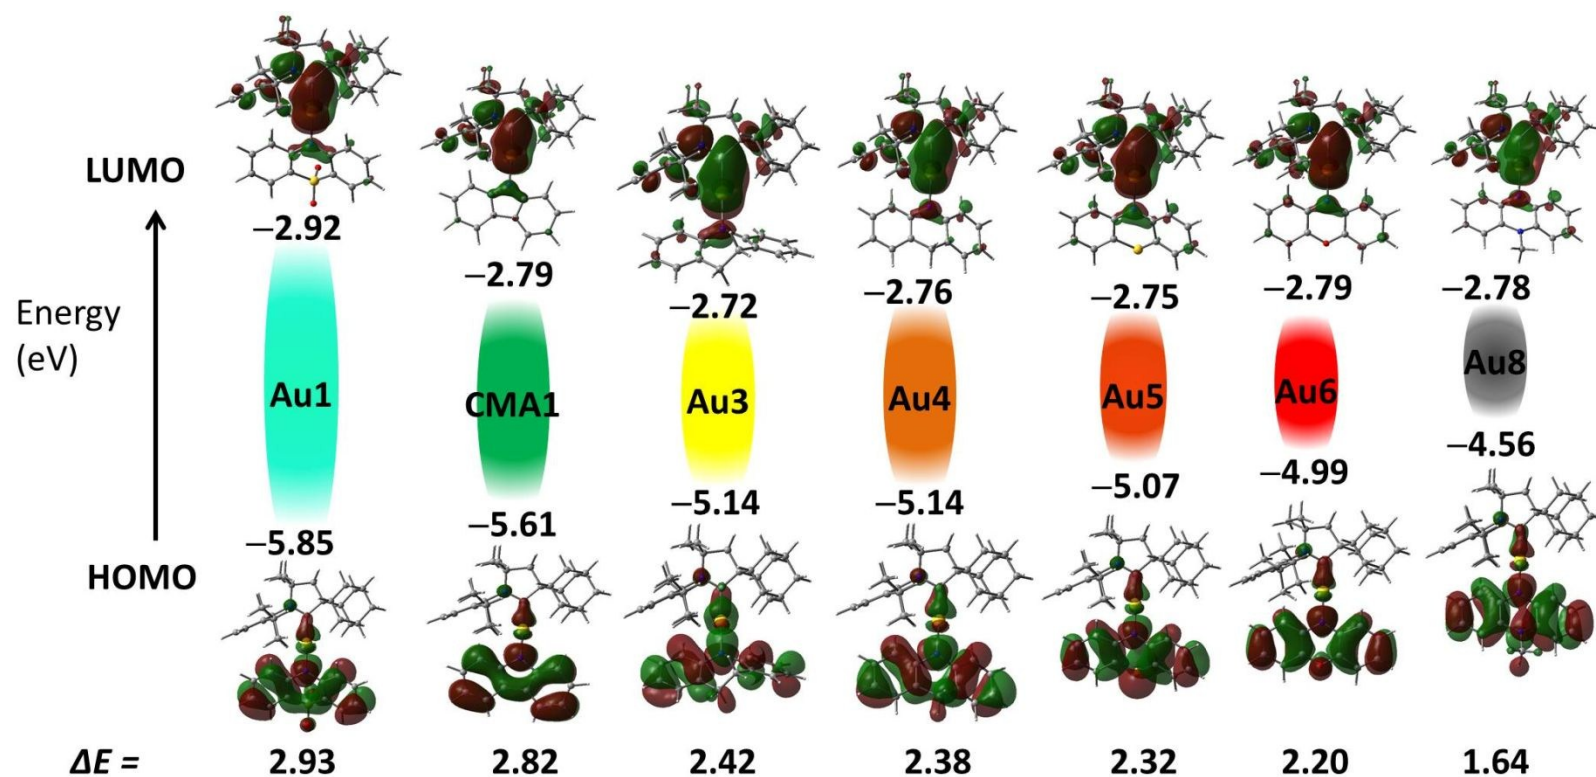


Figure 2. Shapes and energies of HOMOs and LUMOs involved in the vertical excitation ($S_0 \rightarrow S_1$) of gold complexes **Au1** – **Au8**, in comparison with the carbazolate complex **CMA1**.¹³ The E_{HOMO}/E_{LUMO} (eV) and band gap values (ΔE , eV) were obtained by cyclic voltammetry.



Photophysical properties.

The UV/vis absorption spectra for copper and gold complexes in THF solution (Figure 3 and S11) show strong $\pi\text{-}\pi^*$ transitions at ca. 270 nm ascribed to an intra-ligand (IL) transition of the CAAC carbene. The broad low energy absorption band for copper and gold complexes from ca. 380 to 560 nm is assigned to ligand-to-ligand charge transfer L(M)LCT $\{\pi(\text{carbazole})\text{-}\pi^*(\text{CAAC})\}$, with a minor contribution of the metal orbitals according to the DFT calculations. The absorption onset of the CT band and peak position shows a red-shift of over 9600 cm^{-1} (ca. 175 nm) for the gold series of complexes; this trend follows the increase in electron-donor character of the amide ligands and is largely consistent with the decrease in the band gap values (ΔE , Table S1) identified by cyclic voltammetry (*vide supra*). The molar extinction coefficients of the copper complexes are 2–3 times lower than those of their gold analogues, in line with the theoretically calculated trend in oscillator strength (see SI Table S5). The molar extinction coefficients (ϵ) of the L(M)LCT for gold complexes decrease from $\epsilon = 7800$ for **Au2** to $2500\text{ M}^{-1}\text{ cm}^{-1}$ for **Au8** in THF solution. **Au7** is the exception and shows the highest value of $\epsilon = 10,260\text{ M}^{-1}\text{ cm}^{-1}$ due to the dominant contribution of the amide IL $\pi\text{-}\pi^*$ transition.



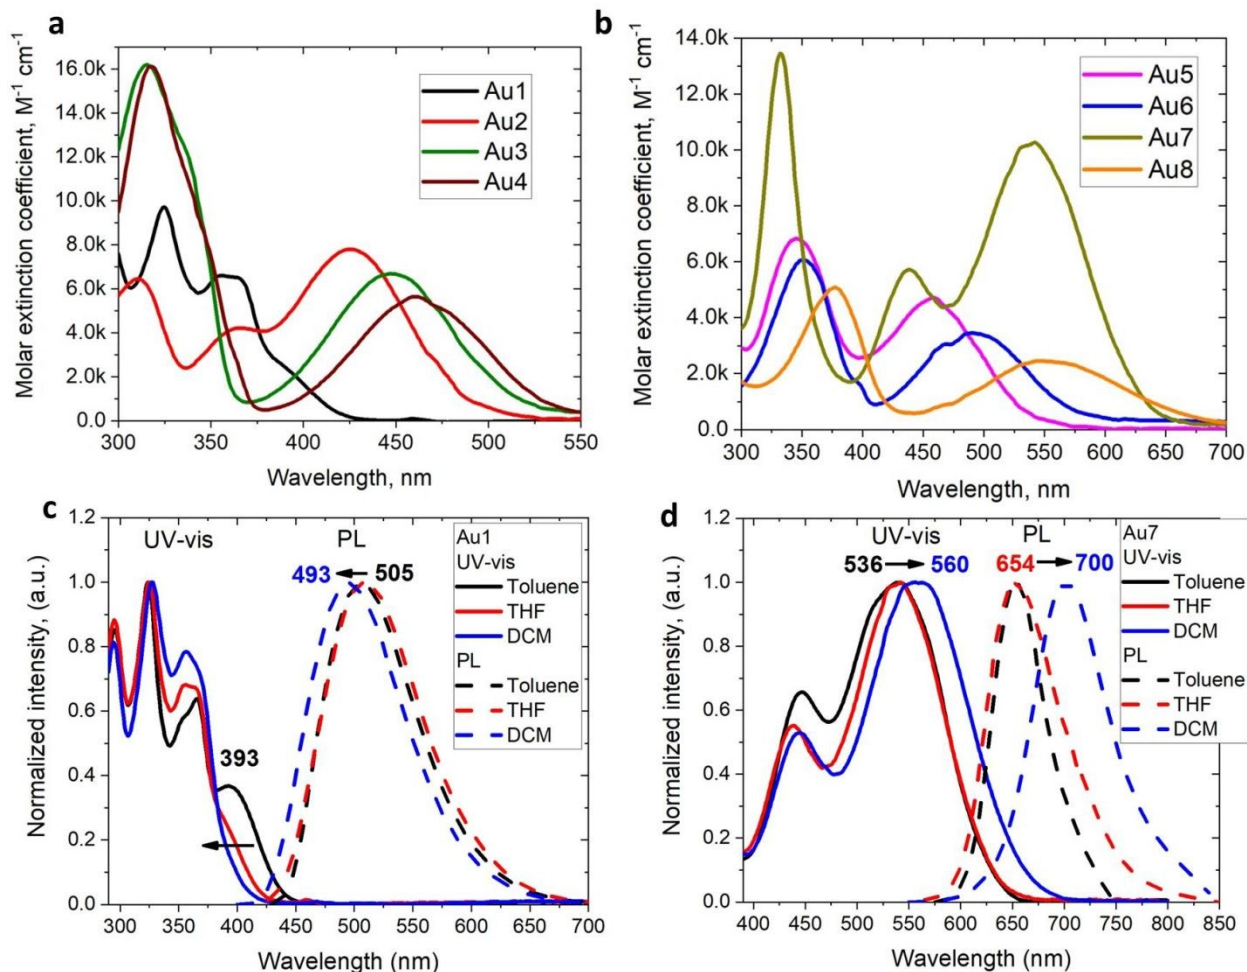


Figure 3. UV/vis spectra of gold **Au1-Au4** (a) and **Au5-Au8** (b) complexes in THF solution (298 K). Normalized UV-vis and emission spectra in toluene, THF and CH₂Cl₂ for gold complex **Au1** (c) and **Au7** (d) showing negative and positive solvatochromism, respectively.

The photoluminescence (PL) properties of copper and gold complexes were investigated in toluene solution at 298 K, in frozen 2-methyltetrahydrofuran (MeTHF) at 77 K, as a 5 weight-% dopant in a polystyrene (PS) matrix, and as neat films under N₂ (Figure 4; see Figure S11 and 13 for copper complexes). The PL data are summarized in Table 2. The complexes exhibit broad intramolecular charge transfer emission profiles with FWHM (full-width half-maximum) values of 65–120 nm. The emission colors range from sky-blue to deep-red/near-IR. In a polystyrene matrix, where molecular flexibility is restricted, emissions are slightly blue-shifted relative to the PL in toluene solution, and in the series of gold complexes **Au1** – **Au7** the PL quantum yields (PLQYs) decrease from 83 to 8% as the wavelength increases. The luminescence of all



complexes is reversibly quenched by O₂. The emission profiles red-shift following the band gap values (ΔE , Table S1), e.g. for the gold complexes in the sequence from **Au1** to **Au8**. The basicity of the amine can be correlated with the emission properties of the CMA materials. For instance, the flexible amine ligand 10H-phenothiazine 5,5-dioxide ($pK_a = 15.7$),⁴¹ which incorporates a strongly electron-withdrawing linker ($Z = \text{SO}_2$), reduces the basicity compared with carbazole ($pK_a = 19.9$), resulting in sky-blue luminescence for **Au1** vs green for **CMA1**. On the other hand, more basic amines with $Z = \text{o-phenylene}$ ($pK_a = 26.1$), ethylene ($pK_a = 25.5$), S ($pK_a = 22.7$) or O ($pK_a = 21.6$)⁴¹ produce either yellow or orange/red emitters **Au2–Au6** and **Au8**. However, since there is a complicated simultaneous interplay between the structural and electronic factors, the emission colours cannot be predicted solely on the amine basicity. For instance, the amines used for complexes **Au2–Au4** have similar pK_a values but the emission profile red-shifts by ca. 10–20 nm from yellow (**Au2**) to yellow-orange (**Au3**) to orange (**Au4**). This can be rationalized by difference in amide geometry, where the rigid linker $Z = \text{o-phenylene}$ (**Au2**) leads to the most acute butterfly angles (α/β), whereas **Au4** shows an almost flat amide ligand (α/β ca. 180°). The same trend is clear when linkers Z are heteroatoms with comparable rigidity: yellow-orange **Au5** ($Z = \text{S}$) show a butterfly angle α which is 20° more acute than in orange-red **Au6** ($Z = \text{O}$). If $Z = \text{NMe}$ this trend can be extended into the near-IR range, as in complex **Au8**.

The 3,7-dinitrophenothiazine compound **Au7** is an exception in the series: the LUMO contains a significant contribution of the amide ligand, while the LUMO+1 is entirely located on the amide ligand (see ESI, Tables S2 and S4). As a result excitation of **Au7** leads to intra-ligand HOMO \rightarrow LUMO+1 transition without flipping of the transition dipole moment value (Table S6). This is supported by positive solvatochromic behavior in the UV-vis and photoluminescence spectra in solvents of different polarities (see Fig. 3). **Au7** differs therefore markedly from the other gold complexes (see Fig. 3 for **Au1** and Fig S15 for **Au2–Au4**) which show a negative solvatochromism due to the flipping of the transition dipole moments between ground and excited states (Table S6).



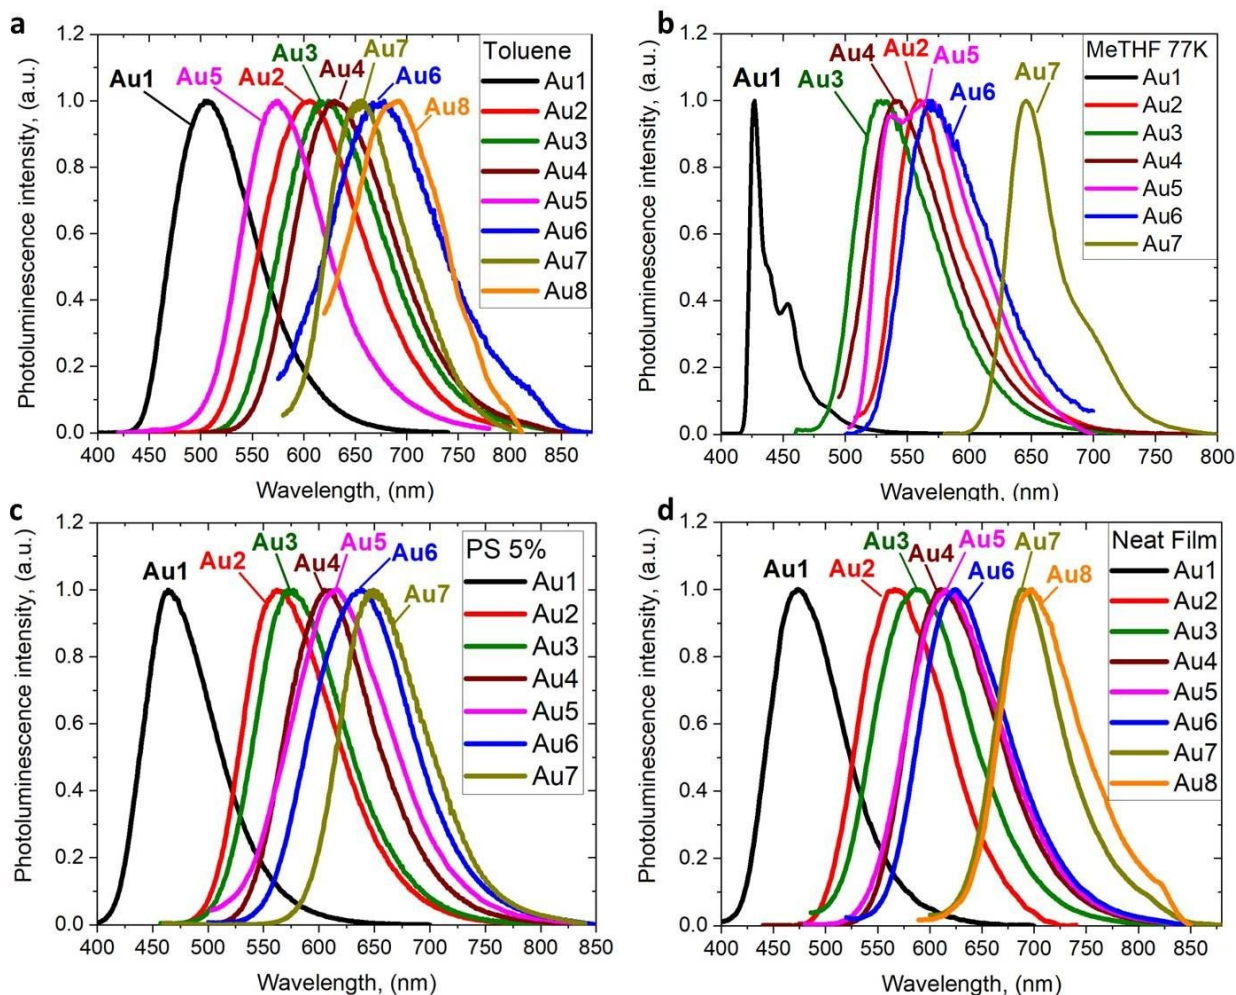


Figure 4. PL spectra of gold CMA complexes **Au1–Au8** in toluene solution at 298 K (a), in MeTHF at 77 K (b), as a 5wt-% dopant in polystyrene (c), and as neat films under N_2 (d).

The emission spectra were measured in frozen 2-MeTHF solution to identify the energy of the local excited triplet 3LE state. All complexes exhibit a significant blue-shift upon cooling to 77K (Fig 4b). Complexes **Au1** and **Au1** show well-structured emission profiles originating from the 3LE state of the amide ligand. Complexes **M2–M6** (M = Cu, Au) show only blue-shifted broad CT emissions (see Fig. 4b) upon cooling, which preclude identification of the 3LE energy and the $\Delta E(^1CT-^3LE)$ energy gap values. A similar behavior has recently been reported for copper carbazolate complexes with mono- and diamidocarbene ligands.³¹ Unlike **M1–M6**, the emission profile for **Au7** is not shifted upon cooling MeTHF solution from 298 to 77K and gives a similar peak maximum at 649 nm, with a narrower emission profile at 77K and a shoulder at the lower wavelength (Fig. 4).



The PLQY values decrease generally from **M1** to **M8** in all media, with a few exceptions. For instance, in PS matrix complexes **Au3** has a higher PLQY than **Au2**, whereas in toluene solution the PLQY of **Au3** is one order lower than that of **Au2**. The excited state lifetimes of **Au2** are 2–4 times shorter than for **Au3**. This behavior is likely a reflection of the relative rigidity of the tribenzoazepine ligand ($Z = o$ -phenylene) compared with the rather flexible 10,11-dihydrobenzazepine ring ($Z =$ ethylene, *vide supra*). The gold complexes **Au1**–**Au6** show short excited state lifetimes of the order of 0.2 – 2.8 μs in PS and 0.1 – 0.7 μs in toluene at 298K, leading to radiative rate constants k_r of $10^4 - 10^6 \text{ s}^{-1}$. The non radiative rate constants k_{nr} increase up to 40 times from **M1** to **M4/6** in line with the decreasing band gaps, which is consistent with the energy gap law.⁴²

Copper complexes are generally less emissive than their gold analogues, with the highest PLQY being displayed by **Cu1** (49.5% in toluene). The lower PLQY values for the copper complexes correlates well with the lower oscillator strength coefficients for $S_1 \rightarrow S_0$ transition and smaller contribution of the metal orbitals into LUMO compared with the analogous gold complexes (see SI, Tables S3 and S5). The copper analogues show excited state lifetime values that are up to three times longer than for the gold analogs (Table 2). The differences due to ligand rigidity are even more pronounced: **Cu3** is almost non-emissive (PLQY 2%) with flexible ethylene bridge, while the emission of **Cu2** is 18 times more intense due to rigid *o*-phenylene bridge.

The decay kinetics for complexes **M1** on cooling from 298 to 77 K show an increase in excited state lifetimes of three orders of magnitude in the solid state, e.g. from 3.3 μs to 9.4 ms for **Cu1** (Figure 5), suggesting that PL at room temperature is due to a thermally activated process. Unlike the behavior in solution, the PL profiles of solid samples of **Cu1** and **Au1** at 77K show a marginal blue-shift with unresolved vibronic structure, indicative of a mixed PL from both 1CT and 3LE states. In agreement with this, the data are best fitted by a biexponential model. Time-resolved emission spectroscopy and applying a delay of 800 μs confirmed the presence of a 3LE emission with characteristic vibronic structure from the sulfone ligand (see for example Fig. 5c).

To get insight into the activation parameters for flexible amide complexes, we have measured the temperature-dependent transient PL for the bright complex **Au3** in neat films. All PL transients show non-exponential kinetics over two distinct time regimes – nanosecond (I) and



microsecond (II) as shown on Fig. 5d. The nanosecond regime (I) exhibits no significant T dependence, with a lifetime of *ca.* 3 ns limited by instrument response. Spectral deconvolution allowed extraction of the emission profile for the prompt fluorescence, which is blue-shifted compared to the delayed emission at later times (Figure 5e). The estimated energy of the prompt fluorescence is in excess of 2.57 eV. The microsecond regime (II) shows unstructured and thermally activated luminescence with an activation energy of 94 meV (Figure S12). The excited state lifetime increases significantly on cooling, from $\tau_{II} = 800$ ns at 300 K to 52 μ s below 100 K. We measured photoluminescence intensity as a function of temperature to determine the nature of the thermally activated emission process for complex **Au3** and discriminate *vs.* rigidity effects which could also lead to longer excited state lifetime at low temperature. The photoluminescence intensity increases upon warming from 100 to 300 K (Fig. 5f) thus indicating that it's primarily the radiative rate that is thermally activated and increases with temperature. We observe a red-shift of the delayed emission upon warming for **Au3** (Figure 5f), which is similar to the behavior of the rigid carbazolate systems.^{15,29} The delayed regime dominates the total emission at room temperature, and even on cooling to below 100K the phosphorescence spectrum could not be resolved. This prevents identification of the ³LE energy level even after applying long delay up to 200 μ s. Similar behavior has been noted before for other carbene metal amides.^{15,29,31}

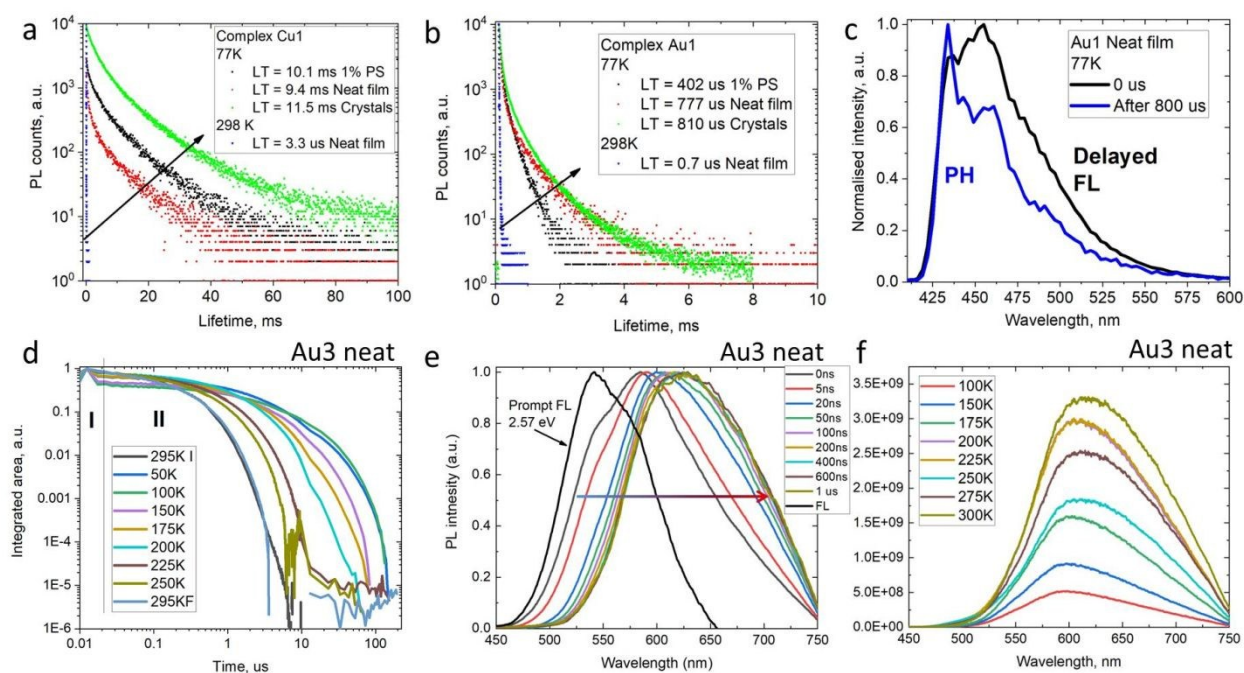


Figure 5. Emission decay kinetics for complexes **Cu1** (a) and **Au1** (b) at 298 and 77K in the solid state with values for the slow decay; (c) Transient emission photoluminescence for **Au1** as neat film (excitation at 380 nm); (d) Temperature-dependent time-resolved PL for **Au3** as neat film. (e) Prompt (0-1 ns) and delayed (up to 1 μ s delay) emission spectra at 295 K; (f) Varied-temperature PL of **Au3** in a neat film in microsecond regime (**II**).

Mechanochromic properties.

CMA complexes bearing rigid carbazolate ligands are known for their triboluminescence and mechanochromic photoluminescence.^{2,15} This behavior may be expected to be even more pronounced in complexes with flexible amide ligands. Indeed, **Au1** shows a mechanochromic response due to its ability to crystallize in two different modifications (*vide supra*): Monoclinic crystals show a bright featureless sky-blue emission at 475 nm, whereas the orthorhombic form emits warm-white light with a maximum at 540 nm accompanied by a minor peak at 475 nm (30% PLQY) (Figure 6). Both modifications differ slightly in the folding angle of the amide ligand; the behavior of **Au1** is therefore likely the result of the different ground state geometries associated with a different angles α/β , as shown in Figure 6. The orthorhombic crystals are very fragile and emit sky-blue light if broken, which explains the origin of the high-energy peak in the warm-white emission profile. Grinding the orthorhombic crystals leads to a hypsochromic shift of 0.32 eV and the disappearance of the broad low energy emission, while the new sky-blue emission almost overlaps with the PL of the monoclinic form. The additional emission at 475 nm for the orthorhombic crystals is therefore due to the mechanoresponsive behavior of this structure. The mechanoresponse of **Au1** is irreversible, that is the warm-white emission can only be obtained after recrystallization, and the effect is therefore most probably due to crystal packing. The switch between the stable blue CT and metastable warm white emission can however be exploited for the fabrication of white emissive OLEDs (*vide infra*).



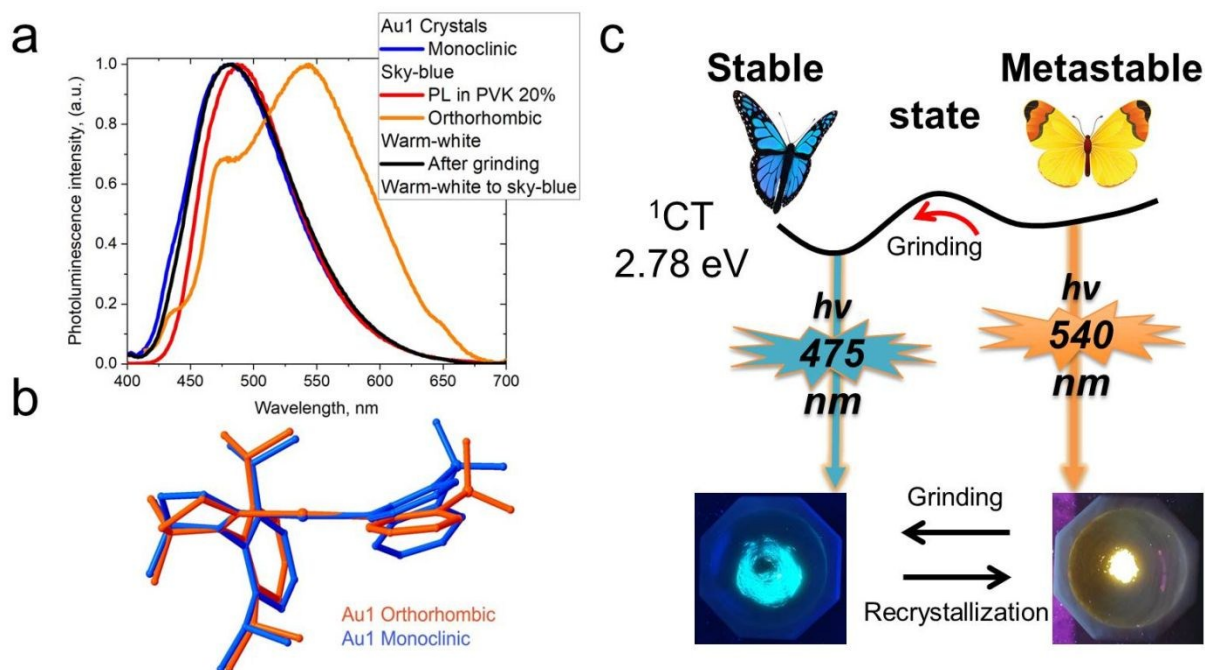


Figure 6. a) Solid-state PL of crystals of **Au1** in the monoclinic and orthorhombic phases; b) superposition of the geometries of the **Au1** phases determined by single crystal X-ray diffraction; c) Schematic diagram for the interconversion between stable sky-blue (monoclinic) and warm-white (orthorhombic) emissive forms.





Table 2. Photophysical properties of copper and gold complexes as neat films, in toluene solution and in polystyrene (PS) matrix at 5 weight-%.

	λ_{em} (nm)	τ (μ s)	Φ (%, N ₂) ^b	k_r (10 ⁵ s ⁻¹) ^c	k_{nr} (10 ⁵ s ⁻¹)	FWHM (nm)	¹ CT/ ³ LE (eV) ^e
Toluene							
Cu1	489	1.13	49.5	4.3	4.4	87	2.85/2.92
Au1	505	0.74	89.6	12.1	1.4	94	2.78/2.95
Cu2	589	0.58	19.5	3.3	13.8	109	2.44/–
Au2	603	0.15	20	13.3	53.3	114	2.38/–
Cu3	607	0.43	3.0	0.07	23.1	111	2.37/–
Au3	620	0.19	1.7	0.9	51.7	114	2.31/–
Au4	629	0.14	2	1.4	70.0	112	2.25/–
Au5	574, 665	0.27	0.4	0.14	36.8	96	2.45/–
Cu6	661	0.11	–	–	–	121	2.16/–
Au6	672	0.25	1	0.4	39.6	126	2.20/–
Au7	654	0.025; 0.6	8	–	–	91	2.08/–
Au8	689	0.04	<0.1	–	–	109	2.11/–
Neat film^a							
Cu1	469	3.3	6.5	0.2	2.8	86	
Au1	473	0.71	24.9	3.5	10.5	82	
Cu2	524	1.37	26.2	1.9	5.3	101	
Au2	566	0.21	11.7	5.5	42.0	98	
Cu3	484	1.6	0.1	0.001	6.2	120	

22

Au3	587	0.8	6.4	0.8	11.7	107
Au4	610	0.27	8.1	3.0	34.0	99
Au5	616	2.75	8.6	0.3	3.3	106
Cu6	611	–	–	–	–	99
Au6	624	0.37	–	–	–	98
Au7	690	–	–	–	–	74
Au8	696	–	–	–	–	90

5% PS matrix ^a

Cu1	458	8.52	25.6	0.3	0.8	76
Au1	464	0.87	65.5	7.5	3.9	75
Cu2	528	3.60	36.8	1.0	1.7	114
Au2	563	0.61	39.7	6.5	9.8	95
Cu3	490	4.1	1.7	0.04	2.3	100
Au3	574	1.5	50	3.3	3.3	93
Au4	607	0.15	32.7	21.8	44.8	93
Au5	615	2.82	29.6	1.0	2.5	104
Cu6	614	–	–	–	–	95
Au6	637	0.77	17.2	2.2	10.7	105
Au7	649	2.2	8.5	–	–	90
Au8	–	–	–	–	–	–





^a Films (neat and in PS host) were prepared by drop-casting from chlorobenzene solutions (10mg/mL) onto a hot quartz substrate and annealed for 5 min; ^b Quantum yields determined using an integrating sphere; ^c radiative rate constant $k_r = \Phi / \tau$, ^c Nonradiative constant $k_{nr} = (1 - \Phi) / \tau$. ^d In case of two-component lifetime τ an average was used: $\tau_{av} = (B_1 / (B_1 + B_2))\tau_1 + (B_2 / (B_1 + B_2))\tau_2$, where B_1 and B_2 are the relative amplitudes for τ_1 and τ_2 , respectively; ^e ¹CT and ³LE energy levels based on the onset values of the emission spectra blue edge in MeTHF glasses at 77 K and in toluene solutions at 298 K.

Electroluminescent (EL) Properties.

Vapor-deposited OLEDs incorporating **Au3** as emitter were fabricated with the architecture shown in Figure 7. OLEDs with 20 wt-% dopant in 1,3-bis(9-carbazolyl)benzene (mCP) show EL peaks at $\lambda_{em} = 590$ nm (Figure 7), while the EL spectra closely match the microsecond-regime PL spectra. Figure 7 shows the current density-voltage and luminance-voltage characteristics of evaporated devices. External quantum efficiencies (EQEs) (for **Au3** of 9.8% at 100 cd/m² and 9.1% at 1000 cd/m²) were achieved, with low roll-off characteristics. The low turn-on voltage of only 2.6 V indicates a good charge balance in OLED device (Table 3).

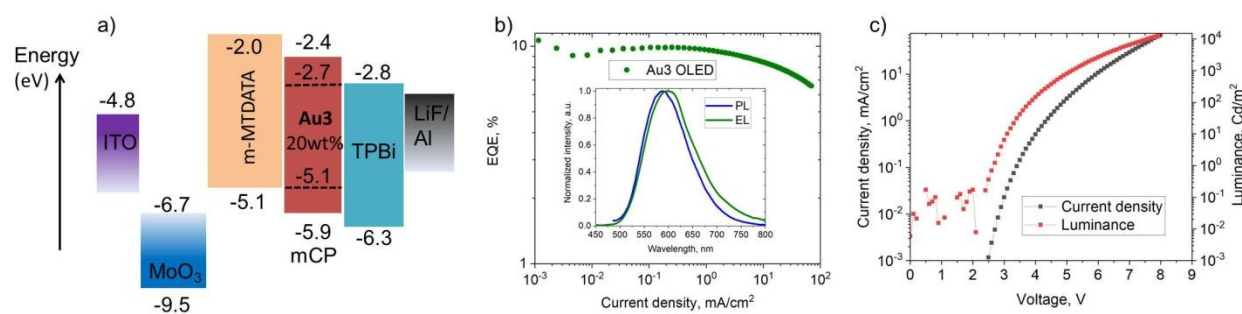


Figure 7. a) Vapour-deposited OLED device architecture based on **Au3**; b) external quantum efficiencies vs. current density of champion OLEDs with inset showing the electroluminescence (EL) and PL spectra; c) current density/luminance vs. voltage curve of champion OLEDs.

Complex **Au1** proved insufficiently stable for thermal vapor deposition but suitable for the fabrication of solution-processed OLEDs, with the device architecture ITO/PEDOT:PSS (40 nm)/ TFB (10 nm)/ PVK or CBP with 20%wt **Au1** (40 nm)/ TPBi (70 nm)/ LiF (0.8 nm)/ Al (100 nm). The OLED glowed initially sky-blue, but in the PVK host the emission quickly (<1 s) broadened and changed to warm-white EL. This transition is likely connected with existence of the two conformational isomers isolated in the crystals of **Au1**, *vide supra* (Figure 6). The initial sky-blue EL is tentatively attributed to an emission from the monoclinic form, while the final warm-white EL largely agrees with the averaged PL profiles of the monoclinic and orthorhombic forms (Figure 8). This explanation was further supported by a second set of **Au1** OLEDs in CBP as host, where the EL profile largely coincides with the warm-white PL of the orthorhombic **Au1** form. The devices produced peak EQEs of 5.8% and 4.6% for **Au1** in PVK and CBP hosts, respectively. This is almost the maximum that can be achieved considering the 30% PLQY value for the warm-white orthorhombic form and 39% PLQY value in 20% PVK (Figure 8).



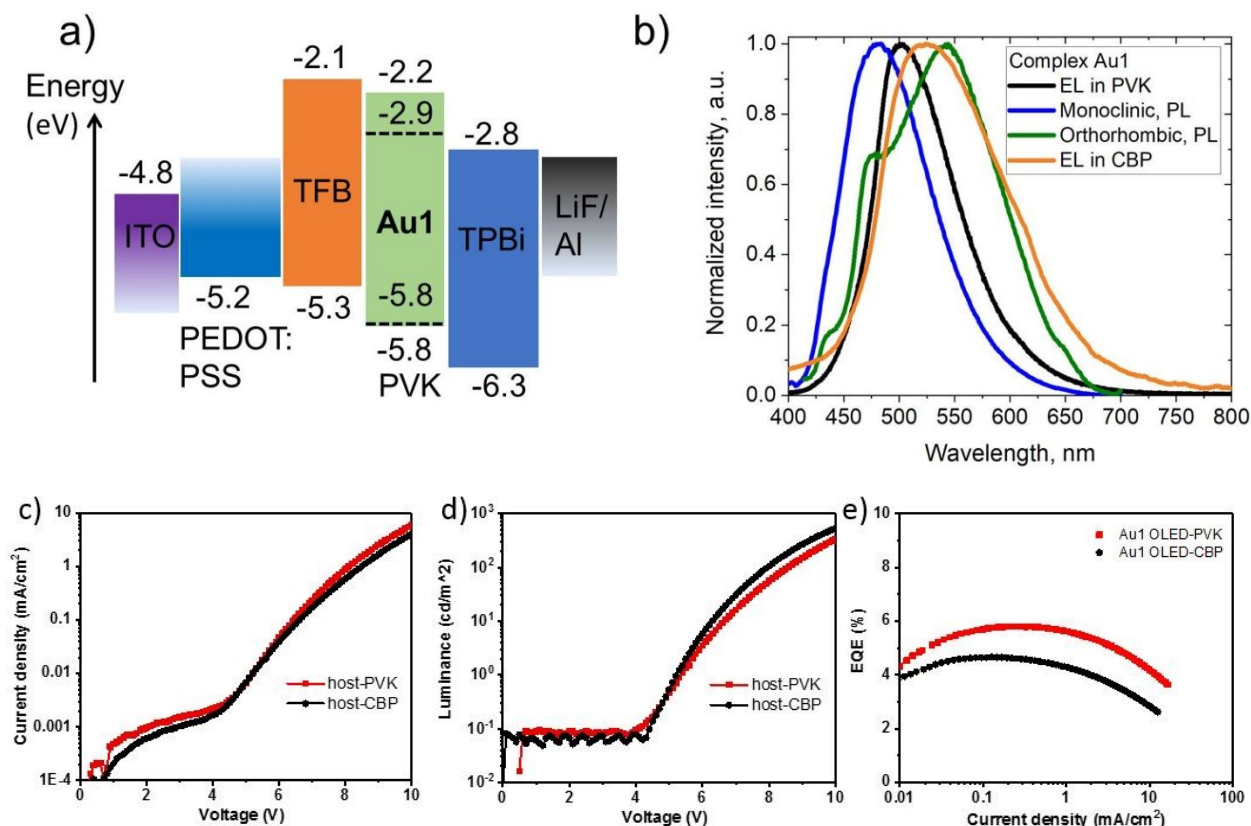


Figure 8. (a) Solution-processed **Au1**-based OLED architectures based on 20 wt.% doped PVK as the emissive layer (EML); (b) Photoluminescence (PL) and electroluminescence (EL) spectra of different conformers and matrices; (c) Current-voltage characteristics and (d) luminance-voltage characteristics for **Au1**-OLED; (e) External quantum efficiencies vs. current density.

Table 3. Performance data of solution and evaporated OLEDs.

Dopant [wt.%]/ Method	V_{ON} [V] ^b	$\eta_{EQE,EL}$ [%] (Max.)	$\eta_{EQE,EL}$ [%] (100 cdm^{-2})	$\eta_{EQE,EL}$ [%] (1000 cdm^{-2})	CIE ^a (x,y)
Au1 [20] Solution, PVK	5.4	5.8	5.5	3.6	(0.15, 0.24)
Au1 [20] Solution, CBP	5.3	4.6	4.2	2.3	(0.18, 0.31)
Au3 [20] Evaporated, mCP	2.6	11.0	9.8	9.1	(0.53, 0.46)

^a Commission Internationale de l'Éclairage (CIE) color co-ordinates; ^b V_{ON} determined at a luminance of 1 cd/m^2

■ CONCLUSION



Carbene Metal Amide (CMA) complexes of copper and gold of the type (L)M-N(C₆H₄)₂Z, where Z = O, S, NMe, CMe₂, SO₂, C₂H₄ or *o*-C₆H₄ provide a range of photoemissive complexes in which the HOMO-LUMO gap is determined by the electronic characteristics of Z, to give photoluminescence ranging from blue to deep red. The amide-N atoms are part of non-planar, flexible 6- and 7-membered heterocycles (“butterfly” conformation). These conformational changes influence the emission behavior. Similar to previously reported CMA compounds with rigid carbazole ligands,^{13-15,29-32} the complexes described here emit predominantly via a thermally activated emission process with sub-microsecond to microsecond excited state lifetimes at room temperature, with radiative rates exceeding 10⁶ s⁻¹. Nitro-substituents on the amide ligands, on the other hand, quench L(M)LCT processes and luminesce. On cooling to 77K the emissions are blue-shifted and excited state lifetimes increase by three orders of magnitude. **M1** (M = Cu and Au) complexes emit *via* both delayed fluorescence and phosphorescence at 77K whereas **Au3** shows predominantly delayed fluorescence. The magnitude of *k*_{nr} increases across the gold and copper series in line with the emission wavelengths, which is consistent with the energy gap law. Proof-of-concept OLEDs were fabricated by thermal vapor deposition, with EQEs of up to 9.8% at 100 cd/m² for a yellow emitter based on the **Au3** complex with the 7-ring amide ligand. The gold complex **Au1** can adopt two conformations which show either blue or warm-white PL; this behavior was exploited in a solution-processed OLED based on **Au1** to provide the first example of a CMA-based white-emitting OLED. Conformational flexibility can therefore be employed as a useful design feature to tailor the emission energies and increase the range of readily accessible CMA materials for light-emitting applications.

■ ASSOCIATED CONTENT

*S Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1039/XXXXXX.

CCDC number 1912300 for **Au1** (Monoclinic), 1912299 for **Au2**, 1911240 for **Au4**, 1911241 for **Au5**, 1911239 for **Au6**, 1911237 for **Au7**, 1911238 for **Au8** contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif. Detailed



experimental procedures, single-crystal X-ray diffraction data, photophysical and OLED device characterization, and computational details.

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

This work was supported by the European Research Council, the Royal Society and the Academy of Finland. M. B. is an ERC Advanced Investigator Award holder (grant no. 338944-GOCAT). D.C. acknowledges support from the Royal Society (grant nos. UF130278 and RG140472). A.S.R. acknowledges support from the Royal Society (grant nos. URF\R1\180288 and RGF\EA\181008). This work was supported by the EPSRC Cambridge NanoDTC, EP/L015978/1. The computations were made possible by use of the Finnish Grid and Cloud Infrastructure resources (urn:nbn:fi:research-infras-2016072533). J.F. acknowledges his parents for financial support on his Ph.D.

■ REFERENCES

- (1) A. S. Romanov, D. Di, L. Yang, J. Fernandez-Cestau, C. R. Becker, C. E. James, B. Zhu, M. Linnolahti, D. Credgington and M. Bochmann, *Chem. Commun.* **2016**, 52, 6379 – 6382 and *Chem. Commun.*, **2018**, 54, 3672.
- (2) A. S. Romanov, C. R. Becker, C. E. James, D. Di, D. Credgington, M. Linnolahti and M. Bochmann, *Chem.-Eur. J.* **2017**, 23 (19), 4625-4637.
- (3) M. Gernert, U. Meller, M. Haehnel, J. Pflaum and A. Steffen, *Chem. Eur. J.* **2017**, 23, 2206 – 2216.
- (4) S. Shi, L. R. Collins, M. F. Mahon, P. Djurovich, M. E. Thompson and M. K. Whittlesey, *Dalton Trans.* **2017**, 46, 745-752.
- (5) V. Lavallo, Y. Canac, C. Prasang, B. Donnadieu and G. Bertrand, *Angew. Chem. Int. Ed.* **2005**, 44, 5705-5709.
- (6) V. Lavallo, Y. Canac, A. DeHope, B. Donnadieu and G. Bertrand, *Angew. Chem. Int. Ed.* **2005**, 44, 7236-7239.
- (7) G. D. Frey, R. D. Dewhurst, S. Kousar, B. Donnadieu and G. Bertrand, *J. Organomet. Chem.* **2008**, 693, 1674-1682.



- (8) M. Soleilhavoup and G. Bertrand, *Acc. Chem. Res.* **2015**, *48*, 256–266.
- (9) M. Melaimi, R. Jazzar, M. Soleilhavoup and G. Bertrand, *Angew. Chem. Int. Ed.* **2017**, *56*, 10046 – 10068.
- (10) O. Back, M. Henry-Ellinger, C. D. Martin, D. Martin and G. Bertrand, *Angew. Chem. Int. Ed.* **2013**, *52*, 2939–2943.
- (11) A. S. Romanov and M. Bochmann, *J. Organomet. Chem.* **2017**, *847*, 114–120.
- (12) A. S. Romanov and M. Bochmann, *Organometallics* **2015**, *34*, 2439–2454.
- (13) D. Di, A. S. Romanov, L. Yang, J. M. Richter, J. P. H. Rivett, S. Jones, T. H. Thomas, M. A. Jalebi, R. H. Friend, M. Linnolahti, M. Bochmann and D. Credgington, *Science* **2017**, *356*, 159–163.
- (14) P. J. Conaghan, S. M. Menke, A. S. Romanov, A. J. Pearson, E. W. Evans, M. Bochmann, N. C. Greenham and D. Credgington, *Adv. Mater.* **2018**, *30*, 1802285.
- (15) A. S. Romanov, S. T. E. Jones, L. Yang, P. J. Conaghan, D. Di, M. Linnolahti, D. Credgington and M. Bochmann, *Adv. Optical Mater.* **2018**, *6*, 1801347.
- (16) J. Föllner and C. M. Marian, *J. Phys. Chem. Lett.* **2017**, *8*, 5643–5647.
- (17) E. J. Taffet, Y. Olivier, F. Lam, D. Beljonne and G. D. Scholes, *J. Phys. Chem. Lett.* **2018**, *9*, 1620–1626.
- (18) S. Thompson, J. Eng and T. J. Penfold, *J. Chem. Phys.* **2018**, *149*, 014304.
- (19) C. R. Hall, A. S. Romanov, M. Bochmann and S. R. Meech, *J. Phys. Chem. Lett.* **2018**, *9*, 5873–5876.
- (20) *Highly Efficient OLEDs - Materials Based on Thermally Activated Delayed Fluorescence*. H. Yersin (ed.), Wiley-VCH, Weinheim, 2019. ISBN: 978-3-527-33900-6.
- (21) H. Yersin, R. Czerwieniec, M. Z. Shafikov, A. F. Suleymanova, *ChemPhysChem* **2017**, *18*, 3508–3535.
- (22) M. J. Leidl, D. M. Zink, A. Schinabeck, T. Baumann, D. Volz and H. Yersin, *Top. Curr. Chem.* **2016**, *374*, 25.
- (23) C. Bizzarri, E. Spuling, D. M. Knoll, D. Volz and S. Bräse, *Coord. Chem. Rev.* **2018**, *373*, 49–82.
- (24) H. Yersin, A. F. Rausch, R. Czerwieniec, T. Hofbeck and T. Fischer, *Coord. Chem. Rev.* **2011**, *255*, 2622–2652.
- (25) *Iridium(III) in Optoelectronic and Photonics Applications*, E. Zysman-Colman (ed.), Wiley, New York, 2017. ISBN: 9781119007135.
- (26) T.-Y. Li, J. Wu, Z.-G. Wu, Y.-X. Zheng, J.-L. Zuo and Y. Pan, *Coord. Chem. Rev.* **2018**, *374*, 55–92.
- (27) C. Bizzarri, F. Hundemer, J. Busch and S. Bräse, *Polyhedron* **2018**, *140*, 51–66.
- (28) M.-C. Tang, A. K.-W. Chan, M.-Y. Chan, V. W.-W. Yam, *Top. Curr. Chem.* **2016**, *374*, 46.



- (29) A. S. Romanov, L. Yang, S. E. T. Jones, D. Di, O. J. Morley, B. H. Drummond, A. P. Reponen, M. Linnolahti, D. Credgington and M. Bochmann, M., *Chem. Mater.* **2019**, *31*, 3613–3623.
- (30) R. Hamze, J. L. Peltier, D. Sylvinson, M. Jung, J. Cardenas, R. Haiges, M. Soleilhavoup, R. Jazzar, P. I. Djurovich, G. Bertrand and M. E. Thompson, *Science* **2019**, *363*, 601–606.
- (31) S. Shi, M. C. Jung, C. Coburn, A. Tadle, M. R. D. Sylvinson, P. I. Djurovich, S. R. Forrest and M. E. Thompson, *J. Am. Chem. Soc.* **2019**, *141*, 3576–3588.
- (32) R. Hamze, S. Shi, S. C. Kapper, D. S. M. Ravinson, L. Estergreen, M.-C. Jung, A. C. Tadle, R. Haiges, P. I. Djurovich, J. L. Peltier, R. Jazzar, G. Bertrand, S. E. Bradforth and M. E. Thompson, *J. Am. Chem. Soc.* **2019**, *141*, 8616–8626.
- (33) For a preliminary report on color-tuning based on 6-ring amide CMAs see M. Bochmann, A. S. Romanov, D. J. N. Credgington, D. Di and L. Yang. PCT Internat. Pat. Applic. WO2017/046572 A1 (9.9.2016, to University of East Anglia and Cambridge Enterprises Ltd).
<https://register.epo.org/application?number=EPI6766064&tab=main>
- (34) K. Mielech-Lukasiewicz, H. Puzanowska-Tarasiewicz and A. Panuszko, *Analyt. Lett.* **2008**, *41*, 789–805.
- (35) H. Zollinger, *Color Chemistry*, 3rd ed.; Wiley-VCH: Zurich, 2001; p 550.
- (36) F. Furche and D. Rappoport, in: *Computational Photochemistry*; M. Olivuccim (ed.), Elsevier: Amsterdam, 2005, pp. 93–128.
- (37) H. S. Yu, X. He, S. L. Li, and D. G. Truhlar, *Chem. Sci.* **2016**, *7*, 5032–5051.
- (38) F. Weigend, M. Häser, H. Patzelt and R. Ahlrichs, *Chem. Phys. Lett.* **1998**, *294*, 143–152.
- (39) F. Weigend and R. Ahlrichs, *Phys. Chem. Chem. Phys.* **2005**, *7*, 3297–3305.
- (40) D. Andrae, U. Haeussermann, M. Dolg, H. Stoll and H. Preuss, *Theor. Chim. Acta* **1990**, *77*, 123–141.
- (41) V. M. Vlasov and I. A. Os'kina, *Russ. J. Org. Chem.*, **2002**, *38(12)*, 1705–1718. Translated from *Zh. Org. Khim.*, **2002**, *38(12)*, 1767–1780.
- (42) J. V. Caspar and T. J. Meyer, *J. Phys. Chem.* **1983**, *87(6)*, 952–957.



TABLE OF CONTENTS ENTRY

Conformationally flexible “Carbene-Metal-Amide” (CMA) complexes of copper and gold show photoemissions across the visible spectrum, including mechanochromic behavior which led to the first CMA-based white light-emitting OLED.

