

UNIVERSITY OF BIRMINGHAM

University of Birmingham
Research at Birmingham

Viscoelastic response of carbon fibre reinforced polymer during push-out tests

Corujeira Gallo, Santiago; Li, Xiaoying; Zhang, Zhenxue; Charitidis, Constantinos; Dong, Hanshan

DOI:

[10.1016/j.compositesa.2018.06.003](https://doi.org/10.1016/j.compositesa.2018.06.003)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

Document Version

Peer reviewed version

Citation for published version (Harvard):

Corujeira Gallo, S, Li, X, Zhang, Z, Charitidis, C & Dong, H 2018, 'Viscoelastic response of carbon fibre reinforced polymer during push-out tests', *Composites Part A: Applied Science and Manufacturing*, vol. 112, pp. 178-185. <https://doi.org/10.1016/j.compositesa.2018.06.003>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

Checked for eligibility: 13/09/2018

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

1 **Viscoelastic response of carbon fibre reinforced polymer during push-out tests**

2
3 Santiago CORUJEIRA GALLO ^a, Xiaoying LI ^a, Zhenxue ZHANG ^a, Constantinos
4
5 CHARITIDIS ^b and Hanshan DONG ^a
6
7

8
9
10 ^a University of Birmingham, School of Metallurgy and Materials

11
12 Edgbaston, Birmingham, B15 2TT, United Kingdom.
13
14
15

16
17
18 ^b School of Chemical Engineering, National Technical University of Athens

19
20 Iroon Polytechniou 9, Zografou 157 80, Greece.
21
22
23

24
25 *Corresponding author: S. Corujeira Gallo
26

27
28 Phone: +

29
30 E-mail: corujeis@bham.ac.uk
31
32
33
34

35 **Abstract**

36
37 Push-out is one of the available techniques to assess the bond strength between
38 the reinforcing fibres and the matrix in composite materials. The test is conducted on
39 thin sections of composite, and a small indenter is used to apply increasing load on
40 single fibres while measuring the displacement, until the debonding occurs. This study
41 used push-out tests to assess the debonding mechanism of carbon fibres in an epoxy
42 matrix. The tests were conducted at multiple loading rates (0.1 mN/s, 1 mN/s and 10
43 mN/s) and temperatures (24°C and 125°C). The results were analysed and contrasted
44 with scanning electron microscopy and atomic force microscopy observations. The data
45 showed evidence of push-out events and provided new insights into the contribution of
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 the viscoelastic behaviour of the fibre/matrix interface and/or the matrix. This finding
2
3 could pave new pathways for improving the bond strength between the carbon fibres
4
5 and the matrix in composite materials.
6
7
8
9

10 **Keywords:** Carbon fibres (A); Polymer-matrix composites (A); Debonding (B); Creep
11
12 (D)
13
14
15
16
17

18 **1. Introduction**

19

20 Carbon fibre reinforced polymers are composed of two phases: the carbon fibres,
21
22 which provide strength and stiffness, and the polymeric matrix, which holds the
23
24 reinforcing fibres in place and distributes the load among individual fibres [1]. The
25
26 interfacial strength (IFS) between carbon fibres and polymeric matrices has important
27
28 implications for the mechanical properties of composite materials [2, 3]. In spite of the
29
30 extensive research efforts, the appropriate assessment of the IFS and its link to the
31
32 macroscopic properties of composites remains challenging. Several testing methods
33
34 have been developed to assess the IFS [4], including: micro-bond [5], pull-out [6, 7] or
35
36 push-out tests [8, 9], fragmentation tests [10, 11] and Raman spectroscopy
37
38 measurements of specimens under stress [12]. Even though each of these methods can
39
40 be used to effectively rank the IFS, the results obtained by different methods are not
41
42 directly comparable [13]. Moreover, it is difficult to link the microscopic test results
43
44 with the macroscopic properties of composites. The inconsistencies are frequently
45
46 attributed to the different stress states developed in microscopic and macroscopic
47
48 conditions [13].
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 In addition, there is no general agreement on the operating interfacial failure
2 modes. Several models have been proposed with this regard, mainly based on stress and
3 energy failure criteria [9, 14]. However, the limitations of both approaches have been
4 discussed by several authors [15, 16], which could be attributed to the different load-
5 displacement responses of ceramic-matrix and polymer-matrix composites. Clearly,
6 further advance in scientific understanding of the debonding mechanism is important to
7 improve the IFS and to predict the behaviour of composites materials in real operating
8 environments. In this article, the results of push-out tests, conducted at multiple loading
9 rates and temperatures, are presented and discussed. The micro-mechanical tests were
10 supported by microscopic observations to identify the debonding mechanisms.

27 **2. Materials and Methods**

28 *2.1. Sample preparation*

29 The samples used for the tests were extracted from a rod of Toray Rebar S12
30 unidirectional composite, consisting of T700 carbon fibres in an epoxy matrix (Table 1).
31 Discs, 700 μm thick (Figure 1), were extracted from the rod of Rebar S12 using a
32 Struers Accutom 5 precision cut-off machine, fitted with an Al_2O_3 abrasive disc and
33 applying abundant cooling fluid. At least 300 μm of material were removed from each
34 side of the discs by wet grinding with #1200 SiC abrasive paper. Finally, both sides of
35 the discs were ground with #2500 and #4000 SiC abrasive paper and polished for 10
36 minutes with colloidal silica suspension. In their final condition, the discs had a
37 thickness between 20 μm and 40 μm , which reduces the load needed for the push-out to
38 occur. The samples for the tests were cut from these discs using a sharp scalpel and
39 stored in glass vials under room conditions (20°C and 50% relative humidity).

1 The glass transition temperature (T_g) of the Rebar S12A was determined using a
2
3 Mettler Toledo DSC 1 Star calorimeter. Small samples, approximately 14.5 mg in
4
5 weight, were placed in aluminium pans and heated from room temperature (24°C) to
6
7 250°C at a rate of 20°C/min in a nitrogen atmosphere, and subsequently cooled down to
8
9 room temperature (Figure 2). The first curve obtained in this way was discarded, and the
10
11 glass transition temperature was determined from the second run, as recommended in
12
13 Ref. [17].
14
15

16 2.2. Push-out tests

17
18 The tests were conducted in a Micro Materials Vantage nanoindentation
19
20 instrument, fitted with a Berkovich tip and a hot stage. A custom-made holder was
21
22 manufactured, having 60 μm wide slots produced by electro discharge machining
23
24 (EDM), where the fibres could be pushed out (Figure 3). The samples were fixed onto
25
26 the holder using cyanoacrylate adhesive. Individual fibres were selected at random,
27
28 using an optical microscope with a magnification of 400X. The positioning accuracy of
29
30 the stage was in the order of 0.5 μm and it was re-calibrated every 8 to 12 tests. The
31
32 instrument was operated in the displacement-control mode (through a feedback loop
33
34 with the load) and the loading conditions are listed in Table 2, which consisted of two
35
36 loading cycles. The first loading cycle was interrupted when the displacement reached
37
38 1 μm , which was expected to be close to producing a push-out event, but not sufficient
39
40 for the Berkovich indenter to contact the surrounding fibres. The load held for 5 s
41
42 (dwell time at maximum load), and then gradually removed for the fibre and the sample
43
44 to recover elastically. The second loading cycle was conducted until the displacement
45
46 reached 2 μm or the load reached 200 mN (whichever condition was reached first). This
47
48 cycle was expected to reveal information about the friction between the debonded
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 sections of the carbon fibre and the surrounding matrix, as well as to complete the crack
2
3 propagation thus resulting in a push-out event [15].
4

5
6 During the push-out tests, the temperature of the sample was controlled using a K-
7
8 type thermocouple embedded in the hot stage of the nano-indentation instrument. The
9
10 samples were heated up to the target temperature of 125°C, above the T_g of the material,
11
12 at a rate of 1.6°C/min; the indenter was not actively heated. The temperature was left to
13
14 stabilise for a minimum of 30 minutes and it was kept constant throughout the test using
15
16 a temperature controller. The convection losses were minimised using a ceramic wool
17
18 shielding around the specimen.
19
20

21
22 The results presented in the article are the average of 16 experiments or the most
23
24 representative curve of the set. The fitting of the data was conducted with Wolfram
25
26 Mathematica version 11.3, accounting for the stochastic variation between experiments.
27
28
29
30

31 32 2.3. Characterisation 33

34
35 The specimens were observed in a Jeol 7000 FEG-SEM using a thin carbon
36
37 coating to improve the conductivity. The observations were only conducted once the
38
39 tests were finished, so that the damage by the vacuum environment and the localised
40
41 heating under the electron beam would not affect the results of the push-out tests.
42
43

44
45 AFM observations were conducted in a Veeco MultiMode SPM, fitted with an
46
47 AS12 scanner and a silicon nitride cantilever for contact mode. The elastic constant of
48
49 the selected tip was 0.12 N/m. The results were analysed using the Bruker NanoScope
50
51 Analysis 1.5 software.
52
53

54 55 3. Results 56 57 58 59 60 61 62 63 64 65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

3.1. Validity and limitations of the push-out tests

The SEM observations conducted after the push-out tests clearly revealed single fibres which were pushed-in on the loading side of the samples, i.e. the surface of these fibres was at a lower plane compared to the nearest neighbours (Figure 4a). The pushed-in fibres exhibited minimum surface damage, although the edges of the Berkovich indenter clearly made contact with the surrounding material, causing damage to the neighbouring fibres. In addition, the observations conducted on the back side of the samples revealed that the fibres were pushed-out, i.e. the surface of these fibres was at a higher plane in relation to the surrounding material (Figure 4b).

The AFM observations on the back side of the specimens confirmed that the fibres were pushed-out (Figure 5). The push-out distance was between 1.0 μm and 1.2 μm in all cases, which is in agreement with the geometrical limitations of the Berkovich indenter used for the experiments. Once this displacement threshold was reached, the Berkovich indenter made contact with the surrounding material, thus pushing or damaging the surrounding fibres. A careful observation of Figure 4 shows the damage on the surrounding fibres and the displacement of the nearest neighbouring fibres, relative to the rest of the sample.

Based on these results, it can be concluded that the load-displacement data obtained during the push-out tests for displacements below the 1.2 μm is representative of the micro-mechanical response of single fibres in the composite.

3.2. Load-displacement curves

The typical load-displacement curve of the push-out tests is illustrated in Figure 6. The load and the displacement readings are directly obtained from the nanoindentation

1 instrument, whereas the strain and the stress were calculated using the following
2
3 equations:

$$\sigma = \frac{L}{A} = \frac{L}{\pi \varnothing t} \quad (1)$$

$$\varepsilon = \frac{d}{t} \quad (2)$$

4
5
6
7
8
9
10
11 where σ is the stress, ε is the strain, L is the applied load, A is the average interface area,
12
13 \varnothing is the average diameter of the carbon fibres, d is the displacement and t is the
14
15
16
17 thickness of the specimen.

18
19 The characteristic regions of the load-displacement curve are indicated in
20
21 Figure 6. The curves typically show a non-linear region at the beginning of the loading
22
23 cycle, which finishes at displacements of approximately 200 nm (point 1). This section
24
25 of the curve is associated with elastic and plastic deformation of the loaded fibre, until a
26
27 conformal contact with the Berkovich indenter is reached. Larger deformations in this
28
29 region are typically attributed to the elastic bending of the thin sample between the
30
31 supports [18]; the samples exhibiting such behaviour were omitted from this study. The
32
33 curve shows a linear region (2), which is attributed to the stiffness of the interface or the
34
35 stable crack growth between the carbon fibre and the polymeric matrix. This region
36
37 typically finishes at displacements in the order of 650 nm (point 3). At this point, the
38
39 displacement increases more rapidly and a departure from the linear trend is observed.
40
41 This is attributed to the debonding of the fibre from the matrix or the unstable crack
42
43 growth, which often ended with a large displacement at constant load (IFS).
44
45
46
47
48
49
50

51 The inset in Figure 6 shows the displacement during the dwell time (region 4).
52
53 The increasing deformation at constant load is characteristic of a viscoelastic behaviour
54
55 and some push-out events were observed in this region; these events were marked by a
56
57 stepwise increase in displacement at constant load. The maximum displacement at the
58
59
60
61
62
63
64
65

1 end of this region was invariably in the order 1.2 μm , in agreement with the AFM
2
3 observations of the fibre displacement after the test. At this point, the load was removed
4
5 to allow for an elastic recovery and a hysteresis loop was formed upon reloading, which
6
7 is frequently attributed to energy losses due to friction between the carbon fibre and the
8
9 polymer [9]. The displacement of the indenter beyond the 1.2 μm threshold is associated
10
11 with a considerable increase in load, because of the physical contact between the
12
13 Berkovich indenter and the surrounding fibres.
14
15
16

17
18 Table 3 summarises the results of the push-out tests conducted at room
19
20 temperature and high temperature with different loading rates. In general terms, the
21
22 samples tested at a low loading rate (0.1 mN/s) showed lower stress values at the
23
24 characteristic points, compared to the samples tested at 1 mN/s and 10 mN/s; the
25
26 differences between the latter were negligible. The strain at the characteristic points was
27
28 comparable for all the loading rate conditions, whereas the loop area (region 5)
29
30 increased with the loading rate. The results of the tests conducted at high temperature
31
32 revealed similar trends, although the slope of the linear section (2) was lower, indicating
33
34 a higher **sample** compliance at high temperature. In addition, the stress values at
35
36 characteristic points tended to be lower, but the results were also more scattered. The
37
38 loop area showed very similar results at room temperature and high temperature, in both
39
40 cases increasing with the loading rate.
41
42
43
44
45
46

47 These comments are reflected on the stress and strain curves plotted as a function
48
49 of time (Figure 7). The stress increased linearly until a maximum point, where the
50
51 displacement of the fibre reached 1 μm . At this point, the load was held for 5 seconds
52
53 before unloading. The strain curves show clear signs of residual deformation at the end
54
55 of the first loading cycle, which are attributed to the pushing-in/out of the carbon fibre
56
57
58
59
60
61
62
63
64
65

1 under load. The second loading cycle was conducted in a similar way, but in this case
2
3 the maximum deformation reached 2 μm . It must be mentioned that the displacements
4
5 beyond 1.2 μm are affected by the interference between the Berkovich indenter and the
6
7 surrounding material.
8
9

10 The samples tested at high temperature typically required lower loads to reach the
11
12 1 μm displacement, defined as the limit for the first loading cycle, thus the total loading
13
14 time was shorter. The shape of the strain curves at the end of the first loading cycle is
15
16 noteworthy, where the deflection increases rapidly with minimum changes in the stress
17
18 or even during the dwell time at constant stress. In addition, some differences can be
19
20 observed depending on the loading rate and the temperature. The dwell time at
21
22 maximum load is clearly visible for the high loading rate (10 mN/s), as 5 seconds are a
23
24 significant portion of the total duration of the experiment. However, the dwell time is
25
26 relatively short for the experiments conducted at lower loading rates (1 mN/s and 0.1
27
28 mN/s) so these curves are presented separately in Figure 8.
29
30
31
32
33
34

35 The shape of the curves in Figure 8 can be related with the viscoelastic response
36
37 of the polymeric matrix, which is more evident at high loading rates, in which case the
38
39 dwell time takes place before the system reaches equilibrium. On the other hand, the
40
41 response during dwell time is almost linear for the low loading rate (0.1 mN/s),
42
43 reflecting a system closer to equilibrium. In addition, the viscoelastic response during
44
45 dwell time is also affected by temperature. The samples tested at high temperature
46
47 exhibited a much higher compliance compared to the ones tested at room conditions,
48
49 which is attributed to the different response of the polymer below and above the T_g .
50
51
52
53
54
55
56

57 **4. Discussion**

58
59
60
61
62
63
64
65

1 The results presented in the previous section are in agreement with the literature
2 [2, 9, 14-16]. However, the time-dependent response as a function of the loading rate
3 and temperature, as well as the occurrence of push-out events during the dwell time at
4 constant load, are noteworthy (Figure 8a, inset). These phenomena seem to be
5 associated with viscoelastic response of the interface between the carbon fibres and the
6 matrix, or the viscoelastic deformation of the polymer in the immediate vicinity of the
7 tested carbon fibres.

8 Jäger et al. [16] studied the influence of plastic deformation on the push-out test
9 of carbon fibre reinforced epoxy. The authors observed a deviation in the force-
10 displacement curve from the linear behaviour, which they attributed to plastic
11 deformation as opposed to crack growth. This remark highlights the different response
12 of polymer-matrix and ceramic-matrix composites [9, 14-16]. The time-dependent or
13 viscoelastic deformation is an important mechanism in polymers, which has been
14 reported in nanoindentation experiments [19, 20].

15 High magnification observations of the pushed-out fibres revealed elongated
16 filaments of polymer still attached to the carbon fibres, even after debonding occurred
17 (Figure 9). The filaments rarely formed in the thin sections of polymer between
18 neighbouring fibres, but they were frequently observed in the isles of polymer between
19 3 staggered fibres, which resembles the plastic strain simulations in Ref. [16]. These
20 filaments would continue to resist the displacement of the fibre, even at large strains,
21 with the viscoelastic behaviour characteristic of the polymeric matrix.

22 The viscoelastic response of polymers is often described using a Kelvin-Voigt
23 (Eq. 3) [19, 20] or a logarithmic model (Eq. 4) [21, 22]:

$$\varepsilon(t) = \frac{1}{k} \left(1 - e^{-\frac{t}{\tau}}\right) = \frac{\sigma}{E} \left(1 - e^{-\frac{\eta}{E}t}\right) \quad (3)$$

$$\varepsilon(t) = m_{eff} \ln\left(\frac{t}{\Gamma} + 1\right) \quad (4)$$

where ε is the strain, k is the stiffness parameter related with the stress (σ) and the elastic modulus of the interface (E), and τ is the relaxation time constant associated with the viscosity (η) and the elastic modulus (E) and t is the time, m_{eff} is the strain rate sensitivity and Γ is the creep time.

Table 4 shows a summary of the fitting results, which indicate the prevalence of viscoelasticity in the experiments conducted at high loading rates (1 mN/s and 10 mN/s), whereas the samples tested at lower loading rate (0.1 mN/s) exhibited a more linear response during the dwell time. The values also reflect the higher compliance observed in the high temperature experiments, which can be attributed to the softening and **drop in stiffness** of the polymeric matrix above T_g . The high modulus observed at short time range and low temperature can be attributed to the deformation of the intermolecular distance, which is a high energy distortion mechanism [23]. On the other hand, the reorientation and translation of the chain segments becomes possible at longer times and higher temperatures, and this relaxation is reflected on the decrease in modulus. Unfortunately, the fitting parameters can only be used as figures of merit at this stage, and further work is needed to obtain a detailed molecular interpretation of these values [24].

It is known that physical ageing can have a marked effect on the viscoelastic properties of polymers below T_g [25]. In our case, the samples were stored at room temperature for over 6 months ($> 15 \times 10^6$ seconds), and the duration of the push-out tests was short in comparison (between 10 and 600 seconds). Therefore, the physical ageing during the tests was negligible and the load-displacement-time curves presented in this article are characteristic of a single aged condition (momentary curves) [26].

1 Mendels et al. [27] reported that the physical ageing of the polymeric matrix had
2
3 no significant influence on the IFS in micro-bond tests, and the observed changes were
4
5 attributed to variations in internal stresses. Greisel et al. [14] conducted push-out tests
6
7 on samples annealed at temperatures above T_g [25], where thermal rejuvenation occurs.
8
9 The change in failure mode, from brittle to ductile, was linked with the relaxation of
10
11 thermal stresses but the ageing time after annealing was not reported. In view of this,
12
13 the effect of physical ageing on the push-out tests may require further study.
14
15
16

17
18 The viscoelastic response has interesting implications for the micro-mechanical
19
20 models that predict the interaction between the carbon fibres and the polymeric matrix.
21
22 In first place, the deviation in the force-displacement curve from the linear behaviour,
23
24 which is often associated with debonding, could occur at different stresses depending on
25
26 the loading conditions, mainly loading rate, holding time and temperature. This region
27
28 dominated by viscoelastic phenomena could be considered an intermediate regime
29
30 between the cohesive and frictional regimes [2].
31
32
33

34
35 In addition, the contribution made by the friction force between debonded regions
36
37 of the carbon fibre and the polymer is likely to be masked by the viscoelastic
38
39 components acting on the bonded areas. A separation of these two components would
40
41 be difficult, unless a complete debonding of the fibre is achieved. Unfortunately, this
42
43 condition was beyond the experimental limitations of the Berkovich indenter used in
44
45 this study. The viscoelastic deformation would also take longer time to recover [19],
46
47 and this should be taken into account when assessing the dissipative and non-dissipative
48
49 mechanisms [16].
50
51
52

53
54 Finally, the surface treatment of the carbon fibres may alter the mechanical
55
56 properties of the interface material and the thickness of the interface, thus affecting its
57
58
59
60
61
62
63
64
65

1 viscoelastic response. Battisti et al. [28] reported an increase in the interlaminar shear
2 strength when multi-wall carbon nanotubes (MWCNTs) were grafted on the carbon
3 fibres, despite the lack of interaction between the MWCNTs and the carbon fibres.
4
5 Therefore, it is speculated that the deviation in the force-displacement curve from the
6 linear behaviour observed after some surface treatments could be related with changes
7 in viscoelastic response of the polymer around the fibres, instead of the IFS. This
8 phenomenon could reveal new strengthening and toughening strategies for composite
9 materials [15, 29].
10
11
12
13
14
15
16
17
18
19
20
21
22

23 **5. Conclusions**

24
25 The push-out tests conducted on carbon fibre reinforced epoxy using different
26 loading rates and testing temperatures revealed the following conclusions:
27

- 28 - It was possible to push-out single carbon fibres from the matrix with a Berkovich
29 indenter under different loading rates and temperatures (below and above T_g).
30
- 31 - The deviation in the force-displacement curve from the linear behaviour, which is
32 often associated with debonding, could occur at different stresses depending on the
33 loading conditions, mainly loading rate, holding time and temperature.
34
- 35 - The interfacial strength (IFS) and stiffness increased with increasing loading rate and
36 decreased with increasing temperature.
37
- 38 - A time-dependent response was observed in all cases but was more noticeable in the
39 experiments conducted at high loading rate or at high temperature. The behaviour
40 could be described with simple viscoelastic models.
41
42
43
44
45
46
47
48
49
50
51
52
53

54 The viscoelastic response has interesting implications for the micro-mechanical
55 models that predict the interaction between the carbon fibres and the polymeric matrix.
56
57
58
59
60
61
62
63
64
65

1 This phenomenon could reveal new strengthening and toughening strategies for
2
3 composite materials.
4
5
6
7

8 **Acknowledgements** 9

10 The research leading to these results has received funding from the European
11 Union (GA604248 & GA685844). SCG would like to thank Alan Riley, from Toray
12 International UK Ltd, for providing samples of RebarS12.
13
14
15
16
17
18
19

20 **References** 21

- 22
23 [1] Karger-Kocsis J, Mahmood H, Pegoretti A. Recent advances in fiber/matrix
24 interphase engineering for polymer composites. *Prog Mater Sci.* 2015;73:1-43.
25
26
27
28 [2] Esqué-de los Ojos D, Ghisleni R, Battisti A, Mohanty G, Michler J, Sort J, et al.
29 Understanding the mechanical behavior of fiber/matrix interfaces during push-in
30 tests by means of finite element simulations and a cohesive zone model. *Comp Mater*
31 *Sci.* 2016;117:330-337.
32
33
34
35
36
37
38
39 [3] Kabel J, Hosemann P, Zayachuk Y, Armstrong DEJ, Koyanagi T, Katoh Y, et al.
40 Ceramic composites: A review of toughening mechanisms and demonstration of
41 micropillar compression for interface property extraction. *J Mater Res.*
42 2018;33(4):424-439.
43
44
45
46
47
48
49
50 [4] Zhandarov S, Mäder E. Characterization of fiber/matrix interface strength:
51 Applicability of different tests, approaches and parameters. *Compos Sci Technol.*
52 2005;65(1):149-160.
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [5] Sockalingam S, Nilakantan G. Fiber-matrix interface characterization through the
2
3 microbond test: A review. *Int J Aeronaut Space*. 2012;13(3):282-295.
4
5
6
- 7 [6] Zhandarov S, Mäder E. Indirect estimation of fiber/polymer bond strength and
8
9 interfacial friction from maximum load values recorded in the microbond and pull-
10
11 out tests. Part II: Critical energy release rate. *J Adhes Sci Technol*. 2003;17(7):967-
12
13 980.
14
15
16
- 17 [7] Zhandarov SF, Mäder E, Yurkevich OR. Indirect estimation of fiber/polymer bond
18
19 strength and interfacial friction from maximum load values recorded in the
20
21 microbond and pull-out tests. Part I: Local bond strength. *J Adhes Sci Technol*.
22
23 2002;16(9):1171-1200.
24
25
26
- 27 [8] Sha JJ, Dai JX, Li J, Wei ZQ, Hausherr JM, Krenkel W. Measurement and analysis
28
29 of fiber-matrix interface strength of carbon fiber-reinforced phenolic resin matrix
30
31 composites. *J Compos Mater*. 2014;48(11):1303-1311.
32
33
34
35
36
- 37 [9] Mueller WM, Moosburger-Will J, Sause MGR, Horn S. Microscopic analysis of
38
39 single-fiber push-out tests on ceramic matrix composites performed with Berkovich
40
41 and flat-end indenter and evaluation of interfacial fracture toughness. *J Eur Ceram
42
43 Soc*. 2013;33(2):441-451.
44
45
46
- 47 [10] Andersons J, Joffe R, Hojo M, Ochiai S. Fibre fragment distribution in a single-
48
49 fibre composite tension test. *Compos Part B-Eng*. 2001;32(4):323-332.
50
51
52
53
- 54 [11] Huang Y, Young RJ. Analysis of the fragmentation test for carbon-fibre/epoxy
55
56 model composites by means of Raman spectroscopy. *Compos Sci Technol*.
57
58 1994;52(4):505-517.
59
60
61
62
63
64
65

- 1 [12] Paipetis A, Galiotis C. Modelling the stress-transfer efficiency of carbon-epoxy
2
3 interfaces. P R Soc A. 2001;457(2011):1555-1577.
4
5
6
- 7 [13] Pisanova E, Zhandarov S, Mäder E. How can adhesion be determined from
8
9 micromechanical tests? Compos Part A-Appl S. 2001;32(3-4):425-434.
10
11
12
- 13 [14] Greisel M, Jäger J, Moosburger-Will J, Sause MGR, Mueller WM, Horn S.
14
15 Influence of residual thermal stress in carbon fiber-reinforced thermoplastic
16
17 composites on interfacial fracture toughness evaluated by cyclic single-fiber push-out
18
19 tests. Compos Part A-Appl S. 2014;66:117-127.
20
21
22
- 23 [15] Mueller WM, Moosburger-Will J, Sause MGR, Greisel M, Horn S. Quantification
24
25 of crack area in ceramic matrix composites at single-fiber push-out testing and
26
27 influence of pyrocarbon fiber coating thickness on interfacial fracture toughness. J
28
29 Eur Ceram Soc. 2015;35(11):2981-2989.
30
31
32
- 33 [16] Jäger J, Sause MGR, Burkert F, Moosburger-Will J, Greisel M, Horn S. Influence
34
35 of plastic deformation on single-fiber push-out tests of carbon fiber reinforced epoxy
36
37 resin. Compos Part A-Appl S. 2015;71:157-167.
38
39
40
41
- 42 [17] ASTM E1356 Standard Test Method for Assignment of the Glass Transition
43
44 Temperatures by Differential Scanning Calorimetry; 2014.
45
46
47
- 48 [18] Medina CM, Molina-Aldareguía JM, González C, Flores P, Llorca J. Comparison
49
50 of push-in and push-out tests for measuring interfacial shear strength in nano-
51
52 reinforced composite materials. J Compos Mater. 2016;50(12):1651-1659.
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [19] Yang S, Zhang Y-W, Zeng K. Analysis of nanoindentation creep for polymeric
2 materials. *J Appl Phys.* 2004;95(7):3655-3666.
3
4
5
6
7 [20] Gibson RF. A review of recent research on nanoindentation of polymer composites
8 and their constituents. *Compos Sci Technol.* 2014;105:51-65.
9
10
11
12 [21] Chen J, Bell GA, Dong H, Smith JF, Beake BD. A study of low temperature
13 mechanical properties and creep behaviour of polypropylene using a new sub-
14 ambient temperature nanoindentation test platform. *J Phys D Appl Phys.*
15 2010;43(42):425404.
16
17
18
19
20
21
22
23 [22] Beake BD. Modelling indentation creep of polymers: a phenomenological
24 approach. *J Phys D Appl Phys.* 2006;39(20):4478.
25
26
27
28
29 [23] Shaw MT, MacKnight WJ. Introduction to polymer viscoelasticity. 3rd ed. USA:
30 Wiley Interscience; 2005.
31
32
33
34
35 [24] Fischer-Cripps AC. A simple phenomenological approach to nanoindentation
36 creep. *Mat Sci Eng A.* 2004;385(1):74-82.
37
38
39
40
41 [25] Odegard GM, Bandyopadhyay A. Physical aging of epoxy polymers and their
42 composites. *J Polym Sci Pol Phys.* 2011;49(24):1695-1716.
43
44
45
46
47 [26] Struik LCE. Physical aging in plastics and other glassy materials. *Polym Eng Sci.*
48 1977;17(3):165-173.
49
50
51
52
53 [27] Mendels D-A, Leterrier Y, Manson J-AE, Nairn JA. The Influence of Internal
54 Stresses on the Microbond Test II: Physical Aging and Adhesion. *J Compos Mater.*
55 2002;36(14):1655-1676.
56
57
58
59
60
61
62
63
64
65

1 [28] Battisti A, Esqué-de los Ojos D, Ghisleni R, Brunner AJ. Single fiber push-out
2
3 characterization of interfacial properties of hierarchical CNT-carbon fiber
4
5 composites prepared by electrophoretic deposition. *Compos Sci Technol.*
6
7
8 2014;95:121-127.
9

10
11 [29] Moosburger-Will J, Jäger J, Strauch J, Bauer M, Strobl S, Linscheid FF, et al.
12
13 Interphase formation and fiber matrix adhesion in carbon fiber reinforced epoxy
14
15 resin: influence of carbon fiber surface chemistry. *Compos Interface.*
16
17
18 2017;24(7):691-710.
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 **Figure captions**
2

3 Figure 1: Macrographs of the Rebar S12 samples: a) Discs extracted from the rod and b)
4
5 thin specimen on a spatula, during the final stage of preparation.
6
7

8 Figure 2: Differential scanning calorimetry (DSC) curve of Rebar S12.
9

10 Figure 3: Schematic diagram of the experimental set-up used for the push-out tests.
11

12 Figure 4: SEM micrographs of a specimen after the push-out tests: a) front side
13
14 (pushed-in) and b) back side (pushed-out) of the specimen.
15
16
17

18 Figure 5: AFM observations of a specimen after the push-out test: a) 3D image of the
19
20 pushed-out fibre and b) cross section profile of the same fibre.
21
22

23 Figure 6: Typical load-displacement curve of the push-out tests. The arrows indicate the
24
25 loading direction and the inset corresponds to the displacement during the
26
27 dwell time at constant load (region 4).
28
29

30 Figure 7: Strain-time (solid) and stress-time (dash) curves obtained with different
31
32 loading rates and temperatures.
33
34

35 Figure 8: Strain-time curves at dwell time (constant load) obtained with different
36
37 loading rates and temperatures. The graphs show the strain relative to the
38
39 deformation at the beginning of the dwell time. The fitted exponential (dot
40
41 line) and logarithmic (dash line) curves are superimposed to the experimental
42
43 data.
44
45
46

47 Figure 9: High magnification SEM micrograph of a pushed-out fibre.
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8 **Tables**
9

10
11
12
13
14
15
16 Table 1: Nominal mechanical properties of Rebar S12 from specification sheet.

17

18 Material	19 Young's modulus	20 Tensile strength	21 Strain at break	22 Shear strength	23 Rod diameter	24 Volume fraction of fibres
25 Rebar S12	26 150 GPa	27 > 1900 MPa	28 > 1.30%	29 200 MPa	30 12 mm	31 70%

32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Table 2: Loading conditions used for the push-out tests.

Mode	Number of cycles	Displacement per cycle	Maximum load	Loading rate	Dwell time	Unloading rate
Multiple cycles, depth controlled	2	1 μm	200 mN	0.1 mN/s	5 s	0.1 mN/s
				1.0 mN/s		1.0 mN/s
				10 mN/s		10 mN/s

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

Table 3: Summary of results from push-out tests. The reference points correspond to Figure 6.

Loading rate	Stress at point 1 [MPa]	Strain at point 1 []	Slope of linear section 2 [mN / nm]	Stress at point 3 [MPa]	Strain at point 3 []	Maximum stress in Cycle 1 (point 4) [MPa]	Maximum strain in Cycle 1 (point 4) []	Loop area (5) [μ J]
RT 0.1	7.2 ± 1.2	0.007 ± 0.001	35.1 ± 3.5	30.5 ± 3.9	0.021 ± 0.002	39.3 ± 5.4	0.032 ± 0.001	0.80 ± 0.23
RT 1	9.9 ± 1.9	0.009 ± 0.003	39.9 ± 5.4	40.5 ± 6.1	0.025 ± 0.005	53.6 ± 8.0	0.041 ± 0.008	1.30 ± 0.38
RT 10	9.7 ± 1.4	0.008 ± 0.001	40.2 ± 3.9	42.9 ± 1.9	0.023 ± 0.003	52.2 ± 2.7	0.035 ± 0.001	2.84 ± 0.41
HT 0.1	2.8 ± 3.0	0.004 ± 0.004	19.6 ± 4.4	27.2 ± 9.2	0.030 ± 0.005	40.5 ± 12.9	0.054 ± 0.003	0.38 ± 0.14
HT 1	7.3 ± 1.2	0.009 ± 0.002	29.9 ± 3.0	40.9 ± 4.7	0.033 ± 0.005	52.3 ± 4.6	0.050 ± 0.001	1.65 ± 0.22
HT 10	7.4 ± 2.4	0.009 ± 0.002	27.4 ± 4.6	41.9 ± 9.4	0.036 ± 0.006	51.0 ± 8.4	0.048 ± 0.004	2.51 ± 0.86

RT: room temperature (24°C); HT: High temperature (125°C)

Table 4: Fitting parameters from Kelvin-Voigt and logarithmic models.

Loading rate	Kelvin-Voigt model				Logarithmic model			
	Room temperature		High temperature		Room temperature		High temperature	
	k	τ	k	τ	m_{eff}	Γ	m_{eff}	Γ
0.1 mN/s	635	3.30	216	6.60	0.09%	1.57	0.33%	4.57
1 mN/s	116	1.50	78	1.45	0.33%	0.23	0.45%	0.29
10 mN/s	80	1.30	70	1.60	0.42%	0.38	0.52%	0.35

1 **Viscoelastic response of carbon fibre reinforced polymer during push-out tests**
2

3 Santiago CORUJEIRA GALLO ^a, Xiaoying LI ^a, Zhenxue ZHANG ^a, Constantinos
4
5 CHARITIDIS ^b and Hanshan DONG ^a
6
7
8
9

10 ^a University of Birmingham, School of Metallurgy and Materials
11
12 Edgbaston, Birmingham, B15 2TT, United Kingdom.
13
14
15

16
17
18 ^b School of Chemical Engineering, National Technical University of Athens
19
20 Iroon Polytechniou 9, Zografou 157 80, Greece.
21
22
23

24
25 *Corresponding author: S. Corujeira Gallo
26
27 Phone: +44 (0)121 414 5163
28
29 E-mail: corujeis@bham.ac.uk
30
31
32
33
34

35 **Abstract**
36

37 Push-out is one of the available techniques to assess the bond strength between
38 the reinforcing fibres and the matrix in composite materials. The test is conducted on
39 thin sections of composite, and a small indenter is used to apply increasing load on
40 single fibres while measuring the displacement, until the debonding occurs. This study
41 used push-out tests to assess the debonding mechanism of carbon fibres in an epoxy
42 matrix. The tests were conducted at multiple loading rates (0.1 mN/s, 1 mN/s and 10
43 mN/s) and temperatures (24°C and 125°C). The results were analysed and contrasted
44 with scanning electron microscopy and atomic force microscopy observations. The data
45 showed evidence of push-out events and provided new insights into the contribution of
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 the viscoelastic behaviour of the fibre/matrix interface and/or the matrix. This finding
2
3 could pave new pathways for improving the bond strength between the carbon fibres
4
5 and the matrix in composite materials.
6
7
8
9

10 **Keywords:** Carbon fibres (A); Polymer-matrix composites (A); Debonding (B); Creep
11
12 (D)
13
14
15
16

17 **1. Introduction**

18
19 Carbon fibre reinforced polymers are composed of two phases: the carbon fibres,
20
21 which provide strength and stiffness, and the polymeric matrix, which holds the
22
23 reinforcing fibres in place and distributes the load among individual fibres [1]. The
24
25 interfacial strength (IFS) between carbon fibres and polymeric matrices has important
26
27 implications for the mechanical properties of composite materials [2, 3]. In spite of the
28
29 extensive research efforts, the appropriate assessment of the IFS and its link to the
30
31 macroscopic properties of composites remains challenging. Several testing methods
32
33 have been developed to assess the IFS [4], including: micro-bond [5], pull-out [6, 7] or
34
35 push-out tests [8, 9], fragmentation tests [10, 11] and Raman spectroscopy
36
37 measurements of specimens under stress [12]. Even though each of these methods can
38
39 be used to effectively rank the IFS, the results obtained by different methods are not
40
41 directly comparable [13]. Moreover, it is difficult to link the microscopic test results
42
43 with the macroscopic properties of composites. The inconsistencies are frequently
44
45 attributed to the different stress states developed in microscopic and macroscopic
46
47 conditions [13].
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 In addition, there is no general agreement on the operating interfacial failure
2
3 modes. Several models have been proposed with this regard, mainly based on stress and
4
5 energy failure criteria [9, 14]. However, the limitations of both approaches have been
6
7 discussed by several authors [15, 16], which could be attributed to the different load-
8
9 displacement responses of ceramic-matrix and polymer-matrix composites. Clearly,
10
11 further advance in scientific understanding of the debonding mechanism is important to
12
13 improve the IFS and to predict the behaviour of composites materials in real operating
14
15 environments. In this article, the results of push-out tests, conducted at multiple loading
16
17 rates and temperatures, are presented and discussed. The micro-mechanical tests were
18
19 supported by microscopic observations to identify the debonding mechanisms.
20
21
22
23
24
25
26

27 **2. Materials and Methods**

28 *2.1. Sample preparation*

29
30 The samples used for the tests were extracted from a rod of Toray Rebar S12
31
32 unidirectional composite, consisting of T700 carbon fibres in an epoxy matrix (Table 1).
33
34 Discs, 700 μm thick (Figure 1), were extracted from the rod of Rebar S12 using a
35
36 Struers Accutom 5 precision cut-off machine, fitted with an Al_2O_3 abrasive disc and
37
38 applying abundant cooling fluid. At least 300 μm of material were removed from each
39
40 side of the discs by wet grinding with #1200 SiC abrasive paper. Finally, both sides of
41
42 the discs were ground with #2500 and #4000 SiC abrasive paper and polished for 10
43
44 minutes with colloidal silica suspension. In their final condition, the discs had a
45
46 thickness between 20 μm and 40 μm , which reduces the load needed for the push-out to
47
48 occur. The samples for the tests were cut from these discs using a sharp scalpel and
49
50 stored in glass vials under room conditions (20°C and 50% relative humidity).
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 The glass transition temperature (T_g) of the Rebar S12A was determined using a
2
3 Mettler Toledo DSC 1 Star calorimeter. Small samples, approximately 14.5 mg in
4
5 weight, were placed in aluminium pans and heated from room temperature (24°C) to
6
7 250°C at a rate of 20°C/min in a nitrogen atmosphere, and subsequently cooled down to
8
9 room temperature (Figure 2). The first curve obtained in this way was discarded, and the
10
11 glass transition temperature was determined from the second run, as recommended in
12
13 Ref. [17].
14
15

16 2.2. *Push-out tests*

17
18 The tests were conducted in a Micro Materials Vantage nanoindentation
19
20 instrument, fitted with a Berkovich tip and a hot stage. A custom-made holder was
21
22 manufactured, having 60 µm wide slots produced by electro discharge machining
23
24 (EDM), where the fibres could be pushed out (Figure 3). The samples were fixed onto
25
26 the holder using cyanoacrylate adhesive. Individual fibres were selected at random,
27
28 using an optical microscope with a magnification of 400X. The positioning accuracy of
29
30 the stage was in the order of 0.5 µm and it was re-calibrated every 8 to 12 tests. The
31
32 instrument was operated in the displacement-control mode (through a feedback loop
33
34 with the load) and the loading conditions are listed in Table 2, which consisted of two
35
36 loading cycles. The first loading cycle was interrupted when the displacement reached
37
38 1 µm, which was expected to be close to producing a push-out event, but not sufficient
39
40 for the Berkovich indenter to contact the surrounding fibres. The load held for 5 s
41
42 (dwell time at maximum load), and then gradually removed for the fibre and the sample
43
44 to recover elastically. The second loading cycle was conducted until the displacement
45
46 reached 2 µm or the load reached 200 mN (whichever condition was reached first). This
47
48 cycle was expected to reveal information about the friction between the debonded
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 sections of the carbon fibre and the surrounding matrix, as well as to complete the crack
2
3 propagation thus resulting in a push-out event [15].
4

5
6 During the push-out tests, the temperature of the sample was controlled using a K-
7
8 type thermocouple embedded in the hot stage of the nano-indentation instrument. The
9
10 samples were heated up to the target temperature of 125°C, above the T_g of the material,
11
12 at a rate of 1.6°C/min; the indenter was not actively heated. The temperature was left to
13
14 stabilise for a minimum of 30 minutes and it was kept constant throughout the test using
15
16 a temperature controller. The convection losses were minimised using a ceramic wool
17
18 shielding around the specimen.
19
20
21

22
23 The results presented in the article are the average of 16 experiments or the most
24
25 representative curve of the set. The fitting of the data was conducted with Wolfram
26
27 Mathematica version 11.3, accounting for the stochastic variation between experiments.
28
29
30
31

32 *2.3. Characterisation*

33
34
35 The specimens were observed in a Jeol 7000 FEG-SEM using a thin carbon
36
37 coating to improve the conductivity. The observations were only conducted once the
38
39 tests were finished, so that the damage by the vacuum environment and the localised
40
41 heating under the electron beam would not affect the results of the push-out tests.
42
43
44

45 AFM observations were conducted in a Veeco MultiMode SPM, fitted with an
46
47 AS12 scanner and a silicon nitride cantilever for contact mode. The elastic constant of
48
49 the selected tip was 0.12 N/m. The results were analysed using the Bruker NanoScope
50
51 Analysis 1.5 software.
52
53
54
55
56

57 **3. Results**

58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

3.1. Validity and limitations of the push-out tests

The SEM observations conducted after the push-out tests clearly revealed single fibres which were pushed-in on the loading side of the samples, i.e. the surface of these fibres was at a lower plane compared to the nearest neighbours (Figure 4a). The pushed-in fibres exhibited minimum surface damage, although the edges of the Berkovich indenter clearly made contact with the surrounding material, causing damage to the neighbouring fibres. In addition, the observations conducted on the back side of the samples revealed that the fibres were pushed-out, i.e. the surface of these fibres was at a higher plane in relation to the surrounding material (Figure 4b).

The AFM observations on the back side of the specimens confirmed that the fibres were pushed-out (Figure 5). The push-out distance was between 1.0 μm and 1.2 μm in all cases, which is in agreement with the geometrical limitations of the Berkovich indenter used for the experiments. Once this displacement threshold was reached, the Berkovich indenter made contact with the surrounding material, thus pushing or damaging the surrounding fibres. A careful observation of Figure 4 shows the damage on the surrounding fibres and the displacement of the nearest neighbouring fibres, relative to the rest of the sample.

Based on these results, it can be concluded that the load-displacement data obtained during the push-out tests for displacements below the 1.2 μm is representative of the micro-mechanical response of single fibres in the composite.

3.2. Load-displacement curves

The typical load-displacement curve of the push-out tests is illustrated in Figure 6. The load and the displacement readings are directly obtained from the nanoindentation

1 instrument, whereas the strain and the stress were calculated using the following
2
3 equations:

$$\sigma = \frac{L}{A} = \frac{L}{\pi \varnothing t} \quad (1)$$

$$\varepsilon = \frac{d}{t} \quad (2)$$

4
5
6
7
8
9
10
11 where σ is the stress, ε is the strain, L is the applied load, A is the average interface area,
12
13 \varnothing is the average diameter of the carbon fibres, d is the displacement and t is the
14
15
16
17 thickness of the specimen.

18
19 The characteristic regions of the load-displacement curve are indicated in
20
21 Figure 6. The curves typically show a non-linear region at the beginning of the loading
22
23 cycle, which finishes at displacements of approximately 200 nm (point 1). This section
24
25 of the curve is associated with elastic and plastic deformation of the loaded fibre, until a
26
27 conformal contact with the Berkovich indenter is reached. Larger deformations in this
28
29 region are typically attributed to the elastic bending of the thin sample between the
30
31 supports [18]; the samples exhibiting such behaviour were omitted from this study. The
32
33 curve shows a linear region (2), which is attributed to the stiffness of the interface or the
34
35 stable crack growth between the carbon fibre and the polymeric matrix. This region
36
37 typically finishes at displacements in the order of 650 nm (point 3). At this point, the
38
39 displacement increases more rapidly and a departure from the linear trend is observed.
40
41 This is attributed to the debonding of the fibre from the matrix or the unstable crack
42
43 growth, which often ended with a large displacement at constant load (IFS).
44
45
46
47
48
49
50

51 The inset in Figure 6 shows the displacement during the dwell time (region 4).
52
53 The increasing deformation at constant load is characteristic of a viscoelastic behaviour
54
55 and some push-out events were observed in this region; these events were marked by a
56
57 stepwise increase in displacement at constant load. The maximum displacement at the
58
59
60
61
62
63
64
65

1 end of this region was invariably in the order 1.2 μm , in agreement with the AFM
2 observations of the fibre displacement after the test. At this point, the load was removed
3 to allow for an elastic recovery and a hysteresis loop was formed upon reloading, which
4 is frequently attributed to energy losses due to friction between the carbon fibre and the
5 polymer [9]. The displacement of the indenter beyond the 1.2 μm threshold is associated
6 with a considerable increase in load, because of the physical contact between the
7 Berkovich indenter and the surrounding fibres.
8

9
10
11 Table 3 summarises the results of the push-out tests conducted at room
12 temperature and high temperature with different loading rates. In general terms, the
13 samples tested at a low loading rate (0.1 mN/s) showed lower stress values at the
14 characteristic points, compared to the samples tested at 1 mN/s and 10 mN/s; the
15 differences between the latter were negligible. The strain at the characteristic points was
16 comparable for all the loading rate conditions, whereas the loop area (region 5)
17 increased with the loading rate. The results of the tests conducted at high temperature
18 revealed similar trends, although the slope of the linear section (2) was lower, indicating
19 a higher sample compliance at high temperature. In addition, the stress values at
20 characteristic points tended to be lower, but the results were also more scattered. The
21 loop area showed very similar results at room temperature and high temperature, in both
22 cases increasing with the loading rate.
23
24

25
26
27 These comments are reflected on the stress and strain curves plotted as a function
28 of time (Figure 7). The stress increased linearly until a maximum point, where the
29 displacement of the fibre reached 1 μm . At this point, the load was held for 5 seconds
30 before unloading. The strain curves show clear signs of residual deformation at the end
31 of the first loading cycle, which are attributed to the pushing-in/out of the carbon fibre
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 under load. The second loading cycle was conducted in a similar way, but in this case
2
3 the maximum deformation reached 2 μm . It must be mentioned that the displacements
4
5 beyond 1.2 μm are affected by the interference between the Berkovich indenter and the
6
7 surrounding material.
8
9

10 The samples tested at high temperature typically required lower loads to reach the
11
12 1 μm displacement, defined as the limit for the first loading cycle, thus the total loading
13
14 time was shorter. The shape of the strain curves at the end of the first loading cycle is
15
16 noteworthy, where the deflection increases rapidly with minimum changes in the stress
17
18 or even during the dwell time at constant stress. In addition, some differences can be
19
20 observed depending on the loading rate and the temperature. The dwell time at
21
22 maximum load is clearly visible for the high loading rate (10 mN/s), as 5 seconds are a
23
24 significant portion of the total duration of the experiment. However, the dwell time is
25
26 relatively short for the experiments conducted at lower loading rates (1 mN/s and 0.1
27
28 mN/s) so these curves are presented separately in Figure 8.
29
30
31
32
33
34

35 The shape of the curves in Figure 8 can be related with the viscoelastic response
36
37 of the polymeric matrix, which is more evident at high loading rates, in which case the
38
39 dwell time takes place before the system reaches equilibrium. On the other hand, the
40
41 response during dwell time is almost linear for the low loading rate (0.1 mN/s),
42
43 reflecting a system closer to equilibrium. In addition, the viscoelastic response during
44
45 dwell time is also affected by temperature. The samples tested at high temperature
46
47 exhibited a much higher compliance compared to the ones tested at room conditions,
48
49 which is attributed to the different response of the polymer below and above the T_g .
50
51
52
53
54
55
56

57 **4. Discussion**

58
59
60
61
62
63
64
65

1 The results presented in the previous section are in agreement with the literature
2 [2, 9, 14-16]. However, the time-dependent response as a function of the loading rate
3 and temperature, as well as the occurrence of push-out events during the dwell time at
4 constant load, are noteworthy (Figure 8a, inset). These phenomena seem to be
5 associated with viscoelastic response of the interface between the carbon fibres and the
6 matrix, or the viscoelastic deformation of the polymer in the immediate vicinity of the
7 tested carbon fibres.
8

9
10
11
12
13
14
15
16
17
18 Jäger et al. [16] studied the influence of plastic deformation on the push-out test
19 of carbon fibre reinforced epoxy. The authors observed a deviation in the force-
20 displacement curve from the linear behaviour, which they attributed to plastic
21 deformation as opposed to crack growth. This remark highlights the different response
22 of polymer-matrix and ceramic-matrix composites [9, 14-16]. The time-dependent or
23 viscoelastic deformation is an important mechanism in polymers, which has been
24 reported in nanoindentation experiments [19, 20].
25
26
27
28
29
30
31
32
33
34

35 High magnification observations of the pushed-out fibres revealed elongated
36 filaments of polymer still attached to the carbon fibres, even after debonding occurred
37 (Figure 9). The filaments rarely formed in the thin sections of polymer between
38 neighbouring fibres, but they were frequently observed in the isles of polymer between
39 3 staggered fibres, which resembles the plastic strain simulations in Ref. [16]. These
40 filaments would continue to resist the displacement of the fibre, even at large strains,
41 with the viscoelastic behaviour characteristic of the polymeric matrix.
42
43
44
45
46
47
48
49
50
51

52 The viscoelastic response of polymers is often described using a Kelvin-Voigt
53 (Eq. 3) [19, 20] or a logarithmic model (Eq. 4) [21, 22]:
54
55

$$\varepsilon(t) = \frac{1}{k} \left(1 - e^{-\frac{t}{\tau}} \right) = \frac{\sigma}{E} \left(1 - e^{-\frac{\eta}{E}t} \right) \quad (3)$$

$$\varepsilon(t) = m_{eff} \ln\left(\frac{t}{\Gamma} + 1\right) \quad (4)$$

where ε is the strain, k is the stiffness parameter related with the stress (σ) and the elastic modulus of the interface (E), and τ is the relaxation time constant associated with the viscosity (η) and the elastic modulus (E) and t is the time, m_{eff} is the strain rate sensitivity and Γ is the creep time.

Table 4 shows a summary of the fitting results, which indicate the prevalence of viscoelasticity in the experiments conducted at high loading rates (1 mN/s and 10 mN/s), whereas the samples tested at lower loading rate (0.1 mN/s) exhibited a more linear response during the dwell time. The values also reflect the higher compliance observed in the high temperature experiments, which can be attributed to the softening and drop in stiffness of the polymeric matrix above T_g . The high modulus observed at short time range and low temperature can be attributed to the deformation of the intermolecular distance, which is a high energy distortion mechanism [23]. On the other hand, the reorientation and translation of the chain segments becomes possible at longer times and higher temperatures, and this relaxation is reflected on the decrease in modulus. Unfortunately, the fitting parameters can only be used as figures of merit at this stage, and further work is needed to obtain a detailed molecular interpretation of these values [24].

It is known that physical ageing can have a marked effect on the viscoelastic properties of polymers below T_g [25]. In our case, the samples were stored at room temperature for over 6 months ($> 15 \times 10^6$ seconds), and the duration of the push-out tests was short in comparison (between 10 and 600 seconds). Therefore, the physical ageing during the tests was negligible and the load-displacement-time curves presented in this article are characteristic of a single aged condition (momentary curves) [26].

1 Mendels et al. [27] reported that the physical ageing of the polymeric matrix had
2
3 no significant influence on the IFS in micro-bond tests, and the observed changes were
4
5 attributed to variations in internal stresses. Greisel et al. [14] conducted push-out tests
6
7 on samples annealed at temperatures above T_g [25], where thermal rejuvenation occurs.
8
9 The change in failure mode, from brittle to ductile, was linked with the relaxation of
10
11 thermal stresses but the ageing time after annealing was not reported. In view of this,
12
13 the effect of physical ageing on the push-out tests may require further study.
14
15
16

17
18 The viscoelastic response has interesting implications for the micro-mechanical
19
20 models that predict the interaction between the carbon fibres and the polymeric matrix.
21
22 In first place, the deviation in the force-displacement curve from the linear behaviour,
23
24 which is often associated with debonding, could occur at different stresses depending on
25
26 the loading conditions, mainly loading rate, holding time and temperature. This region
27
28 dominated by viscoelastic phenomena could be considered an intermediate regime
29
30 between the cohesive and frictional regimes [2].
31
32
33
34

35 In addition, the contribution made by the friction force between debonded regions
36
37 of the carbon fibre and the polymer is likely to be masked by the viscoelastic
38
39 components acting on the bonded areas. A separation of these two components would
40
41 be difficult, unless a complete debonding of the fibre is achieved. Unfortunately, this
42
43 condition was beyond the experimental limitations of the Berkovich indenter used in
44
45 this study. The viscoelastic deformation would also take longer time to recover [19],
46
47 and this should be taken into account when assessing the dissipative and non-dissipative
48
49 mechanisms [16].
50
51
52
53

54 Finally, the surface treatment of the carbon fibres may alter the mechanical
55
56 properties of the interface material and the thickness of the interface, thus affecting its
57
58
59
60
61
62
63
64
65

1 viscoelastic response. Battisti et al. [28] reported an increase in the interlaminar shear
2 strength when multi-wall carbon nanotubes (MWCNTs) were grafted on the carbon
3 fibres, despite the lack of interaction between the MWCNTs and the carbon fibres.
4
5 Therefore, it is speculated that the deviation in the force-displacement curve from the
6 linear behaviour observed after some surface treatments could be related with changes
7
8 in viscoelastic response of the polymer around the fibres, instead of the IFS. This
9
10 phenomenon could reveal new strengthening and toughening strategies for composite
11 materials [15, 29].
12
13
14
15
16
17
18
19
20
21
22

23 **5. Conclusions**

24
25 The push-out tests conducted on carbon fibre reinforced epoxy using different
26 loading rates and testing temperatures revealed the following conclusions:
27

- 28 - It was possible to push-out single carbon fibres from the matrix with a Berkovich
29 indenter under different loading rates and temperatures (below and above T_g).
30
- 31 - The deviation in the force-displacement curve from the linear behaviour, which is
32 often associated with debonding, could occur at different stresses depending on the
33 loading conditions, mainly loading rate, holding time and temperature.
34
- 35 - The interfacial strength (IFS) and stiffness increased with increasing loading rate and
36 decreased with increasing temperature.
37
- 38 - A time-dependent response was observed in all cases but was more noticeable in the
39 experiments conducted at high loading rate or at high temperature. The behaviour
40 could be described with simple viscoelastic models.
41
42
43
44
45
46
47
48
49
50
51
52
53

54 The viscoelastic response has interesting implications for the micro-mechanical
55 models that predict the interaction between the carbon fibres and the polymeric matrix.
56
57
58
59
60
61
62
63
64
65

1 This phenomenon could reveal new strengthening and toughening strategies for
2
3 composite materials.
4
5
6
7

8 **Acknowledgements** 9

10 The research leading to these results has received funding from the European
11 Union (GA604248 & GA685844). SCG would like to thank Alan Riley, from Toray
12 International UK Ltd, for providing samples of RebarS12.
13
14
15
16
17
18
19

20 **References** 21

- 22
23 [1] Karger-Kocsis J, Mahmood H, Pegoretti A. Recent advances in fiber/matrix
24 interphase engineering for polymer composites. Prog Mater Sci. 2015;73:1-43.
25
26
27
28 [2] Esqué-de los Ojos D, Ghisleni R, Battisti A, Mohanty G, Michler J, Sort J, et al.
29 Understanding the mechanical behavior of fiber/matrix interfaces during push-in
30 tests by means of finite element simulations and a cohesive zone model. Comp Mater
31 Sci. 2016;117:330-337.
32
33
34
35
36
37
38 [3] Kabel J, Hosemann P, Zayachuk Y, Armstrong DEJ, Koyanagi T, Katoh Y, et al.
39 Ceramic composites: A review of toughening mechanisms and demonstration of
40 micropillar compression for interface property extraction. J Mater Res.
41 2018;33(4):424-439.
42
43
44
45
46
47
48
49 [4] Zhandarov S, Mäder E. Characterization of fiber/matrix interface strength:
50 Applicability of different tests, approaches and parameters. Compos Sci Technol.
51 2005;65(1):149-160.
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [5] Sockalingam S, Nilakantan G. Fiber-matrix interface characterization through the
2
3 microbond test: A review. *Int J Aeronaut Space*. 2012;13(3):282-295.
4
5
6
- 7 [6] Zhandarov S, Mäder E. Indirect estimation of fiber/polymer bond strength and
8
9 interfacial friction from maximum load values recorded in the microbond and pull-
10
11 out tests. Part II: Critical energy release rate. *J Adhes Sci Technol*. 2003;17(7):967-
12
13 980.
14
15
16
- 17 [7] Zhandarov SF, Mäder E, Yurkevich OR. Indirect estimation of fiber/polymer bond
18
19 strength and interfacial friction from maximum load values recorded in the
20
21 microbond and pull-out tests. Part I: Local bond strength. *J Adhes Sci Technol*.
22
23 2002;16(9):1171-1200.
24
25
26
- 27 [8] Sha JJ, Dai JX, Li J, Wei ZQ, Hausherr JM, Krenkel W. Measurement and analysis
28
29 of fiber-matrix interface strength of carbon fiber-reinforced phenolic resin matrix
30
31 composites. *J Compos Mater*. 2014;48(11):1303-1311.
32
33
34
35
36
- 37 [9] Mueller WM, Moosburger-Will J, Sause MGR, Horn S. Microscopic analysis of
38
39 single-fiber push-out tests on ceramic matrix composites performed with Berkovich
40
41 and flat-end indenter and evaluation of interfacial fracture toughness. *J Eur Ceram
42
43 Soc*. 2013;33(2):441-451.
44
45
46
- 47 [10] Andersons J, Joffe R, Hojo M, Ochiai S. Fibre fragment distribution in a single-
48
49 fibre composite tension test. *Compos Part B-Eng*. 2001;32(4):323-332.
50
51
52
53
- 54 [11] Huang Y, Young RJ. Analysis of the fragmentation test for carbon-fibre/epoxy
55
56 model composites by means of Raman spectroscopy. *Compos Sci Technol*.
57
58 1994;52(4):505-517.
59
60
61
62
63
64
65

- 1 [12] Paipetis A, Galiotis C. Modelling the stress-transfer efficiency of carbon-epoxy
2
3 interfaces. P R Soc A. 2001;457(2011):1555-1577.
4
5
6
- 7 [13] Pisanova E, Zhandarov S, Mäder E. How can adhesion be determined from
8
9 micromechanical tests? Compos Part A-Appl S. 2001;32(3-4):425-434.
10
11
12
- 13 [14] Greisel M, Jäger J, Moosburger-Will J, Sause MGR, Mueller WM, Horn S.
14
15 Influence of residual thermal stress in carbon fiber-reinforced thermoplastic
16
17 composites on interfacial fracture toughness evaluated by cyclic single-fiber push-out
18
19 tests. Compos Part A-Appl S. 2014;66:117-127.
20
21
22
- 23 [15] Mueller WM, Moosburger-Will J, Sause MGR, Greisel M, Horn S. Quantification
24
25 of crack area in ceramic matrix composites at single-fiber push-out testing and
26
27 influence of pyrocarbon fiber coating thickness on interfacial fracture toughness. J
28
29 Eur Ceram Soc. 2015;35(11):2981-2989.
30
31
32
- 33 [16] Jäger J, Sause MGR, Burkert F, Moosburger-Will J, Greisel M, Horn S. Influence
34
35 of plastic deformation on single-fiber push-out tests of carbon fiber reinforced epoxy
36
37 resin. Compos Part A-Appl S. 2015;71:157-167.
38
39
40
41
- 42 [17] ASTM E1356 Standard Test Method for Assignment of the Glass Transition
43
44 Temperatures by Differential Scanning Calorimetry; 2014.
45
46
47
- 48 [18] Medina CM, Molina-Aldareguía JM, González C, Flores P, Llorca J. Comparison
49
50 of push-in and push-out tests for measuring interfacial shear strength in nano-
51
52 reinforced composite materials. J Compos Mater. 2016;50(12):1651-1659.
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1 [19] Yang S, Zhang Y-W, Zeng K. Analysis of nanoindentation creep for polymeric
2 materials. *J Appl Phys.* 2004;95(7):3655-3666.
3
4
5
6
7 [20] Gibson RF. A review of recent research on nanoindentation of polymer composites
8 and their constituents. *Compos Sci Technol.* 2014;105:51-65.
9
10
11
12 [21] Chen J, Bell GA, Dong H, Smith JF, Beake BD. A study of low temperature
13 mechanical properties and creep behaviour of polypropylene using a new sub-
14 ambient temperature nanoindentation test platform. *J Phys D Appl Phys.*
15 2010;43(42):425404.
16
17
18
19
20
21
22
23 [22] Beake BD. Modelling indentation creep of polymers: a phenomenological
24 approach. *J Phys D Appl Phys.* 2006;39(20):4478.
25
26
27
28
29 [23] Shaw MT, MacKnight WJ. Introduction to polymer viscoelasticity. 3rd ed. USA:
30 Wiley Interscience; 2005.
31
32
33
34
35 [24] Fischer-Cripps AC. A simple phenomenological approach to nanoindentation
36 creep. *Mat Sci Eng A.* 2004;385(1):74-82.
37
38
39
40
41 [25] Odegard GM, Bandyopadhyay A. Physical aging of epoxy polymers and their
42 composites. *J Polym Sci Pol Phys.* 2011;49(24):1695-1716.
43
44
45
46
47 [26] Struik LCE. Physical aging in plastics and other glassy materials. *Polym Eng Sci.*
48 1977;17(3):165-173.
49
50
51
52
53 [27] Mendels D-A, Leterrier Y, Manson J-AE, Nairn JA. The Influence of Internal
54 Stresses on the Microbond Test II: Physical Aging and Adhesion. *J Compos Mater.*
55 2002;36(14):1655-1676.
56
57
58
59
60
61
62
63
64
65

1 [28] Battisti A, Esqué-de los Ojos D, Ghisleni R, Brunner AJ. Single fiber push-out
2
3 characterization of interfacial properties of hierarchical CNT-carbon fiber
4
5 composites prepared by electrophoretic deposition. *Compos Sci Technol.*
6
7
8 2014;95:121-127.
9

10
11 [29] Moosburger-Will J, Jäger J, Strauch J, Bauer M, Strobl S, Linscheid FF, et al.
12
13 Interphase formation and fiber matrix adhesion in carbon fiber reinforced epoxy
14
15 resin: influence of carbon fiber surface chemistry. *Compos Interface.*
16
17
18 2017;24(7):691-710.
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 **Figure captions**
2

3 Figure 1: Macrographs of the Rebar S12 samples: a) Discs extracted from the rod and b)
4
5 thin specimen on a spatula, during the final stage of preparation.
6
7

8 Figure 2: Differential scanning calorimetry (DSC) curve of Rebar S12.
9

10 Figure 3: Schematic diagram of the experimental set-up used for the push-out tests.
11

12 Figure 4: SEM micrographs of a specimen after the push-out tests: a) front side
13
14 (pushed-in) and b) back side (pushed-out) of the specimen.
15
16
17

18 Figure 5: AFM observations of a specimen after the push-out test: a) 3D image of the
19
20 pushed-out fibre and b) cross section profile of the same fibre.
21
22

23 Figure 6: Typical load-displacement curve of the push-out tests. The arrows indicate the
24
25 loading direction and the inset corresponds to the displacement during the
26
27 dwell time at constant load (region 4).
28
29

30 Figure 7: Strain-time (solid) and stress-time (dash) curves obtained with different
31
32 loading rates and temperatures.
33
34

35 Figure 8: Strain-time curves at dwell time (constant load) obtained with different
36
37 loading rates and temperatures. The graphs show the strain relative to the
38
39 deformation at the beginning of the dwell time. The fitted exponential (dot
40
41 line) and logarithmic (dash line) curves are superimposed to the experimental
42
43 data.
44
45
46

47 Figure 9: High magnification SEM micrograph of a pushed-out fibre.
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Tables

Table 1: Nominal mechanical properties of Rebar S12 from specification sheet.

Material	Young's modulus	Tensile strength	Strain at break	Shear strength	Rod diameter	Volume fraction of fibres
Rebar S12	150 GPa	> 1900 MPa	> 1.30%	200 MPa	12 mm	70%

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Table 2: Loading conditions used for the push-out tests.

Mode	Number of cycles	Displacement per cycle	Maximum load	Loading rate	Dwell time	Unloading rate
Multiple cycles, depth controlled	2	1 μm	200 mN	0.1 mN/s	5 s	0.1 mN/s
				1.0 mN/s		1.0 mN/s
				10 mN/s		10 mN/s

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

Table 3: Summary of results from push-out tests. The reference points correspond to Figure 6.

Loading rate	Stress at point 1 [MPa]	Strain at point 1 []	Slope of linear section 2 [mN / nm]	Stress at point 3 [MPa]	Strain at point 3 []	Maximum stress in Cycle 1 (point 4) [MPa]	Maximum strain in Cycle 1 (point 4) []	Loop area (5) [μ J]
RT 0.1	7.2 ± 1.2	0.007 ± 0.001	35.1 ± 3.5	30.5 ± 3.9	0.021 ± 0.002	39.3 ± 5.4	0.032 ± 0.001	0.80 ± 0.23
RT 1	9.9 ± 1.9	0.009 ± 0.003	39.9 ± 5.4	40.5 ± 6.1	0.025 ± 0.005	53.6 ± 8.0	0.041 ± 0.008	1.30 ± 0.38
RT 10	9.7 ± 1.4	0.008 ± 0.001	40.2 ± 3.9	42.9 ± 1.9	0.023 ± 0.003	52.2 ± 2.7	0.035 ± 0.001	2.84 ± 0.41
HT 0.1	2.8 ± 3.0	0.004 ± 0.004	19.6 ± 4.4	27.2 ± 9.2	0.030 ± 0.005	40.5 ± 12.9	0.054 ± 0.003	0.38 ± 0.14
HT 1	7.3 ± 1.2	0.009 ± 0.002	29.9 ± 3.0	40.9 ± 4.7	0.033 ± 0.005	52.3 ± 4.6	0.050 ± 0.001	1.65 ± 0.22
HT 10	7.4 ± 2.4	0.009 ± 0.002	27.4 ± 4.6	41.9 ± 9.4	0.036 ± 0.006	51.0 ± 8.4	0.048 ± 0.004	2.51 ± 0.86

RT: room temperature (24°C); HT: High temperature (125°C)

Table 4: Fitting parameters from Kelvin-Voigt and logarithmic models.

Loading rate	Kelvin-Voigt model				Logarithmic model			
	Room temperature		High temperature		Room temperature		High temperature	
	k	τ	k	τ	m_{eff}	Γ	m_{eff}	Γ
0.1 mN/s	635	3.30	216	6.60	0.09%	1.57	0.33%	4.57
1 mN/s	116	1.50	78	1.45	0.33%	0.23	0.45%	0.29
10 mN/s	80	1.30	70	1.60	0.42%	0.38	0.52%	0.35

Figure 01

[Click here to download high resolution image](#)

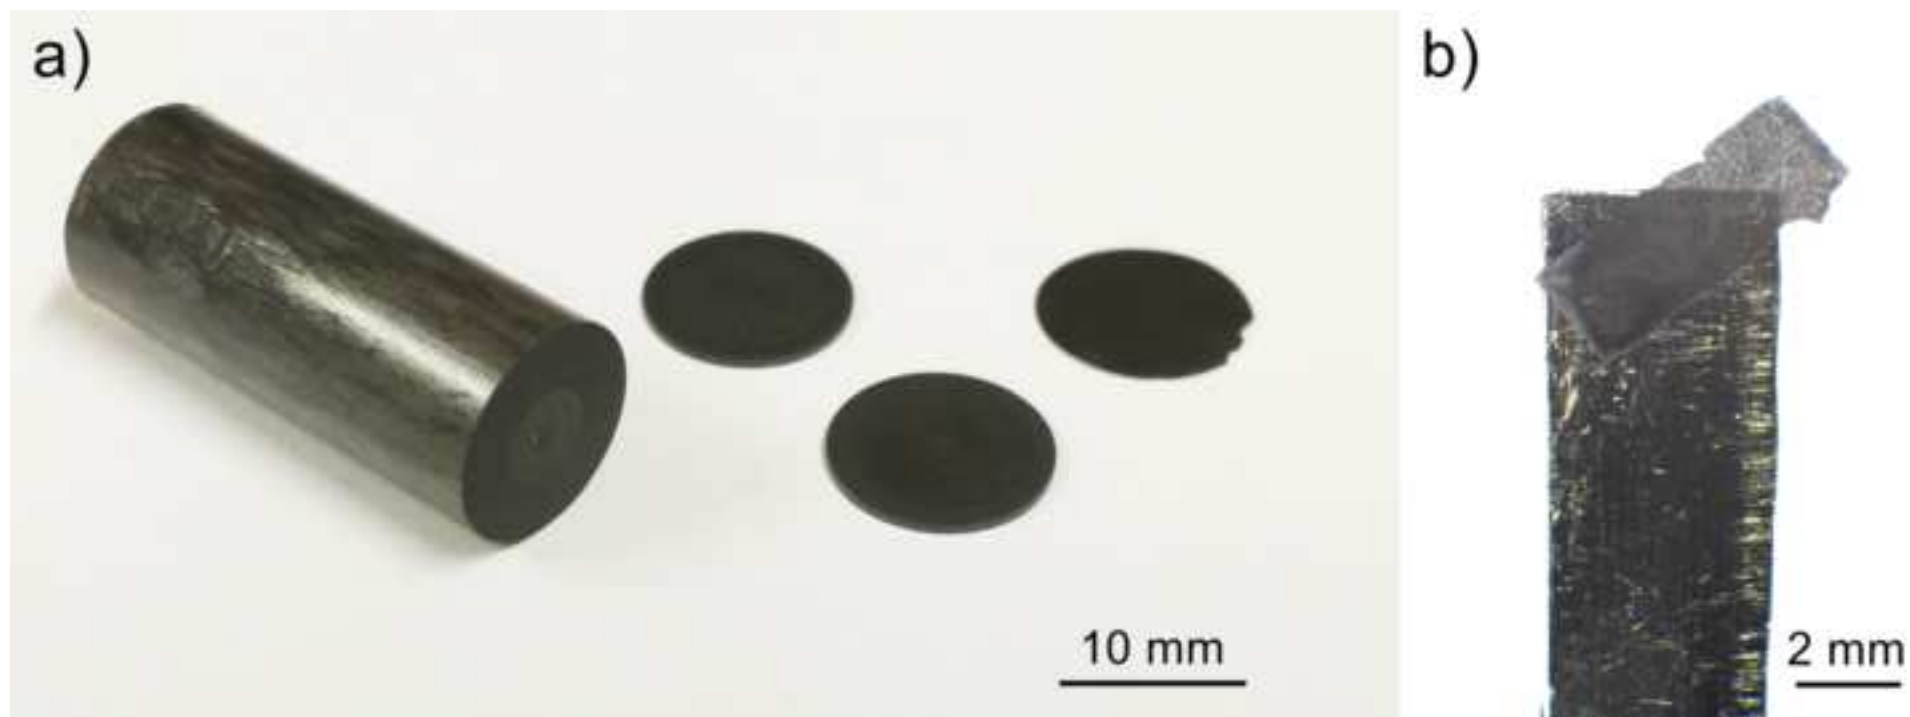


Figure 02
[Click here to download high resolution image](#)

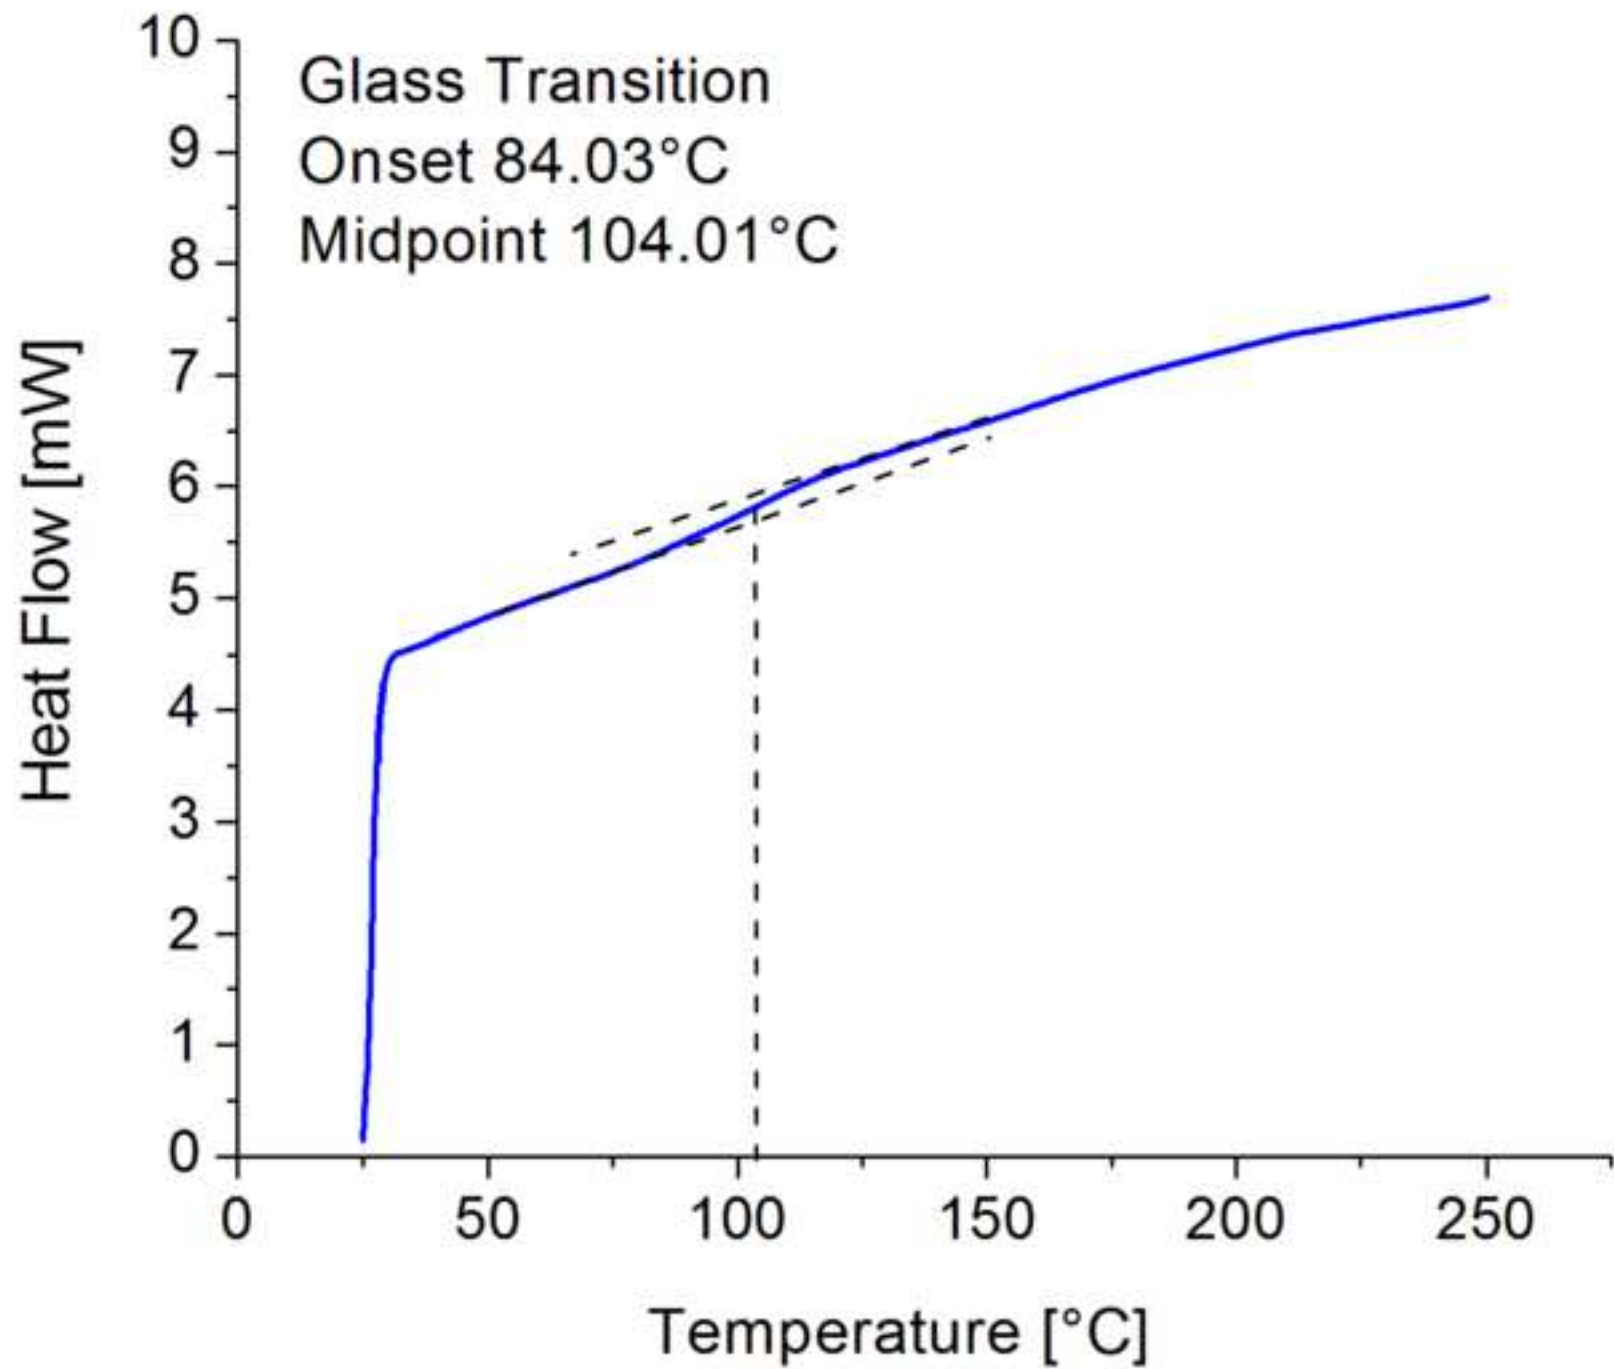


Figure 03
[Click here to download high resolution image](#)

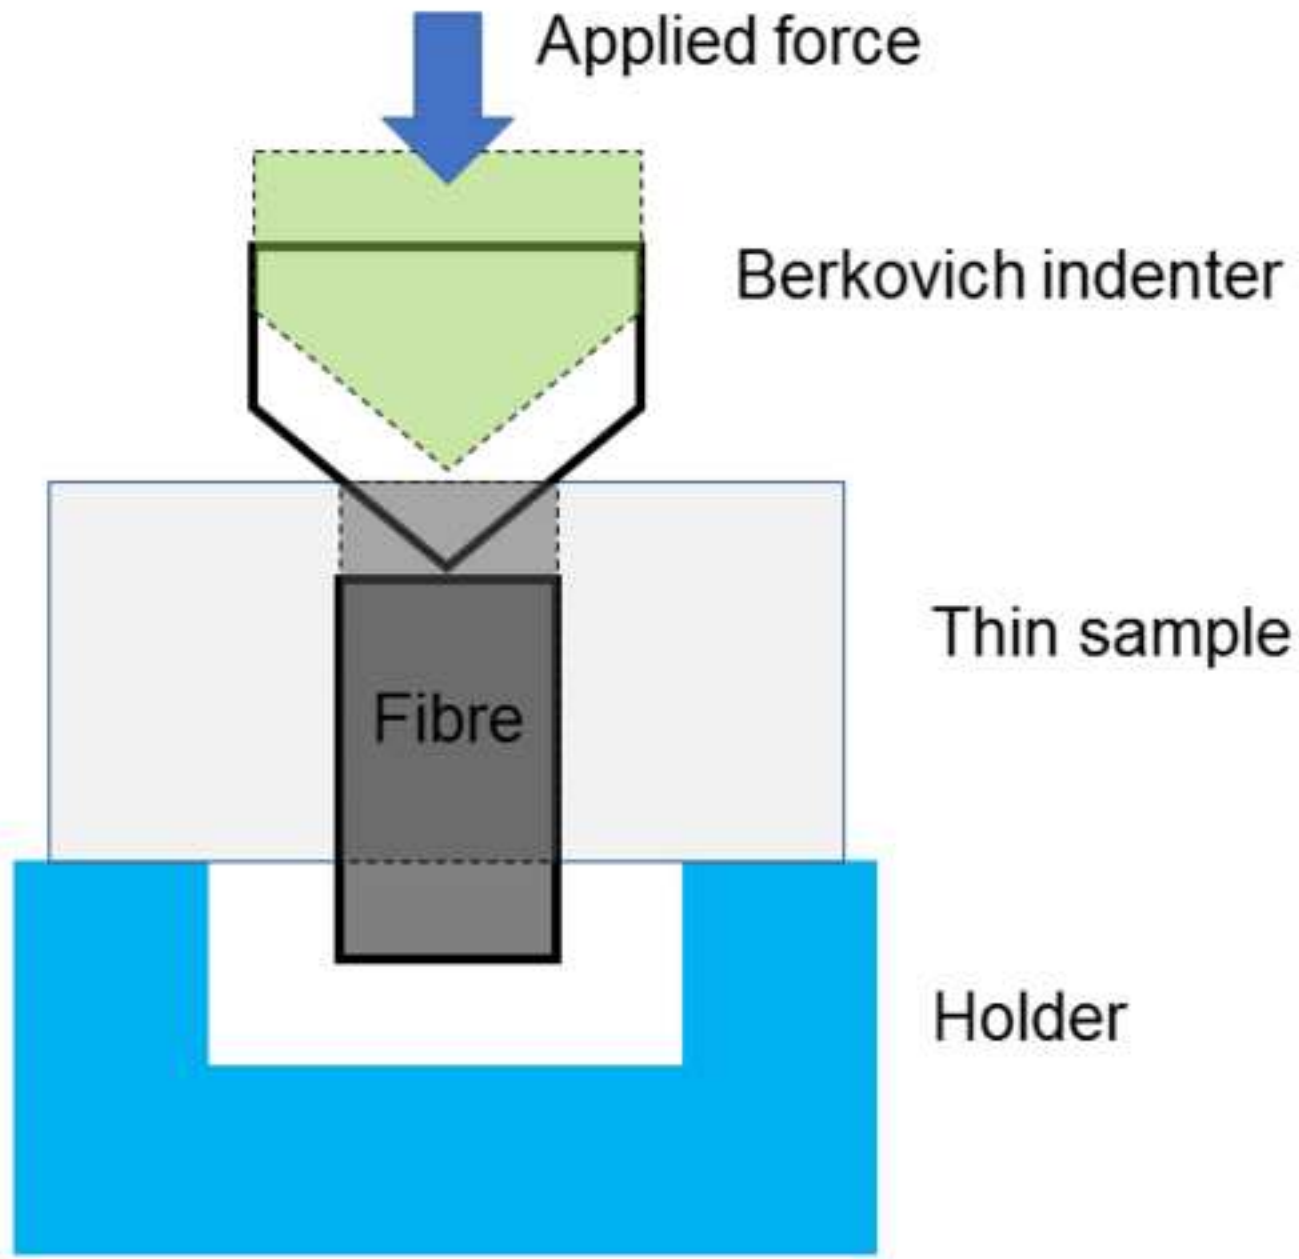


Figure 04

[Click here to download high resolution image](#)

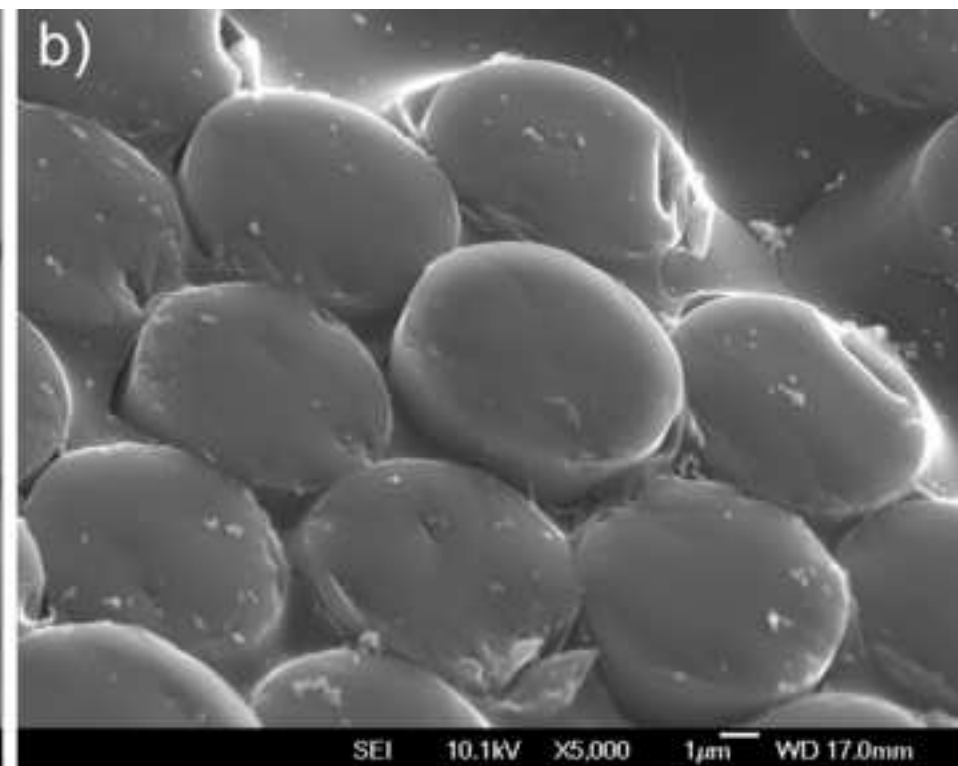
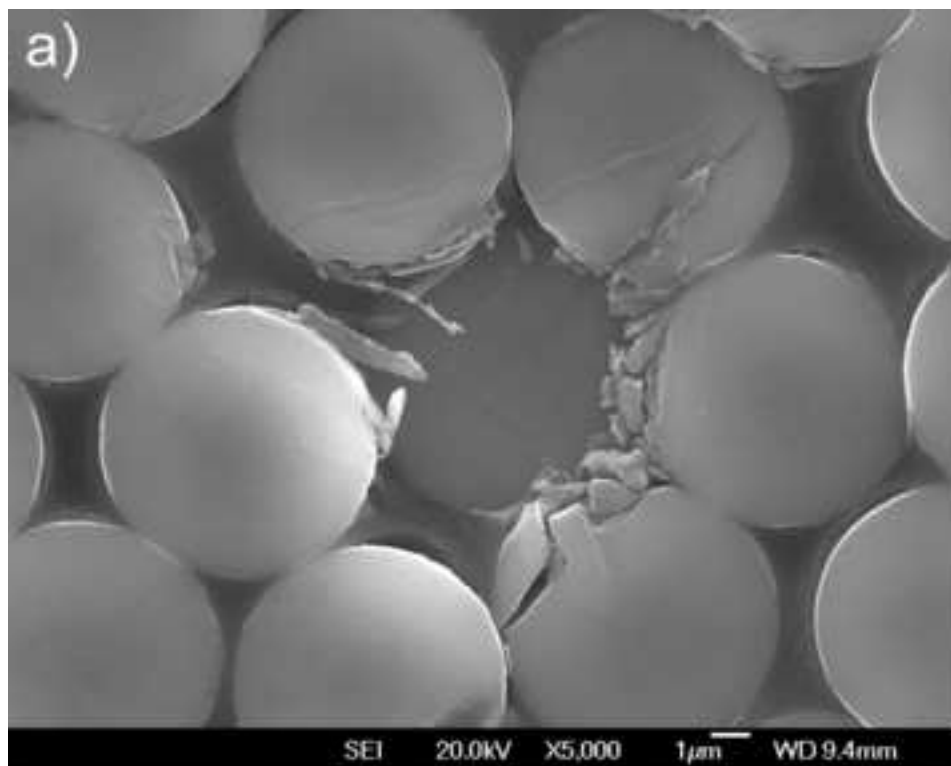


Figure 05

[Click here to download high resolution image](#)

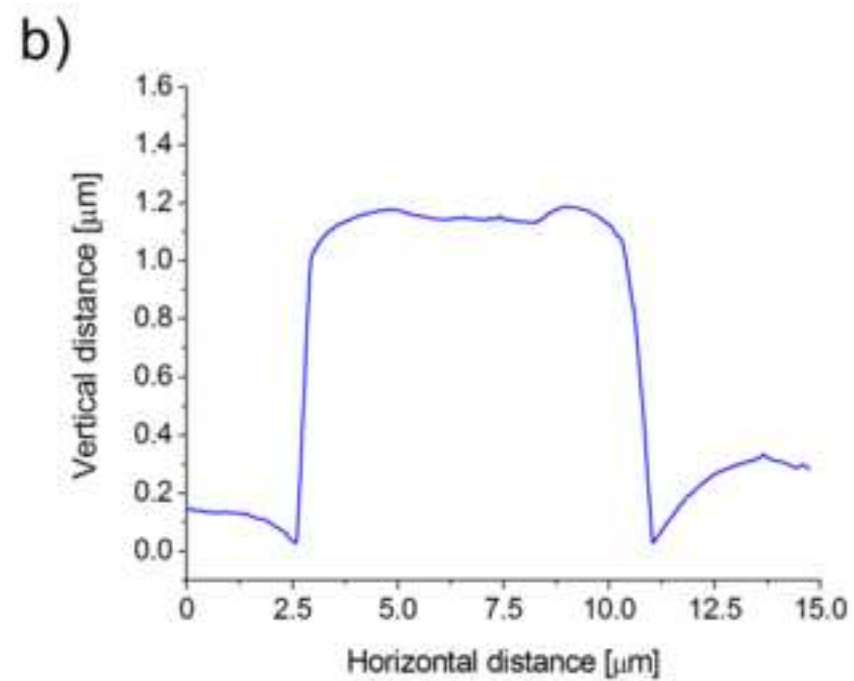
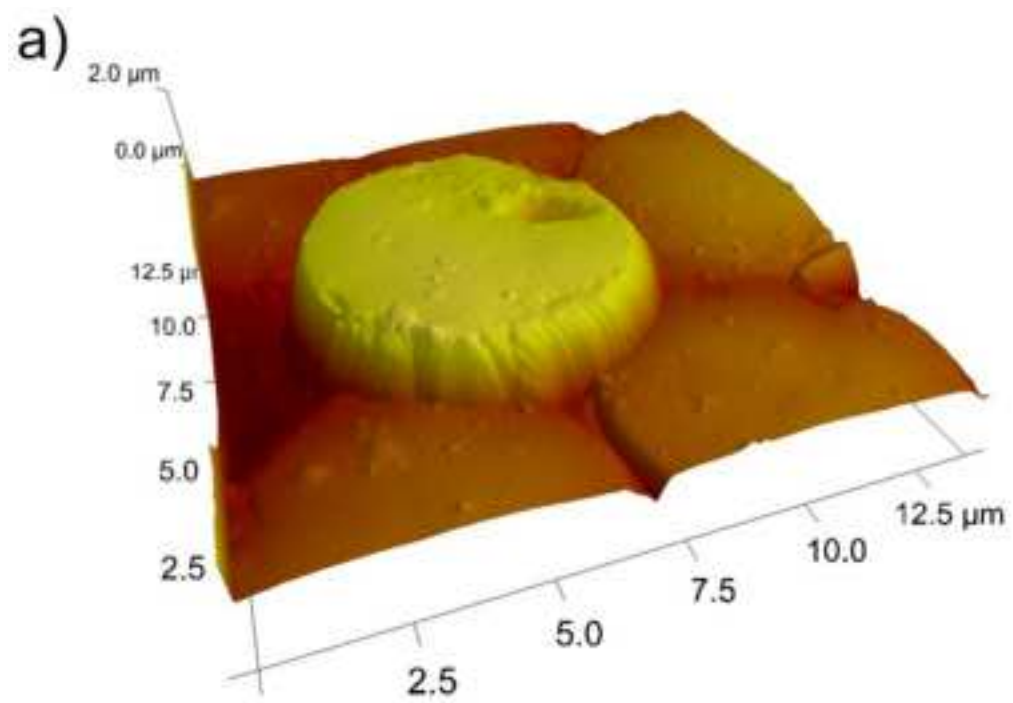


Figure 06
[Click here to download high resolution image](#)

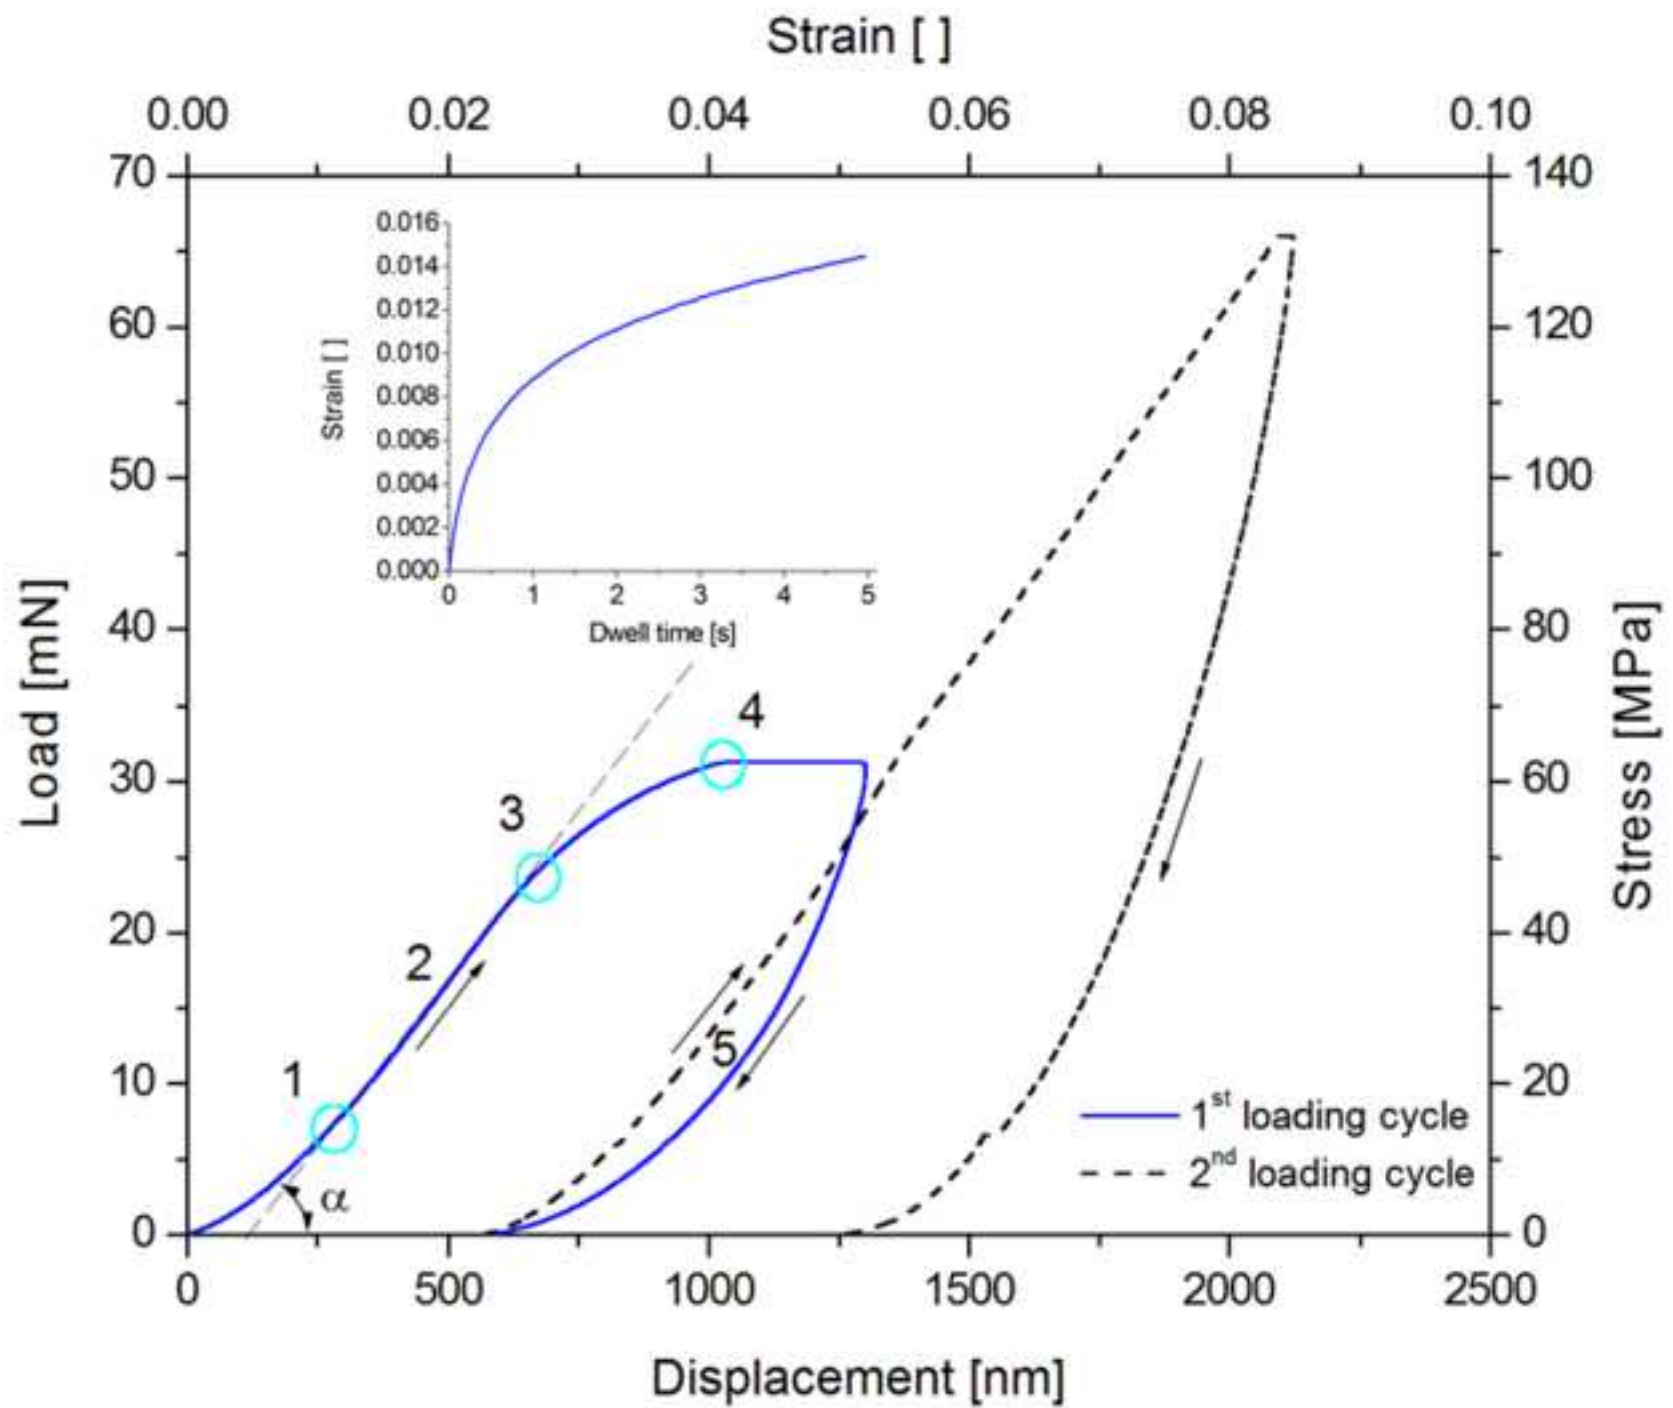


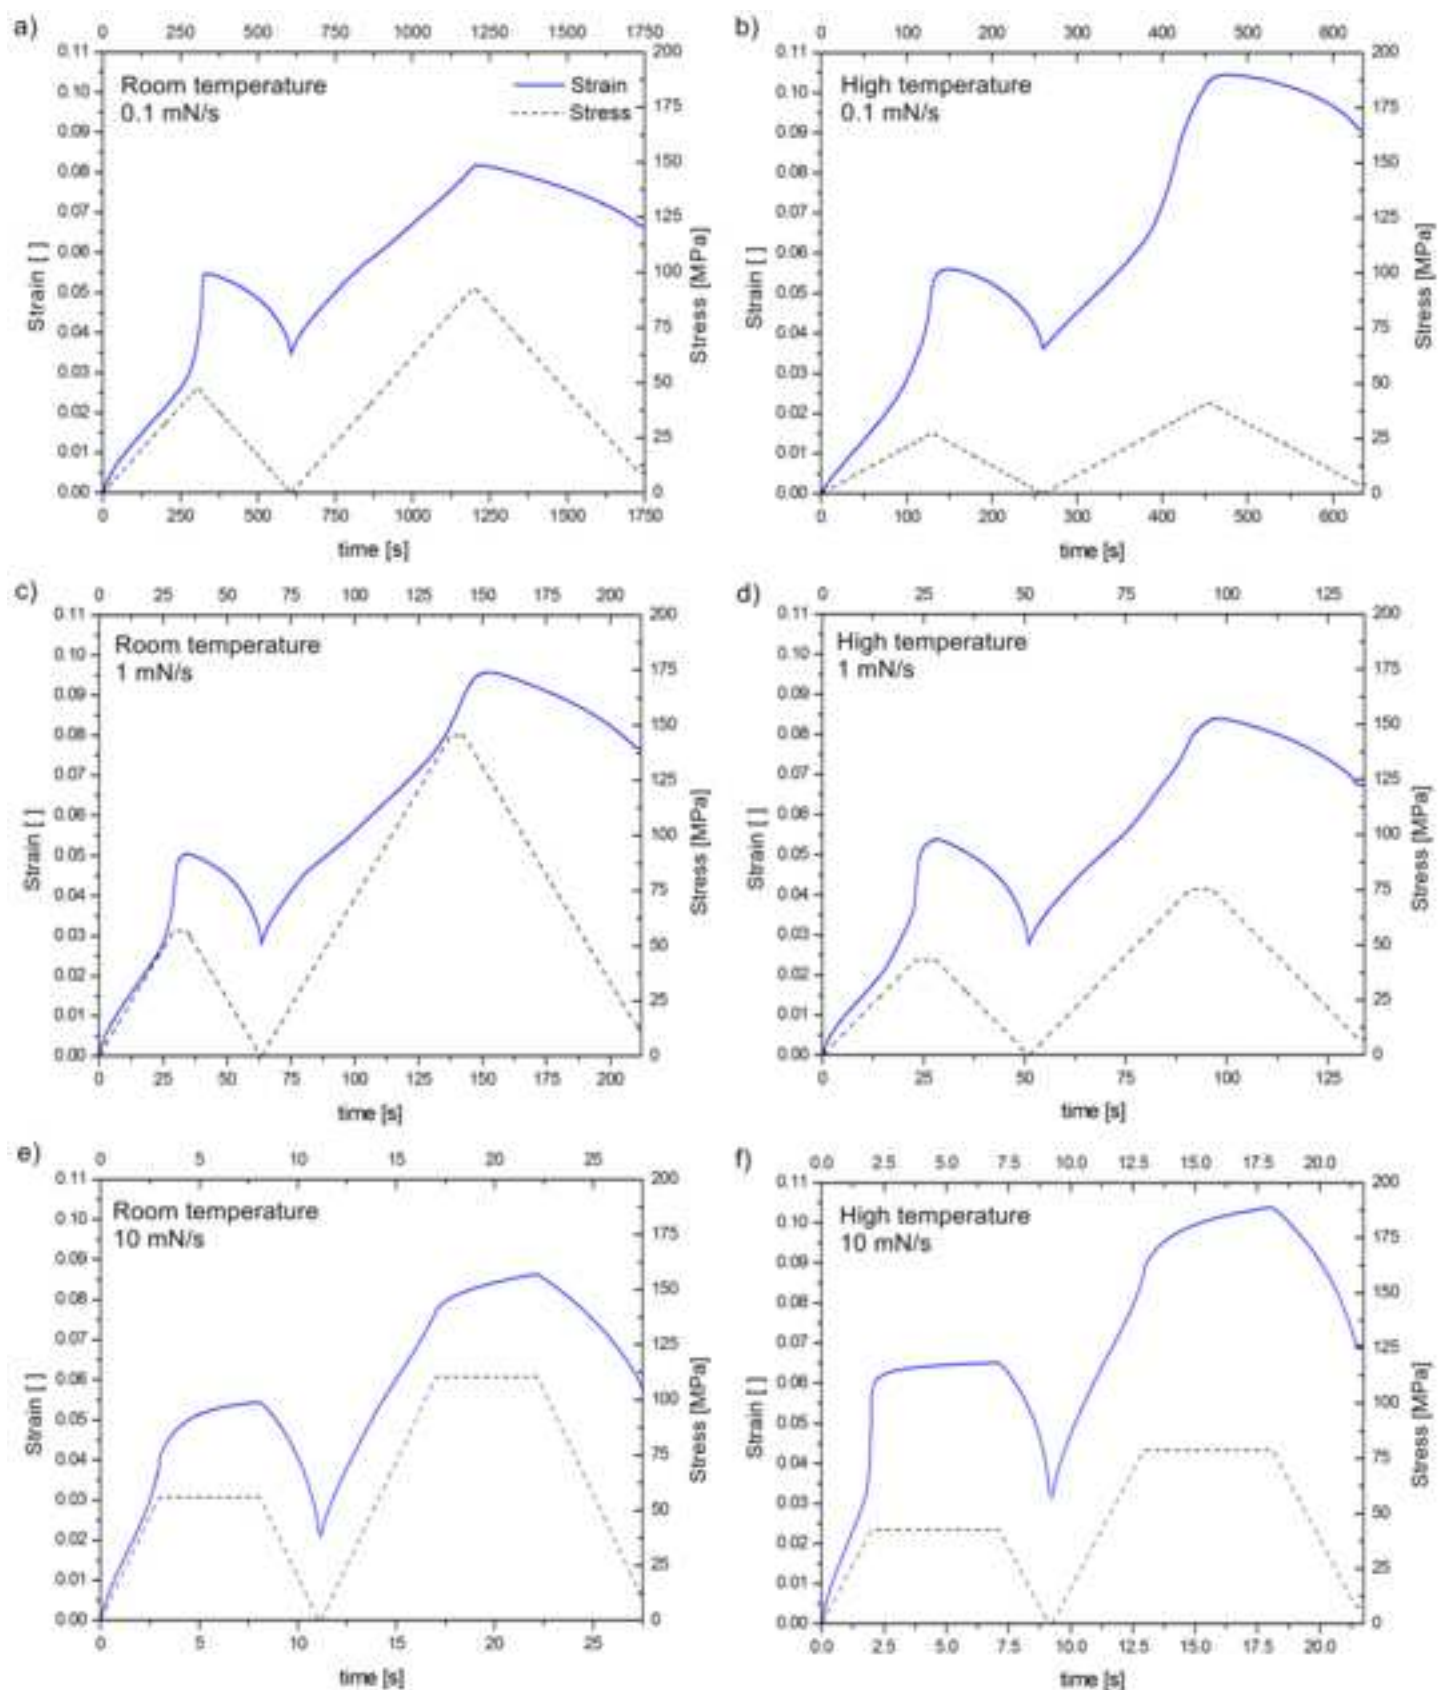
Figure 07[Click here to download high resolution image](#)

Figure 08

[Click here to download high resolution image](#)

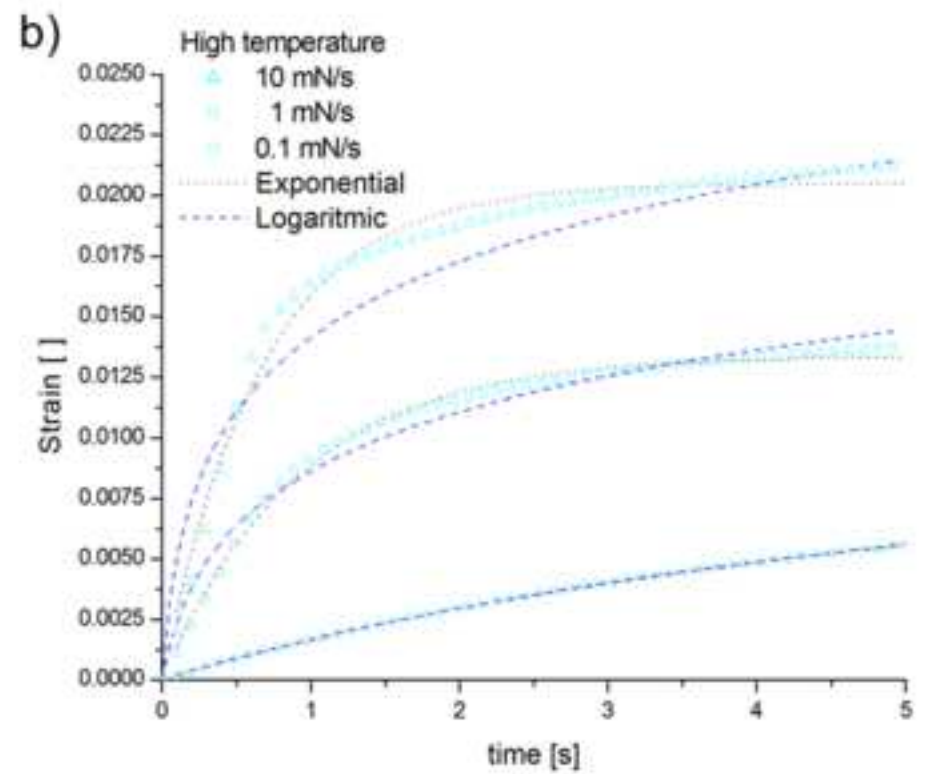
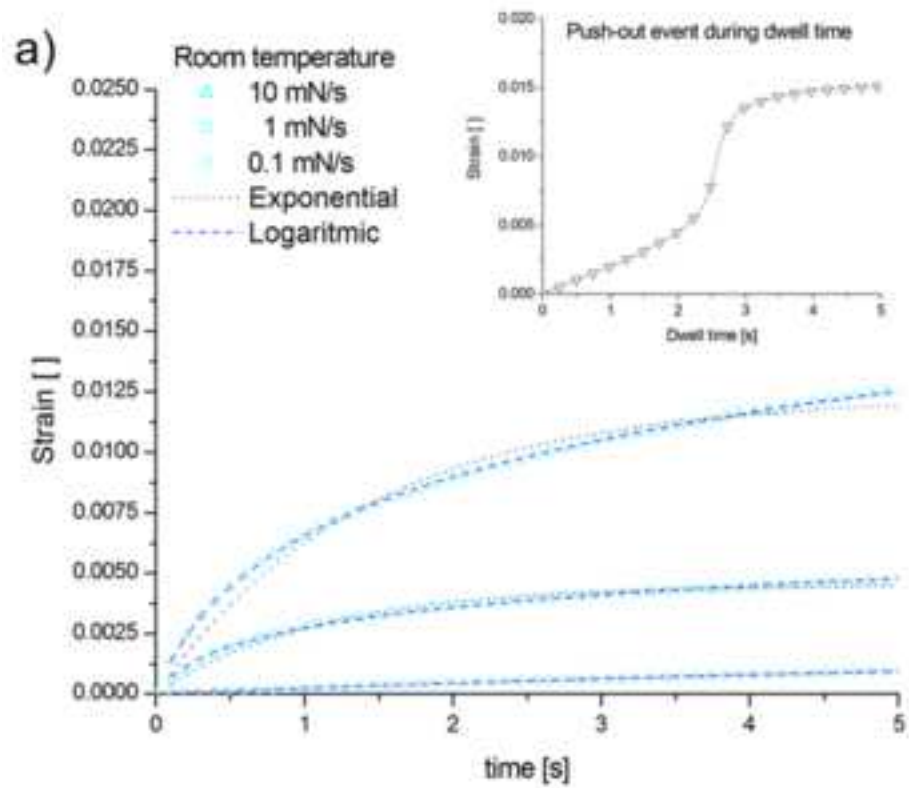


Figure 09

[Click here to download high resolution image](#)

