



# PAM Review

Subject 68412 [www.uts.edu.au](http://www.uts.edu.au)

## Impact of Nanofluids and Specific Frequency Absorbers in Parabolic Trough Collector Solar Furnaces

Genevieve Geehan <sup>1,\*</sup>, Ritika Ritika <sup>2</sup> and Coen Winchester <sup>3</sup>

University of Technology Sydney, Faculty of Science, PO Box 123, Ultimo NSW 2017, Australia

<sup>1</sup> [genevieve.geehan@student.uts.edu.au](mailto:genevieve.geehan@student.uts.edu.au)

<sup>2</sup> [ritika.ritika@student.uts.edu.au](mailto:ritika.ritika@student.uts.edu.au)

<sup>3</sup> [coen.s.winchester@student.uts.edu.au](mailto:coen.s.winchester@student.uts.edu.au)

\* Author to whom correspondence should be addressed.

DOI: <http://dx.doi.org/10.5130/pamr.v5i0.1502>

### **1: Abstract**

This meta-study aims to identify methods of optimising efficiency of upcoming parabolic trough collector (PTC) solar furnace technology by analysing thermodynamic properties of both: solar absorbers SiC, Pyromark 2500, Polychromic Al-AlN and C54-TiSi<sub>2</sub> nanoparticles; and heat transfer nanofluids SiO<sub>2</sub>, TiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, Cu and Al<sub>2</sub>O<sub>3</sub>-Cu with a 50:50 ratio. The thermodynamic properties investigated are energy absorbance and emittance, melting point, thermal conductivity and viscosity. Our study revealed that the optimal transfer fluid is the hybrid nanofluid Al<sub>2</sub>O<sub>3</sub>-Cu of 50:50 ratio with a 1-2% volume fraction in an ethylene glycol base. The optimal solar absorber for use in combination with this nanofluid was found to be polychromic Al-AlN cermet absorber.

**Keywords:** Parabolic trough collector; solar power; nanofluids; nanoparticles; high absorption materials; meta-analysis



Copyright 2018 by the authors. This is an Open Access article distributed under the terms of the Creative Commons Attribution 4.0 Unported (CC BY 4.0) License (<https://creativecommons.org/licenses/by/4.0/>), allowing third parties to copy and redistribute the material in any medium or format and to remix, transform, and build upon the material for any purpose, even commercially, provided the original work is properly cited and states its license.  
**Citation:** Geehan, G., Ritika, R. and Winchester, C. 2018. Impact of Nanofluids and Specific Frequency Absorbers in Parabolic Trough Collector Solar Furnaces. *PAM Review: Energy Science & Technology*, Vol. 5, pp. 89-103. <http://dx.doi.org/10.5130/pamr.v5i0.1502>

**PAM Review is a UTS ePRESS Student Journal showcasing outstanding student works.**

### Nomenclature

$\eta$ : viscosity	$Q_u$ : Useful Energy
Nu: Nusselt Number	$Q_s$ : Available Energy
k: Thermal Conductivity	h: Convection Coefficient
D: Pipe Diameter	Pr: Prandtl number
A: cross sectional area for heat transfer	<i>nf</i> : nanofluids
m: mass flow rate	<i>bf</i> : basefluids
$\Delta T$ : Temperature at heat transfer boundary	<i>p</i> : nanoparticle

## 2: Introduction

Due to the increasing demand for reliable and renewable energy sources, higher efficiency power generation technology is essential to meet increasing electrical energy requirements. Solar energy is one of the most abundant sources of renewable energy available on earth, with areas in Africa, America, Asia and Australia commonly receiving upwards of 7 kilowatt hours per square meter of direct normal irradiation per day [1]. Taking advantages of this energy has been the focus of countless technological advancements since the industrial revolution and continues to be one of the most popular fields of research to date.

An advancing technology in the harnessing of solar power is the Parabolic Trough Collector (PTC). In this system, solar radiation is reflected by a parabolic mirror onto the surface of the absorber tube as shown in Figure 1. A transfer fluid within the tube then absorbs the heat conducted through the surface of the tube. Modern PTCs use a variety of transfer fluids, such as molten salts with high specific heat capacity, synthetic oils with low viscosity, and aqueous solutions that carry heat utilising evaporative techniques [2]. This transfer fluid then transports generated heat to an engine which produces electricity.

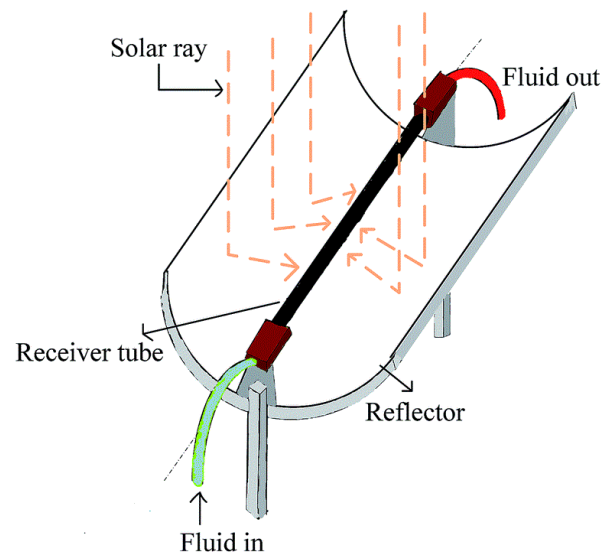


Figure 1. Design of the pipe & mirror components of a parabolic trough collector. Credit to Soroush Dabiri (Dabiri, Rahimi 2016, 3<sup>rd</sup> International Conference and Exhibition on Solar Technology)

The particular component of the system that this paper will be focusing on is the tube system. Despite the simplicity of the core concept, advanced technologies can be applied to these systems that drastically increase their efficiency. These technologies come from fields such as nanomaterials, photonics, optics and advanced materials. This meta-analysis focuses on the potential improvements that can be made to the tube system using advanced black body and specific frequency absorption coatings and nanofluid-enhanced transfer fluids. Advanced absorbers are investigated as they have become increasingly popular over the last few years and, as a result, have experienced substantial improvements to the feasibility and efficiency [3]. For similar reasons, nanofluid based non-evaporative PTC systems have been analysed. Advancements in nanomaterial synthesis processes have facilitated study in a wide variety of nanofluid applications, thus over time research has shown that nanofluids are better heat carriers than normal heat transfer fluids [4].

This meta-analysis aims to collate a wide variety of data on recent advancements in the fields of advanced absorbers and nanofluids. These advancements are assessed and discussed in relation to the properties that make them useful in PTC. The information found is used to summarise recent advancements in PTC research. Additionally, the information is combined with thermodynamic principles in order to propose a combination of new technologies that could be used to construct an optimally efficient solar collection, transformation and transport system.

### **3: Methodology**

This meta-analysis was conducted using research that investigates the properties of two components of the PTC system: the absorbers used to convert sunlight into heat, and the thermal fluids used to transport that heat. The results of each study were collated in respect to their component of focus so that broad and reliable figures could be drawn for conclusions. These figures were then used to propose the properties of an ideal PTC design. For the sake of validity, only papers from the last ten years were used as sources and papers with little to no recorded citations for the duration of their availability were excluded.

## PAM Review 2018

Papers were drawn from multiple scientific databases. These were: Science Direct (Elsevier), The Journal of Applied Physics, Research Gate, Springer Link, and the American Institute of Physics. Some statistics, constants and designs were also drawn from industrial databases such as The World Bank's solar research program, Solargis, and Tempil temperature indication technologies. These sources have been chosen as the cited parties would likely be involved in the development and distribution of the technology examined in this meta-analysis.

The scope of this meta-analysis has been limited to strictly thermodynamic perspectives for the ease of the reader. Social, political, cultural, economic and logistical perspectives have not been formally assessed, as these aspects are either too problematic or nuanced to be commented on by non-field-experts. The thermodynamic perspective has been chosen primarily in order to assess the ideal and achievable efficiencies of PTC systems by analysing the properties of their individual components and the thermal interactions between them.

When collecting and using data, various similar experimental results were sampled and averaged to provide more practically expectable results. Equations and data (from figures) were also taken from reputable papers and used to calculate required values and create original figures for analysis. This data includes specific heat capacities, thermal conductivity, density, emissivity, viscosity, optimal operating temperature, and boiling point. Using this data, the thermal properties of the PTC pipe system were modelled based on our interpreted superior materials and properties. As this meta-analysis focuses on the pipe system only, the attached solar furnace and respective engine efficiency. Instead the system was modelled with focus on its ability to retain heat. This model incorporated thermal radiation and heat transfer theories and equations to describe the processes the energy generated by this system undergo.

## **4: Results**

### **4.1: High Absorption Coatings**

Black body absorbers and selective frequency absorbers were studied to assess the efficiency of precision absorption bandwidths compared to standard black body absorption techniques. These absorbers take the form of layered materials that can be used to treat a surface and nanoparticles that are grown on a substrate. Many absorbers were researched for this meta-analysis, but only four were selected to be analysed in relation to the rest of the system. These absorbers are Silicon Carbonate, Pyromark 2500, Polychromic Al-AlN cermet and C54-TiSi<sub>2</sub> Nanoparticles. These materials were selected for their high absorbances (either theoretically or measurably) over specific operation temperatures. This way the right absorber may be applied to a system based on its other thermal requirements. Figure 2 lists the chosen materials and their properties at optimum output.

<b>Material</b>	<b>Absorbance (<i>e</i>)</b>	<b>Power (Suns)</b>	<b>Temperature (K)</b>
SiC	90%	500	292
Pyromark 2500	95%	500	1228
Polychromic Al-AlN	94.2%	n/a	353
C54-TiSi <sub>2</sub> Nanoparticles	94.4%	1000	1023

Figure 2. The names and relevant properties of the final four selected solar absorbers (X. Wang et al, 2018; D. Bellas, E. Lidorkis, 2017; K. Burlafinger, A. Vetter, C.J. Brabec, 2015; C. Wang et al, 2016; Hofmeister et al, 2009). At the time of writing, no substantial data could be sourced on the optimal incident solar intensity for polychromic aluminium.

Parabolic trough collector based solar furnaces tend to favour high operating temperatures due to Carnot efficiency principles and heat retention ability [3]. For this reason, multiple absorbers were assessed with very high heat thresholds and optimum absorption temperatures. However, the operating temperature of the system is limited by the thermal robustness of the transfer fluid used to store generated heat. Considering this meta-analysis assesses a wide variety of nanofluids, some with lower temperature thresholds than others, several low-optimum-temperature absorbers were assessed as well.

The emission spectra of nano-C54-TiSi<sub>2</sub> was compared to the spectra of the remaining three absorbers on account of the nanoparticles ability to be added to various other materials. C54-TiSi<sub>2</sub> was found by X. Wang et al. to be extremely useful in this regard due to its thermal robustness and high percentage absorbance in specific frequencies. This analysis found that, in conjunction with Silicon Carbide [5] or Pyromark [3] based absorbers, overall absorbance could potentially be increased due to the difference in absorbance wavelengths and similarities in operation temperatures. This potential is not shared with the Al-AlN cermet however, as it does not possess the same thermal robustness as nano-C54-TiSi<sub>2</sub> [6]. Furthermore, polychromic Al-AlN cermet out-performs nano-C54-TiSi<sub>2</sub> over low operating temperatures.

#### 4.2: Heat Transfer Fluids

Nanofluids are more recently being investigated as the transfer fluid for use in PTCs. These nanofluids consist of a base fluid such as water containing nanoparticles usually made up of metals, oxides or carbon nanotubes. The most common nanoparticles used in PTC technology are Al<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub>, Cu, and SiO<sub>2</sub> and for base fluids, the most commonly used are water, ethylene glycol and Syltherm800 thermal oil. Because of the breadth of research on these particular materials, they have been decided on as the focus of our study on transfer fluids.

Properties of these base fluids and nanoparticles were analysed to determine the most suitable for use in PTCs. Values collected from the papers along with equations 1 and 2 were used to create the figures below, that facilitated simple comparison of the thermal properties of nanofluids under study. It also allowed us to find the most efficient heat transfer fluid to be used in PTC systems.

##### 4.2.1: Base fluids

Figure 3 below shows the thermal conductivity of the base fluids (water, ethylene glycol and Syltherm800) at different temperature based on the collected results. Also, in Figure 4 we plotted the viscosity versus temperature graph of the same base fluids.

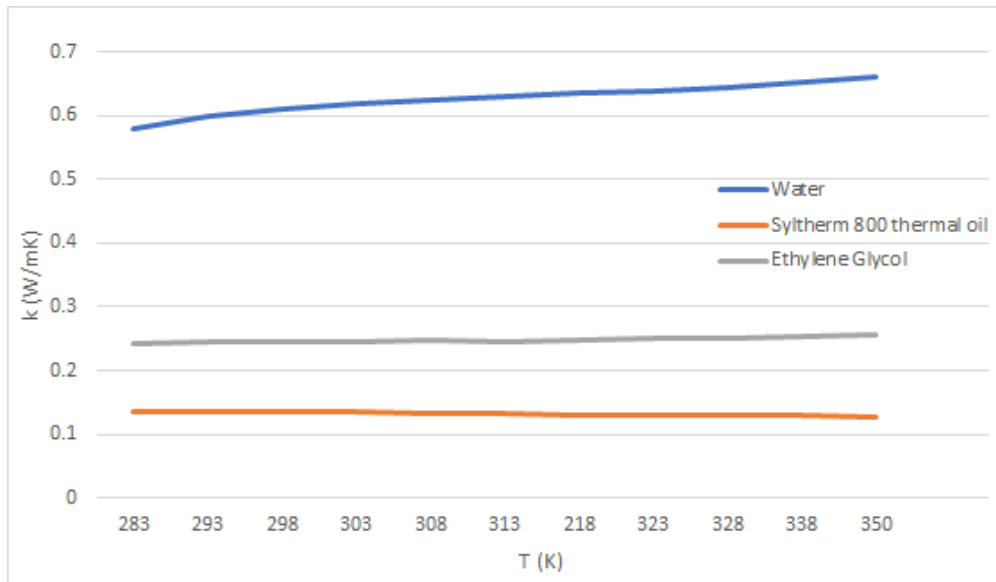


Figure 3. Thermal conductivity ( $k$ ) of the base fluids water, Syltherm 800 and ethylene glycol as a function of temperature ( $T$ ) (Allouhi et al. 2018; Bellos & Tzivanidis 2018; Syam Sundar, Singh, & Sousa 2014; Pastoriza-Gallego et al. 2011)

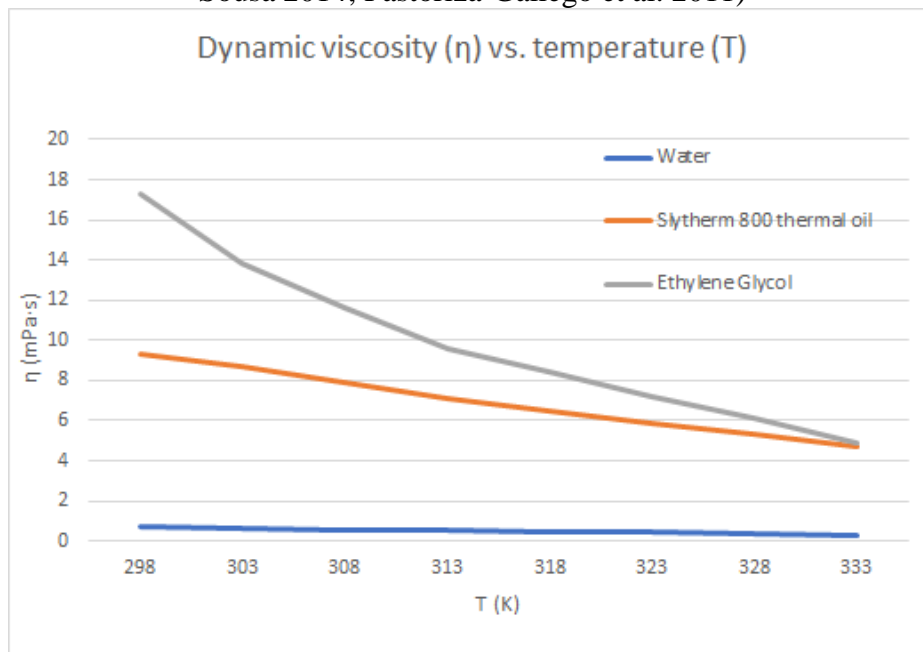


Figure 4. Viscosity ( $\eta$ ) of the base fluids water, Syltherm 800 and ethylene glycol as a function of temperature ( $T$ ) (Allouhi et al. 2018; Bellos & Tzivanidis 2018; Madhesh, Parameshwaran, & Kalaiselvam 2014; Syam Sundar, Singh, & Sousa 2014; Pastoriza-Gallego et al. 2011)

As seen in Figure 3 water held the highest thermal conductivity which increase proportional to temperature over the given range. Syltherm800 and ethylene glycol had much lower average thermal conductivity with Syltherm800 as the lowest overall. Water can be seen (Figure 4) to have the lowest viscosity, nearly constant with change in temperature over the given range at around 1mPa·s approaching 0. Ethylene glycol has very high viscosity at low temperatures, but this quickly drops as temperature increases to approach the viscosity of Syltherm800 at 333K. Hence, it can be said that ethylene glycol is the most optimal base fluid to be used.

In order to judge the appropriateness of each base fluid for use in the PTC a relation was derived between the system efficiency and the parameters in question, thermal conductivity and viscosity. Reynolds number ( $Re$ ) is given by:

$$Re = \frac{4 \cdot m\pi}{D \cdot \eta}$$

Therefore, by eliminating the constants we can write the proportionality relationship:

$$Re \propto \frac{1}{\eta}$$

Also, the efficiency of the PTC system is given by the ratio of  $Q_u$  (useful energy), and  $Q_s$  (available energy).

$$efficiency = \frac{Q_u}{Q_s}$$

$$Q_u = h \cdot A \cdot (\Delta T)$$

$$h = \frac{Nu \cdot k}{D}$$

$$Nu = 0.023 Re^{0.8} Pr^{0.4} \quad [6]$$

Therefore

$$efficiency = \frac{0.023 \left( \frac{4 \cdot m\pi}{D \cdot \eta} \right)^{0.8} Pr^{0.4} \cdot k \cdot (D)^{-1} \cdot A \cdot (\Delta T)}{Q_s}$$

All terms except  $\eta$  and  $k$  are constant for constant flow rate for a specific fluid in a constant state (see nomenclature for definitions). Therefore, by eliminating the constants we can write the proportionality relationship:

$$efficiency \propto \frac{1}{\eta} \propto k \quad [1]$$

As a result, it is preferable to choose a base fluid with low viscosity as this increases the flow turbulence which in turn increases the efficiency of the PTC. A high thermal conductivity is also important in maximising the efficiency of energy transformation. Water showed maximum values in both these properties but was decided against due to its low boiling point. It is possible to use water as a base fluid as high temperatures using a pressurised system, however Coccia et al. (2016) reports this leads to many complications and additional costs and is not recommended. Furthermore, the authors of Coccia et al conclude that only minor improvements to system efficiency can be yielded by the addition of nanoparticles. Therefore, water was decided against to be used as the base-fluid in the study.

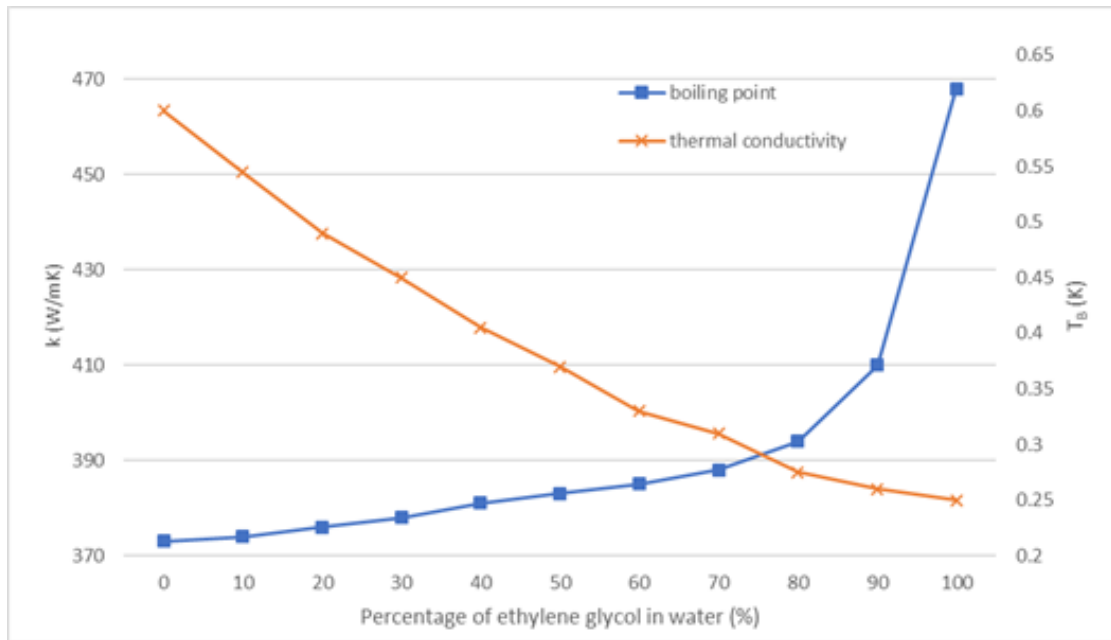


Figure 5. Boiling point (TB) thermal conductivity (k) as independent functions of percentage of ethylene glycol in water, (Pastoriza-Gallego et al. 2011), (The MEGlobal Group of Companies 2008)

A mixture of ethylene glycol and water was considered in order to draw on both the high boiling point of ethylene glycol and the high thermal conductivity and low viscosity of water. Figure 5 was constructed to find the optimal ratio of the two fluids. It can be seen however that the boiling point of the fluid rises exponentially with increased ethylene glycol concentration. This means that even a small addition of water causes a large decrease in boiling point. It was decided for this reason that any gain in thermal conductivity by adding water is not worth the subsequent decrease in boiling point.

Ethylene glycol was chosen as the optimal fluid. As it has a relatively high thermal conductivity and at high temperatures its viscosity drops dramatically.

#### 4.2.2: Nanoparticles

Many nanoparticles are in use for PTC technology but the four most common were found to be SiO<sub>2</sub>, TiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub> and Cu [4]. These were chosen for analysis as there is a wider range of research on these materials from which to collect data, leading to more reliable and consistent results. The properties of the nanomaterials in question are displayed in Figure 6.

Nanoparticles	Density (kg/m <sup>3</sup> )	Specific heat (J/kg·K)	Thermal conductivity (W/m·K)
SiO <sub>2</sub>	2200	0.97	1.4
TiO <sub>2</sub>	4240	689	8.7
Al <sub>2</sub> O <sub>3</sub>	3963	769	40
Cu	6000	551	383

Figure 6. properties of the studied nanoparticles SiO<sub>2</sub>, TiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub> and Cu (Allouhi, Benzakour Amine, Saidur, Kousksou & Jamil 2018), (Bellos & Tzivanidis 2018), (Rafati, Hamidi & Shariati Niaser 2012), (Patel, Sundararajan & Das 2010), (Donghyun & Debjyoti 2011)



It can be seen from the above table that Cu and  $\text{Al}_2\text{O}_3$  possess superior thermal conductivity.  $\text{Al}_2\text{O}_3$  also exhibits highest specific heat. Although Cu has slightly lower specific heat compared to  $\text{TiO}_2$ , its thermal conductivity is far greater.

#### 4.2.3: Nanofluids

Nanofluids comprising of the nanoparticles listed in figure 3 were analysed through their properties of thermal conductivity and viscosity in order to find the most efficient in accordance to equation (1). Both mono and hybrid nanofluids were investigated.

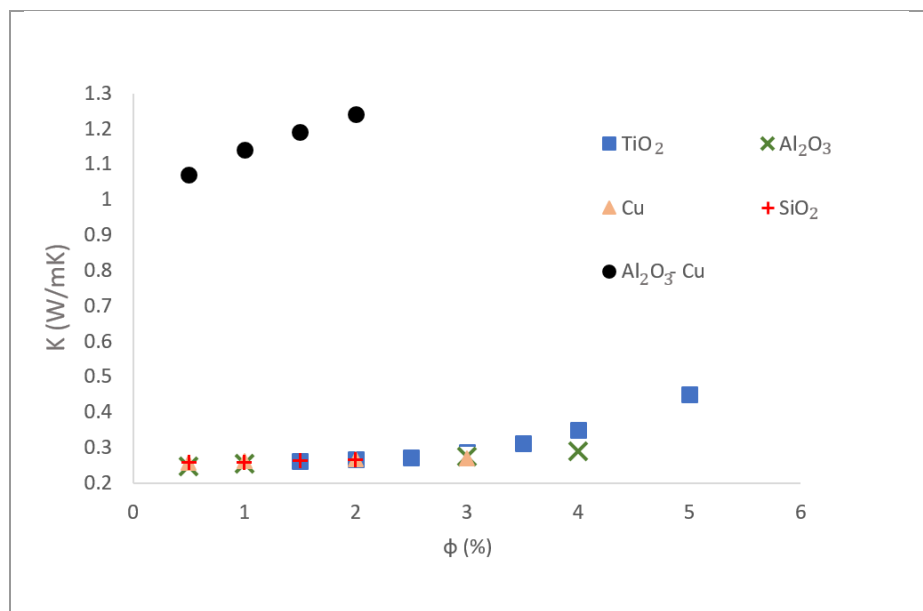


Figure 7. Thermal conductivity ( $k$ ) as a function of volume fraction ( $\phi$ ) for ethylene glycol based nanofluids enhanced by nanoparticles;  $\text{TiO}_2$ ,  $\text{Al}_2\text{O}_3$ , Cu,  $\text{SiO}_2$  and  $\text{Al}_2\text{O}_3\text{-Cu}$  (hybrid), (Murshed, Leong, & Yang 2008; Pastoriza-Gallego et al. 2010; Garg et al. 2008; Nikkam et al. 2017; Akilu et al. 2017; Parsian, A. & Mohammad, A. 2017)

As seen in Figure 7, the hybrid nanofluid investigated ( $\text{Al}_2\text{O}_3\text{-Cu}$ ) produced much higher thermal conductivity than the mono nanofluids investigated. The data from Figure 7 is represented on a smaller scale to better represent the trends apparent.

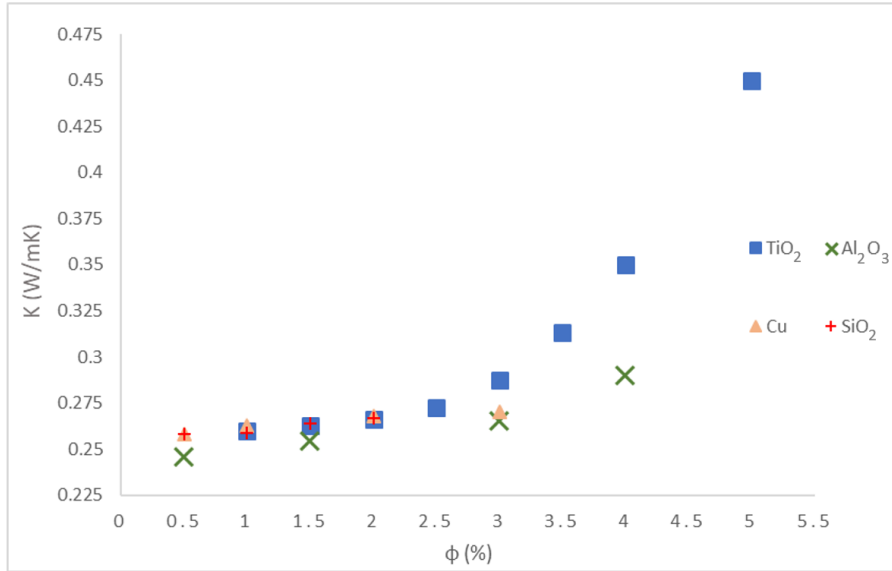


Figure 8. Thermal conductivity (k) as a function of volume fraction ( $\phi$ ) for ethylene glycol based nanofluids enhanced by nanoparticles; TiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, Cu and SiO<sub>2</sub> (Murshed, Leong & Yang 2008; Pastoriza-Gallego et al. 2010; Garg et al. 2008; Nikkam et al. 2017; Akilu et al. 2017)

Figures 7 and 8 present an obvious increasing trend of thermal conductivity with concentration of nanoparticles. Although the thermal conductivity of TiO<sub>2</sub> seems to increase exponentially; all other nanofluids exhibit a more linear relationship between thermal conductivity and volume fraction. This linear relationship is backed up by trends shown by Akilu et al. (2017), Parsian, A. & Mohammad, A. (2017), Nikkam et al. (2017) and Bellos & Tzivanidis (2017). It is further reinforced by Maxwell's equation,

$$k_{nf} = k_f \left( \frac{k_p + 2k_f + 2(k_p - k_f)\phi}{k_p + 2k_f - (k_p - k_f)\phi} \right) \quad [2] \quad (2)$$

which describes a linear relationship between the thermal conductivity of the nanofluid and the volume fraction at constant temperature, shown by Mehta, Chauhan, & Kanagaraj (2011).

It is shown by Bellos & Tzivanidis (2017) that the viscosity of a nanofluid can be calculated by the equations:

$$\eta_{nf} = \eta_{bf} \cdot (1 + 2.5 \cdot \phi + 6.5 \cdot \phi^2)$$

and

$$\eta_{nf} = \frac{\eta_{bf}}{(1-\phi)^{2.5}} \quad (3)$$

The above equations show that the theoretical viscosity of a nanofluid is only dependant on the volume fraction of the nanofluid and the regular viscosity of the base fluid. For this reason, this paper does not compare the viscosities of different types of nanofluids with common bases. Instead the nanofluid with the highest thermal conductivity was selected and its conductivity and viscosity over various volume

fractions was compared. The chosen nanofluid was a 50:50 mix of  $\text{Al}_2\text{O}_3$  and Cu. Figure 9 shows the viscosity and conductivity of  $\text{Al}_2\text{O}_3$ -Cu from 0 to 4% volume fractions. Viscosity was calculated using equation (3). Viscosity is graphed in descending order on the second y-axis to better illustrate where the volume fraction minimises viscosity while maximising thermal conductivity. Due to the linear relationship between thermal conductivity and volume fraction (as outlined above and in equation (2)) a linear trend line is chosen to show the predicted thermal conductivity over a wider range of volume fraction of nanoparticles. Figure 8 was used to determine the volume fraction of 50:50  $\text{Al}_2\text{O}_3$ -Cu that maximises thermal conductivity and minimises viscosity. This volume fraction was found to be in the range 1-2% volume fraction.

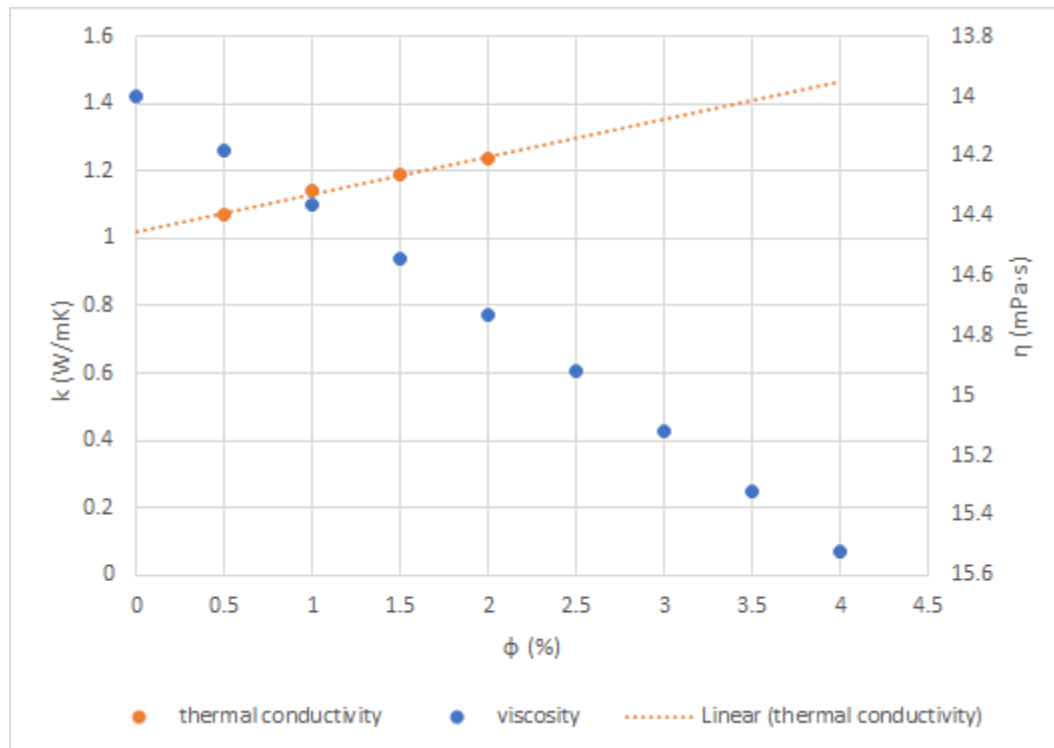


Figure 9. The viscosity axis of this graph has been flipped to create a crossover point near which the properties of the nanofluid will be optimised.

## 5: Discussion

In this meta-analysis multiple scientific articles were analysed to find the optimal pipe properties that would increase the efficiency of the parabolic trough collector based solar furnaces. In order to achieve that aim papers from past the 10 years were studied and the most reputable and relevant data was compared. Papers were analysed specifically from the fields of nanofluids, black-body absorbers and specific frequency absorbers with the aim of collating a diverse range of materials whose properties could work in conjunction with one-another in order to increase the efficiency and heat retention of the Parabolic Trough Collector system.

Several absorbers were analysed and considered, but the selection was trimmed down to just the materials that appear in this paper. This was either because the materials did not have properties that would have made them compatible with the system, or because there were other materials found that possessed better absorptions at similar temperature and solar concentration ranges. The four remaining materials then were Silicon Carbide (SiC), Pyromark 2500, Polychromic Aluminium + Aluminium Nitride, and Titanium Silicarbide nanoparticles. Each material has a specific property that makes it

stand out from the others. Initially, Silicon Carbide is the only material that does not need to be layered onto another material. Silicon Carbides structural properties make it more than eligible for use as a fluid pipe, as it is used in the Solair Thermal Solar Power Plant in Switzerland. Pyromark 2500 was kept for final analysis as it has the highest operating temperature of all the absorbers analysed. Polychromic Aluminium remained in this paper as it is a low-temperature-operating, high absorption black body with specific high absorption frequencies. Finally, Titanium Silicarbide nanoparticles were further analysed as they can be grown on some other high absorption materials to add their specific absorption frequencies to the resulting composite.

In addition, various papers were analysed to find an ideal nanofluid that would maximize the efficiency of the entire process. To increase the PTC's efficiency, fluids with high thermal conductivity and low viscosity are necessary [7] (as show in equation (1)). Nanofluids were also judged by boiling point. Despite the model of Risi, Milanese & Laforgia (2013) showing that nanofluids can function evaporatively in PTC systems, this meta-analysis focuses on non-evaporative systems on account of a much greater breadth of pre-existing research. In this paper, the thermal conductivity and viscosity of commonly used base fluids: Water, Ethylene Glycol and Syltherm800 were compared. Although water exhibited optimal properties in terms of thermal conductivity and viscosity, Ethylene Glycol was considered the best to use because of its high boiling point which was decided more important in increasing the overall efficiency of the system.

Furthermore, the thermal conductivity and viscosity data of ethylene glycol based nanofluid was obtained with both mono and hybrid nanoparticles. The nanoparticles used to carry out this analysis are  $\text{TiO}_2$ ,  $\text{Al}_2\text{O}_3$ , Cu,  $\text{SiO}_2$  and hybrid  $\text{Al}_2\text{O}_3$ -Cu (50:50). Of the many nanofluids investigated it was decided the hybrid nanofluid consisting of  $\text{Al}_2\text{O}_3$  and Cu with a ratio of 50:50 and volume fraction ranging 1-2% with a base fluid of ethylene glycol would provide the most efficient energy transfer in the system.

For the pipe system to operate non-evaporatively using the ethylene glycol  $\text{Al}_2\text{O}_3$ -Cu nanofluid the operating temperature is restricted to under  $\approx 190^\circ\text{C}$ . For this temperature polychromic Al-AlN cermet would provide optimal energy generation as it possesses the best absorption below  $500^\circ\text{K}$  of all absorbers analysed by this study [6]. For operating temperatures up to  $1383^\circ\text{K}$  this study recommends the consideration of a hybrid of Pyromark 2500 and nano- $\text{C}_{54}$ - $\text{TiSi}_2$ , as hybrid black-body and selective absorbers have shown not only incredibly high but robust thermal conversion efficiencies [3,8]. However, systems with such high temperatures would likely have to operate either conductively or evaporatively, and thus have not been studied in greater detail by this paper.

Despite the increasing popularity of investigated fields, there is still as shortage of sufficient data to make a conclusive statement on the properties of an ideal parabolic trough collector based solar furnace pipe system. Hybrid nanofluids showed great potential in terms of their thermal properties, however due to the lack of data in this area, only one hybrid nanofluid could be properly analysed. Further studies on this technology is highly recommended. In particular, due to the high thermal conductivity enhancement of  $\text{TiO}_2$  nanoparticles with increasing volume fraction, it is suggested that the properties of  $\text{TiO}_2$  based hybrid nanofluids are investigated.

## **6: Conclusion**

This meta-analysis has assessed several enhancements that can be made to the pipe system of the parabolic trough collector based thermal solar generator. Specifically, these enhancements are the

surface-coat absorber used to convert solar energy into heat and the fluid used in the pipe to transfer heat to a furnace or storage unit, we have constructed original figures using data and equations from reputable papers, to gather and reconfigure existing information in a succinct and easily accessible format for the comparison of nanofluids in heat transfer applications (specifically for use in PTCs). It was found that, out of all the assessed possible pipe systems, that a combination of a polychromic Al-AlN cermet absorber and a nanofluid consisting of an ethylene glycol based 50:50 Al<sub>2</sub>O<sub>3</sub>-Cu hybrid nanofluid with a 1-2% volume fraction would provide the optimum efficiency of heat generation and transfer. The operating temperature of this system constrains the energy generation per meter of pipe that this system possesses, but the optimisation of the process by which this heat is transformed into electricity is beyond the scope of this meta-analysis.

## **7: Acknowledgements:**

Our team would like to sincerely thank Martin Bell, Blake Regan, Jurgen Schulte and Joshua Pritchard for their criticism and guidance throughout the progress of researching and writing this meta-analysis. We would also like to extend our acknowledgments to our classmates for their consistent and constructive peer reviews, and Maryna Bilokur for inspiration for the study.

## **7: Bibliography**

1. 2017 *The World Bank, Solar Resource Data: Solargis*, 2017, <<https://solargis.com/maps-and-gis-data/download/world>>. *SOLAIR*, 2008, vol. 4,.
2. Risi, A., Milanese, M. & Laforgia, D. 2013, 'Modelling and optimization of transparent parabolic trough collector based on gas-phase nanofluids', *Renewable Energy*, vol. 58, pp. 134-9. <https://doi.org/10.1016/j.renene.2013.03.014>
3. Burlafinger, K., Vetter, A. & Brabec, C.J. 2015, 'Maximizing concentrated solar power (CSP) plant overall efficiencies by using spectral selective absorbers at optimal operation temperatures', *Solar Energy*, vol. 120, pp. 428-38. <https://doi.org/10.1016/j.solener.2015.07.023>
4. Bellos, E & Tzivanidis, C. 2018, 'Thermal analysis of parabolic trough collector operating with mono and hybrid nanofluids', *Sustainable Energy Technologies and Assessments*, vol. 26, pp. 105-115. <https://doi.org/10.1016/j.seta.2017.10.005>
5. Hofmeister, A.M., Pitman, K.M., Goncharov, A.F. & Speck, A.K. 2009, 'Optical Constants of Silicon Carbide for Astrophysical Applications II. Extending Optical Functions from Infrared to Ultraviolet Using Single-Crystal Absorption Spectra', *The Astrophysical Journal*, vol. 696, pp. 1502-16. <https://doi.org/10.1088/0004-637X/696/2/1502>
6. Wang, C., Shi, J., Geng, Z. & Ling, X. 2016, 'Polychromic Al-AlN cermet solar absorber coating with high absorption efficiency and excellent durability', *Solar Energy Materials and Solar Cells*, vol. 144, pp. 14-22. <https://doi.org/10.1016/j.solmat.2015.07.049>
7. Mwesigye, A. & Huan, Z. 2015, 'Thermal and Thermodynamic performance of a parabolic trough receiver with Syltherm800-Al<sub>2</sub>O<sub>3</sub> nanofluid as the heat transfer fluid', *Energy Procedia*, vol. 75, pp. 394-402 <https://doi.org/10.1016/j.egypro.2015.07.402>
8. Wang, X., Yu, X., Fu, S., Lee, E., Kekalo, K. & Liu, J. 2018, 'Design and optimization of nanoparticle-pigmented solar selective absorber coatings for high-temperature concentrating solar thermal systems', *Journal of Applied Physics*, vol. 123, no. 3. <https://doi.org/10.1063/1.5009252>
9. Bellas, D.V. & Lidorikis, E. 2017, 'Design of high-temperature solar-selective coatings for application in solar collectors', *Solar Energy Materials and Solar Cells*, vol. 170, no. 2017, pp. 102-13.
10. Dabiri, S. & Rahimi, M.F. July 12, 2017, 'Introduction of Solar Collectors and Energy and Exergy Analysis of a Heliostat Plant', *The 3rd International Conference and Exhibition on Solar Energy* University of Tehran, Tehran, Iran.
11. Fuqiang, W., Ziming, C., Yuan, Y., Yong, S. & Linhua, L. 2017, 'Progress in Concentrated Solar Power Technology With Parabolic Trough Collector System: A Comprehensive Review', *Renewable and Sustainable Energy Reviews*, vol. 75, pp. 105-115. <https://doi.org/10.1016/j.rser.2017.05.023>

*Energy Reviews*, , no. 79, pp. 1314-28.

<https://doi.org/10.1016/j.rser.2017.05.174>

12. Mahbubul, I.M., Khan, M.M.A., Ibrahim, N.I., Ali, H.M., Al-Sulaiman, F.A. & Saidur, R. 2018, 'Carbon nanotube nanofluid in enhancing the efficiency of evacuated

tube solar collector', *Renewable energy*, vol. 121, no. 2018, pp. 36-44.

13. Murshed, S.M.S., Leong, K.C. & Yang, C. 2008, 'Investigations of thermal conductivity and viscosity of nanofluids', *International Journal of Thermal Sciences*, vol. 47, no. 5, pp. 560-8.

<https://doi.org/10.1016/j.ijthermalsci.2007.05.004>

14. Shuman, F. & Vernon Boys, C. 1912, *Sun-Boiler*, no. US1240890A, .

15. Yue, H., Zhao, Y., Ma, X. & Gong, J. 2012, 'Ethylene Glycol: Properties, synthesis and Applications', *Chemical Society Reviews*, vol. 41, no. 11, pp. 4218-44.

<https://doi.org/10.1039/c2cs15359a>

16. ASHRAE Handbook, Fundamentals, American Society of Heating, Refrigerating and Air-Conditioning Engineers Inc., Atlanta, GA, 2005

17. Allouhia, A., Benzakour Amine, M., Saidur, R., Kousksou, T. & Jamil, A. 2018, 'Energy and exergy analyses of a parabolic trough collector operated with nanofluids for medium and high temperature applications', *Energy Conversion and Management*, vol. 155, pp. 201-217.

<https://doi.org/10.1016/j.enconman.2017.10.059>

18. Rafati, M., Hamidi, A.A. & Shariati Niaser, M. 2012, 'Application of nanofluids in computer cooling systems (heat transfer performance of nanofluids)', *Applied Thermal Engineering*, vol. 45-46, pp. 9-14.

<https://doi.org/10.1016/j.applthermaleng.2012.03.028>

19. Patel, H.E., Sundararajan, T. & Das, S.K. 2010, 'An experimental investigation into the thermal conductivity enhancement in oxide and metallic nanofluids', *Journal of Nanoparticle Research*, vol. 12, no. 3, pp. 1015-1031.

<https://doi.org/10.1007/s11051-009-9658-2>

20. Donghyun, S. & Debjyoti, B. 2011, 'Enhancement of specific heat capacity of high-temperature silica-nanofluids synthesized in alkali chloride salt eutectics for solar thermal-energy storage applications', *International Journal of Heat and Mass Transfer*, vol. 54, no. 5-6, pp. 1064-1070.

<https://doi.org/10.1016/j.ijheatmasstransfer.2010.11.017>

21. Madhesh, D., Parameshwaran, R. & Kalaiselvam, S. 2014, 'Experimental investigation on convective heat transfer and rheological characteristics of Cu-TiO<sub>2</sub> hybrid nanofluids', *Experimental Thermal and Fluid*

*Science*, vol. 52, pp. 104-115.

<https://doi.org/10.1016/j.expthermflusci.2013.08.026>

22. Syam Sundar, L., Singh, M.K. & Sousa, A.C.M. 2014, 'Enhanced heat transfer and friction factor of MWCNT-Fe<sub>3</sub>O<sub>4</sub>/water hybrid nanofluids', *International Communications in Heat and Mass Transfer*, vol. 52, pp. 73-83.

<https://doi.org/10.1016/j.icheatmasstransfer.2014.01.012>

23. Pastoriza-Gallego, M.J., Lugo, L., Legido, J.L. & Piñeiro, M.M. 2011, 'Thermal conductivity and viscosity measurements of ethylene glycol-based Al<sub>2</sub>O<sub>3</sub> nanofluids', *Nanoscale Research Letters*, vol. 6, no. 221.

<https://doi.org/10.1186/1556-276X-6-221>

24. Selinger, J., Timofeeva, E.V., Gavrilov, A.N., McCloskey, J.M. & Tolmachev, Y.V. 2007, 'Thermal conductivity and particle agglomeration in alumina nanofluids: Experiment and theory', *Physical Review*, vol. 76, no. 61203, pp. 1-16.

25. Lee, S.P., Choi, S.U.S., Li, S. & Easterman, J.A. Measuring Thermal Conductivity of Fluids Containing Oxide Nanoparticles

26. Garg, J., Poudel, B., Chiesa, M., Gordon, J. B., Ma, J. J., Wang, J. B., Ren, Z. F., Kang, Y. T., Ohtani, H., Nanda, J., McKinley, G. H., & Chen, G. 2008, 'Enhanced thermal conductivity and viscosity of copper nanoparticles in ethylene glycol nanofluid', *Journal of Applied Physics*, vol. 103, no. 74301, pp. 1-6.

<https://doi.org/10.1063/1.2902483>

27. Nikkam, N., Ghanbarpour, M., Khodabandeh, R. & Toprak, M.S. 2017, 'The effect of particle size and base liquid on thermo-physical properties of ethylene and diethylene glycol based copper micro- and nanofluids', *International Communications in Heat and Mass Transfer*, vol. 86, pp. 143-

149. <https://doi.org/10.1016/j.icheatmasstransfer.2017.05.026>

28. Akilu, S., Baheta, A.T., Minea, A.A. & Sharma, K.V. 2017, 'Rheology and thermal conductivity of non-porous silica (SiO<sub>2</sub>) in viscous glycerol and ethylene glycol based nanofluids', *International Communications in Heat and Mass Transfer*, vol. 88, pp. 245-253. <https://doi.org/10.1016/j.icheatmasstransfer.2017.08.001>

29. Parsian, A. & Mohammad, A. 2017, 'New experimental correlation for the thermal conductivity of ethylene glycol containing Al<sub>2</sub>O<sub>3</sub>-Cu hybrid nanoparticles', *Journal of Thermal Analysis and Calorimetry*, vol. 131, pp. 1605-1613. <https://doi.org/10.1007/s10973-017-6694-5>

30. Bellos, E., Tzivanidis, C. & Tsimpoukis, D. 2018, 'Enhancing the performance of parabolic trough collectors using nanofluids and turbulators', *Renewable and*

*Sustainable Energy Reviews*, vol. 91, pp. 358-375.  
<https://doi.org/10.1016/j.rser.2018.03.091>

31. The MEGlobal Group of Companies 2008, *Ethylene Glycol*, product guide, viewed 26 April 2018, <[http://www.meglobal.biz/media/product\\_guides/MEGlobal\\_MEG.pdf](http://www.meglobal.biz/media/product_guides/MEGlobal_MEG.pdf)>

32. Mehta, S., Chauhan, K.P. & Kanagaraj, S. 2011, Modeling of thermal conductivity of nanofluids by modifying Maxwell's equation using cell model approach, *Journal of Nanoparticle Research*, vol.13, pp. 2791-2798.  
<https://doi.org/10.1007/s11051-010-0167-0>

33. Dorfman, A.S. 2017, *Applications of Mathematical Heat Transfer and Fluid Flow Models in Engineering and Medicine*, John Wiley & Sons, Incorporated, Chicester.