

Rowan University

Rowan Digital Works

Henry M. Rowan College of Engineering Faculty
Scholarship

Henry M. Rowan College of Engineering

12-1-2019

Bicontinuous Interfacially Jammed Emulsion Gels (bijels) as Media for Enabling Enzymatic Reactive Separation of a Highly Water Insoluble Substrate

Sanghak Cha

Pohang University of Science and Technology

Hyun Lim

Pohang University of Science and Technology

Martin Haase

Rowan University

Kathleen Stebe

University of Pennsylvania

Gyoo Jung

Pohang University of Science and Technology

Follow this and additional works at: https://rdw.rowan.edu/engineering_facpub

 [next page for additional authors](#)
Part of the [Chemical Engineering Commons](#)

Let us know how access to this document benefits you - share your thoughts on our feedback form.

Recommended Citation

Cha, Sanghak; Lim, Hyun; Haase, Martin; Stebe, Kathleen; Jung, Gyoo; and Lee, Daeyeon, "Bicontinuous Interfacially Jammed Emulsion Gels (bijels) as Media for Enabling Enzymatic Reactive Separation of a Highly Water Insoluble Substrate" (2019). *Henry M. Rowan College of Engineering Faculty Scholarship*. 84. https://rdw.rowan.edu/engineering_facpub/84

This Article is brought to you for free and open access by the Henry M. Rowan College of Engineering at Rowan Digital Works. It has been accepted for inclusion in Henry M. Rowan College of Engineering Faculty Scholarship by an authorized administrator of Rowan Digital Works. For more information, please contact rdw@rowan.edu.

Authors

Sanghak Cha, Hyun Lim, Martin Haase, Kathleen Stebe, Gyoo Jung, and Daeyeon Lee

SCIENTIFIC REPORTS



OPEN

Bicontinuous Interfacially Jammed Emulsion Gels (bijels) as Media for Enabling Enzymatic Reactive Separation of a Highly Water Insoluble Substrate

Sanghak Cha¹, Hyun Gyu Lim¹, Martin F. Haase³, Kathleen J. Stebe⁴, Gyo Yeol Jung^{1,2} & Daeyeon Lee⁴

Although enzymes are efficient catalysts capable of converting various substrates into desired products with high specificity under mild conditions, their effectiveness as catalysts is substantially reduced when substrates are poorly water-soluble. In this study, to expedite the enzymatic conversion of a hydrophobic substrate, we use a bicontinuous interfacially jammed emulsion gel (bijel) which provides large interfacial area between two immiscible liquids: oil and water. Using lipase-catalyzed hydrolysis of tributyrin as a model reaction in a batch mode, we show that bijels can be used as media to enable enzymatic reaction. The bijel system gives a four-fold increase in the initial reaction rate in comparison to a stirred biphasic medium. Our results demonstrate that bijels are powerful biphasic reaction media to accelerate enzymatic reactions with various hydrophobic reagents. This work also demonstrates that bijels can potentially be used as reaction media to enable continuous reactive separations.

Enzymes are highly efficient natural catalysts that accelerate various reactions with high activity and (stereo-) specificity under mild reaction conditions, making them attractive catalysts for the industry-scale conversion of chemicals^{1,2}. Despite these advantages, application of enzymatic reactions are typically limited to the conversion of water-soluble chemicals^{3,4}. When a substrate is hydrophobic and thus insoluble in water, its conversion via enzymatic reaction is significantly reduced because the enzyme is typically water soluble and the substrate is present at a very low concentration in the aqueous phase. To enable catalytic conversion of such a hydrophobic substrate, a biphasic system consisting of water and organic solvent is required⁵⁻⁷. However, slow mass transfer due to the limited interfacial area between two immiscible liquid phases significantly limits efficient conversion⁸⁻¹⁰. Although the interfacial area could be increased by energy-intensive emulsification, the addition of surfactants¹¹, or the use of sponge phases^{12,13} and microemulsions¹⁴⁻¹⁶, these approaches may not be favored because enzymes can be undesirably deactivated by shear stress¹⁷⁻¹⁹ or surfactants, resulting in inefficient conversion²⁰⁻²². Surfactants at the interface also form barriers to interphase mass transfer, reducing the efficacy of the enzymatic process. Particle-stabilized Pickering emulsions offer great potential to enable reactive separation of biphasic systems using enzymes²³⁻²⁷. However, these emulsion-based systems do not offer the possibility of performing reactive separation continuously because the dispersed phase remain isolated, making it challenging to add or remove agents to/from the dispersed phase.

Recently, a new class of biphasic liquid mixture known as bicontinuous interfacially jammed emulsion gel (bijel) has been introduced. The bijel is a structurally stable biphasic bicontinuous emulsion generated by

¹Department of Chemical Engineering, Pohang University of Science and Technology, 77 Cheongam-Ro, Nam-Gu, Pohang, Gyeongbuk, 37673, Korea. ²School of Interdisciplinary Bioscience and Bioengineering, Pohang University of Science and Technology, 77 Cheongam-Ro, Nam-Gu, Pohang, Gyeongbuk, 37673, Korea. ³Department of Chemical Engineering, Rowan University, Henry M. Rowan College of Engineering, Glassboro, NJ, 08028, USA. ⁴Department of Chemical and Biomolecular Engineering, University of Pennsylvania, Philadelphia, PA, 19104, USA. Sanghak Cha and Hyun Gyu Lim contributed equally. Correspondence and requests for materials should be addressed to G.Y.J. (email: gyjung@postech.ac.kr) or D.L. (email: daeyeon@seas.upenn.edu)

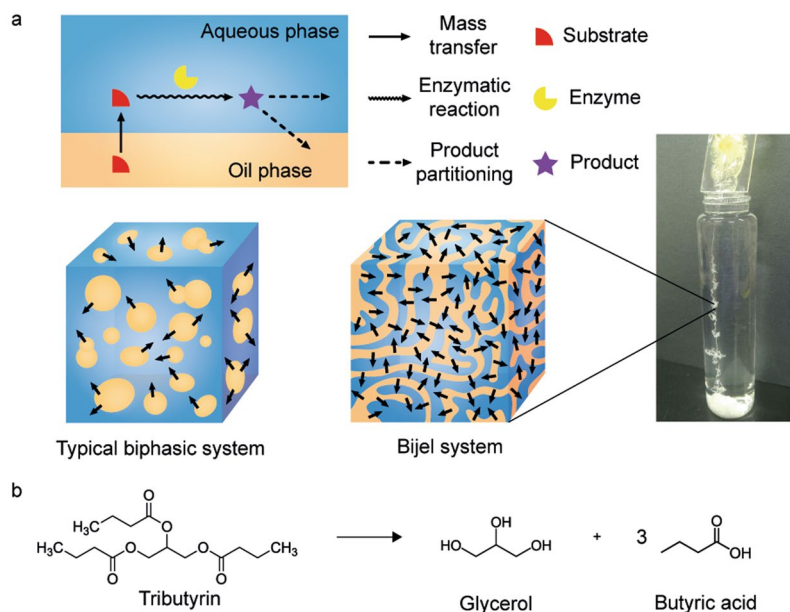


Figure 1. A schematic diagram of overall strategies used in this study. **(a)** In a biphasic system for the enzymatic reaction, the enzyme and the substrate exist in the aqueous phase and the oil phase, respectively. Once the substrate in the oil phase is transferred to the aqueous phase, it is converted to product by enzymatic reaction, which will be partitioned to either aqueous or oil phase. While the limited interfacial area of a typical biphasic system impedes the mass transfer from oil to the aqueous phase, the enormous interfacial area of the bijel system leads to the efficient transfer, facilitating the enzymatic conversion. **(b)** Lipase-catalyzed hydrolysis of tributyrin was chosen as a model reaction.

jamming nanoparticles at the interface between immiscible liquids during spinodal decomposition^{28,29}. Unlike typical emulsions, the structures in bijels do not undergo coarsening over time due to the rigidity provided by the interfacially jammed nanoparticle layers. The size of the biphasic domains in bijels can be systematically varied, even below the micrometer scale, by changing the size and concentration of nanoparticles³⁰. Although the first examples of bijels were produced by arresting thermally quenched mixtures of oil and water, a recent study has demonstrated that bijels can be continuously produced using a wide variety of oil and nanoparticles by solvent transfer-induced phase separation (STRIPS). This method enables continuous fabrication of bijels in diverse formats (nanoparticle, fiber, and membrane), potentially enabling various applications in biphasic chemical processes (Fig. 1)³⁰. STRIPS bijels could potentially be used as reaction media for biphasic enzymatic reactions of hydrophobic substrates by enabling rapid interphase mass transfer.

In this study, we test the feasibility of using a STRIPS bijel to induce enzymatic conversion of a hydrophobic substrate in a batch mode. As a model reaction, we choose tributyrin hydrolysis via lipase which requires intimate contact between aqueous and organic phases due to the low solubility of the substrate in water. This reaction has been widely utilized to assay the kinetic activity of lipase^{31–34}. Bijel fibers containing tributyrin in the oil phase are produced with different concentrations of silica nanoparticle and cetyltrimethylammonium bromide (CTAB) to control the domain sizes. We show that the bijel fiber with the smallest domains and thus highest interfacial area leads to the highest rate of enzymatic conversion of tributyrin. When compared to a conventional biphasic system that has been used to induce conversion of hydrophobic substrates, the bijel system gives almost four-fold increase in the initial reaction rate, demonstrating that the bijel can potentially be used as a biphasic medium for the continuous enzymatic conversion of hydrophobic substances.

Results

Fabrication of bijel fiber containing tributyrin. The fabrication of bijel fiber by the STRIPS method uses a homogeneous ternary mixture consisting of two immiscible liquids (water and diethylphthalate) and a co-solvent, ethanol. To employ the STRIPS bijel fiber for the conversion of tributyrin (Fig. 1), we added this substrate in the oil phase. We also used 2.4 wt% SiO₂ nanoparticle and 53 mM CTAB for stabilization of the bijel, similar to a previous study²⁸. To ensure that the addition of the substrate did not alter bijel formation, we confirmed its morphology via confocal microscopy. As shown in Fig. 2, we observed typical bijel structures, regardless of addition of tributyrin. The domain sizes were approximately 25–30 μm regardless of addition of tributyrin, indicating successful formation of bicontinuous biphasic media with large interfacial area for enzymatic reaction.

Effect of SiO₂ and CTAB concentration to the domain size of bijel fiber. When spinodal decomposition is triggered via STRIPS, silica nanoparticles, modified *in situ* by CTAB molecules, attach to the oil-water interface and undergo jamming to arrest the phase separation and thus stabilize the resulting bicontinuous microstructures. Since the point at which interface becomes jammed is determined by the amount of nanoparticles

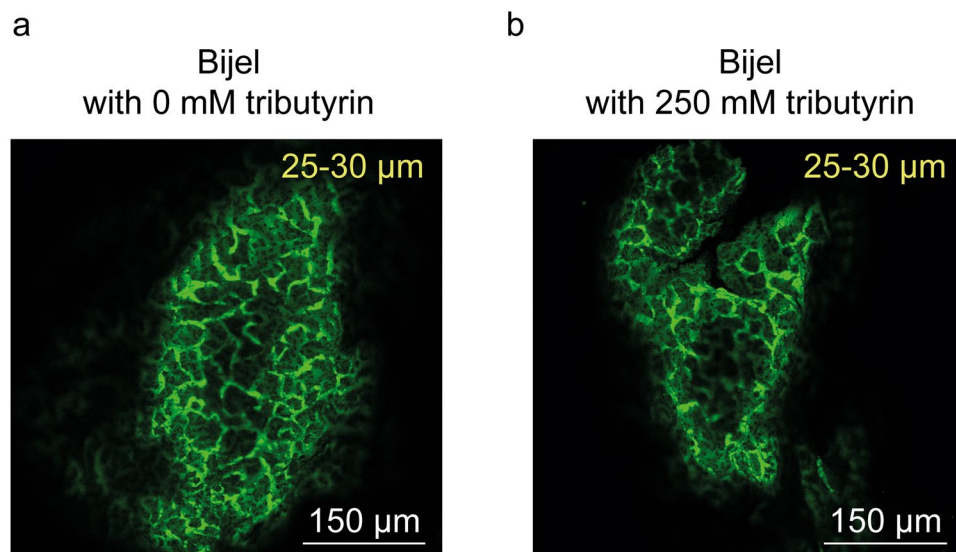


Figure 2. Confocal images of bijel fibers (a) without tributyrin and (b) with tributyrin. The oil phase of bijel was visualized by addition of the hydrophobic fluorescent dye (Nile Red) in the oil phase. The numbers indicate the pore size of each bijel fiber. The scale bar represents 150 μm .

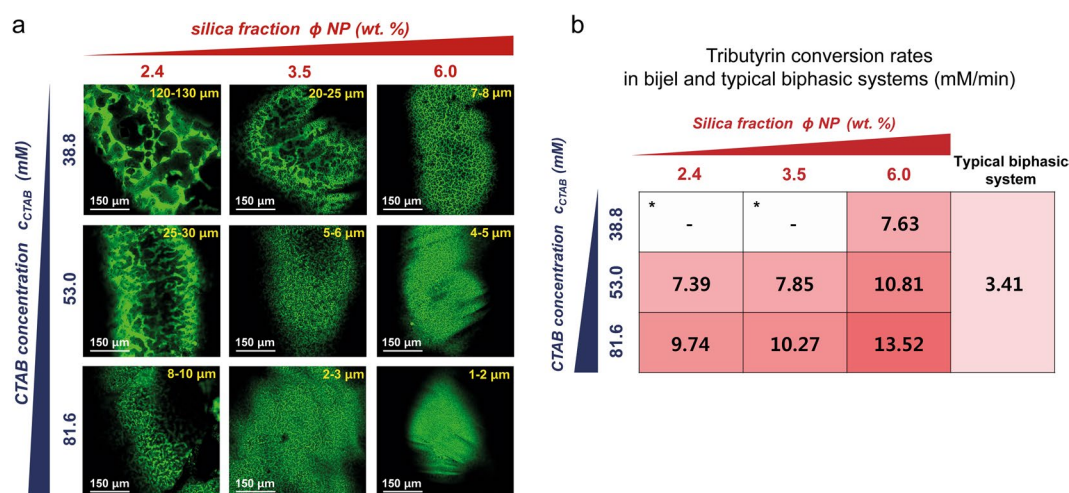


Figure 3. Effect of concentration of stabilizing reagents (SiO_2 nanoparticle and CTAB) to pore size and the reaction rate of tributyrin hydrolysis. (a) Confocal images of different bijel fibers prepared with various concentration of SiO_2 nanoparticle (2.4, 3.5, 6.0 wt%) and CTAB (38.8, 53.0, 81.6 mM). The oil phase of the bijel was visualized by addition of the hydrophobic fluorescent dye (Nile Red) in the oil phase. The numbers indicate the pore size of each bijel fiber. The scale bar represents 150 μm . (b) Comparison of tributyrin conversion rate (mM/min) between the bijel system and the conventional biphasic system.

present in the ternary mixture, the concentrations of SiO_2 nanoparticle and CTAB are critical factors that determine the domain size of the fabricated bijel fiber^{30,35}. At elevated nanoparticle concentrations with sufficient surfactant, interfacial jamming arrests the phase separation in the early stages and thus stabilizes small structures, resulting in small domain size. In contrast, the domain size would be increased if nanoparticles do not attach to the interface efficiently due to the lack of CTAB that modifies the nanoparticles.

To control the domain size of STRIPS bijel fibers, we varied the concentration of SiO_2 nanoparticles (2.4, 3.5, 6.0 wt %) and CTAB (38.8, 53.0, 81.6 mM) in the quaternary mixture. As expected, we observed that the domain size in the bijel fibers changed by 100-fold (from 130 μm to 1 μm) by changing the concentration of SiO_2 nanoparticle and CTAB (Fig. 3a). The domain size decreased with increased concentration of the SiO_2 nanoparticle and increased CTAB concentration. With 6.0 wt% SiO_2 nanoparticle and 81.6 mM CTAB, we successfully obtained bijel fibers with domain sizes ranging between 1 and 2 μm .

Enhanced enzymatic conversion of tributyrin with bijel fiber. To investigate the effect of the interfacial area of bijel fiber, we compared the initial reaction rates of tributyrin hydrolysis with the bijel fibers with

different domain sizes. Two bijels that were prepared with 2.4 or 3.5 wt% nanoparticles along with 38.8 mM CTAB were unstable during buffer exchange. We focused on conducting enzymatic hydrolysis with the remaining bijel fibers.

In this lipase reaction, one mole of tributyrin is converted to one mole of glycerol and three moles of butyric acid (Fig. 1b). Therefore, we quantified the concentration of butyric acid in the aqueous phase upon the termination of the enzymatic reaction. As illustrated in Fig. 3b, the reaction rates generally increased with a decrease in the domain size, indicating that large interfacial area of bijel is critical to improve the rate of the enzymatic reaction. In particular, the bijel fiber with the smallest domain size showed close to a two-fold increase in the reaction rate (13.52 mM/min) than that with the largest domain size (7.39 mM/min). We also compared this bijel system to the conventional biphasic system which was formed by agitating an oil/water mixture at 150 rpm using an orbital shaker. Similar methods have been used previously to induce enzymatic conversion of hydrophobic substrates in biphasic mixtures^{36–38}. The reaction rate in the bijel system showed close to four-fold enhancement compared to the conventional biphasic reaction system. This result demonstrates that bijels with large interfacial area function as an effective reaction medium to accelerate the enzymatic conversion of poorly water-soluble substances. To the best of our knowledge, this is the first report on demonstrating the application of bijel for enzymatic conversion of hydrophobic substrates in a biphasic medium.

Discussion

The main bottleneck during enzymatic conversion of a water-insoluble substrate in a biphasic medium is the limited interphase mass transfer to the enzyme-containing aqueous phase^{39,40} due to limited interfacial area. In this study, we have demonstrated that bijel prepared by the STRIPS method can be effectively used as a biphasic reaction medium with high interfacial area to enhance the enzymatic hydrolysis of tributyrin. Because of the versatility in preparing bijels with various sets of nanoparticles and oils, STRIPS bijels could potentially be used in various biphasic enzymatic reactions with various hydrophobic and highly water insoluble substrates. Additionally, other versatile bijels for the conversion of poorly water-soluble substances can potentially be developed to exploit nanoparticles with catalytic activities^{41,42}.

It is important to place our current work in the context of bijel development since it was first described in 2005. A key envisioned application was to use bijels as media to enable continuous reactive separations. The results presented in this work, albeit in a batch mode, clearly demonstrate that STRIPS bijels can be used as reaction medium to induce reactive separation involving enzymatic conversion of hydrophobic substrates and interphase mass transfer of chemicals. Several additional hurdles, however, must be cleared to fully realize the original vision of continuous reactive separation using bijels. For example, mass transfer of the reactant and/or product in the two liquid phases could potentially limit the efficiency of reactive separation. One potential approach to overcome such a challenge is to induce convection in one or both liquid phases. A recent development has shown that bijels can be reinforced to withstand shear and flow⁴³. By combining these recent advances in the preparation and application of bijels, we believe our current work brings us one step closer to realizing the vision of bijel-based continuous reactive separations.

Methods

Chemical reagents and apparatus. Most chemical reagents were purchased from Sigma (St. Louis, MO, USA) unless otherwise mentioned. For bijel fabrication, Ludox TMA colloidal silica (SiO₂, 34 wt. % suspension in water), cetyltrimethylammonium bromide (CTAB, BioUltra > 99%), diethylphthalate (DEP, 99.5%), absolute ethanol (analytical grade), Nile Red, and tributyrin (97%, FG) were used. Lipase from porcine pancreas (Type II, Sigma catalog number L3126) was used for conversion of tributyrin. Round glass capillary (outer diameter 1.0 mm, inner diameter 0.58 mm) and square capillary (outer diameter 1.5 mm, inner diameter 1.05 mm, length 150 mm) were obtained from World Precision Instruments (Sarasota, FL, USA) and Atlantic International Technologies Incorporation (Rockaway, NJ, USA), respectively. The diameter of tip for the round glass capillary was narrowed to be 20–300 μm. The round capillary was inserted into the square capillary and aligned concentrically to fabricate the device for STRIPS bijel fabrication. The capillaries were coated with polydiallyldimethylammonium chloride (PDADMAC) to avoid undesirable adsorption of extruded bijel fibers. The syringe pumps were purchased from KD Scientific (Holliston, MA, USA).

Fabrication of bijel fiber by the STRIPS method. Bijel fibers were prepared by the STRIPS method as previously reported³⁰. Specifically, bijel fibers were fabricated by injecting ternary mixture and continuous phase solutions through round and square glass capillaries, respectively. The extruded ternary mixture was collected in a container filled with the continuous phase solution.

The ternary mixture was prepared by mixing 5 different liquids: (i) de-ionized water (ii) SiO₂ nanoparticle suspension in water at pH 3 (pH was adjusted by addition of 1 M HCl for uniform dispersion of silica and the concentration was changed to 32.4 wt% during pH adjustment) (iii) absolute ethanol (iv) CTAB solution (200 mM CTAB dissolved in ethanol) (v) DEP. The final 1 mL (as an example volume) of the mixture contains 0.076 mL of water, 0.108 mL of SiO₂ nanoparticle suspension, 0.143 mL of absolute ethanol, 0.265 mL of CTAB solution, and 0.408 mL of DEP. This ternary mixture contains 41 vol% DEP, 41 vol% ethanol, 18 vol% water after mixing. The continuous phase is aqueous solution at pH 3 which contains 1 mM CTAB and 5 wt% ethanol. For the fabrication of bijel fiber for tributyrin conversion, tributyrin-DEP solution (250 mM tributyrin dissolved in DEP) was used instead of pure DEP to result in a quaternary mixture. After fabrication of bijel fiber, the bicontinuous structures were imaged by using a confocal microscope (laser excitation at 480 nm and emission at 600–700 nm) with Nile red staining.

Enzymatic hydrolysis of tributyrin with bijel and biphasic system. For tributyrin conversion in the bijel system, bijel fiber was fabricated with 2.5 mL of the quaternary mixture containing 1 mL of tributyrin-DEP solution. Upon bijel formation, the continuous phase in the container was completely removed and re-filled with up to 9 mL of 100 mM potassium phosphate buffer (pH 7). This exchange ensured that concentration of CTAB in the reaction solution was reduced below its critical micelle concentration (~1 mM in water)⁴⁴. For a control experiment, 1 mL of tributyrin-DEP solution was added to 8 mL of the buffer to catalyze the reaction under the biphasic system. It should be noted that the amounts of tributyrin are the same in both experiments.

The enzymatic reactions were initiated by adding 1 mL of enzyme solution (250 U/mL lipase in the 100 mM potassium phosphate buffer) and carried out in an orbital shaker (150 rpm) at 37 °C. The experiments were conducted in duplicate. The samples were obtained every 90 seconds and incubated at 65 °C for 20 minutes to deactivate the enzyme. Thereafter, the samples were stored at -80 °C before analysis.

Analytical methods. The enzymatic reaction rate was calculated based on the amount of produced butyric acid. To measure the amount of butyric acid, we quantified its concentration by high-performance liquid chromatography (HPLC). Subsequently, we estimated the butyric acid in oil DEP by considering the partitioning coefficient of the butyric acid in DEP and water.

For HPLC analysis, UltiMate™ 3000 analytical HPLC system (Dionex, Sunnyvale, CA, USA) equipped with an Aminex HPX-87H column (Bio-Rad Laboratories, Richmond, CA, USA) was used. As the mobile phase, 5 mM of H₂SO₄ was used at a flow rate of 0.6 mL/min. The temperature of the column oven was set to 65 °C. The refractive index (RI) signal was monitored by a Shodex RI-101 detector (Shodex, Klokkefaldet, Denmark).

References

- Sanchez, S. & Demain, A. L. Enzymes and bioconversions of industrial, pharmaceutical, and biotechnological significance. *Org. Process Res. Dev.* **15**, 224–230 (2011).
- Klibanov, A. M. Improving enzymes by using them in organic solvents. *Nature*. **409**, 241–246 (2001).
- Schmid, A. *et al.* Industrial biocatalysis today and tomorrow. *Nature*. **409**, 258–268 (2001).
- Klibanov, A. Why are enzymes less active in organic solvents than in water. *Trends. Biotechnol.* **15**, 87–101 (1997).
- Cremonesi, P., Carrea, G., Sportoletti, G. & Antonini, E. Enzymatic dehydrogenation of steroids by β -hydroxysteroid dehydrogenase in a two-phase system. *Arch. Biochem. Biophys.* **159**, 7–10 (1973).
- Cremonesi, P., Carrea, G., Ferrara, L. & Antonini, E. Enzymatic Dehydrogenation of Testosterone Coupled to Pyruvate Reduction in a Two Phase System. *Eur. J. Biochem.* **44**, 401–405 (1974).
- Pesheck, P. S. & Lovrien, R. E. Cosolvent control of substrate inhibition in cosolvent stimulation of β -glucuronidase activity. *Biochem. Biophys. Res. Commun.* **79**, 417–421 (1977).
- Piradashvili, K., Alexandrino, E. M., Wurm, F. R. & Landfester, K. Reactions and polymerizations at the liquid-liquid interface. *Chem. Rev.* **116**, 2141–2169 (2016).
- Wang, H., Yang, H., Liu, H., Yu, Y. & Xin, H. A mesoporous silica nanocomposite shuttle: PH-Triggered phase transfer between oil and water. *Langmuir*. **29**, 6687–6696 (2013).
- Stepankova, V. *et al.* Strategies for stabilization of enzymes in organic solvents. *ACS Catal.* **3**, 2823–2836 (2013).
- Solans, C. & Garcia-Celma, M. J. Surfactants for microemulsions. *Curr. Opin. Colloid Interface Sci.* **2**, 464–471 (1997).
- Roux, D., Coulon, C. & Cates, M. E. Sponge phases in surfactant solutions. *J. Phys. Chem.* **96**, 4174–4187 (1992).
- Stefan, W. *et al.* The DFPase from *Loligo vulgaris* in sugar surfactant-based bicontinuous microemulsions: structure, dynamics, and enzyme activity. *Eur. Biophys. J.* **40**, 761–774 (2011).
- Schwarze, M., Pogrzeba, T., Volovych, I. & Schomacker, R. Microemulsion system for catalytic reactions and processes. *Catal. Sci. Technol.* **5**, 24–33 (2015).
- Xenakis, A., Zoumpantioti, M. & Stamatis, H. Enzymatic reactions in structured surfactant-free microemulsions. *Curr. Opin. Colloid Interface Sci.* **22**, 41–45 (2016).
- Xue, L. *et al.* The catalytic efficiency of lipase in a novel water-in-[Bmim][PF₆] microemulsion stabilized by both AOT and Triton X-100. *Colloids Surf. B Biointerfaces.* **92**, 360–366 (2012).
- Cantarella, M., Mucciante, C. & Cantarella, L. Inactivating effects of lignin-derived compounds released during lignocellulosic biomass pretreatment on the endo-glucanase catalyzed hydrolysis of carboxymethylcellulose: A study in continuous stirred ultrafiltration-membrane reactor. *Bioresour. Technol.* **156**, 48–56 (2014).
- Basu, S. N. & Pal, P. N. An unfavourable effect of shaking on fungal cellulases. *Nature*. **178**, 312–313 (1956).
- Lee, Y. K. & Choo, C. L. The kinetics and mechanism of shear inactivation of lipase from *Candida cylindracea*. *Biotechnol. Bioeng.* **33**, 183–190 (1989).
- Jelinska, A. *et al.* Denaturation of proteins by surfactants studied by the Taylor dispersion analysis. *PLoS One*. **12**, e0175838 (2017).
- Glohuber, C. & Klunzler, K. Anionic surfactants: biochemistry, toxicology, dermatology, Second ed. (1992).
- Otzen, D. E. Protein unfolding in detergents: Effect of micelle structure, ionic strength, pH, and temperature. *Biophys. J.* **83**, 2219–2230 (2002).
- Yang, H., Zhou, T. & Zhang, W. A strategy for separating and recycling solid catalysts based on the pH-triggered pickering-emulsion inversion. *Angew. Chemie - Int. Ed.* **125**, 7603–7607 (2013).
- Crossley, S., Faria, J., Shen, M. & Resasco, D. E. Solid nanoparticles that catalyze biofuel upgrade reactions at the water/oil interface. *Science*. **327**, 68–72 (2010).
- Zhang, M. *et al.* Compartmentalized Droplets for Continuous Flow Liquid-Liquid Interface Catalysis. *J. Am. Chem. Soc.* **138**, 10173–10183 (2016).
- Cho, J. *et al.* Janus colloid surfactant catalysts for: *In situ* organic reactions in Pickering emulsion microreactors. *Green Chem.* **20**, 2840–2844 (2018).
- Wei, L., Zhang, M., Zhang, X., Xin, H. & Yang, H. Pickering Emulsion as an Efficient Platform for Enzymatic Reactions without Stirring. *ACS Sustain. Chem. Eng.* **4**, 6838–6843 (2016).
- Cates, M. E. & Clegg, P. S. Bijels: a new class of soft materials. *Soft Matter*. **4**, 2132 (2008).
- Stratford, K., Adhikari, R., Pagonabarraga, I., Desplat, J. C. & Cates, M. E. Chemistry: Colloidal jamming at interfaces: A route to fluid-bicontinuous gels. *Science*. **309**, 2198–2201 (2005).
- Haase, M. F., Stebe, K. J. & Lee, D. Continuous Fabrication of Hierarchical and Asymmetric Bijel Microparticles, Fibers, and Membranes by Solvent Transfer-Induced Phase Separation (STRIPS). *Adv. Mater.* **27**, 7065–7071 (2015).
- Hirata, D. B. *et al.* Evaluation of different immobilized lipases in transesterification reactions using tributyrin: Advantages of the heterofunctional octyl agarose beads. *J. Mol. Catal. B Enzym.* **133**, 117–123 (2016).
- Otero, C., Pastor, E., Fernández, V. M. & Ballesteros, A. Influence of the support on the reaction course of tributyrin hydrolysis catalyzed by soluble and immobilized lipases. *Appl. Biochem. Biotechnol.* **23**, 237–247 (1990).

33. Hermansyah, H. *et al.* Kinetic Model for Triglyceride Hydrolysis Using Lipase: Review. *Makara J. Technol.* **11**, 30–35 (2007).
34. Gupta, R., Rathi, P., Gupta, N. & Bradoo, S. Lipase assays for conventional and molecular screening: an overview. *Biotechnol. Appl. Biochem.* **37**, 63–71 (2003).
35. Witt, J. A., Mumm, D. R. & Mohraz, A. Bijel reinforcement by droplet bridging: A route to bicontinuous materials with large domains. *Soft Matter*. **9**, 6773 (2013).
36. Erlando, A., Giacomo, C. & Piero, C. Enzyme catalysed reactions in water-organic solvent two-phase systems. *Enzyme Microb. Technol.* **3**, 291–296 (1981).
37. Oliveira, A. C. & Rosa, M. F. Enzymatic transesterification of sunflower oil in an aqueous-oil biphasic system. *J. Am. Oil. Chem. Soc.* **83**, 21–25 (2006).
38. Zhang, Z. *et al.* Significant enhancement of (R)-mandelic acid production by relieving substrate inhibition of recombinant nitrilase in toluene-water biphasic system. *J. Biotechnol.* **152**, 24–29 (2011).
39. Carrea, G. Biocatalysis in water-organic solvent two-phase systems. *Trends. Biotechnol.* **2**, 102–106 (1984).
40. Antonini, E., Carrea, G. & Cremonesi, P. Enzyme catalysed reactions in water - Organic solvent two-phase systems. *Enzyme. Microb. Technol.* **3**, 291–296 (1981).
41. Popova, M. *et al.* Iron-Functionalized Silica Nanoparticles as a Highly Efficient Adsorbent and Catalyst for Toluene Oxidation in the Gas Phase. *Chem. Cat. Chem.* **5**, 986–993 (2013).
42. Tang, D., Zhang, W., Qiao, Z., Liu, Y. & Huo, Q. Functionalized mesoporous silica nanoparticles as a catalyst to synthesize a luminescent polymer/silica nanocomposite. *RSC Adv.* **6**, 16461–16466 (2016).
43. Di Vitantonio, G., Wan, T., Haase, M. F., Stebe, K. J. & Lee, D. Robust bijels for reactive separation via silica-reinforced nanoparticle layers. *ACS Nano.* **13**, 26–31 (2019).
44. Kile, D. E. & Chiou, C. T. Water solubility enhancements of DDT and trichlorobenzene by some surfactants below and above the critical micell concentration. *Environ. Sci. Technol.* **23**, 832–838 (1989).

Acknowledgements

Acknowledgment is made to the Donors of the American Chemical Society Petroleum Research Fund, for support of this research. This work was also supported by Brain Pool Program through the Korean Federation of Science and Technology (KOFST, HR14C0006) and Global Research Laboratory Program [Grant Number NRF-2016K1A1A2912829] funded by the Ministry of Science and ICT. M.F.H. acknowledges the support from NSF-1751479.

Author Contributions

S.C. and H.G.L. equally designed the project and performed the experiments. S.C., H.G.L., D.L. and G.Y.J. conducted data analysis and wrote the manuscript. M.F.H. and K.J.S. significantly contributed to data analysis and writing of the manuscript. D.L. and G.Y.J. equally supervised the project. All authors read and approved the final manuscript.

Additional Information

Competing Interests: The authors declare no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2019