

Vietnam Journal of Chemistry, International Edition, **55**(2): 172-177, 2017
DOI: 10.15625/2525-2321.2017-00439

The photocatalytic activity of g-C₃N₄/Ta₂O₅ composite under visible light irradiation

Nguyen Thi Viet Nga^{1*}, Vo Vien^{1,2}

¹Department of Chemistry, Quy Nhon University

²Applied Research Institute for Science and Technology, Quy Nhon University

Received 28 February 2017; Accepted for publication 11 April 2017

Abstract

The g-C₃N₄/Ta₂O₅ composites were synthesized by heating mixtures of urea and Ta₂O₅ at 500 °C. The as-prepared samples were denoted as CN-500/TaO-W, where W is weight ratio of urea/Ta₂O₅ and equals to 3, 4 and 5. The materials were characterized by X-ray diffraction, X-ray photoelectron spectroscopy, and Ultraviolet-visible diffuse reflectance spectroscopy. The photocatalytic activity of CN-500/TaO-W samples was assessed by degradation of methylene blue in aqueous solution under visible light. Among them, CN-500/TaO-4 exhibited the best performance. An enhancement in photocatalytic activity of the composites is believed to be the presence of g-C₃N₄.

Keywords. g-C₃N₄, Ta₂O₅, photocatalytic activity, methylene blue, g-C₃N₄/Ta₂O₅ composite.

1. INTRODUCTION

The study of materials that could absorb light from the sun to decompose organic pollutants in water and air is not only an opportunity but also a challenge for many researchers and attracts a lot of interest from society. The semiconductors that highly exhibit the catalytic performance under light have been known as potential photocatalysts. They possess many advantages including high efficiency in conversion of solar energy, strongly catalytic activity, highly capable decomposition of organic pollutants, reusability and especially environmental friend.

Among the semiconductors, in recent years, Ta₂O₅ has attracted much attention in photocatalysis. However, with the large band gap energy (about 3.8 to 5.3 eV), its photocatalytic activity only exhibits in ultraviolet region [1], leading to limit its application in practice. To solve this problem, many works have been done to modify Ta₂O₅ by doping with some other elements to improve optical absorbance in visible light [2, 3].

At the same time, g-C₃N₄ material, a polymer organic semiconductor with graphitic-like structure, can absorb visible light (the band gap energy of about 2.7 eV), taking a lot interest of researchers due to its wide range of applications. However, the fast recombination rate of photoinduced electron-hole pair for this material leads to its low photoefficiency.

This is a drawback when using it in individual status. Therefore, many attempts to enhance the photocatalytic performance of g-C₃N₄ by modifying it with other elements have been done [4, 5].

To improve the photocatalytic capability of each material when using them in separate systems, we synthesized g-C₃N₄/Ta₂O₅ composite as described in details in the previous works [6]. In this article, we focused on effect of the ratio (urea/Ta₂O₅) on properties of the products and evaluated their photocatalytic activity by photodegrading methylene blue in aqueous solution.

2. EXPERIMENTAL

2.1. Chemicals

Tantalum pentoxide (Ta₂O₅), urea (CH₄N₂O), and methylene blue (C₁₆H₁₈N₃S) were purchased from Merck. All chemicals were analytical grade and used without further treatment.

2.2. Synthesis

Urea and Ta₂O₅ were mixed with different weight ratios (urea/Ta₂O₅ in weight = 3, 4 and 5). The mixtures were put into a porcelain cup sealed with aluminum foil and then calcined at 500 °C with a heating rate 10 °C min⁻¹ for 2 hours. The samples were denoted as CN-500/TaO-W, where W is

weight ratio between urea and Ta₂O₅.

For comparison, pure g-C₃N₄ was also prepared by heating urea at 500 °C, and denoted as CN-500.

2.3. Characterization

Powder X-ray diffraction (XRD) patterns were conducted using a Bruker D8 Advance with Ni-filtered CuK_α radiation ($\lambda = 1.5418 \text{ \AA}$). X-ray photoelectron spectroscopy (XPS) was performed using an ESCALab spectrometer (Thermo VG, UK) with monochromated AlK_α radiation. Ultraviolet-Visible Diffuse reflectance spectroscopy (UV-Vis DRS) was investigated on a GBC Instrument - 2885 spectrophotometer.

2.4. Photocatalytic Activity

To evaluate photocatalytic activity of the prepared materials, methylene blue (MB) was selected as an organic pollutant. To 200 mL of 50 mg/L MB solution, 0.1 g of the prepared sample was dispersed under stirring and the solution kept in dark condition for 3 h to reach equilibrium of adsorption-desorption process. Then, the solution was irradiated by visible light using a 75W-220V lamp with a filter cutting UV rays. MB degradation was monitored by taking suspension at irradiation time intervals of 1 h. Each suspension was centrifuged to separate the catalyst from the MB solution. The degradation rate was calculated as a function of irradiation time from the change in absorbance at wavelength of 663 nm as measured using a UV-Vis spectrophotometer (Jenway 6800).

3. RESULTS AND DISCUSSION

3.1. Characterization of catalysts

3.1.1. XRD

The XRD patterns of the samples in figure 1 show that the main diffraction peaks of all samples are from orthorhombic Ta₂O₅ [7], indicating that orthorhombic Ta₂O₅ phase still remains in the as-prepared samples under thermal treatment of the mixture of Ta₂O₅ and urea at 500 °C.

In addition, it is worth to note that an extra peak with 2θ value at about 13.2 and 27.3° belonging to g-C₃N₄ [8] (figure 1) can be seen clearly for CN-500/TaO-4. This diffraction is indexed to (100) and (002) plane, respectively, for graphite-like layer structure of g-C₃N₄. This peak is very strong for the CN-500/TaO-5, proving a larger amount of g-C₃N₄ in this material.

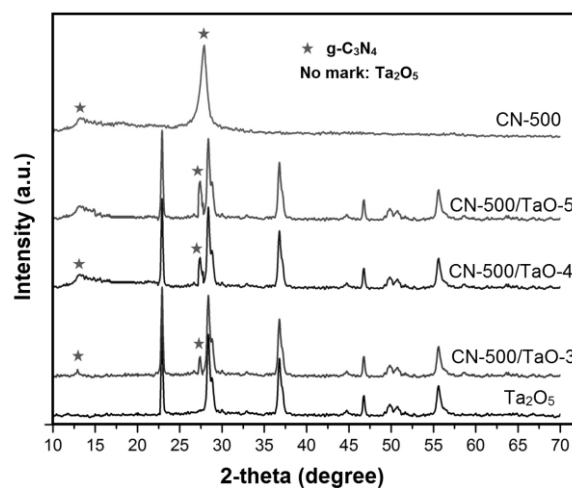


Figure 1: XRD patterns of Ta₂O₅, CN-500 and CN-500/TaO-3, CN-500/TaO-4 and CN-500/TaO-5

3.1.2. XPS

XPS was used to examine the surface composition and chemical state of C, N, O and Ta in the samples. Figure 2 and table 1 show XPS of C, N, O and Ta of a representative sample, CN-500/TaO-4.

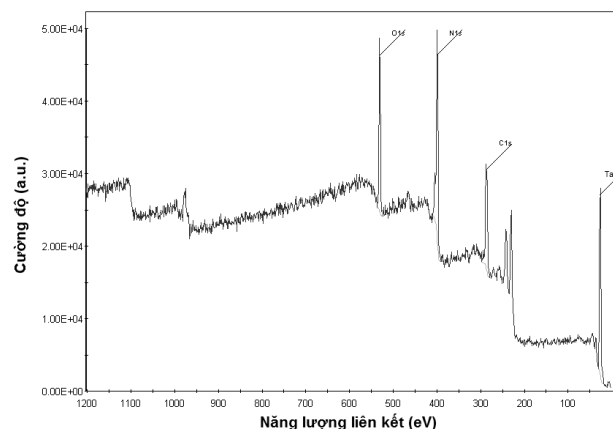


Figure 2: XPS spectrum of CN-500/TaO-4

Table 1: Binding energy of Ta4f, O1s, C1s, N1s

Orbital	Ta4f	O1s	C1s	N1s
E _{binding} (eV)	25.5 27.3	530.6	287.7 284.5	398.6

For C1s XPS, in addition to the peak at 287.7 eV corresponding to the referenced C, a strong peak at 284.5 eV can be attributed to carbon in the C-N-C configurations of g-C₃N₄ [9, 10]. The presence of g-C₃N₄ in the sample can be further confirmed by N1s XPS in table 1. The intense pic at 398.6 eV may be assigned to sp² hybridized aromatic nitrogen atoms bonded to carbon atoms (N=C) [11]. The peak at 530.6 eV for O1s is usually reported as O in Ta₂O₅

[12]. Also shown in table 1, Ta 4f7/2, and Ta 4f5/2 peaks appeared at 25.5 eV and 27.3 eV, respectively, which correspond to Ta⁵⁺ in Ta₂O₅ [12]. However, compared to pure Ta₂O₅ (26.6 eV and 28.5 eV, respectively), a slight shift to lower energy has been obtained. Such a shift may be caused by presence of an interaction between Ta and *g*-C₃N₄ in the composite. These results rather demonstrated that CN-500/TaO-4 is a composite consisting of Ta₂O₅ and *g*-C₃N₄.

3.1.3. UV-Vis DRS

The optical absorption spectra and band gap energy of Ta₂O₅, CN-500/TaO-3, CN-500/TaO-4, and CN-500/TaO-5 are shown in figure 3.

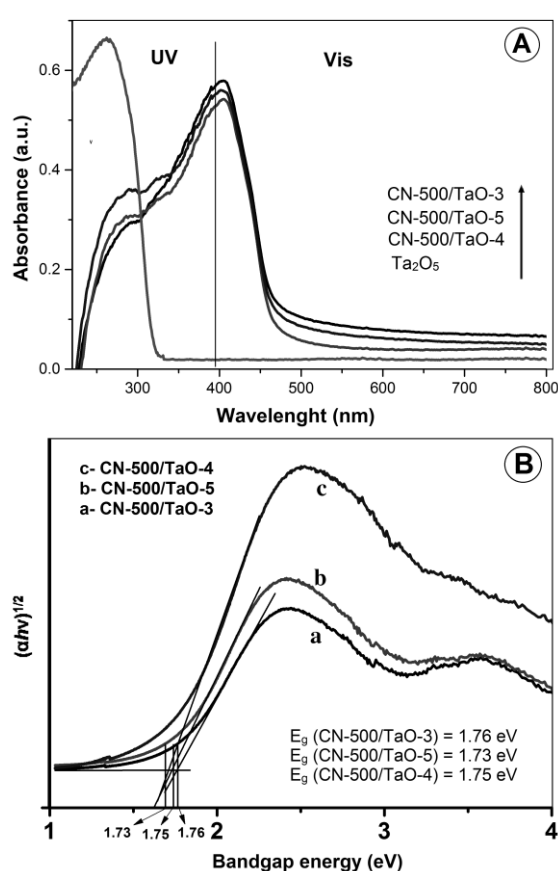



Figure 3: (A) UV-Vis DRS and (B) band gap energy of Ta₂O₅, CN-500/TaO-3, CN-500/TaO-4, CN-500/TaO-5

In figure 3A, Ta₂O₅ exhibits an absorption peak centered at approximately 275 nm which is assigned to the O2p to Ta5d charge transfer band of the Ta₂O₅ [13]. This peak can be observed in the composites, however their intensity strongly reduced. Compared to the pristine Ta₂O₅, a broad absorption band covering the range of 300-500 nm with a peak centered at about 380 nm for the composites has been obtained. This broad absorption in the visible

light region may come from *g*-C₃N₄ in the composites. This indicates that the *g*-C₃N₄ may serve as a sensitizer to extend the absorption in visible light region for the composites and thus improve their photocatalytic activities under visible light irradiation.

Based on the document [14] and Kubelka-Munk equation [15], the band gap energy of the materials was determined and shown in Figure 3B. With a reduced band gap energy, CN-500/TaO-3, CN-500/TaO-4, CN-500/TaO-5 materials might possess good catalyst activity in visible light region.

The formation of the composites can be explained by that when heating the mixture of urea and Ta₂O₅, first, polymerization of urea can occur via some following steps [16, 17]:

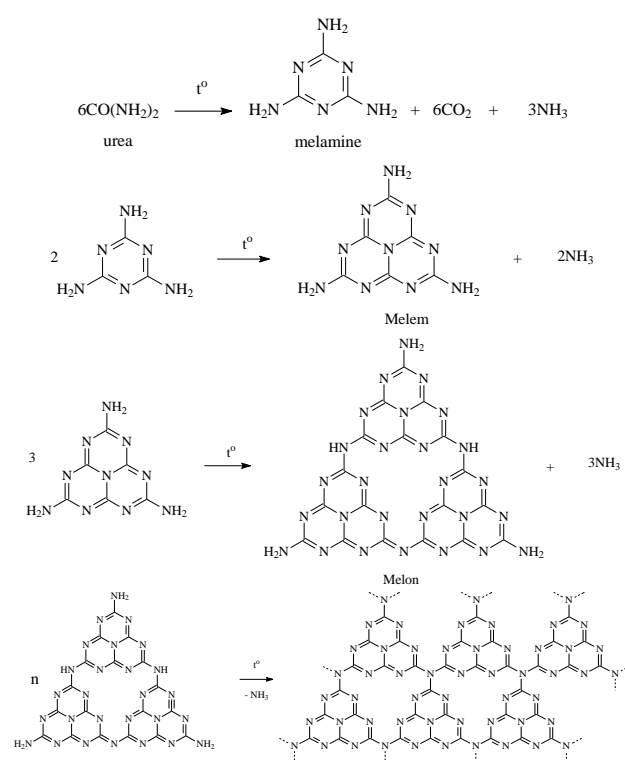

The *g*-C₃N₄ was then formed on surface of the Ta₂O₅ particles to yield the composites.

3.2. Photocatalytic Activity

The photocatalytic activity of the samples was determined by degradation of MB in water under visible light. For comparison, photocatalytic activity of the pristine Ta₂O₅ and *g*-C₃N₄ (CN-500) was also presented. Figure 4 shows the variation of MB concentration (*C*/*C*₀) versus irradiation time on the five samples.

Ta₂O₅ exhibited a low photocatalytic activity in visible light which may be due to its large band gap energy. For *g*-C₃N₄ (CN-500), although relatively

small band gap energy, about 2.70 eV [1], its photocatalytic activity is still low. This is explained by that the high recombination rate of electron-hole pair in pure $g\text{-C}_3\text{N}_4$ [18] leads to reduced photocatalytic activity.

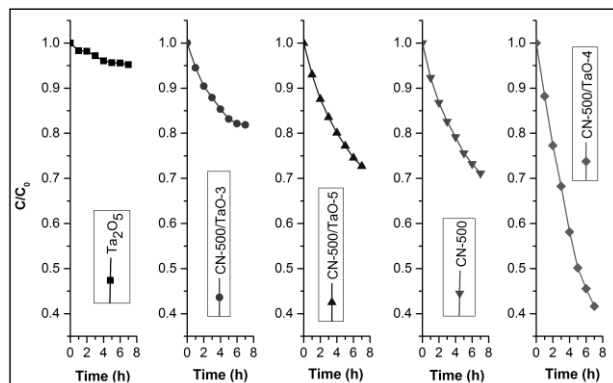


Figure 4: Photocatalytic activity of Ta_2O_5 , CN-500, CN-500/TaO-3 and CN-500/TaO-4, CN-500/TaO-5 toward the degradation of MB

For $g\text{-C}_3\text{N}_4/\text{Ta}_2\text{O}_5$ composites, a difference in catalytic performance of the materials can be observed. On the CN-500/TaO-4 sample, the decrease in C/C_0 is much faster than for the others. For the CN-500/TaO-3 and CN-500/TaO-5, the decrease in C/C_0 is slower compared to CN-500/TaO-4. This may be attributed to a reduced recombination rate of electron-hole in CN-500/TaO-4. The photocatalytic activity of CN-500/TaO-4 is better than that of Ta_2O_5 and $g\text{-C}_3\text{N}_4$, indicating that a synergistic effect occurs in the composite during the photocatalytic reaction. Graphitic $g\text{-C}_3\text{N}_4$ playing a key role in enhancement of photocatalytic activity for composites was discussed in several reports [19]. On the basis of a number of works published [20, 21], decomposition mechanism of MB on the $g\text{-C}_3\text{N}_4/\text{Ta}_2\text{O}_5$ composites is proposed in figure 5A. In these composites, the photogenerated electrons on the conduction band of the $g\text{-C}_3\text{N}_4$ can directly inject into the conduction band of Ta_2O_5 . This phenomenon can lead to a significant decrease in the electron-hole recombination for the pure $g\text{-C}_3\text{N}_4$. Hence, this may contribute to the enhancement of photocatalytic reactivity.

However, for CN-500/TaO-3 and CN-500/TaO-5 in this work, the photocatalytic activity is lower than that of the pure $g\text{-C}_3\text{N}_4$. This may be explained by that a small or too large amount of $g\text{-C}_3\text{N}_4$ in the two materials as shown in the characterizations does not form the synergistic effect mentioned above. In CN-500/TaO-5, when covered with a quite thick layer of $g\text{-C}_3\text{N}_4$, this material will show photocatalyst closing to that of pure $g\text{-C}_3\text{N}_4$. In

contrast, with a smaller amount of $g\text{-C}_3\text{N}_4$, the activity of CN-500/TaO-3 is close to Ta_2O_5 . This shows that a proper amount of $g\text{-C}_3\text{N}_4$ in composite is very important.

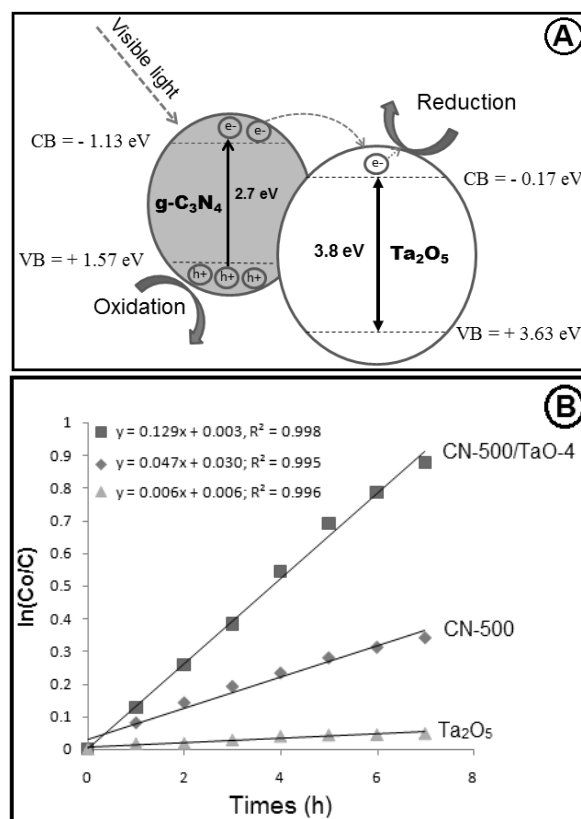


Figure 5: (A) Proposed mechanism for the photodegradation of MB on the $g\text{-C}_3\text{N}_4/\text{Ta}_2\text{O}_5$ composites; (B) linear plots of $\ln(C_0/C_t)$ vs. time for degradation of MB in aqueous solution under visible light

In order to investigate kinetics of the photocatalytic reactions, the Langmuir-Hinshelwood model has been usually employed. For solid-liquid reactions, the Langmuir-Hinshelwood equation can be expressed:

$$r = k \cdot \theta = k \cdot KC / (1 + KC) \quad (1)$$

where r and k are the reaction rate and rate constant, respectively, θ is the surface coverage, K is the adsorption coefficient of the reactant, and C is the equilibrium concentration of the reactant. When C is at low concentration, $K \cdot C \ll 1$, hence $r = k \cdot KC / (1 + KC) \approx k \cdot K \cdot C = k_{app} \cdot C$. Therefore, the pseudo first-order kinetics equation (Eq. (2)) is applied:

$$\ln(C_0/C_t) = k_{app} \cdot t \quad (2)$$

where C_0 and C_t are the reactant concentrations at reaction times, $t = 0$ and $t = t$, respectively, k_{app} is the apparent reaction rate constant.

A relationship between $\ln(C_0/C_t)$ and t was plotted in figure 5B. It can be clearly seen that the plots of $\ln(C_0/C_t)$ versus reaction time (t) are well

fitted with the pseudo first-order rate model with high correlation coefficients ($R \geq 0.995$). From the plots, the k_{app} values were calculated for CN-500/TaO-4, CN-500 và Ta₂O₅ to be 0.129 và 0.047 và 0.006 h⁻¹, respectively. These results show that the reaction rate on the catalyst CN-500/TaO-4 is much stronger than CN-500 and Ta₂O₅.

The above obtained results show that weight ratio of urea and Ta₂O₅ in reaction mixture for the synthesis of g-C₃N₄/Ta₂O₅ composites plays an important role to determine their band gap energy and photocatalytic properties.

4. CONCLUSIONS

1. Composites of Ta₂O₅ and g-C₃N₄ with different weight ratios of the precursors (urea/Ta₂O₅ = 3, 4 và 5) have been successfully synthesized with a new method by calcining urea with Ta₂O₅ at temperature of 500 °C.

2. The composites demonstrate photocatalytic activity for degradation of methylene blue in aqueous solution under visible light irradiation. Among the composites, the sample derived from thermal treatment at 500 °C, weight ratio of urea/Ta₂O₅ = 4 exhibits the best photocatalytic activity.

3. Decomposition rate of methylene blue on CN-500/TaO-4 composite is more than 2.7 times the g-C₃N₄ and 21.5 times higher than Ta₂O₅.

Acknowledgement. This research was partly funded by TEAM project (code ZEIN2016PR431).

REFERENCES

- Ramy Nashed, Walid M. I. Hassan, Yehea Ismail and Nageh K. Allam. *Unravelling the interplay of crystal structure and electronic band structure of tantalum oxide (Ta₂O₅)*, Phys. Chem. Chem. Phys., **15**, 1352-1357 (2013).
- Tomiko M. Suzuki, Tadashi Nakamura, Shu Saeki, Yoriko Matsuoka, Hiromitsu Tanaka, Kazuhisa Yano, Tsutomu Kajino and Takeshi Morikawa. *Visible light-sensitive mesoporous N-doped Ta₂O₅ spheres: synthesis and photocatalytic activity for hydrogen evolution and CO₂ reduction*, J. Mater. Chem., **22**, 24584-24590 (2012).
- Chao Zhou, Lu Shang, Huijun Yu, Tong Bian, Li-Zhu Wu, Chen-Ho Tung and Tierui Zhang. *Mesoporous plasmonic Au-loaded Ta₂O₅ nanocomposites for efficient visible light photocatalysis*, Catal. Today, **225(15)**, 158-163 (2014).
- Sergey Stolbov and Sebastian Zuluaga. *Sulfur doping effects on the electronic and geometric structures of graphitic carbon nitride photocatalyst: insights from first principles*, J. Phys.: Condens. Matter, **25**, 085507 (2013).
- Muhammad Tahir, Chuanbao Cao, Faheem K. Butt, Sajid Butt, Faryal Idrees, Zulfiqar Ali, Imran Aslam, M. Tanveer, Asif Mahmood and Nasir Mahmood. *Large scale production of novel g-C₃N₄ micro strings with high surface area and versatile photodegradation ability*, CrystEngComm, **16**, 1825-1830 (2014).
- Nguyen Van Kim, Nguyen Thi Viet Nga, Sai Cong Doanh, Le Truong Giang, Vo Vien. *Synthesis of g-C₃N₄/Ta₂O₅ composite materials with various contents of g-C₃N₄*. Vietnam Journal of Chemistry, **53(6e1,2)**, 116-119 (2015).
- T. J. Bright, D. B. Tanner, J. I. Watjen, Z. M. Zhang, and D. J. Arenas, C. Muratore, A. A. Voevodin, D. I. Koukis, T. J. Bright, J. I. Watjen, Z. M. Zhang, C. Muratore, A. A. Voevodin, D. I. Koukis, D. B. Tanner, and D. J. Arenas. *Infrared optical properties of amorphous and nanocrystalline Ta₂O₅ thin films*, Journal of Applied Physics, **114**, 083515-10 (2013).
- Gang Xin and Yali Meng. *Pyrolysis Synthesized g-C₃N₄ for Photocatalytic Degradation of Methylene Blue*, Journal of Chemistry, **2013**, 5 pages (2013).
- Yongchao Bao, Kezheng Chen. *AgCl/Ag/g-C₃N₄ Hybrid Composites: Preparation, Visible Light-Driven Photocatalytic Activity and Mechanism*, Nano-Micro Letters, **8(2)**, 182-192 (2016).
- H. Katsumata, T. Sakai, T. Suzuki, S. Kaneco. *Highly efficient photocatalytic activity of g-C₃N₄/Ag₃PO₄ hybrid photocatalysts through z-scheme photocatalytic mechanism under visible light*, Ind. Eng. Chem. Res., **53(19)**, 8018-8025 (2014).
- Y. W. Zhang, J. H. Liu, G. Wu, W. Chen. *Porous graphitic carbon nitride synthesized via direct polymerization of urea for efficient sunlight-driven photocatalytic hydrogen production*, Nanoscale, **4(17)**, 5300-5303 (2012).
- Rupesh S. Devan, Ching-Ling Lin, Shun-Yu Gao, Chia-Liang Cheng, Yung Liou and Yuan-Ron Ma. *Enhancement of green-light photoluminescence of Ta₂O₅ nanoblock stacks*, Phys. Chem. Chem. Phys., **13**, 13441-13446 (2011).
- Sreethawong T., Ngamsinlapasathian S., Suzuki Y., Yoshikawa S. *Nanocrystalline mesoporous Ta₂O₅-based photocatalysts prepared by surfactant-assisted templating sol-gel process for photocatalytic H₂ evolution*, Journal of Molecular Catalysis A: Chemical, **235**, 1-11 (2005).
- Sebastian Zuluaga, Li-Hong Liu, Natis Shafiq, Sara Rupich, Jean-Francois Veyan, Yves J. Chabal and Timo Thonhauser, *Structural band-gap tuning in g-C₃N₄*, Phys. Chem. Chem. Phys., **17**, 957-962 (2015).
- Kubelka P., Munk F. *The Kubelka-Munk Theory of Reflectance*, Zeits. f. Techn. Physik, **12**, 593-601 (1931).

16. Hideo Kinoshita. *Synthesis of melamine from urea*, The Review of Physical of Japan, **23(1)**, 1-9 (1953).
17. Yuexiang Li, Ying Xianga, Shaoqin Peng, Xuwen Wang, Lang Zhou. *Modification of Zr-doped titania nanotube arrays by urea pyrolysis for enhanced visible-light photoelectrochemical H₂ generation*, Electrochimica Acta, **87**, 794-800 (2013).
18. Muhammad Tahir, Chuanbao Cao, Faheem K. Butt, Sajid Butt, Faryal Idrees, Zulfiqar Ali, Imran Aslam, M. Tanveer, Asif Mahmoodc and Nasir Mahmood. *Large scale production of novel g-C₃N₄ micro strings with high surface area and versatile photodegradation ability*, CrystEngComm, **16**, 1825-1830 (2014).
19. Huang L., Xu H., Li Y., Li H., Cheng X., Xia J., Xu Y., Cai G. *Visible-light-induced WO₃/g-C₃N₄ composites with enhanced photocatalytic activity*, Dalton Trans., **42 (24)**, 8606-16 (2013).
20. C. Miranda, H. Mansilla, J. Yanez, S. Obregón, G. Colón. *Improved photocatalytic activity of g-C₃N₄/TiO₂ composites prepared by a simple impregnation method*, Journal of Photochemistry and Photobiology A: Chemistry, **253**, 16-21 (2013).
21. Haiyan Ji, Xiaocui Jing, Yuanguo Xu, Jia Yan, Hongping Li, Yeping Li, Liying Huang, Qi Zhang, Hui Xu and Huaming Li. *Magnetic g-C₃N₄/NiFe₂O₄ hybrids with enhanced photocatalytic activity*, RSC Adv., **5**, 57960-57967 (2015).

Corresponding author: **Nguyen Thi Viet Nga**

Department of Chemistry, Quy Nhon University

No. 170, An Duong Vuong Street

Quy Nhon City, Binh Dinh Province

E-mail: nguyenthivietnga@qnu.edu.vn; Telephone number: 0914481795.