

Fluorinated Zn^{II} Porphyrins for Dye-Sensitized Aqueous Photoelectrosynthetic Cells

Alessio Orbelli Biroli,[†] Francesca Tessore,^{*,‡} Gabriele Di Carlo,[‡] Maddalena Pizzotti,[‡] Elisabetta Benazzi,^{*,§} Francesca Gentile,[§] Serena Berardi,[§] Carlo Alberto Bignozzi,[§] Roberto Argazzi,^{||} Mirco Natali,[§] Andrea Sartorel,[⊥] and Stefano Caramori[§]

[†]Institute of Molecular Science and Technologies of the National Research Council (CNR-ISTM), SmartMatLab Centre, via Golgi 19, 20133 Milano, Italy

[‡]Department of Chemistry, University of Milano, INSTM RU, via Golgi 19, 20133 Milano, Italy


[§]Department of Chemical and Pharmaceutical Sciences and ^{||}CNR/ISOF c/o Department of Chemical and Pharmaceutical Sciences, University of Ferrara, Via L. Borsari 46, 44121 Ferrara, Italy

[⊥]Department of Chemical Sciences, University of Padova, Via Marzolo 1, 35131 Padova, Italy

Supporting Information

ABSTRACT: Three perfluorinated Zn^{II} porphyrins were evaluated as n-type sensitizers in photoelectrosynthetic cells for HBr and water splitting. All the dyes are featured by the presence of pentafluorophenyl electron-withdrawing groups to increase the ground-state oxidation potential and differ for the nature and position of the π -conjugate linker between the core and anchoring group tasked to bind the metal oxide, in order to assess the best way of coupling with the semiconductor. A phenyl-triazole moiety was used to link the carboxylic anchoring group onto the *meso* position, while an ethynyl-phenyl linker was chosen to bridge carboxylic and cyanoacrylic groups onto the β -pyrrolic position. A combination of electrochemical, computational, and spectroscopic investigations confirmed the strong electron-withdrawing effect of the perfluorinated porphyrin core, which assures all the investigated dyes of the high oxidation potential required to the coupling with water oxidation catalysts (WOC). Such an electron-poor core, however, affects the charge separation character of the dyes, as demonstrated by the spatial distribution of the excited states, leading to a nonquantitative charge injection, although tilting of the molecules on the semiconductor surface could bring the porphyrin ring closer to the semiconductor, offering additional charge-transfer pathways. Indeed, all the dyes demonstrated successful in the splitting of both aqueous HBr and water, with the best results found for the SnO₂/TiO₂ photoanode sensitized with the β -substituted porphyrin equipped with a cyanoacrylic terminal group, achieving 0.4 and 0.1 mA/cm² photoanodic currents in HBr and water under visible light, respectively. The faradaic yield for oxygen evolution in the presence of an Ir^{IV} catalyst was over 95%, and the photoanode operation was stable for more than 1000 s. Thus, the perfluorinated porphyrins with a cyanoacrylic anchoring group at the β -position should be considered for further development to improve the charge-transfer character.

KEYWORDS: porphyrins, perfluorination, dye-sensitized photoelectrosynthetic cell, hydrohalic acid splitting, water splitting

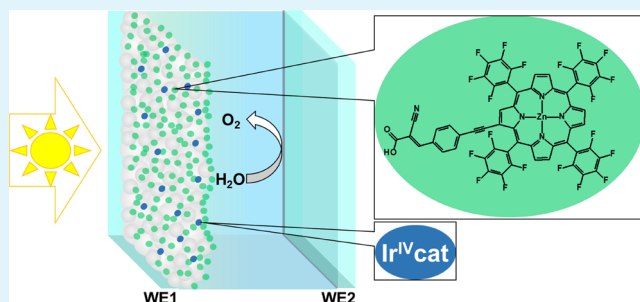

INTRODUCTION

The implementation of a solar grid depends on strategies of energy storage, among which the generation of solar fuels, where energy is stored in the form of chemical bonds of energy-rich molecules, is one of the most promising.^{1,2} Besides splitting of water into hydrogen and oxygen, hydrohalic acid (HX) splitting, notably HBr splitting,³ by photoelectrochemical means (dye-sensitized photoelectrosynthetic cells, DSPECs) is attracting an increasing interest from the scientific community. DSPECs based on polypyridine Ru^{II} complexes characterized by MLCT absorption centered at about 450 nm have been reported to intercept the Br₂/Br⁻ couple with high efficiencies, resulting in photocurrents in the milliamperage range associated with the net

production of H₂ and Br₃⁻ at the respective cathodic and photoanodic compartment of the cell.^{4,5}

Among light-harvesting molecules for DSPEC, porphyrins are particularly promising since they present various optical transitions in the visible region with high extinction coefficient (Soret or B band) covering the high energy portion of the visible spectrum and less intense, but broader, Q bands extending to the red. The electrochemical properties of Zn^{II} porphyrins can be easily tuned by varying the peripheral substituents,⁶ resulting in

Received: May 8, 2019

Accepted: August 20, 2019

Published: August 20, 2019


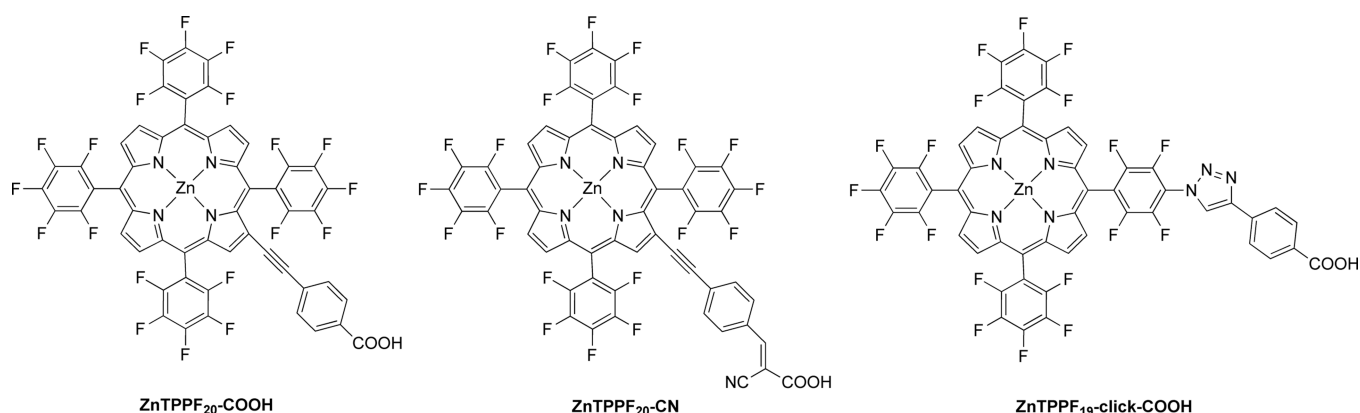


Figure 1. Zn^{II} porphyrins investigated in this work.

Scheme 1. Synthesis of β -Pyrrolic-Substituted Zn^{II} Porphyrins^a

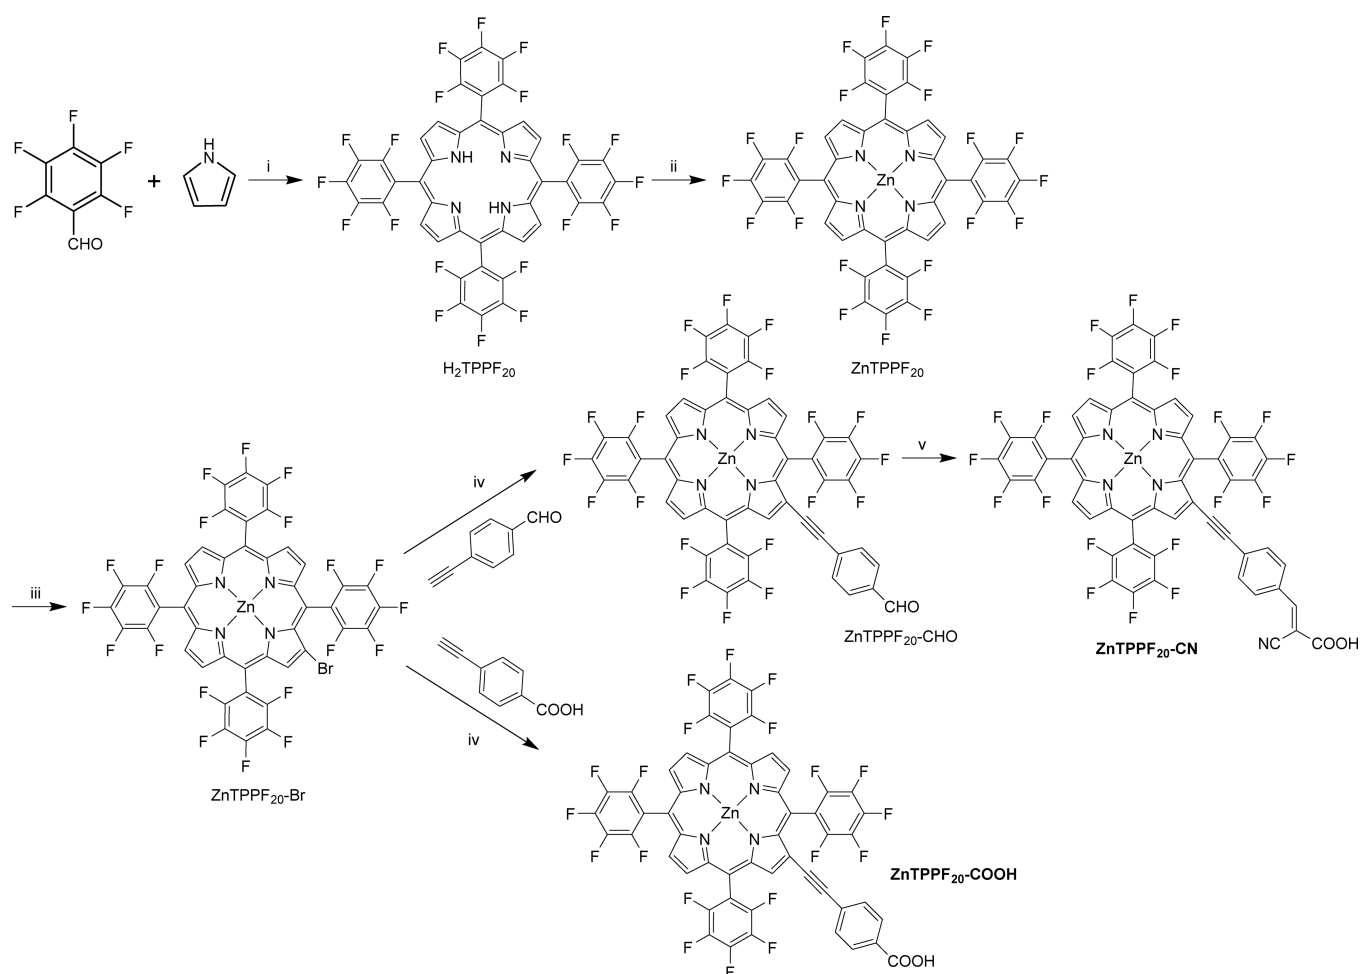


^a(i) (a) BF₃·OEt₂, N₂, CH₂Cl₂, RT, and overnight; (b) DDQ, CH₂Cl₂, RT, 2 h, and 61%. (ii) Zn(CH₃CO₂)₂·2H₂O, CHCl₃, CH₃OH, reflux, 4 h, and >98%. (iii) NBS, CH₂Cl₂, py, reflux, overnight, and product not isolated. (iv) NEt₃, [Pd(PPh₃)₄], CuI, DMF, mW 120 °C, 1 h, and 27% for ZnTPPF₂₀-COOH as well as 46% for ZnTPPF₂₀-CHO. (v) CNCH₂COOH, CHCl₃, piperidine, reflux, overnight, and 56.5%.

some of the best performing dyes for dye-sensitized regenerative solar cells.^{7–9}

A symmetrical fluorinated porphyrin has been employed by Brudvig et al.¹⁰ in conjunction with an iridium catalyst in a DSPEC for water splitting. This example was later followed by other works employing a perfluorinated free-base porphyrin based on a hydroxamic acid linkage¹¹ and by other studies

demonstrating the possibility of electron injection into semiconductors by porphyrins having very positive ground-state potentials,^{12–15} potentially useful for artificial photosynthesis.

In this contribution, we focus on the electronic and photoelectrochemical properties of a series of Zn^{II} porphyrins (Figure 1), explored in the framework of photoelectrochemical cells for HBr and water splitting. With our molecular design, we

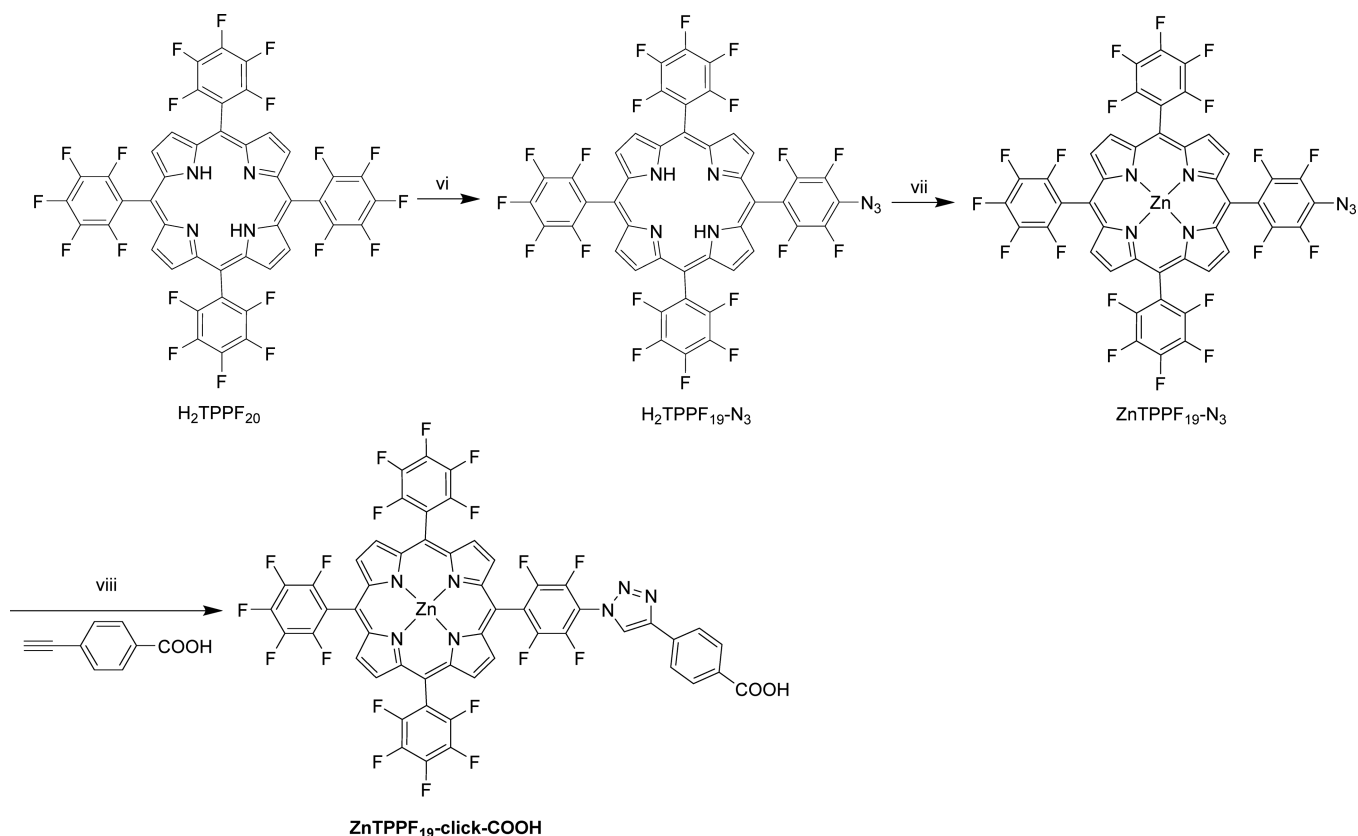Scheme 2. Synthesis of *meso*-Substituted Zn^{II}-Click Porphyrin^a

^a(vi) NaN₃, N₂, DMF, 60 °C, 3 h, and 47%. (vii) Zn(CH₃CO₂)₂·2H₂O, CHCl₃, py, reflux, 4 h, and >98%. (viii) DIPEA, CuI, N₂, 1:1 THF/CH₃CN, RT, overnight, and 89%.

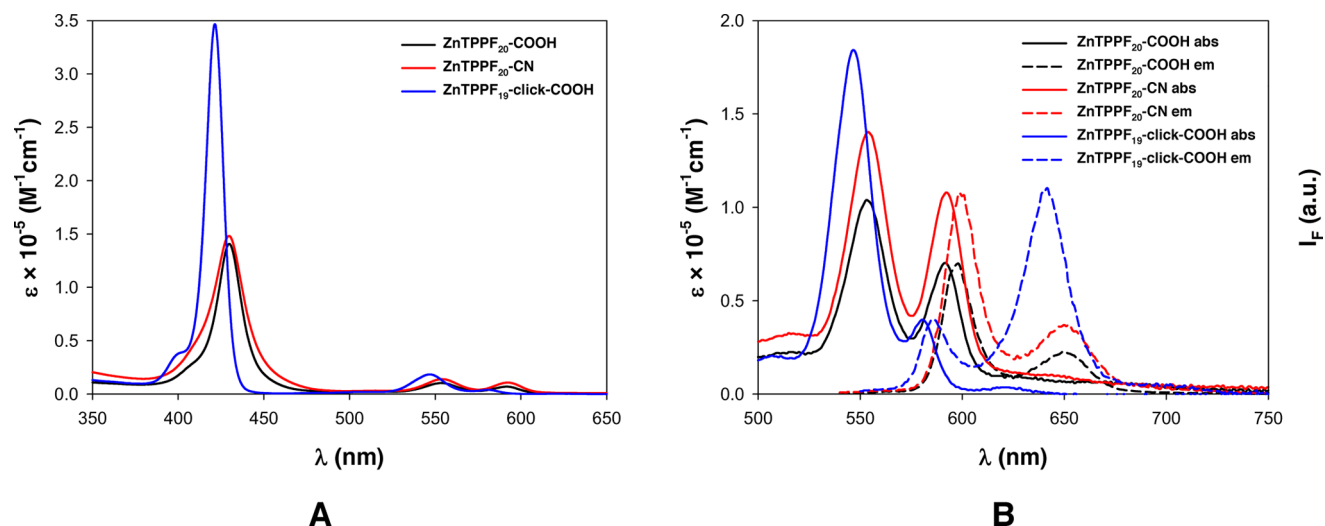


Figure 2. (A) UV-vis spectra recorded in toluene solution. (B) ϵ -Normalized spectra of Q bands and emission spectra recorded in toluene solution at 10^{-6} M concentration.

have tried to optimize charge separation at the semiconductor/dye interface by: (1) introducing four electron-withdrawing C₆F₅ groups to obtain an electron-deficient tetrapyrrolic ring and increase the driving force for electron transfer in oxidation reactions involving the photooxidized dye and (2) inserting a π -conjugated electron acceptor linker, equipped with either a carboxylic group or a cyanoacrylic group, tasked to bind metal oxides and obtain the proper directionality of the excited state


for charge injection. In addition, either β - or *meso*-substitution positions were explored to evaluate their impact on the dye energetics and sensitization efficiency.

RESULTS AND DISCUSSION

Syntheses. The syntheses of chromophores ZnTPPF₂₀-COOH and ZnTPPF₂₀-CN were performed according to Scheme 1.

Table 1. Absorption and Emission Data in Toluene Solution and Spectroscopic HOMO–LUMO Energy Gap

dye	λ_{Soret} (nm) ($\log \epsilon$)	λ_{Q} (nm) ($\log \epsilon$)	λ_{ex} (nm)	λ_{em} (nm)	τ (ns)	Φ (%)	E^{0-0} (eV)
ZnTPPF ₂₀ -COOH	430 (5.15)	553 (4.02) / 592 (3.85)	430	598 / 649	1.6	2.5	2.09
ZnTPPF ₂₀ -CN	430 (5.17)	554 (4.15) / 592 (4.03)	430	599 / 650	1.6	3.9	2.08
ZnTPPF ₁₉ -click-COOH	421 (5.54)	547 (4.27) / 581 (3.60)	421	585 / 642	1.3	2.0	2.21

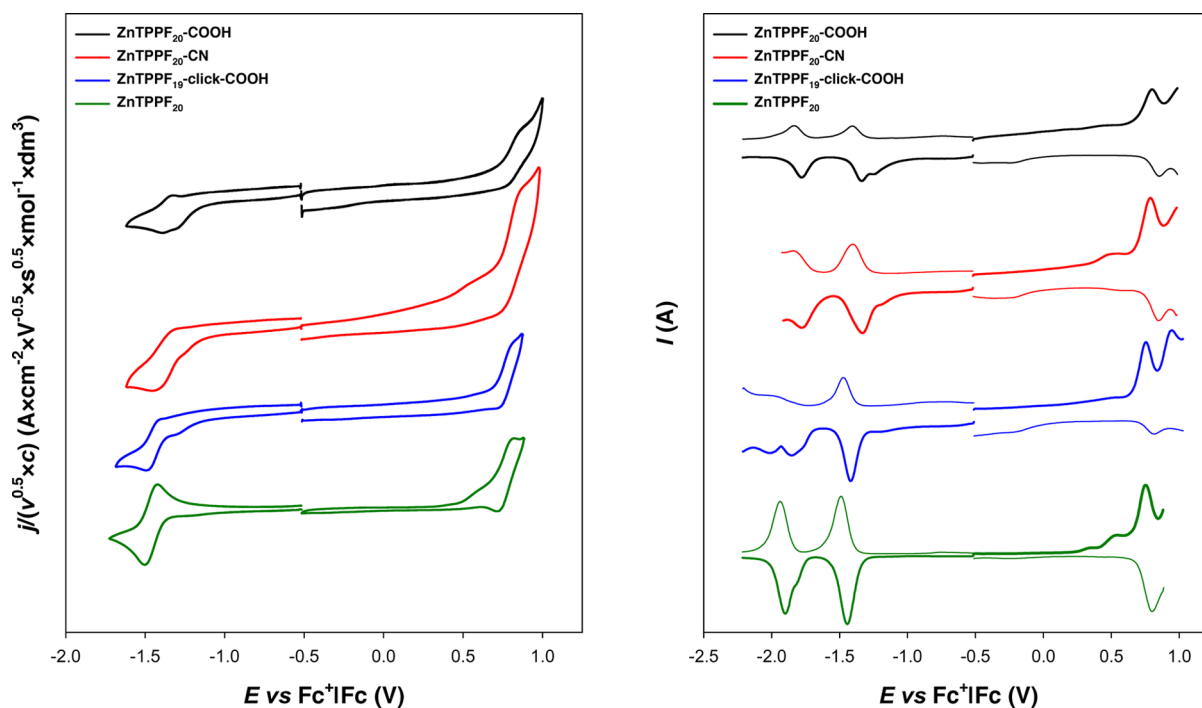**Figure 3.** CVs including only first oxidation and reduction peaks (left) and DPVs including the second reduction process (right).

The H₂TPPF₂₀ porphyrin core was prepared in good yield by the Lindsey method,¹⁶ through a BF₃·OEt₂-catalyzed condensation of pyrrole with pentafluorobenzaldehyde, followed by oxidation of the porphyrinogen to porphyrin upon the addition of DDQ.

The reaction of the free base with Zn(CH₃CO₂)₂·2H₂O afforded the Zn^{II} complex in almost quantitative yield.

Then, ZnTPPF₂₀ was monobrominated in the β -pyrrolic position by reaction with *N*-bromosuccinimide (NBS), and then the crude ZnTPPF₂₀-Br was immediately used for the following Sonogashira coupling with 4-ethynylbenzoic acid or 4-ethynylbenzaldehyde to afford ZnTPPF₂₀-COOH or ZnTPPF₂₀-CHO, respectively, with *N,N*-dimethylformamide as a solvent, triethylamine as a base, and catalytic amounts of [Pd(PPh₃)₄] and CuI, using a microwave-assisted approach successfully developed by some of us to obtain β -substituted Zn^{II} porphyrins in good yield (1 h reaction at 120 °C).¹⁷

Finally, a Knoevenagel condensation between ZnTPPF₂₀-CHO and cyanoacetic acid in CHCl₃ with piperidine as a base afforded ZnTPPF₂₀-CN in 56% yield.

The synthesis of ZnTPPF₁₉-click-COOH (Scheme 2) involved a “click-chemistry” approach. The selective nucleophilic substitution of only one of the four *para*-fluorine atoms of the pentafluorophenyl rings in 5, 10, 15, and 20 *meso* positions of H₂TPPF₂₀ was achieved by the reaction of the free base with 1 equiv of sodium azide,¹⁸ followed by complexation with Zn^{II}. Then, a Cu^I-catalyzed Huisgen 1,3-dipolar cycloaddition between ZnTPPF₁₉-N₃ and 4-ethynylbenzoic acid in a 1:1 THF/CH₃CN mixture,¹⁹ with *N,N*-diisopropylethylamine

(DIPEA) as a base afforded ZnTPPF₁₉-click-COOH in 89% yield.

The three new dyes were characterized by ¹H- and ¹⁹F-NMR spectroscopies (Figures S1–S3), elemental analysis, and mass spectrometry (see Supporting Information).

Spectroscopic and Electrochemical Properties in Solution. All the dyes have been investigated by UV–vis spectroscopy in toluene solution, and the ϵ -normalized spectra are reported in Figure 2.

The spectra of ZnTPPF₂₀-COOH and ZnTPPF₂₀-CN (Figure 2A and Figures S4 and S7) show the typical pattern of β -substituted Zn^{II} porphyrins with two evident Q bands and a sizeable redshift of about 10 nm (for both B and Q bands) compared to the *meso*-substituted compound ZnTPPF₁₉-click-COOH, indicating a more pronounced push–pull character for the β -substituted compounds. At the same time, the presence of the stronger acceptor cyanoacrylic acid group in ZnTPPF₂₀-CN barely affects the push–pull character as observed in other porphyrinic systems.^{17,20} Therefore, the high degree of fluorination, which produces a strong electron-poor porphyrin core, is not weakening the effect of the cyanoacrylic group.

On the contrary, the absorption pattern of ZnTPPF₁₉-click-COOH (Figure S10) resembles that of *meso*-substituted porphyrins where only one peak is clearly detectable for the Q band. However, a more detailed analysis reveals a second Q band at 581 nm featured by a very low intensity (Figure 2A).

Normalized emission spectra recorded for each dye at a 10^{−6} M concentration in toluene solution are reported in Figure 2B, and the relative data are summarized in Table 1.

Table 2. Key DPV Features of Dyes and Benchmark, their Electrochemical Energy Levels HOMO and LUMO Derived Therefrom $E^{0'}_{\text{Ia}}$ and $E^{0'}_{\text{Ic}}$ (or $E_{\text{p,Ia}}$ and $E_{\text{p,Ic}}$), all Referred to Fc^+/Fc

dye	$E_{\text{p,Ia}}$ (V) (Fc^+/Fc)	$E^{0'}_{\text{Ia}}$ (V) (Fc^+/Fc)	$E_{\text{p,Ic}}$ (V) (Fc^+/Fc)	$E^{0'}_{\text{Ic}}$ (V) (Fc^+/Fc)	HOMO (eV)	LUMO (eV)	$\Delta E^{0'}$ (V) ($E_{\text{g,EC}}$ (eV))
ZnTPPF ₂₀ -COOH	0.80	0.82	-1.34	-1.36	-5.62	-3.44	2.18
ZnTPPF ₂₀ -CN	0.79	0.81	-1.33	-1.35	-5.61	-3.45	2.16
ZnTPPF ₁₉ -click-COOH	0.75	0.77	-1.42	-1.44	-5.57	-3.36	2.21
ZnTPPF ₂₀	0.75	0.77	-1.44	-1.46	-5.57	-3.34	2.23

Table 3. Hole (Blue) and Electron (Green) Density Maps Corresponding to Optical Transitions in Perfluorinated Zn^{II} Porphyrins^a

Transition number	Computed vertical excitation energies (eV/oscillator strength)	Experimentally observed band (eV) (band type)	Energy dispersion $ \Delta E $ (eV) with respect to exp. band maximum	KS orbital contribution to excited state	Density map
ZnTPPF₁₉-click-COOH					
1	2.26/1.3 × 10 ⁻³	2.25 (Q)	0.01	H-1 → L -0.17035 H-1 → L+1 0.46155 H → L 0.47475 H → L+1 0.17096	
2	3.06/1.876	2.96 (B)	0.09	H-8 → L -0.10630 H-1 → L 0.47859 H → L+1 0.48478	
3	3.07/1.522	2.96 (B)	0.10	H-8 → L+1 -0.11016 H-1 → L+1 0.48737 H → L -0.48419	
ZnTPPF₂₀-COOH					
2	2.26/0.044	2.22 (Q ₁) 2.07 (Q ₂)	0.04 0.19	H-1 → L 0.19031 H-1 → L+1 0.41454 H → L 0.50371 H → L+1 -0.18224	
3	2.83/0.948	2.90 (B)	0.07	H-2 → L 0.53246 H-1 → L 0.14917 H-1 → L+1 0.28229 H → L -0.26882 H → L+1 0.17466	
4	3.00/0.8006	2.90 (B)	0.10	H-2 → L+1 0.40042 H-1 → L -0.34594 H-1 → L+1 0.20572 H → L -0.16015 H → L+1 -0.37446	
5	3.08/1.0446	2.90 (B)	0.18	H-3 → L 0.18509 H-2 → L 0.41892 H-1 → L+1 -0.36639 H → L 0.28678 H → L+1 -0.10032 H → L+2 0.14562	
ZnTPPF₂₀-CN					
1	2.22/0.203	2.22 (Q ₁) 2.07 (Q ₂)	0.00 0.19	H-1 → L 0.21646 H-1 → L+1 -0.34679 H → L 0.52670 H → L+1 0.18437 H → L+2 -0.10319	
2	2.23/0.014	2.22 (Q ₁) 2.07 (Q ₂)	0.01 0.16	H-1 → L 0.47176 H-1 → L+1 0.17604 H-1 → L+2 -0.13478 H → L -0.22586 H → L+1 0.40923	
3	2.58/0.841	2.22 (Q ₁)	0.36	H-2 → L -0.18134 H-1 → L+1 0.32706 H → L 0.33183 H → L+1 0.110406 H → L+2 0.47185	
5	2.79/0.549	2.90 (B)	0.11	H-2 → L 0.56634 H-1 → L+1 -0.15159 H-1 → L+2 0.16548 H → L+2 0.33595	
6	3.01/0.400	2.90 (B)	0.11	H-2 → L+1 0.51314 H-1 → L 0.16443 H-1 → L+1 -0.11269 H-1 → L+2 -0.28653 H → L+1 -0.31030	
7	3.13/1.319	2.90 (B)	0.23	H-2 → L 0.17876 H-2 → L+1 0.28888 H-2 → L+2 -0.30189 H-1 → L+1 0.34701 H-1 → L+2 0.12718 H → L 0.16246 H → L+1 0.12075 H → L+2 -0.27810	

^aTransitions are numbered according to Figure S22.

As observed in the UV–vis spectra, β - and *meso*-substituted porphyrins present similar emission spectra reflecting the shape of their absorption Q bands. The excitation spectra (Figures S5, S8, and S11) superimpose with the relative UV–vis absorption spectra, indicating that the population of the lowest emitting state occurs upon both the Soret and the Q band excitation. Moreover, the minimal Stokes shift between the peak of the absorption band at lower energy and the peak of the emission band at higher energy confirms the rigidity of these systems and reduced molecular structure distortions during the absorption and emission processes.

The lifetime has been measured in solution by the single-photon counting method using a pulsed laser source at 450 nm (Experimental Section in the Supporting Information), and from the deconvolution fitting of the decay profiles (Figures S6, S9, and S12), τ values in the range 1.3–1.6 ns for each dye have been recorded (Table 1). Quantum yield (QY, ϕ) of fluorescence has been measured in toluene solution at 10^{-6} M concentration, obtaining values in the range of 2–4% (Table 1).

Finally, from the spectroscopic data recorded in toluene, the E^{0-0} value has been calculated, which corresponds to the spectroscopic HOMO–LUMO energy gap (Table 1).

The electronic properties of the dyes have been investigated by cyclic voltammetry (CV) and compared to those of ZnTPPF₂₀ under the same experimental conditions, as a benchmark. Complete CV patterns obtained at 0.2 V/s on a glassy carbon (GC) electrode in 0.1 M tetrabutylammonium perchlorate (TBAP) in DMF solution are reported in the Supporting Information (Figures S13, S15, S17, and S19) and in Figure 3, and their key features are summarized in Table S1 in the Supporting Information.

In all cases, one oxidation peak and at least two reduction peaks have been observed in the potential window investigated, consistent with the electron-poor features of this class of perfluorinated porphyrins, resulting in a general anodic shift of the faradaic waves involving the frontier energy levels of these chromophores. The oxidation peak and the first reduction peak of each dye are reversible or quasi-reversible from both the electrochemical and chemical point of view, allowing for the calculation of the formal potentials of first oxidation (anodic, $E^{0'}_{pa}$) and first reduction (cathodic, $E^{0'}_{pc}$) processes in the chosen supporting electrolyte (formal potentials $E^{0'}$ approximate standard potentials E^0 under the assumption of neglecting the activity coefficients). The experimental $E^{0'}$ values also allow the evaluation of the electrochemical HOMO and LUMO energy levels⁶ and therefore of the HOMO–LUMO energy gap E_g (Table S1), employing the ferrocenium/ferrocene redox couple as a reference for intersolvental comparison of electrode potentials.²¹

The electrochemical HOMO–LUMO E_g values of the β -substituted dyes are slightly higher than the spectroscopic ones (Table 1), in particular for ZnTPPF₂₀-CN for which a narrower gap was expected.

In search for a better resolution of the relevant electrochemical processes, DPV analysis has allowed a clearer determination of the peak potentials (Figure 3 and Figures S14, S16, S18, and S20). Moreover, a perfect correspondence with the CV data has been obtained for the dyes having a well-defined CV pattern, confirming the great potential of this technique for the evaluation of ambiguous cases.

The energy gaps obtained by DPV measurements (Table 2) are in good agreement with the spectroscopic data and with a narrower HOMO–LUMO gap achieved for the porphyrin

endowed with a cyanoacrylic group, as reported in the literature.¹⁷

The *meso*-substituted ZnTPPF₁₉-click-COOH dye shows electrochemical potentials very similar to those of ZnTPPF₂₀, resulting in the same oxidation potential values, but in a slightly shifted reduction process. In general, it can be concluded that the strongly oxidizing ground-state potential of these species should allow to trigger energy demanding oxidation reactions, keeping at the same time a sufficient driving force for the oxidative quenching of the excited state by charge injection to appropriate semiconductors.

Computational Results. TDDFT calculations in THF (IEFCPM) at the B3LYP 6311 G* level¹⁷ were used to extract information about the electronic distribution in the chromophores at their singlet ground and excited states. The EDDMs (electron density difference maps) generated from the Kohn–Sham (KS) orbitals associated with the main electronic transitions in the visible region are shown in Table 3. The computed electronic transitions, the KS contributions to the calculated optical transitions, and the KS orbitals involved in these latter are reported in Figures S21 and S22 and Table 3. Generally, despite a systematic red shift (0.1–0.2 eV) of the most intense transition associated with the B band, the computation reproduces in an acceptable fashion the main spectral features of these fluorinated Zn^{II} porphyrins. In all cases, the group of the most intense transitions falls in proximity of the experimental B band centered around 2.9 eV. Consistent with the experimental evidence, the *meso*ZnTPPF₁₉-click-COOH architecture is characterized by the narrowest B band, originated by two nearly degenerate transitions (2.3 and 3.06–3.07 eV, Table 3) from the highest occupied orbitals to LUMO and LUMO+1. In the case of ZnTPPF₂₀-CN and ZnTPPF₂₀-COOH, a larger number of allowed transition occurs, broadening the B band, thanks to allowed excitations from HOMO–2 to LUMO+2. Indeed, while in ZnTPPF₁₉-click-COOH, the B band excitation leads to ring-centered EDDMs with practically no change in the electronic density of the electron acceptor arm, the electronic redistribution following high energy optical excitation in ZnTPPF₂₀-CN and ZnTPPF₂₀-COOH shows a significant charge-transfer character where, however, the linker arm is depleted of electronic density, while the tetrapyrrolic ring is enriched, consistent with the strong electron-withdrawing character induced by the perfluorinated substituents. Thus, in principle, in all cases, the electronic distribution upon interception of the B band is unfavorable to charge injection into the semiconductor. Concerning the lowest singlet state, generated upon Q bands excitation for energy ≥ 2.2 eV, weaker oscillator strengths are correctly predicted for all structures under examination. Again, no involvement of the electron accepting arm is found for ZnTPPF₁₉-click-COOH (transition 1 at 2.26 eV), while ZnTPPF₂₀-CN shows a small increase in the electronic density of the cyanoacrylic group, with most of the hole density delocalized on the ring. The largest electronic density on the arm is however found for transition 3 (2.58 eV). No involvement of the electron-withdrawing arm is found with ZnTPPF₂₀-COOH either, probably due to the weaker electron-accepting properties of its linker compared to that of ZnTPPF₂₀-CN. Higher energy excitations (>2.23 eV) result in either π – π^* states centered on the tetrapyrrolic structure or in their mixing with charge-transfer states shifting charge density from the linker to the electron-poor ring. Thus, calculations predict that in none of the chromophores under investigation, a really satisfactory directionality of the excited states for electron injection is

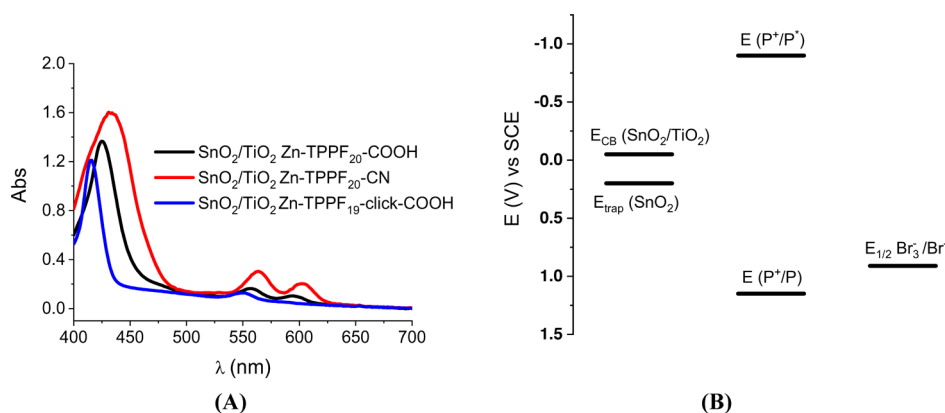


Figure 4. (A) Absorption spectra of $\text{SnO}_2/\text{TiO}_2$ electrodes sensitized with $\text{ZnTPPF}_{20}\text{-COOH}$, $\text{ZnTPPF}_{20}\text{-CN}$, and $\text{ZnTPPF}_{19}\text{-click-COOH}$. (B) Electrochemical levels relevant to the photoelectrochemical process in 0.1 M HBr/0.4 M NaBr. The diagram was built by considering the onset of the reductive processes of the different semiconductor films together with the energy levels of $\text{ZnTPPF}_{20}\text{-CN}$ from Table 4. The half wave potential of the $\text{Br}_3^-/\text{Br}^-$ couples was measured by cyclic voltammetry at a glassy carbon electrode at pH 1. Notice that $\text{ZnTPPF}_{20}\text{-CN}$ was used to exemplify the energetics common to the porphyrin (P) series under consideration and that the $E_{1/2}$ potential of the redox couple may not describe the details of the energetics involved in the photoinduced oxidation of Br^- .^{2,4}

obtained, with the possible exception represented by $\text{ZnTPPF}_{20}\text{-CN}$ for which some states, including the lowest one, could lead to an acceptable coupling for semiconductor sensitization. Clearly, the realistic situation on the disordered nanocrystalline semiconductor is more complicated: tilting of the molecules on the semiconductor surface could bring the porphyrin ring closer to the semiconductor, in a situation favorable for through-space remote charge injection. The accidental proximity of the dye ring to other adjacent nanoparticles may also offer additional charge-transfer pathways, which cannot be accounted for by this type of simple calculation.

Spectroscopic and Electrochemical Characterization of the Sensitized Photoanodes. Adsorption from 0.1 mM dye solutions on TiO_2 leads to a very high absorption in the Soret band region, which in all cases saturated the instrumental response with absorbance values greater than 3, while the absorbance in the Q region varies in the order $\text{ZnTPPF}_{20}\text{-CN}$ (≈ 0.9) > $\text{ZnTPPF}_{20}\text{-COOH}$ (≈ 0.7) > $\text{ZnTPPF}_{19}\text{-click-COOH}$ (≈ 0.5) (Figure S23). Absorption spectra thus point to a better surface uptake of the β structures compared to *meso*- $\text{ZnTPPF}_{19}\text{-click-COOH}$ having the highest molar extinction coefficients. At the same time, the better harvesting achieved by $\text{ZnTPPF}_{20}\text{-CN}$ is probably due to both its stronger dipole moment and superior affinity to the TiO_2 surface with respect to $\text{ZnTPPF}_{20}\text{-COOH}$. Sensitization of SnO_2 electrodes (Figure S24) results in the same trend already described with TiO_2 , but the optical density of the resulting photoanodes was considerably lower, with maximum values in the B band of the order of ≈ 0.6 . The dye uptake by SnO_2 thin films could be improved by treating them with TiCl_4 followed by firing at 450 °C to form a nanometric coating of TiO_2 on top of the SnO_2 nanoparticles and increase the surface area and the reactivity for dye adsorption. AFM maps of the SnO_2 electrodes following TiCl_4 treatment show an increased surface roughness (Figure S27), with R_q increasing from 30.9 to 47.1 μm after the treatment, without a noticeable increase in the SnO_2 nanoparticle size, having a diameter varying from 20 to 40 nm (Figures S28 and S29). This evidence is consistent with the coverage of SnO_2 by thin TiO_2 , which cannot be clearly resolved in our AFM maps on such type of disordered substrate but is evident in the form of a microroughness in the cross-sectional analysis by sampling along various directions of the imaged surface portion at high magnification. As a result, the absorbance

of $\text{SnO}_2/\text{TiO}_2$ electrodes loaded with this series of Zn^{II} porphyrins more than doubles relative to unmodified SnO_2 , reaching a close-to-unity light harvesting in the Soret region (Figure 4A). By using $A(\lambda) = 1000\epsilon(\lambda)\Gamma$ it is possible to calculate the surface loading Γ of the dyes, of the order of 2×10^{-8} mol/cm², in good agreement with ICP results based on Zn determination, affording values around 1.7×10^{-8} mol/cm². The $\text{SnO}_2/\text{TiO}_2$ photoanodes were thus preferred over the SnO_2 ones for the subsequent photophysical and photoelectrochemical investigations. It is also interesting to evaluate the impact of the TiCl_4 treatment on the SnO_2 energetics, which can be conveniently studied by electrochemical means in a solvent medium relevant to the intended use of such photoanodes. In aqueous 0.1 M HBr + 0.4 M NaBr, SnO_2 is characterized by a broad reductive wave, which appears chemically reversible (Figure S30), having onset at about 0.3 V versus SCE, followed by a small hump centered at about 0.2 V, assigned to the filling of surface states as the potential is scanned toward negative values. A change in the J/E slope occurs at about -0.05 V versus SCE probably indicating the threshold of the reduction of conduction band states. Consistent with the n-type nature of SnO_2 in the chosen electrolyte, no faradaic processes are observed in the interval 0.3/0.6 V versus SCE where a small capacitive current (ca. 1 μA) flows. $\text{SnO}_2/\text{TiO}_2$ electrodes (Figure S30) maintain the same conduction band edge energetics as of those of bare SnO_2 , with a clear reductive wave having onset between 0 and -0.05 V versus SCE, but the electrochemical processes originating from sub-band gap states are dramatically reduced in intensity, consistent with the passivation of many SnO_2 surface states by the TiO_2 layer. Adsorption of $\text{ZnTPPF}_{20}\text{-CN}$ does not change the surface energetics significantly, being the electrochemical features practically coincident with that of the undyed electrode in the -0.2/0.8 V versus SCE interval (Figure S32). A notable exception occurs at potentials higher than 1 V versus SCE where the electrocatalytic oxidation of Br^- mediated by the surface-adsorbed dye becomes evident, with an irreversible wave having a $\times 10$ increased intensity compared to the same process observed at bare $\text{SnO}_2/\text{TiO}_2$ (in this latter case, the oxidation process occurs ostensibly at some exposed FTO). This is already a qualitative confirmation of the ability of the oxidized

porphyrins to intercept the redox chemistry of the $\text{Br}^-/\text{Br}_3^-$ couple.

Finally, while data in Table 2 are useful to understand the general electronic properties of the dye series under investigation, the energetics relevant to charge injection and regeneration are more properly accounted for by including the interaction of the dye with the semiconductor oxide and the influence of operational solvent chosen for the DSPEC (water), wherein the electrochemical measurements in solution are precluded due to solubility. Emission spectra and DPV were recorded on SnO_2 treated with TiCl_4 : the emission spectra (Figure S25) show the vibronic components associated with the lowest excited singlet state, with a slight blue shift with respect to the measurements in organic solution from which the E^{0-0} spectroscopic energy can be determined. DPV afforded (Figure S26, Table 4) the first ground-state oxidation potential (E_{pa}),

Table 4. Spectroscopic Energy (E^{0-0}), anodic Peak Potential (E_{pa}) and Oxidation Potential (E_{ox}^*) of $\text{SnO}_2/\text{TiO}_2$ Electrodes Modified with $\text{ZnTPPF}_{20}\text{-COOH}$, $\text{ZnTPPF}_{20}\text{-CN}$, and $\text{ZnTPPF}_{19}\text{-click-COOH}$ ^a

dye	E^{0-0}	E_{pa} (V vs SCE)	E_{ox}^* (V vs SCE)
$\text{ZnTPPF}_{20}\text{-COOH}$	2.04	1.20	-0.84
$\text{ZnTPPF}_{20}\text{-CN}$	2.05	1.15	-0.9
$\text{ZnTPPF}_{19}\text{-click-COOH}$	2.09	1.17	-0.92

^aMeasurements performed on the thin films in contact with in 0.1 M HClO_4 .

and the first excited state oxidation potential was consequently calculated according to $E_{\text{ox}}^* = E_{\text{pa}} - E^{0-0}$. These three structures exhibit similar ground and excited state energetics, with first excited state oxidation potential sufficiently negative for injection into semiconductor electrodes and a sufficiently positive ground state to trigger, in principle, oxidation of bromide or activate water oxidation catalysts. The electrochemical potentials of interest to the sensitization processes, by considering $\text{SnO}_2/\text{TiO}_2$ electrodes, are summarized in Figure 4B where $\text{ZnTPPF}_{20}\text{-CN}$ was used to exemplify the energetics common to the porphyrin (P) series under consideration.

Transient Absorption Spectroscopy. Transient absorption (TA) spectra, following 532 nm excitation of $\text{ZnTPPF}_{20}\text{-CN}$ either in toluene solution or loaded on TiO_2 or $\text{SnO}_2/\text{TiO}_2$ thin films, are reported in Figure 5. $\text{ZnTPPF}_{20}\text{-COOH}$ and $\text{ZnTPPF}_{19}\text{-click-COOH}$ share qualitatively common spectroscopic features with those of $\text{ZnTPPF}_{20}\text{-CN}$, and they are

reported, for brevity, in the Supporting Information (Figures S33, S35, and S36).

The TA spectra of 5×10^{-4} M $\text{ZnTPPF}_{20}\text{-CN}$ in toluene (Figure 5A) are consistent with the formation of the T1 state, dominated by the strong absorption centered at 500 nm, whose population falls within the excitation pulse and disappears completely within about 10 μs (Figure 5A). The 500 nm absorption is followed by the ground-state bleaching and by a flat and featureless absorption extending to the NIR. Such features have been observed in other β -substituted porphyrins carrying donor and acceptor groups²² but are also typical of more symmetric structures²³ where the lowest electronic states are prevalently localized on the tetrapyrrolic ring, indicating a relatively small influence of the electron-withdrawing linker arm on the electronic properties of the lowest excited state.

TA spectra of the dye-sensitized semiconductors are characterized, along with the Q band bleaching at 570 and 610 nm, by a well-defined sharp absorption band centered around 700 nm, which is assigned to the oxidized dye $\text{ZnTPPF}_{20}\text{-CN}^+$ formed upon charge injection into the semiconductor. On TiO_2 , the spectral signature of the oxidized dye is accompanied by the 500 nm absorption feature of the excited state decreasing by 33% during the first 120 ns, whereas in other spectral regions where the excited state absorption is less important, a marginal evolution of TA spectra is found. For example, the 710 nm band dominated by $\text{ZnTPPF}_{20}\text{-CN}^+$ is reduced, due to recombination, by just about 3% on a comparable time scale. The residual T1 absorption indicates that, at least for a fraction of the $\text{ZnTPPF}_{20}\text{-CN}$ population adsorbed on TiO_2 , the intersystem crossing process from S1 to T1 is kinetically competitive with charge injection into the semiconductor and that, ostensibly, T1 is not capable to inject.²⁴

Ultrafast measurements on structurally related, albeit not identical, compounds, revealed that intersystem crossing on push-pull β -porphyrins occurs within 200/400 ps, setting thus a lower limit for the charge injection rate constant on similar time scales.²⁵ The triplet residue on the TiO_2 film is even more pronounced in $\text{ZnTPPF}_{20}\text{-COOH}$ and $\text{ZnTPPF}_{19}\text{-click-COOH}$ (Figure S35), confirming, in qualitative agreement with the calculations, the better directionality and surface coupling of the lowest $\text{ZnTPPF}_{20}\text{-CN}$ singlet state for charge injection.

The observation of excited state residual on TiO_2 is somewhat surprising, in consideration of the dye excited state oxidation potential of the order of -0.8/-0.9 V versus SCE, while the flat band potential of TiO_2 can be estimated (in V vs SCE) according to $V_{\text{fb}} = -0.4 - 0.06 \times \text{pH}$.²⁶ The activation energy for the electron transfer, ΔG_{ET}^* , is given, according to the classical

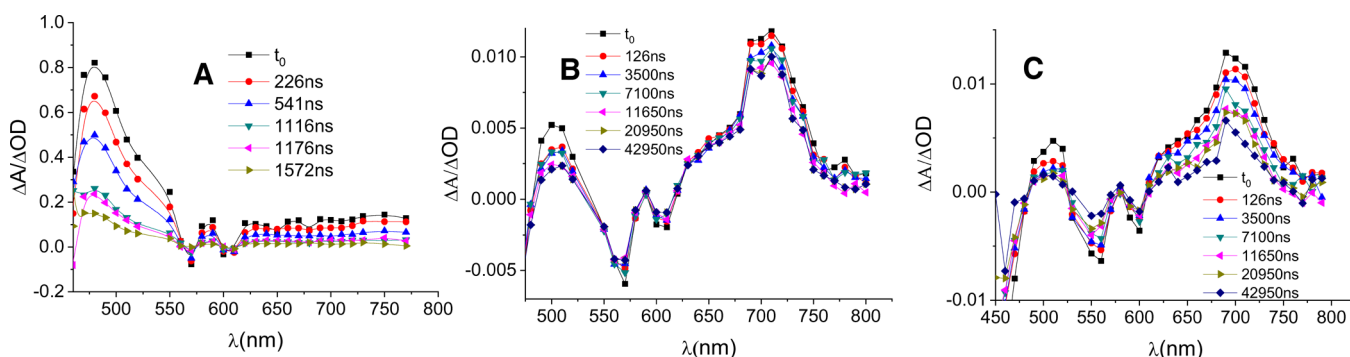


Figure 5. (A) Transient absorption spectra of $\text{ZnTPPF}_{20}\text{-CN}$ in toluene solution (5×10^{-4} M). (B) Loaded on TiO_2 . (C) Loaded on $\text{SnO}_2/\text{TiO}_2$. Thin films were in contact with 0.1 M NaClO_4 at pH 3. Oscilloscope input impedance is 350 Ω .

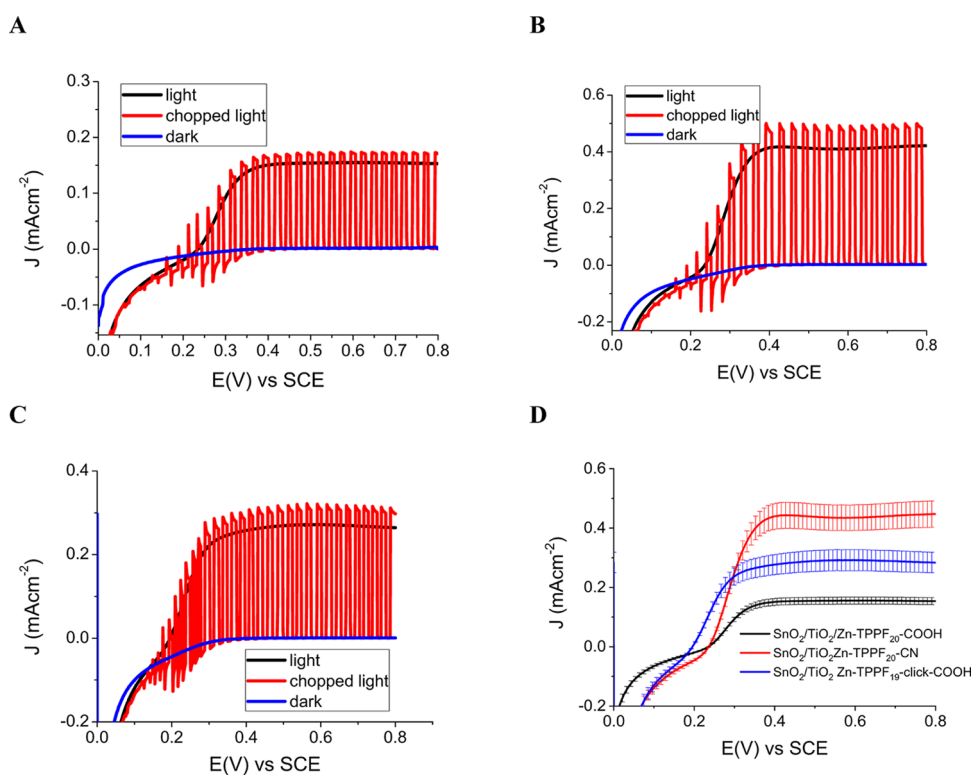


Figure 6. Current voltage curves recorded with SnO₂/TiO₂ photoanodes in HBr 0.1 M, NaBr 0.3 M under AM 1.5 G. (a) ZnTPPF₂₀-COOH, (b) ZnTPPF₂₀-CN, (c) ZnTPPF₁₉-click-COOH photoanodes irradiated from the FTO side, and (d) averaged J/E curves taken on a series of 10 photoanodes.

Marcus expression by $(\Delta G_{ET}^* = (E_{ox}^* - E_{FB} + \lambda)^2 / 4\lambda)^{27}$ where the reorganization energy $\lambda = \lambda_{in} + \lambda_{out}$ of symmetrical porphyrins in apolar solvents, such as toluene, was estimated of the order of 0.4 eV.²⁸ However, it has been also reported that the presence of perfluorinated groups may increase significantly λ_{in} due to high-frequency C–F stretching associated with the contraction and expansion of the porphyrinic core, up to doubling the value reported in the presence of conventional C–H bonds (i.e., 0.8 eV).²⁹ It has also to be considered that the outer contribution λ_{out} increases in aqueous media, where reorganization of solvent dipoles is important. By taking into account these facts, the electron transfer from the excited dye to TiO₂ in aqueous acidic medium (from pH 1 to 3, which are the conditions explored in this work) may become activated in the presence of reorganization energy of the order of 0.8–1 eV, which appears to be a reasonable estimate in consideration of refs 27 and 28 and our electrolyte conditions. To check whether thermodynamic, besides electronic, limitations to the charge injection kinetics are present, we explored the TA of the dyes loaded on SnO₂/TiO₂ electrodes where we hoped that the thin TiO₂ layer, created on top of SnO₂ upon TiCl₄ hydrolysis, was not constituting a significant barrier to electron transfer.

On SnO₂/TiO₂ (Figure 5C), the absorption intensity of the excited state residue associated with the T1 state is decreased compared to the 710 nm feature, ($\Delta A_{710} / \Delta A_{500} = 2.3$ on TiO₂; $\Delta A_{710} / \Delta A_{500} = 2.8$ on SnO₂/TiO₂) indicating, on SnO₂/TiO₂, a higher yield of charge injection, consistent with the larger driving force offered by the lower flat band potential of SnO₂ (ca. 0.2 V vs SCE) compared to TiO₂. Again, the same trend is observed for ZnTPPF₂₀-COOH and ZnTPPF₁₉-click-COOH (Figure S36). Finally, we can observe that, once generated, the charge separated state (CS) is long lived with either TiO₂ or

SnO₂/TiO₂, and its recovery is far from being complete on a time scale of 50 μ s, leaving in a principle sufficient time for intercepting redox reactions of a potential interest in the field of energy storage. In the following discussion, the indications extracted by TAS are corroborated by photoelectrochemical measurements in the presence of hole scavengers.

Photoelectrochemical Properties in the Presence of Hole Scavengers. Photocurrents registered with the porphyrin-sensitized TiO₂ photoanodes under AM 1.5 G light (0.1 W/cm²) in the presence of 0.1 M HBr are reported in Figure S37. The photocurrent onset is observed between –0.1 and –0.2 V versus SCE and rises by moving to positive potentials, as expected from an n-type/electrolyte junction. The limiting value is reached in all cases at about 0.2 V versus SCE, but the photocurrent is generally very modest. TiO₂/ZnTPPF₂₀-CN represents the best photoanode, yielding up to 40 μ A/cm² net photocurrent at 0.2 V versus SCE, while TiO₂/ZnTPPF₂₀-COOH and TiO₂/ZnTPPF₁₉-click-COOH gave plateau values of 30 and 10 μ A/cm², respectively. Despite the modest conversion, the photoaction spectra, regardless of the substrate on which they were recorded (Figure S42 and Figure 7), are sensibly consistent with the related absorption spectra of the thin films, confirming in all cases the involvement of the excited state of the porphyrin in the sensitization process. The use of SnO₂ films to oxidatively quench the excited state of dyes, which are not capable of efficient injection into TiO₂, has been reported by Bergeron et al.,³⁰ and, similarly to indium tin oxide (ITO),³¹ has been later implemented in DSPECs by other authors, often in combination with ALD-deposited overlayers with the task of prolonging the lifetime of the charge separated state at the semiconductor/electrolyte interface.^{32,33}

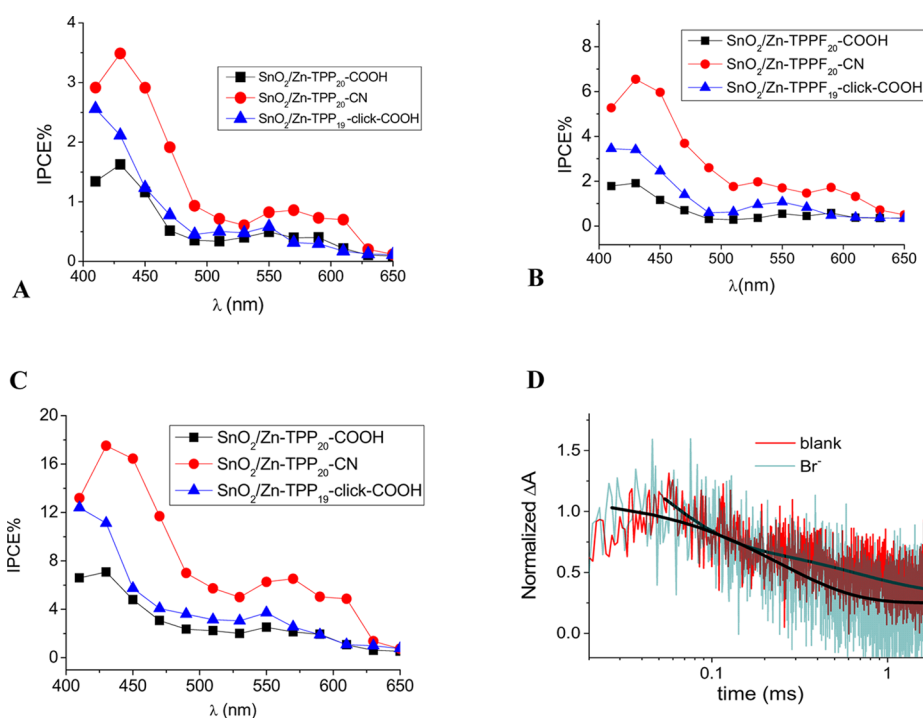


Figure 7. Photoaction spectra taken on SnO₂/TiO₂-sensitized substrate at 0.7 V: SnO₂/ZnTPPF₂₀-COOH, SnO₂/ZnTPPF₂₀-CN, SnO₂/ZnTPPF₁₉-click-COOH in: (A) HBr 0.1 M, (B) HBr 0.1 M and NaBr 0.3 M, (C) 0.1 M ascorbic acid, and (D) 700 nm recovery of ZnTPPF₂₀-CN⁺ loaded on SnO₂/TiO₂ in 0.1 M HClO₄ (blank) and 0.3 M NaBr, 0.1 M HBr biased at 0.7 V vs Pt. Oscilloscope input impedance is 10 kΩ.

J/E characteristics recorded with 0.1 M HBr with SnO₂/TiO₂-sensitized photoanodes undergo a 5- to 10-fold increase in photocurrent, compared to TiO₂, consistent with an improved charge injection by the excited state of the Zn^{II} porphyrins and retarded recombination owing to surface state passivation by TiO₂. The J/E curves evidence a positive shift of the photoanodic threshold, in agreement with the expected flat band of SnO₂, about 0.2 V versus SCE. Photocurrent plateau values in 0.1 M HBr are generally found at about 0.35 V versus SCE and vary in the order of ZnTPPF₂₀-CN (≈ 0.35 mA/cm²) > ZnTPPF₁₉-click-COOH (≈ 0.2 mA/cm²) > ZnTPPF₂₀-COOH (≈ 0.15 mA/cm²) (Figure S38). By contrast, the undyed electrode produces a marginal photocurrent (<5 μA/cm²), while, in the dark, the electrochemical oxidation of Br⁻ occurs at about 0.8 V versus SCE, probably through pinholes in the film, leaving exposed FTO sites. Nevertheless, the anodic current, out to 1 V versus SCE, is very small, about 2.5 μA/cm² (Figure S40). This means that at least 0.6 eV can be stored in the sensitized single junction, consistent with the expected difference between the quasi Fermi levels of the photoanode, apparently pinned on the SnO₂/TiO₂ surface states and the Fermi level of the electrolyte. Better passivation of the interface and quantitative dye regeneration by the electrolyte are expected to further improve cell energetics.

An optimized performance was found employing a mixture of 0.3 M NaBr and 0.1 M HBr (Figure 6) where ZnTPPF₂₀-CN generated a steady state limiting value of 0.4 mA/cm², with transients reaching 0.5 mA/cm², showing a good match with the shape of the current potential characteristics. Reproducibility in photoanode performance under [Br⁻] = 0.4 M was good, as shown by statistical error bars in a value of about 10% with respect to the average photocurrent plateau value (Figure 6D). Further attempts by increasing the [Br⁻] up to 0.5 M and above were unfortunately unsuccessful, as the unstable operation of the

cell was observed, associated with spectral changes the Q band structure, which suggested porphyrin demetallation under such circumstances. Otherwise, in 0.4 M Br⁻, the dye stability was satisfactory and no decrease in the dye absorption nor modification of the spectral features of ZnTPPF₂₀-CN was observed, with Soret and Q bands maintaining their shape and relative intensity. Only a blue shift of a few nanometers was observed and tentatively ascribed to Stark perturbation upon surface adsorption of protons, following immersion and potentiodynamic cycling in the acidic electrolyte medium (Figure S39).

Even in our optimized electrolyte conditions, the photoaction spectra, whose conversion efficiencies agree with the trend outlined by the J/E curves, show modest charge separation efficiencies. Maximum conversions of the order of about 7 and 2% are observed with 0.4 M Br⁻ in correspondence of the respective B and Q manifolds of the best dye ZnTPPF₂₀-CN, which, given the homogeneous ground and excited state properties found within the series under investigation, probably benefits most of the better electronic coupling offered by the cyanoacrylic group. The corresponding APCE spectra (Figure S43) are quite constant throughout the visible range, indicating that the quantum yield of charge injection is substantially independent from the state which is initially populated by light absorption, a statement not necessarily true when ultrafast charge injection is in kinetic competition with thermalization of the electronic excited states higher than S1. While injection can still be less than optimal with SnO₂/TiO₂ substrates, these low conversion values could also be indicative of kinetic competition between dye regeneration by Br⁻ and recombination, as already suggested by the strong impact of electrolyte composition on photoanode performance. Recombination kinetics involving SnO₂/TiO₂/ZnTPPF₂₀-CN fully develops in the millisecond time domain and was monitored at 700 nm in the presence of

Br^- 0.4 M (pH 1) at 0.7 V versus Pt, a voltage falling well within the limiting photocurrent of the photoanode, corresponding thus to the maximum bias-assisted charge separation rate (Figure S44 and Table S3). In the presence of HBr, a substantial shortening of the oxidized dye decay is observed (Figure 7D) due to electron donation by Br^- , affording a regeneration efficiency $\eta_{\text{reg}} = 49\%$ (Table S4). Let us set aside electronic effects, such value could not come as a surprise in consideration of the ground-state oxidation potential (ca. 1.2 V vs SCE) of the porphyrin, less positive of about 0.4 V compared to those of other dyes (ca. 1.6 V vs SCE), which exhibited nearly unitary η_{reg}^4 . From $\text{APCE} = \Phi_{\text{inj}}\eta_{\text{reg}}$ assuming negligible losses due to electron recapture by Br_3^- , we obtain a charge injection yield of the order of 14%. Such a value is in good agreement with APCE spectra obtained in the presence of ascorbic acid (AA), a better hole scavenger than Br^- , generating, in the best case represented again by $\text{ZnTPPF}_{20}\text{-CN}$, photocurrents of 1.5 mA/cm^2 at 0.7 V versus SCE (Figure S41) and APCE of the order of 16–18% (Figure S43C). Actually, in the presence of ascorbic acid, TA spectra revealed the formation of the radical anion of the porphyrin (Figure S34), living hundreds of microseconds in deaerated DMSO, indicating that injection might also occur from the long lived reduced state of the porphyrin, as a result of the triplet reductive quenching by ascorbic acid. Injection from the reduced state was observed previously in the case of other poorly reducing Ru^{II} sensitizers.³⁴ This would also explain the slightly higher injection yield calculated with AA with respect to the approximate estimate obtained at the same pH in the presence of Br^- .

Coupling to Water Splitting Redox Catalyst. The proof of hole transfer from the porphyrin dyes immobilized on the $\text{TiO}_2/\text{SnO}_2$ photoanodes to a water oxidation catalyst, capable to oxidize water to dioxygen under acidic conditions, was searched by coadsorbing a binuclear iridium catalyst acting as the water oxidation catalyst whose properties were previously reported on modified ITO.³⁵

The successful adsorption of the binuclear Ir complex (Figure 8, IrWOC) on the $\text{SnO}_2/\text{TiO}_2$ $\text{ZnTPPF}_{20}\text{-CN}$ photoanode,

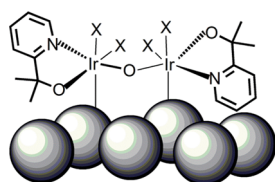


Figure 8. Schematic structure of the Binuclear Iridium(IV) (IrWOC) complex obtained following oxidation of the Ir^{III} monomer with NaIO_4 . The complex is shown to interact with a mesoporous metal oxide. Recent findings suggest a single μ -oxo bridge between the two iridium atoms of the dimeric Ir-WOC.^{36–38}

after 2 h soaking, was testified by the appearance of a catalytic wave having onset at about 1.1 V versus SCE (Figure S45). Soaking of the dyed thin films in the catalyst solution was optimized by considering the long term response of the photoanode under constant potential chronoamperometry (Figure S46). The best initial performances were achieved after soaking for 1 h, but the long term response was slightly better with the electrode subjected to 2 h immersion in the catalyst solution, which was then adopted for all the subsequent experiments. Under these last conditions, the ICP showed that the loading of $\text{ZnTPPF}_{20}\text{-CN}$ was $1.7 \pm 0.4 \times 10^{-8} \text{ mol/cm}^2$,

while Ir was $2.5 \pm 1.2 \times 10^{-9} \text{ mol/cm}^2$. Leaching of about 30% of the initial Ir concentration however usually occurred during 1 h photoelectrolysis under conventional open configuration cell (i.e., no thin layer cell).

Consistent with electron transfer from the co-adsorbed catalyst to $\text{ZnTPPF}_{20}\text{-CN}^+$, the 700 nm absorption of the latter undergoes a shortening, particularly evident from Figure 8 between 1 and 4 ms, resulting in a decreased τ_{av} , from 3.26 to 2.15 ms (cyan line) when the catalyst is present. Irrespective of the presence of the water oxidation catalyst, the recovery of $\text{ZnTPPF}_{20}\text{-CN}^+$ is incomplete on a time scale of 5 ms, and after 4 ms, both the green and blue traces seem to evolve with a similar kinetics, probably indicating that only a fraction of $\text{ZnTPPF}_{20}\text{-CN}^+$ has a sufficient coupling with the redox catalyst on the surface to give rise to electron transfer. Nevertheless, chronoamperometry of the $\text{SnO}_2/\text{TiO}_2/\text{ZnTPPF}_{20}\text{-CN}/\text{IrWOC}$ in a thin layer cell under visible illumination ($\lambda > 450 \text{ nm}$) demonstrates that the $\text{SnO}_2/\text{TiO}_2/\text{ZnTPPF}_{20}\text{-CN}/\text{IrWOC}$ is able to split water with a high faradaic yield.

The photoanodic current generated by $\text{SnO}_2/\text{ZnTPPF}_{20}\text{-CN}/\text{IrWOC}$, where a bare FTO electrode biased at -0.6 V versus SCE under bipotentiostatic control serves as the oxygen collector (Scheme S1), was found to increase during the first 600 s, after which a constant value of about 0.1 mA/cm^2 was maintained (Figure 9B). The trend followed by the photoanodic current was mirrored by the cathodic current associated with oxygen reduction occurring at the counter electrode. At present, we do not have a fully satisfying explanation to the observed evidence. Possibly, during the first minutes of operation, the Ir complex is converted to an IrO_x species, more active in oxygen evolution. Previous studies however remarked an excellent stability of IrWOC with respect to oxidative degradation.³⁵ A better explanation could be the achievement of a steady state condition for the electrode under polarization and under illumination, related to desorption of – part of the weakest adsorbed catalyst, which may both compete in light absorption with the porphyrin and cause excessive recombination.

Nonetheless, after attaining the steady state, the photocurrent was stable for thousand seconds even at a lower bias (0.3 V vs SCE, Figure 9D), and it was unambiguously associated with oxygen evolution, ceasing quickly in the absence of illumination. The calculated faradaic yield, obtained from the integrated chronoamperograms according to the Faraday law, is independent from the applied bias and turns out to be larger than 95% in the presence of Ir-WOC compared to less than 10% when the catalyst is absent (Figure 9C and Figure S47).

It can also be observed that the performances during generation/collection experiments in a thin layer cell are higher by at least about 30% and also more stable with respect to those found with the photoanode under open configuration (i.e., in a regular three electrodes cell, Figure S46), and that was attributed to the continuous removal of photogenerated oxygen by the collector electrode, oxygen that can otherwise locally accumulate at the surface of the photoanode whereupon is generated and act as an electron scavenger, reducing the photoanodic output of the cell.

CONCLUSIONS

A series of perfluorinated Zn^{II} porphyrins with different acceptor/linker groups were evaluated as n-type dyes for photoelectrosynthetic cells. The perfluorinated design was successful in creating an electron-poor porphyrin core, allowing to obtain a sufficiently positive ground-state oxidation potential

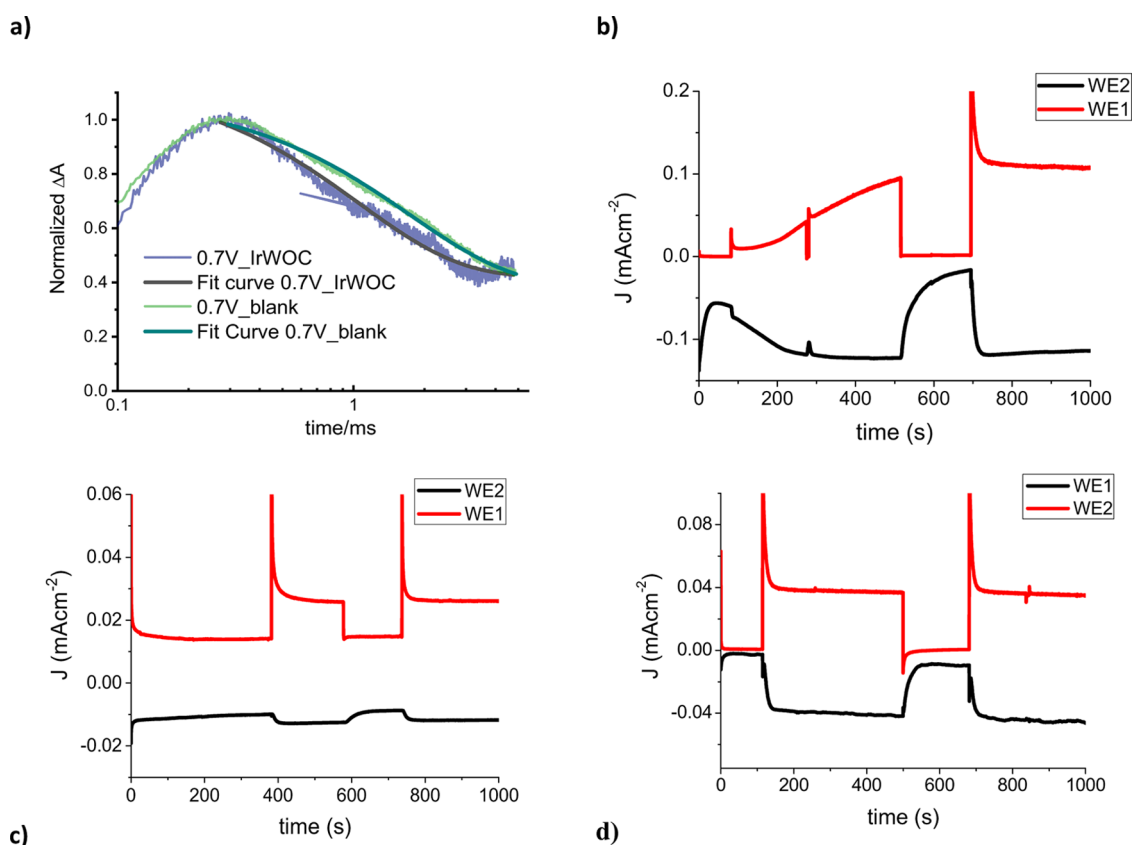


Figure 9. (a) Recovery of ZnTPPF₂₀-CN⁺ in the absence (blank, green line) and in the presence of IrWOC (blue line) monitored at 700 nm. Oscilloscope impedance is 1 M Ω ; (b)–(d) Photocurrent delivered by the photoanode (WE1) (red) associated with oxygen reduction (black) at the collector electrode (WE2) held at constant -0.6 V vs SCE. (b) SnO₂/TiO₂/ZnTPPF₂₀-CN/IrWOC at 0.7 V vs SCE; (c) SnO₂/TiO₂/ZnTPPF₂₀-CN at 0.7 V vs SCE; and (d) SnO₂/TiO₂/ZnTPPF₂₀-CN/IrWOC at 0.3 V vs SCE; 0.1 M HClO₄, AM 1.5 G, with 450 nm cut off filter.

to trigger energetically demanding redox reactions for solar energy conversion and storage. The dye series was used to sensitize TiO₂ and SnO₂ substrates, which displayed satisfactory adsorption stability in acidic water, thanks to the hydrophobic properties of these dyes. Nevertheless, the perfluorinated design increased the reorganization energy and decreased the coupling of the excited state with the semiconductor, resulting in relatively low injection yields, which were found, in the best case, of the order of 12% with SnO₂-based electrodes. Better results, with yields of the order of 15–18% were found in the presence of AA, thanks to the reductive quenching of the triplet excited state and the injection from the reduced state of the dye. Consistent with the calculations, the best results were found for ZnTPPF₂₀-CN bearing the cyanoacrylic group as the strongest electron-withdrawing group, leading to the best coupling for injection. ZnTPPF₂₀-CN was thus the best performer in the splitting of HBr (APCE % = 6/7%) and, when coupled to a suitable catalyst, of water, where a stable photoanode operation in acidic conditions was observed, exploiting visible radiation up to 650 nm with nearly quantitative faradaic yield. Thus, the perfluorinated porphyrins equipped with cyanoacrylic terminal group at the β -position should be considered for further development intended to improve the charge-transfer character. For example, the insertion of strong electron acceptors in the linker arm might increase the electronic coupling for charge injection, while the use of CF₃-substituted phenyl groups might further enhance dye stability. At the same time, by exploiting the information gained by this study, we are now trying to fabricate molecular dyads integrating both porphyrin dyes and catalytic

complexes, where reductive quenching of the porphyrin-excited state will simultaneously increase both the injection quantum yield and activate the catalyst for oxygen evolution.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acsami.9b08042.

Syntheses and characterization of the dyes; preparation of the photonades; computational results; spectroscopic and electrochemical characterization of the sensitized photoanodes; transient absorption spectra; current–voltage curves and photoaction spectra in the presence of hole scavengers; cyclic voltammetry and chronoamperometry curves after coupling to water splitting redox catalyst (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

*E-mail: francesca.tessore@unimi.it (F.T.).

*E-mail: Elisabetta.Benazzi@newcastle.ac.uk (E.B.).

ORCID

Alessio Orbelli Biroli: 0000-0002-5463-1444

Francesca Tessore: 0000-0002-6691-0256

Gabriele Di Carlo: 0000-0002-8782-7945

Serena Berardi: 0000-0002-0275-6501

Mirco Natali: 0000-0002-6638-978X

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

A.O.B., F.T., G.D.C., and M.P. gratefully acknowledge Regione Lombardia and Fondazione Cariplo for financial support and for the use of instrumentation purchased through the SmartMatLab Centre project (Fondazione Cariplo grant 2013-1766) and Riccardo Moneta for the help with the syntheses. G.D.C. greatly thanks the University of Milano (Piano Sostegno alla Ricerca 2018 LINEA 2 Azione A – Giovani Ricercatori) for financial support. A.S. thanks the Department of Chemical Sciences at the University of Padova for funding (Project PHOETRY, P-DiSC #10BIRD2018-UNIPD). UniFe acknowledges POR-FESR HP-Solar for funding.

REFERENCES

- (1) Faunce, T.; Styring, S.; Wasielewski, M. R.; Brudvig, G. W.; Rutherford, A. W.; Messinger, J.; Lee, A. F.; Hill, C. L.; deGroot, H.; Fontecave, M.; Macfarlane, D. R.; Hankamer, B.; Nocera, D. G.; Tiede, D. M.; Dau, H.; Hillier, W.; Wang, L.; Amal, R. Artificial Photosynthesis as a Frontier Technology for Energy Sustainability. *Energy Environ. Sci.* **2013**, *6*, 1074–1076.
- (2) Brennaman, M. K.; Dillon, R. J.; Alibabaei, L.; Gish, M. K.; Dares, C. J.; Ashford, D. L.; House, R. L.; Meyer, G. J.; Papanikolas, J. M.; Meyer, T. J. Finding the Way to Solar Fuels with Dye-Sensitized Photoelectrosynthesis Cells. *J. Am. Chem. Soc.* **2016**, *138*, 13085–13102.
- (3) Mei, B.; Mul, G.; Seger, B. Beyond Water Splitting: Efficiencies of Photo-Electrochemical Devices Producing Hydrogen and Valuable Oxidation Products. *Adv. Sustainable Syst.* **2017**, *1*, 1600035.
- (4) Brady, M. D.; Troian-gautier, L.; Sampaio, R. N.; Motley, T. C.; Meyer, G. J. Optimization of Photocatalyst Excited- and Ground-State Reduction Potentials for Dye-Sensitized HBr Splitting. *ACS Appl. Mater. Interfaces* **2018**, *10*, 31312–31323.
- (5) Brady, M. D.; Sampaio, R. N.; Wang, D.; Meyer, T. J.; Meyer, G. J. Dye-Sensitized Hydrobromic Acid Splitting for Hydrogen Solar Fuel Production. *J. Am. Chem. Soc.* **2017**, *139*, 15612–15615.
- (6) Mussini, P. R.; Orbelli Biroli, A.; Tessore, F.; Pizzotti, M.; Biaggi, C.; Di Carlo, G.; Lobello, M. G.; De Angelis, F. Modulating the Electronic Properties of Asymmetric Push-Pull and Symmetric Zn(II)-Diarylporphyrinates with Para Substituted Phenylethynyl Moieties in 5,15 Meso Positions: A Combined Electrochemical and Spectroscopic Investigation. *Electrochim. Acta* **2012**, *85*, 509–523.
- (7) Yella, A.; Lee, H.-W.; Tsao, H. N.; Yi, C.; Chandiran, A. K.; Nazeeruddin, K.; Diau, E. W.-G.; Yeh, C.-Y.; Zakeeruddin, S. M.; Grätzel, M. Porphyrin-Sensitized Solar Cells with Cobalt(II/III)-Based Redox Electrolyte Exceed 12 Percent Efficiency. *Science* **2011**, *334*, 629–634.
- (8) Wang, Y.; Chen, B.; Wu, W.; Li, X.; Zhu, W.; Tian, H.; Xie, Y. Efficient Solar Cells Sensitized by Porphyrins with an Extended Conjugation Framework and a Carbazole Donor : From Molecular Design to Cosensitization. *Angew. Chem., Int. Ed.* **2014**, *53*, 10779–10783.
- (9) Xie, Y.; Tang, Y.; Wu, W.; Wang, Y.; Liu, J.; Li, X.; Tian, H.; Zhu, W. H. Porphyrin Cosensitization for a Photovoltaic Efficiency of 11.5%: A Record for Non-Ruthenium Solar Cells Based on Iodine Electrolyte. *J. Am. Chem. Soc.* **2015**, *137*, 14055–14058.
- (10) Moore, G. F.; Blakemore, J. D.; Milot, R. L.; Hull, J. F.; Song, H.-E.; Cai, L.; Schmittenmaer, C. A.; Crabtree, R. H.; Brudvig, G. W. A Visible Light Water-Splitting Cell with a Photoanode Formed by Codeposition of a High-Potential Porphyrin and an Iridium Water-Oxidation Catalyst. *Energy Environ. Sci.* **2011**, *4*, 2389–2392.
- (11) Materna, K. L.; Jiang, J.; Regan, K. P.; Schmittenmaer, C. A.; Crabtree, R. H.; Brudvig, G. W. Optimization of Photoanodes for Photocatalytic Water Oxidation by Combining a Heterogenized Iridium Water-Oxidation Catalyst with a High-Potential Porphyrin Photosensitizer. *ChemSusChem* **2017**, *10*, 4526–4534.
- (12) Nayak, A.; Knauf, R. R.; Hanson, K.; Alibabaei, L.; Concepcion, J. J.; Ashford, D. L.; Dempsey, J. L.; Meyer, T. J. Synthesis and Photophysical Characterization of Porphyrin and Porphyrin-Ru(II) polypyridyl Chromophore-Catalyst Assemblies on Mesoporous Metal Oxides. *Chem. Sci.* **2014**, *5*, 3115–3119.
- (13) Milot, R. L.; Schmittenmaer, C. A. Electron Injection Dynamics in High-Potential Porphyrin Photoanodes. *Acc. Chem. Res.* **2015**, *48*, 1423–1431.
- (14) Lim, G. N.; Hedström, S.; Jung, K. A.; Smith, P. A. D.; Batista, V. S.; D'Souza, F.; Van Der Est, A.; Poddutoori, P. K. Interfacial Electron Transfer Followed by Photooxidation in N,N-Bis(p-anisole)-aminopyridine–Aluminum(III) Porphyrin-Titanium(IV) Oxide Self-Assembled Photoanodes. *J. Phys. Chem. C* **2017**, *121*, 14484–14497.
- (15) Lee, S. H.; Regan, K. P.; Hedström, S.; Matula, A. J.; Chaudhuri, S.; Crabtree, R. H.; Batista, V. S.; Schmittenmaer, C. A.; Brudvig, G. W. Linker Length-Dependent Electron-Injection Dynamics of Trimesitylporphyrins on SnO₂ Films. *J. Phys. Chem. C* **2017**, *121*, 22690–22699.
- (16) Lindsey, J. S.; Schreiman, I. C.; Hsu, H. C.; Kearney, P. C.; Marguerettaz, A. M. Rothmund and Adler-Longo Reactions revisited: Synthesis of Tetraphenylporphyrins under Equilibrium Conditions. *J. Org. Chem.* **1987**, *52*, 827–836.
- (17) Di Carlo, G.; Orbelli Biroli, A.; Pizzotti, M.; Tessore, F.; Trifiletti, V.; Ruffo, R.; Abbotto, A.; Amat, A.; De Angelis, F.; Mussini, P. R. Tetraaryl Zn^{II} Porphyrinates Substituted at β -Pyrrolic Positions as Sensitizers in Dye-Sensitized Solar Cells: A Comparison with Meso-Disubstituted Push-Pull ZnII Porphyrinates. *Chem. – Eur. J.* **2013**, *19*, 10723–10740.
- (18) Golf, H. R. A.; Reissig, H. U.; Wiehe, A. Regioselective Nucleophilic Aromatic Substitution Reaction of meso-Pentafluorophenyl-Substituted Porphyrinoids with Alcohols. *Eur. J. Org. Chem.* **2015**, *2015*, 1548–1568.
- (19) Kolb, H. C.; Finn, M. G.; Sharpless, K. B. Click Chemistry: Diverse Chemical Function from a Few Good Reactions. *Angew. Chem., Int. Ed.* **2001**, *40*, 2004–2021.
- (20) Colombo, A.; Di Carlo, G.; Dragonetti, C.; Magni, M.; Orbelli Biroli, A.; Pizzotti, M.; Roberto, D.; Tessore, F.; Benazzi, E.; Bignozzi, C. A.; Casarin, L.; Caramori, S. Coupling of Zinc Porphyrin Dyes and Copper Electrolytes: A Springboard for Novel Sustainable Dye-Sensitized Solar Cells. *Inorg. Chem.* **2017**, *56*, 14189–14197.
- (21) Gritzner, G.; Kůta, J. Recommendations on Reporting Electrode Potentials in Nonaqueous Solvents: IUPC Commission on Electrochemistry. *Electrochim. Acta* **1984**, *29*, 869–873.
- (22) Di Carlo, G.; Caramori, S.; Trifiletti, V.; Giannuzzi, R.; De Marco, L.; Pizzotti, M.; Biroli, A. O.; Tessore, F.; Argazzi, R.; Bignozzi, C. A. Influence of Porphyrinic Structure on Electron Transfer Processes at the Electrolyte/Dye/TiO₂ Interface in PSSCs: A Comparison between Meso Push–Pull and β -Pyrrolic Architectures. *ACS Appl. Mater. Interfaces* **2014**, *6*, 15841–15852.
- (23) Kim, D.; Holten, D.; Gouterman, M. Evidence From Picosecond Transient Absorption and Kinetic Studies of Charge-Transfer States in Copper(II) Porphyrins. *J. Am. Chem. Soc.* **1984**, *106*, 2793–2798.
- (24) Young, K. J.; Martini, L. A.; Milot, R. L.; Snoeberger, R. C., III; Batista, V. S.; Schmittenmaer, C. A.; Crabtree, R. H.; Brudvig, G. W. Light-Driven Water Oxidation for Solar Fuels. *Coord. Chem. Rev.* **2012**, *256*, 2503–2520.
- (25) Di Carlo, G.; Caramori, S.; Casarin, L.; Biroli, A. O.; Tessore, F.; Argazzi, R.; Oriana, A.; Cerullo, G.; Bignozzi, C. A.; Pizzotti, M. Charge Transfer Dynamics in β - and Meso-Substituted Dithienylethylene Porphyrins. *J. Phys. Chem. C* **2017**, *121*, 18385–18400.
- (26) Enright, B.; Redmond, G.; Fitzmaurice, D. Spectroscopic Determination of Flatband Potentials for Polycrystalline TiO₂ Electrodes in Mixed Solvent Systems. *J. Phys. Chem.* **1994**, *98*, 6195–6200.
- (27) Wilkinson, G.; Gillard, R. D.; McCleverty, J. A. *Comprehensive Coordination Chemistry : The Synthesis, Reactions, Properties & Applications of Coordination Compounds*; Pergamon Press: 1987.

(28) Wasielewski, M. R.; Niemczyk, M. P.; Svec, W. A.; Pewitt, E. B. Dependence of Rate Constants for Photoinduced Charge Separation and Dark Charge Recombination on the Free Energy of Reaction in Restricted-Distance Porphyrin-Quinone Molecules. *J. Am. Chem. Soc.* **1985**, *107*, 1080–1082.

(29) Sun, H.; Smirnov, V. V.; DiMagno, S. G. Slow Electron Transfer Rates for Fluorinated Cobalt Porphyrins: Electronic and Conformational Factors Modulating Metalloporphyrin ET. *Inorg. Chem.* **2003**, *42*, 6032–6040.

(30) Bergeron, B. V.; Marton, A.; Oskam, G.; Meyer, G. J. Dye-Sensitized SnO₂ Electrodes with Iodide and Pseudohalide Redox Mediators. *J. Phys. Chem. B* **2005**, *109*, 937–943.

(31) Alibabaei, L.; Brennaman, M. K.; Norris, M. R.; Kalanyan, B.; Song, W.; Losego, M. D.; Concepcion, J. J.; Binstead, R. A.; Parsons, G. N.; Meyer, T. J. Solar Water Splitting in a Molecular Photoelectrochemical Cell. *Proc. Natl. Acad. Sci. U. S. A.* **2013**, *110*, 20008–20013.

(32) Alibabaei, L.; Sherman, B. D.; Norris, M. R.; Brennaman, M. K.; Meyer, T. J. Visible Photoelectrochemical Water Splitting into H₂ and O₂ in a Dye-Sensitized Photoelectrosynthesis Cell. *Proc. Natl. Acad. Sci. U. S. A.* **2015**, *112*, 5899–5902.

(33) Sheridan, M. V.; Wang, Y.; Wang, D.; Troian-Gautier, L.; Dares, C. J.; Sherman, B. D.; Meyer, T. J. Light-Driven Water Splitting Mediated by Photogenerated Bromine. *Angew. Chem., Int. Ed.* **2018**, *57*, 3449–3453.

(34) Ronconi, F.; Santoni, M. P.; Nastasi, F.; Bruno, G.; Argazzi, R.; Berardi, S.; Caramori, S.; Bignozzi, C. A.; Campagna, S. Charge Injection into Nanostructured TiO₂ Electrodes from the Photo-generated Reduced Form of a New Ru(II) Polypyridine Compound: The “Anti-Biomimetic” Mechanism at Work. *Dalton Trans.* **2016**, *45*, 14109–14123.

(35) Graeupner, J.; Hintermair, U.; Huang, D. L.; Thomsen, J. M.; Takase, M.; Campos, J.; Hashmi, S. M.; Elimelech, M.; Brudvig, G. W.; Crabtree, R. H. Probing the Viability of Oxo-Coupling Pathways in Iridium-Catalyzed Oxygen Evolution. *Organometallics* **2013**, *32*, 5384–5390.

(36) Sharninghausen, L. S.; Sinha, S. B.; Shopov, D. Y.; Choi, B.; Mercado, B. Q.; Roy, X.; Balcells, D.; Brudvig, G. W.; Crabtree, R. H. High Oxidation State Iridium Mono- μ -Oxo Dimers Related to Water Oxidation Catalysis. *J. Am. Chem. Soc.* **2016**, *138*, 15917–15926.

(37) Sinha, S. B.; Shopov, D. Y.; Sharninghausen, L. S.; Stein, C. J.; Mercado, B. Q.; Balcells, D.; Pedersen, T. B.; Reiher, M.; Brudvig, G. W.; Crabtree, R. H. Redox Activity of Oxo-Bridged Iridium Dimers in an N,O-Donor Environment: Characterization of Remarkably Stable Ir(IV,V) Complexes. *J. Am. Chem. Soc.* **2017**, *139*, 9672–9683.

(38) Michaelos, T. K.; Shopov, D. Y.; Sinha, S. B.; Sharninghausen, L. S.; Fisher, K. J.; Lant, H. M. C.; Crabtree, R. H.; Brudvig, G. W. A Pyridine Alkoxide Chelate Ligand That Promotes Both Unusually High Oxidation States and Water-Oxidation Catalysis. *Acc. Chem. Res.* **2017**, *50*, 952–959.