

Tetracyanoethylene-based organic magnets

Joel S. Miller^{a†} and Arthur J. Epstein^{b‡}^a Department of Chemistry, University of Utah, Salt Lake City, Utah 84112-0850, USA^b Department of Physics and Department of Chemistry, The Ohio State University, Columbus, Ohio 43210-1106, USA


Several classes of organic magnets based upon the tetracyanoethylene radical anion, [TCNE]^{•−}, either unbound, μ , and μ_4 bonded to zero, two and four metal sites have been reported. The putative μ_4 bonded V(TCNE)_x room temperature magnet has been extended to include M(TCNE)_x (M = Mn, Fe, Co, Ni) magnets. M for this class of magnets is assigned to be in the divalent oxidation state. A σ -[TCNE]₂^{2−} dimer intermediate has been isolated. The intrachain magnetic coupling for the 1-D coordination polymers having [TCNE]^{•−} μ -bridge bonded to [Mn^{III}porphyrins]⁺ is discussed in the context of a structure–function correlation arising from the dihedral angle between the [Mn^{III}TTPP]⁺'s MnN₄ and [TCNE]^{•−} mean planes and the magnitude of magnetic coupling. This correlation is ascribed to the increasing importance of the σ -Mn^{III} d_{z²}/[TCNE]^{•−} p_z overlap with decreasing dihedral angle.}

From time immemorial magnets comprised a few metals or their oxides with the key component of all magnets, the unpaired electron spins, solely residing in d- or f-orbitals. Extension to organic radicals was first discussed in 1963 from a conceptual point of view,¹ but their experimental realization was not achieved until 1985. At that time [Fe(C₅Me₅)₂]⁺[TCNE]^{•−} (TCNE = tetracyanoethylene) with a magnetic ordering temperature, T_c, of 4.8 K was reported to be the first magnet with spin residing in a p-orbital² that (i) required spins in p-orbitals, (ii) exhibited magnetic hysteresis, (iii) did not have extended network bonding in 1, 2 or 3 dimensions, (iv) was soluble in conventional organic solvents, and (v) did not require metallurgical preparative methods. Today, molecule-based magnets include many diverse examples of materials exhibiting magnetic ordering including ferromagnets, ferrimagnets, canted/weak ferromagnets, metamagnets and spin glasses. Materials range from p-orbital-based organic nitroxides,^{3,4} p/d-orbital-based mixed organic radicals/organometallic or inorganic coordination systems,^{4–6} to the more classical d-orbital-based inorganic coordination compounds (*e.g.* mixed metal oxalates and cyanides),^{4,5} with several classes of the organic/metal-ion-containing-ones possessing TCNE studied in our laboratory. As is the intent of feature articles in this journal, we provide a personal account of the results on two classes of TCNE-based magnets, namely, M[TCNE]_x and [Mn(porphyrin)][TCNE] magnets. Broad reviews on molecule-based magnets, however, are available.^{3–6}

M(TCNE)_x Magnets

In 1991 V(TCNE)_x·y(CH₂Cl₂) (x ~ 2; y ~ 1/2) **1a**, prepared from the room temperature reaction of V⁰(C₆H₆)₂ and TCNE, was reported to be a magnet below a critical temperature estimated to be ~400 K.^{4,7} Owing to the structural disorder, variable composition and extreme oxygen/water sensitivity the structure and oxidation state assignment of this valence-ambiguous material has yet to be elucidated. Although the structure is as yet unknown, based upon the magnetic, IR, and elemental analyses data, **1a** is formulated as V^{II}(TCNE)₂·

1/2(CH₂Cl₂) with S = 3/2 V^{II} and two S = 1/2 [TCNE]^{•−} systems. A 3-D network structure **2**, with each vanadium



surrounded by up to six ligands which are primarily nitrogens from different [TCNE]^{•−} species, and the [TCNE]^{•−} species binding up to four different vanadiums *via* σ -N bonds, is proposed.

Compound **1a** exhibits a field-dependent magnetization, M(H), between 1.4 and 350 K (Fig. 1), and saturates to *ca.* 6 ×

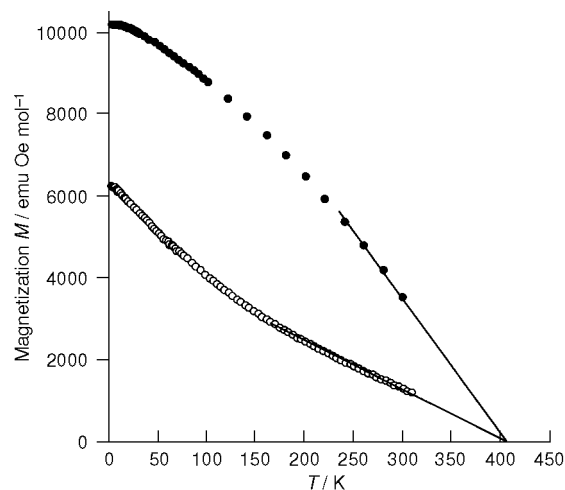


Fig. 1 Magnetization as a function of temperature [M(T)] at 1 kG for V(TCNE)_x·y(CH₂Cl₂) prepared from (○) V(C₆H₆)₂ **1a**⁷ and (●) V(CO)₆ **1b**⁸

10³ emu Oe mol^{−1} at 2 K and 19.5 kG. Assuming a Landé g value of 2, the expected maximum or saturation magnetization, M_s, for ferromagnetic coupling between S = 3/2 V^{II} and the two S = 1/2 [TCNE]^{•−} species (*ie.* S_{total} = 5/2) is 28 × 10³ emu Oe mol^{−1}. In contrast, antiferromagnetic coupling, leading to ferrimagnetic behavior as observed for magnetite (Fe₃O₄), leads to an S_{total} of 1/2 with M_s expected to be 5.6 × 10³ emu Oe mol^{−1}. The latter is in good agreement with the observed value. Hysteresis, characteristic of magnets' composition and shape, with a coercive field of 60 G is observed at room temperature (Fig. 2). The strong magnetic behavior is readily observed by its being attracted to a permanent magnet at room temperature (Fig. 3). Thus, **1a** is the first example of organic-based material with a critical temperature exceeding room temperature. The critical temperature exceeds 350 K, the thermal decomposition temperature of the sample, and a linear extrapolation to the

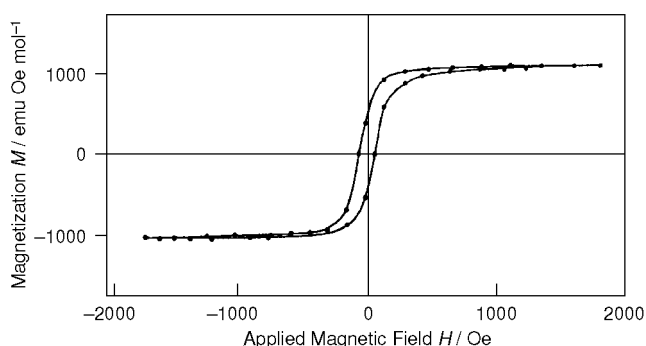


Fig. 2 Hysteresis $M(H)$, of $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$ **1a**, at room temperature



Fig. 3 Photograph of a powdered sample of **1a** being attracted to a Co_5Sm magnet at room temperature

temperature at which the magnetization should vanish leads to an estimate of $T_c \sim 400$ K (Fig. 1). Compound **1a** is also a semiconductor with a room temperature conductivity of $\sim 10^{-3}$ S cm^{-1} which decreases with decreasing temperature. At low temperatures the conductivity becomes frequency dependent, suggesting a hopping conduction mechanism.^{7d}

Thermal treatment of **1a** reduces the magnetization. At room temperature **1a** has a *ca.* 50 day half-life. Sealed samples heated for 10 h at 100°C are significantly less magnetic, while heating to 160°C for 48 h destroys magnetic ordering; however, the number of spins remains essentially unchanged. Concomitantly, the infrared spectra in the ν_{CN} region are altered slightly with the absorption at 2195 cm^{-1} moving to higher energy at 2206 cm^{-1} . Air exposure further alters the infrared spectra, with the major absorption in the $\nu_{\text{C=N}}$ region shifting to 2220 cm^{-1} . Likewise, **1a** rapidly decomposes in air and loses magnetic ordering. Infrared analysis of the decomposed product has much weaker absorptions at 2225 cm^{-1} which is in the region reported for TCNE^0 ⁹ as well as $\text{TCNE } \pi$ -bonds to metals atoms or ions.¹⁰

The reaction of $V(\text{C}_6\text{H}_6)_2$ and other strong acceptors such as TCNQ , perfluoro- TCNQ (TCNQF_4), $\text{C}_4(\text{CN})_6$, 2,3,5,6-tetrachlorobenzoquinone (chloranil), 2,3-dichloro-5,6-dicyanobenzoquinone (DDQ) and 2,3,5,6-tetracyanobenzoquinone (cyanil)¹¹ led to insoluble precipitates of unknown composition. These materials do not exhibit field-dependent magnetic susceptibilities and their high temperature susceptibilities can be fitted to the Curie–Weiss expression with $\theta < 0$ characteristic of antiferromagnetic, not ferromagnetic, behavior. Hence, magnets of nominal $V(\text{acceptor})_x \cdot y(\text{solvent})$ composition based on strong acceptors other than TCNE have yet to be prepared.

Compound **1a** is a structurally disordered material; hence, improved preparative routes leading to less disorder as well as avoiding the difficult-to-obtain $V(\text{C}_6\text{H}_6)_2$ were sought. Unlike

$V^0(\text{C}_6\text{H}_6)_2$, the reaction of isoelectronic $V^0(\text{C}_5\text{H}_5)(\text{C}_7\text{H}_7)$ with TCNE did not afford a room-temperature magnet.⁸ This is due to the greater oxidation potential of $V^0(\text{C}_5\text{H}_5)(\text{C}_7\text{H}_7)$ (0.34 V vs. SCE) with respect to $V^0(\text{C}_6\text{H}_6)_2$ (-0.28 V). Similarly, the reactions of $[\text{TCNE}]^-$ and $[\text{V}^1(\text{C}_6\text{H}_6)_2]^+$ or TCNE and $V^{\text{II}}(\text{C}_5\text{H}_5)_2$ did not afford a room-temperature magnet. Since the reaction of $V^0(\text{C}_6\text{H}_6)_2$ and TCNE leads to a strongly magnetic material, but the reaction of $[\text{V}^1(\text{C}_6\text{H}_6)_2]^+$ and $[\text{TCNE}]^-$ does not, the mechanism of the reaction is crucial in the formation of the room-temperature magnet and it is presently being investigated. In contrast, the room-temperature reactions of $V^0(\text{CO})_6$, $[\text{V}^1(\text{C}_6\text{H}_6)_2][\text{V}^{-1}(\text{CO})_6]$, $[\text{V}^{\text{II}}(\text{NCMe})_6][\text{V}^{-1}(\text{CO})_6]_2$, $[\text{V}^{\text{II}}(\text{NCMe})_6]^{2+}$ and $[\text{V}^{\text{II}}(\text{THF})_6][\text{V}^{-1}(\text{CO})_6]_2$ with TCNE led to room-temperature magnets; while the reactions of $[\text{Et}_4\text{N}][\text{V}^{-1}(\text{CO})_6]$ and $\text{Na}[\text{V}^{-1}(\text{CO})_6] \cdot 2\text{diglyme}$ did not.⁸ The reaction of $V^0(\text{CO})_6$ with TCNE was studied in detail.⁸

The elemental composition suggests that the magnets prepared from $V(\text{C}_6\text{H}_6)_2$ or $V(\text{CO})_6$ have similar compositions. The similarity of the IR spectra for the magnets prepared from $V(\text{C}_6\text{H}_6)_2$ (*i.e.* **1a**) and $V(\text{CO})_6$ (*i.e.* **1b**) and the absence of $\nu_{\text{C=O}}$ stretches in the 1800 to 2000 cm^{-1} region for the latter magnet strongly suggest that all the carbonyls are expelled from the vanadium coordination sphere upon the reaction of $V(\text{CO})_6$ with TCNE .⁸ This was confirmed from the quantification of CO -loss *via* Toepler pump measurements for [eqn. (1)],



with $x = 5.9 \pm 0.1$. Thus, all the six carbonyls are lost. Based on the lack of CO and the similarity between the IR spectra for the magnets prepared from $V(\text{CO})_6$ (**1b**) and $V(\text{C}_6\text{H}_6)_2$ (**1a**), both are assigned the same structural building block **2**. Nonetheless, differences between the ν_{CN} absorptions for **1a** and **1b** indicate that the two magnets are structurally inequivalent and different magnetic behavior is observed, although both have a T_c 400 K (Fig. 1).

The M for **1b** (Fig. 1), is $10\,300\text{ emu Oe mol}^{-1}$ at 4.2 K and $3600\text{ emu Oe mol}^{-1}$ at room temperature and an applied magnetic field of 1 kG ; an increase of 67 and 133% at these temperatures, respectively, as compared to **1a**. Whereas M decreases monotonically with increasing T for **1a**, this is less evident at low temperatures for **1b**. The unusual linear decrease of M with increasing T is consistent with extensive disorder in the sample, and suggests that the **1b** is less disordered. Hysteresis with a coercive field of 15 Oe is observed at room temperature and at 4.2 K for the **1b**. This is significantly lower than the 60 Oe value observed for **1a** (Fig. 2).⁷ The extrapolated T_c for **1b** is $\sim 400\text{ K}$, comparable to **1a** (Fig. 1).⁷ The results of the magnetic behavior for **1** give hope that more molecular/organic/polymeric magnets with higher T_c s will be available in the future. Already a room temperature Prussian blue-structured magnet, also based on vanadium, has been reported.¹²

In addition to forming **1** *via* the solution reaction of TCNE and $V(\text{C}_6\text{H}_6)_2$ or $V(\text{CO})_6$, these reactions were also carried out without solvent. No reaction occurred upon the reaction of TCNE and $V(\text{C}_6\text{H}_6)_2$, while an immediate blue precipitate occurred with TCNE and $V(\text{CO})_6$ at the surface of the TCNE crystals or on the walls of the reaction vessel if both TCNE to $V(\text{CO})_6$ were co-sublimed. For the latter product, the IR spectrum and magnetic properties were very similar to materials prepared from solution. However, this material has reduced oxygen sensitivity. This difference is attributed to its much lower surface area when compared to the fine ($\sim 100\text{ m}^2\text{ g}^{-1}$) powders that are formed from solution.¹³

Due to T_c exceeding room temperature, applications for this magnet can be envisioned.¹⁴ One application is for magnetic shielding, the attenuation of magnetic fields found in many electronic applications, *e.g.* high voltage lines. The feasibility of using **1** for this applications has been demonstrated (Fig. 4).¹⁵

Synthesis of the $V(\text{TCNE})_{x,y}(\text{solvent})$ magnet using solvents other than CH_2Cl_2 results in similar materials with varying

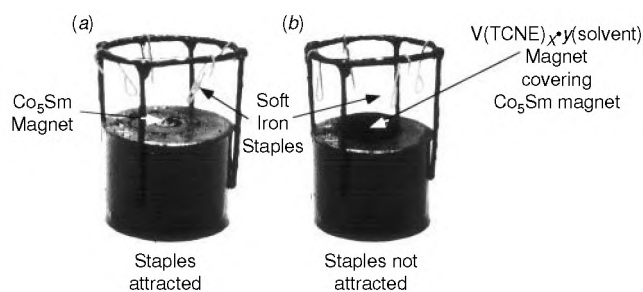


Fig. 4 Illustration of the $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$ magnet being an effective magnetic shield at room temperature; rods (paper clips) of soft-iron are attracted to a Co_5Sm permanent magnet (a); however, when a 1.7 mm pellet of $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$ is placed between the Co_5Sm magnet and the rods they hang freely (b) demonstrating magnetic shielding

degrees of structural order. For example, there is increasing disorder in the structure as the CH_2Cl_2 is replaced by THF^{7b} ($T_c \sim 210$ K) and MeCN^{7c} ($T_c \sim 100$ K). The exact magnetic ordering temperature varies with preparation conditions and resulting structural order. With increasing order these materials show features of correlated spin glass behavior. Additional examples of this class of magnets are needed to understand the chemistry and physics.^{7,8} To date the reaction of $V(\text{C}_6\text{H}_6)_2$ or $V(\text{CO})_6$ with other strong acceptors does not form magnetically ordered materials. Attempts to replace V with Cr, *i.e.* the reaction of TCNE with $\text{Cr}(\text{C}_6\text{H}_6)_2$ or $\text{Cr}(\text{CO})_6$, lead to nonmagnetically ordered, but ferromagnetically coupled, $[\text{Cr}(\text{C}_6\text{H}_6)_2][\text{TCNE}]^{16}$ and a substitution reaction with $\text{Cr}(\text{CO})_6$ forming $\text{Cr}(\text{CO})_5(\text{TCNE})^{17}$. However, magnets of $M(\text{TCNE})_{2,y}(\text{solvent})$ stoichiometry have recently been reported.

$M(\text{TCNE})_{2,y}(\text{CH}_2\text{Cl}_2)$ ($M = \text{Mn, Fe, Co, Ni}$) have been prepared *via* the reaction of $\text{MI}_2 \cdot x\text{MeCN}$ in CH_2Cl_2 .¹⁸ The ν_{CN} absorption bands for $M(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ are consistent with coordinated $[\text{TCNE}]^-$ and are similar, albeit sharper and occur at higher in energy, to that observed for $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$. In contrast to disordered $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$, $M(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ ($M = \text{Mn, Fe}$) give X-ray powder patterns, which have yet to be indexed.

The spin and oxidation states of $\text{Fe}(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ **3** were determined from ^{57}Fe Mössbauer spectroscopy.¹⁸ Above 95 K, **3** has absorptions with large chemical shift [$\delta = 1.23$ mm s^{-1}] and quadrupole coupling [$\Delta E_{\text{q}} = 3.26$ mm s^{-1}] characteristic of hexacoordinate, high-spin Fe^{II} compounds¹⁹ (Fig. 5). Below 95 K, the spectra become more complex due to magnetic

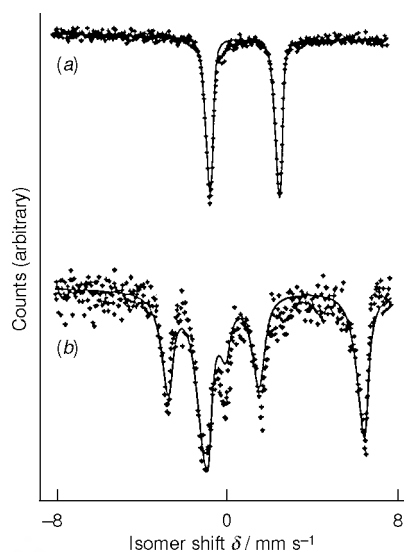


Fig. 5 ^{57}Fe Mössbauer spectra of $\text{Fe}(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ at (a) 50 and (b) 100 K¹⁸

splitting [$\delta = 1.24$ mm s^{-1} ; $\Delta E_{\text{q}} = 3.31$ mm s^{-1} , $H_{\text{int}} = 229$ KOe] (Fig. 5) in agreement with the critical temperature determined *via* magnetic studies (*vide infra*).

Complex **3** has a complex magnetic behavior which is essentially independent of preparation and amount of solvent.¹⁸ The susceptibility cannot be fitted to the Curie–Weiss law, $\chi \propto (T - \theta)^{-1}$, as expected for high-spin d^6 Fe^{II} in an octahedral environment with spin-orbit coupling. A spontaneous magnetization occurs below a T_c of 121 K, taken here as the intercept with the temperature axis of the initial slope of the magnetization as a function of temperature (Fig. 6). At 2 K the

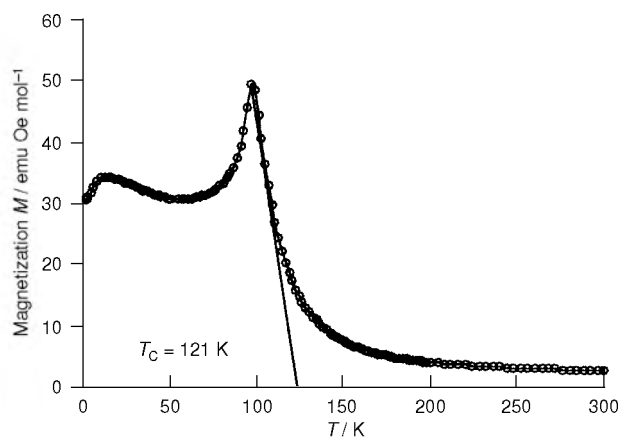


Fig. 6 Zero-field cooled magnetization as function of temperature for $\text{Fe}(\text{TCNE})_{2,0.75}\text{CH}_2\text{Cl}_2$

magnetization shows a complex, poorly understood response to the field, reminiscent of metamagnetic behavior. At 5 T and 2 K the observed magnetization is *ca.* 16 900 emu Oe mol^{-1} ; however, higher fields are necessary to achieve saturation. This value of saturation magnetization corresponds to three $S = 1/2$ spins and exceeds the comparable value of 10 300 emu Oe mol^{-1} for $V(\text{TCNE})_{x,y}(\text{CH}_2\text{Cl}_2)$ prepared from $V(\text{CO})_6$ ⁸ by 63%, as well as exceeding the expectation of that from antiferromagnetically coupling between an $S = 2$ Fe^{II} site and two $S = 1/2$ $[\text{TCNE}]^-$, *i.e.* 11 200 emu Oe mol^{-1} , but is substantially less than the expectation from ferromagnetic coupling, *i.e.* 33,500 emu Oe mol^{-1} . Although the T_c shows little dependence on the synthetic route, hysteresis loops taken at 2 K show a strong variation in the coercive field ranging from 300 to 3000 G. Likewise, the detailed field and zero field cooled curves also have a strong dependency on reaction conditions and aging.

$\text{Fe}(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ shows remarkable thermal stability. The IR spectrum and X-ray powder pattern, as well as magnetic data of a sample heated at 130 °C for 38 h, suggest that the chemical and structural features of the materials are preserved after the heat treatment, except for the apparent solvent loss. Some thermal degradation is observed from magnetic measurements on a sample treated at 180 °C, and massive decomposition is evident from IR studies when the material is heated to 200 °C. TGA data show that although desolvation starts at temperatures as low as 40 °C, it does not approach completion until the sample decomposes. Since CH_2Cl_2 is a poorly coordinating solvent, the high desolvation temperature may be attributed to CH_2Cl_2 being trapped into a three-dimensional network, and is only completely released when the structure collapses. $\text{Fe}(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ is not pyrophoric as is $V(\text{TCNE})_{x,y}(\text{solvent})$, but it does decompose in air.

Reactions of TCNE and MeCN solvates of MI_2 ($M = \text{Mn, Co, Ni}$) led to $M(\text{TCNE})_{2,x}\text{CH}_2\text{Cl}_2$ species which magnetically order with T_c values of 44 ($M = \text{Ni, Co}$) and 107 K ($M = \text{Mn}$)⁸ (Table 1). The nearest neighbor spin coupling energy, J , can be estimated from the mean-field expression of $T_c = JzS(S + 1)/3k_{\text{B}}$, where k_{B} = Boltzmann's constant, z = number of nearest neighbors, *i.e.* 6, and assuming $H = -2J\text{S}_a \cdot \text{S}_b$. The

Table 1 Summary of the infrared ν_{CN} absorption bands, saturation magnetization M_s , ordering temperature T_c and exchange energy J for $M(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ ($M = \text{V}, \text{Mn}, \text{Fe}, \text{Co}, \text{Ni}$)¹⁸

Metal	Saturation magnetization ^a $M_s/\text{emu Oe mol}^{-1}$	T_c/K	J/K^b
V ^c	10 300	~400	53
Mn ^d	19 000	107	6.1
Fe ^d	16 900	121	10
Co ^d	8 000	44	5.9
Ni ^d	15 800	44	11

^a 2 K and 5 T. ^b See text. ^c Ref. 7. ^d Ref. 18.

resulting estimates of J ranges as $\text{V} \gg \text{Ni} \sim \text{Fe} > \text{Mn} \sim \text{Co}$ (Table 1). $\text{Mn}(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ is isostructural to $\text{Fe}(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ based upon powder diffraction data; however, for $M = \text{Ni}, \text{Co}$ the solids diffract poorly and do not appear to be isomorphous to $M(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ ($M = \text{Fe}, \text{Mn}$). Hence, based upon the composition and the similarity of the ν_{CN} absorptions for $M = \text{Mn}, \text{Co}$ and Ni , we assign all the metals as being divalent. Likewise, the elusive oxidation state of V in the room temperature $\text{V}(\text{TCNE})_2 \cdot y\text{CH}_2\text{Cl}_2$ magnet is again assigned the divalent oxidation state.^{7,8}

Hysteresis is observed for all the magnets below T_c , however, as observed for $\text{V}(\text{TCNE})_2 \cdot y(\text{CH}_2\text{Cl}_2)$,^{7,8} the coercive field varies from preparation to preparation. Nonetheless, the observed coercive fields range from 50 ($M = \text{Ni}$) to 6500 Oe ($M = \text{Co}$). The shape of the hysteresis curves is characteristic of metamagnetic behavior in some cases, e.g. for $\text{Fe}(\text{TCNE})_2 \cdot 0.75\text{CH}_2\text{Cl}_2$ at 2 K (Fig. 7) and, along with more detailed magnetic studies, including ac measurements, is the focus of future research.


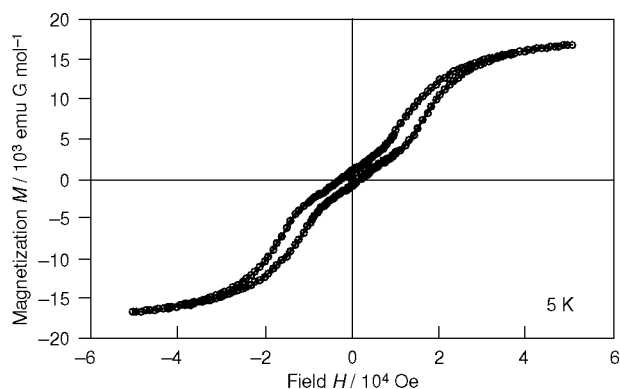


Fig. 7 An example of the observed hysteretic $M(H)$ for $\text{Fe}(\text{TCNE})_2 \cdot 0.75\text{CH}_2\text{Cl}_2$ at 2 K. The observed coercive field for this sample is 2300 Oe and the sample saturates to 16 900 emu Oe mol^{-1} .

Hence, a new synthetic route enabling the preparation of several new examples of molecule-based magnets of $M^{\text{II}}(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ composition has been identified. These new magnets have T_c values that exceed 100 K and coercive fields as great as 6500 Oe.

While preparing the $M^{\text{II}}(\text{TCNE})_2 \cdot x\text{CH}_2\text{Cl}_2$ magnets, crystals (light yellow for $M = \text{Mn}$; dark brown for $M = \text{Fe}$) which did not magnetically order were isolated. Single crystal X-ray diffraction studies revealed the unprecedented octacyano-butanediide dianion, $[\text{C}_4(\text{CN})_8]^{2-}$ **4**, bound to four octahedral

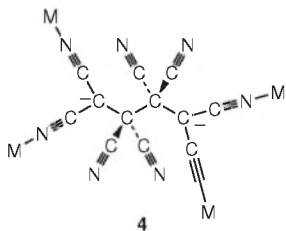


M^{II} s in a plane with the MeCN molecules filling the axial coordination sites, i.e. $\text{Mn}[\text{C}_4(\text{CN})_8](\text{NCMe})_2 \cdot \text{CH}_2\text{Cl}_2$ **5** and $\text{Fe}[\text{C}_4(\text{CN})_8](\text{NCMe})_2 \cdot \text{MeCN}$ **6**.²⁰ Compound **4** is disordered about the midpoint of the central C–C bond for $M = \text{Mn}$, but is ordered for $M = \text{Fe}$, and has long 1.59 (2) ($M = \text{Mn}$) and 1.627 (14) Å ($M = \text{Fe}$) central C–C bonds suggesting that it is a weak bond. This is the first example of a σ -dimer of $[\text{TCNE}]^-$, however, several examples of a structurally related σ -dimer of $[\text{TCNQ}]^-$ ($\text{TCNQ} = 7,7,8,8$ -tetracyano-*p*-quinodimethane) have been reported.²¹

Compounds **5** and **6** are paramagnets obeying the Curie–Weiss law above 5 K. This is consistent with diamagnetic $[\text{C}_4(\text{CN})_8]^{2-}$ weakly coupling the metal spin sites ($S = 5/2$ Mn^{II}). Upon desolvation of **5** and **6** at 100 °C the ν_{CN} IR absorptions disappear and new ν_{CN} bands characteristic of the $M(\text{TCNE})_2 \cdot x\text{S}$ magnets²⁰ ($M = \text{Mn}, \text{Fe}$) appear. Desolvated **5** magnetically orders at a T_c of 95 K,²⁰ in reasonable agreement with samples prepared from CH_2Cl_2 .¹⁸ Compound **6** behaves in a similar fashion upon desolvation. These observations suggest that upon desolvation the $S = 0 \mu_4-[\text{C}_4(\text{CN})_8]^{2-}$ reforms two $S = 1/2$ $[\text{TCNE}]^-$ units which can bind to additional metal centers, providing stronger spin coupling leading to the observed magnetic ordering. Evidence for this type of bond breaking has been reported for σ -dimers of $[\text{TCNQ}]^-$.^{21a}

Hence, additional members of the $M(\text{TCNE})_x$ class of magnets have been characterized, and in the case of Fe the metal is assigned to be divalent as previously proposed for $\text{V}(\text{TCNE})_2 \cdot y\text{solvent}$.⁷ Furthermore, an intermediate in the formation of the $M(\text{TCNE})_x$ class of magnets, namely $[\text{C}_4(\text{CN})_8]^{2-}$ **6**, has been identified and structurally characterized.

[Mn(porphyrin)][TCNE]-based magnets

Another class of TCNE-based magnets is exemplified by $[\text{Mn}^{\text{III}}\text{TPP}][\text{TCNE}]^-$ (TPP = *meso*-tetraphenylporphyrinato), which forms a coordination polymer (1-D) that was characterized to be a ferrimagnet with T_c 14 K.²² With the goal of identifying the importance of 1-D with respect to 3-D interactions and developing a structure–function relationship for this class of magnetic materials, as well as preparing new molecule-based magnets with enhanced T_c s, we have pursued the study of this class of compounds.

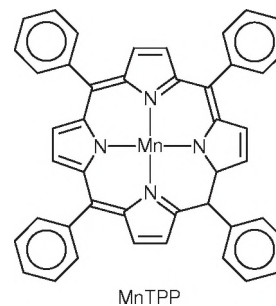

$[\text{Mn}^{\text{III}}\text{TPP}][\text{TCNE}]^-$ forms uniform parallel 1-D chains in the solid state with each $S = 2$ Mn^{III} bonded to four porphyrin nitrogens (ca. 2.00 Å) and axially to two $[\text{TCNE}]^-$ nitrogens (ca. 2.30 Å), and each $S = 1/2$ $[\text{TCNE}]^-$ is *trans-μ*-bonded to two Mn^{III} species, [Fig. 8 (a)]. The magnetic susceptibility of $[\text{MnTPP}][\text{TCNE}]^- \cdot 2\text{PhMe}$ can be fitted to the Curie–Weiss expression above 280 K with $\theta \sim -15$ K, and between 115 and 250 K with an effective θ, θ' , of +61 K. A minimum in the value of χT , characteristic of 1-D ferrimagnetic behavior, is observed at ~310 K and field-dependent susceptibility is observed below 50 K. Magnetic ordering occurs below 13 K (as determined by scaling analysis^{22c}) and hysteresis with a coercive field of 375 G was obtained at 5 K.²² Thus, $[\text{MnTPP}][\text{TCNE}]$ is a representative example of a new structure type of organic-based magnetic materials, and is an excellent model system for

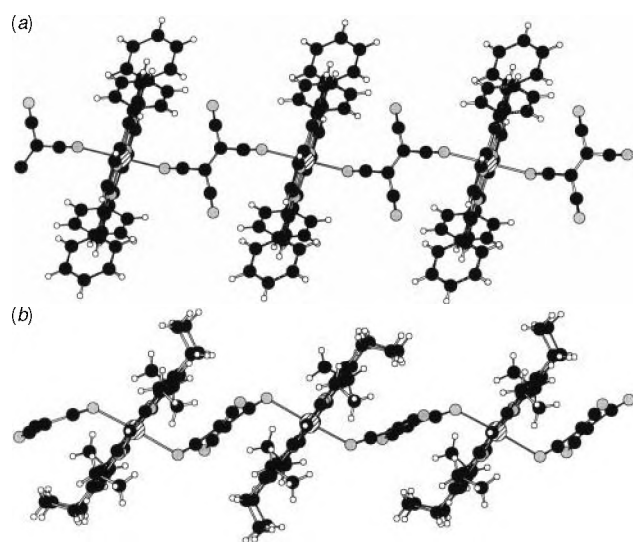


Fig. 8 (a) Segment of a uniform chain of the ferrimagnetic $[\text{Mn}^{\text{III}}\text{TPP}][\text{TCNE}]\cdot 2\text{PhMe}$ coordination polymer (the solvent is omitted for clarity). (b) Alternating chain segment of the paramagnetic $[\text{Mn}^{\text{III}}\text{OEP}][\text{TCNE}]$ coordination polymer.

studying a number of unusual magnetic phenomena, for example, the magnetic behavior of mixed quantum/classical spin systems.

In addition to modification of the porphyrin ring, the clathrate nature of this class of metalloporphyrins²³ enables the introduction of different solvents into the structure to alter the inter- and intra-chain couplings and the magnetic properties. In this review we focus on modification of the $[\text{MnTPP}][\text{TCNE}]$ structure type and discuss the consequent magnetic properties.

$[\text{MnTPP}][\text{TCNE}]\cdot 2\text{PhMe}$ **6**^{22a} has been crystallographically characterized. Likewise, the $[\text{TCNE}]^-$ salts of 4-methoxyphenyl (**7**),²⁴ 4-chlorophenyl (**8**)²⁵ and 2-fluorophenyl substituted $[\text{MnTPP}]^+$ (**9**)²⁴ and *meso*-tetrakis(3,5-di-*tert*-butyl-4-hydroxyphenyl)porphyrinatomanganese(III), MnTP^{P} ²⁶ (**10**), have been studied by single crystal X-ray diffraction. Furthermore, to extend this system the analogous TCNE electron-transfer salt was prepared with the easier-to-oxidize MnOEP (OEP = octaethylporphyrinato).²⁷

$[\text{MnOEP}][\text{TCNE}]$ has weak ferromagnetic coupling as evidenced by the fitting of the susceptibility to the Curie–Weiss expression with a θ' of +7 K.²⁷ However, unlike $[\text{MnOEP}][\text{TCNE}]$, magnetic ordering is not observed above 2 K. The differences in the magnetic properties are ascribed to structural differences. Although both $[\text{MnTPP}][\text{TCNE}]\cdot 2\text{PhMe}$ and $[\text{MnOEP}][\text{TCNE}]$ form parallel 1-D chains (Fig. 8), due to the differing orientations of $[\text{TCNE}]^-$ within a chain they are alternating chains for $[\text{MnOEP}][\text{TCNE}]$ instead of being uniform chains as for $[\text{MnTPP}][\text{TCNE}]\cdot 2\text{PhMe}$. Thus, uniform chains appear to be important to achieve long range magnetic order.²⁷

A correlation of the dihedral angle, ϕ , between the $[\text{Mn}^{\text{III}}\text{TPP}]^+$ MnN_4 and $[\text{TCNE}]^-$ mean planes and the magnitude of magnetic coupling has been observed for ditoluene solvates of five $[\text{TCNE}]^-$ salts, **6–10**.²⁸ The magnitude of magnetic coupling is determined from T_{min} , the temperature at which a minimum in $\chi T(T)$ or $\mu(T)$ plots occurs, as expected for antiferromagnetically coupling linear chain systems,²⁹ and the effective θ , θ' , obtained from a fit of the data to the Curie–Weiss expression. A correlation to T_{min} is preferred as it is model independent; however, for strongly coupled systems T_{min} is not observed as it occurs at temperatures exceeding the measurement range. T_{min} , however, can be estimated from a fit of the data to the Seiden expression for isolated 1-D chains comprised of alternating quantum ($S = 1/2$) and classical ($S > 1/2$) spins.³⁰

The smaller ϕ the stronger the magnetic coupling, *i.e.* the greater T_{min} and θ' (Fig. 9). Hence to attain strong intrachain coupling systems with more acute dihedral angles are sought and, based on **10**, 3,5-disubstituted $[\text{MnTPP}]^+$ s are preferred over 2- or 4-substituted $[\text{MnTPP}]^+$ s which from the data acquired to date have higher ϕ values. To test this postulate several 3,5-disubstituted systems are being studied. Likewise, pressure also may force such systems to have reduced angles and also lead to higher T_c values.

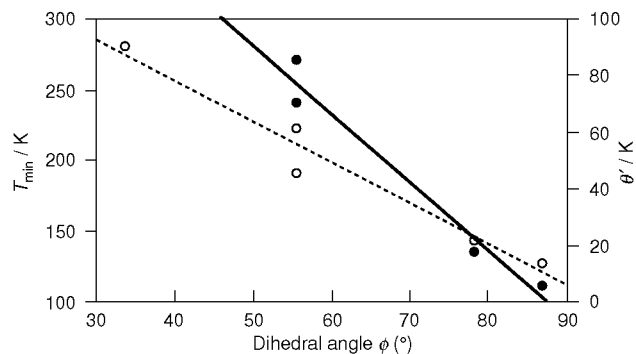


Fig. 9 Correlation of the dihedral angle ϕ between the MnN_4 and $[\text{TCNE}]^-$ mean planes with the temperature at which $\chi T(T)$ data has a minimum, (T_{min} , ● and solid line) and the effective θ value (θ' ; ○ and dashed line).²⁸

The aforementioned correlation between ϕ and T_{min} and θ' is attributed to the overlap between the $[\text{TCNE}]^-$ N -bound to Mn^{III} π^* SOMO and the four Mn^{III} SOMO d orbitals. [The energy of the latter increase as d_{xy}^1 (b_1) < d_{xz}^1 , d_{yz}^1 (e) < $d_{z^2}^1$ (a_1) < $d_{x^2-y^2}$ (b_1).³¹] From MO considerations (determined from semi-empirical INDO/SCF calculations) the expected $d_{\pi}-p_z$ ($d_{\pi} = d_{xz}, d_{yz}$) overlap is not as important as the $\sigma-d_z/p_z$ overlap between Mn^{III} and the $[\text{TCNE}]^-$ (Fig. 10).²⁸ Furthermore, the smaller ϕ increases the $\sigma-d_z/p_z$ overlap between Mn^{III} and the $[\text{TCNE}]^-$ leading to an increased intrachain coupling, as reflected in T_{min} and θ' (Fig. 10).

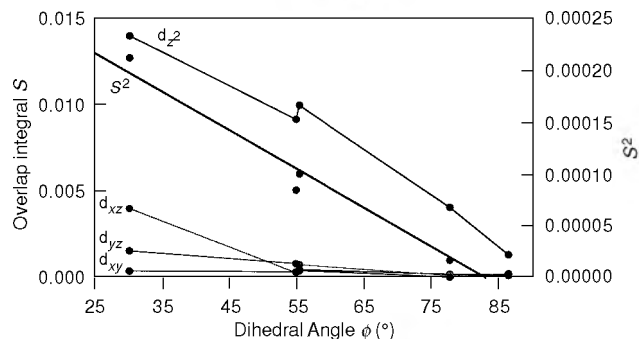


Fig. 10 Correlation of the dihedral angle ϕ between the MnN_4 and $[\text{TCNE}]^-$ mean planes with the semi-empirical INDO/SCF calculated d_{yz} , d_{xz} , d_{xy} and d_{z^2} -like overlap integrals S with the $[\text{TCNE}]^-$ π^* SOMO and the sum of the squares of these overlap integrals ΣS^2

While the σ overlap between the $[\text{TCNE}]^-$ p_z orbital and the $\text{Mn } d_{z^2}$ orbital controls the intrachain magnetic exchange, the three-dimensional magnetic ordering temperature, T_c , depends upon this term *and* the interchain exchange. The later term is governed by the competition between antiferromagnetic exchange due to orbital overlap between porphyrin moieties of adjacent chains and an effective exchange due to dipolar interactions between chains. The dipolar term can be ferromagnetic or antiferromagnetic depending upon the structural order in the compound and the role of single ion anisotropy.³²

Acknowledgments

The authors gratefully acknowledge support from the U.S. Department of Energy Division of Materials Science (Grant

Table 2 Summary of the structural and magnetic parameters for the several [TCNE][−] magnets

Porphyrin	Mn–N _{TCNE} distance/Å	Dihedral angle (°)	Mn···Mn distance/Å	Effective θ/K	T _{min} /K
[Mn _n TTPP][TCNE]·2PhMe	2.306	55.4	10.116	61	270
[MnTCIPP][TCNE]·2PhMe	2.267	86.8	10.189	13	110
[MnTOMePP][TCNE]·2PhMe	2.289	78.1	10.256	21	134
[MnTFPP][TCNE]·2PhMe	2.313	55.4	10.185	45	240
[MnTP ⁺ P][TCNE]·2PhMe	2.299	33.6	8.587	90	> 300 ^b

^a Intrachain. ^b Not plotted in Fig. 10.

Nos. DE-FG03-93ER45504 and DE-FG02-86ER45271.A000) and the U.S. National Science Foundation (Grant No. CHE-9320478).

Joel S. Miller was born in Detroit, MI and received his Bachelor of Science in Chemistry from Wayne State University (1967) and PhD from UCLA (1971). After a postdoctoral fellowship at Stanford University he joined the Xerox Webster Research Center in 1972 and later joined the now-defunct Occidental Research Corporation. He was Visiting Professor of Chemistry at the University of California, Irvine, CA. He joined the Central Research & Development Department at the Du Pont Company in 1983 where he was a Research Supervisor for solid state science. He has been a Visiting Scientist at the Weizmann Institute (1985) and a Visiting Professor of Chemistry at the University of Pennsylvania (1988). He joined the faculty of Department of Chemistry at the University of Utah in 1993. He is on the advisory board of *Advanced Materials* and *Journal of Materials Chemistry*, and a member of the Inorganic Synthesis Corporation. His research interests focus on the solid state magnetic, electrical and optical properties of molecular (organic, organometallic and inorganic coordination) compounds and electron transfer complexes as well as the surface modification of solids. Currently he is actively involved in synthesis and characterization of molecular/organic based ferromagnets. In addition to patents he has edited eleven monographs and published over 300 papers in these and other areas.

Arthur J. Epstein was born in Brooklyn, NY and received his BS in Physics from the Polytechnic Institute of Brooklyn in 1966 and his PhD in Physics from the University of Pennsylvania in 1971. After a year as Member of the Technical Staff of The MITRE Corporation and thirteen years at the Xerox Webster Research Center where he was Principal Scientist, he joined The Ohio State University in 1985 as Professor of Physics and Professor of Chemistry. In 1997 he was appointed as Distinguished University Professor. He has been the Director of The Ohio State University Center for Materials Research since 1989. He also has been adjunct Professor of Physics at the University of Florida and has been a visiting Professor at the Université Paris-Sud and the Technion—Israel Institute of Technology—and is presently Adjunct Professor of Chemistry at University of Utah. He is a Regional Editor for *Synthetic Metals*. His current research interests include experimental and theoretical study of magnetic, electronic/optical and transport phenomena of synthetic magnets (molecular, organic and polymeric magnets) and synthetic metals (conducting polymers, organic and molecular materials), including the study of excitations and their dynamics. He is also active in the exploration of potential applications of unconventional magnetic, electronic and optical materials for which he consults with several companies. In addition to having originated twenty patents and editing five conference proceedings, he has published over 500 papers in these and other areas.

Notes and References

† E-mail: jsmiller@chemistry.chem.utah.edu

‡ E-mail: epstein.2@osu.edu

- 1 P. W. Anderson, *Concepts in Solids*, W. A. Benjamin, Inc., 1963, p. 7; H. M. McConnell, *J. Chem. Phys.* 1963, **39**, 1910; H. M. McConnell, *Proc. Robert A. Welch Found. Conf. Chem. Res.* 1967, **11**, 144.
- 2 J. S. Miller, A. J. Epstein and W. M. Reiff, *Mol. Cryst., Liq. Cryst.*, 1985, **120**, 27; J. S. Miller, J. C. Calabrese, A. J. Epstein, R. W. Bigelow, J. H. Zhang and W. M. Reiff, *J. Chem. Soc., Chem. Commun.* 1986, 1026; J. S. Miller, J. C. Calabrese, H. Rommelmann, S. Chittipeddi, A. J. Epstein, J. H. Zhang and W. M. Reiff, *J. Am. Chem. Soc.*, 1987, **109**, 769.
- 3 M. Kinoshita, *Jpn. J. Appl. Phys.* 1994, **33**, 5718; R. Chiarelli, A. Rassat, Y. Dromzee, Y. Jeannin, M. A. Novak and J. L. Tholence, *Phys. Scr.*, 1993, **T49**, 706.
- 4 J. S. Miller, and A. J. Epstein, *Angew. Chem.*, 1994, **106**, 399; *Angew. Chem. Int. Ed. Engl.*, 1994, **33**, 385; J. S. Miller and A. J. Epstein, *Chem. Eng. News*, 1995, **73**(#40), 30.
- 5 O. Kahn, *Molecular Magnetism*, VCH, Weinheim, 1993.
- 6 D. Gatteschi, *Adv. Mater.*, 1994, **6**, 635; A. Caneschi, D. Gatteschi, R. Sessoli and P. Rey, *Acc. Chem. Res.*, 1989, **22**, 392; A. Caneschi and D. Gatteschi, *Prog. Inorg. Chem.*, 1991, **37**, 331.
- 7 (a) J. M. Manriquez, G. T. Yee, R. S. McLean, A. J. Epstein and J. S. Miller, *Science*, 1991, **252**, 1415; J. S. Miller, G. T. Yee, J. M. Manriquez and A. J. Epstein, *Proceedings of Nobel Symposium #NS-81, Conjugated Polymers and Related Materials: The Interconnection of Chemical and Electronic Structure*, Oxford University Press, 1993, p. 461; *Chim. Ind.*, 1992, **74**, 845; A. J. Epstein and J. S. Miller, *Proceedings of Nobel Symposium #NS-81 Conjugated Polymers and Related Materials: The Interconnection of Chemical and Electronic Structure*, Oxford University Press, 1993, p. 475; *Chim. Ind.*, 1993, **75**, 185; (b) P. Zhou, B. Morin, A. J. Epstein and J. S. Miller, *Phys. Rev. B.*, 1993, **48**, 1325; (c) P. Zhou, S. M. Long, J. S. Miller and A. J. Epstein, *Phys. Lett. A*, 1993, **181**, 71; (d) G. Du, J. Joo, A. J. Epstein and J. S. Miller, *J. Appl. Phys.*, 1993, **73**, 6566.
- 8 J. Zhang, P. Zhou, W. B. Brinckerhoff, A. J. Epstein, C. Vazquez, R. S. McLean and J. S. Miller, *ACSSymp. Ser.*, 1996, **644**, 311.
- 9 D. A. Dixon and J. S. Miller, *J. Am. Chem. Soc.*, 1987, **109**, 3656.
- 10 E.g. W. Beck, R. Schlodder, and K. H. Lechler, *J. Organomet. Chem.*, 1973, **54**, 303; A. Maisonnat, J.-J. Bionnet and R. Poilblanc, *Inorg. Chem.*, 1980, **19**, 3168; M. I. Bruce, T. W. Hambley, M. R. Snow and A. G. Swincer, *J. Organomet. Chem.*, 1982, **235**, 105; W. H. Baddley, *J. Am. Chem. Soc.*, 1968, **90**, 3705; W. H. Baddley and L. M. Venanzi, *Inorg. Chem.*, 1966, **5**, 33.
- 11 C. Vazquez, J. C. Calabrese, D. A. Dixon and J. S. Miller, *J. Org. Chem.*, 1993, **58**, 65.
- 12 T. Mallah, S. Thiébaud, M. Verdaguer and P. Veillet, *Science*, 1993, **262**, 1554.
- 13 D. G. Gordon and J. S. Miller, unpublished results.
- 14 J. S. Miller, *Adv. Mater.*, 1994, **6**, 322; C. P. Landee, D. Melville and J. S. Miller, in *NATO ARW Molecular Magnetic Materials*, ed. O. Kahn, D. Gatteschi, J. S. Miller and F. Palacio, 1991, **E198**, 395.
- 15 B. G. Morin, C. Hahn, A. J. Epstein and J. S. Miller, *J. Appl. Phys.*, 1994, **75**, 5782.
- 16 J. S. Miller, D. M. O'Hare, A. Chackraborty and A. J. Epstein, *J. Am. Chem. Soc.*, 1989, **111**, 7853.
- 17 B. Olbrich-Deussner, R. Gross and W. Kaim, *J. Organomet. Chem.*, 1989, **366**, 155; M. Heberhold, *Angew. Chem., Int. Ed. Engl.*, 1968, **7**, 305; B. Olbrich-Deussner, W. Kaim and R. Gross-Lannert, *Inorg. Chem.*, 1989, **28**, 3113.
- 18 J. Zhang, J. Ensling, V. Ksenofontov, P. Gülich, A. J. Epstein and J. S. Miller, *Angew. Chem. Int. Ed. Engl.*, 1998, **37**, 657.

- 19 P. Gülich, R. Link and A. Trautwein, in *Inorganic Concepts 3: Mössbauer Spectroscopy and Transition Metal Chemistry*, Springer-Verlag, Berlin, Heidelberg, New York, 1988, pp. 19, 56–77.
- 20 J. Zhang, L. M. Liable-Sands, A. L. Rheingold, R. E. Del Sesto, D. C. Gordon, B. M. Burkhardt and J. S. Miller, *Chem. Commun.*, 1998, 1385.
- 21 (a) R. H. Harms, H. J. Keller, D. Nöthe, M. Werner, D. Grundel, H. Sixl, Z. Soos and R. M. Metzger, *Mol. Cryst. Liq. Cryst.* 1981, **65**, 179; (b) S. K. Hoffman, P. J. Corvan, P. Singh, C. N. Sethuklekshmi, R. M. Metzger and W. E. Hatfield, *J. Am. Chem. Soc.*, 1983, **105**, 4608; (c) V. Dong, H. Endres, H. J. Keller, W. Moroni and D. Nöthe, *Acta Crystallogr.*, 1977, **B33**, 2428; H. Zhao, R. A. Heintz, K. R. Dunbar and R. D. Rogers, *J. Am. Chem. Soc.*, 1996, **118**, 12 844; B. Morosin, H. J. Platas, L. B. Coleman and J. M. Stewart, *Acta Crystallogr.*, 1978, **B34**, 540.
- 22 (a) J. S. Miller, J. C. Calabrese, R. S. McLean and A. J. Epstein, *Adv. Mater.*, 1992, **4**, 498; (b) P. Zhou, B. G. Morin, A. J. Epstein, R. S. McLean and J. S. Miller, *J. Appl. Phys.*, 1993, **73**, 6569; (c) W. B. Brinckerhoff, B. G. Morin, E. J. Brandon, J. S. Miller and A. J. Epstein, *J. Appl. Phys.*, 1996, **79**, 6147.
- 23 I. Goldberg, H. Krupitsky, Z. Stein, Y. Hsiou and C. E. Strouse, *Supramol. Chem.*, 1995, **4**, 203; H. Krupitsky, Z. Stein and I. Goldberg, *Inclusion Phenom. Mol. Recognit.*, 1995, **20**, 211; I. Goldberg, *Mol. Cryst. Liq. Cryst.*, 1996, **278**, 767; M. P. Byrn, C. J. Curtis, Y. Hsiou, S. I. Kahn, P. A. Sawin, S. K. Tendick, A. Terzis and C. E. Strouse, *J. Am. Chem. Soc.*, 1993, **115**, 9480.
- 24 E. J. Brandon, A. M. Arif, B. M. Burkhardt and J. S. Miller, unpublished work.
- 25 E. J. Brandon, D. K. Rittenberg, A. M. Arif and J. S. Miller, unpublished work.
- 26 A. Böhm, C. Vazquez, R. S. McLean, J. C. Calabrese, S. E. Kalm, J. L. Manson, A. J. Epstein and J. S. Miller, *Inorg. Chem.*, 1996, **35**, 3083.
- 27 J. S. Miller, C. Vazquez, N. L. Jones, R. S. McLean and A. J. Epstein, *J. Mater. Chem.*, 1995, **5**, 707.
- 28 E. J. Brandon, C. Kollmar and J. S. Miller, *J. Am. Chem. Soc.*, 1998, **120**, 1822; E. J. Brandon and J. S. Miller, *NATO ARW Supramolecular Engineering of Synthetic Metallic Materials: Conductors and Magnets*, ed. J. Veciana, C. Rovira and D. Amabilino, in the press.
- 29 E. Coronado, M. Drillon and R. Georges, in *Research Frontiers in Magnetochemistry*, ed. C. J. O'Connor, World Scientific, 1993, p. 26.
- 30 J. Seiden, *J. Phys. Lett.*, 1983, **44**, L947.
- 31 L. B. Dugad, D. V. Behere, V. R. Marathe and S. Mitra, *Chem. Phys. Lett.*, 1984, **104**, 353.
- 32 C. M. Wynn, M. Girtu, W. B. Brinckerhoff, K.-I. Sugiura, J. S. Miller and A. J. Epstein, *Chem. Mater.*, 1997, **9**, 2156.

8/00922H