

Journal Article

Synthesis of cationic alkylated chitosans and an investigation of their rheological properties and interaction with anionic surfactant

Burr, S., Williams, P.A. and Ratcliffe, I.

This article is published by Carbohydrate Polymers. The definitive version of this article is available at: <https://www.sciencedirect.com/science/article/pii/S0144861718310142#!>

Recommended citation:

Burr, S., Williams, P.A. and Ratcliffe, I. (2018), 'Synthesis of cationic alkylated chitosans and an investigation of their rheological properties and interaction with anionic surfactant', Carbohydrate Polymers, vol 201, pp. 615-623. doi: 10.1016/j.carbpol.2018.08.105

Accepted Manuscript

Title: Synthesis of cationic alkylated chitosans and an investigation of their rheological properties and interaction with anionic surfactant

Author: S.J. Burr P.A. Williams I. Ratcliffe



PII: S0144-8617(18)31014-2
DOI: <https://doi.org/doi:10.1016/j.carbpol.2018.08.105>
Reference: CARP 14002

To appear in:

Received date: 25-6-2018
Revised date: 1-8-2018
Accepted date: 24-8-2018

Please cite this article as: S.J. Burr, P.A. Williams, I. Ratcliffe, Synthesis of cationic alkylated chitosans and an investigation of their rheological properties and interaction with anionic surfactant, *Carbohydrate Polymers* (2018), <https://doi.org/10.1016/j.carbpol.2018.08.105>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Synthesis of cationic alkylated chitosans and an investigation of their rheological properties and interaction with anionic surfactant

Burr, S.J.* , Williams, P.A.* , Ratcliffe, I.*

*Centre for Water Soluble Polymers
Wrexham Glyndwr University, Wrexham, LL11 2AW, Wales, UK*

Abstract

Two methods were used to alkylate high M_W chitosan with glycidyltrimethylammonium chloride (GTAC) in order to produce chitosan derivatives that are water-soluble throughout the pH range. In addition, a novel chitosan derivative was created by alkylating one of the products with the GTAC analogue Quab 342 containing C12 alkyl chains. The phase behaviour and rheological characteristics of the chitosan derivatives were studied in the presence of anionic surfactant. The derivatives were found to form soluble complexes at low and high SDS concentrations and the Quab 342 derivative was able to form gels.

Keywords: chitosan, quaternisation, rheology, anionic surfactant interactions

1. Introduction

1 Chitin (poly β -(1 \rightarrow 4)-*N*-acetyl-D-glucosamine) is found in arthropod shells (Mao et al., 2017)
2 and the cell walls of yeasts and fungi. It is the second most abundant natural polysaccharide
3 after cellulose (Dutta et al., 2004), and it is in increasing demand as a raw material for many
4 sophisticated applications in medicine, agriculture and other areas (Dutta et al., 2004), (Xia
5 et al., 2011), (Pillai et al., 2009), (Hayes et al., 2008b), (Kumar et al., 2004). Chitin's desirable
6 properties include biocompatibility, biodegradability to normal body constituents, safety, non-
7 toxicity, binding to mammalian and microbial cells, and antimicrobial activity against bacteria
8 and fungi (Bellich et al., 2016), (Sahariah and Másson, 2017). These properties are shared by
9 its acid-soluble derivative chitosan, which is prepared by removing at least 50% of the *N*-acetyl
10 groups, and also by a wide variety of chemical derivatives.
11

12
13 Chitin is generally extracted from marine sources, such as shrimp shells and other shellfish
14 by-products, although there is also interest in fungal and insect chitin (Sajomsang and Gonil,
15 2010). The extraction process (reviewed by Hayes et al. (2008a) and Younes and Rinaudo (2015))
16 consists of demineralisation, deproteination, decolourisation, and in the case of chitosan, deacety-
17 lation. It generally involves strong acids and alkali, and may be extended to depolymerise the
18 chitosan if low M_W products are desired (Mohammed et al., 2013). Alternatively a specific de-
19 polymerisation step may be added, such as ultrasound or enzyme hydrolysis (Lodhi et al., 2014).
20

*Corresponding author. Tel: +441978 293126

Email addresses: S.Burr@glyndwr.ac.uk (Burr, S.J.), p.a.Williams@glyndwr.ac.uk (Williams, P.A.),
i.ratcliffe@glyndwr.ac.uk (Ratcliffe, I.)

21 Chemically, chitosan is a linear polyamine, basic, carrying reactive amino and hydroxyl
22 groups, capable of chelating transition metal ions, and soluble in water below pH 6.5. Its hy-
23 droxyl and amino groups can be acylated or alkylated, which is very useful, because its uses
24 under physiological conditions are limited by the fact that it precipitates when the pH is raised
25 above 6.5 (e.g. (Snyman et al., 2002), (Lim and Hudson, 2004) (Tungtong et al., 2012)). This
26 problem can be solved by adding polar or charged groups to the polysaccharide backbone. Hy-
27 drophobic groups such as dodecyl moieties are also sometimes added to make chitosan soluble in
28 organic solvents (Mourya and Inamdar, 2008) , or enable it to bind to plastics as a biodegradable
29 component (Kumar et al., 2004). Chemical derivatives of chitosan have been comprehensively
30 reviewed by Mourya and Inamdar (Mourya and Inamdar, 2008) while Sahariah and Másson dis-
31 cuss their antibacterial activity (Sahariah and Másson, 2017).

32
33 One potentially extremely useful modification is to convert the 2-amino group into a quater-
34 nary amine (Mourya and Inamdar, 2008), (Sahariah and Másson, 2017). The quaternary amine
35 remains charged throughout the pH range and if the degree of substitution (D.S.) is high enough
36 it can render even high M_W chitosans completely water-soluble. The simplest quaternised chi-
37 tosan is N,N,N-trimethyl chitosan, synthesised by reductive alkylation (Guo et al., 2007), which
38 has very promising antifungal (Snyman et al., 2002) and antibacterial activity (Sahariah and
39 Másson, 2017). However, because the reductive methylation synthesis requires iodomethane and
40 N-methyl pyrrolidine as a solvent, an alternative reaction which can be carried out in aqueous
41 solution is often preferred. Glycidyl trimethylammonium chloride (GTAC) alkylates the amino
42 groups via its epoxide ring and it already carries a quaternary amine group. The GTAC alkyla-
43 tion is well studied, and typically carried out under neutral conditions at temperatures of 70°C –
44 100°C (Kim et al., 2003), (Lim and Hudson, 2004), (Nam et al., 1999) and (Ruihua et al., 2012),
45 and the resulting quaternised chitosan also has antimicrobial activity (Sahariah and Másson,
46 2017), (Kim et al., 2003), (Lim and Hudson, 2004) and (Nam et al., 1999).

47
48 With its wide solubility range, quaternised chitosan has obvious potential applications in
49 a broad range of commercial products, including pharmaceuticals, nutraceuticals, cosmetics
50 and personal care products. As Dutta *et al* point out, chitosan can form a clear elastic skin
51 on hair (which is negatively charged), and it can form gels in aqueous alcohol solvents (many
52 types of cosmetics, skincare products and pharmaceuticals are applied as gels) and furthermore,
53 high M_W chitosans do not pass through the skin barrier (Dutta et al., 2004). If quaternised
54 chitosans share all these chitosan traits, they would be desirable components for these formula-
55 tions. In the case of shampoos it would also be desirable for the chitosans to have foaming and
56 emulsifying properties, either by themselves or when combined with surfactants in a formulation.

57
58 This study was undertaken to synthesise quaternised chitosans with high D.S. using GTAC.
59 Two synthetic methods were attempted. 1) Heterogeneous GTAC alkylation at high pH to alky-
60 late both the amino and hydroxyl groups on the chitosan backbone. Our first hypothesis was
61 that at high pH, the 3- and 6- hydroxyl groups may be alkylated as well, increasing the D.S. and
62 the charge density by up to three times. 2) Homogeneous GTAC alkylation in dilute perchloric
63 acid by Ruihua's method (Ruihua et al., 2012). In addition, a second alkylating agent was tested:
64 Quab 342, a GTAC analogue which carries a dodecyl chain in place of one of the quaternary
65 amine's methyl groups. The second hypothesis was that this quaternised chitosan derivative (with
66 hydrophobic groups in addition to the positively charged substituents) would have enhanced rhe-
67 ological characteristics due to intermolecular hydrophobic interaction and that the interactions
68 could be enhanced by the presence of anionic surfactants. Hydrophobically associating polymers,
69 which are predominately non-ionic or anionic, are finding increasing application in commercial

formulations in many industrial sectors and since the formulations invariably include surfactants a knowledge of the polymer-surfactant interactions is important (Williams, 2003), (Goddard and Ananthapadmanabhan, 1998), (Langevin, 2009).

2. Materials and Methods

2.1. Materials

High molecular weight chitosans ChitopharmTM S (S#2265, 17% Degree of Acetylation, DA) and ChitopharmTM L (L#2272, 16% DA) were supplied by Chitonor AS, Norway. Quab 342 (3-chloro-, 2-hydroxypropyl-*N,N,N*-dimethylammonium chloride) was a gift from Croda Ltd UK. Glycidyl trimethylammonium chloride (GTAC) was obtained from Sigma Aldrich; sodium dodecyl sulphate and all other chemicals were from Sigma-Aldrich or Fisher.

2.2. Alkylation of chitosan with Quab reagents

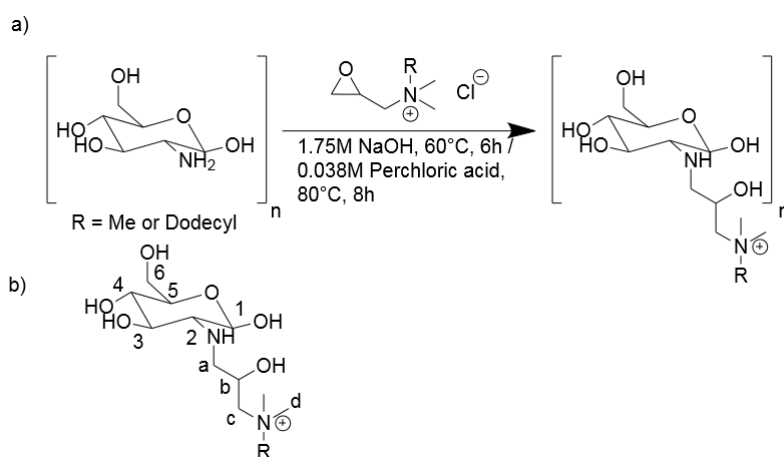


Figure 1: a) Reaction of GTAC or Quab 342 with chitosan monomer either by the high pH method: 1.75M NaOH, 60°C, 6h or Ruihua method: 0.038M perchloric acid, 80°C, 8h. b) Location of protons on the GTAC- or Quab 342-alkylated glucosamine monomer (R = Methyl, R = Dodecyl, respectively).

For the high pH GTAC alkylation reaction, the following method was used: 20g of high molecular weight chitosan S#2265 was suspended in 400g deionised water under mechanical stirring. 35 g sodium hydroxide pellets were dissolved in 100g distilled water, which was then added dropwise to the chitosan slurry. The vessel was then purged with inert nitrogen gas and the temperature raised to 60°C. 12.08g of GTAC was added via a pressure equalising funnel over 20 minutes at 0, 2 and 4 hours. At 6 hours the sample was allowed to cool, and neutralised with 32% HCl. The sample (G-2265) was subsequently washed with isopropanol.

To produce the G- and GQ-chitosan samples (see Table 2), the method of Ruihua et al (Ruihua et al., 2012) was employed. 5g of chitosan L#2272 was suspended in 750ml ultrapure water, and dissolved by dropwise addition of 4.75ml perchloric acid, with stirring. The sample was then heated to 60°C, with mechanical stirring. 12.5g of GTAC was added at 0, 30 and 60 minutes, then the temperature was raised to 80°C and the reaction continued for 8 hours. For the

95 G-chitosan, the product was then extracted by precipitation in acetone. For the GQ-chitosan,
 96 the pH was raised to 11.2 with 1M NaOH and the alkylation procedure was repeated, using Quab
 97 342 reagent in place of GTAC. The reactions are shown in Figure 1.

98 2.3. Characterisation of derivatised chitosans

99 FT-IR spectra of chitosans and chitosan derivatives were measured by the KBr disc method on
 100 a Perkin Elmer Spectrum RX1 FT-IR Spectrophotometer. Proton NMR spectra were recorded
 101 in D₂O on a Bruker Spectrophotometer at 400MHz, 298.2K, 256 scans and the fid files were
 102 analysed in MestReNova 9.0 software for Windows. Noise was removed by apodisation along t1
 103 (Exponential 0.3 and Gaussian 5.0) and background correction by Whitaker Smoother. Phase
 104 correction was applied as necessary. Peaks were integrated manually and normalised to the
 105 chitosan N-acetyl peak at 1.94 ppm. The degree of acetylation (DA%) was calculated from the
 106 areas of the N-acetyl group and the combined areas of H₂ and H₃₋₆ in equation 1.

$$\frac{\delta H_{NAc}/3}{\delta H_{2-6}/6} = DA\% \quad (1)$$

107 The degree of substitution of GTAC (DG%) for the G-chitosan was calculated from the areas
 108 of the N-acetyl protons and the single methine proton (b) on the 2-hydroxypropyl moiety in
 109 equation 2.

$$\frac{\delta H_b}{\delta H_{NAc}/3} * DA\% = DG\% \quad (2)$$

110 The degree of substitution of Quab 342 (DQ%) for the GQ-chitosan was calculated from the
 111 areas of the N-acetyl protons and the methylene protons of the dodecyl chain in equation 3.

$$\frac{\delta H_{methylene}/18}{\delta H_{NAc}/3} * DA\% = DQ\% \quad (3)$$

112 The degree of substitution of GTAC (DG%) for the GQ-chitosan calculated from the areas of
 113 the N-acetyl protons and the single methine proton (b) on the GTAC 2-hydroxypropyl moiety,
 114 with the methine proton of the Quab 342 2-hydroxypropyl group subtracted (equation 4). (It
 115 was assumed to be the equivalent of 1/18th of the $\delta H_{methylene}$ signal.)

$$\frac{\delta H_b - (\delta H_{methylene}/18)}{\delta H_{NAc}/3} * DA\% = DG\% \quad (4)$$

116 2.4. Molecular mass determination

117 The molar mass of the chitosan samples was determined using Gel Permeation Chromatog-
 118 raphy (GPC). The system consisted of a TSK G5000 PWxL and TSK G6000 PWxL column
 119 connected in series, with a TSK G3000 PWxL guard cartridge, equipped with an Optilab DSP
 120 interferometric refractometer and a Dawn EOS enhanced Multi Angle Laser Light Scattering
 121 detector (Wyatt Technology, Santa Barbara). The elution buffer was 0.1M sodium acetate, ad-
 122 justed to pH4.8 with 0.2M acetic acid, and the flow rate was 0.5ml/min. Chitosan samples were
 123 dissolved in 1% acetic acid (10mg/ml) and diluted in 1:1 0.1M sodium acetate / 0.2M acetic
 124 acid. M_W values were calculated in Astra 4.9 software using a Debye model using first order
 125 polynomial results fitting (measured dn/dc value of 0.151)(Mohammed et al., 2013).

126
 127 The Degree of Polymerisation (DP) was calculated for the S#2265, L#2272, G.2265 and
 128 G-chitosans from the chitosan M_W divided by the monomer masses of N-acetylglucosamine (203

129 Da), glucosamine (161 Da), and GTAC-labelled glucosamine (277 Da), multiplied by their re-
 130 spective monomer percentages DA%, DD% and DG%.

131

$$132 \quad DA\% * 203 + DD\% * 161 + DG\% * 277 = M_W(Monomer) \quad (5)$$

$$\frac{M_W}{M_W(Monomer)} = DP \quad (6)$$

133 2.5. Rheology

134 The steady shear viscosities and storage and loss moduli (G' and G'') were measured on a TA
 135 Advanced Rheometer AR2000 (TA Instruments, New Castle, DE), using standard sized recessed
 136 end concentric cylinders (for dilute solutions) and 6 cm diameter 2° stainless steel cone and plate
 137 geometry (for gels). Viscosity measurements included a 3 minute preconditioning step at 25°C,
 138 followed by a single measurement at 1 s⁻¹ or a stepped flow measurement from 0.01 - 1000 s⁻¹.
 139 Mechanical spectra were recorded from 0.1 - 100 Hz at 25°C, 10% strain, which was determined
 140 to be in the linear viscoelastic region by performing a strain sweep. Solution pH was adjusted
 141 to 3 using 1M HCl, or to 10 using 1M NaOH.

142 2.6. Interaction with anionic surfactant

143 Aqueous solutions of G-Chitosan and GQ-Chitosan at pH~6.5 were added to aqueous SDS
 144 solutions to obtain a range of concentrations from 0.02% to 1% chitosan and 0.1mM to 350mM
 145 SDS. The phase behaviour of the mixtures were observed visually (solution, gel or precipitate),
 146 and viscosities, G' and G'' were subsequently measured at 1 s⁻¹ and 1 Hz, 10% strain if the
 147 mixture formed a solution or a gel.


148 3. Results

149 3.1. Synthesis of G-2265, G- and GQ-chitosan


150 The initial GTAC alkylations tested a method designed for the synthesis of N,N,N-trimethyl-
 151 3-amino-2-hydroxypropyl glucosamine, i.e. for the derivatisation of the monosaccharide on the
 152 high M_W polysaccharide. The protocol is similar to established methods applied to chitosan
 153 oligosaccharides (Kim et al., 2003), and polysaccharides (Nam et al., 1999) and (Lim and Hud-
 154 son, 2004)), except that sodium hydroxide was used to deprotonate the hydroxyl groups and
 155 a nitrogen atmosphere was used to prevent oxidation. This method produced products (e.g.
 156 G-2265) which were soluble in acid solution but not in water, in contrast to the neutral GTAC
 157 alkylations in the reports listed above. They were observed to precipitate when the pH was raised
 158 above 6.5, as was the case of the unmodified chitosans. By contrast, the method of Ruihua *et*
 159 *al* (Ruihua et al., 2012) yielded derivatised chitosan samples (G- and GQ-chitosan) which were
 160 soluble at all pH values tested, from pH3 - 11. This suggested that the Ruihua method had pro-
 161 duced chitosans with a degree of substitution (DG%) higher than the solubility threshold, but
 162 that the alkaline method failed in this regard. This is probably due to the fact that the chitosan
 163 substrates were soluble in the reaction medium, as opposed to the high pH alkylation method,
 164 where they were merely dispersed.

165

166 Figures 2(a) and 2(b) show the FT-IR spectra of the unmodified chitosans S#2265 and
 167 L#2272 and their GTAC derivatives. The most important peaks in the chitosan IR spectrum
 168 are listed by Kasaai (Kim, 2010). The -NH₂ peak at 1590 cm⁻¹ is clearly visible in the S#2265
 169 spectrum of Figure 2(a) (black line) but in the spectrum of GTAC-derivatised S#2265 it has

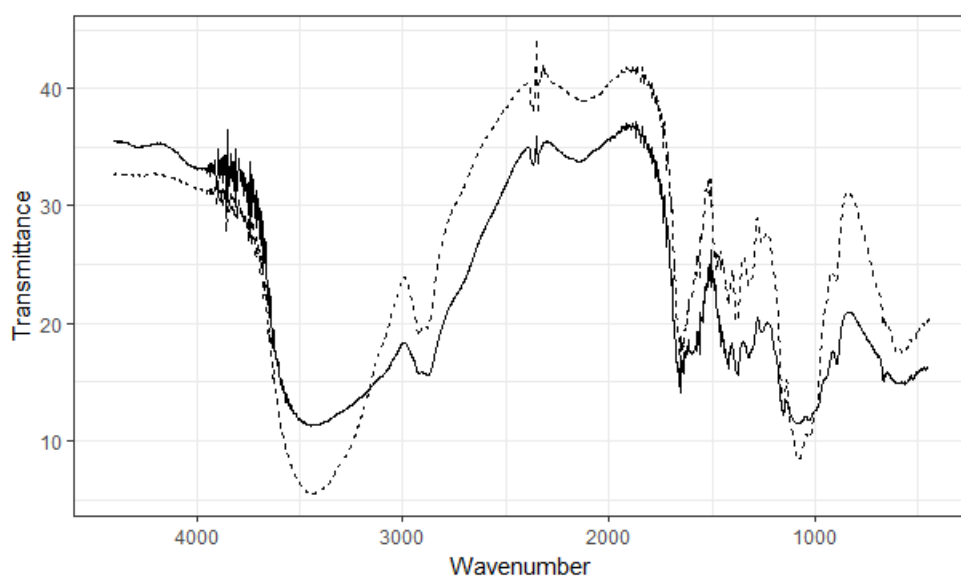


(a)

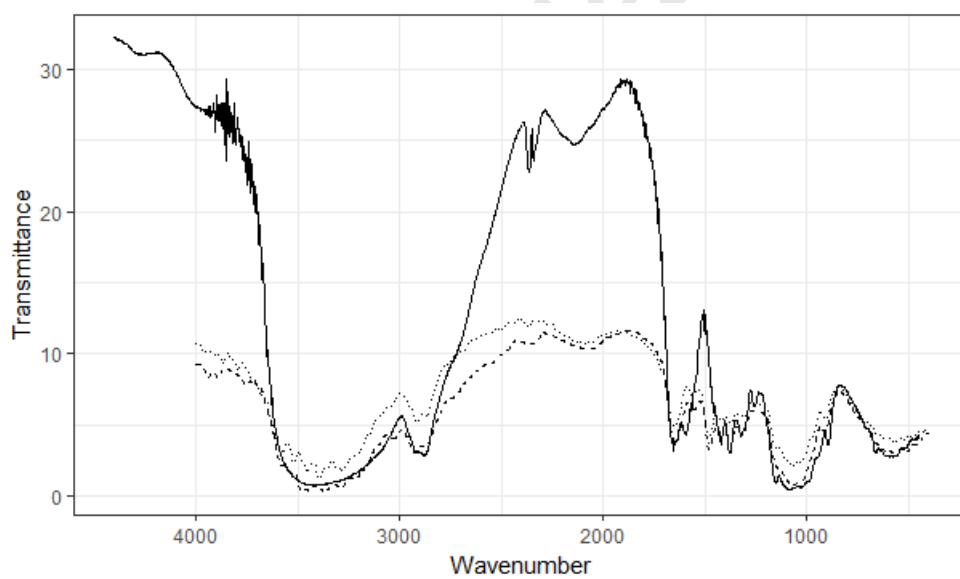


(b)

Figure 2: a) FT-IR spectra of unmodified chitosan S#2265 (solid), and GTAC-modified chitosan S#2265 (G-2265) (dashed). b) FT-IR spectra of unmodified chitosan L#2272 (solid), G-chitosan (dashed) and GQ-chitosan (dotted). The C-H stretch is at 2930 cm^{-1} and the amide I and chitosan NH_2 bands at 1650 and 1590 cm^{-1} , respectively.

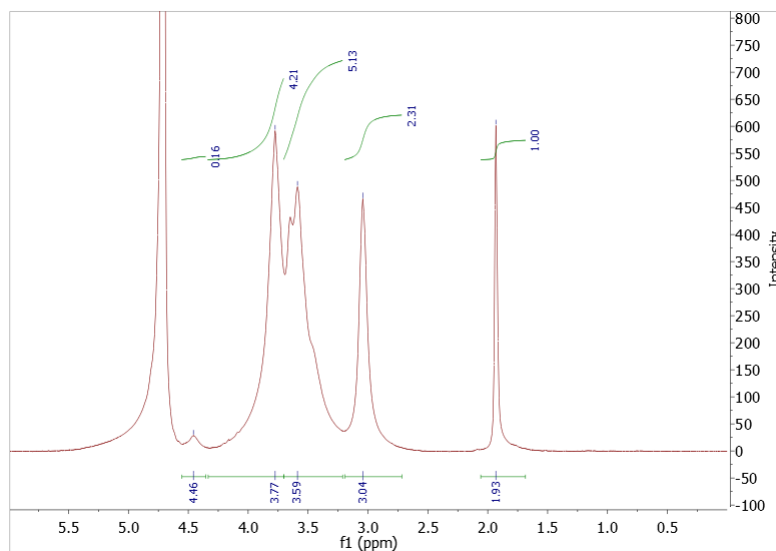


(a) Chitosan S#2265

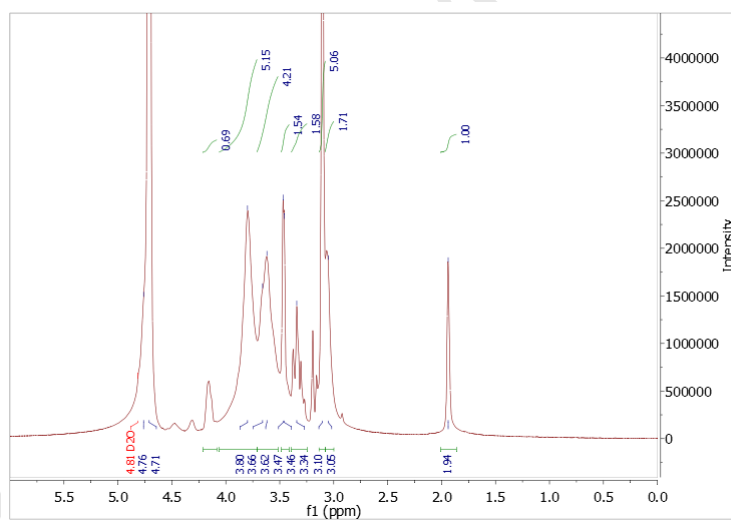


(b) G-2265


Figure 3: ¹H-NMR spectra for (a) unmodified S#2265 and (b) G-2265.

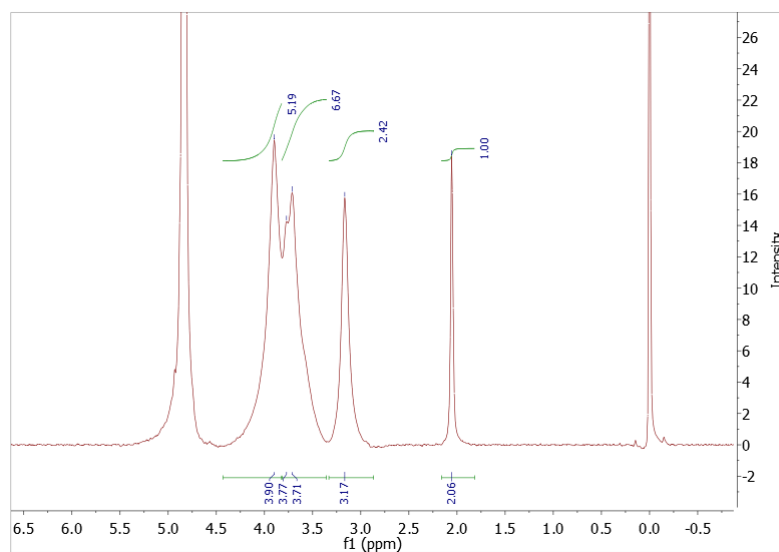

(a) Chitosan L#2272

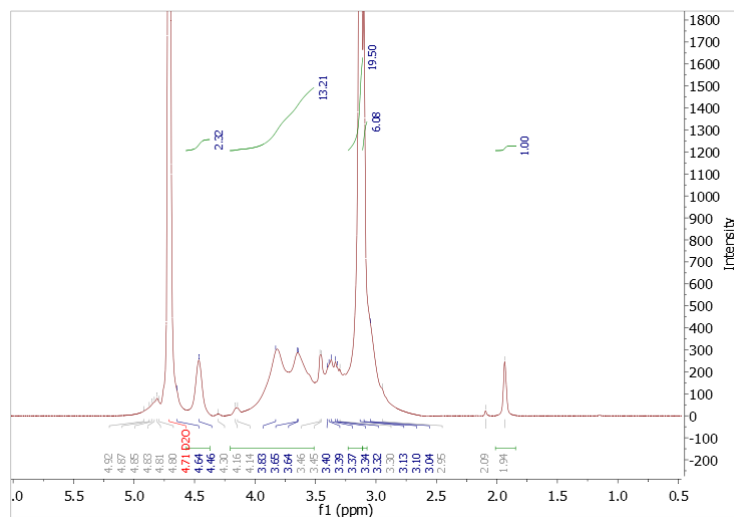

(b) G-chitosan

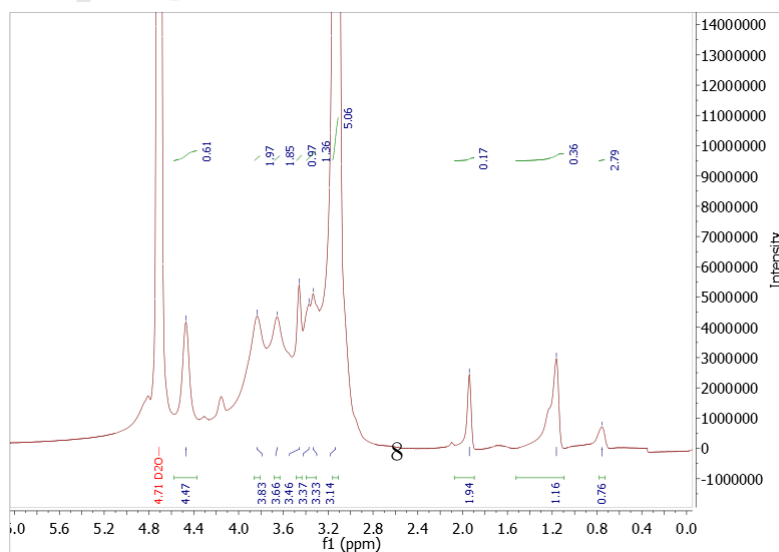

(c) GQ-chitosan

Figure 4: ^1H -NMR spectra for (a) unmodified L#2272, (b) G-chitosan, and (c) GQ-chitosan

170 diminished to a shoulder (dashed line). The initial GTAC alkylation method has reduced the
 171 amount of -NH_2 detectable, probably by alkylating the 2-amino group. When Ruihua's method
 172 was used, the 2-amino peak vanished entirely (Figure 2(b), dashed and dotted lines). Also of
 173 interest is the 2930 cm^{-1} C–H stretch, which shows a noticeable increase in the GTAC-modified
 174 chitosan in Figure 2(a) (dashed) and the G-chitosan in Figure 2(b) (dashed) due to the presence
 175 of the trimethyl-ammonium groups. The GQ-chitosan in Figure 2(b) (dotted line) has a greater
 176 peak at 2930 cm^{-1} than the G-chitosan, due to the presence of the dodecyl group. This data
 177 suggests that the reason the G- and GQ-chitosans had become soluble at neutral and alkaline pH
 178 was that they were more highly substituted with quaternary amine than the G-chitosan S#2265,
 179 because the second derivatisation method was more efficient than the first.

180
 181 NMR spectra are shown in Figures 3 and 4, NMR peaks and peak areas in Table 1 and
 182 the structure of the G-chitosan monomer in Figure 1. GTAC δH_b was chosen for the DG%
 183 calculations because it was relatively isolated from the chitosan peaks, unlike GTAC δH_d , which
 184 occurs between the H_{3-6} complex and H_2 of the glucosamine monomer.

Peaks	ppm	protons	I(G-chitosan)	I(GQ-chitosan)	I(G-2265)
Chitosan δH_{NAc}	1.94	3	1.00	1.00	1.00
Chitosan $\delta H_{2(GluNH)}$	3.1	1	6.08	5.88	1.71
Chitosan $\delta H_{2(GluNAc)}, \delta H_{3-6}$	3.83, 3.65	5	13.21	16.42	9.36
GTAC δH_b	4.46	1	2.32	3.28	0.69
GTAC δH_d	3.13	9	19.5	21.21	5.06
Quab 342 $\delta H_{methylene}$	1.17	18		2.34	

Table 1: $^1\text{H-NMR}$ peak intensity (I) used to calculate degrees of substitution for G- and GQ-chitosans.

185 Table 2 shows the degrees of substitution for the derivatised chitosans, their molecular weights
 186 (as calculated from GPC results using the Debye method), and DP values.

Chitosan	DA%	DG%	DQ%	M_W (Da)	Monomer average (Da)	DP
L#2272	16%	N.A.	N.A.	1.70×10^5	167.7	1013.7
S#2265	17%	N.A.	N.A.	1.68×10^5	168.1	999.4
G-chitosan	10.4%	72.4%	N.A.	1.69×10^5	250.1	676
GQ-chitosan	9.0%	85.1%	3.5%		273.8	
G-2265	18.1%	23.0%	N.A.	5.86×10^4	195.3	300

Table 2: DA%, DG%, DQ% and M_W for chitosans alkylated by the perchloric acid method (G- and GQ-chitosan) and the alkaline method (G-2265). Equations 5 and 6 give the average monomer size and DP.

187 The NMR data corroborates the solubility data and the FT-IR data. The perchloric acid
 188 method has produced higher yields in terms of substituted chitosan monomer : $>70\%$ compared
 189 to 23%, and the result is a derivatised chitosan polysaccharide soluble throughout the aqueous
 190 pH range. The DA% appears to have declined for the G- and GQ-chitosans. It was difficult
 191 to determine the relative abundances of H3 and H6 from the NMR spectra, but the fact that
 192 DQ% remained low and DG% did not increase above 100% in the GQ-chitosan suggests that few
 193 hydroxyl groups were alkylated at high pH. The intensity of the alkylated chitosans increased
 194 dramatically, presumably due to their increased solubility.

195

196 3.2. Molar Mass

197 The weight-average molecular weights of the S#2265 and L#2272 chitosans were determined
 198 by GPC to be 1.68×10^5 Da and 1.70×10^5 Da, respectively. The G-chitosan's M_W was found to
 199 be 1.69×10^5 Da. The average monomer size equation (5) has to take into account the presence
 200 of the substituent DG% (72.4% for G-chitosan as shown in Table 2) as well as the DA%. The
 201 DP equation (6) gives a figure of 1013.7 monomer units per chain for the unmodified chitosan
 202 L#2272, 999.4 for unmodified S#2265, and 676 for the G-chitosan: a significant decline in degree
 203 of polymerisation due to GTAC alkylation. The G.2265 chitosan had declined to 5.86×10^4 Da.
 204 Given an average monomer size of 174.2 gmol^{-1} the DP had declined to 336.4 monomer units
 205 per chain. It was not possible to determine the molar mass of GQ-chitosan since it was found to
 206 interact with the GPC column substrate.

207

208 3.3. Rheology

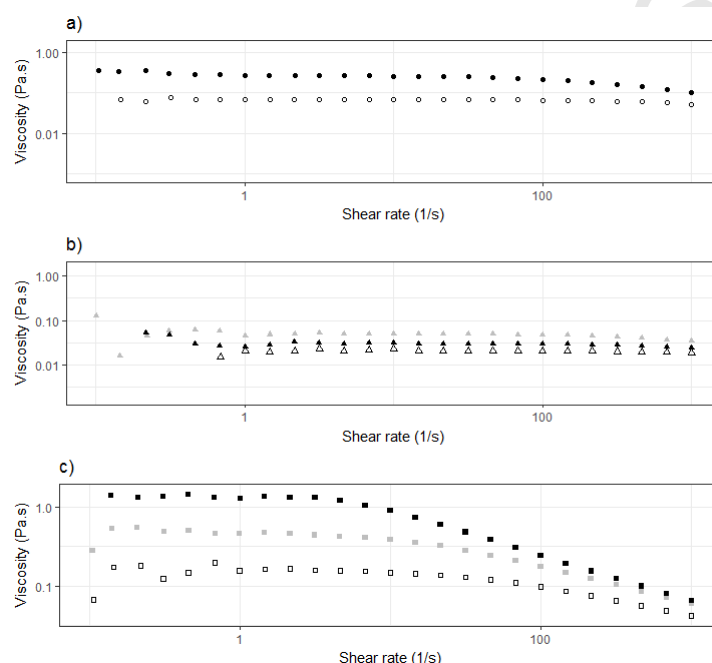


Figure 5: Viscosity v. shear rate for a) L#2272 (closed circles) and S#2265 (open circles); b) G-chitosan (triangles) at pH 3 (white), pH 6 (grey) and pH 10 (black); c) GQ-chitosan (squares) at pH 3 (white), pH 6 (grey) and pH 10 (black).

209 The steady shear viscosities for 1% solutions of chitosans L#2272 and S#2265 at pH3 (the
 210 samples are insoluble at neutral and alkaline pHs) are plotted as a function of shear rate in
 211 Figure 5 a) Similar plots for the G-chitosan and the GQ-chitosan at pH 3, 6 and 10 are shown
 212 in Figure 5 b) and c). The unmodified chitosans and G-chitosan have very low viscosities and
 213 are essentially Newtonian in behaviour. The fact that the viscosity of the G-chitosan is lower
 214 than the parent chitosan is due to the fact that it has a lower DP as shown in Table 2. In
 215 the case of the GQ-chitosan, the solutions have higher viscosities than the parent chitosans
 216 despite that fact that the DP is reduced slightly and exhibit shear thinning as the shear rate

217 is increased. This is evidence of intermolecular hydrophobic association which gives rise to a
218 weak three-dimensional intermolecular network. Interestingly the viscosity of the GQ-chitosan
219 increases with increasing pH. This may be due to a slight increase in the ionic strength caused
220 through pH adjustment which would inhibit intermolecular electrostatic repulsions and promote
221 intermolecular hydrophobic association.
222


223 3.4. Interaction with anionic surfactant

224 The phase behaviour of the highly substituted G- and GQ-chitosans is summarised in Figure
225 6. For the G-chitosan (Figure 6 a) and c)) solutions containing up to 1% (w/v) G-chitosan and
226 0.5mM SDS remained as clear solutions. At higher SDS concentrations precipitation occurred
227 and then as the concentration of SDS increased even further (to 2mM to > 100mM depending on
228 the G-chitosan concentration) a clear solution was observed. The GQ-chitosan shows a similar
229 behaviour (Figure 6 b) and d)), but with the presence of a gel phase rather than a precipitate
230 when the GQ-chitosan concentration was above 0.2%.
231


232 The mechanical spectra for selected samples are presented in Figure 7. Figure 7 a) shows
233 G'' values only as a function of frequency for 1% G-chitosan systems in the presence of 0.1 mM
234 and 350mM SDS which were seen to be clear solutions. The values are very low and typical
235 of a low viscosity solution. The G' values were close to zero and are not included in the plot.
236 Figure 7 b) shows G' (filled squares) and G'' (open squares) as a function of frequency for 1%
237 GQ-chitosan systems in the absence of SDS, which was a clear solution, and in the presence
238 of 0.1mM, 1mM, 10mM and 350mM SDS which were seen to be a clear solution, gel, gel and
239 clear solution respectively. At 0.1mM SDS (black tiny squares), the system showed weak gel
240 characteristics in that G' was slightly higher than G'' but both varied with frequency. At 1mM
241 SDS (blue small squares), the value of G' was two orders of magnitude higher than G'' and was
242 independent of frequency thus indicating that the system exhibited the properties of a gel. At
243 10mM SDS (green medium squares), G' had similar values to the system in the presence of 1mM
244 SDS but G'' was significantly higher, about one order of magnitude lower than G' . At very much
245 higher SDS concentration (350mM, red large squares) G'' is very low and strongly dependent on
246 frequency and G' is close to zero (not included in the plot) and displays typical behaviour for a
247 dilute polymer solution.
248

249 4. Discussion


250 In terms of producing a water-soluble high-molecular weight chitosan, the adaptation of Rui-
251 hua's perchloric acid method has been successful. The GTAC alkylation reaction yields are
252 nearly 16 times higher in terms of DS% for the perchloric acid reaction compared to the re-
253 action in alkaline medium. The alkaline method was initially used because of the tendency
254 of GTAC to convert from the epoxide to a relatively inactive chlorhydrin form (3-chloro, 2-
255 hydroxypropyltrimethylammonium chloride) under acid conditions (Goclik et al., 2004). How-
256 ever, the final yield was low (5.4% D.S.). There are several possible reasons. The GTAC epoxide
257 can also react with hydroxyl ions to form the inactive 2,3-dihydroxy product in a side reaction,
258 resulting in potential loss of yield. Also, the chitosan was not dissolved in the reaction medium,
259 but remained in a semi-crystalline form, so that many of the reactive amino groups must have
260 been inaccessible to the GTAC reagent. In the neutral GTAC alkylations reported in the liter-
261 ature (Kim et al., 2003), (Nam et al., 1999), (Lim and Hudson, 2004), the solid chitosan was
262 suspended in a medium less than 2 pH points from the amino pKa (c. 5.6). A sufficient minority

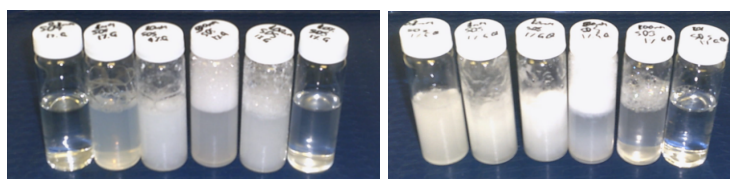

(a) 1% G-Chitosan with increasing SDS (b) 1% GQ-Chitosan with increasing SDS

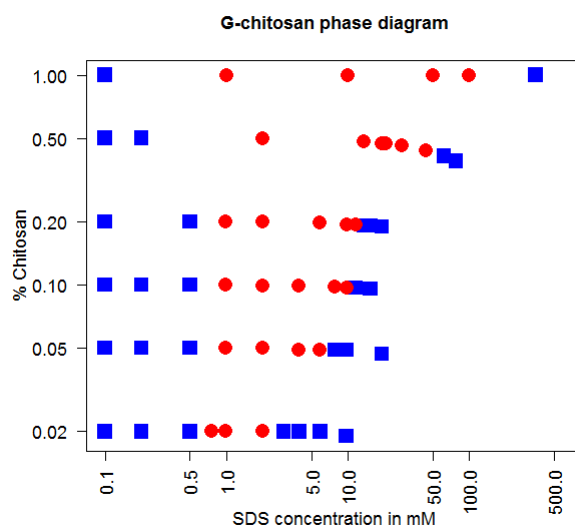

(c) G-chitosan plotted against SDS

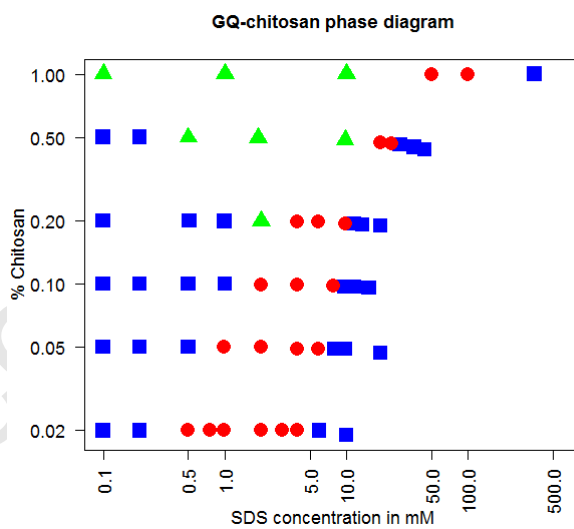

(d) GQ-chitosan plotted against SDS

Figure 6: a) - b) Effect of SDS concentration on solubility of G- and GQ-chitosans (1% in water). From left to right: 0.1, 1, 10, 50, 100 and 350mM SDS. c) - d) Plot of phase behaviour of G- and GQ-chitosans in the presence of SDS surfactant. Blue squares = solution, red circles = precipitate, green triangles = gel.

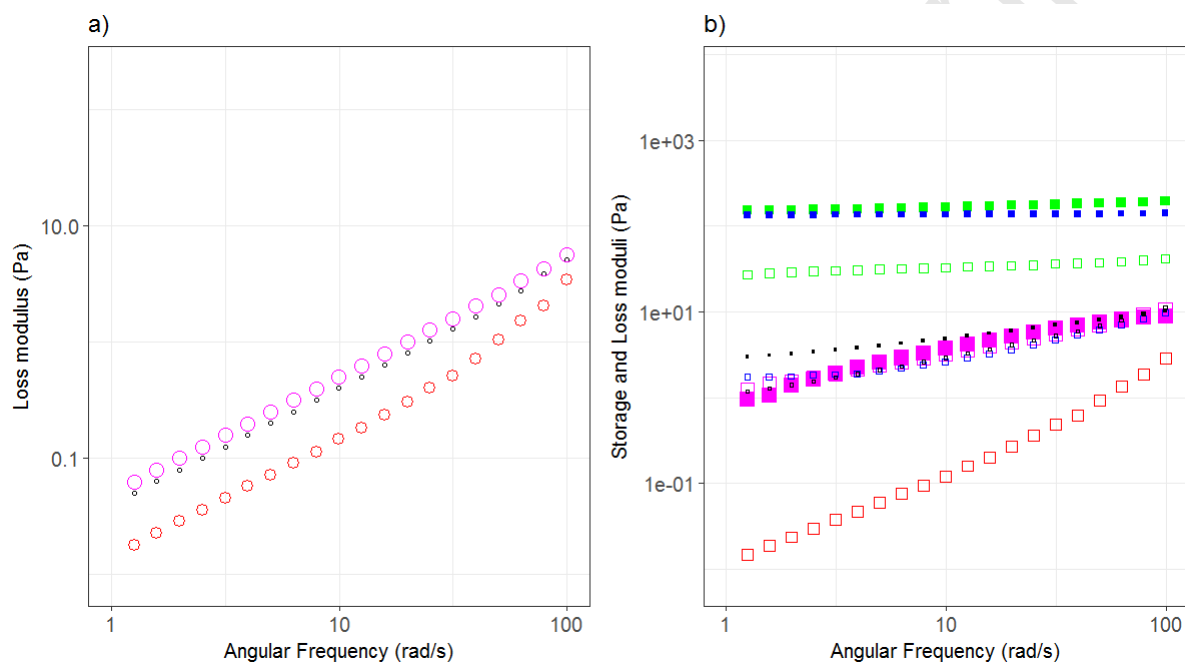


Figure 7: Frequency spectra with G' (filled) and G'' (open) for G-chitosan (circles) and GQ-chitosan (squares) in the presence of 0mM (magenta, largest), 0.1mM (black, smallest), 1mM (blue, small), 10mM (green, large) and 350mM SDS (red, larger). a) 1% G-chitosan, SDS 0mM, 0.1mM and 350mM. b) 1% GQ-chitosan, SDS 0mM, 0.1mM, 1mM, 10mM and 350mM.

263 of glucosamine residues must have been protonated, enough to solvate the surrounding chains
264 and open them up to the GTAC alkylating agent. As the reaction proceeded, the chitosan would
265 become gradually completely dissolved. At pH values of 11 and above, there would be no proto-
266 nation and therefore little solvation.

267
268 The problem was solved by using aqueous perchloric acid as the reaction medium. The chi-
269 tosan dissolves under conditions of low pH, and the perchloric acid has a low nucleophilicity, so
270 that it does not open the epoxide ring. In the G-chitosan synthesis, both the chitosan and the
271 GTAC were able to react under optimum conditions.

272
273 The Quab 342 alkylation was carried out on a chitosan already alkylated with GTAC, un-
274 der alkaline conditions, because the reagent was supplied in the unreactive chlorhydrin form.
275 The unsatisfactory results with the alkaline heterogeneous GTAC alkylation suggested that the
276 chitosan had to be rendered alkali-soluble first. Accordingly, the DQ% of GQ-chitosan is low, be-
277 cause most of the active sites were already taken by hydroxypropyltrimethylammonium groups.
278 However, the presence of a small 3.5% Quab 342-derived hydrophobic dodecyl chains have made
279 a considerable difference to the physicochemical properties of the GQ-chitosan. Its viscosity is
280 considerably increased compared to the G-chitosan, especially at high pH as the chitosan 2-amino
281 groups are deprotonated. The increase in viscosity is attributed to intermolecular hydrophobic
282 interactions of the C₁₂ alkyl chains present along the GQ chitosan backbone as has been reported
283 for other hydrophobically modified polymers (Tanaka et al., 1992). Its phase behaviour with SDS
284 is also altered and it has acquired surfactant properties; it is observed to foam during mixing,
285 unlike its parent compounds, the G-chitosan and the unmodified chitosan L#2272.

286
287 There has been considerable interest over many years in the interaction of polymers and sur-
288 factants including polyelectrolytes and oppositely charged surfactants (Williams, 2003), (Langevin,
289 2009). It is generally observed that association occurs at a critical surfactant concentration (crit-
290 ical aggregation concentration) which is much lower than the critical micelle concentration and
291 is due to cooperative binding. A number of studies have been reported on the interaction of
292 unmodified chitosan with SDS under acid conditions (Petrovic et al., 2016), (Onesippe and
293 Lagerge, 2008), (Chiappisi and Gradzielski, 2015), other anionic surfactants (Desbrieres et al.,
294 2010), (Petrovic et al., 2017) (Chiappisi and Gradzielski, 2015), or with polyanions such as car-
295 boxymethylcellulose (Rosca et al., 2005). It is expected that binding occurs through electrostatic
296 interaction between the surfactant sulphate groups and the protonated amine group on the chi-
297 tosan chain.

298
299 Chiappisi and Gradzielski (2015) have argued that at very low SDS concentrations some non-
300 cooperative binding occurs but the complexes are soluble and the solution remains clear. At
301 intermediate SDS concentrations, polymer / surfactant aggregation occurs at a critical concen-
302 tration, the critical aggregation concentration (CAC) as a result of cooperative binding resulting
303 in micellar-like aggregates forming along the polymer chain and that turbidity can be observed.
304 A further increase in SDS concentration results in the saturation of the polymer chain. One-
305 sippe and Lagerge (2008) have reported that, for a 0.05% chitosan solution, the CAC occurred
306 at 1.8mM SDS which is considerably lower than the critical micelle concentration (CMC) which
307 is 8mM SDS. Senra et al. (2018) studied the interaction of cationically modified chitosan with
308 sodium decyl sulphonate and showed through conductometric measurements that for a 1mM
309 chitosan solution interaction occurred at a concentration of 1mM surfactant which is much lower
310 than its CMC (40mM). For the cationically modified chitosans in our study, at a polymer concen-
311 tration of 0.02%, turbidity was observed at concentrations of approximately 0.7mM and 0.5mM

312 SDS for G-chitosan and GQ-chitosans respectively, confirming that significant interaction had
313 occurred at these concentrations. The concentrations correspond to a molar ratio of SDS to
314 G- and GQ-chitosan monomer units of 0.88 and 0.54 at which the electrostatic charge on the
315 complex is expected to be close to zero. Chiappisi and Gradzielski also determined the elec-
316 trophoretic mobility of chitosan/SDS complexes and reported that for a 0.01% chitosan solution
317 charge neutralisation occurred at an SDS concentration of 0.45mM and at higher SDS concen-
318 trations the complexes became negatively charged.

319
320 In addition to the interesting phase behaviour, the GQ-chitosan has novel rheological prop-
321 erties. It is noted in Figure 6 that a number of the samples have gel-like characteristics and
322 this is confirmed through the rheological data shown in Figure 7. It is believed that the gels
323 are formed through intermolecular hydrophobic interactions between the C₁₂ chains on the GQ-
324 chitosan. This behaviour is typical of ‘associative thickeners’ and is supported by the fact that
325 G-chitosan, which does not contain C₁₂ chains, does not form gels. G’ values were found to
326 increase significantly in the presence of SDS up to concentrations close to its CMC (8mM). It is
327 evident that the SDS promotes intermolecular hydrophobic association of the GQ-chitosan poly-
328 mer chains by increasing the number and/or life-time of the crosslinks as has been reported for
329 other hydrophobically-modified polymers (Tanaka et al., 1992), (Jiménez-Regalado et al., 2000).
330 At higher SDS concentrations, above the SDS CMC each C₁₂ chain will be encapsulated within
331 an SDS micelle and hence intermolecular associations will be inhibited and the systems will have
332 the characteristics of a dilute solution.

334 5. Conclusions

335 This study has demonstrated that cationic chitosan derivatives with a high DS can be syn-
336 thesised using GTAC in dilute perchloric acid and that the derivatives are soluble over a broad
337 pH range. Furthermore, it has been shown that the introduction of C₁₂ alkyl groups along the
338 chitosan chain leads to the formation of viscoelastic gels in the presence of SDS molecules. These
339 materials have potential application in a range of commercial formulations, including cosmetics,
340 pharmaceuticals and personal care.

342 6. Acknowledgements

343 The authors would like to thank Innovate UK and Innovation Norway for funding this work
344 (Technology Strategy Board: Project Number 101440), the collaborative partners Unilever Re-
345 search, Croda Europe Ltd, Almac Sciences Ltd and Seagarden ASA Norway. They would also
346 like to thank Craig Fairgrieve of Unilever Research for carrying out the NMR measurements.

348 7. References

- 349 Bellich, B., D’Agostino, I., Semeraro, S., Gamini, A., 2016. “the good, the bad and the ugly” of
350 chitosans. *Marine Drugs* 14 (5), 99–130.
- 351 Chiappisi, L., Gradzielski, M., 2015. Co-assembly in chitosan-surfactant mixtures: thermody-
352 namics, structures, interfacial properties and applications. *Advances in Colloid and Interface*
353 *Science* 220, 92–107.

- 354 Desbrieres, J., Bousquet, C., Babak, V., 2010. Surfactant–chitosan interactions and application
355 to emulsion stabilization. *Cellulose Chemistry and Technology* 44 (9), 395–406.
- 356 Dutta, P., Dutta, J., Tripathi, V., 2004. Chitin and chitosan: Chemistry, properties and appli-
357 cations. *J. Sci. & Ind. Res.* 63, 20–31.
- 358 Goclik, V., Stach, S., Mischnick, P., 2004. Determination of (2,3-
359 epoxypropyl)trimethylammonium chloride, (3-chloro-2-hydroxypropyl)trimethylammonium
360 chloride, and (2,3-dihydroxypropyl)trimethylammonium chloride by capillary electrophoresis.
361 *J. Chromatography A* 1038, 283–289.
- 362 Goddard, E., Ananthapadmanabhan, K., 1998. Applications of polymer- surfactant systems.
363 Dekker M. Inc New York, pp. 21–64.
- 364 Guo, Z., Xing, R., Liu, S., Zhong, Z., Ji, X., Wang, L., Li, P., 2007. Antifungal properties
365 of schiff bases of chitosan, n-substituted chitosan and quaternized chitosan. *Carbohydrate*
366 *Research* 342, 1329–1332.
- 367 Hayes, M., Carney, B., Slater, J., Bruck, W., 2008a. Mining marine shellfish wastes for bioactive
368 molecules: Chitin and chitosan –part a: extraction methods. *Biotechnol. J.* 3, 871–877.
- 369 Hayes, M., Carney, B., Slater, J., Bruck, W., 2008b. Mining marine shellfish wastes for bioactive
370 molecules: Chitin and chitosan –part b: Applications. *Biotechnol. J.* 3, 878–889.
- 371 Jiménez-Regalado, E., Selb, J., Candau, F., 2000. Effect of surfactant on the viscoelastic behavior
372 of semidilute solutions of multisticker associating polyacrylamides. *Langmuir* 16 (23), 8611–
373 8621.
- 374 Kim, J., Lee, J., Lee, T., Park, W., 2003. Synthesis of chitooligosaccharide derivative with
375 quaternary ammonium group and its antimicrobial activity against *Streptococcus mutans*. *Int.*
376 *J. Biol. Macromolecules* 32, 23–27.
- 377 Kim, S.-K., 2010. Chitin, Chitosan, Oligosaccharides and their Derivatives: Biological Activities
378 and Applications. CRC Press.
- 379 Kumar, M. N. V. R., Muzzarelli, R. A. A., Muzzarelli, C., Sashiwa, H., Domb, A. J., 2004.
380 Chitosan chemistry and pharmaceutical perspectives. *Chem. Rev.* 104, 6017–6084.
- 381 Langevin, D., 2009. Complexation of oppositely charged polyelectrolytes and surfactants in aque-
382 ous solutions. a review. *Advances in Colloid and Interface Science* 147-8, 170–177.
- 383 Lim, S.-H., Hudson, S., 2004. Synthesis and antimicrobial activity of a water-soluble chitosan
384 derivative with a fibre-reactive group. *Carbohydrate Research* 339, 313–319.
- 385 Lodhi, G., Kim, Y.-S., Hwang, J.-W., Kim, S.-K., Jeon, Y.-J., Je, J.-Y., Ahn, C.-B., Sang-
386 HoMoon, Jeon, B.-T., Park, P.-J., 2014. Chitooligosaccharide and its derivatives: Preparation
387 and biological applications. *BioMed Research International* 2014, 654913–654926.
- 388 Mao, X., Guo, N., Sun, J., Xue, C., 2017. Comprehensive utilization of shrimp waste based on
389 biotechnological methods: a review. *Journal of Cleaner Production* 143, 814–823.
- 390 Mohammed, M. H., Williams, P. A., Tverezovskaya, O., 2013. Extraction of chitin from prawn
391 shells and conversion to low molecular mass chitosan. *Food Hydrocolloids* 31, 166–171.

- 392 Mourya, V. K., Inamdar, N. N., 2008. Chitosan – modifications and applications: Opportunities
393 galore. *Reactive & Functional Polymers* 68, 1013–1051.
- 394 Nam, C.-W., Kim, Y.-H., Ko, S.-W., 1999. Modification of polyacrylonitrile (pan) fiber by blend-
395 ing with *N*-(2-hydroxy)propyl-3-trimethylammonium chitosan chloride. *Journal of Applied*
396 *Polymer Science* 74, 2258–2265.
- 397 Onesippe, C., Lagerge, S., 2008. Study of the complex formation between sodium dodecyl sul-
398 phate and chitosan. *Colloids and Surfaces A: Physiochem. Eng. Aspects* 317, 100–108.
- 399 Petrovic, L., Milinkovic, J., Fraj, J., Bucko, S., Katona, J., Spasojevic, L., 2017. Study of
400 interaction between chitosan and sodium lauryl ether sulphate. *Colloid Polym. Sci.* 295, 2279–
401 2285.
- 402 Petrovic, L. B., Milinkovic, J. R., Fraj, J. L., Bucko, S. D., Katona, J. M., 2016. An investigation
403 of chitosan and sodium dodecyl sulphate interactions in acetic media. *J. Serb. Chem. Soc.*
404 81 (5), 575–587.
- 405 Pillai, C., Paul, W., Sharma, C. P., 2009. Chitin and chitosan polymers: Chemistry, solubility
406 and fiber formation. *Progress in Polymer Science* 34, 641–678.
- 407 Rosca, C., Popa, M. I., Lisa, G., Chitanu, G. C., 2005. Interaction of chitosan with natural or syn-
408 thetic anionic polyelectrolytes. 1. the chitosan–carboxymethylcellulose complex. *Carbohydrate*
409 *Polymers* 62, 35–41.
- 410 Ruihua, H., Bingchao, Y., Zheng, D., Wang, B., 2012. Preparation and characterisation of a
411 quaternised chitosan. *J. Mater. Sci.* 47, 845–851.
- 412 Sahariah, P., Másson, M., 2017. Antimicrobial chitosan and chitosan derivatives: A review of
413 the structure–activity relationship. *Biomacromolecules* 18 (11), 3846–3868.
- 414 Sajomsang, W., Gonil, P., 2010. Preparation and characterization of α -chitin from cicada sloughs.
415 *Mater. Sci. Eng. C* 30 (3), 357–363.
- 416 Senra, T., Campana-Filho, S. P., Desbrieres, J., 2018. Surfactant-polysaccharide complexes based
417 on quaternized chitosan. characterization and application to emulsion stability. *European Poly-*
418 *mer Journal* 104, 128–135.
- 419 Snyman, D., Hamman, J., Kotze, J., Rollings, J., Kotzé, A., 2002. The relationship between the
420 absolute molecular weight and the degree of quaternisation of *n*-trimethyl chitosan chloride.
421 *Carbohydrate Polymers* 50, 145–150.
- 422 Tanaka, R., Meadows, J., Williams, P. A., Phillips, G. O., 1992. The interaction of hydrophobi-
423 cally modified hydroxyethyl cellulose with various added surfactants. *Macromolecules* 25 (4),
424 1304–1310.
- 425 Tungtong, S., Okonogi, S., Chowwanapoonpohn, S., Phutdhawong, W., Yotsawimonwat, S.,
426 2012. Solubility, viscosity and rheological properties of water-soluble chitosan derivatives.
427 *Maejo Int. J. Sci. Technol.* 6 (02), 315–322.
- 428 Williams, P. A., 2003. Surfactant-waterborne polymer interactions in coating applications. Black-
429 well Publishing Ltd Oxford, UK, pp. 180–210.
- 430 Xia, W., Liu, P., Zhang, J., Chen, J., 2011. Biological activities of chitosan and chitoooligosac-
431 charides. *Food Hydrocolloids* 25, 170–179.

⁴³² Younes, I., Rinaudo, M., 2015. Chitin and chitosan preparation from marine sources. structure,
⁴³³ properties and applications. Mar. Drugs 13, 1133–1174.

Accepted Manuscript

Highlights

- Chitosan was alkylated with GTAC to form water-soluble G-chitosan.
- The G-chitosan was alkylated with Quab 342 to form the novel GQ-chitosan derivative.
- GQ-chitosan has increased viscosity compared to G-chitosan and unmodified chitosan.
- The derivatives form complexes with the anionic surfactant SDS.
- The GQ-chitosan-SDS complex has a gel phase, due to its long alkyl chains.

Accepted Manuscript