

# Spectral Irradiance Effects on the Outdoor Performance of Photovoltaic Modules

R. Eke<sup>1,\*</sup>, T.R. Betts<sup>2</sup>, R. Gottschalg<sup>2</sup>

<sup>1</sup>Mugla Sıtkı Koçman University, Department of Physics, Faculty of Science and Clean Energy R&D Centre, 48100, Muğla, Turkey

<sup>2</sup>Loughborough University, Centre for Renewable Energy Systems Technology, School of Electronic, Electrical and Systems Engineering, Loughborough, Leicestershire LE11 3TU, UK

## Abstract

The outdoor performance of photovoltaic modules is influenced by spectrum. Even if the irradiance level and the operating temperature is the same, performance difference of photovoltaic modules between the seasons can be increase up to 15% depending on the photovoltaic module type. In this paper, seasonal spectral irradiance effects on the outdoor photovoltaic module performance and previous studies has been summarised thoroughly. The spectrum indicators which are used for spectra characteristics, Useful Fraction and Average Photon Energy are described in detail. This study also indicates spectrum effects on PV performance and outlines the present studies investigating this effect.

**Keywords:** spectral effect, photovoltaic module, outdoor performance, useful fraction, average photon energy

## Contents

Abstract.....	1
1 Introduction.....	3
1.1 Solar Spectrum and Additional Spectral Irradiance Descriptors .....	3
1.1.1 Spectral Mismatch Factor (MMF) .....	4
1.1.2 Useful Fraction (UF) .....	5
1.1.3 Average Photon Energy (APE).....	6
1.2 Natural solar spectral variation .....	6
2 PV performance and effect of spectrum.....	7
2.1 Spectral response.....	9
3 Conclusions.....	10
Acknowledgements .....	10
References .....	10

\*Corresponding author. Tel +902522111601, Fax: +902522111472, E-mail address: erustu@gmail.com

## Nomenclature

$G(\lambda)$	Spectral irradiance	$R_s$	Series resistance ( $\Omega$ )
$b(\lambda)$	Flux density per unit wavelength	$R_{sh}$	Shunt resistance ( $\Omega$ )
$f(\lambda)$	Incident photon flux	$a$	Modified ideality factor
$SR(\lambda)$	Spectral response	$N_s$	Number of series-connected cell/module
$\epsilon_\lambda$	Energy of a photon (J)	$n_I$	Diode ideality factor
$E_g$	Band gap (eV)	$k_B$	Boltzmann constant (J/K)
$\phi(\lambda)$	Spectral photon flux density	$q_e$	Electronic charge (C)
$\lambda_a$	Lower absorption wavelength limit	$P_{in}$	Power of incident light (W)
$\lambda_b$	Higher absorption wavelength limit	PV	Photovoltaic
h	Planck constant (Js)	STC	Standard Test Conditions
c	Velocity of light in the vacuum (m/s)	G	Total (broadband) irradiance ( $W/m^2$ )
SR	Spectral Response	ASTM	American Society for Testing and Materials
I	Current (A)	IEC	International Electrotechnical Commission
V	Voltage (V)	AoI	Angle of Incidence
$K_T$	Clearness index (daily)	AM	Air mass
$k_T$	Clearness index (hourly)	$\alpha$	Solar altitude angle ( $^\circ$ )
H	Measured daily Total Solar Radiation	$\gamma_s$	Solar azimuthal angle ( $^\circ$ )
$H_0$	Extra-terrestrial daily Total Solar Radiation	$E_{AM1.5}(\lambda)$	Spectral irradiance distribution of the AM1.5
I	Measured hourly Total Solar Radiation	$SR_{DUT}(\lambda)$	SR of the device under test
$I_0$	Extra-terrestrial hourly Total Solar Radiation	$SR_{ref}(\lambda)$	SR of the reference cell
$I_{ph}$	Photocurrent (A)	AM0	Air Mass zero, Spectral representation outside the atmosphere
$I_L$	Light-generated current (A)	AM1.5	Air Mass at solar zenith angle $48.2^\circ$
$I_{sc}$	Short circuit current (A)	UF	Useful Fraction
$V_{oc}$	Open circuit voltage (V)	APE	Average Photon Energy (eV)
$P_{mpp}$	Power at mpp (Wp)	a-Si	Amorphous Silicon
$I_{mpp}$	Current at mpp (A)	CIS	Copper Indium (di)Selenide
$V_{mpp}$	Voltage at mpp (V)	CdTe	Cadmium Telluride
A	Module area ( $m^2$ )	SPCTRL2	Spectral model developed by NREL
$T_c$	Operating cell temperature (K)	FF	Fill Factor

## 1 Introduction

PV modules are rated by their power output under standard test conditions (STC) which are a set of reference PV device measurement conditions consisting of irradiance of 1000 W/m<sup>2</sup>, AM1.5G spectrum, and a module temperature of 25°C. However, STC are not representatives of actual outdoor conditions in most regions of the world. Therefore, it is suspected that the score of a PV module by power rating method under STC is different from the actual performance in outdoor conditions [1-5]. The performance of photovoltaic (PV) modules installed outdoor is greatly influenced by various ambient environmental factors such as incident irradiance, the module temperature and the spectral irradiance distribution.

In this study, solar spectrum, the spectral effects on PV performance is discussed. There are a lot papers presented in different organizations outlines the effect on the installed PV systems. More than 200 studies are reviewed and some of them are published in journals or conference proceedings, the rest are unpublished or contains only local data.

### 1.1 Solar Spectrum and Additional Spectral Irradiance Descriptors

Emission of radiation from the sun contributes to the solar spectrum as observed from Earth. Just above the Earth's atmosphere, the radiation intensity, or Solar Constant, is about 1.353 kW/m<sup>2</sup> [6,7] and the spectral distribution is referred to as an air mass zero (AM0) radiation spectrum. The Air Mass is a measure of how absorption in the atmosphere affects the spectral content and intensity of the solar radiation reaching the Earth's surface. The Air Mass number is given by

$$\text{Air Mass, } AM = \frac{1}{\cos\theta} \quad (1)$$

where  $\theta$  is the angle of incidence ( $\theta = 0$  when the sun is directly overhead). Moreover, the outdoor solar spectrum distribution changes during a day because of the aerosol and water vapour. Hence, it is rare to fit the standard solar spectrum (Fig.1) AM1.5G defined in ASTM GE173-03 and standard IEC 60904-3 [8,9]. Measured spectral irradiance data does not lend itself well to use in simple analysis or modelling approaches as it consists of an ensemble of measurements. Ideally, a spectral distribution would be summarised as a single parameter, which could then be used in much the same way as broadband irradiance and device temperature to isolate and quantify the different environmental effects acting on the PV device. The colour temperature associated with a blackbody radiator is an option that can reasonably represent the solar spectrum outside the Earth's atmosphere, but is unsuitable for terrestrial application because the various gas absorption bands and wavelength dependent scattering prove too distorting [10]. A few terrestrial spectral descriptors can be found in the existing literature, although not as many as might appear since often the same measure is used under different names by various groups [10].

1 The sun's location in the sky relative to a location on the surface of the earth can be specified by two  
2 angles. They are: (1) the solar altitude angle ( $\alpha$ ) and the solar azimuthal angle ( $\beta$ ). The angle  $\alpha$  is the  
3 angle between the sun's position and the horizontal plane of the earth's surface, while the angle  $\beta$   
4 specifies the angle between a vertical plane containing the solar disk and a line running due north [11].  
5 Therefore, a new parameter, angle of incidence ( $AoI$ ) is defined to explain the position of solar rays on  
6 the plane [10].  $AoI$  is a measure of deviation of something from "straight on". A surface directly facing  
7 the sun has an  $AoI$  of zero, and a surface parallel to the sun (such as a sunrise striking a horizontal  
8 plane) has an  $AoI$  of  $90^\circ$ . Sunlight with an incident angle of  $90^\circ$  tends to be absorbed, while lower  
9 angles tend to be reflected.

10  
11  
12  
13  
14  
15 Another important parameter effecting the solar radiation on a plane is the clearness index ( $K_T$ ), which  
16 is defined as the value of a particular day's radiation to the extra-terrestrial radiation for that day, or an  
17 hourly clearness index ( $k_T$ ) can be defined in equation forms:

$$K_T = \frac{H}{H_0} \text{ (daily)} \quad \text{and} \quad k_T = \frac{I}{I_0} \text{ (hourly)} \quad (2)$$

18  
19  
20  
21  
22  
23  
24  
25 Where  $H$  and  $I$  are measured values of total solar radiation and  $H_0$  and  $I_0$  are the extra-terrestrial  
26 values which can be calculated using several methods [6,11]. This value depends on atmospheric  
27 conditions; usually the value lies between zero and unity. Under clear weather conditions clearness  
28 index is high and if the atmosphere is turbid or cloudy it is generally low (e.g.  $K_T \leq 0.4$  heavily  
29 overcast)

30  
31  
32  
33  
34 The outdoor performance and the energy yield of PV modules depend on a large number of factors.  
35 The most important factor is the amount of irradiation that arrives on the plane of the PV modules,  
36 which in turn depends on the local environmental conditions such as rain, ambient temperature, and  
37 wind. To enable more wide spread deployment of PV modules, it is important to analyse the influences  
38 of environmental factors on outdoor performance of PV modules [12-21].

39  
40  
41  
42  
43 Decreases refer absorption by chemical elements in the atmosphere. The intensity of light in the  
44 frequency of incident photons is absorbed. There are some computational models developed by  
45 several laboratories which compute clear sky spectral direct beam, hemispherical diffuse, and  
46 hemispherical total irradiances on a plane (tilted or horizontal) at a defined location in time [22-24].

### 47 48 49 50 51 52 1.1.1 Spectral Mismatch Factor (MMF)

53  
54 One of the discrepancies between indoor and outdoor measurements is Spectral Mismatch errors.  
55 Spectral mismatch errors may influence the estimation of the short-circuit current and arise when  
56 using a reference cell with a spectral response (SR) different from that of the device under test. The  
57 amount of the spectral mismatch depends strongly on the difference of the spectral irradiance  
58 distribution of the solar simulator with respect to the reference spectrum AM 1.5G. The procedure for  
59  
60  
61  
62  
63  
64  
65

correcting the error introduced in the testing of a PV device, caused by the mismatch between the test spectrum and the reference spectrum and by the mismatch between the SRs of the reference cell and of the device under test. According to IEC 60904-7 [25], the mismatch MMF is defined as:

$$MMF = \frac{\int E_{AM1.5}(\lambda)SR_{ref}(\lambda)d\lambda \int E_{\lambda}(\lambda)SR_{DUT}(\lambda)d\lambda}{\int E_{\lambda}(\lambda)SR_{ref}(\lambda)d\lambda \int E_{AM1.5}(\lambda)SR_{DUT}(\lambda)d\lambda} \quad (3)$$

where  $E_{AM1.5}(\lambda)$  is the spectral irradiance distribution of the AM1.5 spectrum according to IEC 60904-3,  $E_{\lambda}(\lambda)$  is the spectral irradiance distribution of the incoming light at the time of measurement,  $SR_{ref}(\lambda)$  is the SR of the reference cell, and  $SR_{DUT}(\lambda)$  is the SR of the device under test [4].

### 1.1.2 Useful Fraction (UF)

To illustrate the effect of the solar spectral variations, it is useful to define a parameter that can represent a spectral shift towards higher energies (which will result in a larger proportion of blue or ultraviolet light) than a spectral shift towards lower energies. Different authors use different indices to evaluate this behaviour [10,26]. The most used parameters are the Useful Fraction (UF) that is dependent from the PV technology under investigation and the Average Photon Energy (APE) [27-31].

If the spectral irradiance encountered by a given device/cell (electrically series or parallel connected cells form PV modules) is  $G(\lambda)$ ; the total irradiance,  $G$ ; is defined as [28],

$$G \equiv \int_0^{\infty} G(\lambda) d\lambda = \int_0^{\infty} \epsilon_{\lambda} b(\lambda) d\lambda \quad (4)$$

where  $b(\lambda)$  is the flux density (number per unit area and unit time) per unit wavelength of photons of energy  $\epsilon_{\lambda}$  and wavelength  $\lambda$ . UF is the ratio of the solar irradiance within the usable wavelength range of a PV device to the total solar irradiance and defined as

$$UF \equiv \frac{1}{G} \int_0^{\lambda(E_g)} G(\lambda) d\lambda \quad (5)$$

Here,  $E_g$  is the band-gap of the solar device/cell which equates to a long wavelength cut-off of wavelength  $\lambda$ . For example, for amorphous silicon cells the cut-off wavelength is  $\sim 780 \text{ nm}$  and for the standard AM1.5 spectrum,  $UF \cong 0.604$ . A value of  $UF > 0.604$  therefore indicates a spectral shift towards the blue, relative to this standard. This will tend to occur when the incident light is mainly diffuse (and thus has a low total irradiance  $G$ ) or when the light is incident with a very low air mass (and thus has a high total irradiance  $G$ ). Conversely, a value of  $UF < 0.604$  indicates a spectral shift towards the red [28].

### 1.1.3 Average Photon Energy (APE)

The other unique value to characterize the spectrum shape is APE. The APE is an instantaneous value defined as the ratio of the total irradiance of the spectrum over the photon flux density. Consequently, the definition of APE is usually referred to as a finite integration interval APE, expressed in the unit of electronvolt (eV),

$$APE = \frac{\int_{\lambda_a}^{\lambda_b} G(\lambda) d\lambda}{q_e \int_{\lambda_a}^{\lambda_b} \Phi(\lambda) d\lambda} \quad (6)$$

where  $q_e$  is the electron charge,  $\Phi(\lambda)$  is the spectral photon flux density,  $\lambda_a$  and  $\lambda_b$  are the lower and the higher absorption wavelength limits of the device. It should be noted that the calculated APE value depends on the integration limits in Eq.(6). This wavelength interval effect is shown in Table 1 for the AM1.5G standard spectrum.

The spectral photon flux density at a specific value of wavelength  $\lambda$  can be determined by dividing the spectral irradiance evaluated at  $\lambda$  between the energy of a photon ( $\varepsilon_\lambda$ ) with that wavelength (in joules):

$$\Phi(\lambda) = \frac{G(\lambda)}{\varepsilon_\lambda} = \frac{G(\lambda)}{\frac{hc}{\lambda}} \quad (7)$$

where  $h$  is the Planck constant  $h = 6.62606877 \times 10^{-34} \text{ Js}$  and  $c$  is the velocity of light in the vacuum  $c = 2.99792458 \times 10^8 \text{ m/s}$ . With the use of these values, the final result of APE will be expressed in J, but it is usually expressed in *electron Volt, eV* taking into account that  $1 \text{ eV} = 1.602176463 \times 10^{-19} \text{ J}$ . APE value can be expressed in eV as usual.

There are several studies reporting the performance of widely used different PV materials (crystalline silicon technologies, amorphous silicon, Copper Indium (di) selenide CIS, Cadmium Telluride CdTe, third generation PV and other thin film technologies) in real installations at different locations with thermal and spectral effects [1,2,4,5,10-16,18-21,24,26-60].

## 1.2 Natural solar spectral variation

When solar radiation enters the Earth's atmosphere, not only the irradiance but also the spectral content is affected. The standard solar spectrum used for testing PV devices is given in Fig.1 but in general, the shape of spectrum is variable during a day. Increasing air mass displaces the solar spectrum towards the red [60]. The solar radiation that fills the sky can be direct, diffuse and reflected irradiance. Total or global solar radiation measured on a surface is the sum of beam and diffuse radiations. Beam or direct radiation is the solar radiation received from the sun without having been

1 scattered by the atmosphere. Therefore, the solar radiation received from the sun after its direction  
2 has been changed by scattering in the atmosphere is defined as the diffuse component of the total  
3 solar radiation. The effect in the spectral distribution is shown in Fig.2. The global solar irradiance is  
4 composed of the direct irradiance and diffused irradiance and the solar spectral irradiance distribution  
5 has the significant influence on the output of a PV device. When the sky is clear and the sun is very  
6 high in the sky, direct radiation is around 85% of the total insolation striking the ground and diffuse  
7 radiation is about 15%. As the sun goes lower in the sky, the percent of diffuse radiation keeps going  
8 up until it reaches 40% when the sun is 10° above the horizon. Atmospheric conditions like clouds and  
9 pollution also increase the percentage of diffuse radiation. On an extremely overcast day, pretty much  
10 100% of the solar radiation is diffuse radiation. This means the larger the percentage of diffuse  
11 radiation, the less the total incident solar radiation. So overall spectrum depends on ratio of  
12 beam/diffuse [10].  
13  
14  
15  
16  
17  
18

19 However, since diffuse radiation is generally pretty equally distributed throughout the sky, the most  
20 diffuse radiation is gathered when PV modules are lying down horizontally. PV modules are generally  
21 settled with tilted angles to maximise the total irradiance and this also increases the amount of direct  
22 irradiance that reaches on the array plane. The steeper PV modules are tilted, the less of the sky they  
23 are facing and the more of the sky's diffuse radiation they miss out on. Reflected radiation describes  
24 sunlight that has been reflected off of non-atmospheric things such as the ground. Asphalt reflects  
25 about 4% of the light that strikes it and a lawn about 25%. However, PV modules tend to be tilted away  
26 from where the reflected light is going and reflected radiation rarely accounts for a significant part of  
27 the sunlight striking their surface. Besides this, both crystalline silicon and thin film based PV modules  
28 need glass and commercial glass has a solar transmission of 83.7%, i.e 16.3% of the sun's energy do  
29 not even get to the PV material. And reflection off PV front glass affects spectrum incident on active  
30 layers.  
31  
32  
33  
34  
35  
36  
37  
38

39 To show the seasonal variation of UF and APE values during a day, first, two representative days in  
40 July and January are selected for a 37°N latitude location. Then UF and APE values from sunrise to  
41 sunset are calculated with the help of SPCTRAL2 [18]. 15° and 35° seasonal tilt is accepted for  
42 summer and winter, respectively. Both UF and APE values are almost constant during the day time  
43 except in the early and late hours of the day. In summer both UF and APE values are increases in  
44 these hours because of the rising diffuse component of the global irradiation when the sun is behind  
45 the array plane. But in winter the values are decreases in these time intervals.  
46  
47  
48  
49  
50  
51  
52

## 53 **2 PV performance and effect of spectrum**

54  
55  
56

57 The electrical power available from a PV device/cell can be modelled with the well-known equivalent  
58 circuit which includes a series resistance and a diode in parallel with a shunt resistance [41]. This  
59 circuit can be used either for an individual cell, for a module consisting of several cells, or for an array  
60  
61  
62  
63  
64  
65

consisting of several modules. The current–voltage relationship is expressed in Eq. (6) at a fixed cell/module temperature and solar radiation. Five parameters must be known in order to determine the current and voltage, and thus the power delivered to the load. These are: the photocurrent  $I_{ph}$  (also known as  $I_L$  light generated current),  $I_0$  the diode reverse saturation current,  $R_s$  the series resistance,  $R_{sh}$  the shunt resistance, and  $a \equiv N_s n_l k_B T_c / q_e$  the modified ideality factor defined in Eq. (8).

$$I = I_{ph} - I_0 \left[ e^{\frac{V+IR_s}{a}} - 1 \right] - \frac{V+IR_s}{R_{sh}} \quad (8)$$

Where,  $N_s$  is the series connected cell/module,  $n_l$  is the diode ideality factor of a cell,  $k_B$  is the Boltzmann constant,  $k_B = 1.3806504 \times 10^{-23} J/K$  and  $q_e$  is the electronic charge  $q_e = 1.602176463 \times 10^{-19} C$ . The power produced by the PV device/cell or module is the product of the current and voltage. At small applied voltages, the diode current is negligible and the current is just the short circuit current,  $I_{sc}$ , which is so close to  $I_{ph}$  as can be seen when  $V$  is set to zero in Eq. (8). At open circuit  $I = 0$ , all the photocurrent,  $I_{ph} \approx I_{sc}$ , is flowing through diode, for ideal case ( $R_s = 0, R_{sh} = \infty$  and  $n_l = 1$ ) the open-circuit voltage can be written as

$$V_{oc} \approx \frac{k_B T_c}{q_e} \ln \left( \frac{I_{sc} + I_0}{I_0} \right) \quad (9)$$

The rectangle-defined  $V_{oc}$  and  $I_{sc}$  provides a convenient means for characterizing the maximum power point [45]. The fill factor,  $FF$ , is a measure of the squareness of the  $I-V$  characteristic and is always less than one. It is the ratio of the areas of the two rectangles and defined as

$$FF = \frac{P_{mpp}}{I_{sc} V_{oc}} = \frac{I_{mpp} V_{mpp}}{I_{sc} V_{oc}} \quad (10)$$

Where  $P_{mpp}$  is the power of the device/cell or module at the maximum power point,  $I_{mpp}$  and  $V_{mpp}$  are the current and the voltage values at this point, respectively. And the most important figure of merit for a PV device/cell or module is its power conversion efficiency,  $\eta$ , which is defined as

$$\eta = \frac{P_{mpp}}{P_{in}} = \frac{FF \times I_{sc} \times V_{oc}}{P_{in}} \quad (11)$$

where,  $P_{in}$ , is the power of the light determined by the properties of the light spectrum incident upon the device/cell or module. And, can be defined as in Eq. (12) spectrum dependent with the help of Eq. (4), where  $A$  is the surface area.

$$P_{in} = G \times A = A \int_0^{\infty} \epsilon_{\lambda} b(\lambda) d\lambda \quad (12)$$



## 2.1 Spectral response

There are large differences in the sensitivity of different PV materials to spectral variation. This is determined in the first instance by the band gap of the material, which sets the upper wavelength limit of the spectral response.

The sensitivity of different PV device/module electrical parameters to the various environmental influences of these conditions depends on the technology (device material and structure) and the performance is directly proportional to spectral response where spectral response is the ratio of the current generated by the PV device to the solar power incident on its surface. Spectral response of a PV device is given by the probability that the absorbed photon will yield a carrier to the  $I_{ph}$  photogenerated current of the cell and the spectral response is determined by the band gap, cell thickness and transport in the material. The spectral response is defined as the short-circuit current,  $I_{sc}(\lambda)$ , resulting from a single wavelength of light normalized by the maximum possible current [20-23, 41-44]

$$SR(\lambda) = \frac{I_{sc}(\lambda)}{qAf(\lambda)} \quad (13)$$

Where,  $q$  is the electronic charge  $1.6 \times 10^{-19}C$ ,  $A$  is the surface area of the PV device and  $f(\lambda)$  is the incident photon flux (number of photons incident per unit area per second per wavelength). The degree to which the spectral response and the incident irradiance spectrum coincide varies as the spectrum changes and gives rise to a spectral effect on the device current and efficiency. Spectral responses of some module types and AM1.5G spectrum (up to 1300nm) is shown in Fig.2 to show the response differences of different technologies [42].

To quantify matters, some effective measure of spectral distribution is required, one that encapsulates the idea that a spectral shift towards higher energies will result in a larger proportion of blue or ultraviolet light than a spectral shift towards lower energies. Since a-Si devices absorb more strongly in the blue than in the red, and not at all in the infra-red, such shifts will inevitably have an impact on the device parameters, even if all other factors (e.g. total irradiance, incident angle, temperature) remain constant [23,40].

PV device operating temperature may affect the photocurrent in two ways: Through a change in absorption efficiency represented by an instantaneous temperature coefficient, or via material changes caused by annealing recovery of light-induced degradation. Temperature coefficients of  $I_{sc}$ ,  $V_{oc}$  and  $P_{mpp}$  are generally given in manufacturer data sheets, measured under STC irradiance and spectrum. Hence, the operating temperature results variation in  $I_{sc}$  at the same irradiation levels with an enhancement of up to 2% and a winter reduction up to 1% [20, 43, 44]. This effect is severe for thin film devices, yet the parametric sensitivity of these devices to variations in the incident spectrum is still not fully understood but several studies were evaluated to define the main reason of variation for different materials, especially for a-Si based solar cells [8, 20, 23, 35, 42-45, 60].

1  $I_{sc}$  is spectrum dependent as given in Eq. (11) so the other PV device performance parameters  
2 namely  $FF, \eta$  and  $V_{oc}$  are also affected by the spectrum variations [44,62]. Numerous performance  
3 analysis studies have been carried out to assess the magnitudes of these effects on different  
4 technology based PV devices [65-78]. Hence, for a  $1000\text{W/m}^2$  irradiation level, the operating  
5 temperature of the PV devices is transposed to the value at STC which process is known as  
6 temperature correction. There are several analytical and numerical translation methods of the  
7 measured values to desired conditions in the literature [79-83]. Temperature corrected short circuit  
8 current over irradiation ( $I_{sc}/G$ ) variation of the cell/module with respect to the irradiation will give  
9 knowledge about the spectral dependence eliminated from the thermal effects.  
10  
11  
12  
13  
14  
15

### 16 **3 Conclusions**

17  
18  
19  
20 The influence of spectrum on the performance of PV modules is summarised in this paper.  
21 Performance variation is strongly dependent to module type. Based on this, the ratio of available to  
22 global solar radiation had a seasonal variation of 5%. For clear sky days, spectrum has little influence  
23 for low band gap material based PV modules (efficiency varies only 4% or 5% between seasons for  
24 e.g. crystalline silicon solar cells), but for large band gap materials like a-Si this effect is severe  
25 (efficiency varies -10% to +15% between seasons). Temperature corrected ( $I_{sc}/G$ ) variation with  
26 respect to the irradiation will give knowledge about the spectral dependence of the PV device/cell or  
27 module eliminated from the thermal effects. Numerous performance analysis studies investigating the  
28 spectrum effects on different technology based PV devices are addressed.  
29  
30  
31  
32  
33  
34  
35

### 36 **Acknowledgements**

37  
38 One of the authors (RE) is thankful to the Turkish Council of Higher Education for the funding during  
39 the visit to CREST (Centre for Renewable Energy Systems Technology) in Loughborough University,  
40 Leicestershire, UK.  
41  
42  
43  
44  
45

### 46 **References**

- 47  
48 [1] Marion B. A method for modelling the current-voltage curve of a PV module for outdoor  
49 conditions. Progress in Photovoltaics: Research and Applications 2002; 10(3): 205–214.  
50  
51 [2] Knaupp W. Power rating of photovoltaic modules from outdoor measurements. In: Proceedings of  
52 the 22<sup>nd</sup> IEEE PVSC, Las Vegas, 1991. p. 620–624.  
53  
54 [3] Tsutsui J, Kurokawa K. Investigation to estimate the short circuit current by applying the solar  
55 spectrum Progress in Photovoltaics: Research and Applications 2008; 16 (3): 205–211.  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [4] Virtuani A, Müllejans H, Dunlop ED, Comparison of indoor and outdoor performance measurements of recent commercially available solar modules. *Progress in Photovoltaics: Research and Application* 2011; 19: 11-20.
- [5] Pierro M, Bucci F, Cornaro C, Full characterization of photovoltaic modules in real operating conditions: theoretical model, measurement method and results. *Progress in Photovoltaics: Research and Application* 2014;
- [6] Duffie JA, Beckman WA. *Solar engineering of thermal processes*. John Wiley&Sons Inc., Hoboken, New Jersey, 2006.
- [7] Green M, *Solar Cells: operating principles, technology, and system applications*. Prentice Hall, Englewood Cliffs, 1982.
- [8] <<http://rredc.nrel.gov/solar/spectra/am1.5/>>; 10 July 2012.
- [9] International Electro-Technical Commission. *Standard IEC 60904-3: Photovoltaic Devices. Part 3: Measurement Principles for Terrestrial Photovoltaic (PV) Solar Devices With Reference Spectral Irradiance Data (Ed. 2, 2008)*.
- [10] Betts TR. PhD thesis. Investigation of photovoltaic device operation under varying spectral conditions, Loughborough University; 2004.
- [11] Okeke CE, Anuforom AC, Effect of Clearness Index on The Optimum Efficiency of an Array of Silicon Solar Cells. *Energy Conversion and Management* 1990; 30 (3): 215-218.
- [12] Nakajima A, Ichikawa M, Kondo M, Yamamoto K, Yamagishi H, Tawada Y. Optimization of Device Design for Thin-Film Stacked Tandem Solar Modules in Terms of Outdoor Performance. *Japanese Journal of Applied Physics*. 2004; 43: L1162-L1165.
- [13] Gottschalg R, Betts TR, Infield DG, del Cueto JA. Seasonal performance of a-Si single and multijunction modules in two locations . In: *Proceedings of 31<sup>st</sup> IEEE-PVSC, Orlando, USA, 2005*. p. 1484–1487.
- [14] Adlstein J, Sekulic B. Performance and reliability of a 1-kW amorphous silicon photovoltaic roofing system. In: *Proceedings of 31<sup>st</sup> IEEE-PVSC, Orlando, USA, 2005*. p. 1627–1630.
- [15] Akhmad K, Okamoto H, Yamamoto F, Kitamura A. Long-term performance modelling of amorphous silicon photovoltaic module. *Japanese Journal of Applied Physics*. 1997; 36: 629-632.
- [16] Nakada Y, Fukushige S, Minemoto T, Takakura H. Seasonal variation analysis of the outdoor performance of amorphous Si photovoltaic modules using the contour map. *Solar Energy Materials & Solar Cells* 2009; 93: 334–337.
- [17] Huld T, Gottschalg R, Beyer HG, Topic M. Mapping the performance of PV modules, effects of module type and data averaging. *Solar Energy* 2010; 84: 324–338
- [18] Nann S, Emery K. Spectral effects on PV-device rating. *Solar Energy Materials and Solar Cells* 1992; 27: 189–216.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [19] Cornaro C, Andreotti A. Influence of Average Photon Energy index on solar irradiance characteristics and outdoor performance of photovoltaic modules. *Progress in Photovoltaics: Research and Applications*. 2013; 21:996–1003
- [20] Shimokawa R, Miyake Y, Nakanishi Y, Kuouano Y, Hamakawa Y. Effect of atmospheric parameters on solar cell performance under global irradiance. *Solar Cells*1986–1987; 19: 59–72.
- [21] Rosell JI, Ibanez M, Modelling power output in photovoltaic modules for outdoor operating conditions. *Energy Conversion and Management* 2006; 47: 2424–2430.
- [22] <<http://www.nrel.gov/rredc/smarts/>> 21 July 2012.
- [23] <<http://rredc.nrel.gov/solar/models/spectral/SPCTRAL2/>>21 July 2012.
- [24] Hassanzadeh BH, de Keizer AC, Reich NH, van Sark WGJHM. The effect of a varying solar spectrum on the energy performance of solar cells. In: proceedings of 22nd European PVSEC, Milan, 2007. p. 2652-2658.
- [25] International Electro-Technical Commission. Standard IEC 60904–7. Photovoltaic devices - Part 7. Computation of the spectral mismatch correction for measurements of photovoltaic devices, (Ed. 3, 2008). Geneva. Switzerland; 2008.
- [26] Gottschalg R, Betts TR, Infield DG, Kearney MJ. On the importance of considering the incident spectrum when measuring the outdoor performance of amorphous silicon photovoltaic devices. *Measurement Science and Technology* 2004; 15: 460–466.
- [27] Ishii T, Otani K, Takashima T, Xue Y. Solar spectral influence on the performance of photovoltaic (PV) modules under fine weather and cloudy weather conditions. *Progress in Photovoltaics: Research and Applications*. 2013; 21: 481–489.
- [28] Gottschalg R, Betts TR, Infield DG, Kearney MJ, The effect of spectral variations on the performance parameters of single and double junction amorphous silicon solar cells. *Solar Energy Materials & Solar Cells* 2005; 85: 415–428.
- [29] Sirisamphanwong C, Ketjoy N. Impact of spectral irradiance distribution on the outdoor performance of photovoltaic system under Thai climatic conditions. *Renewable Energy* 2012; 38: 69-74.
- [30] Fukushige S, Ichida K, Minemoto T, Takakura H. Analysis of the temperature history of amorphous silicon photovoltaic module outdoors. *Solar Energy Materials & Solar Cells* 2009; 93: 926–931.
- [31] Nakada Y, Fukushige S, Minemoto T, Takakura H. Seasonal variation analysis of the outdoor performance of amorphous Si photovoltaic modules using the contour map. *Solar Energy Materials & Solar Cells* 2009; 93: 334–337.
- [32] Williams S, Betts TR, Helf T, Gottschalg R, Beyer H, Infield D. Modelling long- term module performance based on realistic reporting conditions with consideration to spectral effects.In:

Proceedings of the 3rd world conference on photovoltaic energy conversion, Osaka, Japan 2003. p. 1908–1911.

[33] Fabero F, Alonso-Abella M, Chenlo F. Influence of irradiance variations on PV systems at different time scales. In: Proceedings of the 14th PVSEC, Barcelona, 1997. p. 2299–2302.

[34] Jardine CN, Conibeer GJ, Lane K. PV-COMPARE: Direct comparison of eleven PV technologies at two locations in northern and southern Europe. In: Proceedings of the 17th European PVSEC, Munich, 2001. p. 724–727.

[35] Jardine CN, Lane K. PV-COMPARE: Relative performance of photovoltaic technologies in northern and southern Europe. In: Proceedings of the PV in Europe Conference, Rome, 2002. p. 1057–1060.

[36] Faine P, Kurtz SR, Riordan C, Olson JM. The influence of spectral solar irradiance variations on the performance of selected single-junction and multi junction solar cells. *Solar Cells* 1991; 31: 259–278.

[37] Eke R, Oktik S. Comparison of 18 month kWh/kWp energy output of four photovoltaic systems with four different module technologies. In: proceedings of 22nd European PVSEC, Milan, 2007. p. 3163-3166.

[38] Ikisawa M, Nakano A, Igari S, Terashima H. Outdoor exposure tests of photovoltaic modules in Japan and overseas. *Renewable Energy* 1998; 14 (1-4): 95-100.

[39] Minemoto T, Fukushige S, Takakura H. Difference in the outdoor performance of bulk and thin-film silicon-based photovoltaic modules. *Solar Energy Materials & Solar Cells* 2009; 93: 1062–1065.

[40] Johnson L, Ha J. Long-term sequential testing for photovoltaic modules. In: Proceedings of the 26<sup>th</sup> European PVSEC, Hamburg, 2011. p. 3084-3087.

[41] Eke R. Correlation of operating conditions and solar cell parameters, PhD Thesis. Ege University, 2007 (in Turkish).

[42] Sadok M, Mehdaoui A. Outdoor testing of photovoltaic arrays in the saharan region. *Renewable Energy* 2008; 33: 2516– 2524.

[43] Perez-Lopez JJ, Fabero F, Chenlo F. Experimental solar spectral irradiance until 2500 nm: results and influence on the PV conversion of different materials. *Progress in Photovoltaics: Research and Applications* 2007; 15: 303–315.

[44] Kenny RP, Ioannides A, Müllejans H, Zaaiman W, Dunlop ED. Performance of thin film PV modules. *Thin Solid Films* 2006; 511-512: 663 – 672.

[45] Luque A, Hegedus S. Handbook of photovoltaic science and engineering. John Wiley & Sons Inc., England, 2003.

1 [46] Piliougine M, Elizondo D, Mora-López L, Sidrach- de-Cardona M. Photovoltaic module simulation  
2 by neural networks using solar spectral distribution. *Progress in Photovoltaics: Research and*  
3 *Application* 2013; 21: 1222-1235.

4  
5 [47] Hirata Y, Tani T. Output Variation on Photovoltaic Modules With Environmental Factors-I. The  
6 spectral Solar Radiation on Photovoltaic Module Output. *Solar Energy* 1995; 55: 463–468.

7  
8 [48] Bandou F, Hadj Arab A, Belkaid MS, Logerais PO, Riou O, Charki A. Evaluation  
9 performance of photovoltaic modules after a long time operation in Saharan environment.  
10 *International Journal of Hydrogen Energy* 2015; 40: 13839-13848

11  
12 [49] Klugmann-Radziemska E. Degradation of electrical performance of a crystalline  
13 photovoltaic module due to dust deposition in northern Poland. *Renewable Energy* 2015; 78:  
14 418-426.

15  
16 [50] Tossa AK, Soro YM, Azoumah Y, Yamegueu D. A new approach to estimate the performance and  
17 energy productivity of photovoltaic modules in real operating conditions. *Solar Energy* 2014; 110: 543-  
18 560.

19  
20 [51] Ndiaye A, Charki A, Kobi A, Kébé CMF, Ndiaye PA, Sambou V. Degradations of silicon  
21 photovoltaic modules: A literature review. *Solar Energy* 2013; 96: 140-151.

22  
23 [52] Nagae S, Toda M, Minemoto T, Takakura H, Hamakawa Y. *Evaluation of the impact of solar*  
24 *spectrum and temperature variations on output power of silicon-based photovoltaic modules*. *Solar*  
25 *Energy Materials and Solar Cells* 2006; 90: 3568-3575

26  
27 [53] Marion B, Deceglie MG, Silverman TJ. Analysis of measured photovoltaic module performance for  
28 Florida, Oregon, and Colorado locations. *Solar Energy* 2014; 110: 736-744.

29  
30 [54] Kichou S, Silvestre S, Nofuentes G, Torres-Ramírez M, Chouder A, Guasch D. Characterization  
31 of degradation and evaluation of model parameters of amorphous silicon photovoltaic modules under  
32 outdoor long term exposure. *Energy* 2016; 96,: 231-241.

33  
34 [55] Moreno-Sáez R, Sidrach-de-Cardona M, Mora-López L. Analysis and characterization of  
35 photovoltaic modules of three different thin-film technologies in outdoor conditions. *Applied*  
36 *Energy* 2016; 162: 827-838.

37  
38 [56] Pandey AK, Tyagi VV, Selvaraj JAL, Rahim NA, Tyagi SK. Recent advances in solar  
39 photovoltaic systems for emerging trends and advanced applications. *Renewable and Sustainable*  
40 *Energy Reviews*, 2016; 53: 859-884.

41  
42 [57] Tossa AK, Soro YM, Thiaw L, Azoumah Y, Sicot L, Yamegueu D, Lishou C, Coulibaly Y,  
43 Razongles G. Energy performance of different silicon photovoltaic technologies under hot and harsh  
44 climate. *Energy* 2016; 103: 261-270.

- 1  
2  
3 [58] Bai A, Popp J, Balogh P, Gabnai Z, Pályi B, Farkas I, Pintér G, Zsiborács H. Technical and  
4 economic effects of cooling of monocrystalline photovoltaic modules under Hungarian conditions.  
5 Renewable and Sustainable Energy Reviews 2016; 60: 1086-1099.
- 6 [59] Akinyele DO, Rayudu RK, Nair NKC. Global progress in photovoltaic technologies and the  
7 scenario of development of solar panel plant and module performance estimation-Application in  
8 Nigeria. Renewable and Sustainable Energy Reviews 2015; 48: 112-139.
- 9 [60] Gottschalg R, Betts TR, Williams SR, Sauter D, Infield DG, Kearney MJ. A critical appraisal of the  
10 factors affecting energy production from amorphous silicon photovoltaic arrays in a maritime climate.  
11 Solar Energy 2004; 77: 909–916.
- 12 [61] Philipps SP, Peharz G, Hoheisel R, Hornung T, Al-Abbadi NM, Dimroth F, Bett AW. Energy  
13 harvesting efficiency of III–V triple-junction concentrator solar cells under realistic spectral conditions.  
14 Solar Energy Materials & Solar Cells 2010; 94: 869–877.
- 15 [62] Gottschalg R, Infield DG, Kearney MJ. Experimental study of variations of the solar spectrum of  
16 relevance to thin film solar cells. Solar Energy Materials & Solar Cells 2003; 79: 527–537.
- 17 [63] Poortmans J, Arkhipov V. Thin film solar cells: fabrication, characterization and applications. John  
18 Wiley&Sons Ltd., The Atrium, England, 2006.
- 19 [64] Perez-Lopez JJ, Fabero F, Chenlo F. Experimental solar spectral irradiance until 2500 nm:  
20 results and influence on the PV conversion of different materials. Progress in Photovoltaics: Research  
21 and Applications 2007; 15: 303–315.
- 22 [65] Fabero F, Vela N, Chenlo F. Influence of solar spectral variations on the conversion efficiency of  
23 a-Si and m-Si PV devices: A yearly and hourly study. In: Proceedings of the 13th European PVSEC,  
24 Nice, 1995. p. 2281–2284.
- 25 [66] Gonzalez MC, Carrol JJ. Solar cells efficiency variations with varying atmospheric conditions.  
26 Solar Energy 1994; 53: 395–402.
- 27 [67] van Overstraeten RJ, Mertens RP. Physics, technology and use of photovoltaics. Adam Hilger  
28 Ltd., Bristol and Boston, 1986.
- 29 [68] Hartman JS, Lind MA, Chaudiere DA. The sensitivity of calculated short-circuit currents to  
30 selected irradiance distributions and solar cell spectral responses. Solar Cells 1982; 6 (2): 133-148.
- 31 [69] Osterwald CR. Calculated solar cell Isc sensitivity to atmospheric conditions under direct and  
32 global irradiance. In: Proceedings of the IEEE Photovoltaic Specialists Conference, 1985. p. 951–955.
- 33 [70] Mueller RL. The calculated influence of atmospheric conditions on solar cell Isc under direct and  
34 global solar irradiances. In: Proceedings of the IEEE Photovoltaic Specialists Conference, 1987. p. 166–  
35 170.
- 36 [71] Skoplaki E, Palyvos JA. On the temperature dependence of photovoltaic module electrical  
37 performance: A review of efficiency/power correlations, Solar Energy 2009; 83: 614–624.
- 38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 [72] Zhou W, Yang H, Fang Z. A novel model for photovoltaic array performance prediction. Applied  
2 Energy 2007; 84: 1187–1198.

3 [73] Makrides G, Zinsser B, Phinikarides A, Schubert M, Georghiou GE. Temperature and thermal  
4 annealing effects on different photovoltaic technologies. Renewable Energy 2012; 43: 407-417.

5 [74] Jiang JA, Wang JC, Kuo KC, Su YL, Shieh JC, Chou JJ. Analysis of the junction temperature and  
6 thermal characteristics of photovoltaic modules under various operation conditions. Energy 2012; 44:  
7 292-301.

8 [75] Mekhilef S, Saidur R, Kamalisarvestani M. Effect of dust, humidity and air velocity on efficiency of  
9 photovoltaic cells. Renewable and Sustainable Energy Reviews 2012; 16: 2920–2925.

10 [76] Okullo W, Munji MK, Vorster FJ, van Dyk EE. Effects of spectral variation on the device  
11 performance of copper indium diselenide and multi-crystalline silicon photovoltaic modules. Solar  
12 Energy Materials & Solar Cells 2011; 95: 759–764.

13 [77] Kamkird P, Ketjoy N, Rakwichian W, Sukchai S. Investigation on temperature coefficients of three  
14 types photovoltaic module technologies under Thailand operating condition. Procedia Engineering  
15 2012; 32: 376 – 383.

16 [78] Singh P, Ravindra NM. Temperature dependence of solar cell performance-an analysis. Solar  
17 Energy Materials & Solar Cells 2012; 101: 36-45.

18 [79] Asima N, Sopian K, Ahmadi S, Saeedfar K, Alghoul MA, Saadatian O, Zaidi SH. A review on the  
19 role of materials science in solar cells. Renewable and Sustainable Energy Reviews 2012; 16: 5834–  
20 5847.

21 [80] Rütther R, Kleiss G, Reiche K. Spectral effects on amorphous silicon solar module fill factors.  
22 Solar Energy Materials & Solar Cells 2002; 71: 375–385.

23 [81] Marion B, Rummel S, Anderberg A. Current–voltage curve translation by bilinear interpolation.  
24 Progress in Photovoltaics: Research and Application 2004; 12: 593-607.

25 [82] Tsuno Y, Hishikawa Y, Kurokawa K. Translation equations for temperature and irradiance of the  
26 I-V curves of various PV cells and modules. In: Proceedings of Photovoltaic Energy Conversion,  
27 Conference Record of IEEE 4th World Conference, 2006. p. 2246-2249.

28 [83] Picault D, Raison B, Bacha S, de la Casa J, Aguilera J. Forecasting photovoltaic array power  
29 production subject to mismatch losses. C  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



Figure 1-revised  
[Click here to download high resolution image](#)

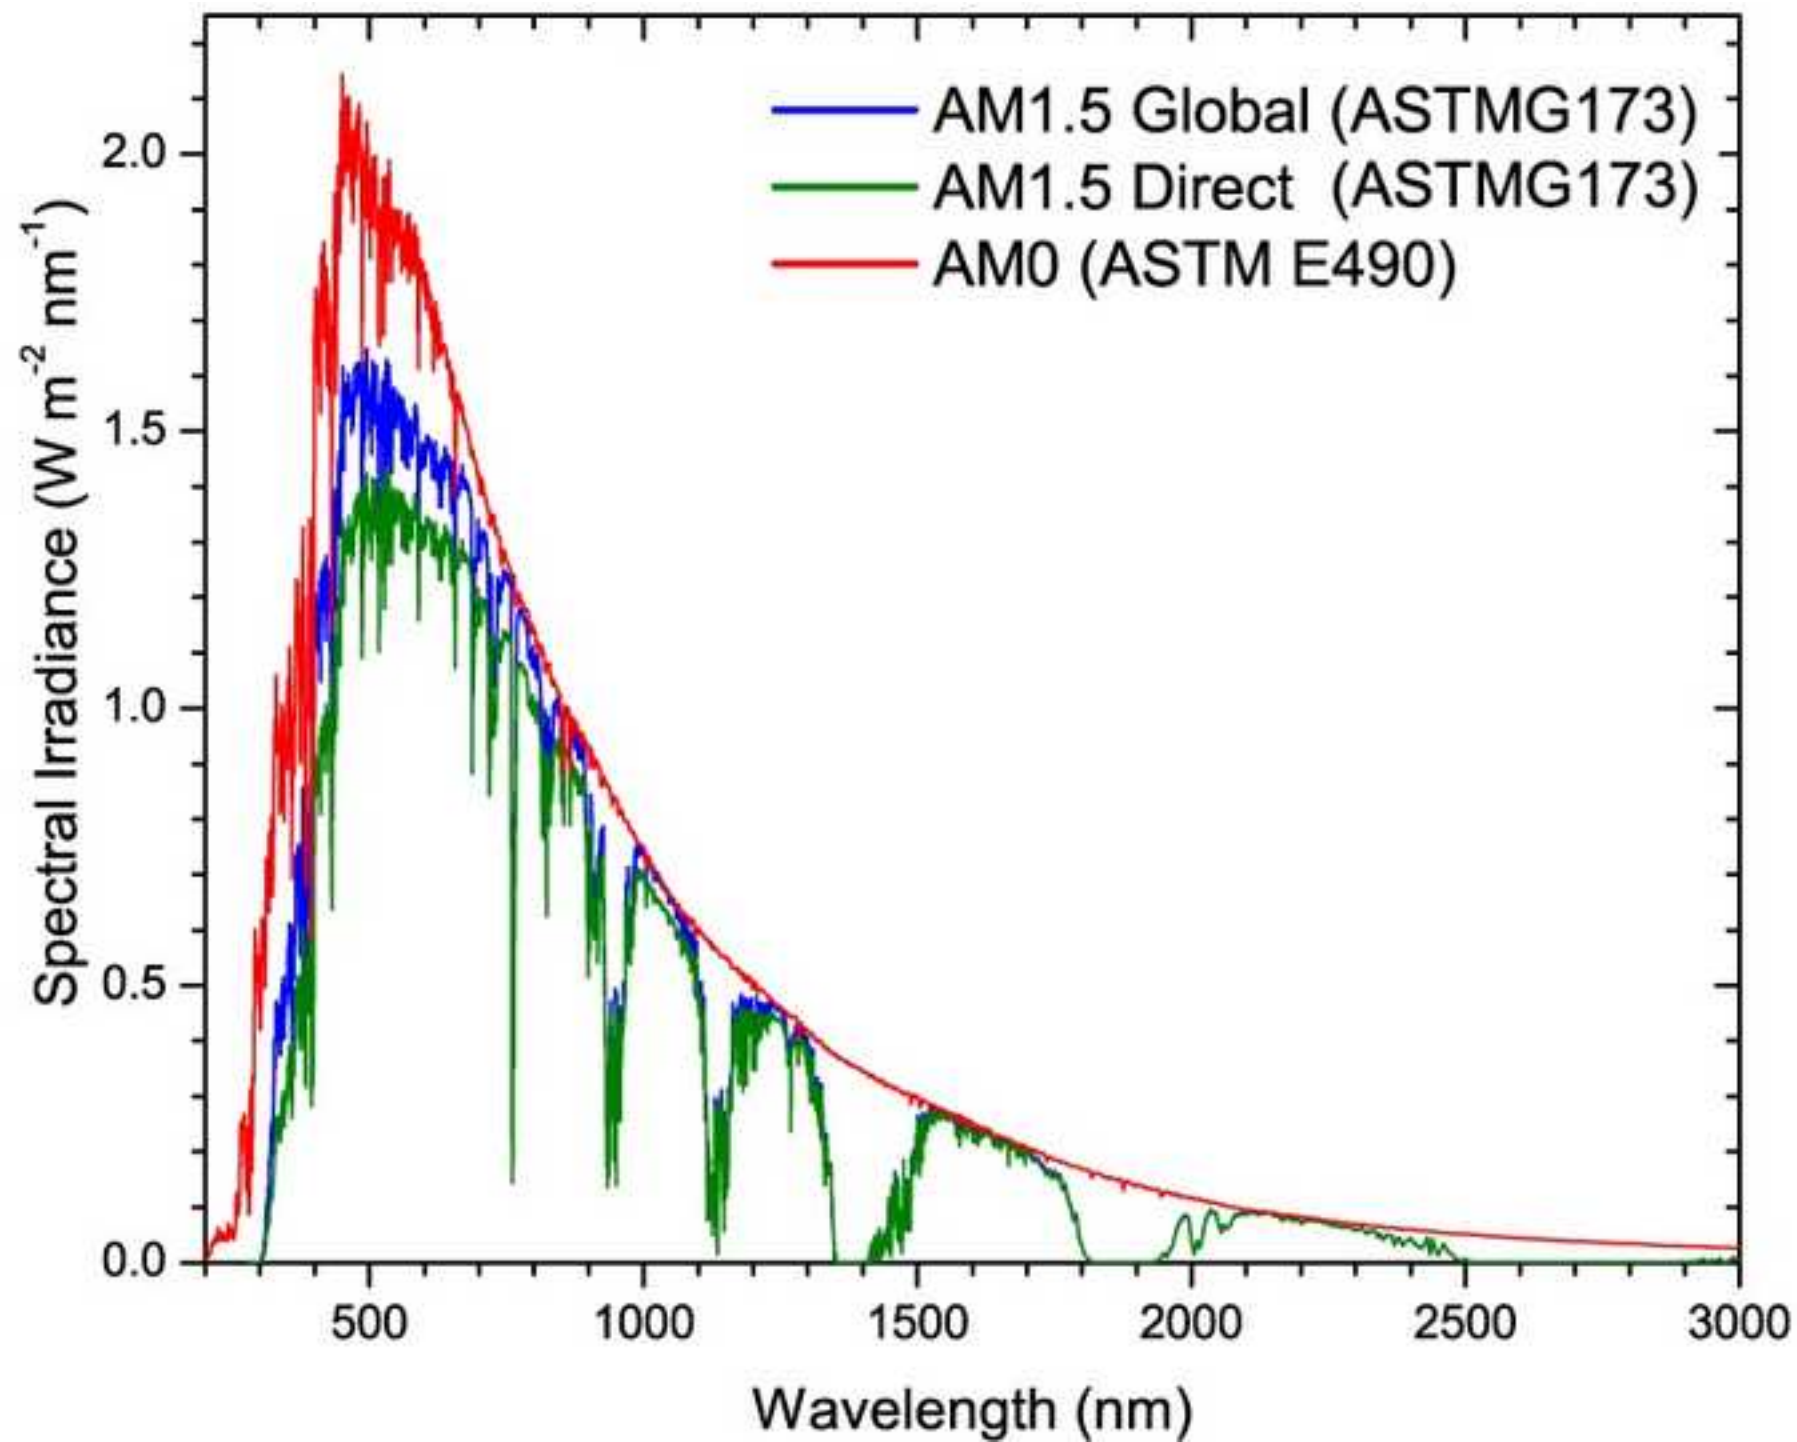


Figure2

[Click here to download high resolution image](#)

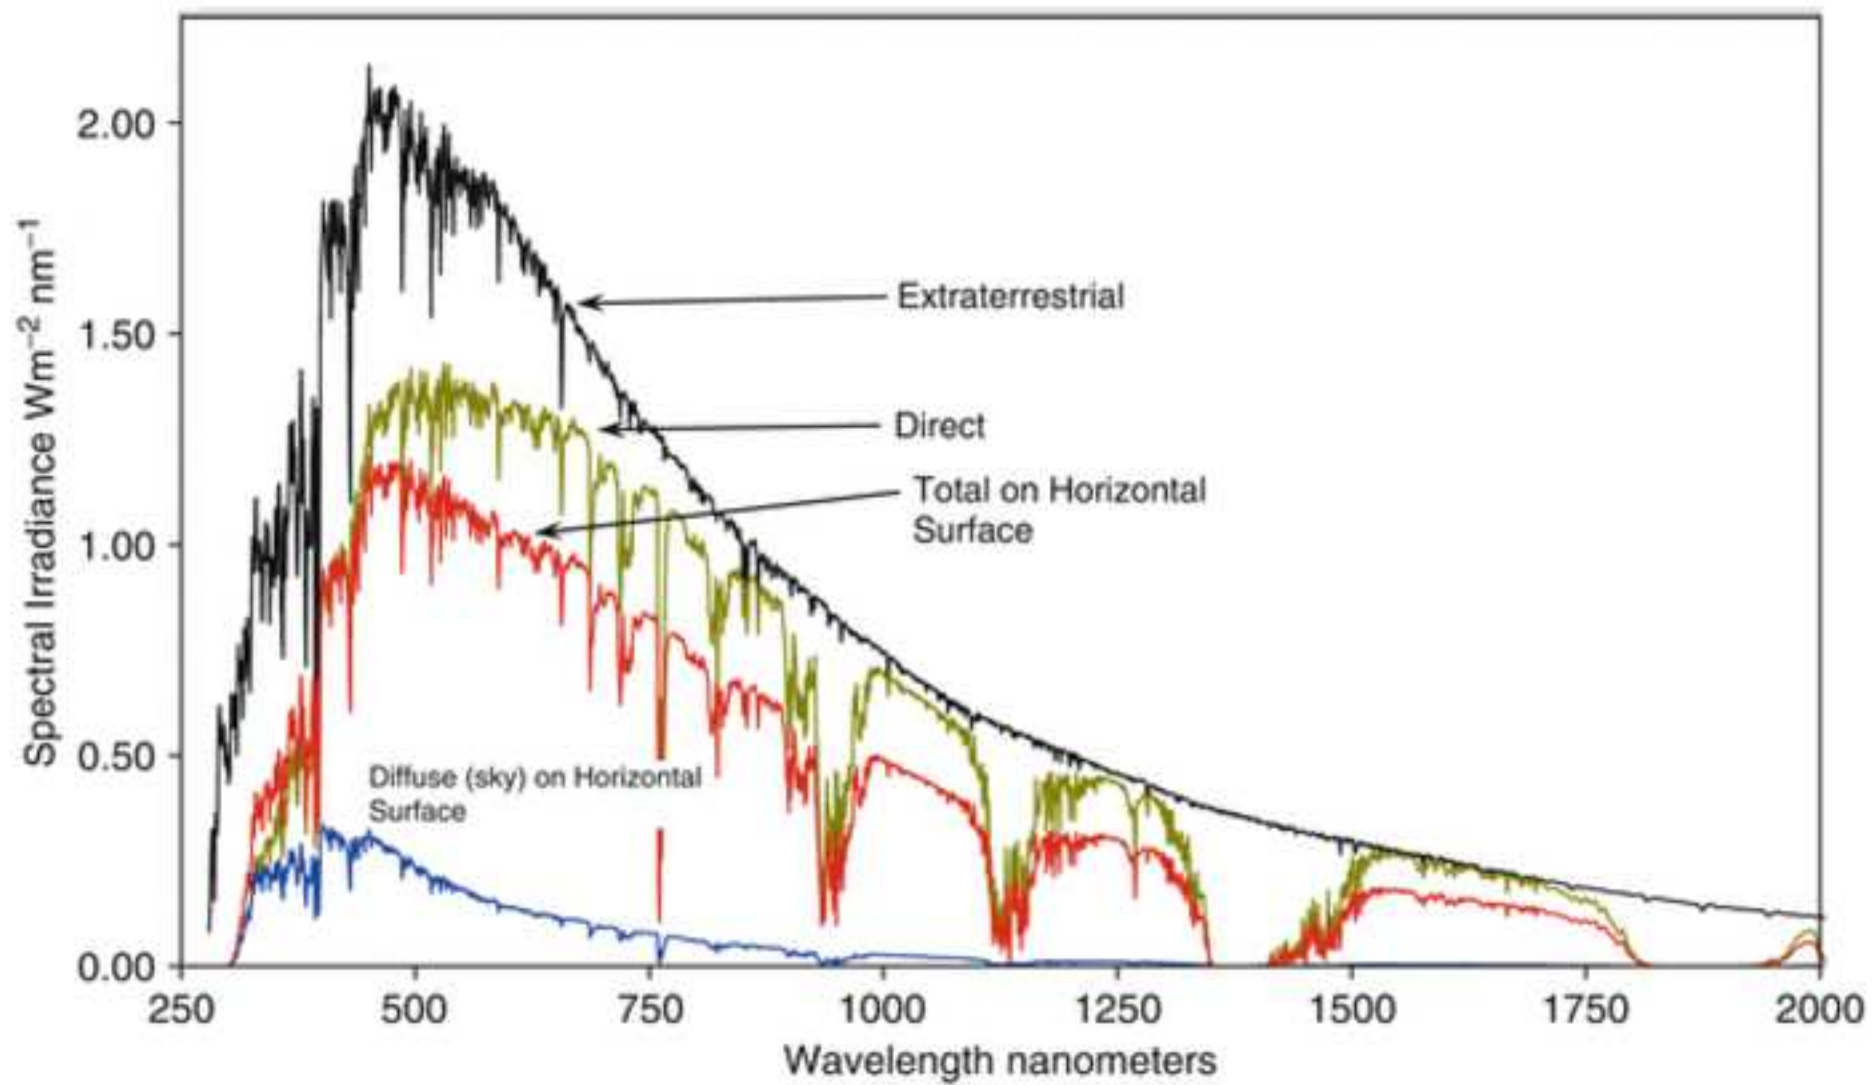


Figure 3-revised  
[Click here to download high resolution image](#)

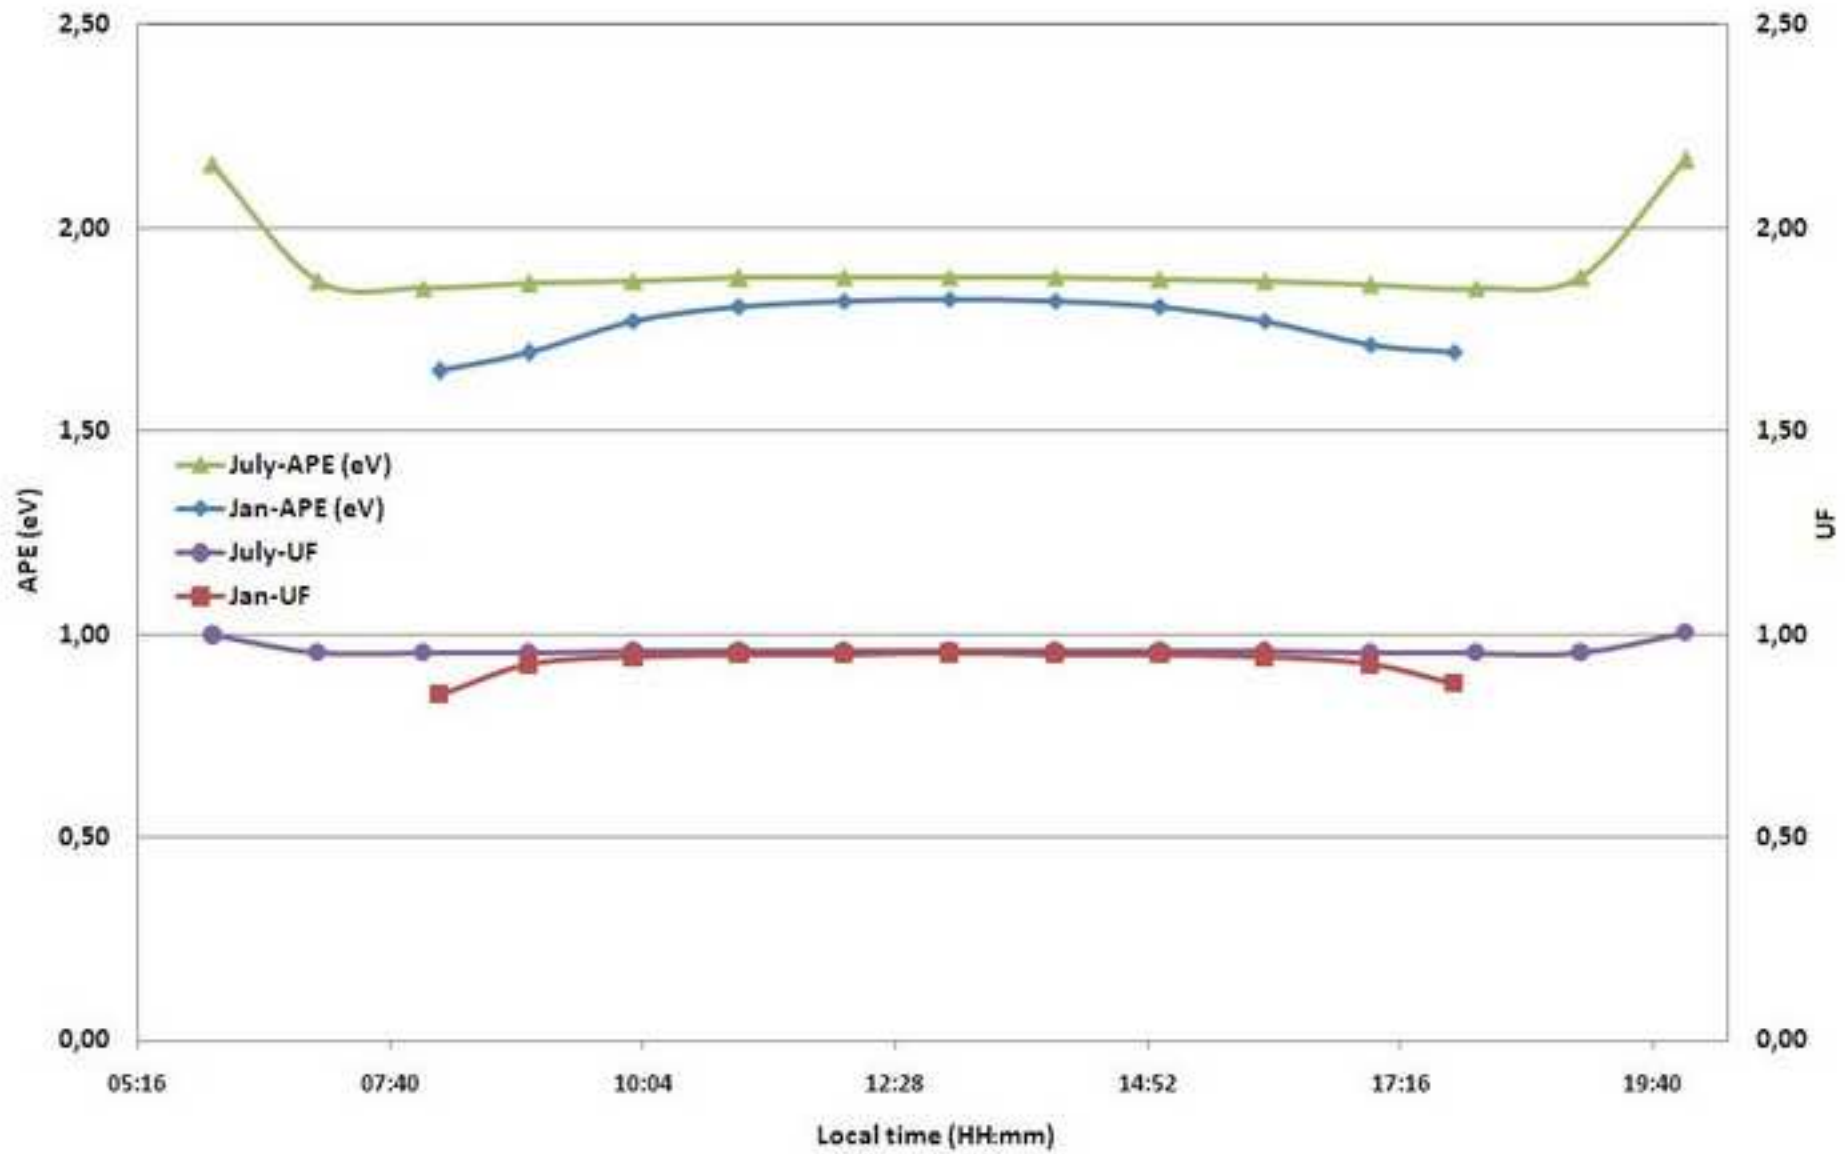


Figure4

[Click here to download high resolution image](#)

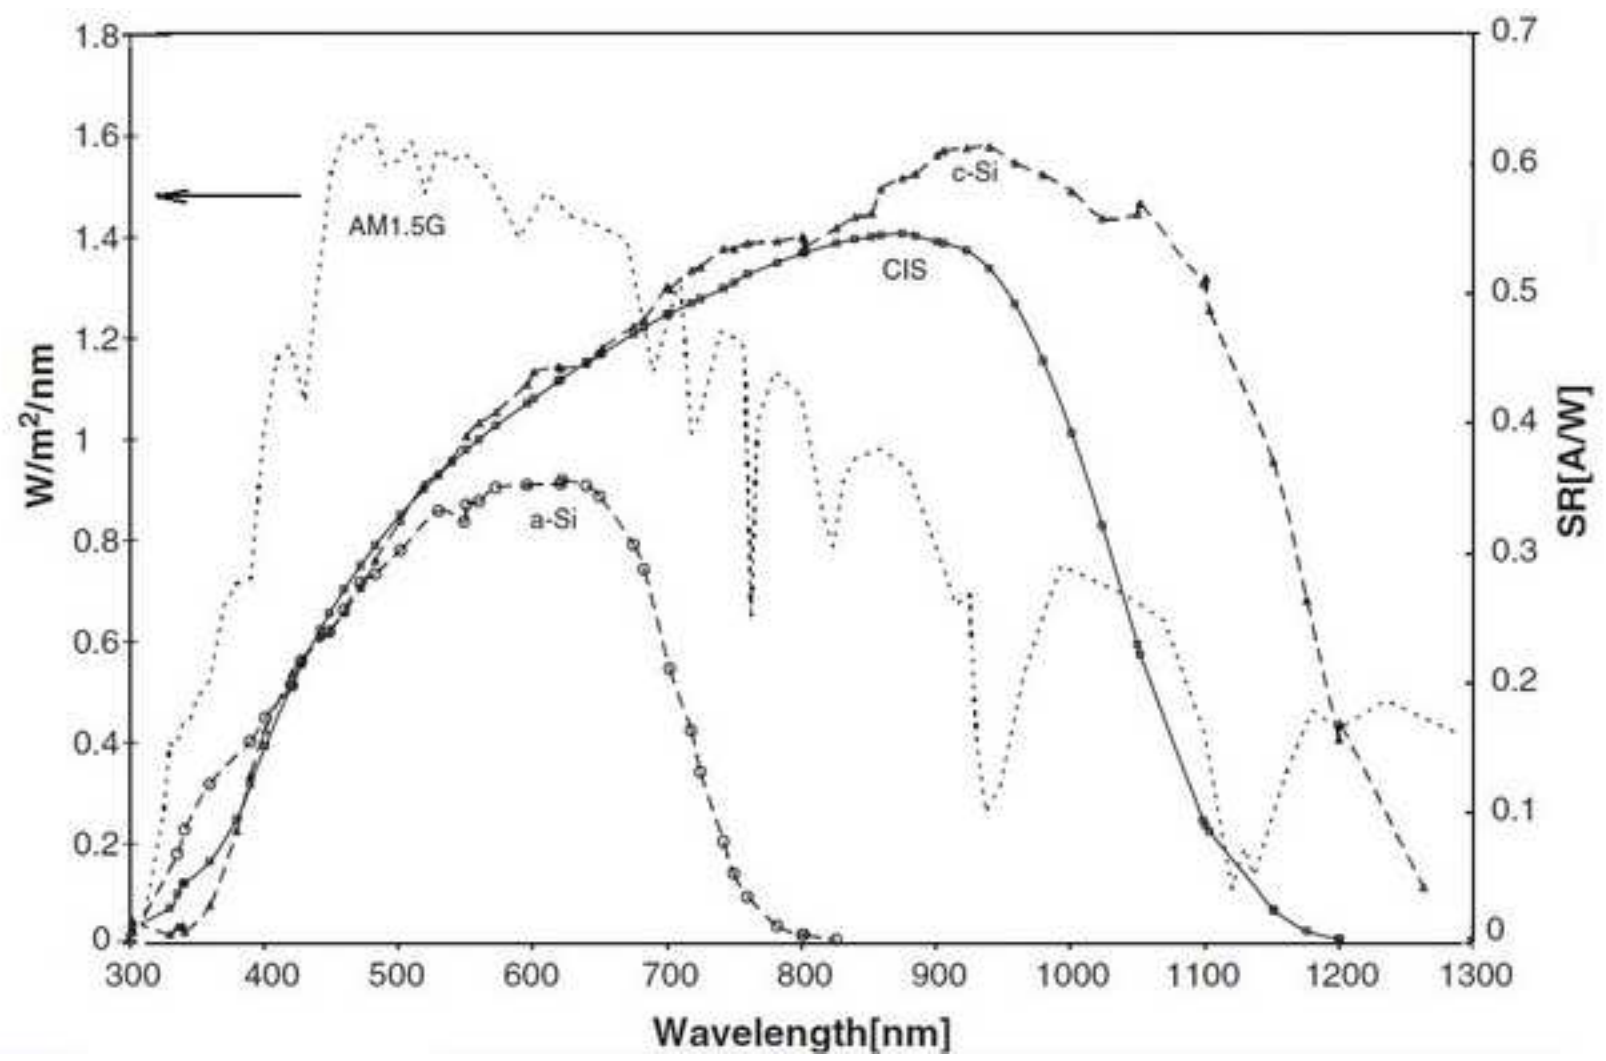


Table 1: APE of the standard spectrum evaluated from different spectral integration limits [19].

Wavelength range (nm)	APE, Average Photon Energy (eV)
300-4000	1.43
300-2500	1.48
300-1700	1.62
300-1100	1.86

## Figure and Table Captions

Figure 1: Standard reference solar spectra.

Figure 2: Solar spectral distribution with its components.

Figure 3: Calculated APE and UF values for clear sky days for a location of 37°N latitude (15° and 35° seasonal tilt is taken for summer and winter, respectively)

Figure 4: Spectral responses of some module types and the AM1.5G spectrum (up to 1300 nm) [39].

Table 1: APE of the standard spectrum evaluated from different spectral integration limits [20].