

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26

**Field assisted sintering of nanostructured zirconia-alumina  
ceramics for demanding applications**

John A. Downs  
*j.a.downs@lboro.ac.uk*  
*Department of Materials*  
*Loughborough University*  
*Loughborough, United Kingdom*

Annapoorani Ketharam  
*k.annapoorani@lboro.ac.uk*  
*Department of Materials*  
*Loughborough University*  
*Loughborough, United Kingdom*

Bala Vaidhyanathan  
*b.vaidhyanathan@lboro.ac.uk*  
*Department of Materials*  
*Loughborough University*  
*Loughborough, United Kingdom*

1 **Abstract:**

2 Flash and Field Assisted Sintering Techniques (FAST) have been demonstrated in many  
3 singular ceramic systems. However, little has been done to thoroughly investigate this  
4 phenomenon in binary systems. Zirconia-alumina composites are of interest because of their  
5 widespread use in demanding situations for health care, petro-chemical and energy  
6 applications. The prospect of minimising grain growth associated with FAST whilst achieving  
7 maximum densification is vital for the above applications to improve performance. Flash  
8 sintering behaviour of several zirconia-alumina formulations was investigated under a range  
9 of DC electric fields up to 700 V/cm. At low alumina contents (<10 wt%) the flash behaviour  
10 was controlled by the zirconia phase; at intermediate compositions (10 wt% - 70 wt%) show a  
11 composite effect; and at high alumina contents (>75 wt%) the effectiveness of field assisted  
12 sintering drops off. These pointers allowed to gain further insight into the mechanisms of  
13 flash sintering and will help to develop pathways for the adaptation of the technique to  
14 process complex ceramic systems.

15

16 **Keywords:** Flash Sintering, FAST, Zirconia-Toughened Alumina, zirconia, bioceramics

17

18

19 **1. Introduction**

20 Zirconia-toughened alumina (ZTA) composites are ideal candidate materials for  
21 demanding applications that require high hardness and high fracture toughness. Here, we are  
22 concerned with biomedical applications like total hip replacements (THR) and total knee  
23 replacements (TKR), but these results can be extended to energy applications like solid oxide  
24 fuel cell (SOFC) electrolytes and petro-chemical valve seats for oil drilling. This composite  
25 ceramic takes advantage of the high hardness and light weight of alumina and the high  
26 fracture toughness of yttria-stabilized zirconia (YSZ) resulting in a superior wear resistant  
27 material optimal for these applications. It is also more biocompatible than the corresponding  
28 metallic or polymeric components that can be toxic and produce wear debris upon  
29 degradation. Despite the apparent advantages of ZTA and also of the corresponding  
30 monolithic YSZ which are also used in biomedical applications, implants have been found to  
31 prematurely fail *in-vivo* after a couple years when the expected lifetime should exceed more  
32 than 10 years and preferably 20 years<sup>1-3</sup>. Upon closer examination, the YSZ component  
33 failure was found to occur due to subcritical crack propagation. Especially YSZ and ZTA  
34 suffer from subcritical crack growth in wet environments. The dominant mechanism for

1 subcritical crack growth is chemical corrosion due to hydrothermal aging (HTA) <sup>4,5</sup> of the  
2 zirconia phase.

3 The mechanisms for HTA still remain unclear. What is commonly accepted is that  
4 during high temperature sintering yttria preferentially segregates to the grain boundary  
5 resulting in concentration gradients of yttria across individual YSZ grains. Yttria is added to  
6 zirconia to stabilize the high temperature tetragonal phase <sup>6</sup>. This stabilization gives YSZ its  
7 fracture toughness because when fracture does occur, the meta-stable tetragonal phase  
8 transitions to the stable monoclinic phase. The energy required for this phase transformation  
9 is absorbed at the crack tip that slows down the crack propagation and is responsible for the  
10 high fracture toughness of YSZ and ZTA. When yttria segregation to the grain boundaries  
11 occurs, the cores of the grains are left under-stabilized. If the core is penetrated by a crack tip,  
12 there is no longer the advantageous phase transformation and, hence, no increased fracture  
13 toughness. In wet environments, since crack tip corrosion is severe due to HTA and the  
14 advantages of the yttria stabilization are no longer present in large volumes of the material,  
15 crack propagation continues unhindered <sup>1,7</sup>. In implant applications where exposure to wet  
16 environments can be for 10 – 20 years, these mechanisms must be considered. These issues  
17 are further exasperated in the steam sterilization condition used to treat implants and surgical  
18 tools before use. The sterilising temperatures have been found ideal for HTA and the high  
19 pressures increase the degradation resulting in accelerated aging conditions. Even after short  
20 treatment times, aging is noticed to occur resulting in increased surface roughness<sup>7</sup>. In SOFCs,  
21 HTA occurs during heating and cooling when the cells pass through the 200-300°C  
22 temperature range with wet fuels, and this results in the degradation of the YSZ electrolytes <sup>5</sup>.

23 Various methods have been shown to prevent HTA: ensuring high density, changing  
24 doping/stabilization levels, use of additional dopants, and various surface treatments to avoid  
25 the initial chemical attack and initial crack propagation <sup>8</sup>. Of importance here, is the reduction  
26 of grain size and grain size dependent phase-stabilisation <sup>9,10</sup>. By reducing grain size to 200-  
27 300 nm <sup>11-13</sup>, HTA resistance begins to increase. If grain sizes are further reduced to an  
28 average of 90 nm, 3YSZ has been shown to be completely immune to HTA, showing no  
29 tetragonal to monoclinic transformation even in the most aggressive steam environment and  
30 the equivalent of 1350 years *in-vivo* <sup>7</sup>. There was no detected yttria gradient across grains  
31 because of the nanometric grain size, meaning, there is no chemical driving force for HTA  
32 and the tetragonal-monoclinic transformation is prevented leaving hardness and fracture  
33 toughness values at pre-treatment levels.

1 Control of grain growth has been a historic issue with the sintering of ceramics. In Ref  
2 [7] the HTA resistant nano-YSZ was prepared by a two-step sintering procedure. In this case,  
3 the sintering cycle was 6 sec at 1150 °C and up to 10 hr at 1050°C to achieve full density.  
4 Two-step sintering, while effective, requires very long sintering time to achieve full densities  
5 and is therefore equipment and energy intensive due to the long times and high temperatures  
6 involved.

7 Field Assisted Sintering Techniques (FAST) are a class of sintering methodologies  
8 that use the application of various electric, magnetic and electromagnetic fields to accelerate  
9 sintering, reduced processing temperature, and shorten dwell times, resulting in fine grained  
10 material when compared to conventional or two-stage sintering. The most common FAST  
11 methodologies include techniques like Spark Plasma Sintering (SPS) <sup>14</sup> and microwave  
12 assisted sintering as well as the more recently developed flash sintering (FS). SPS has very  
13 limited shape capability, a hindrance for biomedical needs, requires highly specialized, very  
14 expensive equipment that operates mainly in inert atmosphere (due to the use of graphite die),  
15 and requires additional post processing to deal with carbon contamination. Microwave  
16 assisted sintering, in pure (MW only) and hybrid heating (MW and radiant heating) forms, are  
17 more adapted to processing of complex shapes but also require specialized equipment  
18 (magnetron and containment) and the materials that can be used are limited. ZTA is an ideal  
19 candidate because zirconia is a good microwave absorber while alumina is microwave  
20 transparent. Fine grained ZTA ceramics have been produced by pure microwave or hybrid-  
21 microwave sintering in shorter times<sup>15,16</sup>. Flash sintering is a newly developed technique that  
22 uses the direct application of DC or AC currents to process ceramic materials. It has been  
23 found that below a threshold E-field strength, sintering has been found to be moderately  
24 accelerated with sintering onset occurring at similar temperatures as in conventional sintering.  
25 If the E-field strength exceeds this threshold, sintering onset temperatures are lowered  
26 significantly and sintering times reduced to the order of seconds rather than hours/days. The  
27 E-fields and current required, their relation to temperature and the threshold temperature for  
28 the onset of flash behaviour are material dependent and have relationships to their  
29 conductivity. The effect of flash sintering on grain growth has resulted in mixed observations.  
30 In some cases, grain growth is shown to be accelerated, even at the low processing  
31 temperatures and in some cases, grain growth is reduced or prevented. There appears to be a  
32 useful processing window (E-field strength-temperature- current density) that allow for good  
33 sintering while allowing for grain growth retardation. These regimes remain determined  
34 empirically for each material being examined.

1           3YSZ was the first material used to demonstrate the flash sintering technique <sup>17</sup>. The  
2 critical E-field for the onset of flash sintering was found to be ~50V/cm. With 120 V/cm,  
3 sintering occurred to near full density at 850°C in a matter of seconds. Conventional  
4 treatments would be at 1450 °C for 2-5 hours. Flash sintering in alumina has also been  
5 investigated with very different results <sup>17</sup>. With 120 V/cm, sintering occurred to near full  
6 density at 850°C in a matter of seconds. Conventional treatments would be at 1450 °C for 2-5  
7 hours. In pure alumina, flash sintering was not observed up to E-field strengths of 1000 V/cm  
8 <sup>18</sup>. With the addition of 0.25 wt% MgO, a typical liquid phase sintering aid, accelerated  
9 sintering occurred with the application of 500 V/cm and flash sintering observed with 1000  
10 V/cm. In the ZTA system, only 50:50 vol% (60 wt% 3YSZ) has been investigated and is the  
11 only biphasic investigation we are aware of <sup>19</sup>. It was found that the composite system shows  
12 a good flash sinterability, with the behaviour determined primarily by the zirconia phase.

13           However, the full range of zirconia-alumina ratios, especially in the biomedical range  
14 where ZTA is more useful is not investigated through FS. Flash sintering has significant  
15 potential for biomedical grade ZTA fabrication because more complex parts can be achieved  
16 compared to SPS and grain growth reduction is possible in the ZTA system, potentially  
17 eliminating the problems associated with HTA. Also, with flash sintering processing time and  
18 sintering temperatures can be reduced, thus minimising equipment demand and energy  
19 requirements.

20           The development of an effective flash sintering program is a methodical process. In flash  
21 sintering, the first thing that must be understood is the relationship between the applied E-  
22 field and its effect of the sintering temperature. Here the effect of various E-fields is  
23 investigated across a range of ZTA compositions starting with pure zirconia and increasing  
24 alumina content to the compositional range where structural ZTA applications are  
25 characterized (25ZTA) for biomedical needs. The electrical characterization is the first step  
26 towards having a basic understanding of the densification and microstructural effects of flash  
27 sintering on ZTA composites. After initial understanding of the electrical behaviour and the  
28 relationship between composition, E-field, and flash sintering temperature, more rigorous  
29 electrical controls can be implemented to produce well sintered materials. Further  
30 investigations will ensue to understand the effect of sintering treatments on grain size, HTA  
31 behaviour and mechanical properties. Such a process would have far reaching benefits in  
32 biomedical, petro-chemical and SOFC applications where HTA results in material failures  
33 and shortened lifetimes with fine grain sizes that can be exploited for HTA resistance in  
34 various applications.

## 2. Experimental:

### 2.1 Powder Preparation

Nano-ZTA powders were prepared by spray freeze drying (SFD). SFD allows for a well dispersed ZTA material with good flowability and good crushability of the produced agglomerates. First, nano-3YSZ (nominal grain size 30 nm) and nano-alumina (nominal grain size 150 nm) suspensions (MELOx Chemicals) with concentration of 22.5 wt% and 43.7 wt%, respectively, were mixed in the required amounts to achieve the desired zirconia/alumina weight ratios (Table I). Under constant stirring, the suspension pH was adjusted to 11 using tetra-methyl ammonium hydroxide (TMAH). This pH facilitates the effectiveness of the tri-ammonium citrate (TAC) dispersant. Next, 3 wt%, based on the ceramic solid content, TAC was slowly added. The dispersed suspension was then concentrated to 55 wt% by heating under constant stirring at 60°C until the correct volume was achieved. During concentration, the suspension was sonicated with a high energy sonication probe at regular intervals to break any agglomerates. Once the suspension reached the required concentration and was confirmed by drying a small sample, 3-methyl-2-butanol was added as a foaming agent. The suspension was sprayed using a Buchi Labortechnik AG twin-fluid atomiser into a liquid nitrogen bath at a rate of 3.8 l/min. The resulting powder was freeze-dried for 48-72 hr (VirTis Benchtop BTK-2 Freeze Drier). Once dried, the powder was sieved keeping the fraction between 125 µm and 250 µm for further processing.

### 2.2 Sample Preparation

The dried and sifted powders were uniaxially pressed in a 10 mm diameter die with 375 MPa to produce disks of ~3 mm thickness. To help homogenize stress gradients on the disk edges and minimize issues of delamination, samples were subsequently isopressed at 200 MPa. After pressing, organics were removed by heating to 700°C for 2 hr with heating and cooling rates of 2°C/min.

### 2.3 Flash Sintering and Characterization

For flash sintering, a thin layer of platinum paint was applied to both circular faces of the disk being measured and allowed to dry at room temperature. The disk was sandwiched between graphite sheet electrodes that were in contact with the platinum current carrying wires. The sample was heated in static air with no applied E-field to 450°C and held for at least 30 min to allow for temperature homogenization. After the soak, the voltage required to produce the desired E-field based on the starting thickness was applied and the sample heated

1 at a constant heating rate of 10 °C/min until a flash sintering event occurred as observed using  
2 a high resolution CCD camera. E-fields of 300 V/cm, 500 V/cm or 700 V/cm were applied to  
3 allow for a wider examination of the zirconia/alumina compositional range, where alumina  
4 rich materials would not sinter at the lower E-field strengths. Power supply current was  
5 limited to 1 A to operate in the current limiting regime. Current and voltage were measured  
6 by digital multimeters and the furnace temperature near the sample by a thermocouple  
7 mounted within 3 mm of the sample in the holder. After sintering, fracture surfaces were  
8 plated with gold/palladium and examined by FEG-SEM (JEOL JSM-7800F) to observe the  
9 extent of sintering.

### 11 3. Results and Discussion:

12 The power dissipation during flash sintering behaviour for the range of compositions with a  
13 fixed E-field of 300 V/cm is shown Figure 1. Power dissipation is given as volumetric  
14 dissipation  $\text{W}/\text{mm}^3$  on a logarithmic scale against the inverse temperature. In the case of pure  
15 3YSZ and high zirconia content 90ZTA samples, the power dissipation behaviour is very  
16 similar. In both compositions, with 300 V/cm applied, electrical runaway and sintering  
17 occurred at 762°C. Increasing the alumina content to 20 wt%, the sintering behaviour begins  
18 to shift, and the sintering occurred at ~20°C higher at 783°C. At the alumina rich end of the  
19 composition, 30ZTA flash sintered at 1001°C, but 25ZTA did not exhibit flash behaviour in  
20 the temperature regime investigated with 300 V/cm. The power dissipation does not continue  
21 to increase in this case and begins to taper-off above 1000 °C. This is attributed to  
22 decomposition and oxidation of the graphite electrodes at these temperatures, the limiting  
23 factor in this experimental configuration.

24 As has been observed in other materials, the onset of flash sintering occurs at a  
25 threshold power dissipation that is independent of the composition. The transitions from  
26 activated type behaviour to runaway occurred at a critical power dissipation of  $0.02 \text{ W}/\text{mm}^3$ .  
27 Below this transition, all compositions exhibit linear behaviour. These results are for  
28 measurements performed under constant E-field, meaning any change in power dissipation  
29 results were due to changes in conductivity. The slopes for all compositions are similar  
30 indicating that no significant changes in conductivity activation energy occurred. The shifts to  
31 higher temperatures for a given power density and the corresponding shift in flash sintering  
32 temperature with increasing alumina content resulted from total changes in bulk conductivity  
33 as would be expected with increases in alumina content.

1           The composition of 25ZTA is of interest because it is one of the common  
2 compositions for ZTA applications. The behaviour under three different E-fields is shown in  
3 Figure 2. By increasing the E-field strength from 300 V/cm to 500 V/cm, the change in  
4 conductivity at the higher E-field allows the onset of flash sintering at 1046°C. With 700  
5 V/cm, the flash sintering temperature decreased further to 920°C. Unlike what was found  
6 with a fixed E-field strength and variation of zirconia content, the onset power for flash  
7 decreases with increasing E-field where the critical power density for 700 V/cm is similar to  
8 the 0.02 W/mm<sup>3</sup> found before. For 500 V/cm, the transition to flash sintering is also not as  
9 clear. Again, these differences may be due to electrodes decomposition and require further  
10 investigation to see if the transition is a result of the electrode degradation or if the critical  
11 power dissipation is truly a function of E-field.

12           In this work, the emphasis was placed on finding the electrical behaviour of the  
13 material and the effect of composition. This is the first step in determining an effective flash  
14 sintering programme for any material. In these experiments, current limits were set high (2  
15 A), and times in the current controlled regime after the onset current runaway were not  
16 closely controlled. Figure 3 shows two samples of 25 ZTA sintered at 700 V/cm. These are  
17 typical sintering results regardless of compositions, E-field or temperature. In both samples,  
18 currents localized at one point where the sample surface appears blackened and cratered. The  
19 temperatures that resulted from joule heating during current runaway also resulted in melting  
20 of the ceramic phases in these regions. The localizations of current can occur in any location  
21 on the sample. The final issue is the cracking of the sample. In most cases, when the sample  
22 is removed it is broken in two or more pieces. When this breaking occurs is not clear- it may  
23 occur during the sudden heating when flash sintering is initiated, during cooling once the  
24 power supply is switched off and the sample is allowed to cool, or from differential shrinkage  
25 of areas of different density. The effects of these localized events, however, do no effect the  
26 relationship between the applied E-field and the onset of flash behaviour. If experiments are  
27 stopped at or before the shoulder of the transition right before the runaway, no sintering and  
28 no localized zones were seen.

29           The different regions associated with different extent of sintering are also observed in  
30 the microstructure. Microstructures of the fracture surfaces taken from the samples discussed  
31 above are given in Figure 4. There are under-sintered regions (Fig 4a) which occur farthest  
32 from where flash sintering started—determined by the centre of the melted region—and  
33 closest to the edges where heat losses occur at a higher rate. In these areas, only neck  
34 formation has occurred. Here, there is a clear difference in the grain size between the larger



1 alumina and smaller zirconia grains. Even though the extent of sintering is low, the fact  
2 remains that sintering has occurred at furnace temperatures much lower than would be  
3 expected by conventional methods. The majority of the sample is well sintered (Fig 4b).  
4 Grains are well formed with no evident open porosity. Sintered grains are of a similar  
5 dimension of the under-sintered grains (Fig 4a) meaning no significant grain growth had  
6 occurred during the flash sintering. The sintered grain size is less than 500 nm. Again, the  
7 alumina remains the larger grain and zirconia the smaller grain. This material is expected to  
8 be completely resistant to HTA because the YSZ grains are <100 nm. Finally, in the melted  
9 region (Fig 4c), there is a glued microstructure where there is evidence of melting with a  
10 dispersion of frozen grains in the melted matrix. A large amount of grain growth has occurred  
11 in these regions with the grain sizes of ~10  $\mu\text{m}$ .

12 Preventing the localization of sintering and melting to achieve a full density with a  
13 uniform microstructure is one of the most important and difficult tasks when flash sintering.  
14 With an understanding of the relationship between the onset of current runaway for a given  
15 ZTA composition at a given E-field and furnace temperature, better controls can be  
16 implemented to improve sintering behaviour through controlled FS. These could include  
17 limiting currents, fixing furnace temperature and applying the required E-field to the given  
18 composition, applying the E-field in different steps during heating or at a fixed temperature  
19 etc. Likewise, cooling programs may be optimised to prevent cracking of the sample. Once  
20 uniformly dense samples are achieved, more details can be extracted from the effect of flash  
21 sintering on the microstructure. The extremely fast sintering cycles can also effect yttria  
22 distribution. If the starting material has a uniform yttria distribution across the grains, the  
23 short sintering treatments and temperatures reached may not give sufficient time for  
24 segregation to occur and even grains with larger grain sizes can be made resistant to HTA.

25

#### 26 **4. Conclusions:**

27 The electrical characterization of various zirconia-toughened alumina (ZTA) compositions  
28 were examined under different E-fields to understand the relationship between ZTA  
29 composition, applied E-field, and the onset temperature of flash sintering. It was found that  
30 below 10 wt% alumina, the flash behaviour remains the same as the pure 3YSZ phase. Above  
31 this content, the onset of flash sintering temperature begins to increase with the increase in  
32 alumina content. With the setup used, 300 V/cm was able to cause flash sintering in 30 ZTA  
33 at 1000°C. Regardless of the ZTA composition, the onset of flash sintering occurs at a critical  
34 volumetric power dissipation of 0.02 W/mm<sup>3</sup>.

1 Fixing the composition at 25ZTA, at 300 V/cm flash was not achieved due to electrode  
2 limitations, but by increasing the E-field to 500 V/cm and to 700 V/cm flash sintering was  
3 possible. The flash sintering onset temperature with 700 V/cm, the highest E-field used, was  
4 just 918 °C, around 600 °C lower than conventional sintering needs.

5 A variety of microstructures were found in 25ZTA sintered with 700 V/cm. Areas where  
6 under-sintering had occurred were found at the edges of the material farthest from the starting  
7 of sintering, and melted regions with large amounts of grain growth were found in the area  
8 where sintering was localized. However, in the bulk of the sample, full dense microstructures  
9 that had no evident grain growth were achieved. Zirconia grain sizes lower than 100 nm were  
10 maintained suggesting that the material should have full HTA resistance in those regions.

11 Better control of the current and sintering conditions can be implemented further to solve  
12 the issues of localized melting and under-sintering to achieve fully dense nanostructured ZTA  
13 composites, thus paving the way for fabricating engineering components for demanding  
14 applications.

#### 16 **Acknowledgements:**

17 The authors thank the Engineering and Physical Sciences Research Council (EPSRC), UK  
18 (Nanoplants grant: EP/L024780/1) and Innovate UK for financial support.

1   References

2

3   1.    De Aza, A. H., Chevalier, J., Fantozzi, G., Schehl, M. & Torrecillas, R. Crack growth  
4        resistance of alumina, zirconia and zirconia toughened alumina ceramics for joint  
5        prostheses. *Biomaterials* **23**, 937–945 (2002).

6

7   2.    Piconi, C. & Maccauro, G. Zirconia as a ceramic biomaterial. *Biomaterials* **20**, 1–25  
8        (1999).

9

10  3.    Administration, U. S. F. and D. St. Gobain Desmarquest Zirconia Ceramic Femoral  
11        Head. (2013). at  
12        <[http://www.fda.gov/Safety/MedWatch/SafetyInformation/SafetyAlertsforHumanMedi](http://www.fda.gov/Safety/MedWatch/SafetyInformation/SafetyAlertsforHumanMedicalProducts/ucm172706.htm)  
13        calProducts/ucm172706.htm>

14

15  4.    Reece, M. & Guiu, F. Indentation Fatigue of High-Purity Alumina in Fluid  
16        Environments. *J. Am. Ceram. Soc.* **74**, 148–154 (1991).

17

18  5.    *Hydrothermal Reactions for Materials Science and Engineering.* (Springer Netherlands,  
19        1990). doi:10.1007/978-94-009-0743-0

20

21  6.    Gupta, T. K., Bechtold, J. H., Kuznicki, R. C., Cadoff, L. H. & Rossing, B. R.  
22        Stabilization of tetragonal phase in polycrystalline zirconia. *J. Mater. Sci.* **12**, 2421–  
23        2426 (1977).

24

25  7.    Paul, A., Vaidhyanathan, B. & Binner, J. G. P. Hydrothermal Aging Behavior of  
26        Nanocrystalline Y-TZP Ceramics. *J. Am. Ceram. Soc.* **94**, 2146–2152 (2011).

27

28  8.    Chevalier, J., Gremillard, L. & Deville, S. Low-Temperature Degradation of Zirconia  
29        and Implications for Biomedical Implants. *Annu. Rev. Mater. Res.* **37**, 1–32 (2007).

30

31  9.    Binner, J. & Vaidhyanathan, B. Processing of bulk nanostructured ceramics. *J. Eur.*  
32        *Ceram. Soc.* **28**, 1329–1339 (2008).

33

34  10.   Vaidhyanathan, B. & Binner, J. G. P. Novel Processing of Nanostructured Ceramics  
35        using Microwaves. in *AIChE Annual Meeting* 1419 (2004).

36

37  11.   Eichler, J., Rödel, J., Eisele, U. & Hoffman, M. Effect of Grain Size on Mechanical  
38        Properties of Submicrometer 3Y-TZP: Fracture Strength and Hydrothermal  
39        Degradation. *J. Am. Ceram. Soc.* **90**, 2830–2836 (2007).

40

41  12.   Muñoz-Saldaña, J., Balmori-Ramírez, H., Jaramillo-Vigueras, D., Iga, T. & Schneider,

- 1 G. A. Mechanical properties and low-temperature aging of tetragonal zirconia  
2 polycrystals processed by hot isostatic pressing. *J. Mater. Res.* **18**, 2415–2426 (2011).  
3
- 4 13. Guicciardi, S., Shimozono, T. & Pezzotti, G. Ageing effects on the nanoindentation  
5 response of sub-micrometric 3Y-TZP ceramics. *J. Mater. Sci.* **42**, 718–722 (2007).  
6
- 7 14. Orrù, R., Licheri, R., Locci, A. M., Cincotti, A. & Cao, G. Consolidation/synthesis of  
8 materials by electric current activated/assisted sintering. *Mater. Sci. Eng. R Reports* **63**,  
9 127–287 (2009).  
10
- 11 15. Menezes, R. R. & Kiminami, R. H. G. a. Microwave sintering of alumina–zirconia  
12 nanocomposites. *J. Mater. Process. Technol.* **203**, 513–517 (2008).  
13
- 14 16. Binner, J., Vaidhyanathan, B., Paul, A., Annaporani, K. & Raghupathy, B.  
15 Compositional Effects in Nanostructured Yttria Partially Stabilized Zirconia. *Int. J.*  
16 *Appl. Ceram. Technol.* **8**, 766–782 (2011).  
17
- 18 17. Cologna, M., Rashkova, B. & Raj, R. Flash Sintering of Nanograin Zirconia in 5 s at  
19 850°C. *J. Am. Ceram. Soc.* **93**, 3556–3559 (2010).  
20
- 21 18. Cologna, M., Francis, J. S. C. & Raj, R. Field assisted and flash sintering of alumina  
22 and its relationship to conductivity and MgO-doping. *J. Eur. Ceram. Soc.* **31**, 2827–  
23 2837 (2011).  
24
- 25 19. Naik, K., Sglavo, V. & Raj, R. Field assisted sintering of ceramic constituted by  
26 alumina and yttria stabilized zirconia. *J. Eur. Ceram. Soc.* **34**, 2435–2442 (2014).  
27  
28  
29

1 Tables and Figures:

2


3 Table I: ZTA samples prepared for flash sintering with wt% ratios and the equivalent vol%  
4 for the 3YSZ content.

Composition	wt% 3YSZ	wt% alumina	Vol% 3YSZ
3YSZ	100	0	100
90ZTA	90	10	85.6
80ZTA	80	20	72.5
30ZTA	30	70	22.0
25ZTA	25	75	18.0

5

6

1

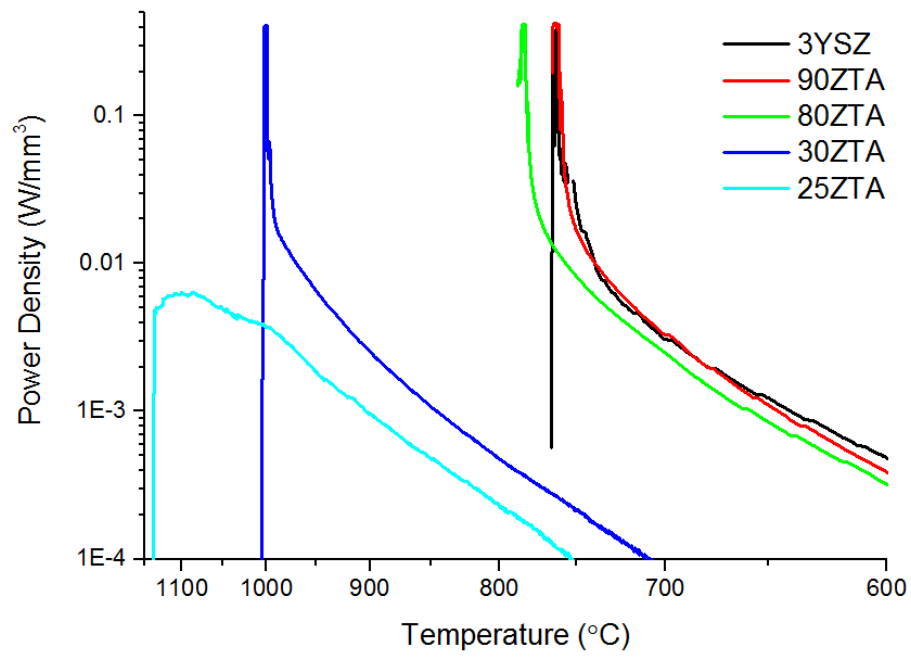


2

3

4 Figure 1: The power dissipation of the flash sintering behaviour for the range of ZTA  
5 compositions with an E-field of 300 V/cm


6

7

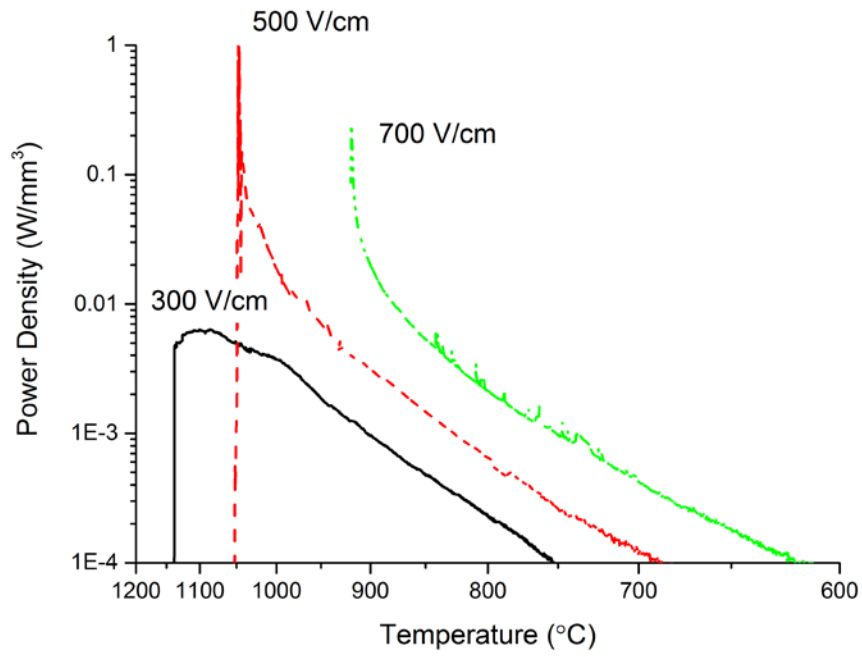

1  
2 Figure 2: Power dissipation behaviour for flash sintering of 25ZTA under different applied E-  
3 fields


4  
5

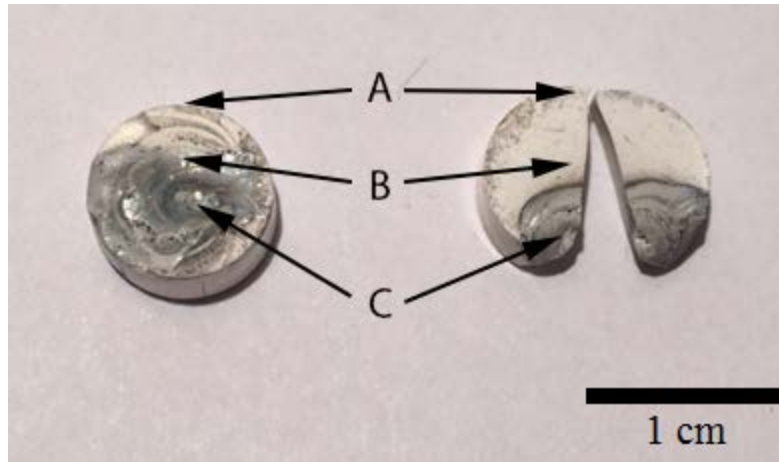

1  
2  
3  
4  
5  
6  
7  
8

Figure 3: Examples of flash sintered 25 ZTA sintered with 700 V/cm with A) under-sintered regions B) well sintered regions, and C) melted regions



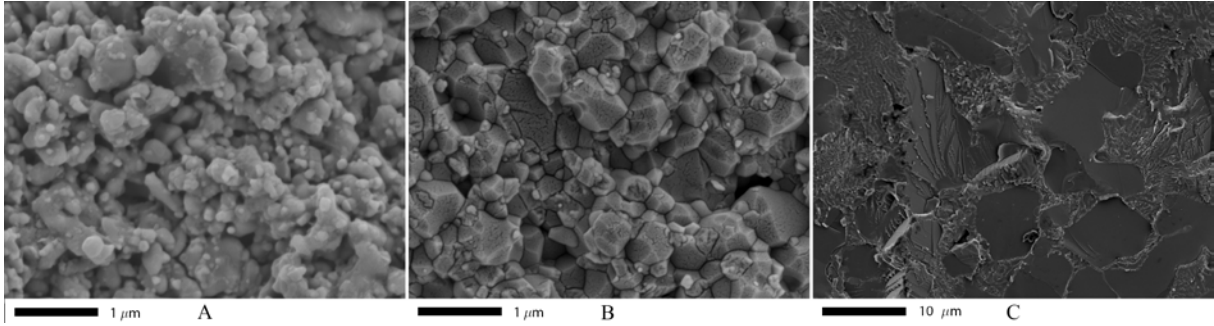

1  
2 Figure 4: Microstructures present in flash sintered 25ZTA with 700 V/cm applied. (A) under-  
3 sintered region (B) well sintered region with no grain growth, and (C) melted region with  
4 grain growth

5