

Old Dominion University
ODU Digital Commons

Engineering Technology Faculty Publications

Engineering Technology

2019

Bayesian Model Averaging Based Storage Lifetime Assessment Method for Rubber Sealing Rings

Di Liu

Shaoping Wang

Chao Zhang


Mileta M. Tomovic

Follow this and additional works at: https://digitalcommons.odu.edu/engtech_fac_pubs



Part of the [Mechanical Engineering Commons](#), and the [Structures and Materials Commons](#)

Bayesian model averaging based storage lifetime assessment method for rubber sealing rings

Advances in Mechanical Engineering
2019, Vol. 11(5) 1–13
© The Author(s) 2019
DOI: 10.1177/1687814019853351
journals.sagepub.com/home/ade


Di Liu¹ , Shaoping Wang¹, Chao Zhang¹  and Mileta M Tomovic²

Abstract

Rubber sealing ring is one of the most widely used seals. It is always stored for a period of time before put into use, especially in aeronautic and aerospace applications. It is necessary to evaluate the storage lifetime of rubber sealing rings. However, due to the long storage lifetime of rubber sealing rings, two issues need to be handled, including model uncertainty and lack of storage lifetime data. A Bayesian model averaging based storage lifetime assessment method for rubber sealing rings is proposed in this article. The Gamma distribution model and Weibull distribution model are selected as the candidate models and combined based on Bayesian model averaging method. The Bayesian model averaging method is applied to handle the model uncertainty. Considering the lack of storage lifetime data, the degradation data are utilized to give the priors of model probability and distribution parameters based on the similarity principle. The results indicate that the proposed method has smaller minus log-likelihood value and is better than the other discussed method, considering both goodness of fit and complexity.

Keywords

Model uncertainty, rubber sealing rings, storage lifetime assessment, Bayesian model averaging method, accelerated degradation tests

Date received: 14 July 2018; accepted: 3 May 2019

Handling Editor: Zhaojun Li

Introduction

Seal is one of the most important components for hydraulic system of aircraft, fuel system of aircraft, and so on.^{1,2} Furthermore, the seals are widely used in centrifugal compressors, pumps, and blowers.³ Generally, the seals are used to prevent leakage of sealed liquid. The leakage caused by failure of seal is very harmful and dangerous.⁴ Precisely, evaluating reliability and lifetime of seals is essential for improving the reliability of the systems, even the aircraft.

Several methods have been proposed to evaluate reliability and lifetime of seals. Zhou and Gu⁵ applied artificial neural networks in lifetime evaluation of mechanical seals. Leakage rate and temperature of sealing zone are selected as performance indicators. The accelerated degradation tests (ADTs) have been carried

out to obtain degradation data, which were processed based on wear equation. The artificial neural networks are trained by the processed degradation data and used to predict the residual lifetime of the mechanical seal. The simulation results show that the artificial neural networks can be used to evaluate the lifetime of mechanical seals precisely under enough experimental data conditions. Sun et al.⁶ proposed a lifetime

¹School of Automation Science and Electrical Engineering, Beihang University, Beijing, China

²Department of Engineering Technology, Old Dominion University, Norfolk, VA, USA

Corresponding author:

Chao Zhang, School of Automation Science and Electrical Engineering, Beihang University, Beijing 100083, China.
Email: czhangstar@gmail.com



Creative Commons CC BY: This article is distributed under the terms of the Creative Commons Attribution 4.0 License

(<http://www.creativecommons.org/licenses/by/4.0/>) which permits any use, reproduction and distribution of the work without

further permission provided the original work is attributed as specified on the SAGE and Open Access pages (<https://us.sagepub.com/en-us/nam/open-access-at-sage>).

evaluation method for mechanical seals based on the wear failure mechanism and fractal geometry theory. The topography parameters of sealing surface, including waviness and roughness, are used to indicate the degradation of mechanical seals. The degradation data of the mechanical seals are obtained experimentally. The relationship between the topography parameters and the degradation of mechanical seals has been obtained. The method is validated by actual mechanical seal degradation data. Zhou et al.⁷ proposed a fatigue lifetime calculation method for lip seal based on stress analysis. The method is focus on the seal failure caused by material fatigue. The rain-flow counting method is used to evaluate the fatigue lifetime of the seals. Based on the proposed method, the effects of the seal–shaft interference on the seal lifetime have been analyzed. Liu et al.⁸ proposed a vibration signal processing–based performance degradation analysis method for mechanical seals. The root mean square of vibration signal of mechanical seal is considered as the indicator of the mechanical seal performance. A wavelet filter is used to reduce noise in the vibration signal caused by cavitation. Simulation results show that the root mean square of vibration signal increases with the increasing film thickness. All above researches are focusing on evaluation and prediction of the seal service life. However, besides evaluation and prediction of service life, it is also important to evaluate the storage life of the seal.

For example, the rubber sealing ring is one of the most widely used kind of seals, as the main sealing elements and auxiliary sealing elements.^{9–12} Generally, the seals are always stored for a period of time, before put into use, especially in aeronautic and aerospace engineering.¹³ The performance of the rubber sealing rings continuously degenerates with the aging of rubber material during storage in air.¹⁴ Similar methods have been proposed in previous works^{15–18} to evaluate the storage life of rubber sealing rings. The ADTs were carried out to obtain the degradation data. The permanent compression ratio is used to indicate the degradation of the rubber sealing rings. The fitting curve function of the degradation indicator is used to extrapolate the rubber sealing ring storage lifetime. Guo and colleagues^{19,20} has studied the degradation process of rotary lip seal during storage. Based on the experimental results, it can be seen that the root mean square roughness becomes smaller during the rubber sealing rings storage and aging in oil. Furthermore, the sealing performance degrades with the decrease of the roughness, resulting in the rubber sealing rings performance degrading during storage. The storage temperature is an important factor effecting the degradation rate. The relationship between degradation rate and storage temperature can be described by the Arrhenius equation.

The similar observations are also presented in Brown and Soulagnet.²¹ Based on above researches, it can be seen that the rubber sealing rings are always kept in air and are not applied any load during storage, so the rubber aging is the only degradation factor. Hence, the storage life only depends on the storage temperature, normally the ambient temperature. Generally, the storage temperature is low, so the storage lifetime is very long.

Due to the long storage lifetime of the rubber sealing rings, it is difficult to obtain enough storage lifetime data and evaluate the storage lifetime of the seal rings precisely. Generally, the storage degradation data of the rings are more easily to be obtained compared to the lifetime data. In most cases, the ADTs are applied to obtain degradation data.²² Due to the limited understanding of the degradation mechanism, limited understanding of failure mechanism, and the lack of lifetime data, the storage lifetime distribution model of rubber sealing rings is difficult to be determined and the distribution model uncertainty issues are inevitable. However, it is difficult to find related researches on storage lifetime assessment for rubber sealing rings considering the uncertainty issue.

Generally, Akaike information criterion (AIC)²³ and Bayesian information criterion (BIC)^{24,25} can be used to select the best fitting model. However, the model selecting criterions cannot be used to handle the model uncertainty, especially for the small lifetime data conditions.²⁶ Generally, the model uncertainty can be handled by evidence theory,^{27,28} adjustment factor method,²⁹ and model averaging method.^{30,31} The model averaging method is always combined with Bayesian inference method and extended into the Bayesian model averaging (BMA) method in the reliability engineering.^{30,31} In order to access the lifetime evaluation with multi-distribution fusion, the BMA method presents the information by random variables and fuses the predicted results based on the candidate distribution possibilities.^{32–35} Liu et al.³⁶ have used BMA method to combine the candidate models, focusing on degradation process. The ability of the proposed method on the s-credibility degradation data analysis is focused. The authors argued that BMA method can handle the model uncertainty issue well. Additional researches on adapting BMA method to handle the model uncertainty can be found in Droguett and Mosleh³⁷ and Kabir et al.³⁸

Considering the handling abilities of model uncertainty and the data fusion, the BMA method is used in this article. There are some issues need to be handled in this kind of applications. One of the most important issues is how to obtain the parameter priors based on the accelerated degradation data. The main contributions of this article are as follows:

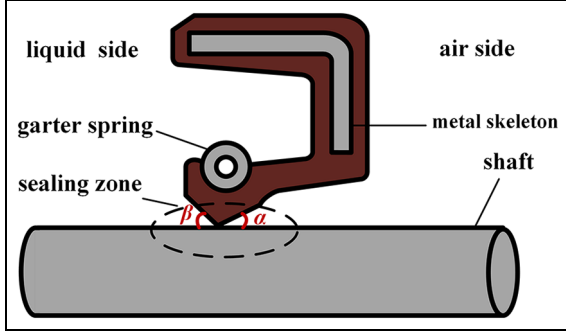


Figure 1. Schematic of typical lip seal.

1. Gamma distribution model and Weibull distribution model are selected as the candidate distribution models for rubber sealing rings storage lifetime and fused based on the BMA method.
2. Considering the lack of lifetime data, the priors of storage life distribution parameters are obtained from the degradation data based on the similarity principle, and the distribution parameters are evaluated by fully Bayesian method.

This article is organized as follows. Section “Preliminaries” preprocesses the ADT degradation data based on Arrhenius model and presents the basic knowledge of BMA method and the basic assumption. In section “The distribution model set,” the candidate distribution models are selected and the degradation data are processed. In section “The BMA-based lifetime assessment method,” the priors of distribution parameters and model probability are obtained based on the similarity principle. The storage lifetime of rubber sealing ring is evaluated based on the proposed method and the effectiveness is validated. Section “Conclusion” concludes the article.

Preliminaries

Preprocessing of the ADT degradation data

As shown in Figure 1, a typical lip seal consists of a metal frame, a spring ring, and a sealing lip. The metal frame is used to support the rubber ring, the spring ring is used to provide the pre-tightening force, and the main sealing lip is used to seal the fluid based on the reverse pumping principle.³⁹ The reverse pumping effect is based on the rough sealing lip surface and the asymmetric profile of sealing lip.⁴⁰ The reverse pumping rate is used to indicate the sealing performance. The roughness of sealing lip and the reverse pumping rate decrease during storage.⁴¹ Generally, the reverse pumping rate decreases with the decrease of the sealing lip surface roughness. The reverse pumping rate is small enough

the seal is leak. Hence, the reverse pumping rate can be used to indicate the performance of rotary lip seal during storage.

Due to the long storage lifetime of rotary lip seals, the ADT is carried out to obtain enough degradation data. Generally, because the seal rubber degradation is sensitive to temperature, temperature is selected as the accelerating factor. Normally, the relationship between the aging rate and accelerating factor can be described by failure physical models, such as Arrhenius model,⁴² Eyring model.⁴³ Furthermore, this relationship can also be described by empirical models, such as inverse power law model,^{44,45} hazard regression model.⁴⁶ The Arrhenius equation is a formula for the temperature dependence of reaction rates. Arrhenius equation gives the dependence of the rate constant of a chemical reaction on the absolute temperature. Consistently with the data source,¹⁹ the relationship between the rubber aging rate and the storage temperature is described by Arrhenius model, as

$$k = A \times \exp\left(\frac{-E}{RT}\right) \quad (1)$$

where k is the rubber aging rate, A is a constant, R is gas constant, T is storage temperature, and E is the activation energy of the seal rubber.

The relationship between degradation rate and temperature is given by

$$\frac{k_2}{k_1} = \exp\left(\frac{-E}{RT_2} - \frac{-E}{RT_1}\right) = \exp\frac{E}{R} \left(\frac{1}{T_1} - \frac{1}{T_2}\right) \quad (2)$$

where k_1 is the degradation rate under temperature T_1 and k_2 is the degradation rate under temperature T_2 .

Hence, the relationship between the storage lifetime and the storage temperature is given by

$$\frac{t_2}{t_1} = \exp\frac{E}{R} \left(\frac{1}{T_2} - \frac{1}{T_1}\right) \quad (3)$$


where t_2 is the storage lifetime under temperature T_2 and t_1 is the storage life under temperature T_1 .

The ADT degradation data presented in Guo et al.¹⁹ is used in this work. In order to obtain the relationship between storage temperature and degradation rate, the rotary lip seals were kept in storage under different temperatures until reach the specified state. The degradation time under different storage temperatures is displayed in Table 1.

In Guo et al.,¹⁹ three groups of degradation tests have been carried out on the rotary lip seals. The storage temperatures are 288, 298, and 308 K, respectively. In the presented work, the degradation test under 288 K storage temperature is considered as the degradation test under normal stress, and the degradation tests

Table 1. The degradation times under different storage temperatures.

Storage temperatures	393 K	383 K	373 K	363 K	353 K
Degradation time	1 day	2 days	3 days	7 days	13 days

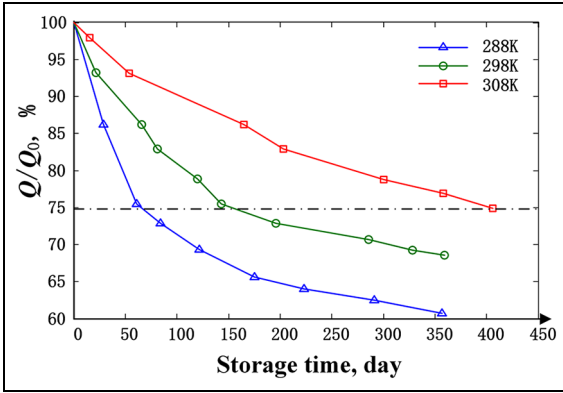**Figure 2.** The reverse pumping rates under different storage temperatures.

under 298 and 308 K storage temperatures are considered as the ADTs.

The degradation dataset is shown in Figure 2, where $Q(t)$ is the reverse pumping rate after storage time t and Q_0 is the initial reverse pumping rate. Furthermore, the failure threshold is set as 75% of the initial reverse pumping rate. It should be noted that this threshold is not the reverse pumping rate which means the seal is failure. It is the reverse pumping rate which means the reliability of the aging seal cannot meet the demand of the systems. It can be observed that the storage lifetimes of the rubber sealing rings under 308, 298, and 288 K storage temperatures are given by

$$t_1^o = 61 \text{ days}, t_2^o = 143 \text{ days}, t_3^o = 401 \text{ days} \quad (4)$$


Based on the relationship between the storage lifetime and storage temperature described in equation (3), the equivalent storage lifetimes under normal storage temperature are given by

$$t_1^E = 450 \text{ days}, t_2^E = 400 \text{ days}, t_3^E = 401 \text{ days} \quad (5)$$

The degradation indicator $q(t)$ is defined based on the reverse pumping rates, as

$$q(t) = \frac{Q_0 - Q(t)}{Q_0} \quad (6)$$

Hence, the degradations of the rotary lip seals during storage are shown in Figure 3.

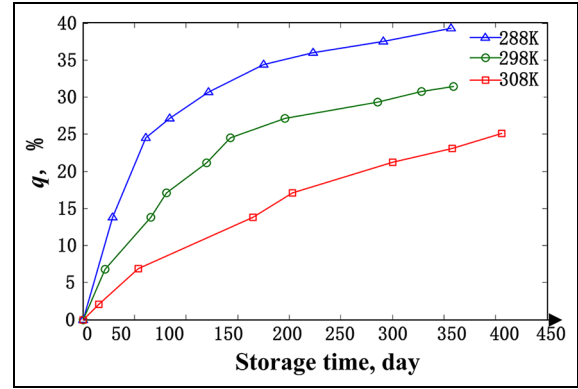**Figure 3.** The degradations of the rotary lip seals under different storage temperatures.

Basic assumption and BMA-based method

Based on the definition of failure rate in reliability engineering, it can be assumed that the failure rate curve of the tested components and the performance degradation curve are cognate curves, as equation (7). Hence, the priors of lifetime distribution shape parameters can be provided by degradation data

$$h(t) \leftrightarrow q(t) \quad (7)$$

Remark. This assumption is intuitive and reasonable based on the definition of the failure rate. Some similar assumptions can be easily found in related researches.^{47,48} The same assumption can be found in Peng.⁴⁸ Weibull distribution model is selected as the lifetime distribution model for the milling head. Considering the lack of lifetime data, the priors of storage life distribution parameters are obtained from the degradation data based on the similarity principle, and the distribution parameters are inferred by fully Bayesian method. The proposed method is demonstrated more precise and flexible for practical use than others.

Based on the above assumption, the main method of the proposed BMA-based storage life assessment method for rotary lip seals is shown in Figure 4. Because it is assumed that the failure rate curves are related to performance degradation curves, the distribution parameters are related to the degradation data. So, the priors of the distribution parameters and the

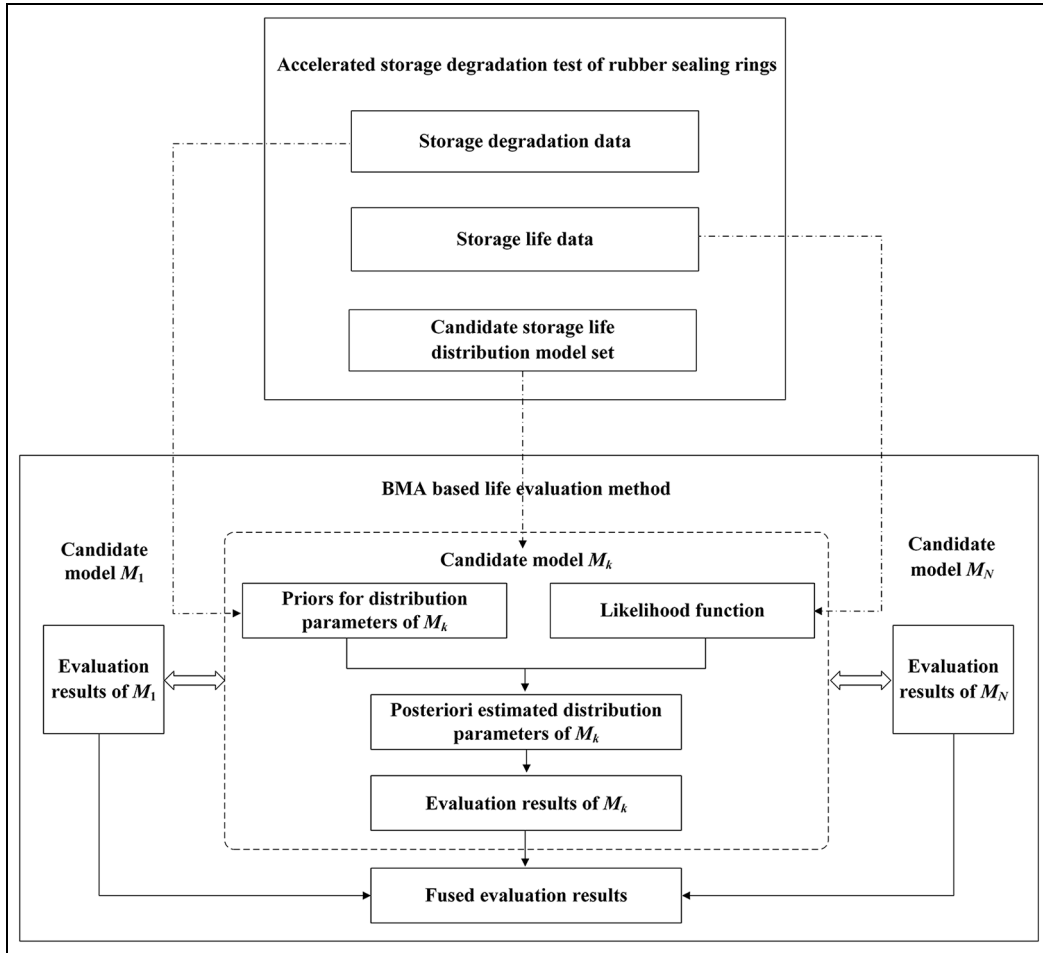


Figure 4. The proposed BMA-based storage life assessment method for rotary lip seals.

model probability can be obtained from the degradation data based on the similarity principle. Using the proposed method to evaluate the storage lifetime of rubber sealing ring, four steps need to be performed. First, the candidate models are selected based on the related engineering experience, lifetime data, and degradation data. Second, the priors of distribution parameters and model prior probability are obtained from the degradation data based on the similarity principle. Third, the distribution parameters and model probability are inferred by fully Bayesian inference method, based on the above priors and the storage lifetime data. Finally, the storage lifetime is predicted by each candidate model and fused based on the BMA method.

The distribution model set

Due to the limited understanding of the rubber sealing rings failure mechanisms, it is difficult to determine the storage lifetime distribution model based on the failure mechanism. Therefore, the BMA method is applied to

handle the model uncertainty issue, in which the predicted results from each possible distribution model are fused based on the model probabilities. Using the BMA method to evaluate the storage life of rubber sealing ring, the candidate models need to be determined first. There are several frequently used lifetime distribution models for mechanical components, such as Gaussian distribution, Gamma distribution, exponential distribution, Rayleigh distribution, Weibull distribution, general Gamma distribution, and log-normal distribution. When the shape parameter is one, the Weibull distribution becomes to be exponential distribution. When the shape parameter is two, the Weibull distribution becomes to be Rayleigh distribution. The lifetime must be positive, so the Gaussian distribution is not suitable. Considering the parameter size and the parameters meaning, scale controlling, and shape controlling, general Gamma distribution and log-normal distribution are also not suitable for this application. Hence, the Gamma distribution and Weibull distribution are selected as the candidate storage lifetime distribution models of rubber sealing rings.

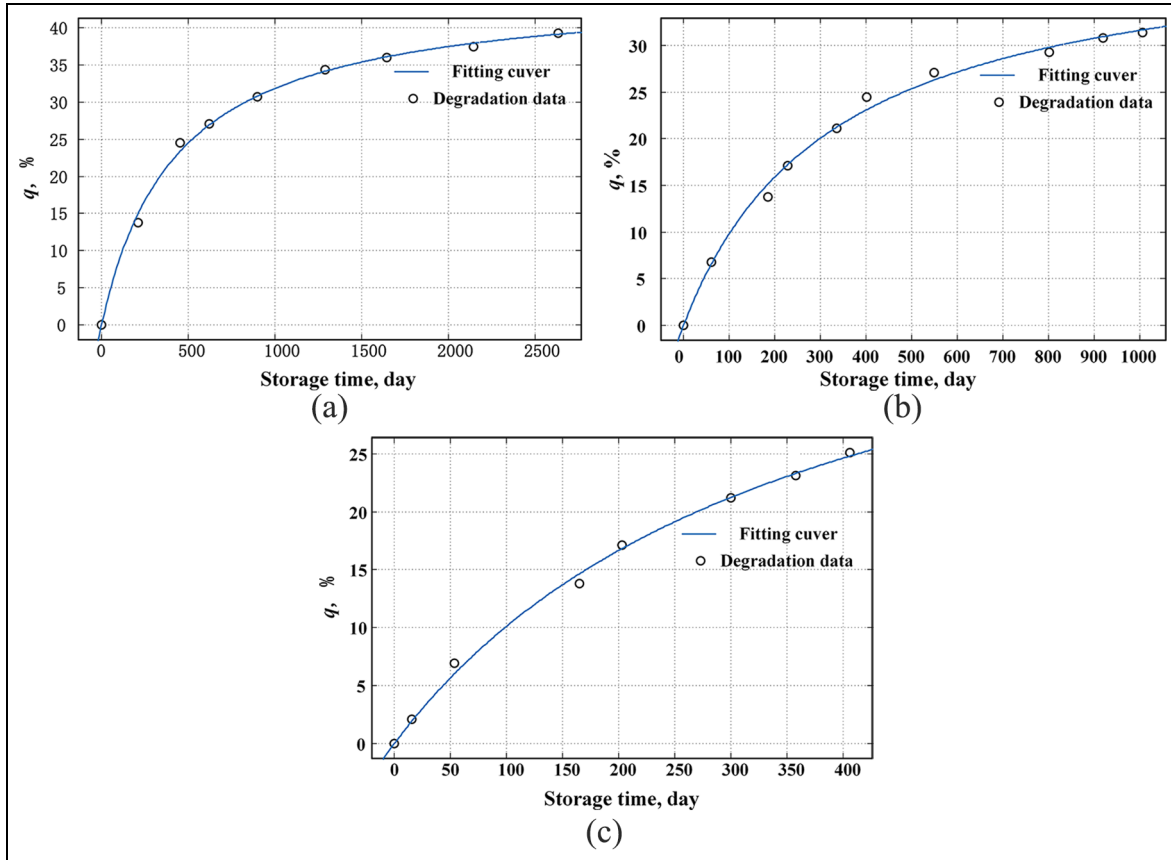


Figure 5. Fitting results of q_1 (a) under 288 K, (b) under 298 K, and (c) under 308 K.

Gamma distribution

The cumulative density function (CDF) of Gamma distribution model is given by

$$F_1(t) = \frac{\gamma^k}{\Gamma(k)} \int_0^t \tau^{k-1} \exp(-\gamma\tau) d\tau \quad (8)$$

where $\Gamma(a) = \int_0^{+\infty} x^{a-1} \exp(-x) dx$ is Gamma function, k and γ are distribution parameters of Gamma distribution model, the parameters vector of Gamma distribution $\theta_1 = [k, \gamma]$.

The probability density function (PDF) of Gamma distribution model is given by

$$f_1(t) = \frac{\gamma}{\Gamma(k)} (\gamma t)^{k-1} \exp(-\gamma t) \quad (9)$$

where f_1 is PDF of Gamma distribution model.

The failure rate function of Gamma distribution model is given by

$$h_1(t) = \frac{\gamma^k t^{k-1} \exp(-\gamma t)}{\Gamma(k) - \gamma^k \int_0^t \tau^{k-1} \exp(-\gamma\tau) d\tau} \quad (10)$$

where h_1 is the failure rate function of Gamma distribution model.

Based on the assumption, the following relationship is satisfied

$$h_1(t) \leftrightarrow q_1(t) = K_q \frac{\gamma_q^{k_q} t^{k_q-1} \exp(-\gamma_q t)}{\Gamma(k_q) - \gamma_q^{k_q} \int_0^t \tau^{k_q-1} \exp(-\gamma_q \tau) d\tau} \quad (11)$$

where q_1 is approaching curve function.

The fitting results for the tested samples are given by equations (12)–(14), and shown in Figure 5

$$q_{1,1}(t) = K_{q1} \frac{\gamma_{q1}^{k_{q1}} t^{k_{q1}-1} \exp(-\gamma_{q1} t)}{\Gamma(k_{q1}) - \gamma_{q1}^{k_{q1}} \int_0^t \tau^{k_{q1}-1} \exp(-\gamma_{q1} \tau) d\tau}$$

$$K_{q1} = 19550, \gamma_{q1} = 0.00233, k_{q1} = 1.833 \quad (12)$$

$$q_{1,2}(t) = K_{q2} \frac{\gamma_{q2}^{k_{q2}} t^{k_{q2}-1} \exp(-\gamma_{q2} t)}{\Gamma(k_{q2}) - \gamma_{q2}^{k_{q2}} \int_0^t \tau^{k_{q2}-1} \exp(-\gamma_{q2} \tau) d\tau}$$

$$K_{q2} = 19550, \gamma_{q2} = 0.00233, k_{q2} = 1.564 \quad (13)$$

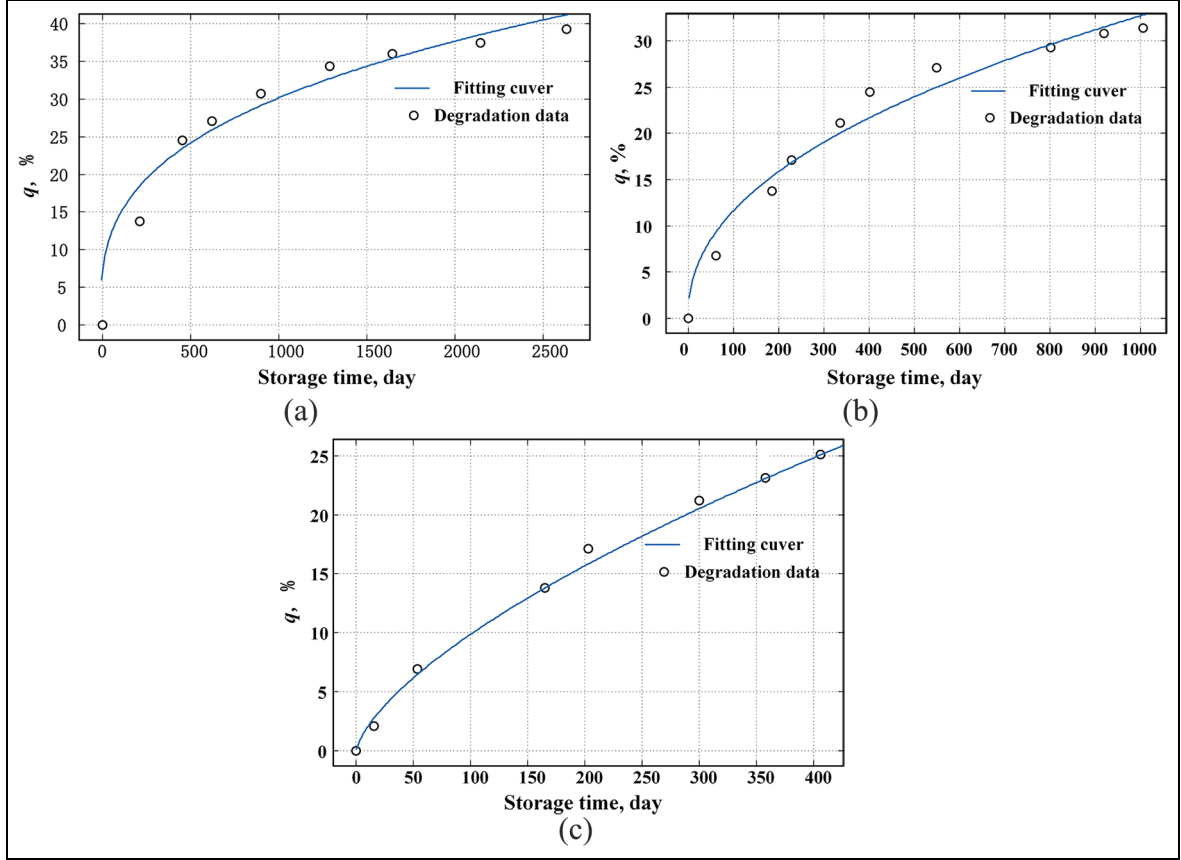


Figure 6. Fitting results of q_2 (a) under 288 K, (b) under 298 K, and (c) under 308 K.

$$q_{1,3}(t) = K_{q_3} \frac{\gamma_{q_3}^{k_{q_3}} t^{k_{q_3}-1} \exp(-\gamma_{q_3} t)}{\Gamma(k_{q_3}) - \gamma_{q_3}^{k_{q_3}} \int_0^t \tau^{k_{q_3}-1} \exp(-\gamma_{q_3} \tau) d\tau}$$

$$K_{q_3} = 19550, \gamma_{q_3} = 0.00233, k_{q_3} = 1.435 \quad (14)$$

where $q_{1,i}$ is the curve fitting function of i th tested sample; γ_{q_i} and k_{q_i} are the curve fitting parameters based on nonlinear least squares method.

Weibull distribution

The Weibull distribution is widely used in reliability engineering to describe the products lifetime distribution, especially mechanical products.^{48–50} The CDF of Weibull distribution model is given by

$$F_2(t) = 1 - \exp(-\lambda t^\beta) \quad (15)$$

where λ and β are Weibull distribution model parameters; the vector $\theta_2 = [\lambda, \beta]$.

The PDF of Weibull distribution model is given by

$$f_2(t) = \lambda \beta t^{\beta-1} \exp(-\lambda t^\beta) \quad (16)$$

where f_2 is the PDF of Weibull distribution model.

The failure rate function of Weibull distribution model is given by

$$h_2(t) = \lambda \beta t^{\beta-1} \quad (17)$$

where h_2 is the failure rate function of Weibull distribution model.

Based on the assumption, the following relationship is satisfied

$$h_2(t) \leftrightarrow q_2(t) = \lambda_q \beta_q t^{\beta_q-1} \quad (18)$$

where q_2 is approaching curve function.

The fitting results are given by equations (19)–(21) and are shown in Figure 6

$$q_{2,1}(t) = 3.1906t^{0.325} \quad \lambda_{q1} = 2.408, \beta_{q1} = 1.325 \quad (19)$$

$$q_{2,2}(t) = 1.4813t^{0.448} \quad \lambda_{q2} = 1.023, \beta_{q2} = 1.448 \quad (20)$$

$$q_{2,3}(t) = 0.5049t^{0.652} \quad \lambda_{q3} = 0.3056, \beta_{q3} = 1.652 \quad (21)$$

where $q_{2,i}$ is the curve fitting function of i th sample; λ_{q_i} and β_{q_i} are the curve fitting parameters based on nonlinear least squares method.

As shown in Figures 5 and 6, the goodness of fit of the failure rate function of Weibull distribution model

is better than that of Gamma distribution model, but we still cannot select one of them as the true model, because the difference of goodness of fits between the two candidate models is not obvious enough. Hence, the distribution uncertainty needs to be considered. The BMA method is a generalization of model averaging method by combining the model averaging method with Bayesian inference method. In order to access the lifetime evaluation with multi-distribution fusion, based on Bayesian framework, this method presents the information by random variables and fuses the predicted results based on the candidate distribution possibilities. The BMA method is used in this article to evaluate the storage lifetime of rotary lip seal due to its ability to quantify the uncertainty.

The BMA-based lifetime assessment method

Normally, degradation data and lifetime data can be obtained from degradation tests. In the presented method, the lifetime data are seemed as sample data, which directly reflect the storage lifetime of the tested samples. The degradation data are seemed as related information and used to give the priors. It should be noted that because the lifetime distribution is used to evaluate the tested samples, only the lifetime data can be used to build the likelihood function.

The fully Bayesian inference method is used to evaluate the distribution parameters, including shape and scale parameters. Using Bayesian inference method, generally, priors of the parameters can be set based on physical meaning or/and engineering experience. However, under non-prior information conditions, the non-informative prior is frequently used. Furthermore, it is common to use both informative prior and non-informative prior in one application, because the Bayesian inference can inference the sample date and the priors. Certainly, the priors are more precise; the evaluated results are more precise. To fully use the sample data, the priors of model probability and shape parameters are given based on similarity principle. However, in the presented application, it is difficult to find the information about the scale parameters. Hence, the model prior probabilities and priors of shape parameters are given based on similarity principle. The non-informative priors of scale parameters are used.

Model prior probability

As discussed above, the failure rate of the candidate distribution model is related to the curve fitting function, so it is reasonable to utilize the degradation data to give

the model prior probability. The tested degradation of the reverse pumping rates vector is expressed by \mathbf{q}_0 , as

$$\mathbf{q}_0(N) = [q_0(t_1), q_0(t_2), \dots, q_0(t_N)] \quad (22)$$

where N is tested samples size.

The predicted degradation of the reverse pumping rates vector from the fitting curve function q_k is expressed by \mathbf{q}_k , as

$$\mathbf{q}_k(N) = [q_k(t_1), q_k(t_2), \dots, q_k(t_N)] \quad (23)$$

The Euclidean distance between the tested degradation and predicted degradation from the fitting curve function is used to reflect the fitting error, as

$$d_k(N) = \frac{1}{N} \sum_{i=1}^N [q_k(t_i) - q_0(t_i)]^2 \quad (24)$$

The similarity measure, S_k , is defined as

$$S_k = \frac{1}{d_k} \quad (25)$$

Based on the similarity principle, it can be assumed that the model prior probability is positively related to the similarity measure. Hence, the model prior probability for k th candidate model $\pi(M_k)$ is given by

$$\pi(M_k) = \begin{cases} \frac{S_k}{\sum_{k=1}^{n_M} S_k} & M_k \text{ is true} \\ 0 & \text{other} \end{cases} \quad (26)$$

where n_M is the candidate model size.

The model prior probabilities for Gamma distribution model and Weibull distribution model in this application are given by equations (27) and (28)

$$\pi(M_1) = \begin{cases} 0.556 & M_1 \text{ is true} \\ 0 & \text{other} \end{cases} \quad (27)$$

$$\pi(M_2) = \begin{cases} 0.444 & M_2 \text{ is true} \\ 0 & \text{other} \end{cases} \quad (28)$$

Parameter priors

Gamma distribution. The likelihood function of Gamma distribution model is given by

$$L(t^E | \lambda, k, M_1) = \prod_{i=1}^{n_t} \frac{1}{\nu \Gamma(k)} \left(\frac{t_i^E}{\nu} \right)^{k-1} \exp\left(-\frac{t_i^E}{\nu}\right) \quad (29)$$

where $\nu = 1/\gamma$ is scale parameter of Gamma distribution model, t_i^E is storage lifetime of the i th storage temperature group, and n_t is the tested group size.

Based on the assumption, equation (11), the priors for the scale parameter of Gamma distribution model are provided from the curve fitting results of parameter k_q as

$$\pi(k) \sim \text{Normal}(E[k_q], \text{Var}[k_q]) \quad (30)$$

where

$$E[k_q] = \sum_{i=1}^{n_t} k_{q,i} \quad (31)$$

$$\text{Var}[k_q] = \frac{1}{n_t} \sum_{i=1}^{n_t} (k_{q,i} - E[k_q])^2 \quad (32)$$

The priors for the shape parameter of Gamma distribution model in the presented application are given by

$$\pi(k) \sim \text{Normal}(1.61, 0.08247) \quad (33)$$

There is no related priori information about the scale parameter ν for Gamma distribution model, so the non-informative prior is adopted to the scale parameter, equation (34). It should be noted that generally, the uniform distributions with large interval are used to describe the non-informative priors. However, the bounds of the uniform distributions are normally set based on lifetime data and/or engineering experience

$$\pi(\nu) \sim \text{Uniform}(0, 800) \quad (34)$$

Weibull distribution. The likelihood function of Weibull distribution model is given by

$$L(t^E | \eta, \beta, M_2) = \prod_{i=1}^{n_t} \beta \eta^{-\beta} t_i^{E\beta-1} \exp(-\eta^{-\beta} t_i^{E\beta}) \quad (35)$$

where $\eta = \lambda^{-1/\beta}$ is scale parameter of Weibull distribution model, t_i^E is the storage lifetime of i th storage temperature group, and n_t is the tested groups size.

Based on the assumption, equation (18), the priors for the scale parameter of Gamma distribution model are provided from the curve fitting results of parameter k_q , as

$$\pi(\beta) \sim \text{Normal}(E[\beta_q], \text{Var}[\beta_q]) \quad (36)$$

where

$$E[\beta_q] = \sum_{i=1}^{n_t} \beta_{q,i} \quad (37)$$

$$\text{Var}[\beta_q] = \frac{1}{n_t} \sum_{i=1}^{n_t} (\beta_{q,i} - E[\beta_q])^2 \quad (38)$$

The priors for the shape parameter of Weibull distribution model in the presented application are given by

$$\pi(\beta) \sim \text{Normal}(1.475, 0.086) \quad (39)$$

There is no related priori information about the scale parameter η for Weibull distribution model, so non-informative prior is adopted to the scale parameter as

$$\pi(\eta) \sim \text{Uniform}(0, 450) \quad (40)$$

Parameters estimation

The fully Bayesian inference method is used to estimate the model probabilities $p(M)$ and distribution model parameters $\boldsymbol{\theta} = (\boldsymbol{\theta}_1, \boldsymbol{\theta}_2) = (\lambda, k, \eta, \beta)$, as shown in equation (41). The system parameters are as follows: the Gamma distribution model parameter $\boldsymbol{\theta}_1 = (\lambda, k)$, the Weibull distribution model parameters $\boldsymbol{\theta}_2 = (\eta, \beta)$. The posterior distribution of the parameters and model probabilities $p(\boldsymbol{\theta}, M | t^E)$ can be obtained from equation (42), where the likelihood function is given by equation (43)

$$p(\boldsymbol{\theta}, M | t^E) = \frac{\sum_{k=1}^{n_M} L(t^E | \boldsymbol{\theta}_k, M_k) \pi(\boldsymbol{\theta}_k | M_k) \pi(M_k)}{\sum_{k=1}^{n_M} \iint_{\boldsymbol{\theta}_k} L(t^E | \boldsymbol{\theta}_k, M_k) \pi(\boldsymbol{\theta}_k | M_k) \pi(M_k) d\boldsymbol{\theta}_k} \quad (41)$$

$$p(\boldsymbol{\theta}, M | t^E) \propto L(t^E | \boldsymbol{\theta}) \pi(\boldsymbol{\theta}) \pi(M) \quad (42)$$

$$L(t^E | \boldsymbol{\theta}) = \prod_{i=1}^{n_t} \left[\frac{1}{\nu \Gamma(k)} \left(\frac{t_i^E}{\nu} \right)^{k-1} \exp\left(-\frac{t_i^E}{\nu}\right) p(M_1) + \beta \eta^{-\beta} t_i^{E\beta-1} \exp(-\eta^{-\beta} t_i^{E\beta}) p(M_2) \right] \quad (43)$$

where M_1 means the Gamma distribution model, M_2 means the Weibull distribution model, $\pi(M)$ is the priors of the model probabilities, equations (27) and (28), $\pi(\boldsymbol{\theta}_k | M_k)$ is the priors of the distribution model parameters $\boldsymbol{\theta}_k$, equations (33)–(40), $L(t^E | \boldsymbol{\theta}_k, M_k)$ is the likelihood function of model M_k , equations (29) and (35), $\{t^E\}$ is the lifetime data, and $p(\boldsymbol{\theta}, M | t_i^E)$ is the posteriors of the model probabilities and distribution model parameters.

Discussions

The posteriori estimates of the model probability and distribution model parameters are obtained based on Markov Chain Monte Carlo (MCMC) simulation method using software OpenBUGS. Generally, the Gelman–Rubin ratio can be used to indicate the

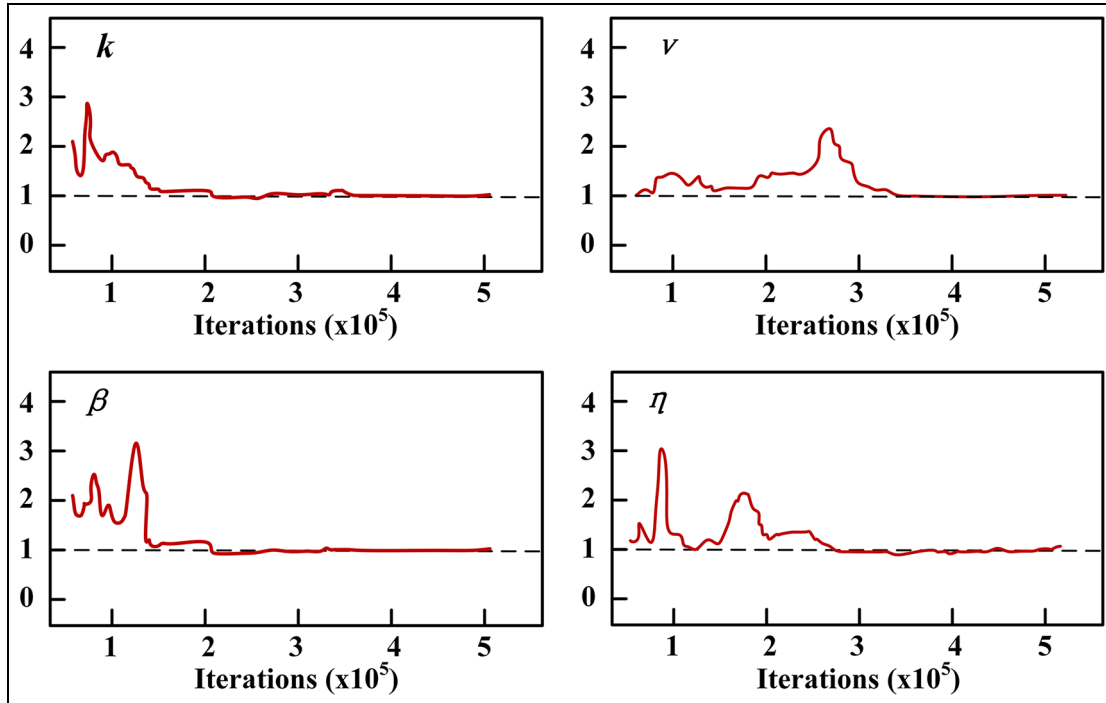


Figure 7. Gelman–Rubin ratio of k , ν , η , and β .

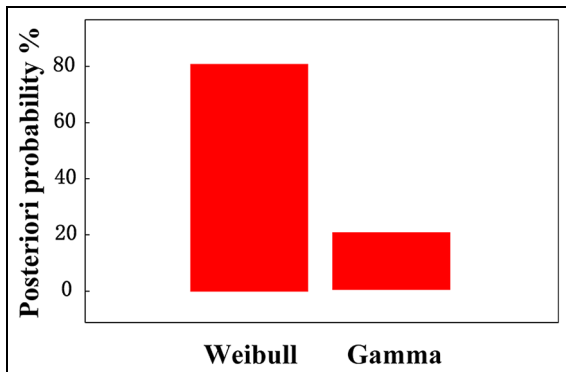


Figure 8. MCMC simulation results of the model probability.

convergence of the computation. The Gelman–Rubin ratio is closer to 1 the computation is more convergent. The plots of the Gelman-Rubin ratios of the parameters are illustrated in Figure 7, which suggest that the values of the parameters become stable and converge after about 300,000 iterations. Therefore, a total of 200,000 iterations, from 300,001 to 500,000, are selected as samples from the posterior distribution.

The posteriori estimates of the model probability are shown in Figure 8. It can be seen that both Gamma distribution model and Weibull model are possibly the storage lifetime distribution model for rubber sealing rings. Hence, it is necessary to consider the model uncertainty in storage lifetime assessment of rubber sealing rings, especially under small life data conditions.

The MCMC simulation results for the distribution parameters are displayed in Table 2. Generally, the mean values of the posterior distribution are used to estimate the distribution parameters. The unreliability of rubber sealing rings after storage t days is given by equation (44)

$$F(t) = 0.2 \times \frac{1}{73.7^{8.459} \Gamma(8.459)} \int_0^t \tau^{8.459-1} \exp\left(-\frac{\tau}{152.1}\right) d\tau + 0.8 \times (1 - 385.3^{-13.44} \exp(-t^{13.44})) \quad (44)$$

The comparisons of predicted results of different methods are displayed in Table 3. The proposed method considers the model uncertainty, so the proposed method has smaller minus log-likelihood value and is a better model considering the goodness of fit. Furthermore, the proposed method utilized the degradation data to obtain the model prior probabilities and priors of distribution model parameters, so the proposed method is more precise in predicting storage lifetime of the rubber sealing rings. It indicates that the proposed method can be more widely used in engineering practices. The prior for the compared BMA-based method is shown in Appendix 1.

Generally, the AIC and BIC are frequently used to describe the appropriateness of the model for fitting a dataset, considering both goodness of fit and complexity of the model. Furthermore, the AIC provides a criterion to estimate both the goodness of fit and

Table 2. MCMC simulation results of the distribution parameters.

Parameter	Mean	Standard deviation	Confidence interval
k	8.459	6.909	(1.662, 27.49)
ν	73.7	42.7	(4.826, 71.46)
η	385.3	97.01	(60.99, 448.0)
β	13.44	12.83	(0.04607, 37.01)

MCMC: Markov Chain Monte Carlo.

Table 3. Comparisons of the predicted results under different methods.

Method	Mean	Standard deviation	Confidence interval	Minus log-likelihood	AIC	BIC
Non-prior BMA-based method	525	350	(414, 1158)	22.7621	30.7621	25.5347
The proposed method	421	142	(309, 751)	18.7781	26.7621	29.5347

AIC: Akaike information criterion; BIC: Bayesian information criterion; BMA: Bayesian model averaging.

estimation complexity of the selected model, while the BIC not only considers these two factors but also includes the effects of the sample size. Hence, the AIC and BIC are introduced to discuss the effectiveness of different models. The definition of AIC value is $AIC = 2k - 2l(\hat{\theta})$, whereas definition of BIC value is $BIC = k \ln(mm_t) - 2l(\hat{\theta})$, where k is the number of parameters in the model, $\hat{\theta}$ represents estimated values of the parameters, n_t is tested sample size, m is the observations size of each sample, and $l(\hat{\theta})$ is the value of the log-likelihood. The calculated results for AIC and BIC values are presented in Table 3. Whether the AIC or BIC is used in model selection, the proposed method is better. The proposed model also provides flexibility for the reliability and lifetime evaluation, and it still performs well considering both the goodness of fit and complexity.

Conclusion

A BMA-based storage lifetime assessment method for rubber sealing rings is proposed in this article. Considering the model uncertainty, Gamma distribution model and Weibull distribution model are selected as the candidate lifetime distribution models and fused based on BMA method. In order to handle the lack of storage lifetime data, the degradation data are utilized to obtain the parameter priors and the model prior probability based on similarity principle. The distribution parameters are estimated by fully Bayesian method.

A storage ADTs dataset, which includes three failure samples, is used to demonstrate the effectiveness of the proposed method. It can be seen that the goodness of fit of the proposed method is better than the

compared method. An important distinguishing feature is that the predicted lifetime of the proposed method is more precise. As degradation data are used, the predictions of the proposed methods are more practicable. The further work will focus on the approach to estimate the storage lifetime of rubber sealing rings using degradation data under zero failure sample conditions.

Declaration of conflicting interests


The author(s) declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

Funding

The author(s) disclosed receipt of the following financial support for the research, authorship, and/or publication of this article: This study was co-supported by the National Natural Science Foundation of China (51620105010, 51875015, 51575019), Natural Science Foundation of Beijing Municipality (L171003), and Program 111.

ORCID iDs

Di Liu  <https://orcid.org/0000-0002-9796-9920>

Chao Zhang  <https://orcid.org/0000-0001-9054-5132>

References

- Ouyang X, Xue Z, Peng C, et al. Analysis on aircraft cylinder seal property based on mixed lubrication theory. *J Beijing Univ Aeronaut Astronaut* 2016; 42: 251–257.
- Yao L, Ma DW, Ren J, et al. Lubrication performance analysis of high-speed rod-less cylinder seal. *J Zhejiang Univ* 2017; 51: 1568–1574.

3. Jiang JB, Peng XD, Li JY, et al. Leakage and stiffness characteristics of bionic cluster spiral groove dry gas seal. *Chin J Mech Eng* 2018; 31: 21.
4. Cai RL. *Fluid sealing technology—principles and engineering applications*. Beijing, China: Chemical Industry Press, 2013, pp.20–21 (in Chinese).
5. Zhou JF and Gu BQ. Lifetime prediction of mechanical seal based on artificial neural networks. *Fluid Machine* 2006; 34: 19–23 (in Chinese).
6. Sun J, Gu B, Wei L, et al. Predicting seal life for contact mechanical seals. *J Chem Ind Eng* 2008; 59: 3095–3100 (in Chinese).
7. Zhou Q, Li ZM, Tang JP, et al. Stress analysis model and fatigue life calculation method of automotive water pump bearing seal. *J East China Univ Sci Tech* 2011; 37: 119–124 (in Chinese).
8. Liu D, Wang S and Zhang C. Performance degradation analysis of mechanical seal based on vibration signal. In: *2017 international conference on processing sensing, diagnostics, prognostics, and control (SDPC)*, Shanghai, China, 16–18 August 2017, pp.387–392. New York: IEEE.
9. Wu D, Wang S and Wang X. A novel stress distribution analytical model of O-ring seals under different properties of materials. *J Mech Sci Tech* 2017; 31: 289–296.
10. Liu D, Wang S and Zhang C. A multiscale wear simulation method for rotary lip seal under mixed lubricating conditions. *Tribol Int* 2018; 121: 190–203.
11. Peng C, Guo S, Ouyang X, et al. Mixed lubrication modeling of reciprocating seals based on a developed multiple grid method. *Tribol Trans* 2018; 61: 1151–1161.
12. Peng C, Ouyang X, Zhu Y, et al. Investigation into the influence of stretching on reciprocating rod seals based on a novel 3-D model vs axisymmetric model. *Tribol Int* 2018; 117: 1–14.
13. Peng X, Que G, Shen M, et al. State-of-the-arts on aging and tribological properties of rubber-like materials in liquid medium. *Lubricat Eng* 2018; 43: 1–11 (in Chinese).
14. Xiao K, Xiaohui GU and Peng C. Reliability evaluation of the O-type rubber sealing ring for fuse based on constant stress accelerated degradation testing. *J Mech Eng* 2014; 50: 62 (in Chinese).
15. Xie HY, Xun WU, Liu CM, et al. Analysis and prediction of on-missile storage life of silicone-rubber sealing material. *Equip Environ Eng* 2011; 8: 15–19 (in Chinese).
16. Zhou Y, Zhou K, Ma HY, et al. Prediction of storage life of silicone-rubber sealing material. *Equip Environ Eng* 2010; 7: 65–70 (in Chinese).
17. Zhou K, Luo TY and Zhang LW. Prediction techniques for storage life of missiles. *Metal Form Tech* 2005; 2: 4–6 (in Chinese).
18. Liu W and He G. Storage life of silicone rubber sealing ring used in solid rocket motor. *Chin J Aeronaut* 2014; 27: 1469–1476.
19. Guo F, Jia X, Huang L, et al. The effect of aging during storage on the performance of a radial lip seal. *Polym Degradat Stabil* 2013; 98: 2193–2200.
20. Guo F, Jia X, Lv M, et al. The effect of aging in oil on the performance of a radial lip seal. *Tribol Int* 2014; 78: 187–194.
21. Brown RP and Soulagnet G. Microhardness profiles on aged rubber compounds. *Polym Test* 2001; 20: 295–303.
22. Nelson WB. *Accelerated testing: statistical models, test plans, and data analysis*. New York: John Wiley & Sons, 2009.
23. Sugiura N. Further analysis of the data by Akaike's information criterion and the finite corrections. *Commun Stat Theory Methods* 1978; 7: 13–26.
24. Park C and Padgett WJ. Stochastic degradation models with several accelerating variables. *IEEE Trans Reliabil* 2006; 55: 379–390.
25. Park C and Padgett WJ. Accelerated degradation models for failure based on geometric Brownian motion and Gamma processes. *Lifetime Data Anal* 2005; 11: 511–527.
26. Zio E. Some challenges and opportunities in reliability engineering. *IEEE Trans Reliabil* 2016; 99: 1–14.
27. Park I and Grandhi RV. Quantification of model-form and parametric uncertainty using evidence theory. *Struct Saf* 2012; 39: 44–51.
28. Riley ME. Evidence-based quantification of uncertainties induced via simulation-based modeling. *Reliab Eng Syst Saf* 2015; 133: 79–86.
29. Zio E and Apostolakis GE. Two methods for the structured assessment of model uncertainty by experts in performance assessments of radioactive waste repositories. *Reliabil Eng Syst Safety* 1996; 54: 225–241.
30. Hoeting JA, Madigan D, Raftery AE, et al. Bayesian model averaging: a tutorial. *Statistical Science* 1999; 14: 382–401.
31. Kabir G, Tesfamariam S and Sadiq R. Predicting water main failures using Bayesian model averaging and survival modelling approach. *Reliabil Eng Syst Safety* 2015; 142: 498–514.
32. Draper D. Assessment and propagation of model uncertainty. *J Roy Statist Soc* 1995; 57: 45–97.
33. Adrian ER, David M and Hoeting JA. Bayesian model averaging for linear regression models. *J Am Statist Assoc* 1997; 92: 179–191.
34. Raftery AE, Gneiting T, Balabdaoui F, et al. Using Bayesian model averaging to calibrate forecast ensembles. *Month Weather Rev* 2005; 133: 1155–1174.
35. Park I and Grandhi RV. A Bayesian statistical method for quantifying model form uncertainty and two model combination methods. *Rel Eng Syst Safety* 2014; 129: 46–56.
36. Liu L, Li XY, Zio E, et al. Model uncertainty in accelerated degradation testing analysis. *IEEE Trans Reliabil* 2017; 99: 1–13.
37. Droguett EL and Mosleh A. Bayesian methodology for model uncertainty using model performance data. *Risk Analysis* 2008; 28: 1457–1476.
38. Kabir G, Tesfamariam S and Sadiq R. Predicting water main failures using Bayesian model averaging and survival modelling approach. *Reliabil Eng System Safety* 2015; 142: 498–514.
39. Müller HK. Concepts of sealing mechanism of rubber lip type rotary shaft seals. In: Nau BS (ed.) *Proceedings of the 11th international conference on fluid sealing*. London: Elsevier, 1987, pp.698–709.

40. Rocke AH and Salant RF. Elastohydrodynamic analysis of a rotary lip seal using flow factors. *Tribol Trans* 2005; 48: 308–316.
41. Guo F, Jia X, Suo S, et al. A mixed lubrication model of a rotary lip seal using flow factors. *Tribol Int* 2013; 57: 195–201.
42. Nelson W. Analysis of accelerated life test data-part I: the Arrhenius model and graphical methods. *IEEE Trans Electr Insulat* 1971; 4: 165–181.
43. Endicott H, Hatch B and Sohmer R. Application of the Eyring model to capacitor aging data. *IEEE Trans Component Parts* 1965; 12: 34–41.
44. Wang Y, Zhou B, Ge T, et al. Small-sample accelerated life test method based on the Inverse Power Law Model. *Appl Math* 2014; 8: 1725–1730.
45. Meeker WQ and Escobar LA. *Analyzing accelerated life test data*. Hoboken, NJ: John Wiley & Sons, 1998.
46. Elsayed EA, Liao HT and Wang XD. An extended linear hazard regression model with application to time-dependent dielectric breakdown of thermal oxides. *IIE Trans* 2006; 38: 329–340.
47. Wang L, Pan R, Li X, et al. A Bayesian reliability evaluation method with integrated accelerated degradation testing and field information. *Reliabil Eng System Safety* 2013; 112: 38–47.
48. Peng W. Bayesian information fusion method for reliability assessment of milling head. *Chin J Mech Eng* 2014; 50: 185–191 (in Chinese).
49. Meng XP, Zhao CQ and Huo L. Maximum likelihood method for parameter estimation of Weibull Distribution Model based on fruit fly optimization algorithm. *Appl Mech Mater* 2014; 602: 3508–3511.
50. Xu H, Hu WM and Sun P. Equipment reliability prediction based on dual-parametric Weibull distribution. *Chin J Mech Eng* 2013; 11:112–116 (in Chinese).

Appendix I

The non-information priors of compared BMA-based method are given as follows. The priors for the shape parameter of Gamma distribution model are given by

$$\pi(k) \sim \text{Uniform}(0, 10) \quad (45)$$

The priors for the scale parameter of Gamma distribution model are given by

$$\pi(\nu) \sim \text{Uniform}(0, 800) \quad (46)$$

The priors for the shape parameter of Weibull distribution model are given by

$$\pi(\beta) \sim \text{Uniform}(0, 100) \quad (47)$$

The priors for the scale parameter of Weibull distribution model are given by

$$\pi(\eta) \sim \text{Uniform}(0, 450) \quad (48)$$

The model prior probabilities for Gamma distribution model and Weibull distribution model are given by

$$\pi(M_1) = \begin{cases} 0.5 & M_1 \text{ is true} \\ 0 & \text{other} \end{cases} \quad (49)$$

$$\pi(M_2) = \begin{cases} 0.5 & M_2 \text{ is true} \\ 0 & \text{other} \end{cases} \quad (50)$$