



# THE UNIVERSITY *of* EDINBURGH

## Edinburgh Research Explorer

### Triplet Dimerization Crossover Driven By Magnetic Frustration in In<sub>2</sub>VO<sub>5</sub>

**Citation for published version:**

Kimber, SAJ, de Vries, MA, Sanchez-Benitez, J, Kamenev, K & Attfield, JP 2008, 'Triplet Dimerization Crossover Driven By Magnetic Frustration in In<sub>2</sub>VO<sub>5</sub>' Physical Review B, vol. 77, 014428. DOI: 10.1103/PhysRevB.77.014428

**Digital Object Identifier (DOI):**

[10.1103/PhysRevB.77.014428](https://doi.org/10.1103/PhysRevB.77.014428)

**Link:**

[Link to publication record in Edinburgh Research Explorer](#)

**Document Version:**

Publisher's PDF, also known as Version of record

**Published In:**

Physical Review B

**Publisher Rights Statement:**

Copyright C 2008 by the American Physical Society. This article may be downloaded for personal use only. Any other use requires prior permission of the author(s) and the American Physical Society.

**General rights**

Copyright for the publications made accessible via the Edinburgh Research Explorer is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

The University of Edinburgh has made every reasonable effort to ensure that Edinburgh Research Explorer content complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [openaccess@ed.ac.uk](mailto:openaccess@ed.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.



## Triplet dimerization crossover driven by magnetic frustration in $\text{In}_2\text{VO}_5$

Simon A. J. Kimber,<sup>1,2</sup> Mark A. de Vries,<sup>1,2</sup> Javier Sanchez-Benitez,<sup>1,3</sup> Konstantin V. Kamenev,<sup>1,3</sup> and J. Paul Attfield<sup>1,2</sup>  
<sup>1</sup>Centre for Science at Extreme Conditions, University of Edinburgh, Erskine Williamson Building, King's Buildings, Mayfield Road,  
 Edinburgh EH9 3JZ, United Kingdom

<sup>2</sup>School of Chemistry, University of Edinburgh, Joseph Black Building, King's Buildings, West Mains Road,  
 Edinburgh EH9 3JJ, United Kingdom

<sup>3</sup>School of Engineering and Electronics, University of Edinburgh, King's Buildings, Mayfield Road,  
 Edinburgh EH9 3JL, United Kingdom

(Received 20 November 2007; published 22 January 2008)

$\text{In}_2\text{VO}_5$ , containing magnetically frustrated zigzag chains, shows a remarkable crossover at 120 K between paramagnetic states with positive (17 K) and negative (−70 K) Weiss temperatures. Magnetic moment and entropy data show that the  $\text{V}^{4+}$   $S=1/2$  spins condense into  $S=1$  triplet dimers below the crossover. A further freezing of the antiferromagnetically coupled triplet dimers into a global singlet state is observed at 2.5 K, with no long range magnetic order down to 0.42 K and in fields up to 9 T. No structural V-V dimerization is observed by high-resolution synchrotron x-ray diffraction down to 10 K, but a subtle lattice anomaly evidences a spin-lattice coupling in the triplet dimer state. This is assigned to longitudinal oxygen displacement modes that reduce frustration within the chains and so couple to the spin dimer fluctuations.

DOI: 10.1103/PhysRevB.77.014428

PACS number(s): 75.10.Pq, 61.50.Ks, 75.30.Wx

### I. INTRODUCTION

The properties of low dimensional quantum magnets have been studied extensively, in particular, the one-dimensional antiferromagnetic (AF)  $S=1/2$  chain, for which the susceptibility has been calculated to very high accuracy.<sup>1</sup> The addition of a next nearest neighbor, frustrating, AF exchange interaction ( $J_2$ ) produces an array of exotic instabilities and ground states; this model is realized by the zigzag chain shown in Fig. 1. The much studied case with  $J_1, J_2 > 0$  (AF-AF) is unstable with respect to a singlet dimerized state with a spin gap when the ratio  $\alpha = |J_2/J_1| > 0.2411$ ,<sup>2,3</sup> as exemplified by the spin-Peierls material  $\text{CuGeO}_3$ .<sup>4</sup> The zigzag chain with ferromagnetic  $J_1$  and antiferromagnetic  $J_2$  (F-AF) couplings has been less studied; however, recent work has shed new light on the phase diagram and thermodynamics of this model. The ground state is reported to be ferromagnetic for  $0 \leq \alpha \leq 1/4$  and an antiferromagnetic helix for  $\alpha > 1/4$ ,<sup>5-7</sup> which has been realized in several materials containing  $S=1/2$   $\text{Cu}^{2+}$ .<sup>8-10</sup>

In this paper, we report magnetic susceptibility, resistivity, heat capacity, synchrotron powder x-ray, and powder neutron diffraction results for  $\text{In}_2\text{VO}_5$ . These reveal a spin dimerization instability in an F-AF  $S=1/2$  zigzag chain. Below 120 K,  $\text{In}_2\text{VO}_5$  behaves as an unfrustrated chain of antiferromagnetically coupled  $S=1$  triplet dimers which show a further condensation into a global singlet ground state at 2.5 K.  $\text{In}_2\text{VO}_5$  has an orthorhombic structure (space group  $Pnma$ ) consisting of edge-sharing  $\text{VO}_6$  chains along the  $\mathbf{b}$  axis, separated by sheets of diamagnetic  $\text{InO}_6$  octahedra.<sup>11</sup> Two recent theoretical papers investigated magnetic exchange in  $\text{In}_2\text{VO}_5$  (Ref. 12) and reported contradictory results of frustrated antiferromagnetic or ferromagnetic exchange interactions, prompting the present experimental study.<sup>13</sup>

### II. SAMPLE PREPARATION

A high purity sample of  $\text{In}_2\text{VO}_5$  was prepared by grinding small single crystals, grown by the previously reported

method.<sup>11</sup> Our samples are black, and resistivity measurements between 350 and 150 K (below which the sample resistance was too high to be measured) showed  $\text{In}_2\text{VO}_5$  to be semiconducting with a 300 K resistivity of  $3.2 \Omega \text{ cm}$  and a band gap of 170 meV.

### III. MAGNETIC MEASUREMENTS

The magnetic susceptibility of  $\text{In}_2\text{VO}_5$ , measured with a Quantum Design magnetic property measurement system in a 150 Oe field, and the inverse susceptibility are shown in Fig. 2. Two distinct linear regions are seen in the inverse susceptibility with a crossover at 120 K. A Curie-Weiss fit in the range of 140–300 K gives a Weiss temperature of  $\Theta = 17$  K, and a moment of  $1.81 \mu_B$ , consistent with an  $S=1/2$  system with  $g=2.09$ . Below 120 K, the Weiss tempera-

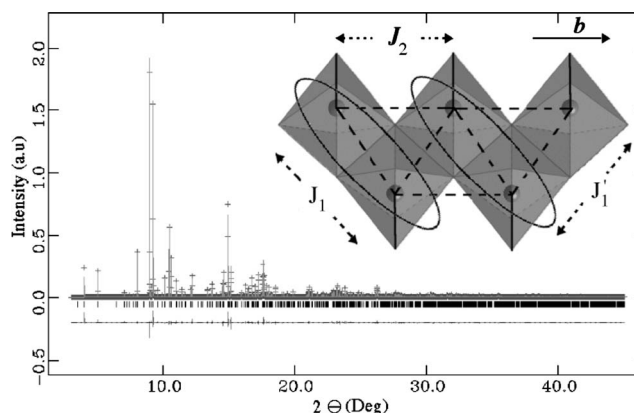


FIG. 1. Observed, calculated, and difference plots for the Rietveld fit to the synchrotron x-ray diffraction profile of  $\text{In}_2\text{VO}_5$  at 10 K. The inset shows the zigzag chain arrangement of  $\text{VO}_6$  octahedra with the magnetic exchange interactions and the triplet dimers formed below 120 K, as indicated. The short V-O bonds perpendicular to the chain direction are shown as solid lines.

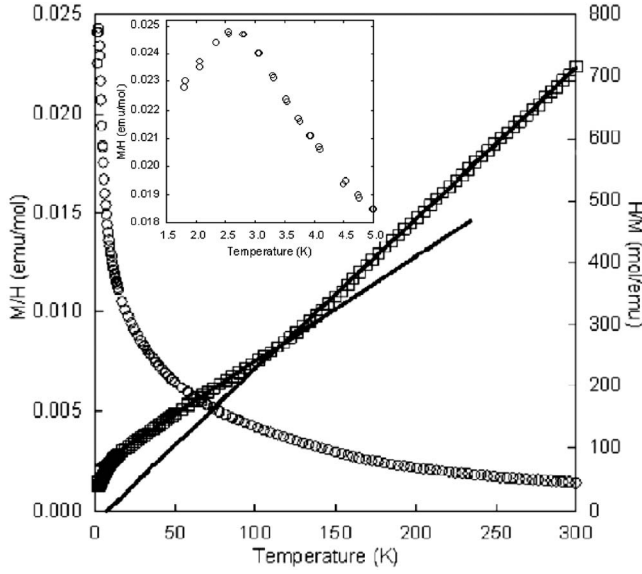


FIG. 2. Magnetic susceptibility of  $\text{In}_2\text{VO}_5$  measured in a 150 Oe field and the inverse susceptibility with Curie-Weiss fits above and below the 120 K crossover shown. The inset shows the low temperature susceptibility maximum in zero field and field cooled measurements.

ture changes sign ( $\Theta = -70$  K) and the paramagnetic moment increases to  $2.2\mu_B$ . A crossover between positive and negative  $\Theta$  regimes is very unusual, and it could signify a transition at which the structure and hence the exchange pathways are significantly altered, but this is ruled out by the diffraction results below. Our alternative explanation, which is supported by the heat capacity measurements, is that the zigzag  $S=1/2$  chains in  $\text{In}_2\text{VO}_5$  undergo a crossover into a chain of triplet dimers, as shown in Fig. 1. This is a plausible ground state for the F-AF zigzag chain with  $\alpha \sim 1$ .<sup>14</sup> The paramagnetic moment of  $2.1\mu_B$  calculated for the triplet ( $S=1$ ) dimerized state, with  $g=2.09$ , is in good agreement with the observed value of  $2.2\mu_B$  below the 120 K crossover.

#### IV. STRUCTURAL STUDIES

To determine whether  $\text{In}_2\text{VO}_5$  undergoes a structural transition at 120 K, synchrotron powder x-ray diffraction data

were collected at temperatures of 10–280 K with wavelength  $\lambda=0.45621$  Å, using the high-resolution instrument ID31 at the ESRF, Grenoble, and a 10 K neutron profile was also recorded using the Super-D2B diffractometer ( $\lambda=1.594$  Å) at the ILL, Grenoble. The data were fitted well by Rietveld refinements, starting from the previously reported 300 K  $Pnma$  structure<sup>15</sup> using the GSAS suite of programs.<sup>16,17</sup>

No superstructure is observed for  $\text{In}_2\text{VO}_5$  between 10 and 280 K, and the coordinates from the combined x-ray and neutron refinement at 10 K (Table I) confirm that no gross structural transition (e.g., V-V dimerization) occurs. The lattice parameters are shown in Table II. The  $a$  and  $c$  parameters and the volume do not show a clear 120 K anomaly. However,  $b$  goes through a minimum at this temperature (Fig. 3), evidencing a coupling between the lattice and the magnetic crossovers. Within error, no significant change to the atomic coordinates, and hence to the bond angles that influence the exchange pathways, is observed around the 120 K crossover. The lattice microstrain parallel to  $b$ ,  $s_{\parallel}[010]$ , which quantifies local variations in the axis length, is larger than the perpendicular component and increases on cooling below 300 K but then decreases at low temperatures [Fig. 3(b)]. This is consistent with a more highly correlated spin state if spin-lattice coupling is significant.

#### V. HEAT CAPACITY MEASUREMENTS

The heat capacities ( $C_p$ ) of  $\text{In}_2\text{VO}_5$  and the diamagnetic analog  $\text{In}_2\text{TiO}_5$  were measured using a Quantum Design physical property measurement system and are plotted in Fig. 4. A  $C_p/T$  peak is seen at 5 K for  $\text{In}_2\text{VO}_5$  and a broad feature is also observed around 120 K. The magnetic heat capacity of  $\text{In}_2\text{VO}_5$  was estimated by subtracting the  $\text{In}_2\text{TiO}_5$  data and the resulting  $C_p(\text{mag})/T$  and magnetic entropy  $S_{\text{mag}}$  are also shown. Two magnetic entropy releases are observed. On warming up to  $\sim 100$  K, the entropy tends toward the  $1/2R \ln 3 \approx 4.5$  J/mol K value expected for  $1/2$  mole of  $S=1$  dimers. Above 120 K, an additional contribution increases the total magnetic entropy to approximately the  $R \ln 2 \approx 5.8$  J/mol K value for the monomeric  $S=1/2$  state. Hence, the magnetic heat capacity variation for  $\text{In}_2\text{VO}_5$  con-

TABLE I. Refined coordinates and components of the anisotropic thermal  $U$ -tensor ( $\text{\AA}^2$ ) from the combined x-ray and neutron refinement of the  $\text{In}_2\text{VO}_5$  structure at 10 K in space group  $Pnma$ . Atoms In(1), V, O(1), O(2), and O(3) are at  $(x, 1/4, z)$ , and In(2), O(4), and O(5) are at  $(x, 3/4, z)$ .

Atom	$x$	$z$	$U_{11}$	$U_{22}$	$U_{33}$	$U_{13}$
In(1)	0.0979(5)	0.08391(2)	0.0024(2)	0.0006(2)	0.0009(1)	-0.0015(1)
In(2)	0.32998(5)	0.23758(2)	0.0028(1)	0.0020(2)	0.0025(1)	-0.0019(1)
V	0.1096(1)	0.42345(6)	0.0023(3)	0.0026(4)	0.0027(3)	-0.0010(3)
O(1)	0.2406(4)	0.3224(2)	0.008(1)	0.006(2)	0.001(1)	0.000(1)
O(2)	0.3457(4)	0.4959(1)	0.004(1)	0.007(2)	0.001(1)	0.000(1)
O(3)	0.3699(3)	0.1504(2)	0.002(1)	0.003(2)	0.003(1)	-0.001(1)
O(4)	0.0602(3)	0.1770(2)	0.002(1)	0.003(2)	0.002(1)	0.000(1)
O(5)	0.0687(4)	0.4515(2)	0.008(2)	0.003(2)	0.006(1)	0.000(1)

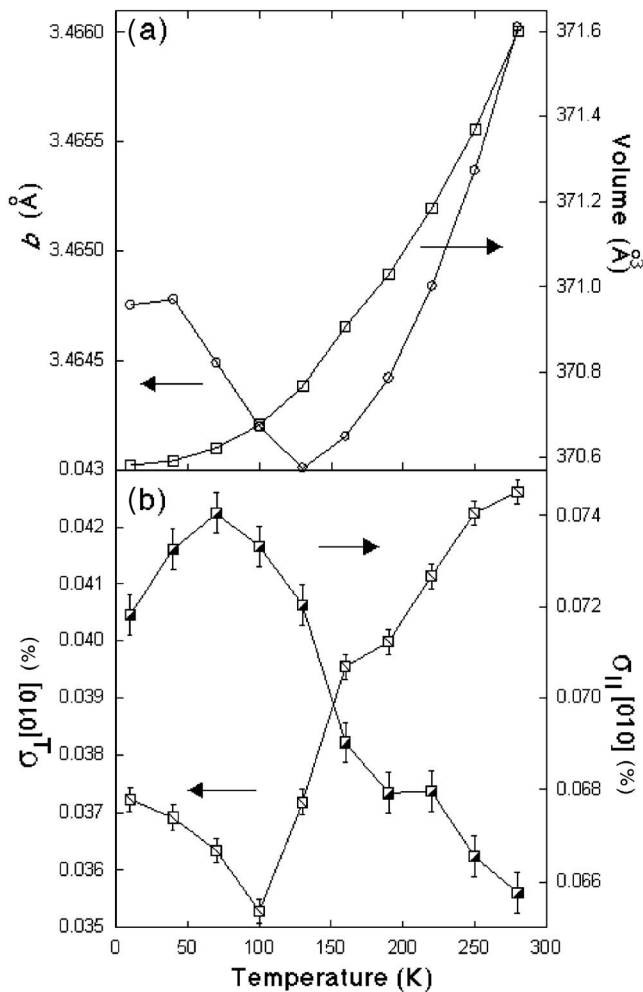


FIG. 3. Temperature evolution of (a) the  $b$ -axis length and cell volume and (b) the lattice microstrains parallel and perpendicular to [010] from the high-resolution synchrotron x-ray diffraction study of  $\text{In}_2\text{VO}_5$ .

firmly the triplet dimerization model proposed above.

A separate magnetic freezing transition below 5 K is evidenced in the low temperature magnetic susceptibility and

TABLE II. Lattice parameters for  $\text{In}_2\text{VO}_5$  at temperatures between 10 and 280 K.

$T$ (K)	$a$ (Å)	$b$ (Å)	$c$ (Å)	Volume (Å <sup>3</sup> )
10	7.2252(1)	3.46475(6)	14.8034(2)	370.583(1)
40	7.2252(1)	3.46478(6)	14.8038(2)	370.593(1)
70	7.2251(1)	3.46449(6)	14.8064(2)	370.623(1)
100	7.2253(1)	3.46420(6)	14.8094(2)	370.677(1)
130	7.2255(1)	3.46401(6)	14.8133(2)	370.767(1)
160	7.2260(1)	3.46415(6)	14.8173(2)	370.907(1)
190	7.2264(1)	3.46442(6)	14.8202(2)	371.029(1)
220	7.2271(1)	3.46484(6)	14.8233(2)	371.185(1)
250	7.2279(1)	3.46542(6)	14.8267(2)	371.370(1)
280	7.2291(1)	3.46602(6)	14.8307(2)	371.600(1)

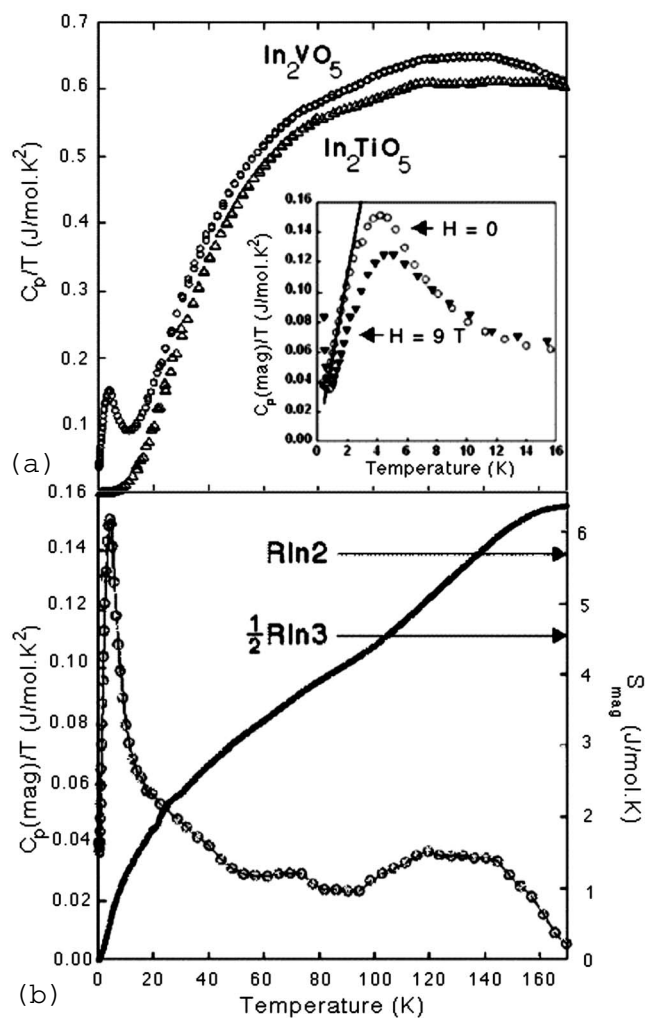


FIG. 4. Heat capacity data for  $\text{In}_2\text{VO}_5$  at low temperatures. (a) Measured heat capacities for  $\text{In}_2\text{VO}_5$  and  $\text{In}_2\text{TiO}_5$  plotted as  $C_p/T$ . The inset shows the magnetic part of the heat capacity of  $\text{In}_2\text{VO}_5$  measured in 0 and 9 T fields, with a power law fit to the zero field data below 2 K. (The upturn in the 9 T data is due to a trace of paramagnetic impurity.) (b) Magnetic heat capacity [shown as  $C_p(\text{mag})/T$ ] and the integrated entropy for  $\text{In}_2\text{VO}_5$ , showing the expected limits for triplet dimer ( $1/2 R \ln 3$ ) and  $S=1/2$  monomer ( $R \ln 2$ ) states.

heat capacity measurements. The broad magnetic susceptibility maximum at 2.5 K (Fig. 2, inset) shows that the global magnetic ground state of  $\text{In}_2\text{VO}_5$  is a spin singlet, as expected for an antiferromagnetic  $S=1$  chain.  $C_p(\text{mag})/T$  also shows a shoulder around 4 K [Fig. 4(a), inset], which decreases slightly in magnitude and moves to higher temperature in a 9 T field. The breadth of this peak and its robustness to a 9 T field show that it does not signify a long range magnetic ordering transition. (For long range order, a field estimated as  $k_B T_{\text{peak}} / g \mu_B \approx 4$  T would be sufficient to suppress the peak.) We have also collected high intensity neutron powder diffraction data, using ILL instrument D20, which show no evidence for long range magnetic order down to 1.7 K (Fig. 5). The heat capacity shows a power law scaling,  $C_p(\text{mag}) \sim T^{1.89(2)}$ , between 0.42 and 2 K. Linear scaling is expected for a truly one-dimensional system, but similar

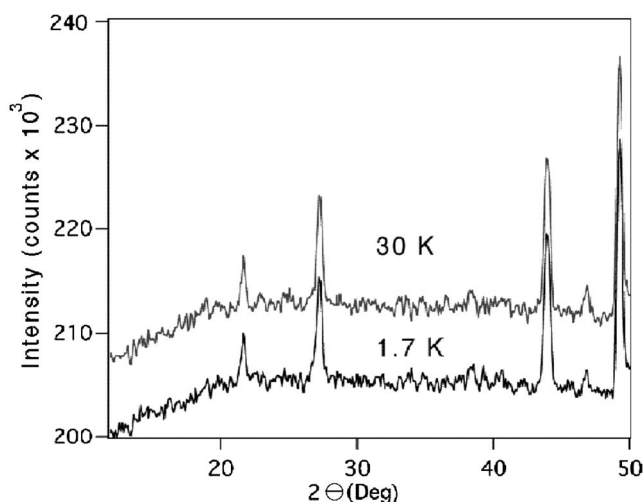


FIG. 5. Low angle region of neutron powder diffraction patterns for  $\text{In}_2\text{VO}_5$  at 30 and 1.7 K ( $\lambda=2.42$  Å), showing no additional peaks to evidence long range spin order below the 5 K magnetic transition.

values of 1.7–1.8 are reported in several quasi-one-dimensional systems (see footnote 21 in Ref. 10).

## VI. DISCUSSION

The  $S=1$  dimer chain is one of the ground states predicted by the F-AF alternating Heisenberg  $S=1/2$  chain model. The ground state varies smoothly from the dimerized (triplet)  $S=1$  Haldane chain to the dimerized (singlet)  $S=0$  chain as the ratio of exchange interactions changes.<sup>18,19</sup> Composite  $S=1$  behavior has also been reported in the asymmetric spin ladder compound  $\text{IPACuCl}_3$ , which shows a susceptibility and excitations characteristic of an  $S=1$  chain with a Haldane gap, and field induced Bose-Einstein condensation.<sup>20–22</sup> Spontaneous triplet dimerization has not been reported in other frustrated networks and so the unconventional ground state of  $\text{In}_2\text{VO}_5$  is notable.  $\text{Cu}^{2+}$  zigzag chains with comparable exchange interaction ratios  $\alpha=0.25–3$  instead form incommensurate spin ordered ground states.<sup>10</sup>

We propose that the ground state found in  $\text{In}_2\text{VO}_5$  evidences a high sensitivity of the  $J_1$  interaction to small fluctuating lattice distortions. A weak spin-lattice coupling ac-

companying the dimer formation in the inset of Fig. 1 leads to inequivalent  $J_1$  (intradimer) and  $J'_1$  (interdimer) interactions. Displacements that give  $J_1/J'_1 > 1$  reduce magnetic frustration and so the spin dimer fluctuations will couple to these modes. The small anomalies observed in the  $b$ -axis parameter and microstrain around the 120 K dimerization crossover are consistent with changes of longitudinal [010] phonon modes. The sensitivity of the  $J_1$  exchange interactions to local distortion lies in the orientation of the magnetic orbitals in  $\text{In}_2\text{VO}_5$ . The unpaired electrons are localized in  $d_{xy}$ -type orbitals, perpendicular to the short V-O bonds (marked on Fig. 1, inset), which are effectively orthogonal within the  $J_1$  pathways in a symmetric zigzag chain, leading to ferromagnetic superexchange. A small distortion such as displacement of oxygen atoms parallel to the chain direction removes the orthogonality and introduces a kinetic exchange component that rapidly decreases the strength of one of the now-inequivalent ferromagnetic interactions ( $J'_1$ ). Hence, longitudinal oxygen vibrations can couple to variations in  $J_1/J'_1$  and the corresponding triplet dimer fluctuations. The freezing of the  $S=1$  dimers below 5 K may be accompanied by the ordering of local displacements, and further studies of the low temperature properties of  $\text{In}_2\text{VO}_5$  will be worthwhile to discover whether a Haldane gap or lattice distortions are observed. High field investigation of possible Bose-Einstein condensation, similar to that in  $\text{IPACuCl}_3$ ,<sup>22</sup> also merits investigation.

In summary,  $\text{In}_2\text{VO}_5$  shows a crossover between  $S=1/2$  and  $S=1$  dimer phases at 120 K. This instability reveals a ground state for the frustrated zigzag chain. Spin-lattice coupling is evidenced by subtle changes in the cell parameters and strains around the crossover, and this is ascribed to coupling between triplet dimer spin fluctuations and longitudinal oxygen vibrations within the zigzag chains. The spin dimers freeze into a global singlet state below 5 K without apparent long range magnetic order.

## ACKNOWLEDGMENTS

We acknowledge the EPSRC for funding and for provision of beam time and the Leverhulme trust for support. The authors thank A. N. Fitch (ESRF), A. W. Hewat (ILL), P. Henry (ILL), and J. W. G. Bos (University of Edinburgh) for assistance with the diffraction experiments and S. T. Bramwell (University College London) for useful discussions.

<sup>1</sup>S. Eggert, I. Affleck, and M. Takahashi, Phys. Rev. Lett. **73**, 332 (1994).

<sup>2</sup>F. D. M. Haldane, Phys. Rev. B **25**, 4925 (1982).

<sup>3</sup>S. R. White and I. Affleck, Phys. Rev. B **54**, 9862 (1996).

<sup>4</sup>M. Hase, I. Terasaki, and K. Uchinokura, Phys. Rev. Lett. **70**, 3651 (1993).

<sup>5</sup>F. Heidrich-Meisner, A. Honecker, and T. Vekua, Phys. Rev. B **74**, 020403(R) (2006).

<sup>6</sup>H. T. Lu, Y. J. Wang, S. J. Qin, and T. Xiang, Phys. Rev. B **74**, 134425 (2006).

<sup>7</sup>R. Jafari and A. Langari, Phys. Rev. B **76**, 014412 (2007).

<sup>8</sup>T. Masuda, A. Zheludev, A. Bush, M. Markina, and A. Vasiliev, Phys. Rev. Lett. **92**, 177201 (2004).

<sup>9</sup>L. Capogna, M. Mayr, P. Horsch, M. Raichle, R. K. Kremer, M. Sofin, A. Maljuk, M. Jansen, and B. Keimer, Phys. Rev. B **71**, 140402(R) (2005).

<sup>10</sup>S.-L. Drechsler, O. Volkova, A. N. Vasiliev, N. Tristan, J. Richter, M. Schmitt, H. Rosner, J. Málek, R. Klingeler, A. A. Zvyagin, and B. Büchner, Phys. Rev. Lett. **98**, 077202 (2007).

<sup>11</sup>P. J. Senegas, J.-P. Manaud, and J. Galy, Acta Crystallogr., Sect.

- B: Struct. Crystallogr. Cryst. Chem. **B31**, 1614 (1975).
- <sup>12</sup>L. M. Volkova, J. Phys.: Condens. Matter **19**, 176208 (2007); U. Schwingenschlögl, Phys. Rev. B **75**, 212408 (2007).
- <sup>13</sup>Two independent investigations of  $\text{In}_2\text{VO}_5$  have been published since the submission of this paper; A. Möller, T. Taetz, N. Hollmann, J. A. Mydosh, V. Kataev, M. Yehia, E. Vavilova, and B. Büchner, Phys. Rev. B **76**, 134411 (2007); Y. Singh, R. W. McCallum, and D. C. Johnston, *ibid.* **76**, 174402 (2007).
- <sup>14</sup>Applying the mean field expression  $\Theta = -S(S+1)\sum J_{ij}/3k_B$  for Heisenberg exchange  $J_{ij}\mathbf{S}_i\mathbf{S}_j$  (positive  $J$  corresponds to AF exchange) to the spin monomer regime  $>120$  K ( $S=1/2$ ,  $\Theta=17$  K,  $\sum J_i=2J_1+2J_2$ ) and below the dimerization crossover ( $S=1$ ,  $\Theta=-70$  K,  $\sum J_i=J_1+2J_2$ ), assuming the exchange interactions are constant, gives  $J_1/k_B=-173$  K and  $J_2/k_B=139$  K, hence  $\alpha=0.8$ .
- <sup>15</sup>All of the ID31 data were Rietveld fitted and a combined x-ray and neutron powder diffraction refinement at 10 K in which all thermal factors were refined anisotropically gave residuals  $wR_p=0.118$  and  $R_p=0.0947$ . The oxygen sites refined to within error of full occupancy. Microstrains (root-mean-squared variations in lattice strain) parallel,  $s_{\parallel}[010]$ , and perpendicular,  $s_{\perp}[010]$ , to the  $\mathbf{b}$  axis were found by fitting the full widths at half maxima  $\Gamma_{hkl}$  of the Lorentzian synchrotron x-ray diffraction peaks as  $\Gamma_{hkl}(\text{rad})=s_{\perp}[010]+(s_{\parallel}[010]-s_{\perp}[010])\cos\phi+s_i\tan\theta$  where  $\phi$  is the angle between  $[010]$  and the normal to the  $(hkl)$  diffraction plane.  $s_i=0.036\%$  is the instrumental broadening contribution found by fitting peaks from a standard silicon powder.
- <sup>16</sup>A. C. Larson and R. B. Von Dreele, Los Alamos National Laboratory Report No. LAUR 86-748, 1994 (unpublished).
- <sup>17</sup>B. H. Toby, J. Appl. Crystallogr. **34**, 210 (2001).
- <sup>18</sup>K. Hida, Phys. Rev. B **45**, 2207 (1992).
- <sup>19</sup>K. Hida, Phys. Rev. B **46**, 8268 (1992).
- <sup>20</sup>H. Manaka, I. Yamada, and K. Yamaguchi, J. Phys. Soc. Jpn. **66**, 564 (1997).
- <sup>21</sup>T. Masuda, A. Zheludev, H. Manaka, L.-P. Regnault, J.-H. Chung, and Y. Qiu, Phys. Rev. Lett. **96**, 047210 (2006).
- <sup>22</sup>V. O. Garlea, A. Zheludev, T. Masuda, H. Manaka, L.-P. Regnault, E. Ressouche, B. Grenier, J.-H. Chung, Y. Qiu, K. Habicht, K. Kiefer, and M. Boehm, Phys. Rev. Lett. **98**, 167202 (2007).