

## Chemical Ordering in Bimetallic FeCo Nanoparticles : from a direct chemical synthesis to application as efficient high frequency magnetic material

Cyril Garnero,<sup>1</sup> Mathieu Lepasant,<sup>1</sup> Cécile Garcia-Marcelot,<sup>1,2</sup> Yooleemi Shin,<sup>3,4</sup> Christian Meny,<sup>3</sup> Pierre Farger,<sup>1,2</sup> Bénédicte Warot-Fonrose,<sup>2</sup> Raul Arenal,<sup>5,6,7</sup> Guillaume Viau,<sup>1</sup> Katerina Soulantica,<sup>1</sup> Pierre Fau,<sup>8</sup> Patrick Poveda,<sup>9</sup> Lise-Marie Lacroix,<sup>1\*</sup> Bruno Chaudret<sup>1</sup>

1. Université de Toulouse, UMR 5215 INSA, CNRS, UPS, Laboratoire de Physique et Chimie des Nano-Objets, 135 avenue de Rangueil F-31077 Toulouse cedex 4, France
2. Centre d'Elaboration de Matériaux et d'Etudes Structurales, CEMES-CNRS, 29 rue Jeanne Marvig, B.P. 94347, 31055 Toulouse, France
3. Institut de Physique et Chimie des Matériaux de Strasbourg, Université de Strasbourg, CNRS, UMR 7504, 23 rue du Loess, 67034 Strasbourg, France
4. Department of Physics, CNRS-Ewha International Research Center, Ewha Womans University, Seoul 120-750, South Korea
5. Instituto de Nanociencia de Aragon (INA), Universidad de Zaragoza, Calle Mariano Esquillor, 50018 Zaragoza, Spain
6. ARAID, 50018 Zaragoza, Spain
7. Instituto de Ciencias de Materiales de Aragon, CSIC-U. de Zaragoza, Calle Pedro Cerbuna 12, 50009 Zaragoza, Spain
8. Laboratoire de Chimie de Coordination, UPR 8241, 205 route de Narbonne, 31400 Toulouse, France
9. ST Microelectronics Tours, 10 rue Thalès de Milet, CS 97155, 37071 Tours Cedex 2, France


Corresponding author: [lmacroix@insa-toulouse.fr](mailto:lmacroix@insa-toulouse.fr), Tel: +33567048833, Fax: +33561559697

**Abstract :** Single crystalline FeCo nanoparticles with tunable size and shape were prepared by co-decomposing two metal-amide precursors under mild conditions. The nature of the ligands introduced in this organometallic synthesis drastically affects the reactivity of the precursors and thus the chemical distribution within the nanoparticles. The presence of the B2 short-range order was evidenced in FeCo nanoparticles prepared in presence of HDAHCl ligands, combining <sup>57</sup>Fe Mössbauer, zero field <sup>59</sup>Co Ferromagnetic Nuclear Resonance (FNR) and X-ray diffraction studies. This is the first time that the B2 structure is directly formed during synthesis without the need of any annealing step. The as-prepared nanoparticles exhibit magnetic properties comparable with the ones of the bulk ( $M_s = 226 \text{ Am}^2.\text{kg}^{-1}$ ). Composite magnetic materials prepared from these FeCo nanoparticles led to a successful

1  
2  
3 proof-of-concept of integration on inductor-based filters (27% enhancement of the  
4 inductance value at 100 MHz).  
5  
6  
7

8 Key words: Magnetic nanoparticles, Zero field  $^{58}\text{Co}$  FNR, Mössbauer spectroscopy, composite  
9 materials, inductor-based filter  
10  
11

12 TOC :  
13  
14

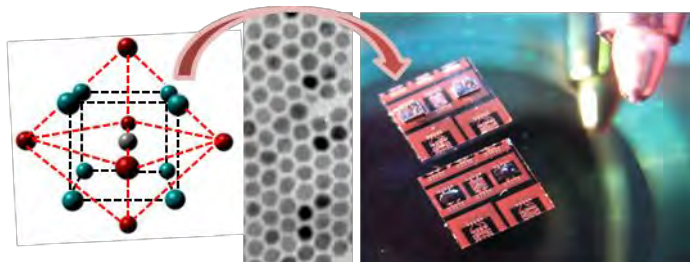

1  
2  
3 The needs for telecommunications have considerably increased in the past decade, requiring  
4 high performance, low power consumption and low cost radiofrequency circuits to support  
5 the huge expansion of local exchanges such as video on demand, interconnections with  
6 mobile phone applications or shared storage. Among the different passive components  
7 present in these circuits, integrated planar inductors play a key role to properly filter the  
8 signal of interest while rejecting the surrounding electromagnetic noise up to the GHz, which  
9 is the range of frequency commonly used for cellular phone networks worldwide. The  
10 efficiency of these inductors, evaluated by the value of their inductance, should be  
11 constantly increased. However, geometrical features, such as number of spires and diameter  
12 of the wires, can no longer be improved without leading to larger inductors. Thus,  
13 alternatives are actively sought, the most promising one consisting in improving the  
14 environment permeability by embedding the inductors in a soft ferromagnetic material.<sup>1</sup> An  
15 alternative to the magnetic thin films commonly used consists in preparing composite  
16 materials composed of optimized magnetic nanoparticles embedded in an insulating matrix.<sup>2</sup>  
17 Thanks to the development of liquid-phase synthesis during the past two decades, various  
18 magnetic nanoparticles (NPs) of controlled sizes and shapes were synthesized,<sup>3</sup> opening  
19 great perspectives for RF filters, as well as answering to the increasing demand in magnetic  
20 data storage<sup>4,5</sup> and in chemical,<sup>6</sup> environmental<sup>7</sup> and biomedical applications.<sup>8</sup> Single  
21 crystalline Fe, Co or Ni NPs have been obtained with a nanometric size control,<sup>9</sup> and shapes  
22 ranging from spheres to cubes, rods or wires, allowing in turn a fine control of their physical  
23 properties.<sup>3</sup> Among the different magnetic materials, the FeCo alloy constitutes the material  
24 of primary choice for magnetic inductors since it combines the highest saturation  
25 magnetization ( $M_s \text{ Fe}_{50}\text{Co}_{50} = 235 \text{ A}\cdot\text{m}^2\cdot\text{kg}^{-1}$ ) with a low anisotropy constant ( $K \text{ Fe}_{50}\text{Co}_{50} =$   
26  $1,5\cdot 10^4 \text{ J}\cdot\text{m}^{-3}$ ),<sup>10</sup> allowing high frequency applications. However, such bimetallic alloy NPs are  
27 highly challenging to synthesize. Segregation issues are often encountered between the two  
28 components, leading to core-shell, onions or dumbbell NPs.<sup>11</sup>  
29  
30 Despite important efforts to develop liquid phase syntheses, including thermal  
31 decomposition,<sup>12</sup> polyol process,<sup>13,14</sup> hydrothermal synthesis<sup>15-17</sup> and sonochemical  
32 method,<sup>18,19</sup> crystalline FeCo nanoparticles (NPs) could rarely be achieved directly. Indeed,  
33 the difference of reactivity of the precursors and the mild temperature of reaction used lead  
34 to poorly crystallized nanoparticles with inhomogeneous chemical structure, which  
35 therefore exhibit a reduced saturation magnetization. A high temperature annealing process  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 is then mandatory to achieve the desired bulk magnetic properties, but at the expense of the  
4 size and shape control of the nanoparticles due to sintering.  
5

6  
7 Our group has previously reported the synthesis of 15 nm FeCo NPs, which self-organize into  
8 millimeter supercrystals, by the co-decomposition of  $\text{Fe}(\text{CO})_5$  and  $\text{Co}(\eta^3\text{-C}_8\text{H}_{13})(\eta^4\text{-C}_8\text{H}_{12})$   
9 under  $\text{H}_2$ .<sup>20-22</sup> The particles exhibited however, a magnetization limited to  $160 \text{ A.m}^2.\text{kg}^{-1}$  due  
10 to a chemically inhomogeneous structure and a partial carburation, which is likely resulting  
11 from the presence of CO in the iron precursor.<sup>23</sup> Thanks to a fine optimization of the  
12 organometallic precursors used, we report here the synthesis of highly crystalline FeCo  
13 nanoparticles with bulk magnetic properties. Depending on the nature of the ligands used,  
14 the structure of the NPs could be varied from a radial composition gradient configuration to  
15 the chemically ordered  $\text{B}_2$  phase, as revealed by the combined  $^{57}\text{Fe}$  Mossbauer, zero field  
16  $^{59}\text{Co}$  Ferromagnetic Nuclear Resonance (FNR) and XRD studies. The efficiency of a highly  
17 magnetic composite material, prepared with optimized FeCo NPs immersed in epoxy resin,  
18 was finally tested onto commercial inductors, leading to a 27% improvement of the  
19 properties over a broad frequency range.  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

## Results and discussion

FeCo nanoparticles (NPs) were obtained by reacting  $\{\text{Fe}[\text{N}(\text{SiMe}_3)_2]_2\}_2$  (Me = CH<sub>3</sub>) and  $\{\text{Co}[\text{N}(\text{SiMe}_3)_2]_2\text{THF}\}$  (THF = tetrahydrofuran) at 150°C with H<sub>2</sub>. Depending on the nature and the concentration of the added ligands, nanoparticles with a mean size varying from 1.5 to 90 nm were obtained (Figure S1). Figures 1a and S2 show transmission electron microscopy images (TEM) of nanocubes, with a mean size of  $8.3 \pm 0.9$  nm, synthesized after 48h of reaction in presence of palmitic acid and hexadecylamine in a 3:4 ratio. These particles will be referred hereinafter as FeCo-PA NPs. Replacing palmitic acid by hexadecylammonium chloride leads to NPs with a mean diameter of  $11.4 \pm 0.7$  nm, referred as FeCo-HDAHCl NPs (Figures 1b, S3-4). The reaction kinetic being fastened in presence of HDAHCl ligands, the reaction time could be shortened to 24h (Figures S5-6).

Both types of particles are highly crystalline and exhibit the expected bcc structure as revealed by high resolution transmission electron microscopy (HRTEM, Figures 1c-d) and X-ray diffraction (XRD, Figure S7). The crystallite sizes could be extracted using Rietveld refinement and are respectively of 7.1 nm and 9.9 nm for FeCo-PA and FeCo-HDAHCl NPs, in good agreement with the TEM mean size. A thin oxide shell (ca. 1 nm) is clearly observed on the HRTEM and high angle annular dark field image scanning TEM (HAADF-STEM, Figure S8). This shell is formed due to air-exposure during the sample introduction through air in the TEM. The freshly prepared particles are purely metallic, as evidenced by the XRD patterns performed under Ar atmosphere as further confirmed by advanced spectroscopies (see below).

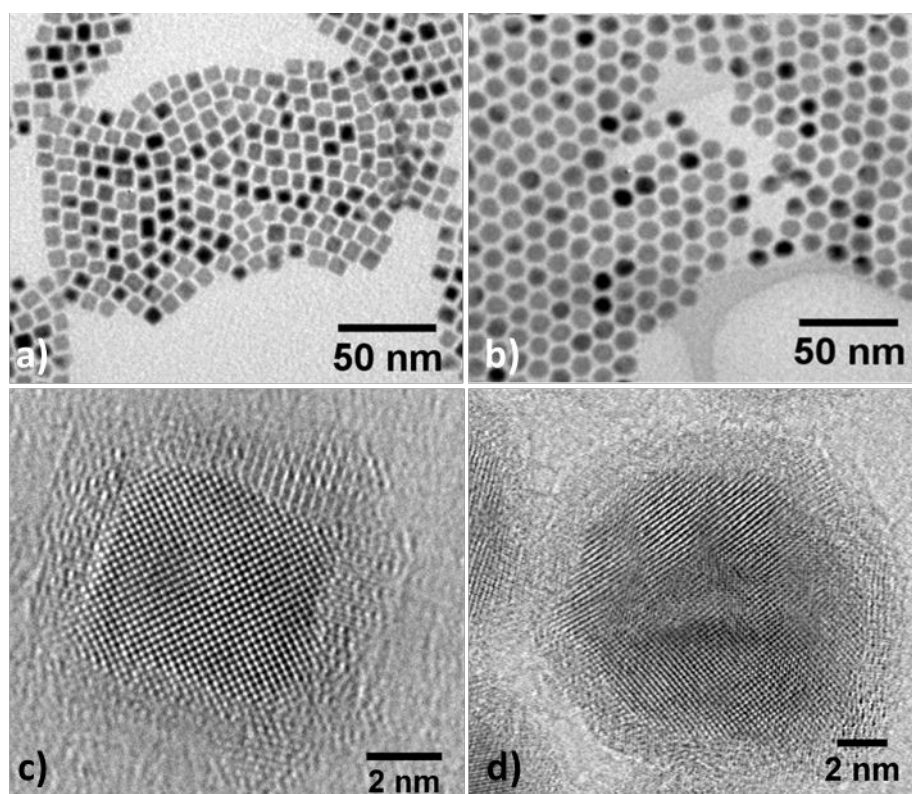


Figure 1: a-b) Conventional transmission electron microscopy (TEM) micrographs. c-d) HRTEM images of FeCo nanoparticles prepared with PA (left column) or HDAHCl (right column).

Chemical analyses were performed on the final powder by inductively coupled plasma mass spectrometry (ICP-MS) revealing a global composition of  $\text{Fe}_{52}\text{Co}_{48}$  for both type of NPs, very close to the equimolar ratio introduced. The local distribution of Fe and Co within the nanoparticles was further characterized by electron energy loss spectroscopy (EELS, Figures S8-9) and energy dispersive X-ray spectroscopy (EDX, Figure S10). STEM-EDX mapping revealed a local composition of  $\text{Fe}_{53}\text{Co}_{47}$ , in good agreement with the ICP-MS, revealing the homogeneity of the NP chemical composition. The distribution of the Fe and Co within individual NPs was further evidenced by probe-corrected STEM-EELS profile. While Co-rich core was always detected for FeCo-PA NPs (Figure S8), three different profiles were statistically identified in the FeCo-HDAHCl NPs, corresponding to Co-rich core, onion-like core and FeCo core (Figure S9).

The chemical order was studied at the atomic scale by combining  $^{57}\text{Fe}$  Mössbauer spectroscopy and Zero field  $^{59}\text{Co}$  ferromagnetic nuclear resonance (FNR i.e. nuclear magnetic

resonance for ferromagnets)<sup>24</sup> to probe respectively the Fe and Co environments without facing the interference of any oxidation artefacts<sup>25,26</sup>.

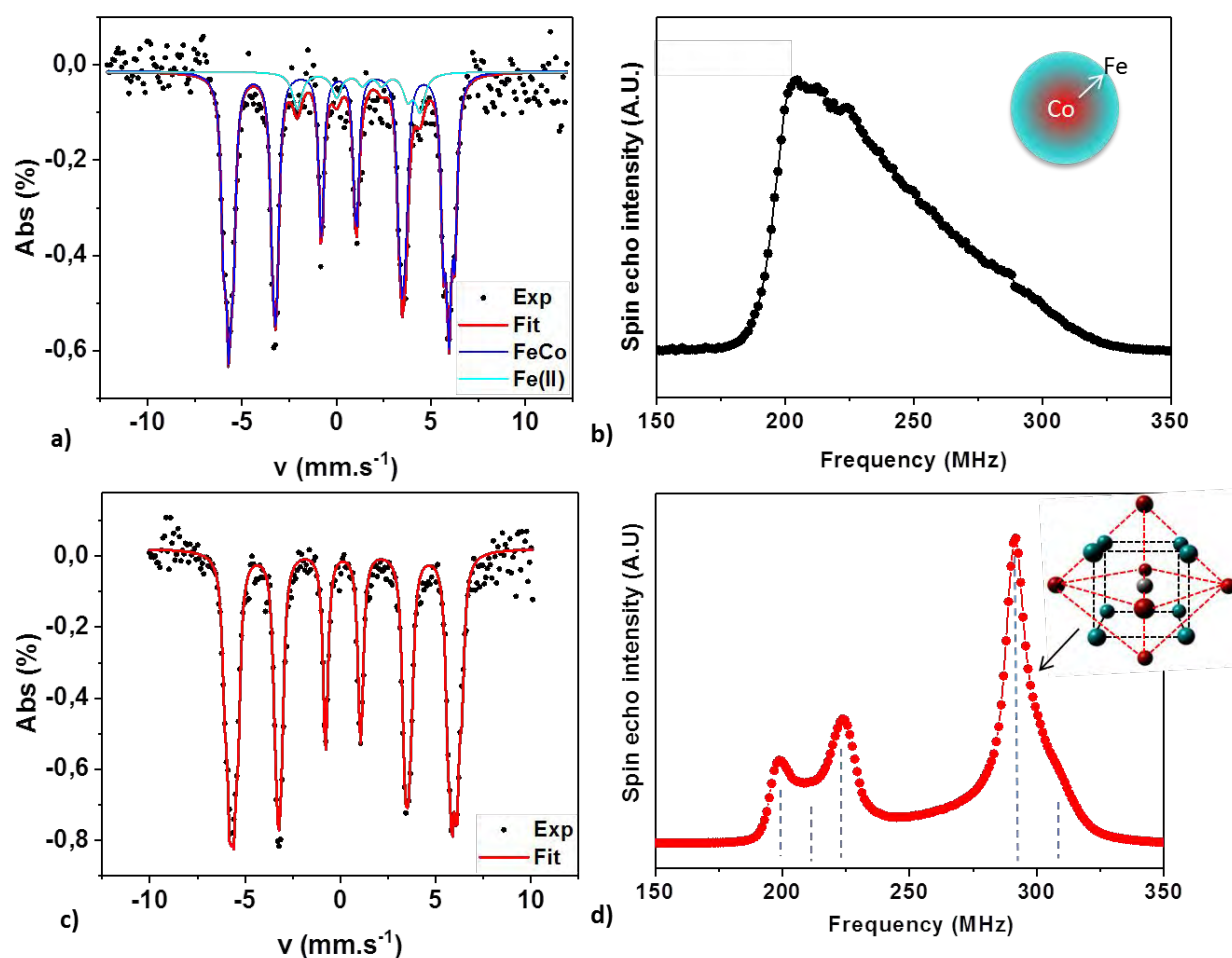


Figure 2: a-c) 5K  $^{57}\text{Fe}$  Mossbauer spectrum and b-d)  $^{59}\text{Co}$  Ferromagnetic Nuclear Resonance spectrum of the a-b) FeCo-PA and c-d) FeCo-HDAHCl nanoparticles. As inset, schematic view of the gradient profile determined for PA NPs and B2 order for the HDAHCl NPs (Fe : blue, Co : red). Dashed lines are guides for the eyes for the different contributions on FeCo-HDAHCl FNR spectrum.

The Mössbauer signals recorded at 5K and 300K (see Figure S11) exhibit a sextet-like contribution, typical from FeCo alloys.<sup>25,27,28</sup> The absence of any large hyperfine field contribution confirmed that after synthesis, the obtained particles are purely metallic and do not present any oxide shell. The fitting of the experimental spectra, reported in Table S1, evidenced broad hyperfine field distributions both for HADHCl and PA ligands. An additional contribution at low field in the case of PA ligands could be attributed to magnetically coupled Fe(II) molecular species as previously reported for pure Fe NPs,<sup>9</sup> evidencing a slower reduction of the Fe species compared to the HDAHCl case.

1  
2  
3 The  $^{59}\text{Co}$  FNR spectra clearly evidenced a major difference between the NPs obtained in the  
4 presence of PA and HDAHCl ligands. Indeed, a broad spin echo peak was observed in the  
5 frequency range from 180 to 320 MHz for FeCo-PA NPs. The fitting of this peak (see figure  
6 S12) reveals the presence of a continuous concentration gradient from pure Co towards pure  
7 Fe across the NP radius (corresponding to 26 atomic layers). In the case of HDAHCl-NPs three  
8 main distinct peaks were observed at 200, 224 and 290 MHz respectively and a shoulder at  
9 211 MHz. The 200 MHz peak can be attributed to a bcc Co metastable phase. Such a phase  
10 has been reported in a bcc epitaxial Fe/Co thin film structure,<sup>29</sup> and could reveal the  
11 presence of NPs exhibiting a pure Co part close to a FeCo alloy. The 211 MHz shoulder and  
12 the 224 MHz contribution peak evidenced a structure composed of Co-rich bcc FeCo phase  
13 with 1st shell coordination polyhedra containing 7 Co : 1 Fe atoms and 6 Co : 2 Fe atoms  
14 respectively. An original short range order favoring even numbers of Fe atoms around Co has  
15 already been reported in CoFe alloy films.<sup>30</sup> The simultaneous observation of the 200 and  
16 224 MHz peaks (with a much smaller 211 MHz shoulder) might be the fingerprint of such  
17 unusual order. Finally, the major contribution in the spectra is at 290 MHz and is  
18 characteristic of the chemically-ordered local environment known as B2, with a CsCl  
19 structure (see inset figure 2d).<sup>31</sup> Since the FNR spectrum reveals Co rich contributions in the  
20 200-224 MHz range, the local B2 order has to be slightly enriched in Fe in order to preserve  
21 the FeCo stoichiometry. This is confirmed by the observation of the shoulder at 310 MHz  
22 characteristic of a Fe enriched B2 order. To our knowledge, it is the first time that the short-  
23 range B2 order is stabilized within NPs directly obtained after a liquid phase synthesis,  
24 thanks to the fine optimization of the precursor reactivity and the ligands used.


25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44 In-situ XRD study was performed during the thermal annealing of FeCo-HDAHCl and FeCo-PA  
45 NPs (Figure 3 and S13) under a reducing atmosphere (95%  $\text{N}_2$ , 5%  $\text{H}_2$ ) following a multi-step  
46 temperature profile up to 800°C (Figure S14). The use of a Co-source avoided the Fe atoms  
47 fluorescence and allowed the detection of the three superstructure reflections (100), (111)  
48 and (210) observed in the long-range crystalline B2 phase.<sup>32</sup> The appearance of the B2  
49 phase, which corresponds to a long-range chemical-ordered CsCl-type structure, was  
50 characterized by the temperature evolution of the order parameter  $S$ , defined by :<sup>33,34</sup>

$$S = \frac{r_A - x_A}{1 - F_A} \quad eq(1)$$




1  
2  
3 With  $r_A$  the fraction of the site A occupied by the right atom A,  $x_A$  the atomic fraction of A in  
4 the alloy ( $x_{Co} = x_{Fe} = 0.5$ ) and  $F_A$  the fraction of the site A ( $F_{Co} = F_{Fe} = 0.5$ ).  
5  
6

7 For a  $Fe_{50}Co_{50}$  alloy, S values vary between  $S=0$  for a fully disordered alloy to  $S=1$  for a fully  
8 ordered B2 alloy. In the case of FeCo-HDAHCl NPs, a shoulder at the (100) peak is already  
9 observed at 300°C, while the three characteristic peaks are clearly evidenced at 400°C,  
10 leading to an order parameter  $S = 0.7$  (Figure 3c). The order parameter keeps on increasing,  
11 reaching  $S= 0.76$  at 700°C. Above this temperature, the order vanishes, as expected from the  
12 bulk phase diagram of FeCo alloys. After cooling down to room temperature, the long-range  
13 B2 phase was retrieved as evidenced by the order parameter  $S = 0.76$ . In contrast for FeCo-  
14 PA NPs, the partial ordering only appears at 500°C and was characterized by an order  
15 parameter of 0.55 (Figure S13). Such thermal behavior is in agreement with the previous  
16 report on the thermal ordering of disordered 30 nm  $Fe_{50}Co_{50}$  NPs prepared by polyol  
17 process.<sup>32</sup> The fact that FeCo-HDAHCl NPs exhibit the B2 structure at lower temperature and  
18 with a better ordering factor than previously reported NPs and FeCo-PA NPs results from the  
19 presence of a short-range B2 order within as-prepared FeCo-HDAHCl NPs, as previously  
20 shown by Co FNR. The short-range B2 order region acted as seeds during the  
21 recrystallization process which was thermally activated, leading to a long-range chemical  
22 ordering under mild conditions (300-400°C).  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

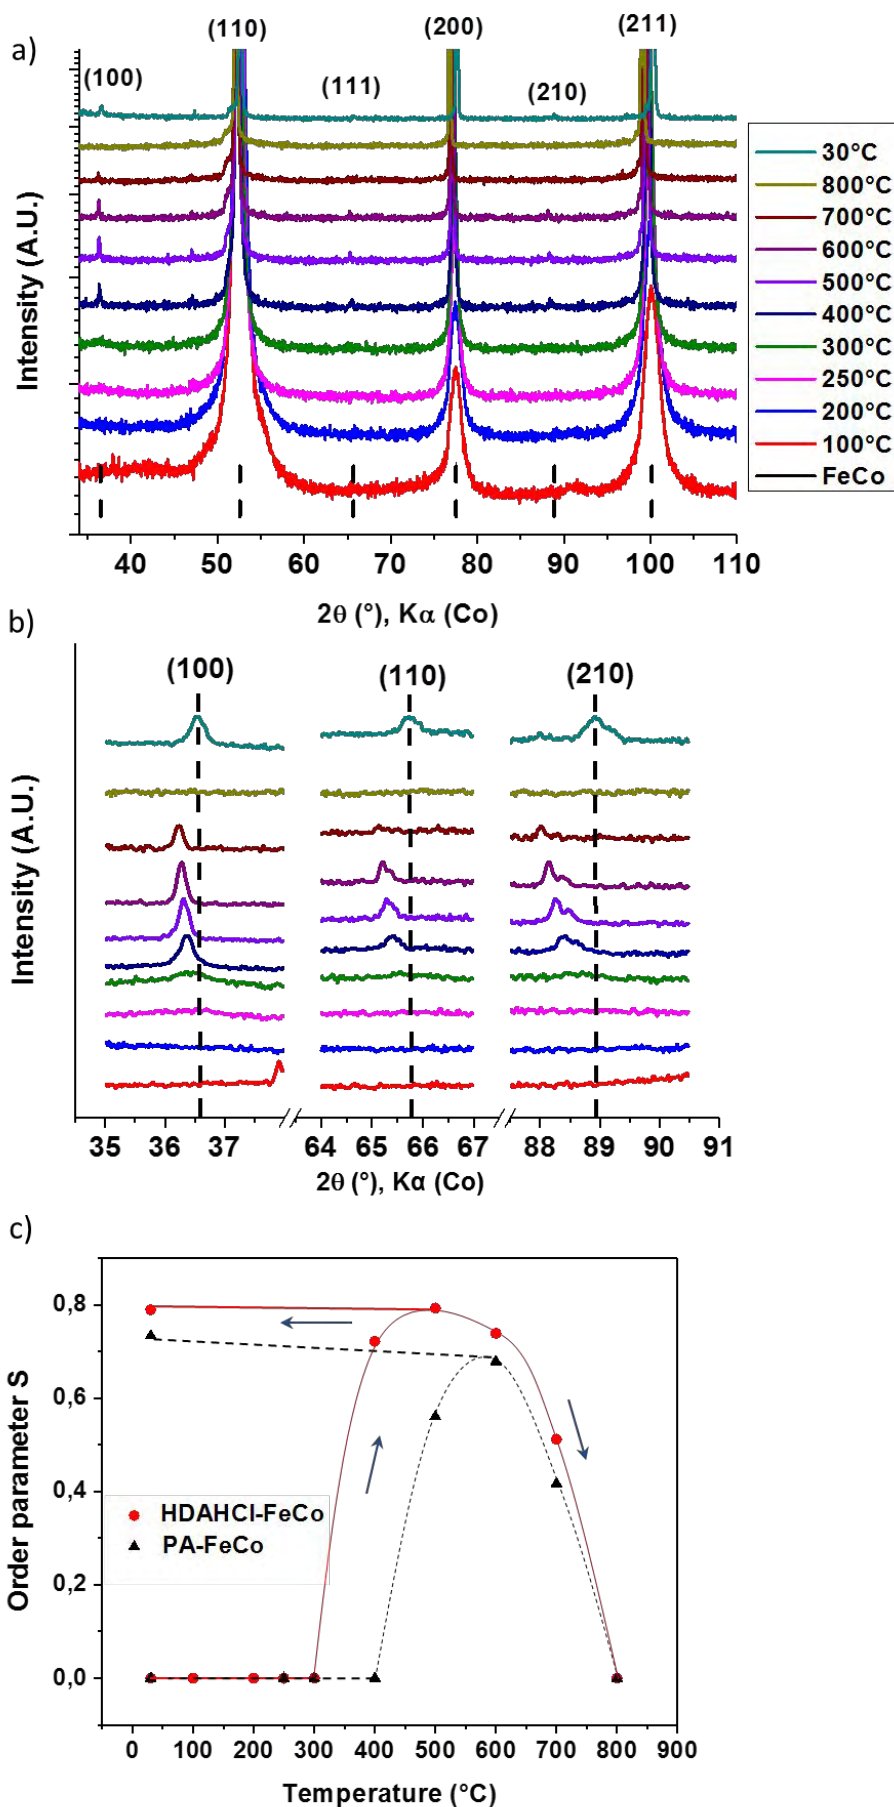

1  
2  
3 *Figure 3: a) In-situ XRD recorded during thermal annealing of FeCo-HDAHCl NPs under*  
4 *reducing atmosphere. b) Enlarged view of the characteristic B2 superstructures peaks. c)*  
5 *Thermal evolution of the order parameter S determined for FeCo-HDAHCl (red dots) and*  
6 *FeCo-PA (black triangles) NPs. Red solid line, black dashed line and blue arrows are guide for*  
7 *the eyes following the temperature increase and the final cooling.*  
8  
9

10  
11  
12 Both type of NPs exhibit a soft magnetic behavior at room temperature (Figure 4), with  
13 saturation magnetizations ( $M_S$ ) of 226 and 204  $\text{A}\cdot\text{m}^2\cdot\text{kg}^{-1}_{\text{FeCo}}$  for HDAHCl and PA NPs  
14 respectively, very close to the expected bulk value ( $M_{S_{\text{Fe}_{50}\text{Co}_{50}}} = 235 \text{ A}\cdot\text{m}^2\cdot\text{kg}^{-1}_{\text{FeCo}}$ ).<sup>10</sup> The low  
15 temperature curve (Figure S15) revealed no exchange bias indicating that the FeCo  
16 nanoparticles are not oxidized, in agreement with the Mössbauer spectroscopy.  
17  
18  
19  
20  
21  
22  
23  
24

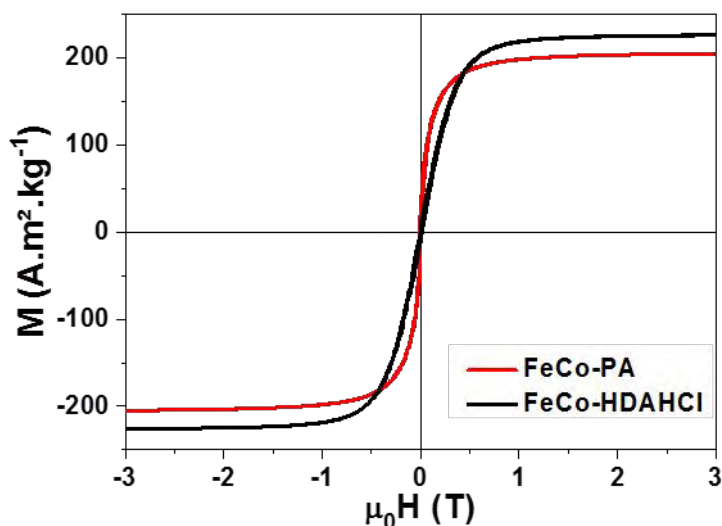

25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43 *Figure 4: Magnetic hysteresis loop at 300K of the as-synthesized FeCo NPs prepared in*  
44 *presence of PA (black line) or HDAHCl ligands (red line).*  
45  
46  
47

48 The organometallic synthesis of FeCo NPs starting from two amide precursors yielded for the  
49 first time highly crystalline NPs with tunable sizes. In the presence of palmitic acid,  
50 carboxylate-containing precursors of Co and Fe which have different stabilities, lead to NPs  
51 exhibiting a concentration gradient.<sup>9,35</sup> Thus, one can assume that the reduction followed a  
52 two-step process consisting in a first nucleation of Co nuclei, which then favored the  
53 decomposition of the more stable Fe-carboxylate precursor, leading to a fairly slow NP  
54 growth. On the contrary, in the presence of HDAHCl, the intermediate chloride species  
55  
56  
57  
58  
59  
60

1  
2  
3 formed seem to have a comparable reactivity, preventing the formation of a pure Co core.  
4  
5 The concomitant decomposition of the Fe and Co species lead for the first time to the  
6  
7 synthesis of the chemically ordered short-range B2 structure. Therefore, a very fine tuning of  
8  
9 the mild reaction conditions opens the route for the synthesis of magnetic alloys with  
10  
11 controllable chemical structure and thus physical properties.  
12

13 For the integration purposes, the net magnetic fraction into the composite materials being a  
14  
15 key parameter, as-synthesized FeCo-HDAHCl NPs were preferred to FeCo-PA NPs since they  
16  
17 exhibit a higher magnetization and a larger metallic content (80% and 50% respectively).  
18  
19 These NPs were mixed with epoxy monomers and let to polymerize at room temperature to  
20  
21 form ca. 250  $\mu\text{m}$  thick self-supporting composite pellets (Figures 5a inset and S16). The  
22  
23 epoxy resin was chosen as a matrix for the FeCo composites since it advantageously  
24  
25 combines electrical insulating characteristics, essential for high frequency applications, with  
26  
27 an enhanced chemical resistance and efficient barrier properties to oxygen and moisture.<sup>36</sup>  
28  
29 The dispersion of the nanoparticles within the composite pellet cross section was  
30  
31 characterized using SEM and TEM (Figures 5a-b). Thanks to a slow evaporation of the NP  
32  
33 solvent, only few aggregates are observed, FeCo NPs being well dispersed along the whole  
34  
35 thickness of the pellet. The loading of the composite could be reproducibly varied from 10 to  
36  
37 65% weight fraction of FeCo NPs, leading to a net magnetization under an applied field of 3T  
38  
39 varying from 26 to 152  $\text{A}\cdot\text{m}^2\cdot\text{kg}^{-1}$  (Figures 5c and S17, and Table S2). Assuming that the  
40  
41 density of each components of the composite materials is similar to its bulk value, namely  
42  
43  $\rho_{\text{FeCo}} = 8.3$ ,  $\rho_{\text{ligands}} = 0.9$  and  $\rho_{\text{epoxy}} = 1.1$ , net magnetic volume fractions varying from 2 to 19%  
44  
45 were determined.  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

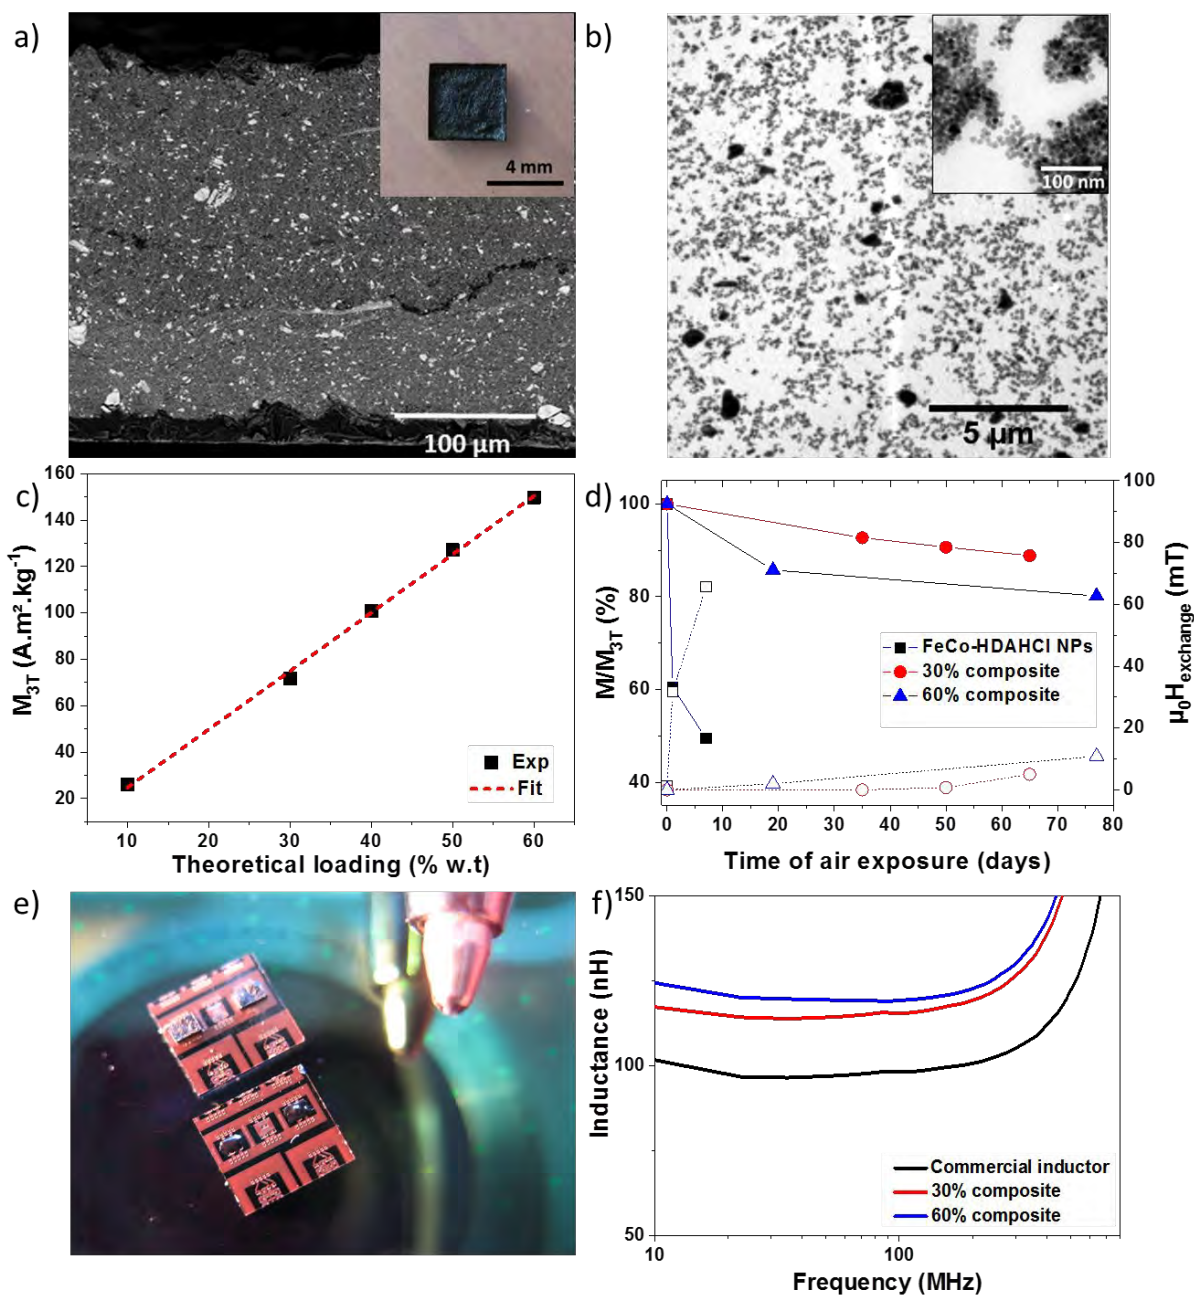


Figure 5: a) SEM image of the cross section of a 30% in weight FeCo-HDAHCl NP loaded pellet. Due to the use of backscattered electrons, the metallic NPs appear as white dots while the epoxy appears grey, inset: optical image of the 4mm squared pellet b) TEM image of an ultramicrotome slice of the epoxy composite. c) Evolution of the room temperature magnetization at 3T ( $M_{3T}$ ) of the composites as a function of the targeted FeCo loading. A linear fitting is superimposed as a guide for the eyes. d) Evolution of the relative 3T magnetization (solid scatters and lines) and the exchange bias (open scatters and dashed lines) as a function of air exposure for pure FeCo-HDAHCl NPs (black) and the epoxy composite loaded with 30% (circles) and 60% (triangles) in weight FeCo-HDAHCl NPs. e) Picture of commercial silicon chip containing copper micro-inductors topped with FeCo rich epoxy composites of this study, f) evolution of the inductance as a function of frequency for the commercial inductor (black line) and a similar inductor covered with epoxy composite loaded with 30% (red line) and 60% (blue line) in weight of FeCo-HDAHCl NPs.

1  
2  
3 The magnetic properties were assessed as a function of time under air exposure to probe  
4 the protection against the oxidation of the epoxy matrix. The magnetization of pure FeCo-  
5 HDAHCl NPs quickly diminished due to a strong oxidation once exposed to the air. The  
6 exchange bias, measured at low temperature increased up to 65 mT after only 5 days. In the  
7 case of the epoxy-FeCo composite, 80 to 90% of the magnetization was retained after a 65-  
8 day air exposure for 60% and 30% loaded composite respectively. An exchange bias limited  
9 to 14 and 8 mT respectively confirmed that the FeCo NPs are fairly well protected against  
10 the oxidation, the epoxy resin acting as an efficient air barrier. The resulting composite was  
11 successfully integrated on a commercial inductor-based filter using a pick and place  
12 approach. Enhancement of 18% and 27% of the inductance value at 100 MHz were  
13 measured with the 30% and 60% loaded composite respectively compared to the air-core  
14 commercial inductor reference. Such increase represents an important step for the  
15 development of commercial planar inductors.  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27

## 28 **Conclusion**

29  
30 We report here a new chemical synthesis of monodisperse FeCo nanoparticles using the co-  
31 decomposition of two metalloids amides under mild conditions without post treatment  
32 annealing. A fine tuning of the precursors reactivity was achieved thanks to the ligands used  
33 leading to two different NP type. For the first time the presence of the ordered B2 phase was  
34 evidenced in NPs prepared in presence of HDAHCl ligands, leading to magnetic properties  
35 comparable with the bulk ones ( $M_s = 226 \text{ A.m}^2.\text{kg}^{-1}$ ). Optimized composite materials were  
36 prepared by mixing these NP with epoxy monomers. Composites with variable magnetic  
37 loadings were prepared and successfully integrated on inductor-based filters, leading to a  
38 27% enhancement of the inductance value at 100 MHz. Although this enhancement remains  
39 modest this study evidences the possibility to use ex situ synthesized NPs for inductance  
40 improvement, opening the path for NP-based composites for advanced microelectronics  
41 applications after improvement of the magnetic volume fraction of the composite and of the  
42 device geometry by the full immersion of the inductors into the magnetic material.  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56

## 57 **Acknowledgements:**

58  
59  
60

1  
2  
3 Lucien Datas and Jean-François Meunier are warmly thanked for high resolution TEM and  
4 Mössbauer spectroscopy measurements. This work was performed in the frame of TOURS  
5 2015, project supported by the French « Programme de l'économie numérique des  
6 Investissements d'Avenir ». We gratefully acknowledge the International Associated  
7 Laboratory (LIA)-M<sup>2</sup>OZART for financial support. Some of the HR-STEM and EELS studies  
8 were conducted at the Laboratorio de Microscopias Avanzadas, Instituto de Nanociencia de  
9 Aragon, Universidad de Zaragoza, Spain. R. A. gratefully acknowledges the support from the  
10 Spanish Ministry of Economy and Competitiveness (MINECO) through project MAT2016-  
11 79776-P (AEF/FEDER. UE). In IPCMS Strasbourg the work was supported by the CNRS LIA  
12 "NANOFUNC" and the LABEX NIE (No. ANR-11-LABX-0058\_NIE).  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32

### 33 **Experimental Section:**

#### 34 *General synthesis*

35  
36 Mesitylene (99%), toluene (99%), tetrahydrofuran (THF, 99%) and pentane (99%) were  
37 purchased from Merck, Acros, Carlo Erba and Fisher respectively. The solvents were purified  
38 on alumina desiccant (Pure Solv, Innovativ Technology) and degassed through three freeze-  
39 pump-thaw cycles. Hexadecylamine (HDA, 99%) was purchased from Sigma-Aldrich. The two  
40 metallic precursors (Fe{N[Si(CH<sub>3</sub>)<sub>3</sub>]<sub>2</sub>})<sub>2</sub> (FeNSi, >99.9%) and Co(N(Si(CH<sub>3</sub>)<sub>3</sub>)<sub>2</sub>)<sub>2</sub>, THF (CoNSi,  
41 >99.9%) were purchased from Nanomeps.  
42  
43  
44  
45  
46  
47  
48  
49

#### 50 *Synthesis of HDAHCl.*

51  
52 Hexadecylamonium chloride (HDAHCl) was synthesized following an adapted procedure  
53 described elsewhere<sup>[37]</sup>. Briefly, a solution of 10 mmol of hexadecylamine (HDA) (2.415 g) in  
54 400 mL of pentane was prepared in the glove box. An excess amount of HCl in diethylether  
55 (14 mL, 1.0 M) was added under Ar atmosphere. The solution turned milky white  
56 immediately. The solution was stirred for 30 min then allowed to decant. After the removal  
57  
58  
59  
60

1  
2  
3 of the supernatant, the resulting white concentrated solution was washed 2 times with  
4 pentane. The final solution was evaporating and 2,5 g (90% yield) of white powder (HDA•HCl  
5 ) was obtained.  
6  
7

8  
9  
10 *Synthesis of FeCo nanoparticles.*

11  
12 \* Preparation of the precursor solution

13  
14 In a glove box, 150 mg (0,4 mmol) of  $\text{Fe}(\text{N}(\text{Si}(\text{CH}_3)_3)_2)_2$  and 180 mg (0,4 mmol) of  
15  $\text{Co}(\text{N}(\text{Si}(\text{CH}_3)_3)_2)_2$ , THF were separately dissolved in 2,5 ml of mesitylene and then mixed  
16 leading to a green solution.  
17  
18

19  
20  
21 \* Preparation of FeCo-PA NPs

22  
23 308 mg (1,2 mmol) of PA and 386 mg (1,6 mmol) of HDA were dissolved in 10 ml and 5 ml of  
24 mesitylene respectively. The PA solution was added onto the precursor mixture, which  
25 became blue. The resulting solution was magnetically stirred during 5 min. The HDA solution  
26 was added, leading to a violet coloration which quickly vanished, the solution returning to  
27 blue after few seconds. The final 20 mL solution was transferred into a Fisher Porter bottle  
28 and pressurized under 3 bars of  $\text{H}_2$ , the solution became darker. The reaction was heated at  
29  $150^\circ\text{C}$  and let to react 48 h to allow the reduction of the stable Fe-carboxylate species  
30 formed in-situ.  
31  
32

33  
34  
35  
36  
37  
38  
39 \* Preparation of FeCo-HDAHCl NPs

40  
41 334 mg (1,2 mmol) of HDAHCl and 386 mg (1,6 mmol) of HDA were dispersed in 10 ml and 5  
42 ml of mesitylene respectively. The precursor solution was added onto the HDAHCl one,  
43 which became brownish. The resulting solution was magnetically stirred during 5 min, the  
44 solution turning to dark blue. Finally, the HDA solution is added. The final 20 mL solution is  
45 transferred into a Fisher Porter bottle and placed in a pre-heated oil bath at  $150^\circ\text{C}$  for 1 h  
46 under Ar blanket to ensure the complete dissolution and homogenization of the reactants.  
47 The solution was then allowed to cool down at room temperature and further pressurized  
48 under 3 bars of  $\text{H}_2$ . The reaction was heated again at  $150^\circ\text{C}$  for 24 h to allow the  
49 decomposition of the precursors.  
50  
51  
52

53  
54  
55  
56  
57  
58  
59 \* Purification of the NPs  
60



1  
2  
3 At the end of both type of reaction, the H<sub>2</sub> atmosphere was released, a black solution was  
4 observed. The NPs were recovered by magnetically assisted precipitation, washed twice with  
5 toluene and twice with THF and finally dried, leading to a black powder kept in the glove  
6 box. Reaction yields were calculated from the final metallic weight content of the powder  
7 over the initial Fe and Co weight introduced. Yields of 23 and 66% were obtained for FeCo-  
8 PA and FeCo-HDAHCl NPs, respectively, due to partial weight losses during the purification  
9 steps and a non complete reduction of the Fe-carboxylate species as previously discussed.

#### 16 17 *Preparation of the magnetic composite.*

18  
19 In a glove box, 1,5 mL of THF is added on 50 mg of powder. To ensure a proper dispersion,  
20 the solution was sonicated for 30 min. To prepare a composite loaded with 30% of metal in  
21 weight, 50 mg of the epoxy monomer (LY5052) and 19 mg of the hardener (Aradur 5052)  
22 were then added. The resulting solution was further sonicated for 30 min and drop casted in  
23 a PDMS mold with 4 pitches of 4 x 4 x 0.5 mm<sup>3</sup>. 5 µL drops were deposited in each pitch and  
24 the THF allowed evaporating. To obtain a sufficient thickness, the process was repeated 13  
25 times. After a 24h reticulation of the epoxy resin at room temperature, mechanically stable  
26 ~250 µm thick composite pellets were retrieved.

#### 34 35 *Structural and chemical characterizations*

36  
37 The chemical compositions were determined by chemical analysis using inductively coupled  
38 plasma mass spectrometry (ICP-MS, Pascher laboratory).

39  
40 FeCo NPs were characterized by transmission electron microscopy (TEM), using a 100kV Jeol  
41 JEM 1011F and a JEM-ARM200F Cold FEG microscope with corrected probe. For sample  
42 preparation, the particles were redispersed in toluene and a drop of the dispersion was  
43 deposited on a carbon coated copper grid. The chemical profile measured by energy loss  
44 spectroscopy were acquired using the Scanning TEM mode with a probe size of 0,15 nm and  
45 steps of 0.477 nm. Energy X-ray dispersive analysis were conducted routinely on a Scanning  
46 Electron Microscopy (SEM) JEOL 2100F equipped with a SSD Bruker detector to determine  
47 the relative FeCo content.

48  
49 Spatial-resolved electron energy loss spectroscopy (EELS) measurements were performed on  
50 probe-corrected scanning transmission electron microscope (STEM) FEI Titan Low-Base 60-

300 operating at 300 keV (fitted with a X-FEG® gun and Cs-probe corrector (CESCOR from CEOS GmbH)). EEL spectra were recorded using the spectrum-imaging (SPIM in 2D or spectrum-line (SPLI) in 1D) mode<sup>[38]</sup> in a Gatan GIF Tridiem ESR 865 spectrometer. The convergent semi-angle was of 25 mrad, the collection semi-angle was of 80 mrad and the energy resolution  $\sim 1.2$  eV.

XRD measurements were performed on a PANalytical Empyrean diffractometer using Co-K $\alpha$  radiation and equipped with a linear Pixcel1D detector. In a glovebox, few mg of the powder was sealed between two kapton sheets to prevent any air exposure. The in-situ annealing measurements were performed in a sealed chamber XRK900 from Anton Paar under a reducing atmosphere (1 bar, 5% H<sub>2</sub>, 95% N<sub>2</sub>). The powder patterns were measured at room temperature, 100°C, 200°C, 250°C, 300°C, 400°C, 500°C, 600°C, 700°C, 800°C then 30°C after cooling down at a rate of *ca.* 17°C/min (Figure S12). For FeCO-PA NPs, the two first steps at 100°C and 200°C were skipped. At each step the sample was maintained for 1h prior to the XRD acquisitions consisting of a 35-110° acquisition in 20 minutes with 0.067°.s<sup>-1</sup> as scan speed and a step of 0.052°, and three high-resolution acquisitions in the 35-38°, 64-67° and 88-91° region with an accumulation of 24 minutes.

The rietveld refinement for the determination of the order parameter S was performed using MAUD software.<sup>[37]</sup> the refinement involved the fit of the background polynomia, the scale factor, the profile parameters, the lattice parameters, one equivalent Debye-Waller factor and the occupancy rate of Co and Fe atoms on the special positions (000) and  $\left(\frac{111}{222}\right)$ . In order to keep the stoichiometry, the atomic occupancy were restrained using the relations below :

$$x_{Co}^{(000)} + x_{Co}^{\left(\frac{111}{222}\right)} = x_{Fe}^{(000)} + x_{Fe}^{\left(\frac{111}{222}\right)} = 1$$

$$x_{Co}^{(000)} + x_{Fe}^{(000)} = x_{Co}^{\left(\frac{111}{222}\right)} + x_{Fe}^{\left(\frac{111}{222}\right)} = 1$$

With  $x_{Co}^{(000)}$  corresponding to  $r_A$  in eq(1).

1  
2  
3 Mössbauer spectra were measured at 300 K and 5K using a  $^{57}\text{Co}$  source (WISSEL). Samples  
4 were prepared in the glovebox, and extreme care was taken to avoid oxidation during  
5 transfer to the apparatus. The analysis of Mossbauer spectra was performed by fitting the  
6 data by Lorentzian shape peaks and applying a least-squares method using Recoil software.  
7  
8  
9

10  
11 The  $^{59}\text{Co}$  FNR experiments (NMR in ferromagnets) were performed at 2K without any  
12 external static field in a home-made spectrometer. The integrated spin-echo intensity was  
13 recorded using a broadband un-tuned (high-pass design) pulsed FNR spectrometer with  
14 phase-sensitive detection and automated frequency scanning (pulse length: 5  $\mu\text{s}$ , delay: 3  
15  $\mu\text{s}$ ). The frequency response of the setup is flat within 0,5 dB. In order to prevent oxidation  
16 the samples were prepared in the glove box and sealed in regular NMR tubes with vacuum  
17 grease and epoxy resin.  
18  
19  
20  
21  
22  
23  
24  
25  
26

### 27 *Physical characterizations*

28  
29  
30 Magnetic measurements were performed using a Quantum Design Physical Property  
31 Measurement System (PPMS) in the Vibrating Sample Magnetometer (VSM) configuration.  
32 For the FeCo NPs, 10 mg of powder were introduced in a Teflon cap sealed by vacuum  
33 grease. For the composite, the pellet was directly mounted on a quartz sample holder. 3T  
34 magnetization cycles were recorded at 300K and 5K after a 3T field cooling.  
35  
36  
37  
38  
39

### 40 **Supporting Information Available**

41  
42 Additional characterizations of FeCo-PA and FeCo-HDAHCl NPs : TEM images (as a function  
43 of acid concentration and reaction time) and the corresponding size distribution, Fe and Co  
44 elemental distribution determined by EELS (2D mapping and line profiles) and EDX, XRD  
45 pattern and 5K magnetization curves. Mössbauer spectrum recorded at 300K for FeCo-  
46 HDAHCl NPs and the full set of parameters used for Mössbauer analysis. FNR spectrum and  
47 the corresponding fit for FeCo-PA NPs. Temperature profile applied during In situ XRD, and  
48 diffractograms obtained on FeCo-PA NPs.  
49  
50  
51  
52  
53

54  
55 Additional characterizations of 30 and 60% loaded composite : TEM images, 300K  
56 magnetization curves of FeCo-HDAHCl and 30 and 60% loaded composite, and theoretical  
57 and experimental loading in weight percentage of the composite.  
58  
59  
60

## References

- [1] V. Korenivski, *J. Magn. Magn. Mater.* **2000**, 215–216, 800–806.
- [2] H. Yun, X. Liu, T. Paik, D. Palanisamy, J. Kim, W. D. Vogel, A. J. Viescas, J. Chen, G. C. Papaefthymiou, J. M. Kikkawa, et al., *ACS Nano* **2014**, 8, 12323–12337.
- [3] L. Wu, A. Mendoza-Garcia, Q. Li, S. Sun, *Chem. Rev.* **2016**, 116, 10473–10512.
- [4] S. Sun, *Adv. Mater.* **2006**, 18, 393–403.
- [5] N. Liakakos, T. Blon, C. Achkar, V. Vilar, B. Cormary, R. P. Tan, O. Benamara, G. Chaboussant, F. Ott, B. Warot-Fonrose, et al., *Nano Lett.* **2014**, 14, 3481–3486.
- [6] A. Bordet, L.-M. Lacroix, P.-F. Fazzini, J. Carrey, K. Soulantica, B. Chaudret, *Angew. Chem. Int. Ed.* **2016**, 55, 15894–15898.
- [7] L. Mohammed, H. G. Goma, D. Ragab, J. Zhu, *Particuology* **2017**, 30, 1–14.
- [8] L.-M. Lacroix, D. Ho, S. Sun, *Curr. Top. Med. Chem.* **2010**, 10, 1184–1197.
- [9] L.-M. Lacroix, S. Lachaize, A. Falqui, M. Respaud, B. Chaudret, *J. Am. Chem. Soc.* **2009**, 131, 549–557.
- [10] J. M. D. Coey, *Magnetism and Magnetic Materials*, Cambridge University Press, Cambridge, **2010**.
- [11] R. Ferrando, J. Jellinek, R. L. Johnston, *Chem. Rev.* **2008**, 108, 845–910.
- [12] T. Ogawa, H. Takano, H. Kura, M. Takahashi, *J. Appl. Phys.* **2012**, 111, 07B533.
- [13] D. Kodama, K. Shinoda, K. Sato, Y. Konno, R. J. Joseyphus, K. Motomiya, H. Takahashi, T. Matsumoto, Y. Sato, K. Tohji, et al., *Adv. Mater.* **2006**, 18, 3154–3159.
- [14] F. Fiévet, S. Ammar-Merah, R. Brayner, F. Chau, M. Giraud, F. Mammeri, J. Peron, J.-Y. Piquemal, L. Sicard, G. Viau, *Chem. Soc. Rev.* **2018**, 47, 5187–5233.
- [15] Q. Yan, S. Li, E. Pang, Y. Wang, *Mater. Lett.* **2014**, 120, 185–188.
- [16] M. Y. Rafique, L. Pan, M. Zubair Iqbal, Q. Javed, H. Qiu, Rafi-ud-din, M. H. Farooq, Z. Guo, *J. Alloys Compd.* **2013**, 550, 423–430.
- [17] Y. Gu, Y. Cao, H. Chi, Q. Liang, Y. Zhang, Y. Sun, *Int. J. Mol. Sci.* **2013**, 14, 14204–14213.
- [18] X.-W. Wei, K.-L. Wu, G.-X. Zhu, Y.-J. Liu, W. Shi, X.-Z. Li, L.-L. Rong, L. Chen, F.-H. Wu, *J. Alloys Compd.* **2012**, 539, 21–25.
- [19] M. Abbas, M. N. Islam, B. P. Rao, K. E. Abou Aitah, C. Kim, *Mater. Lett.* **2015**, 139, 161–164.
- [20] C. Desvaux, C. Amiens, P. Fejes, P. Renaud, M. Respaud, P. Lecante, E. Snoeck, B. Chaudret, *Nat. Mater.* **2005**, 4, 750–753.
- [21] C. Desvaux, F. Dumestre, C. Amiens, M. Respaud, P. Lecante, E. Snoeck, P. Fejes, P. Renaud, B. Chaudret, *J. Mater. Chem.* **2009**, 19, 3268.
- [22] C. Desvaux, P. Lecante, M. Respaud, B. Chaudret, *J. Mater. Chem.* **2010**, 20, 103.
- [23] A. Meffre, B. Mehdaoui, V. Kelsen, P. F. Fazzini, J. Carrey, S. Lachaize, M. Respaud, B. Chaudret, *Nano Lett.* **2012**, 12, 4722–4728.
- [24] P. Panissod, C. Meny, *Appl. Magn. Reson.* **2000**, 19, 447–460.
- [25] M. F. Casula, G. Concas, F. Congiu, A. Corrias, A. Falqui, G. Spano, *J. Phys. Chem. B* **2005**, 109, 23888–23895.
- [26] Y. Liu, J. Luo, Y. Shin, S. Moldovan, O. Ersen, A. Hébraud, G. Schlatter, C. Pham-Huu, C. Meny, *Nat. Commun.* **2016**, 7, 11532.
- [27] B. deMayo, *J. Appl. Phys.* **1970**, 41, 1319.
- [28] G. Concas, F. Congiu, G. Ennas, G. Piccaluga, G. Spano, *J. Non-Cryst. Solids* **2003**, 330, 234–241.
- [29] J. Dekoster, E. Jedryka, C. Meny, G. Langouche, *EPL Europhys. Lett.* **1993**, 22, 433.

- 1  
2  
3 [30] M. Wojcik, J. P. Jay, P. Panissod, E. Jedryka, J. Dekoster, G. Langouche, *Z. Für Phys. B*  
4 *Condens. Matter* **n.d.**, *103*, 5–12.  
5 [31] J. P. Jay, M. Wójcik, P. Panissod, *Z. Für Phys. B Condens. Matter* **1996**, *101*, 471–486.  
6 [32] G. B. Chon, K. Shinoda, S. Suzuki, B. Jeyadevan, *Mater. Trans.* **2010**, *51*, 707–711.  
7 [33] M. Castiella, C. Gatel, J. F. Bobo, N. Ratel-Ramond, R. Tan, M. Respaud, M. J. Casanove,  
8 *Mater. Res. Express* **2015**, *2*, 086401.  
9 [34] B. E. Warren, *X-Ray Diffraction*, Addison-Wesley, **1969**.  
10 [35] N. Liakakos, B. Cormary, X. Li, P. Lecante, M. Respaud, L. Maron, A. Falqui, A. Genovese,  
11 L. Vendier, S. Koinis, et al., *J. Am. Chem. Soc.* **2012**, *134*, 17922–17931.  
12 [36] F.-L. Jin, X. Li, S.-J. Park, *J. Ind. Eng. Chem.* **2015**, *29*, 1–11.  
13 [37] K. Soulantica, A. Maisonnat, M.-C. Fromen, M.-J. Casanove, B. Chaudret, *Angew. Chem.*  
14 *Int. Ed.* **2003**, *42*, 1945–1949.  
15 [38] R. Arenal, F. de la Peña, O. Stéphan, M. Walls, M. Tencé, A. Loiseau, C. Colliex,  
16 *Ultramicroscopy* **2008**, *109*, 32–38.  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60