

**UNIVERSITY OF LEEDS**

This is a repository copy of *Texture analysis of thick bismuth ferrite lead titanate layers*.

White Rose Research Online URL for this paper:

<http://eprints.whiterose.ac.uk/82871/>

Version: Accepted Version

Proceedings Paper:

Palizdar, M, Mallick, D, Maity, T et al. (11 more authors) (2014) Texture analysis of thick bismuth ferrite lead titanate layers. In: Applications of Ferroelectric, International Workshop on Acoustic Transduction Materials and Devices and Workshop on Piezoresponse Force Microscopy, ISAF/IWATMD/PFM 2014. 2014 Joint IEEE International Symposium on the Applications of Ferroelectric, International Workshop on Acoustic Transduction Materials & Devices & Workshop on Piezoresponse Force Microscopy, 12-16 May 2014, State College, Pennsylvania. Institute of Electrical and Electronics Engineers , 1 - 3. ISBN 9781479938605

<https://doi.org/10.1109/ISAF.2014.6922999>

Reuse

Unless indicated otherwise, fulltext items are protected by copyright with all rights reserved. The copyright exception in section 29 of the Copyright, Designs and Patents Act 1988 allows the making of a single copy solely for the purpose of non-commercial research or private study within the limits of fair dealing. The publisher or other rights-holder may allow further reproduction and re-use of this version - refer to the White Rose Research Online record for this item. Where records identify the publisher as the copyright holder, users can verify any specific terms of use on the publisher's website.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

Texture analysis of thick bismuth ferrite lead titanate layers

Meghdad Palizdar^{1,7}, Dhiman Mallick², Tuhin Maity², Saibal Roy², Tim P. Comyn¹, Tim J. Stevenson¹, Chris M. Fancher³, Jacob L. Jones³, Stephen F. Poterala⁴, Gary L. Messing⁴, Ender Suvaci⁵, Annette P. Kleppe⁶, Andrew J. Jehcoat⁶ and Andrew J Bell¹

¹Institute for Materials Research, University of Leeds, Leeds, LS2 9JT, UK

²Micropower-Nanomagnetics Group, Tyndall National Institute, University College Cork, Cork, Ireland

³North Carolina State University, Raleigh NC, 27695, USA

⁴Department of Materials Science and Engineering, Pennsylvania State University, University Park

⁵Department of Materials Science and Engineering, Anadolu University, Eskisehir, Turkey

⁶Diamond Light Source Ltd, Diamond house, Didcot, Oxfordshire

⁷Training and R&D department, GPG Inspection, Dusseldorf, Germany

Email: Palizdar@cpg-gmbh.de

Abstract— The template grain growth technique was used to synthesis textured 60BiFeO₃-PbTiO₃ (60:40BFPT) by using platelets of BaTiO₃ as template. Synchrotron measurement clearly showed textured 60:40BFPT. Moreover, in situ high energy synchrotron radiation was employed to investigate the influence of an external electric field on crystallographic structure of mixed phase 60:40BFPT. Application of an electric field ≥ 1 kV/mm resulted in phase transformation from mixed rhombohedral/tetragonal phases ($\approx 73.5\%$ tetragonal / 26.5% rhombohedral) to predominately tetragonal phase ($\approx 95\%$) at applied field of 6 kV/mm. A crystallographic texture refinement was done by using software package materials analysis using diffraction (MAUD) with a 4th order spherical harmonic orientation distribution function (ODF). This refinement was completed using a P4mm-Cm structure model. Texture coefficients were constrained such that the equivalent texture coefficients of each phase are the same. The resulting texture refinement determined that sample has a 1.3 multiples of random distribution (MRD) {100} crystallographic texture.

Keywords- Texture; Synchrotron; Phase transformation; Refinement

I. INTRODUCTION

In the past few decades lots of investigations have been done on materials with a morphotropic phase boundary to understand their possible phase transition behavior around the morphotropic phase boundary (MPB). The induced phase transition between the ferroelectric tetragonal and rhombohedral phases was highlighted first by Park in piezoelectric materials by applying external electric fields [1, 2]. The phase transition which was reported by Park resulted in a large d_{33} . Consequently, this encouraged different scientific groups in order to induce strain via phase transition inside the materials. To do so, alignment of the dipoles is critical. A material with an entirely random dipole direction has a high potential energy to transform, which precludes a phase transition. Hence, both single crystals and textured materials are points of interest in this regard. However, phase

transition in polycrystalline materials have been reported before, for example in PbZr_xTi_(1-x)O₃ (PZT) as well as K_{1/2}Bi_{1/2}TiO₃-Na_{1/2}Bi_{1/2}TiO₃ (KNBT) during the poling [3].

It is complicated to synthesis single crystals either process wise or price wise. Consequently, there is more intendency to deal with textured structures.

Bismuth ferrite and lead titanate (BFPT) possesses a morphotropic phase boundary (MPB) between the rhombohedral and tetragonal, with a spontaneous strain of 18% on the tetragonal side of the boundary. This considerable amount of strain is a good motivation in order to study about the possibility of employing phase transition in order to create high distortion inside the material.[4]. It is possible that this crystallographic distortion could be harnessed during transformation, generating unprecedented electric field induced strains. In addition, in BFPT the antiferromagnetic Néel temperature drops by approximately 300K on crossing the MPB from the rhombohedral to the tetragonal side [5]. It is of interest to investigate the influence of field-driven rhombohedral-tetragonal phase transitions across the MPB, to determine whether correctly oriented BFPT can provide both giant piezoelectric properties and significant magnetoelectric coupling, ultimately, turning antiferromagnetic ordering off and on.

In the current investigation the textured 60:40BFPT has been studied to evaluate the influence of applied external electric field. Furthermore, the synchrotron analysis was employed for texture investigation. Moreover, the magnetic properties of the specimen were studied.

II. EXPERIMENTAL

60:40BFPT which was made by using template grain growth method as detailed in [6,7]. Platelets of BaTiO₃ were supplied by Penn State and Anadolu Universities which were synthesized via the molten salt method [8].

Synchrotron diffraction was carried out at Beam I15 at the Diamond Light Source facility (Oxfordshire, UK). Sample bars were placed in a thin polypropylene oil bath and submerged in silicone oil, to avoid any electrical breakdown which would be

caused through air. A monochromatic beam X-rays of high energy was incident on the 1 x 6 mm² bar surface, while a voltage was applied across the 1 mm dimension, in 1 kV mm⁻¹ steps. Synchrotron data was collected using a 2D detector (MAR 3450). The Debye rings were “caked” into individual 2θ-intensity diffraction patterns, at +/- 5° between ψ = 0° and 355° as reported by Royles and Jonnes [3, 9].

Room temperature magnetic measurements were carried out using a SQUID magnetometer (superconducting quantum interference device, Quantum Design USA; Model MPMS XL5) over an applied magnetic field range of ±2 Tesla.

III. RESULTS

The effect of external applied electric field on the diffraction patterns of 60:40BFPT has been shown at figure 1. It shows that upon the application of an electric field a significant change to the phase-contributions occurs, as indicated by disappearing of splitted 200 peak at approximately 6.35 Å, showing a transition from mixed phase to single phase. Moreover, 002 tetragonal peak appears by increasing the external field, indicating the gradual formation of a tetragonal single phase. Sample experienced breakdown at field more than 6 kV/mm. Starting the phase transition even after applying low electric field at E=1 kV/mm could suggest the existence of textured structure. This is in agreement with what observed earlier by using synchrotron diffraction for texture analysis of 60:40BFPT [6].

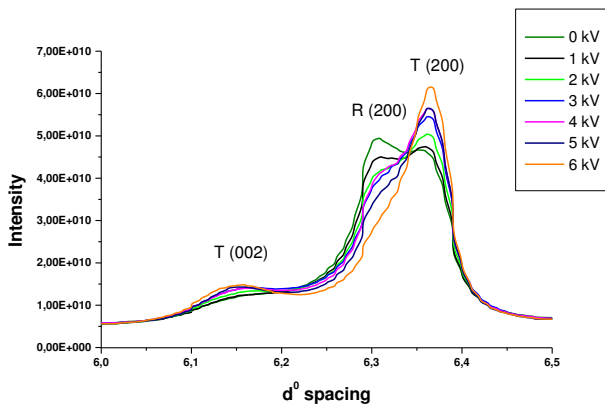


Figure 1. Diffraction patterns for 60:40 BFPT, after the application of electric field.

WinplotR software was used for profile fitting and also calculating the proportion of rhombohedral and tetragonal phases. The data revealed that before applying the external electric field the proportion of tetragonal phase was ≈ 73.5% while at E= 6 kV/mm the proportion of tetragonal phase changed to ≈ 95%. A tetragonal c/a ratio of ≈ 1.04 was calculated, somewhat lower than that reported by Comyn et al.

for 60:40BFPT pellets [9]. This could suggest reaction of the BaTiO₃ template with the matrix.

In order to have crystallographic texture refinement which could complete the texture investigation, the software package of materials analysis using diffraction (MAUD) was employed with a 4th order spherical harmonic orientation distribution function (ODF). It is important to notice that this refinement was completed using a P4mm+Cm structure model. Moreover, the refinement was applied for the sample which had not

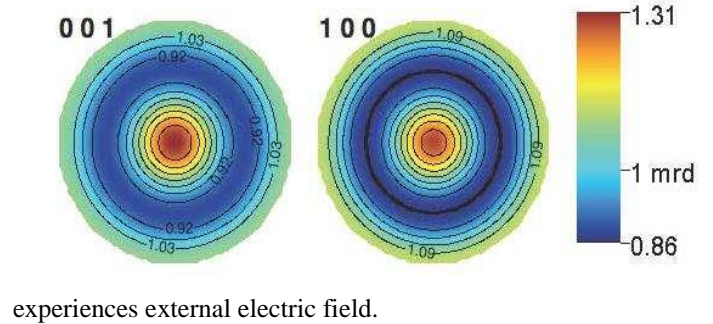


Figure 2. MAUD results for (001) and (100) tetragonal peaks for 60:40 BFPT, at application of zero electric field.

experiences external electric field. Texture coefficients were constrained such that the equivalent texture coefficients of each phase are the same. The resulting texture refinement determined that sample has a 1.3 multiples of random distribution (MRD) {100} crystallographic texture (Figure 2.). The final refinement error was high because MAUD is not capable of modeling the complex peak shapes observed in observed patterns. In addition, a crystallographic structure refinement using GSAS with two different starting structure models, P4mm+R3m and P4mm+Cm was used (Figure 3.). The resulting refinements suggested that the diffraction pattern was not representative of randomly oriented samples.

Refinements that used a P4mm+Cm starting model were able to correctly model the high 2θ peak asymmetry in the (111) reflection and capture a high 2θ reflection near the (222). The high 2θ asymmetry of the (111) and high 2θ peak of the (222) could not be modeled using a P4mm+R3m structure model. These features can be fit to a monoclinic structure. The resulting monoclinic structure that models the (111) and (222) reflections also models the (200) reflection. This leads to this suggestion that the room temperature crystallographic structure of obtained sample is a phase mixture of P4mm+Cm.

The sample was measured in MPMS XL 5 (Quantum Design) SQUID magnetometer to compare the M-H (magnetization vs. applied magnetic field) loops at room

temperature (300K) in two different directions perpendicular (in-plane) and parallel (out-of-plane) to the preferred c-axis of the oriented BFPT bar sample; the data are shown in Figure 3. The coercivity is ~ 940 Oe, with a remanent magnetization (M_R) of 80 m emu/gm and saturation magnetization (M_S) ~ 170 m emu/gm. The values are nearly same for both out-of-plane and in-plane measurements. The M-H loops confirm the existence of a ferromagnetic phase within the material. Since there is no such big difference between in-plane and out-of-plane magnetic measurements, it can be concluded that the sample is magnetically isotropic, which is in contrast into the synchrotron results of the 60:40BFPT sample prepared by the template grain growth method, where it is obvious that there is a considerable degree of texturing.

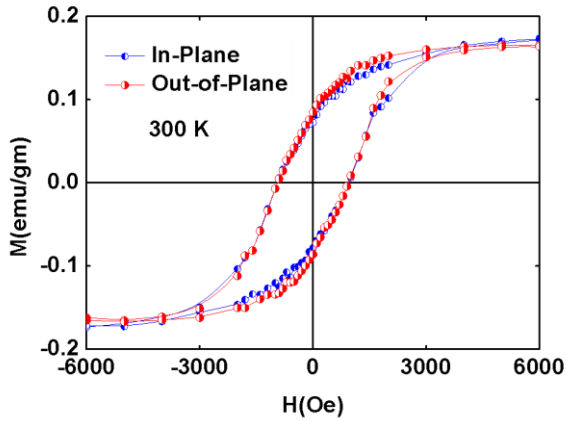


Figure 3. Comparison of M vs H loops for 60:40BFPT at room temperature (300K) with magnetic field perpendicular (in-plane), blue, and parallel (out-of-plane), red, to the preferred c-axis.

The similar in-plane and out-of-plane magnetic data can suggest that the sample is magnetically isotropic, but structurally anisotropic. We can infer from this that the observed magnetization is due entirely to the magnetically isotropic Fe rich secondary phase. We would anticipate that if the textured Aurivillius structure were indeed magnetic, then the resultant magnetic data would be heavily influenced by orientation. However, SQUID magnetometer data is in agreement with work by Das et al, who reported ferromagnetism in Ba-doped BiFeO_3 [10], that is, antiferromagnetic BiFeO_3 transforms to ferromagnetic ordering by doping with Ba^{2+} . They reported the magnetization of 1.2 emu/g for $\text{Bi}_{0.85}\text{Ba}_{0.15}\text{FeO}_3$. Hence, rigorous chemical analysis is essential to find out whether there is any magnetic secondary phase in the sample.

IV. CONCLUSION

In conclusion, synchrotron radiation experiments highlight significant differences in crystallographic orientation between perpendicular and parallel to the cast directions which suggests the existence of the textured structure in BFPT. We

show that an electric field induced phase transition occurs for textured 60:40BFPT in the system from mixed phase rhombohedral and tetragonal to predominately tetragonal phase.

REFERENCES

- [1] S.E. PARK, "Ultra-high strain and piezoelectric behavior in relaxor based ferroelectric single crystals". *Journal of Applied Physics*, 1997, **82**(4), pp.1804-1811.
- [2] B. NOHEDA, J.A. GONZALO, L.E. CROSS, R. GUO, S.E. PARK, D.E. COX and G. SHIRANE. Tetragonal-to-monoclinic phase transition in a ferroelectric perovskite: The structure of $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$. *Physical Review B*, 2000, **61**(13), pp.8687-8695.
- [3] A. ROYLES, A. BELL, A. JEPCOAT, A. KLEPPE, S. MILNE, T. COMYN, "Electric-field-induced phase switching in the lead free piezoelectric potassium sodium bismuth titanate", *Applies Physics Letter*, 2010, **97**, p.132909.
- [4] T. COMYN, T. STEVENSON and A. BELL. Piezoelectric properties of BiFeO_3 - PbTiO_3 ceramics. In: *IEEE*, 2004, pp.122-125.
- [5] W. M. ZHU, H.Y. GUO and Z.G. YE. Structural and magnetic characterization of multiferroic $\text{xBiFeO}_3 - [1-x]\text{PbTiO}_{3-x}$ solid solutions. *Physical Review B*, 2008, **78**(1), p.014401
- [6] M. PALIZDAR, T. COMYN, S. POTERALA, G. MESSING, E. SUVACI, A. KLEPPE, A. JEPCOAT, A. BELL, "Texture analysis of thick BiFeO_3 - PbTiO_3 layer synthesised by tape casting using synchrotron radiation", *IEEE international symposium on the application of ferroelectrics Aveiro, Portugal*, 2012.
- [7] M. PALIZDAR, T. COMYN, S. POTERALA, G. MESSING, E. SUVACI, A. KLEPPE, A. JEPCOAT, A. BELL, "Electric-field-induced phase switching in textured Ba-doped bismuth ferrite lead titanate", *IEEE international symposium on the application of ferroelectrics, Prague, Czech Republic*, 2012
- [8] S. F. POTERALA, CHANG Y. F., CLARK T., MEYER R. J., MESSING G., "Mechanistic Interpretation of the Aurivillius to Perovskite Topochemical Microcrystal Conversion Process", *Jr. Chem. Mater.* 2010, **22**, p. 2061
- [9] J. L. JONES, A. PRAMANICK and J.E. DANIELS. High-throughput evaluation of domain switching in piezoelectric ceramics and application to $\text{PbZr}_{0.6}\text{Ti}_{0.4}\text{O}_3$ doped with La and Fe. *Applied Physics Letters*, 2008, **93**(15).
- [10] T.P. COMYN, T. STEVENSON and A.J. BELL. Piezoelectric properties of BiFeO_3 - PbTiO_3 ceramics. *Journal De Physique Iv*, 2005, **128**, pp.13-17.