

ORIGINAL ARTICLE

HOW DOES STATIC STRETCHING INFLUENCE THE TENDONS MECHANICAL RESPONSE?

NATHALIA POLISELLO ROSSETTO¹, INÁCIO MARIA DAL FABBRO¹, SÉRGIO ROCHA PIEDADE¹

ABSTRACT

Objective: Analyze *in vitro* the mechanical response of bovine calcaneus tendons subjected to static stretching in three different intervals (15, 30, 45 s). **Methods:** Six groups of bovine calcaneus tendons (n=10) were formed according to the static stretching protocol: three different intervals (15, 30, 45 s) and initial stretching percentage (2.5% and 3.5%). The control group (n=10) did not perform prior stretching. At the end of the stretching tests, the specimens were subjected to stress rupture tests. **Results:** The values for force relaxation presented stability after the 30th second ($p < 0.0001$) at both levels of deformation. Greater force relaxation ($p < 0.0026$) and the least

tensile strength ($p = 0.0123$) was observed in the group that was subjected to the highest stretch percentage (3.5%). No difference was observed between the rupture parameters of the stretch and control groups. The variables, stretch duration and percentage did not demonstrate interaction. **Conclusion:** In relation to force relaxation, the 30 second interval seems to be the most effective when stretching tendons. This fact should be considered when establishing new clinical stretching protocols.

Laboratory investigation.

Keywords: Biomechanics. Collagen. Tendons. Time.

Citation: Rossetto NP, Dal Fabbro IM, Piedade SR. How does static stretching influence the tendons mechanical response? *Acta Ortop Bras.* [online]. 2013;21(5): 258-61. Available from URL: <http://www.scielo.br/aob>.

INTRODUCTION

The importance of regular physical activity is widely recognized and confirmed by countless scientific articles. It has a positive effect not only on the locomotor system but also improves functional performance of the cardiovascular and immunological systems^{1,2} whereby influencing quality of life. In this context, stretching exercises play an important role as they help regulate the functional balance of the musculoskeletal system.

Some studies have suggested that stretching can help prevent lesions, reduces tissue stiffness, and improve range of movement,³⁻⁶ it is also recommended by the American College of Sports Medicine⁷ as essential for those who regularly practice physical activities.

However, the parameters that govern the practice of stretching have still not been established⁸. The duration of stretching proposed in the literature is highly variable. Clinical studies, in general, analyze stretching intervals between 15 to 120 seconds,^{3,9-13} while *in vitro* studies consider 100,¹⁴ 600,¹⁵ or

even 1,800 seconds.¹⁶ Another parameter studied is the initial stretch percentage. Studies have shown that greater the initial deformation (stretch), greater is the tissue relaxation.^{14,17}

Wren et al.¹⁸ state that initial deformation has a direct effect on injury, and is the main parameter to predict rupture.

In clinical practice, the rule for stretching in most cases is empirical "stretch to a degree of tension that causes no pain".^{19,20} Lack of consensus, which very often is due to diversity of methodology, has raised questions that reflect the difficulty encountered in interpreting and comparing results.

Physiologically, when biological tissues are submitted to stretching they present progressive decrease in tensile strength resistance, until they reach a plateau and, consequently, the functional balance of the tissue.

This phenomenon is called force relaxation.²¹

Accordingly, the aim of this study was to analyze *in vitro* the mechanical force relaxation response, in tendons submitted to static stretching, considering intervals commonly used in clinical practice and verify the possible influence of stretching on the injurious event (rupture).

All the authors declare that there is no potential conflict of interest referring to this article.

1. Sport and Exercise and Sports Medicine of School of Medical Sciences of State University of Campinas - Unicamp. Campinas, SP, Brazil.

Work performed at the Exercise and Sports Medicine of School of Medical Sciences of State University of Campinas - Unicamp. Campinas, SP, Brazil.

Corresponding: Medicina do Exercício e do Esporte - FCM/Unicamp. Rua: Tessália Vieira de Camargo n°126, Cidade Universitária "Zeferino Vaz", Campinas, SP, Brazil, 13083-887. nprosetto@gmail.com / piedade@fcm.unicamp.br

Article received on 1/21/2013 and approved on 5/14/2013.

MATERIAL AND METHODS

The study material consisted of 70 specimens of bovine calcaneal tendons, from Nellore males, with average age of three years. The material was obtained after death, according to the ethical principles in animal experimentation. The research project was approved by the Committee of Ethics in Animal Use (CEUA/Unicamp), protocol 2005-1/2009.

After harvesting, the tendons were packed in plastic bags, wrapped in gauze dampened in a 0.9% saline solution. The tests were carried out within 5 hours after their obtainment at ambient temperature (28°C). For the performance of the tests, each specimen was carefully dissected, removing all the structures around the tendon, including the paratendon. Then rectangular strips were removed from the tendons using a scalpel.

The test were conducted with a LOYD TA 500 model (Fareham UK) texturometer type press, with a 500N load cell, force resolution of 0.01% and charging speed control between 0.0017 and 17mm/s.

Test protocol

Six groups of ten specimens of bovine calcaneal tendons were defined according to the static stretching protocol: intervals (15, 30, 45 seconds) and initial stretching percentages (2.5 and 3.5%). At the end of the stretching test, all the specimens were immediately submitted to the stress rupture test. The control group (n=10) only performed the stress rupture test.

Cross-sectional area

After the fixation of the gripper system to the Texturometer (Universal Testing Machine), the measurements of length, width and thickness were recorded with a digital caliper (Starret, model 727-6 A150; 0.01mm of precision). Each measurement was taken three times, considering the average of these to calculate the cross-sectional area (CSA).

This procedure favors the use of the tension concept (force/CSA), as it standardizes the force values in relation to the dimensions of the test body.

Mechanical tests

The specimens were submitted to uniaxial tensile tests, conducted at a speed of 10% of the initial length of the test specimen per second. Once the pre-established stretching was reached, force decreases were recorded at one second intervals, within the timeframe considered.

Immediately after the end of the stretching, all the specimens were submitted to the uniaxial tensile test until rupture at a speed of 100% of the initial length per second.

Data acquisition system

The data acquisition system consisted of a standard interface, coupled to the texturometer, and composed of a Pentium Pro computer and NEXIGEN 3.0 software.

Force and deformation were recorded continuously at the frequency of 10 Hz. The values of force (N) and time (s), were used as a basis to calculate: the percentage of force relaxation, for the stretching tests; and the tension (FR/CSA), the relative deformation (L/L0) and the rupture energy per cross-sectional area (FR*L0/CSA) for the rupture tests.

Statistical analysis

A descriptive analysis was used with presentation of position and dispersion measurements for numerical variables. Rank transform ANOVA was used to compare parameters among the factors studied, while the Kruskal-Wallis test was used to compare the independent groups. We used the SAS System for Windows program (Statistical Analysis System), version 9.2, SAS Institute Inc, 2002-2008, Cary, NC, USA. The confidence interval was set at 95%, and the comparison parameter was $p = 0.05$.

RESULTS

Table 1 presents the dimensional parameters of the specimens. At both levels of deformation studied, the force relaxation value in the 30-second interval was significantly higher than in the 15-second interval, yet without any differences when compared with the 45 second group ($p < 0.0001$). When comparing two different levels of deformation (2.5% and 3.5%) it was observed that the higher value resulted in a significant increase ($p < 0.0026$) in force relaxation. (Table 2) The analysis of interaction between the parameters time and stretching percentage showed that the effects are independent ($p = 0.1510$). (Table 2)

In the rupture tests it was possible to observe a significant decrease of the tensile strength required for rupture in the group that performed stretching with a higher rate of deformation (3.5%) ($p = 0.0123$). (Figure 1)

Table 1. Mean values of the dimensional parameters and standard deviation in the seven groups studied.

	Groups (% stretching/time)						
	2.5/15s	2.5/30s	2.5/45s	3.5/15s	3.5/30s	3.5/45s	Control
CSA (mm ²)	27.62 ± 7.27	24.67 ± 7.98	24.42 ± 14.13	26.12 ± 6.17	22.46 ± 8.76	23.6 ± 14.94	27.0 ± 8.18
L0 (mm)	14.51 ± 4.3	15.4 ± 3.89	16.39 ± 5.88	14.78 ± 3.43	11.89 ± 2.65	14.55 ± 3.75	14.3 ± 5.24

CSA: Cross-sectional area; L0: initial length..

Table 2. Statistical analysis of the mean values and standard deviation of the percentage of relaxation, obtained in the static stretching tests, in the three intervals of time (15s, 30s, 45s) and stretching percentages (2.5 and 3.5%) studied.

% stretching	Stretching time		
	15 s	30 s	45 s
2.5	31.57 ± 6.14 Ab	38.86 ± 5.57 Aa	38.60 ± 4.84 Aa
3.5	34.53 ± 4.09 Bb	43.27 ± 9.21 Ba	48.05 ± 5.43 Ba

N.B.: Measurements with the same letter do not differ at the probability of 5%, with rank transform ANOVA. Lower case letters compare the means on the horizontal axis, while upper case letters compare the means on the vertical axis.

The statistical analysis did not identify any influence of the stretching times (15, 30 and 45 seconds) and of the percentages of stretching (2.5% and 3.5%) in relation to the mean values of tensile strength, relative deformation, and rupture energy by cross-sectional area ($p > 0.05$) compared with the control group, without previous stretching. (Table 3)

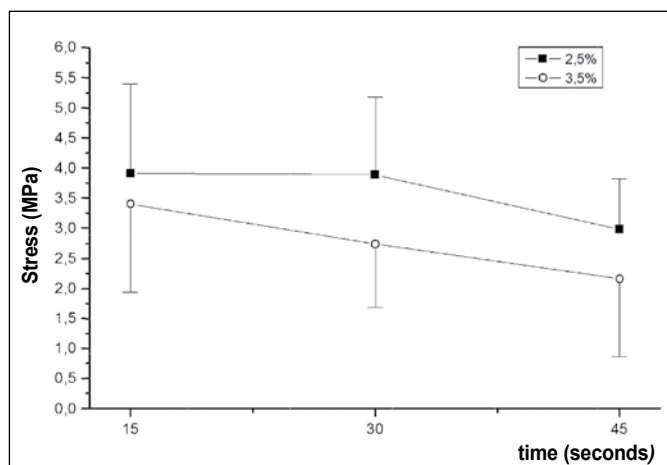


Figure 1. Mean values and standard deviation of the tensile strength obtained at the different stretching levels (2.5% and 3.5%) and time intervals (15 s, 30 s and 45 s) studied..

Table 3. Mean values, standard deviation and statistical analysis of the variables obtained in the rupture tests for the seven groups studied.

Groups	Tensile strength (mpa)	Relative deformation	Rupture energy/CSA (j/mm ²)
2.5 - 15 s	3.9 ± 1.4	1.2 ± 0.4	0.5 ± 0.1
2.5 - 30 s	3.9 ± 1.2	1.4 ± 0.3	0.6 ± 0.2
2.5 - 45 s	3.0 ± 0.8	1.2 ± 0.6	0.6 ± 0.2
3.5 - 15 s	3.4 ± 1.4	1.2 ± 0.5	1.2 ± 1.1
3.5 - 30 s	2.7 ± 1.2	1.4 ± 0.3	0.6 ± 0.2
3.5 - 45 s	2.1 ± 1.2	1.2 ± 0.6	0.6 ± 0.2
Control	3.0 ± 1.1	1.3 ± 0.3	0.4 ± 0.1
p-value	0.0561	0.2082	0.3778

CSA: cross-sectional area

DISCUSSION

The most important finding of this study was to identify that the parameters of time and stretching percentage influence the mechanical response of the tendon. Although several experimental studies indicate an influence of time and of the degree of stretching, in tendon response,^{14,17} there is not yet enough evidence to allow us to establish standardization for its performance.²²

In literature, the lack of uniformity in the execution of stretching is probably a product of the methodological diversity presented in the studies.^{23,24} Within this context, the study of the mechanical behavior of tendons to stretching is essential, as it can help

to establish more effective training strategies and possibly has a positive impact on injury prevention.^{12,25} The approach to this topic involves clinical and laboratory studies, where in vitro mechanical tests represent the initial line of research. These studies have concentrated on analyzing the mechanical response of the tissues (viscoelasticity), in order to establish conducts to be tested, and subsequently, applied in everyday practice. Fung²⁶ defined that 5% of relative deformation in the tendon represents the permissible upper limit for normal human activities. When analyzing the medial collateral ligament of rats, Provenzano *et al.*²⁷ demonstrated that 5.14% of deformation caused damage to the tissue.

In the present study, the tendons were submitted to percentage stretching of 2.5% and 3.5%, as these values do not exceed the physiological limit of the tendon. It is worth emphasizing that non-destructive tests (viscoelastic) are essential, as they can impose mechanical demands on the tendons, similar to those that occur in stretching exercises. In practice, these exercises are based on the pursuit of physiological and functional balance. During the mechanical tests, balance is defined in the stress X time diagram by the force relaxation stabilization plateau.

Screen²⁸ analyzed, under a laser microscope, the phenomenon of force relaxation of isolated Wistar rat tendon fascicles. The author notes that although about 50% of the relaxation occurs in the first 15 seconds of stretching, the phenomenon persists, even after the 200th second.

In this study, the force relaxation plateau was identified in the three stretching time intervals considered (15s, 30s and 45s). However, the 30-second interval was more effective as it provided greater tissue relaxation than the 15s interval, at a level similar to that observed for the 45s interval ($p < 0.0001$).

The tissue relaxation response is also influenced by the stretching percentage. Swedlik and Lanir¹⁴ and Diewald *et al.*¹⁷ emphasize that the greater the initial stretching, the greater the tissue relaxation. According to Wren *et al.*,¹⁸ this initial deformation is the main parameter to predict rupture, and to influence the occurrence of injuries. These data corroborate the findings of this study, while stretching of 3.5% presented a decrease in tensile strength ($p = 0.0123$), compared with the group with 2.5%, and also a higher tissue relaxation (stress relaxation) rate ($p = 0.0026$). Other studies demonstrated the existence of an increase in tendon compliance after stretching, suggesting a probable tendineal ability to resist tensile stress during activities.^{25,29} On the other hand, in this study, previous stretching did not influence the tendineal response in the rupture test (injury event). This fact is consistent with the lack of consensus observed in the literature, on the effectiveness of stretching in injury prevention.²² It is also worth emphasizing that although in vitro studies represent the initial line of research in the study of the mechanical response of tendons to stretching, the results obtained should be ratified by clinical trials.

CONCLUSION

The data obtained in this study allowed to conclude that the 30-second stretching interval was most effective, as it presented tissue relaxation superior to the 15-second interval, and similar to that observed for the 45-second interval, a fact to be considered when establishing of new clinical protocols for stretching.

REFERENCES

1. Osinbowale OO, Milani RV. Benefits of exercise therapy in peripheral arterial disease. *Prog Cardiovasc Dis*. 2011;53(6):447-53.
2. Walsh NP, Gleeson M, Shephard RJ, Gleeson M, Woods JA, Bishop NC, et al. Position statement. Part one: Immune function and exercise. *Exerc Immunol Rev*. 2011;17:6-63.
3. Bandy WD, Irion JM, Briggler M. The effect of static stretch and dynamic range of motion training on the flexibility of the hamstring muscles. *J Orthop Sports Phys Ther*. 1998;27(4):295-300.
4. Bixler B, Jones RL. High-school football injuries: effects of a post-halftime warm-up and stretching routine. *Fam Pract Res J*. 1992;12(2):131-9.
5. Rosenbaum D, Hennig EM. The influence of stretching and warm-up exercises on Achilles tendon reflex activity. *J Sports Sci*. 1995;13(6):481-90.
6. Safran MR, Seaber AV, Garrett WE Jr. Warm-up and muscular injury prevention. An update. *Sports Med*. 1989;8(4):239-49.
7. Franklin B, editor. *ACSM's Guidelines for exercise testing and prescription*. Baltimore: Williams and Wilkins; 2005.
8. Decoster LC, Cleland J, Altieri C, Russell P. The effects of hamstring stretching on range of motion: a systematic literature review. *J Orthop Sports Phys Ther*. 2005;35(6):377-87.
9. Amako M, Oda T, Masuoka K, Yokoi H, Campisi P. Effect of static stretching on prevention of injuries for military recruits. *Mil Med*. 2003;168(6):442-6.
10. Feland JB, Myrer JW, Schulthies SS, Fellingham GW, Measom GW. The effect of duration of stretching of the hamstring muscle group for increasing range of motion in people aged 65 years or older. *Phys Ther*. 2001;81(5):1110-7.
11. Pope R, Herbert R, Kirwan J. Effects of ankle dorsiflexion range and pre-exercise calf muscle stretching on injury risk in Army recruits. *Aust J Physiother*. 1998;44(3):165-172.
12. Ryan ED, Herda TJ, Costa PB, Defreitas JM, Beck TW, Stout J, et al. Determining the minimum number of passive stretches necessary to alter musculotendinous stiffness. *J Sports Sci*. 2009;27(9):957-61.
13. Verrall GM, Slavotinek JP, Barnes PG. The effect of sports specific training on reducing the incidence of hamstring injuries in professional Australian Rules football players. *Br J Sports Med*. 2005;39(6):363-8.
14. Sverdlík A, Lanir Y. Time-dependent mechanical behavior of sheep digital tendons, including the effects of preconditioning. *J Biomech Eng*. 2002;124(1):78-84.
15. Yamamoto E, Hayashi K, Yamamoto N. Mechanical properties of collagen fascicles from stress-shielded patellar tendons in the rabbit. *Clin Biomech (Bristol, Avon)*. 1999;14(6):418-25.
16. Pioletti DP, Rakotomanana LR. On the independence of time and strain effects in the stress relaxation of ligaments and tendons. *J Biomech*. 2000;33(12):1729-32.
17. Duenwald SE, Vanderby R Jr, Lakes RS. Viscoelastic relaxation and recovery of tendon. *Ann Biomed Eng*. 2009;37(6):1131-40.
18. Wren TA, Lindsey DP, Beaupré GS, Carter DR. Effects of creep and cyclic loading on the mechanical properties and failure of human Achilles tendons. *Ann Biomed Eng*. 2003;31(6):710-7.
19. Hartig DE, Henderson JM. Increasing hamstring flexibility decreases lower extremity overuse injuries in military basic trainees. *Am J Sports Med*. 1999;27(2):173-6.
20. de Weijer VC, Gorniak GC, Shamus E. The effect of static stretch and warm-up exercise on hamstring length over the course of 24 hours. *J Orthop Sports Phys Ther*. 2003;33(12):727-33.
21. Taylor DC, Dalton JD Jr, Seaber AV, Garrett WE Jr. Viscoelastic properties of muscle-tendon units. The biomechanical effects of stretching. *Am J Sports Med*. 1990;18(3):300-9.
22. Yeung EW, Yeung SS. A systematic review of interventions to prevent lower limb soft tissue running injuries. *Br J Sports Med*. 2001;35(6):383-9.
23. Small K, Mc Naughton L, Matthews M. A systematic review into the efficacy of static stretching as part of a warm-up for the prevention of exercise-related injury. *Res Sports Med*. 2008;16(3):213-31.
24. Witvrouw E, Mahieu N, Roosen P, McNair P. The role of stretching in tendon injuries. *Br J Sports Med*. 2007;41(4):224-6.
25. Teramoto A, Luo ZP. Temporary tendon strengthening by preconditioning. *Clin Biomech (Bristol, Avon)*. 2008;23(5):619-22.
26. Fung YC. *Biomechanics: mechanical properties of living tissues*. New York: Springer-Verlag; 1993.
27. Provenzano PP, Heisey D, Hayashi K, Lakes R, Vanderby R Jr. Subfailure damage in ligament: a structural and cellular evaluation. *J Appl Physiol*. 2002;92(1):362-71.
28. Screen HR. Investigating load relaxation mechanics in tendon. *J Mech Behav Biomed Mater*. 2008;1(1):51-8.
29. Su WR, Chen HH, Luo ZP. Effect of cyclic stretching on the tensile properties of patellar tendon and medial collateral ligament in rat. *Clin Biomech (Bristol, Avon)*. 2008;23(7):911-7.