



EMMANUEL JOÃO NOGUEIRA LEAL DA SILVA

**“EVALUATION OF CYTOTOXICITY AND
PHYSICOCHEMICAL PROPERTIES OF CALCIUM
SILICATE-BASED ENDODONTIC SEALER – MTA
FILLAPEX”**

***“AVALIAÇÃO DAS PROPRIEDADES FÍSICO-QUÍMICAS E
BIOLÓGICAS DE UM CIMENTO ENDODÔNTICO A BASE
DE SILICATO DE CÁLCIO – MTA FILLAPEX”***

PIRACICABA

2013

i



UNICAMP

UNIVERSIDADE ESTADUAL DE CAMPINAS

FACULDADE DE ODONTOLOGIA DE PIRACICABA

EMMANUEL JOÃO NOGUEIRA LEAL DA SILVA

**“EVALUATION OF CYTOTOXICITY AND
PHYSICOCHEMICAL PROPERTIES OF CALCIUM
SILICATE-BASED ENDODONTIC SEALER – MTA
FILLAPEX”**

Orientador: Prof. Dr. Alexandre Augusto Zaia

***“AVALIAÇÃO DAS PROPRIEDADES FÍSICO-QUÍMICAS E
BIOLÓGICAS DE UM CIMENTO ENDODÔNTICO A BASE
DE SILICATO DE CÁLCIO – MTA FILLAPEX”***

Tese de doutorado apresentada à faculdade de odontologia de Piracicaba, Universidade Estadual de Campinas, para obtenção do título de Doutor em Clínica Odontológica, na área de Endodontia.

Doctorate thesis presented to the Clinical Dentistry Postgraduation Programme of the Piracicaba Dentistry School of the University of Campinas to obtain the Ph.D. grade in Clinical Dentistry, in Endodontics area.

Este exemplar corresponde à versão final da dissertação defendido pelo aluno, e orientada pelo Prof. Dr. Alexandre Augusto Zaia

Assinatura do orientador

PIRACICABA

2013

iii

FICHA CATALOGRÁFICA ELABORADA POR
JOSIDELMA F COSTA DE SOUZA – CRB8/5894 - BIBLIOTECA DA
FACULDADE DE ODONTOLOGIA DE PIRACICABA DA UNICAMP

Si38a Silva, Emmanuel João Nogueira Leal da, 1985-
Avaliação das propriedades físico-químicas e biológicas de um cimento endodôntico a base de silicato de cálcio – MTA Fillapex / Emmanuel João Nogueira Leal da Silva. -- Piracicaba, SP : [s.n.], 2013.

Orientador: Alexandre Augusto Zaia.
Tese (Doutorado) - Universidade Estadual de Campinas, Faculdade de Odontologia de Piracicaba.

1. Endodontia. 2. Materiais dentários. 3. Obturação do canal radicular. I. Zaia, Alexandre Augusto, 1968- II. Universidade Estadual de Campinas. Faculdade de Odontologia de Piracicaba. III. Título.

Informações para a Biblioteca Digital

Título em Inglês: Evaluation of cytotoxicity and physicochemical properties of calcium silicate-based endodontic sealer MTA Fillapex

Palavras-chave em Inglês:

Endodontics

Dental materials

Root canal obturation

Área de concentração: Endodontia

Titulação: Doutor em Clínica Odontológica

Banca examinadora:

Alexandre Augusto Zaia [Orientador]

João Eduardo Gomes-Filho

Tauby de Souza Coutinho-Filho

Luciana Moura Sassone

Marco Antônio Húngaro Duarte

Data da defesa: 01-03-2013

Programa de Pós-Graduação: Clínica Odontológica



UNIVERSIDADE ESTADUAL DE CAMPINAS
Faculdade de Odontologia de Piracicaba



A Comissão Julgadora dos trabalhos de Defesa de Tese de Doutorado, em sessão pública realizada em 01 de Março de 2013, considerou o candidato EMMANUEL JOÃO NOGUEIRA LEAL DA SILVA aprovado.

Prof. Dr. ALEXANDRE AUGUSTO ZAIA

Prof. Dr. TAUBY DE SOUZA COUTINHO FILHO

Profa. Dra. LUCIANA MOURA SASSONE

Prof. Dr. MARCO ANTÔNIO HÚNGARO DUARTE

Prof. Dr. JOÃO EDUARDO GOMES FILHO

DEDICATÓRIA

Aos meus amados pais William e Rosália,

Agradeço a vocês que me ensinaram a sempre seguir em frente, traçando os melhores caminhos com os melhores valores, segurando na minha mão nos momentos de angústia e dúvidas e revelando-me através de gestos delicados os passos a serem seguidos para eu chegar até aqui, ensinando-me a trabalhar e lutar para atingir os meus ideais.

Amo muito vocês.

AGRADECIMENTOS ESPECIAIS

Ao meu orientador de mestrado e doutorado Prof. Dr. **Alexandre Augusto Zaia**, profissional exemplar, amigo e incentivador. Obrigado pela confiança depositada ao me dar a chance de ingressar na vida acadêmica e pelos ensinamentos transmitidos, que contribuíram para minha formação profissional e pessoal. Obrigado pelas palavras de apoio e correção nos momentos chave e de suporte e reconhecimento quando apropriado.

Ao Prof. Dr. **Tauby de Souza Coutinho Filho**, professor da Faculdade de Odontologia da Universidade do Estado do Rio de Janeiro, grande amigo e estimulador do meu interesse pela docência. Agradeço pelo apoio e pela oportunidade de poder desfrutar dos seus ensinamentos e conhecimentos. O seu amor pela endodontia e docência me inspiram a cada dia. Sempre faltarão palavras para expressar a enorme gratidão por tudo que você fez por mim.

AGRADECIMENTOS

À **Deus**, por ser fonte inesgotável de luz e por estar sempre ao meu lado ao longo dessa caminhada. Obrigado por ter me guiado sempre ao caminho mais certo e me colocado sempre nas companhias mais apropriadas e agradáveis.

À Universidade Estadual de Campinas (UNICAMP), na pessoa do Magnífico Reitor, Prof. Dr. **Fernando Ferreira Costa**.

À Faculdade de Odontologia de Piracicaba da Universidade Estadual de Campinas, nas pessoas do diretor Prof. Dr. **Jacks Jorge Júnior** e do diretor associado Prof. Dr. **Alexandre Augusto Zaia**.

À Prof. Dra. **Renata Cunha Matheus Rodrigues Garcia**, coordenadora geral dos cursos de Pós-Graduação e ao Prof. Dr. **Márcio de Moraes**, coordenador do curso de Pós-Graduação em Clínica Odontológica.

Aos docentes da Área de Endodontia da FOP/UNICAMP, Prof. Dr. **Francisco José de Souza Filho**, Profa. Dra. **Brenda Paula Figueiredo de Almeida Gomes**, Prof. Dr. **José Flavio Affonso de Almeida** e Prof. Dr. **Caio César Randi Ferraz**, pela convivência e por todos os ensinamentos transmitidos ao longo do curso de mestrado e doutorado. Muito obrigado!

Aos demais docentes da Faculdade de Odontologia de Piracicaba por toda ajuda e atenção dispensada durante meus anos em Piracicaba.

Aos professores integrantes da banca examinadora de qualificação e defesa de tese: Profa. Dra. **Danna Mota Moreira**, Prof. Dr. **João Eduardo Gomes-Filho**, Prof. Dr. **José Flavio Affonso de Almeida**, Profa. Dra. **Luciana Moura Sassone**, Prof. Dr. **Luciano Tavares**

Angelo Cintra, Prof. Dr. **Marcelo Rocha Marques**, Prof. Dr. **Marco Antônio Húngaro-Duarte**, Prof. Dr. **Marcos Roberto dos Santos Frozoni**, Prof. Dr. **Tauby de Souza Coutinho-Filho**, Profa. Dra. **Thais Accorsi-Mendonça** pela avaliação e colaboração em nosso trabalho.

À minha namorada **Andreia Bufalino** pelo carinho, amor e companherismo, durante este período.

Aos colegas do mestrado **Ana Carolina Pimentel Corrêa**, **Aniele Carvalho Lacerda**, **Ariane Cassia Salustiano Marinho**, **Cimara Barroso Braga Brum**, **Claudia Leal Sampaio Suzuki**, **Érika Manuela Astéria Clavijo**, **Thais Mageste Duque**, **Thiago Farias Rocha Lima** e **Tiago Pereira da Rosa** pelo companheirismo, amizade e pelo convívio durante todo este tempo.

Aos colegas do doutorado, **Ana Carolina Mascarenhas Oliveira**, **Carlos Augusto de Moraes Souto Pantoja**, **Carolina Carvalho de Oliveira Santos**, **Daniel Rodrigo Herrera Morante**, **Daniela Cristina Miyagaki**, **Fernanda Graziela Corrêa Signoretti**, **Gabriel Rocha Campos**, **Gissele Priscila Cruz Abi Rached**, **Jefferson José de Carvalho Marion**, **Juliana Yuri Nagata**, **Karine Schell de Moraes Nicastro**, **Letícia Maria Menezes Nóbrega**, **Marcos Sérgio Endo**, **Maria Rachel Figueiredo Penalva Monteiro**, **Nilton Vivacqua Gomes** pelo companheirismo, amizade e pelo convívio durante todo este tempo.

Aos funcionários da Endodontia da FOP-UNICAMP, pelo carinho com que sempre me receberam e trataram. Vocês tiveram grande participação neste meu caminho.

Aos demais funcionários da FOP-UNICAMP, por toda atenção e ajuda que me prestaram e pela alegria do convívio e oportunidade de crescimento pessoal.

A todos os alunos da graduação e da pós-graduação da FOP-UNICAMP, pela alegria do convívio e amizade que desenvolvemos ao longo destes anos.

A todos os grandes amigos que fiz ao longo de minha estadia na FOP-UNICAMP. Com vocês vivi momentos maravilhosos e inesquecíveis ao longo desses anos.

Aos pacientes da FOP-UNICAMP, pela oportunidade de evoluir profissionalmente e pessoalmente com o seu convívio e atendimento.

A todos os professores e amigos da **Faculdade de Odontologia da Universidade do Estado do Rio de Janeiro** pelos momentos maravilhosos e inesquecíveis que eu vivi e continuo vivendo neste local.

Aos meus grandes amigos de Niterói e do Rio de Janeiro, pela verdadeira amizade, pelo carinho e incentivo. São exemplos de que o tempo e a distância não são capazes de acabar com amizades verdadeiras. Vocês fazem muita falta.

Ao **Prof. Dr. Mark Herzberg**, por ter me recebido em seu laboratório e me orientado durante meu estágio de doutoramento na Universidade de Minnesota, Estados Unidos, pela acolhida em Minneapolis e toda a atenção a mim dispensada e o conhecimento transmitido durante o estágio, as quais fizeram com que esse período fosse extremamente enriquecedor tanto no âmbito pessoal e profissional.

Aos meus amigos que fiz durante o meu estágio de doutoramento na Universidade de Minnesota. O meu ano em Minneapolis foi simplesmente perfeito e inesquecível ao lado de todos vocês.

À Coordenação de aperfeiçoamento pessoal de nível superior (CAPES), pela concessão da bolsa de estudo para o doutorado.

À toda minha família, uma lista enorme de pessoas importantes para minha vida e, sem as quais seria difícil continuar, pelo amor, alegria, respeito e união.

A todos que de alguma forma contribuíram para a realização deste trabalho, que participaram junto comigo e estiveram presentes em minha vida.

Muito obrigado !

EPÍGRAFE

*“Em um determinado dia, em uma dada circunstância, você acha que você tem um limite. E então você busca esse limite e encosta nele, e então você pensa: ‘**Certo, esse é o limite**’. Logo que você atinge esse limite, alguma coisa acontece e de repente você pode ir um pouco mais longe”.*

Ayrton Senna

RESUMO

O cimento endodôntico obturador MTA Fillapex® foi criado numa tentativa de aliar as propriedades físico-químicas e a capacidade seladora dos cimentos resinosos às excelentes propriedades biológicas do agregado trióxido mineral (MTA). Entretanto, ainda existe uma escassez de trabalhos na literatura avaliando as suas características físico-químicas e biológicas. Dessa forma, os objetivos deste estudo foram: 1) avaliar propriedades físico-químicas (radiopacidade, escoamento e pH) e biológicas (citotoxicidade) do cimento endodôntico MTA Fillapex e comparar com o cimento AH Plus, 2) realizar um acompanhamento a longo prazo do efeito citotóxico em fibroblastos 3T3 de diferentes cimentos endodônticos contemporâneos, e 3) avaliar a partir de um ensaio multiparamétrico a longo prazo os efeitos citotóxicos do MTA Fillapex e do AH Plus em uma cultura primária de osteoblastos humanos. Os resultados do estudo mostraram que embora o AH Plus tenha apresentado radiopacidade estatisticamente maior que o MTA Fillapex ($P < 0.05$), ambos os cimentos obtiveram os valores mínimos exigidos pela ISO 6876/2001. O MTA Fillapex apresentou um pH alcalino em todos os períodos experimentais, enquanto o AH Plus demonstrou um pH ligeiramente neutro, com diferenças estatisticamente significantes entre os cimentos ($P < 0.05$). Com relação ao escoamento, ambos os cimentos apresentaram os valores mínimos exigidos pela ISO 6876/2001, no entanto o AH Plus apresentou valor estatisticamente mais baixo do que o do MTA Fillapex ($P < 0.05$). Com relação a citotoxicidade, em todos os períodos testados o MTA Fillapex foi mais citotóxico do que o AH Plus ($P < 0.05$). Quando comparado com diversos cimentos endodônticos, novamente o MTA Fillapex apresentou os maiores valores de citotoxicidade ($P < 0.05$), permanecendo moderadamente citotóxico mesmo após 5 semanas de sua manipulação. Quando testados em um ensaio multiparamétrico utilizando culturas de osteoblastos humanos, ambos os cimentos foram citotóxicos sem apresentar nenhuma diferença significativa quando testados imediatamente após a manipulação ($P > 0.05$). No entanto, uma semana após sua manipulação o AH Plus se tornou não citotóxico em todos os parâmetros avaliados. Por outro lado, o MTA Fillapex permaneceu citotóxico durante todo

o período experimental, mostrando diferenças estatisticamente significantes quando comparados com o AH Plus ($P < 0.05$). Dentro da metodologia empregada e de acordo com os resultados apresentados, pode-se concluir que embora o MTA Fillapex tenha apresentado propriedades físico-químicas adequadas para a utilização na terapia endodôntica, o mesmo apresentou-se altamente citotóxico nas diversas condições testadas.

Palavras-chave: Endodontia; Materiais dentários; Obturação do canal radicular

ABSTRACT

The endodontic sealer MTA Fillapex® was developed in an attempt to combine the physicochemical properties and sealing capacity of resin-based cements to the excellent biological properties of mineral trioxide aggregate (MTA). However, little information exists regarding MTA Fillapex physicochemical properties. Thus, the aims of the present study were: 1) evaluate the physicochemical (radiopacity, flow and pH) and biological (cytotoxicity) properties of MTA Fillapex and compare it with AH Plus, 2) investigate MTA Fillapex effects on the cytotoxicity during a period of 5 weeks in 3T3 fibroblasts and compare with 7 different endodontic sealers, and 3) verify, through a multiparametric in vitro assay, the long term cytotoxic effects in human osteoblasts of the MTA Fillapex and compare it with AH Plus. The results of the study showed that although AH Plus presented higher radiopacity than MTA Fillapex ($P < 0.05$), both sealers showed ISO 6876/2001 minimum required values. MTA Fillapex presented alkaline pH in all experimental times, while AH Plus demonstrated slightly neutral pH ($P < 0.05$). Both sealers showed ISO 6876/2001 required values for flow, however AH Plus flow was significantly lower than that of MTA Fillapex ($P < 0.05$). In all tested periods, MTA Fillapex was more cytotoxic than AH Plus ($P < .05$). When compared to 7 different endodontic sealers, MTA Fillapex was associated with significantly less cell viability ($P < 0.05$) even after 5 weeks of manipulation. When tested in a multiparametric assay using human osteoblasts, no significant difference was found among the materials when fresh mixed ($p > 0.05$). After one week AH Plus become noncytotoxic, on all three parameters evaluated. Conversely, MTA Fillapex remained cytotoxic over the entire experimental period, showing significant differences when compared to AH Plus ($P < 0.05$). Within the employed methodology and according to the results can be concluded that although MTA Fillapex showed suitable physicochemical properties for use in endodontic therapy, it appeared highly cytotoxic in the different tested conditions.

Keywords: Endodontics; Dental materials; root canal obturation

SUMÁRIO

INTRODUÇÃO	1
CAPÍTULO 1	4
CAPÍTULO 2	19
CAPÍTULO 3	34
CONSIDERAÇÕES GERAIS	49
CONCLUSÃO	50
REFERÊNCIAS.....	51
ANEXO	53
APÊNDICE	56

INTRODUÇÃO

O propósito do tratamento endodôntico é a remoção do tecido pulpar, a eliminação da infecção no canal radicular e o adequado selamento do canal. A obturação do canal radicular é a etapa do tratamento endodôntico que objetiva o total preenchimento do sistema de canais radiculares recém descontaminado, a fim de impedir a microinfiltração bacteriana do meio oral, dos tecidos apicais e periapicais para o interior dos mesmos (Ray & Trope, 1995; Cohen & Burns, 2000; Barthel *et al.*, 2001). Esse preenchimento é considerado uma das chaves do sucesso da terapia endodôntica (Schilder, 1967; Saunders & Saunders, 1994).

A maioria dos tratamentos endodônticos utiliza-se da guta-percha em combinação com algum cimento endodôntico. A principal função do cimento é preencher espaços existentes entre a guta-percha e as paredes do canal radicular. Atualmente os cimentos endodônticos são comercialmente disponíveis em diversas fórmulas tais como cimentos à base de óxido de zinco e eugenol; cimentos ionoméricos; cimentos contendo hidróxido de cálcio e cimentos resinosos, dentre outros (Silva *et al.*, 2008). Quando o comportamento dos diferentes cimentos endodônticos que buscam aliar propriedades físicas, químicas e biológicas foi avaliado, verificou-se que todos apresentam significantes limitações, mostrando vantagens e desvantagens (Bouillaguet *et al.*, 2004).

Os esforços em se desenvolver materiais obturadores mais eficazes, aliados ao aperfeiçoamento das técnicas de obturação, fazem com que sejam desenvolvidos materiais

com propriedades favoráveis, tais com plasticidade, estabilidade dimensional, facilidade de inserção e remoção, radiopacidade e, principalmente biocompatibilidade (Siqueira-Jr. & Lopes, 2009). Durante a última década, o agregado trióxido mineral (MTA), uma material a base de silicato de cálcio, foi introduzido e ganhou muita popularidade em endodontia. O MTA foi desenvolvido na Universidade de Loma Linda e recebeu a aprovação do FDA para utilização em humanos no ano de 1998 (Parirokh & Torabinejad, 2010). O MTA é um pó que consiste de finas partículas hidrofílicas que tomam presa na presença de umidade. Este material é constituído principalmente de silicato tricálcico, óxido tricálcico, silicato dicálcico, óxido de silicato, aluminato tricálcico, além de pequenas quantidades de outros minerais que também são responsáveis pelas propriedades físico-químicas deste material, como por exemplo o óxido de bismuto adicionado para aumentar a radiopacidade do material (Parirokh & Torabinejad, 2010; Torabinejad *et al.*, 1995; Asgary *et al.*, 2005).

Apesar de não conter hidróxido de cálcio em sua formulação, após o endurecimento do MTA, é formado óxido de cálcio que ao reagir com os fluidos teciduais ou com água pode produzir hidróxido de cálcio. A presença de hidróxido de cálcio faz com que o cimento atinja um pH altamente alcalino (10.2~12.5), favorecendo as propriedades antimicrobianas desse material (Parirokh & Torabinejad, 2010; Lovato & Sedgley, 2011). Além dessas características, a alta biocompatibilidade (Torabinejad *et al.*, 1995a; Parirokh & Torabinejad, 2010; Silva *et al.*, 2012), associada à baixa microinfiltração (Torabinejad *et al.*, 1995b; Parirokh & Torabinejad, 2010b) e a capacidade de tomar presa, mesmo na presença de sangue ou de umidade (Torabinejad *et al.*, 1994), estão entre as vantagens adicionais do material. Devido as excelentes propriedades biológicas do material, no ano de

1999, Holland *et al.* sugeriram a utilização do MTA como um cimento obturador endodôntico. No entanto, apesar das diversas características favoráveis, o MTA não apresenta as propriedades físicas necessárias para ser utilizado como um cimento endodôntico, principalmente devido as dificuldades de manipulação (Roberts *et al.*, 2008).

Com base nas características biológicas favoráveis do MTA e buscando melhorar as desvantagens físicas da formulação do MTA convencional, novos cimentos obturadores a base de MTA foram lançados no mercado odontológico. Dentre essas novas formulações, um novo cimento que contém MTA em sua formulação, chamado de MTA Fillapex (Angelus, Londrina, PR, Brasil) foi introduzido recentemente. Segundo o fabricante sua composição é basicamente uma mistura do MTA, resina salicilato, resina diluente, resina natural, óxido de bismuto, sílica nanoparticulada e pigmentos. Segundo o fabricante o material é biocompatível apresentando alta radiopacidade, excelente escoamento, tempo de trabalho adequado e baixa solubilidade, proporcionando vedação através da expansão durante a presa. No entanto, até agora poucas são as publicações independentes sobre as propriedades físico-químicas e biológicas do MTA Fillapex e seu possível uso na prática clínica. Portanto o objetivo do presente estudo foi avaliar diferentes propriedades físico-químicas e biológicas do MTA Fillapex.

CAPÍTULO 1

Evaluation of Cytotoxicity and Physicochemical Properties of Calcium Silicate-based Endodontic Sealer MTA Fillapex

Emmanuel João Nogueira Leal da Silva, DDS, MSc,* Tiago Pereira Rosa, DDS,* Daniel Rodrigo Herrera, DDS, MSc,* Rogério C. Jacinto, DDS, MSc, PhD,*^Y Brenda Paula Figueiredo de Almeida Gomes, DDS, MSc, PhD* and Alexandre Augusto Zaia, DDS, MSc, PhD*

*Department of Restorative Dentistry, Endodontics Division, Piracicaba Dental School, State University of Campinas, Piracicaba, SP, Brazil, ^YEndodontics Division, Federal University of Pelotas, Pelotas, Rio Grande do Sul.

Address requests for reprints to Dr. Emmanuel JNL Silva, Department of Restorative Dentistry, Endodontics Division, Piracicaba Dental School, State University of Campinas, Av. Limeira 901, Piracicaba-SP, CEP-13414-018, Brazil. E-mail address: nogueiraemmanuel@hotmail.com

Acknowledgments

The authors deny any conflicts of interest related to this study.

Evaluation of Cytotoxicity and Physicochemical Properties of Calcium Silicate-based Endodontic Sealer MTA Fillapex

Abstract

Introduction: The aim of the study was to evaluate the cytotoxicity, radiopacity, pH and flow of a calcium silicate-based and an epoxy resin-based endodontic sealer: MTA Fillapex and AH Plus, respectively. **Methods:** Cytotoxicity, radiopacity and flow evaluation were performed following ISO requirements. pH was measured at periods of 3, 24, 72, 168 hours. Cytotoxicity was evaluated by MTT assay to check the Balb/c 3T3 cells viability at 1-4 week periods. Data were statistically analyzed by ANOVA and Tukey test with a significance level of 5%. **Results:** In all tested periods, MTA Fillapex was more cytotoxic than AH Plus ($P < .05$). Although AH Plus presented higher radiopacity than MTA Fillapex ($P < .05$), both sealers showed minimum required values. MTA Fillapex presented alkaline pH in all experimental times, while AH Plus cement demonstrated slightly neutral pH. and a flow significantly lower than that of MTA Fillapex ($P < .05$). **Conclusions:** Although MTA Fillapex was more cytotoxic than AH Plus, it demonstrated suitable physicochemical properties for an endodontic sealer.

Key Words

MTA Fillapex; AH Plus; Physicochemical Properties; Cytotoxicity; Root Canal Sealer

INTRODUCTION

The characteristics and physicochemical properties of endodontic sealers are fundamental to allow hermetic sealing, which with an adequate coronal restoration will avoid bacterial leakage (1, 2). Mineral trioxide aggregate (MTA) is a material consisting of tricalcium oxide and other mineral oxides such as tricalcium silicate and silicate oxide. The pH of the material has been determined as 12.5 when set, which is comparable with that of calcium hydroxide (3–6). MTA biocompatibility, low cytotoxicity, antimicrobial properties (3, 7), low microleakage (4, 8), and its ability to set in the presence of blood or moisture are among the material's additional advantages. Because of these properties, it has been used for several dental applications such as root-end filling, root repair materials, and pulp capping (3–5). However, despite its favorable characteristics, MTA does not exhibit the physical properties needed to be used as an endodontic sealer because of its working time, setting time, and difficult handling (9).

MTA Fillapex (Angelus, Londrina, PR, Brazil), a sealer based on calcium silicate, was introduced recently. Its composition after mixing is basically MTA, salicylate resin, natural resin, bismuth oxide, and silica. The manufacturer claims that it has excellent radiopacity, easy handling, a great working time, and low solubility, providing sealing through expansion during setting. However, up to now, there are limited independent publications about the physicochemical and biological properties of MTA Fillapex and its possible use in clinical practice. Thus, the aim of the present study was to evaluate the cytotoxicity, radiopacity, pH, and flow of MTA Fillapex sealer and to compare them with those of AH Plus (Dentsply, Konstanz, Germany).

MATERIALS AND METHODS

Cytotoxicity evaluation was performed according to ISO 10993-5 specifications (10). Radiopacity and flow evaluations were performed according to ISO 6876/2001 specifications (11). The pH level was measured at 3, 24, 72, and 168 hours. AH Plus cement was mixed according to the manufacturer's instructions for all the tests. MTA Fillapex is premixed, so further manipulations were unnecessary. The composition of the evaluated sealers is shown in Table 1.

TABLE 1. Sealers Tested and Their Composition

Material	Composition	Manufacturer
AH Plus	Epoxy paste: diepoxy, calcium tungstate, zirconium oxide, aerosol, and dye Amine paste: 1-adamantane amine, N.N'dibenzyl-5 oxanonandiamine-1,9, TCD-diamine, calcium tungstate, zirconium oxide, aerosol, and silicon oil	Dentsply (Konstanz, Germany)
MTA Fillapex	Salicylate resin, diluting resin, natural resin, bismuth oxide, nanoparticulated silica, MTA, pigments	Angelus (Londrina, Brazil)

Cytotoxicity

Discs of each sealer were fabricated under aseptic conditions in sterile cylindrical Teflon blocks with a 5-mm diameter and a 2-mm height. Excess flash material was removed with a sterile scalpel. Cytotoxicity of the sealers was assessed immediately after mixing and during 4 succeeding weeks. The extraction was made in cell culture medium using a surface area to volume ratio of approximately 150 mm²/mL between the surface of the samples and the volume of the medium (8). The extraction vials were agitated for 24

hours in a water bath at 37°C. Control samples containing only culture medium were treated similarly. Undiluted extracts were used for the testing.

Balb/c 3T3 cells (American Tissue Type Collection, Manassas, VA) were cultured in Dulbecco modified Eagle medium (Gibco, Grand Island, NY) supplemented with 10% fetal bovine serum (Sigma Chemical Co, St Louis, MO), 100 mg/mL streptomycin, and 100 mg/mL penicillin at 37°C in a humidified incubator under ambient pressure air atmosphere containing 5% CO₂. Confluent cells were detached with 0.25% trypsin and 0.05% EDTA for 5 minutes, and aliquots of separated cells were subcultured. Cells were seeded in 24-well plates (1x10⁵ cells/well). After overnight attachment, cells were treated with various extracts of sealers (500 µL/well) for a total of 4 weeks.

Cell viability was determined every week (for 4 weeks) using the 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl tetrazolium bromide (MTT) assay. After the removal of culture medium from each well, the cells were gently washed with 1.0 mL phosphate-buffered saline. The wash was replaced with an MTT-succinate solution (1 mg/mL; Sigma-Aldrich, St Louis, MO) for 4 hours. After aspiration of the solution, the cell monolayers were rinsed with double-distilled water, and then the water was completely removed. Formazan crystals produced within the cells using a succinate dehydrogenase reduction of MTT were dissolved using distaining solution (isopropanol–10%NP40–0.4N HCl). Aliquots (100 µL) of the solution were then transferred from each well to a 96-well plate, and the absorbance was measured at 490 nm using a microplate reader (Urit 660, Urit, Guillin Guanxi, China). The formazan content of each well was computed as a percentage of the control group (untreated cells). All assays were repeated 3 times to ensure reproducibility.

Cytotoxicity responses were rated as severe (30%), moderate (30%–60%), slight (60%–90%), or noncytotoxic (>90%) (12).

Radiopacity Test

Cylindric samples from each material were manufactured by pouring the manipulated cements into metallic rings measuring 10 mm in diameter and 1 mm in thickness. Five samples of each material were prepared. The filled rings were kept at 37°C until the cements were completely set. The specimens were then removed, and the thickness was checked with a digital caliper (700–126; Mitutoyo MTI Corp, Tokyo, Japan). All sealers were placed on 5 occlusal films (Insight; Kodak Company, Rochester, NY) along with an aluminum step wedge graduated from 1 to 10 mm Al (in 1-mm increments). Radiographs were taken by using a radiographic unit (XR 6010; Gnatus, Ribeirão Preto, SP, Brazil) operating at 60 kV and 10 mA, with the exposure set at 0.3 seconds and a focus-film distance of 30 cm. After processing, the radiographs were digitized by using Canon EOS XSi with the Canon 100-mm macro lens (Canon, Tokyo, Japan) and imported into Digora 1.51 for Windows software (Orion Corporation Soredex, Helsinki, Finland). The radiopacity value was determined according to the radiographic density, which was also converted into millimeters of aluminum. Conversion was performed as described previously by Húngaro Duarte et al (13).

pH Analysis

Shortly after manipulation, the sealers were carefully placed in plastic tubes (polyethylene) measuring 1.0 mm in internal diameter and 10.0 mm in length with only 1 open end with the aid of a lentulo spiral. Periapical radiographs were taken to confirm the

complete filling of tubes and the absence of bubbles. Eight samples were used for each material. After being filled and weighed, each specimen was immediately immersed in test glass tubes containing 10 mL deionized water (Permuton, Curitiba, PR, Brazil), which were then sealed with Parafilm (American National Can, Menasha, WI) and placed in oven at 37°C. The pH was measured with a pH meter (QM-400; Quimis, São Paulo, SP, Brazil) previously calibrated with solutions of known pH (4, 7, 10). Before the immersion of specimens, the pH of the deionized water was verified to be 6.5. After the removal of the specimens, the test tubes were shaken for 5 seconds before pH measurement. pH evaluations were performed always in fresh tubes containing deionized water at each evaluation period.

Flow Analysis

A final volume of 0.05 mL cement was prepared and put on a glass plate using a tuberculin syringe of 1.0 mL. At 180 ± 5 seconds after the onset of mixing, the second glass plate (50 x 50 x 3.2 mm and 20-g weight) was carefully and centrally placed on top of the sealer followed by weighting of approximately 100g to make a total mass on the plate of 120g. Ten minutes after the onset of mixing, the weight was removed, and the maximum and minimum diameters of the compressed sealer disks were measured with a digital caliper. Two conditions were necessary to validate the tests: the difference between the maximum and minimum diameters should not exceed 1.0 mm, and the compressed disk should have a uniform shape. If these conditions were not met, the test was repeated. Five samples for each sealer were used, and the mean of 3 measurements for each sample, expressed to the nearest millimeter, was taken as the sample flow. According to ISO

6876/2001 specifications (11) for the flow test, a disk with at least a 20-mm diameter should be obtained.

Statistical Analysis

Data were statistically analyzed by analysis of variance (ANOVA) and Tukey test by using SPSS software 15.0 (SPSS Inc, Chicago, IL). The significance level adopted was $P < .05$.

RESULTS

Cytotoxicity

The results of the MTT assay over all the time periods are represented in [Figure 1](#). AH Plus was moderately cytotoxic in fresh conditions, was mildly cytotoxic after 1 week, and became noncytotoxic after 2 weeks. Conversely, MTA Fillapex remained severely cytotoxic over the entire experimental period. In all tested periods, MTA Fillapex was more cytotoxic ($P < .05$) than AH Plus.

Radiopacity Test

The mean values for radiopacity (mm Al) of the sealers were as follows: AH Plus = 8.59 and MTA Fillapex = 7.06. Data were compared with minimal requirements as specified in ISO 6876/2001. Although ANOVA and the Tukey test showed statistically significant differences between sealers ($P < .05$), both sealers showed values complying with the previously mentioned requirements (minimum equivalent to 3 mm Al).

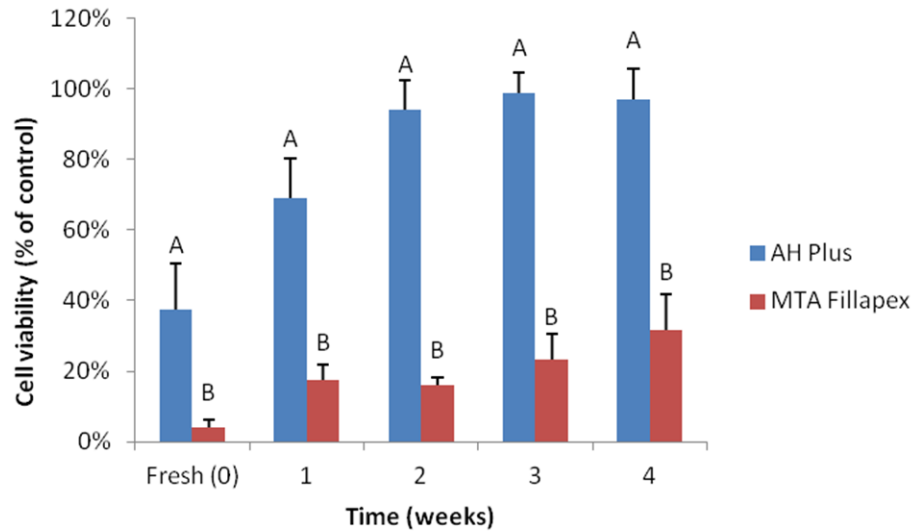


Figure 1. Cytotoxic effects following exposure to sealers in 3T3 fibroblast cells. Results are expressed as mean and standard deviation at different experimental periods. Different letters indicate statistically significant differences according ($P < .05$) in the same experimental time.

pH Analysis

The pH values at the different evaluation periods are shown in [Table 2](#). MTA Fillapex presented an alkaline pH in all experimental times, with the maximum pH value at the 3-hour evaluation. AH Plus cement showed a slightly neutral pH. Differences between sealers were statistically significant at all evaluation periods ($P < .05$).

TABLE 2. Means and Standard Deviations of pH Values at the Different Periods

	3 hours	24 hours	48 hours	72 hours	168 hours
AH Plus	7.08 ± 0.21 ^a	6.93 ± 0.08 ^a	6.78 ± 0.13 ^a	6.90 ± 0.13 ^a	6.92 ± 0.06 ^a
MTA Fillapex	9.68 ± 0.08 ^b	9.34 ± 0.32 ^b	8.25 ± 0.27 ^b	8.02 ± 0.31 ^b	7.76 ± 0.28 ^b
Control	6.50	6.50	6.50	6.50	6.50

Values followed by different superscript letters indicate statistically significant differences according to ANOVA ($P < .05$) in comparison between sealers in the same experimental time.

Flow Analysis

During the flow test, no repetitions were required besides those standardized at the beginning of the experiment. According to the flow test, MTA Fillapex sealer showed a flow greater than 20 mm (31.09 ± 0.67 mm). AH Plus presented a flow significantly lower (25.80 ± 0.83 mm, $P < .05$) than that of MTA Fillapex.

DISCUSSION

The endodontic sealer properties include good sealing, visible radiopacity, easy handling, good resistance, dimensional stability, high flow, and low solubility (14). Thereby, this study evaluated some of the main properties that should be considered for a suitable endodontic sealer. It is important to point out that all materials should be tested in a laboratory before being considered for clinical use. However, these tests must attend international standards. The ISO is the world's largest international standards developer. Cytotoxicity evaluation was performed according to ISO 10993-5 specifications. Radiopacity and flow evaluations were performed according to ISO 6876/2001.

MTA Fillapex was created in an attempt to combine the physicochemical properties of a root canal sealer with the biological properties of MTA. The present study assessed the cytotoxicity, radiopacity, pH, and flow of this novel endodontic sealer. The cytotoxicity analysis, which uses a long-term methodologic strategy, was used to evaluate MTA Fillapex for the first time. According to the present results, MTA Fillapex showed severe cytotoxicity when cells were exposed to fresh elute of the sealer. This toxicity did not decrease over the tested time periods. Our findings are in agreement with previous studies that showed strongly affected cell viability with MTA Fillapex (14, 15). One possible explanation for these results is the presence of toxic components such as salicylate resin, diluting resin, and silica in MTA Fillapex composition. AH Plus exhibited mild cytotoxicity in fresh conditions and became noncytotoxic after 2 weeks, probably as a result of the diminishment in the leaching of toxic substances present in this formulation.

Radiopacity is an essential property of endodontic sealing materials. Among other physical, chemical, and biological properties, the ideal root canal sealing material should have a certain degree of radiopacity to be clearly visible on radiographs and enhance the radiopacity of the root filling materials (16). International standards require a minimal radiopacity equivalent to 3.00 mm Al, yet some commercially available products do not meet this requirement (17). In this study, the radiopacity of both root canal sealers were found to be in agreement with ISO 6876/2001 recommendations (11). The differences between radiopacities of the tested root canal sealers in the present study probably are caused by the presence of different radiopacifying agents in each material. In AH Plus, the radiopacifying agent is zirconium oxide, and in MTA Fillapex it is bismuth oxide.

The pH of MTA Fillapex was significantly higher up to the 7-day period. This result indicates that MTA Fillapex has a strong capacity of releasing hydroxyl ions. A high pH activates alkaline phosphatase, which is present in the tissues, is involved in the mineralization process, and requires a pH around 8.6 to 10.3 to operate (18). The high pH of this sealer may also neutralize the acids secreted by osteoclasts, and this may help prevent further destruction of mineralized tissue. One disadvantage of its alkaline pH is a possible high cytotoxicity, which could explain the results shown by this material. However, its initial cytotoxicity could also be considered as an advantage. The high pH usually has a destructive effect on bacterial cell membranes and protein structure, which seems interesting, especially knowing that microorganisms can remain in the ramifications of the root canal system after chemomechanical preparation and intracanal dressing. Having antimicrobial activity, the sealers can act against such microorganisms, reducing their numbers and providing a better chance of successful root canal treatment (19).

In regard to flow, both MTA Fillapex and AH Plus showed acceptable values according to ISO 6786/2001 recommendations (11) that state the minimal flow required for cements is 20 mm. Flow is the ability of a sealer cement to penetrate into the irregularities and accessory canals of the root canal system, and it is considered to be a very important property—the greater the flow, the greater the ability to penetrate into irregularities. Conversely, if the flow is excessive, the risk of material extravasation to the periapex is increased, which could damage periodontal tissues (20). MTA Fillapex showed significantly superior flow values compared with AH Plus ($P < .05$). The different composition of the tested sealers seems to be the main factor related to their flow

differences. The flow ability is also influenced by the size of the sealer particles—the smaller the particles, the greater the flow ability of the sealer. Because of this property, MTA Fillapex will probably penetrate easier into the ramifications and irregularities of root canal walls than AH Plus. It is important to emphasize that it was not possible to compare the results obtained with MTA Fillapex with previous results because this is one of the pioneer studies using this material. Despite the flow ability shown by MTA Fillapex, this sealer does not seem to display bond strength to root dentin (21). However, recent studies have shown acceptable push-out bond strength values for MTA Fillapex, which were similar to those observed in samples filled with AH Plus sealer (22, 23). These values are related to the degree of residual moisture on dentin surface for both materials (23).

In conclusion, the results of this study showed that the MTA-based endodontic sealer MTA Fillapex showed suitable physicochemical properties although further studies evaluating the biological properties must be conducted to confirm its use in endodontic therapy.

REFERENCES

1. Ray HA, Trope M. Periapical status of endodontically treated teeth in relation to the technical quality of the root filling and the coronal restoration. *Int Endod J* 1995;28:12–8.
2. Santos J, Tjäderhane L, Ferraz C, et al. Long-term sealing ability of resin-based root canal fillings. *Int Endod J* 2010;43:455–60
3. Pariokh M, Torabinejad M. Mineral trioxide aggregate: a comprehensive literature review – Part I: chemical physical, and antibacterial properties. *J Endod* 2010;36:16-27.

4. Pariokh M, Torabinejad M. Mineral trioxide aggregate: a comprehensive literature review – Part II: leakage and biocompatibility investigations. *J Endod* 2010;36:190-202.
5. Pariokh M, Torabinejad M. Mineral trioxide aggregate: a comprehensive literature review – Part III: Clinical applications, drawbacks and mechanism of action. *J Endod* 2010;36:400-13.
6. Schwartz R, Mauger M, Clement D, et al. Mineral trioxide aggregate: a new material for endodontics. *J Am Dent Assoc* 1999;130:967–75.
7. Torabinejad M, Hong CU, Pitt Ford TR, et al. Cytotoxicity of four root-end filling materials. *J Endod* 1995;21:489–92.
8. Torabinejad M, Smith PW, Kettering JD, et al. Comparative investigation of marginal adaptation of mineral trioxide aggregate and other commonly used root-end filling materials. *J Endod* 1995;21:295–9.
9. Roberts HW, Toth JM, Berzins DW, et al. Mineral trioxide aggregate material use in endodontic treatment: a review of the literature. *Dent Mat* 2008;24:149–64.
10. International Organization for Standardization ISO 10993 Biological evaluation of medical devices – Part 5: Tests for *in vitro* cytotoxicity. Geneva, Switzerland: International Organization for Standardization; 2009.
11. International Organization for Standardization ISO 6876 dental root canal sealing materials. Geneva, Switzerland: International Organization for Standardization; 2001.
12. Dahl JE, Frangou-Polyzois MJ, Polyzois GL. *In vitro* biocompatibility of denture relining materials. *Gerodontology* 2006;23:17–22.
13. Húngaro Duarte MA, Kadre GDOL, Vivan RR, et al.. Radiopacity of Portland cement associated with different radiopacifying agents. *J Endod* 2009;35:737–40.
14. Bin CV, Valera MC, Camargo SE, Rabelo SB, et al.. Cytotoxicity and genotoxicity of root canal sealers based on mineral trioxide aggregate. *J Endod* 2012;38:495-50.
15. Scelza MZ, Linhares AB, da Silva LE, et al.. A multiparametric assay to compare the cytotoxicity of endodontic sealers with primary human osteoblasts. *Int Endod J* 2012;45:12-8.

16. Baksi Akdeniz BG, Eyuboglu TF, Sen BH, et al.. The effect of three different sealers on the radiopacity of root fillings in simulated canals. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2007;103:138-41
17. Tagger M, Katz A. Radiopacity of endodontic sealers: development of a new method for direct measurement. *J Endod* 2003; 29:751-4.
18. Eriksen EF. Cellular mechanisms of bone remodeling *Rev Endocr Metab Disord* 2010;11:219-27.
19. Gomes BP, Pedroso JA, Jacinto RC, et al. *In vitro* evaluation of the antimicrobial activity of five root canal sealers. *Braz Dent J* 2004;15:30-5.
20. Almeida JFA, Gomes BP, Ferraz CC, et al. Filling of artificial lateral canals and microleakage and flow of five endodontic sealers. *Int Endod J* 2007;40:692-9.
21. Sagsen B, Ustun Y, Demirbuga S, Pala K. Push-out bond strength of two new calcium silicate-based endodontic sealers to root canal dentine. *Int Endod J* 2011;44:1088-91.
22. Assmann E, Scarparo RK, Bottcher DE, Grecca FS. Dent bond strength of two mineral trioxide aggregate-based and one epoxy resin-based sealers. *J Endod* 2012;38:219-21.
23. Nagas E, Uyanik MO, Eymirli A, et al. Dentin moisture conditions affect the adhesion of root canal sealers. *J Endod* 2012;38:240-4.

CAPÍTULO 2

Long-term cytotoxic effects of contemporary root canal sealers

Emmanuel João Nogueira Leal da Silva – DDS, MSc, PhD student

Carolina Carvalho Santos – DDS, MSc, PhD student

**Alexandre Augusto Zaia – DDS, MSc, PhD, Adjunct Professor Endodontics
Department**

Piracicaba Dental School – Piracicaba - São Paulo - Brazil

Address requests for reprints to Dr. Emmanuel JNL Silva, Department of Restorative Dentistry, Endodontics Division, Piracicaba Dental School, State University of Campinas, Av. Limeira 901, Piracicaba-SP, CEP-13414-018, Brazil. E-mail address: nogueiraemmanuel@hotmail.com

Correspondence author

Dr Emmanuel JNL Silva

Av. Limeira 901, Piracicaba-SP, Brazil

CEP: 13414-018

E-mail: nogueiraemmanuel@hotmail.com

Phone: (55) 21 83575757

Fax: (55) 21 2610 8439

ABSTRACT

Objectives: The aim of the present study was to investigate the effects of root canal sealers on the cytotoxicity during a period of 5 weeks in 3T3 fibroblasts.

Materials and Methods: Fibroblasts (3T3, 1×10^5 cells per well) were incubated with elutes of fresh specimens from eight root canal sealers (AH Plus, Epiphany, Endomethasone N, EndoREZ, MTA Fillapex, Pulp Canal Sealer EWT, RoekoSeal and Sealapex) and with the elutes of the same specimens for 5 succeeding weeks after immersing in simulated body fluid. The cytotoxicity of all root canal sealers was determined using the MTT assay. Data were analyzed using ANOVA and Tukey's test.

Results: RoekoSeal was the only sealer that didn't show any cytotoxic effects ($p < 0.05$). All the other tested sealers exhibited severe toxicity initially (week 0). MTA Fillapex remained moderately cytotoxic after the end of experimental period. Toxicity of the other tested sealers decreased gradually over time. The evaluated root canal sealers presented varying degrees of cytotoxicity mainly in fresh mode.

Conclusions: RoekoSeal had no cytotoxic effect both freshly mixed and in the other tested time points. MTA Fillapex was associated with significantly less cell viability when compared to the other tested root canal sealers.

Key-words: Cytotoxicity; cell culture; fibroblasts; root canal sealers

INTRODUCTION

A complete sealing of the root canal system after cleaning and shaping is critical for successful endodontic therapy¹. In endodontic treatment, most root canals are filled with gutta-percha points in combination with a root canal sealer. Although endodontic sealers are designed to be used only within the root canal during endodontic therapy, sometimes they can extrude through the apical constriction^{2,3}. Indeed, they are often placed in intimate contact with the periapical tissues for an extended period of time^{2,4}. Thus, the biocompatibility of root canal sealers is an important factor in choosing the best material.

The sealers that have been currently used are based on zinc oxide-eugenol, calcium hydroxide, polydimethylsiloxane, silicone, epoxy resin and methacrylate resin. They exhibit a variable degree of cytotoxicity depending on the conditions under which testing was performed^{5,6}. Most of these sealers exert some toxic effect when they are fresh or in short time of test⁵⁻⁹. However these intervals are probably inadequate to predict the biologic response of sealers that may remain in contact with periapical tissues for decades. Only a few studies have attempted to evaluate the longitudinal cytotoxicity effects of root canal sealers^{7,8,10,11}.

Whereas the cytotoxicity of conventional endodontic sealers has been well documented^{6-8,10-12}, little is known about the long term toxicity of newer endodontic sealers such as Epiphany, RoekoSeal and MTA Fillapex. Previous reports have shown variable results^{4,13-15}, so it seems prudent to compare new and old sealers by standardized cell culture methods in the same study. Therefore, the aim of this study was to assess the cytotoxicity of eight root canal sealers, namely AH Plus, Endomethasone N, EndoRez,

Epiphany, MTA Fillapex, Pulp Canal Sealer EWT, RoekoSeal and Sealapex over long time periods. The reason for this study was that long term tests provide a more extensive toxicity profile that would be useful in to determine the clinical performance of root canal sealers.

Materials and Methods

Sample and extract preparation

Eight root canal sealers were evaluated: AH Plus, Endomethasone N, EndoRez, Epiphany, MTA Fillapex, Pulp Canal Sealer EWT, RoekoSeal and Sealapex. The tested materials, product names, manufacturers and components are listed in Table 1.

The sealers were mixed according to the manufacturers' instructions. Nine discs of each sealer were fabricated under aseptic conditions in sterile cylindrical Teflon blocks with 5 mm in diameter and 2 mm in height. Excess material was removed with a sterile scalpel. After one hour sealers were carefully removed from Teflon blocks. Cytotoxicity of the sealers was assessed immediately after mixing and for 5 succeeding weeks (weeks 1-5). The extraction was made eluting the sealers in cell culture medium using the surface area-to-volume ratio of approximately 150 mm²/mL between the surface of the samples and the volume of medium (16). The extraction vials were agitated for 24 h in a water bath at 37°C. Between tests, the specimens were aseptically removed and rinsed twice with sterile simulated body fluid (SBF) as previously reported^{11,12}. Control samples containing only culture medium were treated similarly. Undiluted extracts were used for the testing.

Table 1. Composition of materials and their manufactures

Root Canal Sealer	Components	
AH Plus, Dentsply Germany	Paste A: Epoxy Resins, Calcium Tungstate, Zirconium Oxide, Silica, Iron Oxide Pigments, Aerosil	Paste B: Adamantane amine, N,N-Dibenzyl-5-oxanonane, TCD-Diamine, Calcium Tungstate, Zirconium Oxide, Aerosil
Epiphany, Pentron USA	BisGMA, UDMA, Hydrophilic Methacrylates	
Endomethasone N, Septodont France	Powder: Hydrocortisone Acetate, Thymol Iodide, Barium Sulphate, Zinc Oxide, Magnesium Stearate	Liquid: Eugenol
EndoREZ, Ultradent USA	30% UDMA, Zinc Oxide, Barium Sulphate, Resins, Pigments	
MTA Fillapex, Angelus Brazil	Salicylate Resin, Diluting Resin, Natural Resin, Bismuth Trioxide, Nanoparticulated Silica, MTA, Pigments	
Pulp Canal Sealer EWT, SybronEndo USA	Powder: Silver Powder, Zinc Oxide, Thymol Iodide, Dimeric Acid Resin	Liquid: Clove Oil, Canada Balsam
RoekoSeal, Coltene Germany	Polymethylsiloxane, Silicone Oil, Paraffin-base Oil, Hexachloroplatinic Acid, Zirconium Dioxide	
Sealapex, SybronEndo USA	Paste A: Isobutyl Salicylate Resin, Silicon Dioxide, Bismuth Trioxide, Titanium Dioxide Pigment	Paste B: N-ethyl Toluene Solfanamide Resin, Silicon Dioxide, Zinc Oxide, Calcium Oxide

Cytotoxicity Assay

Balb/c 3T3 cells (American Tissue Type Collection; ATCC, Manassas, VA) were cultured in Dulbecco's Modified Eagle Medium (DMEM) (Gibco, Grand Island, NY) supplemented with 10% foetal bovine serum (FBS) (Sigma Chemical Co, St Louis, MO), 100 µg/mL of streptomycin, 100 mg/mL of penicillin at 37°C in humidified incubator under ambient pressure air atmosphere containing 5% CO₂. Confluent cells were detached with 0.25% trypsin and 0.05% ethylenediaminetetraacetic acid (EDTA) for 5 minutes, and aliquots of separated cells were subcultured. Cells were seeded in 24-well plates (1x10⁵ cell/well). After overnight attachment, cells were exposed to the extracts of the different tested sealers (500 µl/well). Cytotoxicity testing was repeated immediately after mixing (fresh), and then after 1, 2, 3, 4 and 5 weeks to study temporal trends in cytotoxicity of the sealers.

Cell viability was determined each week (1-5 weeks) by the MTT assay: 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl tetrazolium bromide (MTT). After the removal of culture medium from each well, the cells were gently washed with 1.0 mL of phosphate-buffered saline. The wash was replaced with an MTT-succinate solution (1mg/mL; Sigma-Aldrich, St Louis, MO) for 4 hours. After aspiration of the solution, the cell monolayers were rinsed with double-distilled water. Then the water was completely removed. Formazan crystals produced within the cells by succinate dehydrogenase (SDH) reduction of MTT were dissolved using destaining solution (isopropanol-10%NP40-0.4N HCl). Aliquots (100µl) of the solution were then transferred from each well to a 96-well plate and the absorbance was measured at 490 nm using a microplate reader (Hitachi, Tokyo, Japan).

The formazan content of each well was computed as a percentage of the control group (untreated cells). Cytotoxicity responses were rated as severe (30%), moderate (30%-60%), slight (60%-90%) or noncytotoxic (>90%)¹⁷.

Data and statistical analysis

All assays were repeated three times to ensure reproducibility. Toxicity of the endodontic sealers was assessed by measuring cell viability that had been determined by the SDH activity (MTT assay). The data were analyzed by one-way analysis of variance (ANOVA), and follow-up comparison between the groups was made using Tukey multiple comparison test (at 95% confidence interval level, $\alpha = 0.05$). Data were analyzed using the statistical software SPSS® (SPSS, Inc., Chicago, IL, USA).

Results

The results of the MTT assay over the entire time periods are listed in Table 2 and collectively represented in Figure 1. RoekoSeal was the only sealer that didn't show any cytotoxic effects in any time points and was not significantly different from the control ($p < 0.05$). The other sealers appeared to show some toxic effects when they were evaluated in fresh conditions. After one week, Endomethasone N and Pulp Canal Sealer EWT became noncytotoxic with no significant difference from the control group or RoekoSeal ($p < 0.05$). AH Plus fresh was moderately cytotoxic, was mildly cytotoxic after one week and become noncytotoxic after two weeks. Sealapex fresh was mildly cytotoxic and became noncytotoxic after three weeks. EndoREZ and Epiphany exhibited significant increases in the SDH activities over time ($p < 0.05$, table 1) and after 5 weeks both became noncytotoxic.

Conversely, MTA Fillapex remained severely and mildly cytotoxic over the entire experimental period. At the end of the fifth week, this sealer exhibited a toxicity level that was significantly more severe ($p < 0.05$) than the other tested sealers, which had become noncytotoxic.

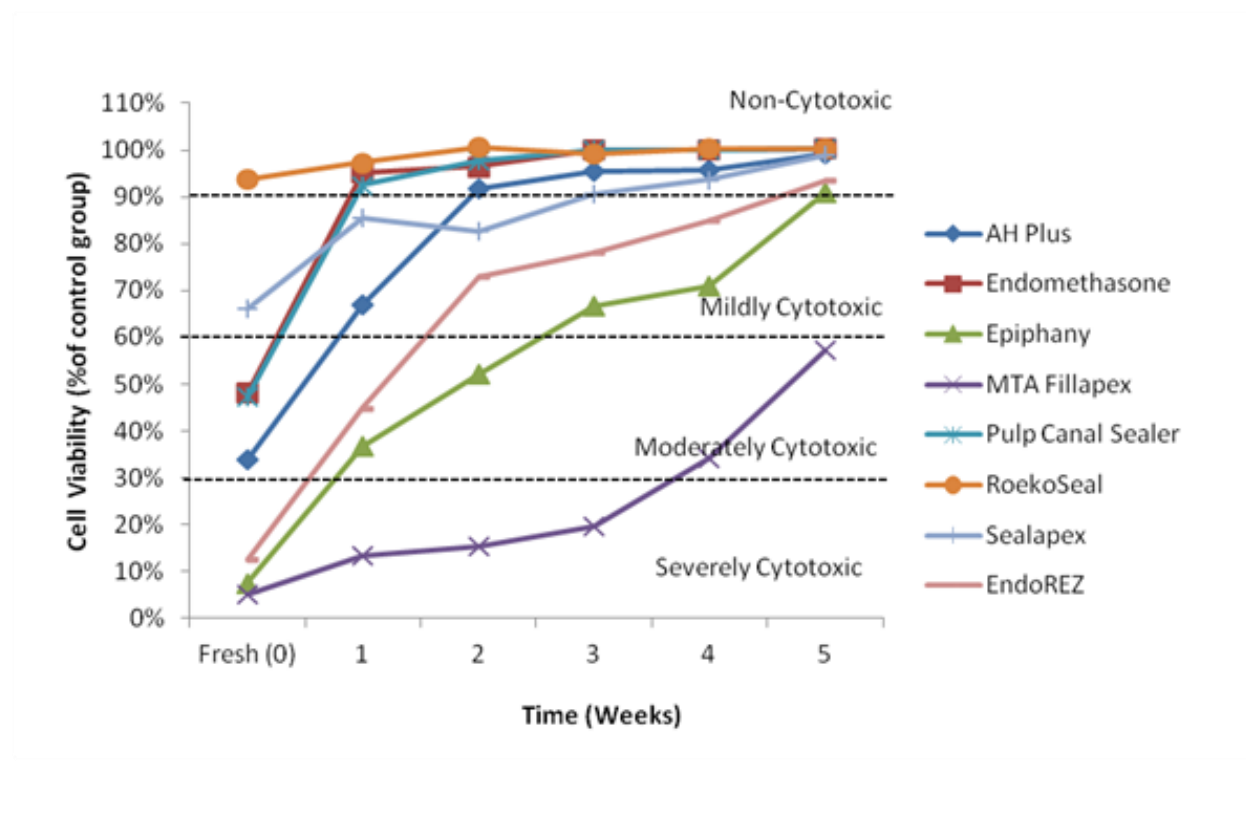


Figure 1 – A line chart depicting the changes in cell viability with time after the eight endodontic sealers were repeatedly immersed in a simulated body fluid. Values are expressed as percentages relative to the control group and classified as severe (<30%), moderate (<60%), slight (60%-90%) or non-cytotoxic (>90%).

TABLE 2. Succinate Dehydrogenase Activities Exhibited by 3T3 Cells in the Presence of Different Root Canal Sealers

Materials	Fresh	Week 1	Week 2	Week 3	Week 4	Week 5
Control	100 ^{A,1}	100 ^{A,1}	100 ^{A,1}	100 ^{A,1}	100 ^{A,1}	100 ^{A,1}
AH Plus	33.9 ^{D,3} (±4.6)	67.0 ^{C,2} (±5.3)	91.7 ^{AB,1} (±5.3)	95.4 ^{A,1} (±8.2)	95.8 ^{A,1} (±6.0)	99.1 ^{A,1} (±6.3)
Endomethasone N	48.2 ^{C,2} (±3.8)	95.1 ^{AB,1} (±6.4)	96.4 ^{A,1} (±6.3)	100.4 ^{A,1} (±15.4)	100.0 ^{A,1} (±9.3)	100.3 ^{A,1} (±7.6)
EndoREZ	12.4 ^{E,4} (±5.7)	44.8 ^{D,3} (±7.9)	73.0 ^{C,2} (±12.3)	78.1 ^{B,2} (±13.6)	84.9 ^{AB,1} (±10.9)	93.5 ^{A,1} (±13.2)
Epiphany	7.5 ^{E,5} (±4.4)	36.8 ^{D,4} (±2.5)	52.1 ^{D,3} (±8.7)	66.7 ^{B,2} (±12.4)	70.8 ^{B,2} (±9.6)	91.3 ^{A,1} (±12.6)
MTA Fillapex	5.0 ^{E,4} (±3.4)	13.4 ^{E,3} (±4.7)	15.3 ^{E,3} (±1.0)	19.7 ^{C,3} (±4.3)	34.0 ^{C,2} (±5.9)	57.3 ^{B,1} (±13.4)
Pulp Canal Sealer EWT	47.3 ^{C,2} (±3.7)	92.4 ^{AB,1} (±11.3)	97.7 ^{A,1} (±12.2)	100.5 ^{A,1} (±12.9)	100.1 ^{A,1} (±13.6)	100.3 ^{A,1} (±13.4)
RoekoSeal	93.7 ^{A,1} (±10.1)	97.3 ^{A,1} (±7.0)	100.7 ^{A,1} (±4.0)	99.1 ^{A,1} (±5.5)	100.4 ^{A,1} (±12.0)	100.2 ^{A,1} (±11.9)
Sealapex	66.0 ^{B,3} (±9.7)	85.4 ^{B,2} (±3.5)	82.7 ^{BC,2} (±3.4)	90.5 ^{AB,1} (±4.2)	93.6 ^{A,1} (±11.8)	98.9 ^{A,1} (±9.8)

The data are normalized against the control group. Values represent means (standard deviations) and are expressed as relative percentages of the SDH activities of the control group (100%). For each column, data with different letter superscripts denote significant difference ($p < 0.05$). For each row, data with different numerical superscripts denote significant difference ($p < 0.05$).

Discussion

Root canal sealers should be biocompatible since they may come in intimate contact with the periapical tissues for an extended period of time. The direct contact and the degradation of sealers over time could induce cytotoxic damage to cells and tissues and adversely affect the outcome of the root canal treatment^{2-4,18}. This study was designed to determine the longitudinal cytotoxicity behavior of eight contemporary endodontic sealers on fibroblasts. Although cytotoxicity testing of freshly mixed sealers is relevant as they are placed into the root canal system in a freshly mixed and incompletely polymerized stage, it is important to evaluate sealers over extended time periods after setting because it is probable that, during some period after clinical application, changes in cytotoxicity levels may be observed after diffusion of toxic components from the materials into the surrounding environment. It could be confirmed as all tested sealers showed different degrees of toxicity reduction after repeated testing at extended time periods.

This long term evaluation is also better than previous strategies that assessed cytotoxicity for the shorter term, because it enables the establishment of distinct toxicity profiles that are characteristic of each sealer. RoekoSeal was the only sealer that did not exhibit cytotoxic effects both freshly mixed and in the other tested time points. RoekoSeal is a sealer based in silicone, which is described as a biocompatible material¹⁹. The findings of the present study are in agreement with many previous studies, that have shown that RoekoSeal was only little or non-cytotoxic even in fresh conditions^{4,8,13,14}. The relatively severe and mildly cytotoxicity responses exhibited by the other sealers in fresh conditions, confirm the results reported in previous studies^{4,7,9,13,14,19-21}. This could be attributed to the

release of small amounts of toxic substances present in the sealers. Probably as a result of the diminishment in the leaching of these toxic substances, the cytotoxicity of the tested sealers decreased in the aged specimens. Previous reports with different methodologies showed similar citotoxic reduction after 5 weeks^{11,12,19}.

MTA Fillapex was created in an attempt to combine the physicochemical properties of an endodontic sealer with the excellent biological properties of MTA. According to the present results, MTA Fillapex showed a severe citotoxicity when cells were exposed to fresh elute of the sealer. This toxicity did not decrease over time. A longer period may then be required before the sealer can be rendered non-cytotoxic. The findings of the present study are in agreement with a previous study which has shown strongly affected cell viability by MTA Fillapex, using several methodologies^{15,22}. The results suggest the correlations between the components, such as Salicylate Resin, Diluting Resin and Silica with the citotoxic effects.

Although the relevance of *in vitro* toxicity tests to clinical conditions has been frequently questioned, it appears that biological risks of endodontic sealers is relatively high as the components of various root canal sealers may induce potential tissue toxicity, leading to apical periodontal tissue damage and inflammatory responses^{6,23}. This is unfortunate knowing that these materials might be placed in close contact with periapical tissues for long periods of time. Even in cases that the sealer does not reach directly the periapical region, there is always the possibility of elutable substances or degradation products from root canal fillings leaching through the dentinal tubules, lateral and accessory canals or apical foramina²⁴. However, according to the results of this study, after

5 weeks, endodontic sealers exhibited non-citotoxic effects to 3T3 fibroblast cells reflecting no long-term risk for adverse effects. So, despite the transitory irritability that endodontic sealers may cause to periapical tissues, endodontists should evaluate the advantages and disadvantages of sealer extrusion since the remaining areas not sealed in the apical region may serve as microorganism niches, initiating or perpetuating an endodontic failure²⁵.

Conclusion

The evaluated root canal sealers presented varying degrees of cytotoxicity mainly in fresh mode. RoekoSeal had no cytotoxic effect both freshly mixed and in the other tested time points. MTA Fillapex was associated with significantly less cell viability when compared to the other tested root canal sealers.

References

- 1- Schilder H. Filling root canal in three dimensions. *Dent Clin North Am* 1967; 11: 723-44.
- 2- Ricucci D D, Langland K. Apical limit of root canal instrumentation and obturation part 2. A histological study. *Int Endod J* 1998; 31: 394-409.
- 3- López-López J, Estrugo-Devesa A, Jané-Salas E, Segura-Egea JJ. Inferior alveolar nerve injury resulting from overextension of an endodontic sealer: non-surgical management using the GABA analogue pregabalin. *Int Endod J* 2012; 45: 98-104.
- 4- Lodiene G, Morisbak E, Bruzell E, Orstavik D. Toxicity evaluation of root canal sealers in vitro. *Int Endod J* 2008; 41: 72-7.

- 5- Brackett MG, Marshall A, Lockwood PE, Lewis JB, Messer RL, Bouillaguet S, Wataha JC. Inflammatory suppression by endodontic sealers after aging 12 weeks in vitro. *J Biomed Mat Res Part B: Appl Biomat* 2009; 91: 839-44.
- 6- Bratel J, Jontell M, Dahlgren U, Bergenholtz G. Effects of root canal sealers on immunocompetent cells in vitro and in vivo. *Int Endod J* 1998; 31: 178-88.
- 7- Araki K, Suda H, Spangberg LS. Indirect longitudinal cytotoxicity of root canal sealers on L929 cells and human periodontal ligament fibroblasts. *J Endod* 1994; 20: 67–70.
- 8- Schwarze T, Leyhausen G, Geurtsen W. Long-term cytocompatibility of various endodontic sealers using a new root canal model. *J Endod* 2002; 28: 749-53.
- 9- Silva E, Accorsi-mendonça T, Almeida J, Ferraz C, Gomes B, Zaia A. Evaluation of cytotoxicity and up-regulation of gelatinases in human fibroblast cells by four root canal sealers. *Int Endod J* 2012; 45: 49-56.
- 10- Miletic I, Devcic N, Anic I, Borcic J, Karlovic Z, Osmak M. The cytotoxicity of Roeko-Seal and AH plus compared during different setting periods. *J Endod* 2005; 31: 307–9.
- 11- Ames JM, Loushine RJ, Babb BR, Bryan TE, Lockwood PE, Sui M, Roberts S, Weller RN, Pashley DH, Tay FR. Contemporary methacrylate resin-based root canal sealers exhibit different degrees of ex vivo cytotoxicity when cured in their self-cured mode. *J Endod* 2009; 35: 225-8.

- 12- Pinna L, Brackett MG, Lockwood PE, Huffman BP, Mai S, Cotti E, Dettori C, Pashley DH, Tay FR. In vitro cytotoxicity evaluation of a self-adhesive, methacrylate resin-based root canal sealer. *J Endod* 2008; 34: 1085-8.
- 13- Eldeniz AU, Mustafa K, Orstavik D, Dahl JE. Cytotoxicity of new resin-, calcium hydroxide- and silicone-based root canal sealers on fibroblasts derived from human gingiva and L929 cell lines. *Int Endod J* 2007; 40: 329–37.
- 14- Karapinar-kazandağ M, Bayrak OF, Yalvaç ME, Ersev H, Tanalp J, Sahin F, Bayirli G. Cytotoxicity of 5 endodontic sealers on L929 cell line and human dental pulp cells. *Int Endod J* 2011; 44: 626-34.
- 15- Scelza MZ, Linhares AB, Da Silva LE, Granjeiro JM, Alves GG. A multiparametric assay to compare the cytotoxicity of endodontic sealers with primary human osteoblasts. *Int Endod J* 2012; 45: 12-8.
- 16- INTERNATIONAL STANDARDS ORGANIZATION. Biological evaluation of medical devices, part 5: tests for cytotoxicity: in vitro models. ISO 10993–5, 1st edition, 1992-12-15. Geneva: ISO, 1997.
- 17- Dahl JE, Frangou-polyzois MJ, Polyzois GL. In vitro biocompatibility of denture relining materials. *Gerodontol* 2006; 23: 17–22.
- 18- Waltimo TM, Boiesen J, Eriksen HM, Ørstavik D. Clinical performance of three endodontic sealers. *O Surg O Med O Pathol O Radiol Endod* 2001; 92: 89–92.
- 19- Scelza MZ, Coli J, Alves GG. Effect of time of extraction on the biocompatibility of endodontic sealers with primary human fibroblasts. *Braz Oral Res* 2012;26:424-30.

- 20- da Silva PT, Pappen FG, Souza EM, Dias JE, Bonetti-Filho I, Carlos IZ, Leonardo RT. Cytotoxicity evaluation of four endodontic sealers. *Braz Dent J* 2008;19:228-31.
- 21- Correa GT, Veranio GA, Silva LE, Hirata Junior R, Coil JM, Scelza MF. Cytotoxicity evaluation of two root canal sealers and a commercial calcium hydroxide paste on THP1 cell line by Trypan Blue assay. *J Appl Oral Sci* 2009;17:457-61.
- 22- Bin CV, Valera MC, Camargo SE, Rabelo SB, Silva GO, Balducci I, Camargo CH. Cytotoxicity and genotoxicity of root canal sealers based on mineral trioxide aggregate. *J Endod* 2012;38:495-500.
- 23- Silva-Herzog D, Ramírez T, Mora J, Pozos AJ, Silva LA, Silva RA, Nelson-Filho P. Preliminary study of the inflammatory response to subcutaneous implantation of three root canal sealers. *Int Endod J* 2011; 44: 440-6.
- 24- Bernath M, Szabo J. Tissue reaction initiated by different sealers. *Int Endod J* 2003;36:256-61.
- 25- Ricucci D, Siqueira JF JR. Fate of the tissue in lateral canals and apical ramifications in response to pathologic conditions and treatment procedures. *J Endod* 2010; 36: 1-15.

CAPÍTULO 3

A multiparametric assay to compare the long-term cytotoxicity of AH Plus and MTA Fillapex

E.J.N.L. Silva*

T. Accorsi-Mendonça**

A.C. Pedrosa***

E.J.L. Moreira**

J.M. Granjeiro***

A.A. Zaia*

*Department of Restorative Dentistry, Endodontic Division, Piracicaba Dental School – State University of Campinas. Piracicaba, Brazil

**Department of Endodontology, Grande Rio University, Rio de Janeiro, Brazil

***Bioengineering Division, National Metrology Institute, Quality and Technology, Duque de Caxias, Brazil

Running title: Long-term cytotoxicity of AH Plus and MTA Fillapex

Key-Words: AH Plus, cytotoxicity, cell culture, MTA Fillapex

Correspondence author

Dr Alexandre Augusto Zaia
Av. Limeira 901, Piracicaba-SP, Brazil
CEP: 13414-018
E-mail: zaia@fop.unicamp.br
Phone: (55) 19 8138 9898
Fax: (55) 19 3421 0144

ABSTRACT

Aim: To verify, through a multiparametric *in vitro* assay, the long term cytotoxic effects of the MTA Fillapex and to compare with AH Plus.

Methodology: Human osteoblast cells were incubated with elutes of fresh specimens from AH Plus and MTA Fillapex, and with elutes of the same specimens for 4 succeeding weeks. A multiparametric cell viability assay was performed, evaluating mitochondrial activity, membrane integrity and cell density. The results were analysed by one-way analysis of variance, complemented with the Tukey post-test ($P < .05$).

Results: No significant difference was found among the materials when fresh mixed ($p > 0.05$). After one week AH Plus become noncytotoxic, on all three parameters evaluated. Conversely, MTA Fillapex remained severely and mildly cytotoxic over the entire experimental period. At the end of the fourth week, this sealer exhibited a toxicity level that was significantly more severe than the AH Plus in all tested time points ($p < 0.01$), except in fresh conditions ($p > 0.05$).

Conclusions: Both materials showed high cytotoxic levels for human primary cells when freshly mixed. After one week AH Plus become noncytotoxic and MTA Fillapex remained cytotoxic over the entire experimental period, as shown by three different cell viability tests.

Key Words: AH Plus, cytotoxicity, cell culture, MTA Fillapex

INTRODUCTION

During the last decade, mineral trioxide aggregate (MTA), a calcium silicate-based material, has gained popularity in endodontics as a root-end filling and pulp-capping material, for the repair of root canal perforations, and for apexification (Torabinejad *et al.* 1993, Main *et al.* 2004, Felipe *et al.* 2006, Nair *et al.* 2008). MTA is a biocompatible, noncytotoxic, nonmutagenic, and neither genotoxic nor carcinogenic material (Braz *et al.* 2006, Ribeiro *et al.* 2006, Washington *et al.* 2011, Silva *et al.* 2012a). In addition, MTA has shown antibacterial (Eldeniz *et al.* 2006) and excellent sealing properties (Torabinejad & Parirokh 2010). However, despite its favorable characteristics, MTA does not exhibit the physical properties needed to be used as an endodontic sealer because of its working time, setting time, and difficult handling (Roberts *et al.* 2008).

MTA Fillapex (Angelus, Londrina, PR, Brazil), a sealer based on calcium silicate, was introduced recently. Its composition after mixing is basically MTA, salicylate resin, natural resin, bismuth oxide, and silica. The manufacturer claims that it has excellent radiopacity, easy handling, a great working time, and low solubility, providing sealing through expansion during setting. A recent study showed suitable radiopacity, pH and flow of MTA Fillapex (Silva *et al.* 2012b). However, in regard to its cytotoxicity and biocompatibility, controversial results have been presented (Gomes-Filho *et al.* 2011, Salles *et al.* 2012, Silva *et al.* 2012b, Tavares *et al.* 2012, Zmener *et al.* 2012). The biocompatibility of endodontic sealers is an important factor in choosing the best material, because endodontic sealers are often placed in intimate contact with the periapical tissues for an extended period of time (Ricucci & Langland 1998, Lodiene *et al.* 2008). Due to

these controversial results, more studies about MTA Fillapex cytotoxic behavior are required to be evaluated before its clinical indication.

Thus, the aim of this study was to assess, through a multiparametric *in vitro* assay, the long term cytotoxic effects of the MTA Fillapex on primary human osteoblasts (hOB) cell line. AH Plus (Dentsply, Germany) was employed as the reference material for comparison. The null hypothesis is that there are no differences between the tested endodontic sealers in any tested time point.

MATERIALS AND METHODS

Sample and extract preparation

Two root canal sealers were evaluated: AH Plus and MTA Fillapex. The tested materials, product names, manufacturers and components are listed in Table 1.

Table 1. Composition of the materials and their manufactures

Root Canal Sealer	Components	
AH Plus, Dentsply Germany	Paste A: Epoxy Resins, Calcium Tungstate, Zirconium Oxide, Silica, Iron Oxide Pigments, Aerosil	Paste B: Adamantane amine, N,N-Dibenzyl-5-oxanonane, TCD-Diamine, Calcium Tungstate, Zirconium Oxide, Aerosil
MTA Fillapex, Angelus Brazil	Salicylate Resin, Diluting Resin, Natural Resin, Bismuth Trioxide, Nanoparticulated Silica, MTA, Pigments	

The sealers were mixed according to the manufacturers' instructions. Discs of each sealer were fabricated under aseptic conditions in sterile cylindrical Teflon blocks with 5

mm in diameter and 2 mm in height. Excess flash material was removed with a sterile scalpel. Cytotoxicity of the sealers was assessed immediately after mixing and for up to 4 weeks. The extraction was made in cell culture medium using the surface area-to-volume ratio of approximately 50 mm²/mL between the surface of the samples and the volume of medium (International Organization for Standardization, 2009), for 24 h at 37°C. Between tests, the specimens were aseptically removed and rinsed twice with PBS. Control samples containing only culture medium were treated similarly. Undiluted extracts were used for the testing.

Culture of Osteoblastic Cells

Human osteoblasts on second passage (hOB) from the Rio de Janeiro Cell Culture Bank were subcultured for 24h at 37°C on 96-well culture plates (1·10⁴ cells per well). After 24 h, the medium was removed gently from each well and replaced by 200 µL of one of the selected test media (AH Plus and MTA Fillapex extracts) in triplicates and was incubated for a further 24 h. Medium not exposed to filling materials was used as a control of culture conditions. During the culture period, cells were incubated at 37°C in a humidified atmosphere of 5% CO₂ and 95% air.

Cytotoxicity assay

After 24 h of cell exposure to each extract medium, cytotoxicity was evaluated with a commercial kit (In Cytotox, Xenometrix, Allschwil, Switzerland) which allows the use of three different tests of cell survival and integrity on the same sample: XTT, neutral red (NR) and crystal violet dye elution (CVDE). The XTT test is based on the ability of mitochondrial dehydrogenase enzymes to convert the yellow water-soluble tetrazolium salt

XTT into orange-coloured soluble compounds of formazan, measured by their absorbance at 480 nm using a microplate UV/Vis spectrophotometer (PowerWave MS2; BioTek Instruments, Rio de Janeiro, RJ, Brazil). NR is a survival/ viability test based on the ability of living cells to incorporate NR dye on their lysosomes, where it accumulates on membrane-intact cells; the amount of dye incorporated can be measured at 540 nm. CVDE is a simple assay that evaluates cell density by staining DNA; after elimination of the excess dye, the absorbance at 540 nm is proportional to the amount of cells in the well (Deus *et al.* 2010, Scelza *et al.* 2012, Silva *et al.* 2012c).

RESULTS

The results of the hOB viability, as measured by the multiparametric cytotoxicity assay over the entire time periods are collectively represented in Figure 1 as a percentage of the control group (cells exposed to unconditioned medium). As seen in panels A, B and C, both sealers showed strong cytotoxic effects during the first 24 h after mixing, as measured by all three methods employed. No significant difference was found among the materials in this time point ($p > 0.05$). After one week AH Plus become noncytotoxic, on all three parameters evaluated. Conversely, MTA Fillapex remained severely and mildly cytotoxic over the entire experimental period. At the end of the fourth week, this sealer exhibited a toxicity level that was significantly more severe than the AH Plus in all tested time points ($p < 0.01$), except in fresh conditions ($p > 0.05$), in all evaluated parameters.

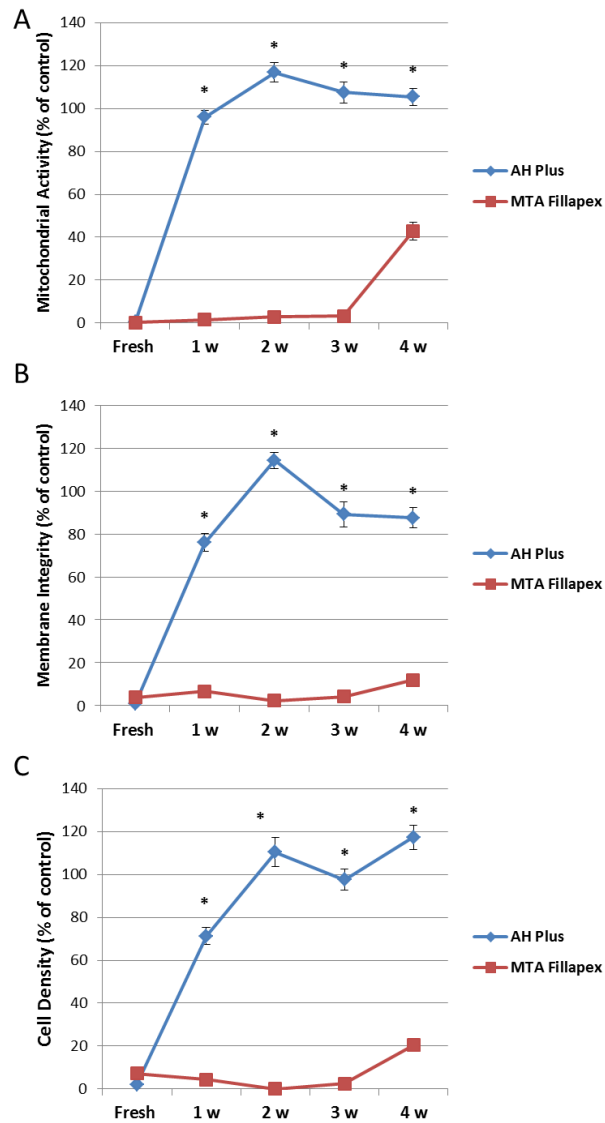


Fig 1. Multiparametric Long-Term cytotoxicity assay. Cytotoxic effects of endodontic sealers on hOB by (a) XTT, (B) NR and (C) crystal violet tests, expressed as percentage of control group. (*) indicates significant difference between the groups ($P < 0.05$).

DISCUSSION

In the present study, the cytotoxicity of MTA Fillapex and AH Plus were tested, employing some *in vitro* methodological strategies that differs from most previous works on these materials. First of all, three different parameters were evaluated on the same samples using a multiparametric assay that evaluates: (1) mitochondrial metabolism and respiratory toxicity, (2) lysosomal integrity and membrane permeability, and (3) the presence of DNA and cell proliferation. This methodology increases the chances of cytotoxic effects detection, allows correlation of different parameters, and sometimes provides hints about the mechanisms of toxicity (De-Deus *et al.* 2012, Scelza *et al.* 2012, Silva *et al.* 2012c).

A long-term cytotoxicity evaluation was also used in the present study. Although cytotoxicity testing of freshly mixed sealers is relevant as they are placed into the root canal system in a freshly mixed and incompletely polymerized stage, it is important to evaluate sealers over extended time periods after setting because it is probable that, during some period after clinical application, changes in cytotoxicity levels may be observed after diffusion of toxic components from the materials into the surrounding environment. It could be confirmed because the tested sealers showed different degrees of toxicity reduction after repeated testing at extended time periods. This long term evaluation is also superior to previous strategies that assessed cytotoxicity for the shorter term, because it enables the establishment of distinct toxicity profiles that are characteristic of each sealer (Lodiene *et al.* 2008).

Several different immortalized cell lines have been used to address endodontic sealers cytocompatibility, especially because they multiply rapidly and have an unlimited lifespan, allowing a higher reproducibility of results (Koh *et al.* 1998). However, biocompatibility assessments through primary cell culture are appealing, because the biomaterials will interact with such kind of cells after *in vivo* implantation (Rosa & Beloti 2003). Also the employment of human primary cells of a relevant type on the study of endodontic materials, has been pointed out previously (Huang & Chang 2002), in the light of several expected differences in the responses of immortalized cells. For this, hOB cells have been considered closest to the ideal cells for cytocompatibility assays because the direct interaction of these cells with biomaterials could play a critical role in the clinical setting (Zhu *et al.* 2000). It is also reported that hOB cells provides a useful tool, able to help to predict the effects of biomaterials on regenerative capability of periapical tissues (De-Deus *et al.* 2012).

Our results revealed that both materials, AH Plus and MTA Fillapex, exhibited strong cytotoxic effects in freshly mixed conditions. This results is in agreement with previous studies that have also observed severe cytotoxic effect of AH Plus and MTA Fillapex immediately after mixing and in the first days after mixed (Bin *et al.* 2012, Salles *et al.* 2012, Scelza *et al.* 2012, Silva *et al.* 2012b). The null hypothesis of the present study was rejected. After one week and in the succeeding weeks AH Plus became non-citotoxic, however MTA Fillapex toxicity did not decrease over time. Therefore, MTA Fillapex does not have the claimed biological advantages over other available products. As far as we know, this is the first attempt to evaluate this condition

with MTA Fillapex. The results suggest the correlations among the components present in MTA Fillapex formulation, such as Salicylate Resin, Diluting Resin and Silica with the cytotoxic effects. Salicylate resin has stimulated the process of apoptosis in human fibrosarcoma and has caused the fragmentation of cell genetic material, determining its precipitation in the cytoplasm (Mahdi *et al.* 2006). Arsenic, a heavy metal that may be found as a contaminant in MTA (Bramante *et al.* 2008) could be also related to MTA Fillapex cytotoxicity. Arsenic reacts with protein thiols, and exposure to high concentrations of this element may induce genotoxicity (Salles *et al.* 2012). Another possible explanation may be related to the physico-chemical properties of MTA Fillapex. Borges *et al.* 2012, demonstrated a higher solubility of MTA Fillapex when compared to AH Plus. This higher solubility can account for a greater amount of sealer particles release during the elution in DMEM, resulting in a higher exposition of MTA Fillapex to the cell culture. The high pH of MTA Fillapex (Silva *et al.*, 2012b) can also be related to an increase in the cytotoxicity values. Although the high pH can be related to cytotoxic effects, it activates alkaline phosphatase stimulating the mineralization process. The high pH may also neutralize acids secreted by osteoclasts inhibiting tissues demineralization (Eriksen 2010).

Despite the obvious cell destructive defect of MTA Fillapex sealer, a recent animal experimental study reported more limited cell destruction, followed by tissue repair activity and mineralization (Gomes-Filho *et al.* 2011). Contrary to this study, two recent studies showed intense and extensive inflammation in response to MTA Fillapex implanted in rat subcutaneous tissues (Tavares *et al.*, 2012; Zmener *et al.*

2012). The conflicting results among the studies are probably related to details in the experimental procedures. In another study, MTA Fillapex clearly showed the ability to stimulate nucleation sites for the formation of apatite crystals in human osteoblast-like cell culture using non-freshly mixed conditions that could have masked the cytotoxicity effects of the sealer (Salles *et al.* 2012).

Well-know and extensively used ISO standards cytotoxicity testes were used in the present study. However, the area-to-volume ratio between the surface of the samples and the volume of medium, recommended by ISO standards, may be superior to the real exposition during root canal treatment. A root experimental model has been suggested to test cytotoxicity of endodontic materials (Susini *et al.*, 2006; De-Deus *et al.*, 2009). This kind of model displays some advantages over assessments performed with isolate sealers, because more realistic material amounts are used, and the interaction between sealer and the surrounding dentin is taken into consideration as well (De-Deus *et al.* 2009). Thus, further studies are needed for a better understating of the cytotoxic effects of MTA Fillapex, and if this cytotoxicity may be related to some impairment of endodontic treatment.

CONCLUSION

AH Plus and MTA Fillapex had similar level of cytotoxicity in fresh conditions. AH Plus become non-cytotoxic after one week and MTA Fillapex remained cytotoxic after 4 weeks.

REFERENCES

Bin CV, Valera MC, Camargo SE, Rabelo SB, Silva GO, Balducci I *et al.* (2012) Cytotoxicity and genotoxicity of root canal sealers based on mineral trioxide aggregate. *Journal of Endodontics* **38**, 495-500.

Borges RP, Sousa-Neto MD, Versiani MA, Rached-Júnior FA, De-Deus G, Miranda CE, Pécora JD (2012) Changes in the surface of four calcium silicate-containing endodontic materials and an epoxy resin-based sealer after a solubility test. *International Endodontic Journal* **45**, 419-28.

Bramante CM, Demarchi AC, Moraes IG *et al* (2008) Presence of arsenic in different types of MTA and white and gray Portland cement. *Oral Surgery Oral Medicine Oral Pathology Oral Radiology and Endodontology* **106**, 909-13.

Braz MG, Camargo EA, Salvadori DMF, Marques MEA, Riberio DA (2006) Evaluation of genetic damage in human peripheral lymphocytes exposed to mineral trioxide aggregate and Portland cement. *Journal of Oral Rehabilitation* **33**, 234–9.

De-Deus G, Canabarro A, Alves G, Linhares A, Senne MI, Granjeiro M (2009) Optimal cytocompatibility of a bioceramic nanoparticulate cement in primary human mesenchymal cells. *Journal of Endodontics* **35**, 1387-90.

De-Deus G, Canabarro A, Alves GG, Marins JR, Linhares AB, Granjeiro JM (2012) Cytocompatibility of the ready-to-use bioceramic putty repair cement iRoot BP Plus with primary human osteoblasts. *International Endodontic Journal* **45**, 508-13.

Eldeniz AU, Hadimli HH, Ataoglu H, Orstavik D (2006) Antibacterial effect of selected root end filling materials. *Journal of Endodontics* **32**, 345–9.

Eriksen EF (2010) Cellular mechanisms of bone remodeling. *Reviews in Endocrine & Metabolic Disorders* **11**, 219-27.

Felippe WT, Felippe MCS, Rocha MJC (2006) The effect of mineral trioxide aggregate on the apexification and periapical healing of teeth with incomplete root formation. *International Endodontic Journal* **39**, 2–9.

Gomes-Filho JE, Watanabe S, Lodi CS, Cintra LT, Nery MJ, Filho JA et al (2011) Rat tissue reaction to MTA Fillapex®. *Dental Traumatology* [Epub ahead of print]

International Organization for Standardization (2009) ISO 10993-5: biological evaluation of medical devices – Part 5: tests for in vitro cytotoxicity. ISO 10993-5:2009.

Koh ET, McDonald F, Pitt Ford TR, Torabinejad M (1998) Cell response to mineral trioxide aggregate. *Journal of Endodontics* **24**, 543-7.

Lodiene G, Morisbak E, Bruzell E, Orstavik D (2008) Toxicity evaluation of root canal sealers in vitro. *International Endodontic Journal* **41**, 72-7.

Mahdi JG, Alkarrawi MA, Mahdi AJ, Bowen ID, Humam D (2006) Calcium salicylate mediated apoptosis in human HT-1080 fibrosarcoma cells. *Cell Proliferation* **39**, 249-60.

Main C, Mirzayan N, Shabahang S, Torabinejad M (2004) Repair of root perforations using mineral trioxide aggregate: a long-term study. *Journal of Endodontics* **30**, 80–3.

Nair PNR, Duncan HF, Pitt-Ford TR, Luder HU (2008) Histological, ultra structural and quantitative investigations on the response of healthy human pulps to experimental capping with mineral trioxide aggregate: a randomized controlled trial. *International Endodontic Journal* **41**, 128–50.

Riberio DA, Sugui MM, Matsumoto MA, Duarte MAH, Marques MEA, Salvidori DMF (2006) Genotoxicity and cytotoxicity of mineral trioxide aggregate and regular and white Portland cements on Chinese hamster ovary (CHO) Cells in vitro. *Oral Surgery Oral Medicine Oral Pathology* **101**, 258–61.

Roberts HW, Toth JM, Berzins DW, Charlton DG (2008) Mineral trioxide aggregate material use in endodontic treatment: a review of the literature. *Dental Materials* **24**, 149–64.

Salles LP, Gomes-Cornélio AL, Guimarães FC, Herrera BS, Bao SN, Rossa-Junior C et al (2012) Mineral trioxide aggregate-based endodontic sealer stimulates hydroxyapatite nucleation in human osteoblast-like cell culture. *Journal of Endodontics* **38**,971-6.

Scelza MZ, Linhares AB, da Silva LE, Granjeiro JM, Alves GG (2012) A multiparametric assay to compare the cytotoxicity of endodontic sealers with primary human osteoblasts. *International Endodontic Journal* **45**, 12-8.

Silva EJ, Herrera DR, Almeida JF, Ferraz CC, Gomes BP, Zaia AA (2012a) Evaluation of cytotoxicity and up-regulation of gelatinases in fibroblast cells by three root repair materials. *International Endodontic Journal* **45**, 815-20

Silva EJ, Rosa TP, Herrera DR, Jacinto RC, Gomes BP, Zaia AA (2012b) Evaluation of cytotoxicity and physicochemical properties of calcium silicate-based endodontic sealer MTA Fillapex. *Journal of Endodontics* doi: 10.1016/j.joen.2012.06.030 [Epub ahead of print]

Silva EJ, Rollemberg CB, Coutinho-Filho TS, Zaia AA (2012c) A multiparametric assay to compare the cytotoxicity of soy milk with different storage media. *Dental Traumatology* doi: 10.1111/j.1600-9657.2012.01175.x. [Epub ahead of print]

Susini G, About I, Tran-Hung L, Camps J (2006) Cytotoxicity of Epiphany and Resilon with a root model. *International Endodontic Journal* **39**, 940-4.

Tavares CO, Bottcher DE, Assmann E, Kopper PMP, Figueiredo JAP (2012). Tissue reactions to a new mineral trioxide aggregate-containing endodontic sealer. *Journal of Endodontics* doi:10.1016/j.joen.2012.10.009 [Epub ahead of print]

Torabinejad M, Parirokh M (2010) Mineral trioxide aggregate: a comprehensive literature review—part II: leakage and biocompatibility investigations. *Journal of Endodontics* **36**, 190–202.

Torabinejad M, Watson TF, Pitt Ford TR (1993) Sealing ability of a mineral trioxide aggregate when used as a root end filling material. *Journal of Endodontics* **19**, 591–5.

Washington JT, Schneiderman E, Spears R, Fernandez CR, He J, Opperman LA (2011) Biocompatibility and osteogenic potential of new generation endodontic materials established by using primary osteoblasts. *Journal of Endodontics* **37**, 1166-70.

Zmener O, Martinez Lalis R, Pameijer CH, Chaves C, Kokubu G, Grana D (2012) Reaction of rat subcutaneous connective tissue to a mineral trioxide aggregate-based and a zinc oxide and eugenol sealer. *Journal of Endodontics* **38**, 1233-8.

CONSIDERAÇÕES GERAIS

O MTA Fillapex foi criado numa tentativa de combinar as propriedades físico-químicas de um cimento obturador endodôntico com as propriedades biológicas do MTA. No presente estudo foi possível verificar que as propriedades físico-químicas testadas no capítulo 1 foram apropriadas, baseadas nas normas ISO 6876/2001. No entanto, no que diz respeito às propriedades biológicas, o MTA Fillapex apresentou resultados de elevada citotoxicidade nos diversos ensaios realizados (Capítulo 1, 2 e 3).

Apesar da óbvia citotoxicidade do MTA Fillapex, a literatura endodôntica ainda é escassa no que diz respeito aos efeitos citotóxicos de um cimento endodôntico, podendo gerar prejuízo ao tratamento endodôntico. Como perspectivas futuras, mais estudos serão necessários para caracterizar novos determinantes biológicos, relacionados com a elevada citotoxicidade do MTA Fillapex, bem como, identificar se os mecanismos de citotoxicidade do MTA Fillapex são capazes de comprometer o prognóstico do tratamento endodôntico.

CONCLUSÃO

Dentro da metodologia empregada e de acordo com os resultados apresentados pode-se concluir que embora o MTA Fillapex tenha apresentado propriedades físico-químicas testadas (radiopacidade, pH e escoamento) adequadas para a utilização na terapia endodôntica, o mesmo apresentou elevada citotoxicidade nas diversas condições testadas.

REFERÊNCIAS

1. Asgary S, Parirokh M, EghbalMJ, Brink F. Chemical differences between white and gray mineral trioxide aggregate. J Endod. 2005;31:101-3.
2. Barthel CR, Zimmer S, Wussogk R, Roulet JF. Long-Term bacterial leakage along obturated roots restored with temporary and adhesive fillings. J Endod. 2001; 27:559-62.
3. Bouillaguet SL, Wataha JC, Lockwood PE, Galgano C, Golay A, Krejci I. Cytotoxicity and sealing properties of four classes of endodontic sealers evaluated by succinic dehydrogenase activity and confocal laser scanning microscopy. Eur J Oral Sci. 2004;112:182-187.
4. Cohen S, Burns RC. Caminhos da polpa. 7ª ed. Rio de Janeiro: Guanabara Koogan; 2000.
5. Holland R, de SouzaV, Nery MJ, Otoboni-Filho JA, Bernabé PF, Dezan-Júnior E. Reaction of rat connective tissue to implanted dentin tubes filled with mineral trioxide aggregate or calcium hydroxide. J Endod. 1999;25:161-6.
6. Lovato KF, Sedgley CM. Antibacterial activity of endosequence root repair material and proroot MTA against clinical isolates of *Enterococcus faecalis*. J Endod. 2011;37:1542-6.
7. Roberts HW, Toth JM, Berzins DW, et al. Mineral trioxide aggregate material use in endodontic treatment: a review of the literature. Dent Mat. 2008;24:149-64.

*De acordo com a norma da UNICAMP/FOP, baseadas na norma do Internacional Committee of Medical Journal Editors – Grupo de Vancouver. Abreviatura dos periódicos em conformidade com o Medline.

8. Saunders WP, Saunders EM. Coronal leakage as a cause of failure in root-canal therapy: a review. *Endod Dent Traumatol.* 1994;10:105-8.
9. Siqueira Jr. JF, Lopes HP. *Endodontia: Biologia e técnica.* Guanabara Koogan, 2009.
10. Silva PT, Pappen FG, Souza EM, Dias JE, Bonetti-Filho I, Carlos IZ *et al.*, Cytotoxicity of four endodontic sealers. *Braz Dent J.* 2008;19:228-31.
11. Torabinejad M, Higa RK, McKendry DJ, Pitt Ford TR. Dye leakage of four root end filling materials effects of blood contamination. *J Endod.* 1994;20:159-63.
12. Torabinejad M, Hong CU, McDonald F, Pitt Ford TR. Physical and chemical properties of a new root-end filling material. *J Endod.* 1995;21:349-53

Confirmação de Publicação do Artigo (Capítulo 1)

ARTICLE IN PRESS

Basic Research—Technology

Evaluation of Cytotoxicity and Physicochemical Properties of Calcium Silicate-based Endodontic Sealer MTA Fillapex

Emmanuel J.N.L. Silva, DDS, MSc,* Tiago P. Rosa, DDS,* Daniel R. Herrera, DDS, MSc,* Rogério C. Jacinto, DDS, MSc, PhD,*† Brenda P.E.A. Gomes, DDS, MSc, PhD,* and Alexandre A. Zaia, DDS, MSc, PhD*

Abstract

Introduction: The aim of the study was to evaluate the cytotoxicity, radiopacity, pH, and flow of a calcium silicate-based and an epoxy resin-based endodontic sealer, MTA Fillapex (Angelus, Londrina, PR, Brazil) and AH Plus (Dentsply, Konstanz, Germany), respectively. **Methods:** Cytotoxicity, radiopacity, and flow evaluation were performed following ISO requirements. The pH level was measured at periods of 3, 24, 72, and 168 hours. Cytotoxicity was evaluated by 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl tetrazolium bromide assay to check the Balb/c 3T3 cells viability at 1- to 4-week periods. Data were statistically analyzed by analysis of variance and the Tukey test with a significance level of 5%. **Results:** In all tested periods, MTA Fillapex was more cytotoxic than AH Plus ($P < .05$). Although AH Plus presented higher radiopacity than MTA Fillapex ($P < .05$), both sealers showed minimum required values. MTA Fillapex presented alkaline pH in all experimental times, whereas AH Plus cement showed a slightly neutral pH and a flow significantly lower than that of MTA Fillapex ($P < .05$). **Conclusions:** Although MTA Fillapex was more cytotoxic than AH Plus, it showed suitable physicochemical properties for an endodontic sealer. (*J Endod* 2012; ■:■-■)

Key Words

AH Plus, cytotoxicity, MTA Fillapex, physicochemical properties, root canal sealer

From the *Department of Restorative Dentistry, Endodontics Division, Piracicaba Dental School, State University of Campinas, Piracicaba, Sao Paulo, Brazil; and †Endodontics Division, Federal University of Pelotas, Pelotas, Rio Grande do Sul, Brazil.

Address requests for reprints to Dr Emmanuel J.N.L. Silva, Department of Restorative Dentistry, Endodontics Division, Piracicaba Dental School, State University of Campinas, Av Limeira 901, Piracicaba-SP, CEP-13414-018, Brazil. E-mail address: nogueiraemmanuel@hotmail.com
0099-2399/5 - see front matter

Copyright © 2012 American Association of Endodontists.
<http://dx.doi.org/10.1016/j.joen.2012.06.030>

The characteristics and physicochemical properties of endodontic sealers are fundamental to allow hermetic sealing, which with an adequate coronal restoration will avoid bacterial leakage (1, 2). Mineral trioxide aggregate (MTA) is a material consisting of tricalcium oxide and other mineral oxides such as tricalcium silicate and silicate oxide. The pH of the material has been determined as 12.5 when set, which is comparable with that of calcium hydroxide (3–6). MTA biocompatibility, low cytotoxicity, antimicrobial properties (3, 7), low microleakage (4, 8), and its ability to set in the presence of blood or moisture are among the material's additional advantages. Because of these properties, it has been used for several dental applications such as root-end filling, root repair materials, and pulp capping (3–5). However, despite its favorable characteristics, MTA does not exhibit the physical properties needed to be used as an endodontic sealer because of its working time, setting time, and difficult handling (9).

MTA Fillapex (Angelus, Londrina, PR, Brazil), a sealer based on calcium silicate, was introduced recently. Its composition after mixing is basically MTA, salicylate resin, natural resin, bismuth oxide, and silica. The manufacturer claims that it has excellent radiopacity, easy handling, a great working time, and low solubility, providing sealing through expansion during setting. However, up to now, there are limited independent publications about the physicochemical and biological properties of MTA Fillapex and its possible use in clinical practice. Thus, the aim of the present study was to evaluate the cytotoxicity, radiopacity, pH, and flow of MTA Fillapex sealer and to compare them with those of AH Plus (Dentsply, Konstanz, Germany).

Materials and Methods

Cytotoxicity evaluation was performed according to ISO 10993-5 specifications (10). Radiopacity and flow evaluations were performed according to ISO 6876/2001 specifications (11). The pH level was measured at 3, 24, 72, and 168 hours. AH Plus cement was mixed according to the manufacturer's instructions for all the tests. MTA Fillapex is premixed, so further manipulations were unnecessary. The composition of the evaluated sealers is shown in Table 1.

Cytotoxicity

Discs of each sealer were fabricated under aseptic conditions in sterile cylindrical Teflon blocks with a 5-mm diameter and a 2-mm height. Excess flash material was removed with a sterile scalpel. Cytotoxicity of the sealers was assessed immediately after mixing and during 4 succeeding weeks. The extraction was made in cell culture medium using a surface area to volume ratio of approximately 150 mm²/mL between the surface of the samples and the volume of the medium (8). The extraction vials were agitated for 24 hours in a water bath at 37°C. Control samples containing only culture medium were treated similarly. Undiluted extracts were used for the testing.

Balb/c 3T3 cells (American Tissue Type Collection, Manassas, VA) were cultured in Dulbecco modified Eagle medium (Gibco, Grand Island, NY) supplemented with 10% fetal bovine serum (Sigma Chemical Co, St Louis, MO), 100 µg/mL streptomycin, and 100 mg/mL penicillin at 37°C in a humidified incubator under ambient pressure air atmosphere containing 5% CO₂. Confluent cells were detached with 0.25% trypsin and

Confirmação de Aceite do Artigo (Capítulo 2)

Data: Mon, 07 Jan 2012 16:37:41

De: suporte.aplicacao@scielo.org

Para: nogueiraemmanuel@hotmail.com;carolinaccos@gmail.com;zaia@fop.unicamp.br

Assunto: [JAOS 2304] Editorial Review of Article - Decision

Dear Authors,

I am delighted to inform you that the revised version of your manuscript "JAOS 2304 - Long-term Cytotoxic effects of Contemporary Root Canal Sealers" has been accepted for publication in the Journal of Applied Oral Science.

We will do our best to send the galley proofs for your approval in a timely fashion.

Thank you for choosing our journal to publish your work.

Please, do not hesitate to contact me for any further clarification or assistance.

Yours sincerely,

Carlos F. Santos, DDS, MSc, PhD, Professor
Editor-in-Chief
Journal of Applied Oral Science
<http://www.scielo.br/jaos>

Confirmação de Envio do Artigo para Publicação (Capítulo 3)

Data: Fri, 11 Jan 2013 15:41

De: iejeditor@cardiff.ac.uk

Para: zaia@fop.unicamp.br

Assunto: **International Endodontic Journal – Manuscript ID IEJ-13-00024**

Dear Dr. Zaia,

Your manuscript entitled “A multiparametric assay to compare the long-term cytotoxicity of AH Plus and MTA Fillapex” has been successfully submitted online to the International Endodontic Journal.

Your manuscript ID is IEJ-13-00024.

Please mention the above manuscript ID in all future correspondence or when calling the Editorial Office for questions. If there are any changes in your postal or e-mail address, please log in to ScholarOne Manuscripts at <http://mc.manuscriptcentral.com/iej> and edit your user information as appropriate.

You can also view the status of your manuscript at any time by checking your Author Centre after logging in to <http://mc.manuscriptcentral.com/iej> .

Thank you for submitting your manuscript to the International Endodontic Journal.

Kind regards

Paul Dummer
Editor, International Endodontic Journal
iejeditor@cardiff.ac.uk

Produção Bibliográfica do aluno

- 1- **Silva EJ**, Rosa TP, Herrera DR, Jacinto RC, Gomes BP, Zaia AA. Evaluation of cytotoxicity and physicochemical properties of calcium silicate-based endodontic sealer MTA Fillapex. *J Endod* 2013;39:274-7.
- 2- **Silva EJ**, Menaged K, Ajuz NC, Monteiro MR, Coutinho-Filho TS. Postoperative pain after foraminal enlargement in anterior teeth with necrosis and apical periodontitis: a prospective and randomized clinical trial. *J Endod* 2013;39:173-6.
- 3- **Silva EJ**, Santos GR, Coutinho-Filho TS, Krebs RL. Surgical alternative for the treatment of vertical root fracture: case report. *Iran Endod J* 2012;7:40-4.
- 4- **Silva EJ**, Herrera DR, Souza-Júnior EJ. Repair of iatrogenic perforation with mineral trioxide aggregate under operating microscope: a one year follow up. *Int J of Dent Clinic* 2012;4:47-9.
- 5- **Silva EJ**, Zaia AA. Open apex type III dens invaginatus: A rare case report of an endodontic retreatment with an anatomical redesign. *Gen Dent* 2012;60:e389-92.
- 6- **Silva EJ**, Herrera DR, Lima TF, Zaia AA. A nonsurgical technique for the removal of overextended gutta-percha. *J Contemp Dent Pract* 2012;13:219-21.
- 7- Coutinho-Filho TS, **Silva EJ**, Magalhães KM, Krebs RL, Ferreira CM, Natividade CO. Avaliação in vitro da eficácia do localizador apical Joypex 5. *ROBRAC* 2012;21:411-4.
- 8- Soares NV, **Silva EJ**, Ferreira CM, Krebs RL, Coutinho-Filho TS. Clinical reproducibility of a low-cost electronic apex locator. *Braz J Oral Sci* 2012;11:112-5.
- 9- **Silva EJ**, Andrade-Júnior CV, Tay LY, Herrera DR. Furcal-perforation repair with mineral trioxide aggregate: two years follow-up. *Indian J Dent Res* 2012;23:542-5.
- 10- Coutinho-Filho TS, Gurgel-Filho ED, Souza-Filho FJ, **Silva EJ**. Preliminary investigation to achieve patency of MB2 canal in maxillary molars. *Braz J Oral Sci* 2012;11:373-6.
- 11- Souza-Júnior EJ, **Silva EJ**, Herrera DR, Sinhoreti MA. Pino anatômico com resina composta: relato de caso. *ROBRAC* 2012;21:534-7.
- 12- Coutinho-Filho TS, Ferreira CM, **Silva EJ**, Souza-Filho FJ. Behavior of subcutaneous tissue of rats in response to infected dentine associated with different endodontic irrigants. *Rev Odonto Ciência* 2012;27:223-7.

- 13- **Silva EJ**, Herrera DR, Almeida JF, Ferraz CC, Gomes BP, Zaia AA. Evaluation of cytotoxicity and up-regulation of gelatinases in fibroblast cells by three root repair materials. *Int Endod J* 2012;45:815-20.
- 14- Coutinho-Filho TS, **Silva EJ**, Gurgel-Filho ED, Martins JS, Henriques L, Ferreira CM. Detecção de fratura radicular vertical utilizando tomografia computadorizada na presença ou ausência de núcleos metálicos. *Rev Soc Port Estom Med Dent* 2012;53:96-8.
- 15- **Silva EJ**, Accorsi-Mendonça T, Almeida JF, Ferraz CC, Gomes BP, Zaia AA. Evaluation of cytotoxicity and up-regulation of gelatinases in human fibroblast cells by four root canal sealers. *Int Endod J* 2012;45:49-56.
- 16- Silva G, **Silva EJ**, Silva JM, Andrade-Júnior CV, Ferraz CC. Sealing ability promoted by three different endodontic sealers. *Iran Endod J* 2011;6:86-9.
- 17- **Silva EJ**, Carvalho NK, Carvalho FR, Capelli Junior J, Coutinho-Filho TS. Abordagem Endodôntica e visão Ortodôntica da Reabsorção Cervical Externa: Relato de Caso. *ROBRAC* 2011;20:16-20.
- 18- **Silva EJ**, Ferreira CM, Krebs RL, Coutinho-Filho TS. Diagnóstico e tratamento endodôntico de um primeiro pré-molar mandibular com três canais radiculares. *Rev Cient CRO-RJ* 2011;1:70-2.
- 19- **Silva EJ**, Ferreira CM, Magalhães KM, Brito PR, Coutinho-Filho TS. Avaliação da temperatura gerada por diferentes pontas carregadoras de calor utilizadas para Termoplastificação de gutta-percha. *Rev Cient CRO-RJ* 2011;2:5-9.
- 20- Corrêa AC, **Silva EJ**, Ferreira CM, Magalhães KM, Coutinho-Filho TS. Eficácia de localizadores apicais na identificação de perfurações de diferentes diâmetros. *Rev Fac Odont UPF* 2011;16:161-5.
- 21- **Silva EJ**, Portela IR, Brito PR, Magalhães KM, Coutinho-Filho TS. Avaliação in vitro da eficiência de um localizador apical eletrônico em dentes com reabsorções radiculares simuladas. *Dent Press Endod* 2011;1:52-6.
- 22- **Silva EJ**, Rocha AC, Ferreira CM, Herrera DR, Coutinho-Filho TS. Assessment of the tip surface of gutta-percha cones after different cutting methods. *Acta Odontol Latinoam* 2011;24:236-9.
- 23- **Silva EJ**, Herrera DR, Santos CC, Gomes BP, Zaia AA. Acuidade do Root ZX II utilizando limas de aço inoxidável e níquel-titânio. *Dent Press Endod* 2011;1:41-44.
- 24- Rocha RS, **Silva EJ**, Magalhães KM, Coutinho-Filho TS. Avaliação da modelagem apical de cones de gutta-percha em canais ovais. *ROBRAC* 2011;20:325-8.
- 25- **Silva EJ**, Coutinho-Filho WP, Andrade AO, Herrera DR, Hirata-Junior R, Coutinho-Filho TS, Krebs RL. Efecto antimicrobiano de la terapia fotodinámica sobre *Enterococcus faecalis*, estudio in vitro. *Rev Estom Hered* 2011;21:185-9.
- 26- Souza-Junior EJ, Oliveira DC, Hirata R, Brandt WC, **Silva EJ**, Borges BC, Sinhoreti MA. Influence of the curing mode on the degree of conversion of a dual-

- cured self-adhesive resin luting cement beneath ceramic. *Acta Odont Scand in press.*
- 27- Silva EJ**, Rollemberg CB, Coutinho-Filho TS, Krebs RL, Zaia AA. Use of soymilk as storage medium for avulsed teeth. *Acta Odont Scand in press.*
- 28- Gurgel-Filho ED, Silva EJ**, Gomes BP, Ferraz CC, Paula RC, Coutinho-Filho TS, Souza-Filho FJ. Correlation between chemical composition and sealing ability of various gutta-percha brands using different filling techniques. *Rev Soc Port Estom Med Dent in press.*
- 29- Silva EJ**, Senna PM, Coutinho-Filho TS, Krebs RL. Tratamento endodôntico de segundo molar inferior com hipertaurodontia. *Rev Gaúcha Odont in press.*
- 30- Andrade-Júnior CV, Silva EJ**, Silva JM, Ferraz CC. Lateral Radiographic Technique: An Alternative Approach for Anterior Teeth. *J Contemp Dent Pract in press.*
- 31- Kurita LM, Cavalcante RB, Gurgel-Filho ED, De-Deus GA, Ximenes AB, Silva EJ**, Souza-Filho FJ. Response of mice connective tissue to three different endodontic materials. *Microsc Res Techn in press.*
- 32- Herrera DR, Santos Z, Tay LY, Silva EJ**, Loguercio AD, Gomes BP. Efficacy of Different Final Irrigant Activation Protocols on Smear Layer Removal by EDTA and Citric Acid. *Microsc Res Techn in press*
- 33- Silva EJ**, Santos CC, Zaia AA. Long-term Cytotoxic effects of Contemporary Root Canal Sealers. *J Appl Oral Sci in press.*
- 34- Accorsi-Mendonça T, Silva EJ**, Marcaccini AM, Gerlach RF, Duarte KM, Pardo AP, Line SR, Zaia AA. Evaluation of Gelatinases, Tissue Inhibitor of Matrix Metalloproteinase-2, and Myeloperoxidase Protein in Healthy and Inflamed Human Dental Pulp Tissue. *J Endod in press.*
- 35- Soares RM, Silva EJ**, Herrera DR, Krebs RL, Coutinho-Filho TS. Evaluation of the Joypex 5 and Root ZX II: an in vivo and ex vivo study. *Int Endod J in press.*
- 36- Silva EJ**, Rollemberg CB, Coutinho-Filho TS, Zaia AA. A multiparametric assay to compare the cytotoxicity of soy milk with different storage media. *Dent Traumatol in press.*