



OPEN ACCESS

Eurasian Journal of Analytical Chemistry

ISSN: 1306-3057

2017 12(6):939-951

DOI: 10.12973/ejac.2017.00223a



Polymerization Inhibitors and Promoters for Unsaturated Polyester Resins; Use of Solid Phase MicroExtraction and Gas Chromatography Coupled to Mass Spectrometry for the Determination of 4-*tert*-Butyl Catechol and Acetylacetone

Stefano Dugheri

Azienda Ospedaliero-Universitaria Careggi, ITALY

Matteo Gentili

Giotto Biotech Srl, Sesto Fiorentino, ITALY

Alessandro Bonari

Università degli Studi di Firenze, ITALY

Ilenia Pompilio

Università degli Studi di Firenze, ITALY

Nicola Mucci

Università degli Studi di Firenze, ITALY

Manfredi Montalti

Università degli Studi di Firenze, ITALY

Giulio Arcangeli

Università degli Studi di Firenze, ITALY

Received 16 November 2016 • Revised 7 July 2017 • Accepted 10 July 2017

ABSTRACT

This paper reports a contribution of three on-sample derivatization sampling techniques for acetylacetone, 4-*tert*-butyl catechol and its oxidated derivatives 4-*tert*-butyl-1,2-benzoquinone determination in unsaturated polyester resins. The use of *O*-(2,3,4,5,6, pentafluorobenzyl)-hydroxylamine, trimethyloxonium tetrafluoroborate and *O*-methylhydroxylamine is combined with automated head space/solid phase microextraction and gas chromatography/mass spectrometry analysis. For an innovative powerful meaning in high-throughput routine, the generality of the structurally informative mass spectrometry fragmentation patterns together with the chromatographic separation are also investigated. The detection limits for these polymerization inhibitors and promoters are less than 27 pg for one mg of unsaturated polyester resin. In this study a new autosampler platform is proposed by using the Multi Fiber Exchange device in a xyz robotic system. We promote these methods as the analytical reference in the polyester resin field. The introduction of dedicated, automated, and robotic systems allowed a friendly use of MS apparatus for high-throughput screening and it reduces the costs of monitoring campaigns.

Keywords: unsaturated polyester resins, 4-*tert*-butyl catechol, acetylacetone, solid phase microextraction, gas chromatography

© **Authors.** Terms and conditions of Creative Commons Attribution 4.0 International (CC BY 4.0) apply.

Correspondence: Stefano Dugheri, *Laboratorio di Igiene e Tossicologia Industriale, Azienda Ospedaliero-Universitaria Careggi, Largo P. Palagi 1, 50139, Firenze, Italy.*

✉ stefano.dugheri@unifi.it

INTRODUCTION

Global unsaturated polyester resins (UPR) market is expected to witness growth owing to commercial use in fiberglass reinforced plastics which have extensive applications in the construction industry. Therefore, worldwide production is expected to increase by more than 30% by 2020 (7,000 kilo tonnes) [1]. The invention of UPR is ascribed to Carleton Ellis. The first patents with regard to polyester resins emerged in the 1930s. Commercial production started in 1941 already reinforced with glass fibers for radar domes, also referred to as radomes [2, 3]. High ambient storage temperatures or long storage times, result in preliminary self-polymerization of these resins. A monetary loss due to the deterioration of the work ability of the resins occurs. So, inhibitors are used to increase the lifetime.

The existing methods for UPR characterization are nuclear magnetic resonance spectroscopy, size exclusion chromatography, and gas chromatography (GC) [4-6]. The main drawbacks in these analytical procedures are the use of solvents and/or cleanup steps, which have been reported to extract and eliminate most of the interfering compounds from the UPR, thus impeding their identification and quantification. Moreover, these procedures result in a large number of manual operations, uncertainty of the determination, higher overall cost and possible analyte loss.

In the last 10 years, miniaturization has attracted much attention in analytical chemistry and has driven solvent and sample savings, sample enrichment, rapid sample preparation, and easier automation. Sample preparation remains one of the more time-consuming and error-prone aspects of analytical chemistry. To overcome drawbacks of conventional extraction techniques, alternative miniaturized methods have been proposed both as solid phase microextraction, as Solid Phase MicroExtraction (SPME) [7-9], MicroExtraction by Packed Sorbent (MEPS) [10], Stir Bar Sorptive Extraction (Twister, SBSE) [11], Solid Phase Dynamic Extraction (Magic Needle, SPDE) [12], In-Tube Extraction (ITEX) [13] and liquid phase microextraction like Single-Drop MicroExtraction (SDME) [14], Hollow Fiber Liquid-Phase Microextraction (HF-LPME) [15,16], Dispersive Liquid-Liquid Microextraction (DLLME) [17], Solvent Bar MicroExtraction (SBME) [18]. On-sample derivatizations applied in miniaturized extraction systems and their simultaneous GC and liquid chromatography analysis has been described for the determination of analytes in aqueous matrices [19, 20]. These methods employ a sample derivatization technique to convert such polar substances into hydrophobic compounds whose volatility is sufficiently high for a GC determination. Within analytical chemistry, the SPME analysis is considered one of major breakthroughs that shaped 20th-century analytical chemistry [21]. SPME integrates sampling, extraction, concentration and sample introduction into a single step and the extraction requires no polluting organic solvent.

Accordingly, we developed three innovative methods for the determination of acetylacetone, 4-tert-butyl catechol (TBC) and its oxidated derivatives 4-tert-butyl-1,2-benzoquinone (TBBC) in UPR, in which automated head space (HS)/SPME technique after

on-sample derivatization is coupled to GC/mass spectrometry (MS). The aim of this work is a high-throughput assay with a molecular discrimination performed by structurally informative MS fragmentation patterns. Finally, we proposed a new off-line platform, called SPME Multi Off-Line Sampler, coupled to MultiFiber Exchange (MFX) installed on a *xyz* autosampler.

EXPERIMENTAL

On-sample derivatization

Dilution of UPR

As indicated in a previous paper [22], 100 mg of UPR were dissolved in 10 mL of chloroform (CAS n. 67-66-3). The resulting solution was diluted 1/10 in dimethylsulfoxide (CAS n. 67-68-5). The third solution was made by 1/100 to 1/10 000 water dilutions.

TBC by trimethyloxonium tetrafluoroborate

2 mL of water diluted UPR were transferred into a 10 mL autosampler vial with a magnetic stirring bar and mixed with 40 μ L of the internal standard (IS) TBC methyl-D6 methanol solution (50 μ g/mL). To convert the TBC (CAS n. 98-29-3, Cat. n. 19670, Aldrich) into its methylether, derivatization with trimethyloxonium tetrafluoroborate (TMO, CAS n. 420-37-1, Cat. n. 281077, Aldrich) was performed at room temperature in two steps. While stirring, about 20 mg of Na_2CO_3 (CAS n. 497-19-8) were added and within 4 minutes approximately 30 mg of solid TMO were added in two aliquots. After 1 minute the solution was neutralized with about 15 mg of NaHCO_3 (CAS n. 144-55-8). This procedure was repeated again. Finally, for HS by polyacrylate 85 μ m Fast Fit Assemblies (FFA) SPME fiber (Cat. n. FFA 57294-U, Supelco), NaCl (0.5 g) (CAS n. 7647-14-5) was added and the vials were processed by extraction. For TBC-dimethylether, the mass number of the target ion was $m/z=179$ and the confirming ion was $m/z=194$.

Acetylacetone by O-(2,3,4,5,6, pentafluorobenzyl)-hydroxylamine

2 mL of water diluted UPR were transferred into a 10 mL autosampler vial and mixed with 10 μ L cyclohexanone (CAS n. 108-94-1, Cat. n. 398241 Sigma-Aldrich) IS solution (240 μ g/mL) plus 100 μ L of 40 mg/mL *O*-(2,3,4,5,6, pentafluorobenzyl)-hydroxylamine hydrochloride (PFBHA, CAS n. 57981-02-9, Cat. n. 76735, Sigma-Aldrich) aqueous solution. The condition used for full reaction to convert the acetylacetone (CAS n. 123-54-6, Cat. n. 005581, Sigma-Aldrich) into its PFB-*bis*-oximes was 20 hours at room temperature. The SPME-HS sampling was performed by 30 μ m polydimethylsiloxane (PDMS) FFA SPME fiber (Cat. n. FFA 57289-U, Supelco). The target and the confirming ions were $m/z=181$ and $m/z=236, 293$, respectively.

TBBC by methoxylamine

2 mL of water diluted UPR were transferred into a 10 mL autosampler vial and mixed with 10 μ L TBBC methyl-D9 IS solution 240 μ g/mL plus 300 μ L of 80 mg/mL *O*-

methylhydroxylamine hydrochloride (MHA, CAS n. 593-56-6, Alfa Aesar Cat. n. A19188) aqueous solution. The condition used for full reaction to convert the TBBC (CAS n. 1129-21-1) into its methyl-*bis*-oxime was 20 hours at room temperature. The SPME-HS sampling was performed by 30 μm PDMS FFA SPME fiber. The confirming ion was $m/z=222$.

On-line SPME conditions and xyz robotic apparatus

Automation of the GC procedure was achieved using a new Flex autosampler (EST Analytical, Fairfield, USA). For HS-SPME absorption, a pulsed agitation (on for 2 s at 500 rpm and off for 4 s, 50 °C) was carried out for incubation, before automatically introducing the fiber into the vial in the same conditions. After the absorption, the SPME fiber was introduced into the GC injector port by *xyz* autosampler.

Off-line SPME sampling and xyz robotic apparatus

The SPME Multi Off-Line Sampler (Chromline, Prato, Italy) is designed to be used with FFA SPME fibers. The holder works as a support to expose the SPME fiber into the vial, placed on plate of the 32-position magnetic stirrer (Chromline). After the exposure FFA SPME fibers are automatically removed by the Multi Off-Line Sampler and placed into a 45-position tray, allowing the exchange of SPME fibers on the Flex autosampler. Desorption of sampled fibers was performed into the GC instrument equipped with Merlin Microseal System (Cat. n. 24817-U, Sigma-Aldrich). A connection with the Laboratory Information Management System (Bika Lab System) allowed a user-programmable suite.

GC/MS

Analysis were performed with a Varian 3900 GC equipped with electronic flow control and a 320-MS (Varian Inc.) detector. A MEGA-5-MS fused silica capillary column (internal diameter 0.25 mm, length 30 m and film thickness 0.25 μm , Cat. No. MS-5-025-025-30, MEGA, Legnano, Italy) was used. TBC and TBBC analysis were performed with column temperature set to 50 °C for 1 min and then increased at 10 °C/min to 240 °C (total run time 20.00 min). In acetylacetone (CAS n. 123-54-6) determination, column oven was set to 40 °C for 2 min and then increased at 25 °C/min to 210 °C, 3 °C/min to 230 °C and finally 30 °C/min to 300 °C for 2.2 min (total run time 20.00 min). Desorption of the analytes was performed introducing the SPME fiber into the 1079 Varian GC injector port (10:1 split mode) for 4 min. The MS was operated in single quadrupole and electron ionization (EI) source with electron energy of 70 eV. Helium (99.999%) at a flow rate of 1.2 mL/min was used as carrier gas.

SYNTHESIS

TBC-D6

Methylation of the catecholic hydroxyls with methyl iodide-D3 (CAS n. 865-50-9) afforded TBC-D6 in good yield (**Figure 1**). Methyl iodide-D3 (5.00 g, 34.5 mmol) was added to a suspension of 4-tert-butyl catechol (2.39 g, 14.4 mmol) and K_2CO_3 (5.97 g, 43.2 mmol) (CAS

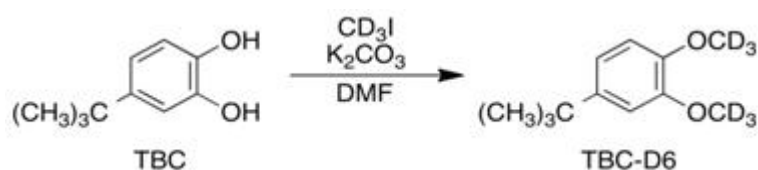


Figure 1. Methylation of TBC with methyl iodide-D3

n. 584-08-7). The mixture was heated at 60 °C for 16 hours, then poured on 200 mL of water, extracted three times with Et₂O (CAS n. 60-29-7), the combined organic layers were dried over anhydrous Na₂SO₄ (CAS n. 7757-82-6), filtered and evaporated. The resulting residue was purified by flash column chromatography on silica gel [25% CH₂Cl₂ (CAS n. 75-09-2) in petroleum ether (CAS n. 8032-32-4)] to give pure TBC-D6 (2.44 g, 85% yield). ¹H-NMR (400 MHz, CDCl₃) δ 6.92-6.88 (m, 2H), 6.77 (d, 1H), 1.30 (s, 9H); ¹³C-NMR (100 MHz, CDCl₃) δ 148.2, 146.6, 143.7, 116.9, 110.6, 109.0, 55.61, 55.60, 34.2, 31.3; ESI-MS: *m/z* 201.31 [M+H]⁺.

TBC-D9

In a flame dried Schlenk flask under N₂ atmosphere, *tert*-butanol-D10 (CAS n. 53001-22-2) (300 mg, 3.56 mmol) was added to a solution of catechol (CAS n. 120-80-9) (392 mg, 3.56 mmol) in trifluoroacetic acid-D (CAS n. 599-00-8) (4.5 mL) and D₂SO₄ (CAS n. 13813-19-9) (200 μL). The obtained yellow solution was stirred at 40 °C overnight. The reaction was diluted with CH₂Cl₂, washed twice with water and then twice with a saturated solution of NaHCO₃ and dried over anhydrous Na₂SO₄. After evaporation of the solvent, the residue was purified by flash column chromatography on silica gel [20% ethyl acetate (CAS n. 141-78-6) in petroleum ether] obtaining pure TBC-D9 (90 mg, 15% yield) as an oil. ¹H-NMR (200 MHz, CDCl₃) δ 6.77-6.83 (m, 2H), 6.58 (s, 1H); ¹³C-NMR (50 MHz, CDCl₃) δ 144.9, 142.7, 140.6, 118.0, 115.9, 113.4, 34.0; ESI-MS: *m/z* 198.16 [M+Na]⁺.

TBBC-D9

To obtain TBBC-D9, TBC-D9 was first synthesized following the procedure reported for the preparation of the protonated analogue [23]. Briefly, catechol was alkylated at position 4 with *tert*-butanol-D10 under acidic conditions of trifluoroacetic acid-D and D₂SO₄. The deuterated environment proved to be essential for the obtainment of the fully deuterated compound, as otherwise the *tert*-butyl cation D9 can exchange with the protic medium leading to the formation of partially deuterated derivatives. Oxidation of the catechol by NaIO₄ (CAS n. 7790-28-5) under phase transfer conditions provided the correspondent ortho-quinone TBBC-D9. In detail, to a solution of TBC-D9 (80 mg, 0.46 mmol) in CH₂Cl₂ (45 mL) shielded from light, a solution of NaIO₄ (103 mg, 0.48 mmol) in H₂O (5 mL) was added. To this mixture tetrabutylammonium bromide (CAS n. 64-20-0) (148 mg, 0.46 mmol) was added. The reaction was vigorously stirred in the dark for 1 hour. After diluting the reaction with CH₂Cl₂, the organic phase was collected and washed twice with H₂O, then dried over anhydrous Na₂SO₄. After evaporation of the solvent, the residue was purified by flash column chromatography

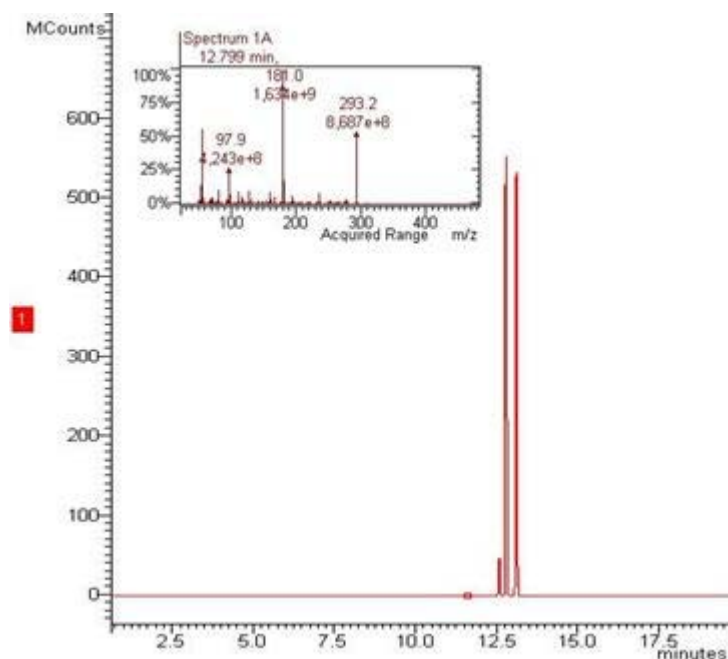


Figure 2. GC chromatogram and EI-MS spectrum of the three stereoisomers of acetylacetone-bis-PFB-oxime

on silica gel (25% ethyl acetate in petroleum ether) obtaining pure TBBC-D9 (16 mg, 20% yield) as a green solid. M.p. = 61-62 °C; $^1\text{H-NMR}$ (200 MHz, CDCl_3) δ 7.19 (dd, 1H), 6.38 (d, 1H), 6.27 (d, 1H); $^{13}\text{C-NMR}$ (50 MHz, CDCl_3) δ 190.44, 162.25, 140.20, 129.53, 123.94, 35.77; ESI-MS: m/z 196.14 $[\text{M}+\text{Na}]^+$.

RESULTS AND DISCUSSION

Sampling of UPR by HS/SPME sampling and following GC/MS analysis has aroused interest in the authors of this work and has been investigated as a possible alternative to conventional methods. The aim of this paper is to provide a simple, fast, sensitive, and organic-solvent free innovative procedure for analysis of polymerization inhibitors and promoter in UPR. So, to achieve successful method, two fundamental requisites were satisfied by the Authors.

Carbonyl and hydroxyl functional groups on-sample derivatizations

On-sample derivatization of carbonyl group to hydrazones and oximes is frequently used. The procedure involves derivatization of the analyte with 2,4-dinitrophenylhydrazine (CAS n. 119-26-6) [24], 2,4,6-trichlorophenylhydrazine [25], pentafluorophenylhydrazine (CAS n. 828-73-9) [26], PFBHA and MHA. These last two reacts in weakly acidic media (pH 4-6) with CO- groups to produce the corresponding oximes.

The GC/EI positive ion MS base peak for all PFB-derivatives is m/z 181, the pentafluorotropylium cation [27] (Figure 2).

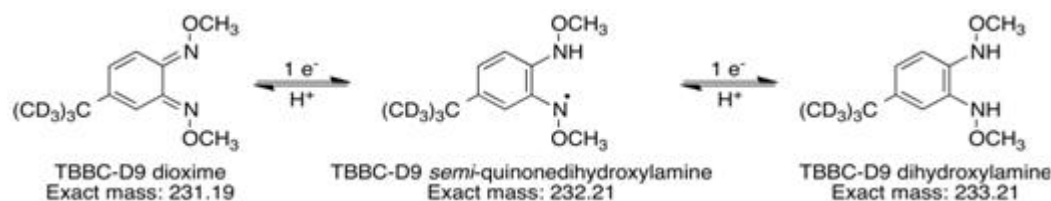


Figure 3. Redox equilibria in TBBC-D9 dioxime

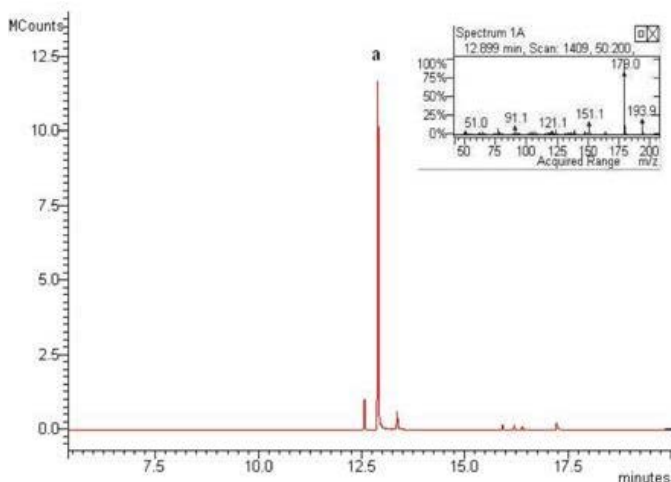


Figure 4. GC chromatogram and EI-MS spectrum of the TBC-bis-methylether

Differently, a characteristic base peak was not observed for methyloxime derivatives of model carbonyl compounds [28]. Methyloxime derivatives produce several abundant fragment ions with low molecular weight that result from simple cleavage or rearrangement followed by fragmentation [29]. We revealed that the *o*-quinones readily react with MHA to give the corresponding bis-oximes, and the reaction can be pushed to completion if an excess of hydroxylamine is used [30]. The presence of different peaks in the mass spectrum of TBBC-D9 after the derivatization with MHA can be explained taking into account the redox equilibria which quinones and related molecules undergo by simple monoelectronic transfer [31]; indeed the mass peaks that were observed correspond to the TBBC-D9 dioxime, TBBC-D9 *semi*-quinonedihydroxylamine and TBBC-D9 quinonedihydroxylamine which coexist in equilibrium (**Figure 3**).

Trialkyloxonium ions (Meerwein salts), R_3O^+ , with various counterions such as SbF_6^- , BF_4^- , $SbCl_6^-$, and PF_6^- are excellent alkylating agents for nucleophiles containing heteroatoms such as N, O, or S [32]. With TMO a methyl group of the oxonium ion reacts with the anion of the α -OH functional group to form the methyl ether. The MS spectrum of TBC-*bis*-methylether is indicated in **Figure 4**.

Table 1. Physical properties and partition coefficients of the TBBC-methyl-bis-oxime^{a)}, acetylacetone-PFB-bis-oximes^{b)} and TBC-dimethylether^{c)} using SPARC software (<http://www.archemcalc.com/index.html>).

SMILES strings	CAS n.	T _{eb} °C	D _{water} cm ² /s	D _{air} cm ² /s	K _H atm/(mol/m ³)	P _{vap} Pa
CO\N=C1/C=C(C=C/C1=N\OC)C(C)(C)C ^{a)}	unknown	373	5*10 ⁻⁶	4*10 ⁻²	5.21*10 ⁻⁵	1*10 ⁻²
Fc2c(CO\N=C(\C)CC(/C)=N\OCc1c(F)c(F)c(F)c(F)c1F)c(F)c(F)c(F)c2F ^{b)}	unknown	348	4*10 ⁻⁶	3*10 ⁻²	7.1*10 ⁻⁵	2*10 ⁻⁵
COc1cc(ccc1OC)C(C)(C)C ^{c)}	41280-64-2	269	6*10 ⁻⁶	5*10 ⁻²	1.3*10 ⁻⁶	1.9

Verify the suitability to HS-SPME technique

The first objective was to develop the derivatization conditions onto HS-SPME technologies to obtain compounds which are stable under a variety of conditions and easily amenable of sampling and analysis. The PA and PDMS absorptive liquid coatings were chosen for the SPME sampling of a very complex matrix such as UPR because of the lack of competition between the analytes. The HS-SPME techniques were described in a previous work by examining a three-phase system in which a liquid polymeric coating, a HS and an aqueous solution were involved [33]. The mass (n) of analytes absorbed by a coating after the equilibrium has been reached is related to the overall equilibrium of analytes in a three-phase system

$$n = (C_0 V_1 V_2 K_1 K_2) / (K_1 K_2 V_1 + K_2 V_3 + V_2)$$

where K₁ is the SPME coating/HS partition coefficient, K₂ is the HS/aqueous matrix partition coefficient, C₀ is the initial concentration of the analyte in the aqueous solution, and V₁, V₂ and V₃ are the volumes of the coating, the aqueous solution, and the HS, respectively. Since K values of the analytes (where K = K₁ × K₂) are often very close to the octanol-water partition coefficient (K_{ow}), and K₂ = K_H/RT, where K_H is Henry's constant (C₀, concentration gas phase/C₀, concentration liquid phase). It derives that the equilibrium is controlled by K_{ow} and K_H values. Therefore, the constant of distribution estimated from physicochemical tables or by using the structural unit contribution method can anticipate trends in SPME analysis. The K_H of the TBC-dimethylether, acetylacetone-PFB-oximes and TBBC-methyl-bis-oxime derivatives were 1.3, 71 52 and atm cm³/mol, which were in agreement with that reported by Pacenti et al [34], and indicated that HS-SPME is efficient for compounds with the K_H higher than 0.17 atm cm³/mol (Table 1).

Furthermore, we found better sensitivity using HS-SPME by an increase in the ion strength by adding bivalent salts instead monovalent salts. The solubility decrease of the methyloxime in the presence of inorganic salts is quantified by the Setschenow equation [35]

$$\log S_0/S = \log \gamma = K_s (\text{salt,solute}) C$$

Table 2. Calibration curve. Accuracy and precision of acetylacetone-PFB-*bis*-oximes and TBC-dimethylether analytical methods.

Calibration curve point	acetylacetone-PFB- <i>bis</i> -oximes		TBC-dimethylether	
	Concentration (pg/mg)			
	Nominal	Measured (mean, n=5)	Nominal	Measured (mean, n=5)
1	80	78	100	75
2	160	159	200	202
3	320	321	400	407
4	640	640	800	817
5	1280	1280	1600	1604
6	2560	2559	3200	3193
Response factor plot				
Least-squares linear regression plot parameters (m=slope b=intercept)	m = 0.5361		m = 0.5868	
	b = 0.6457		b = 8.621	
Coefficient of correlation	0.99		0.99	
Standard Error	0.556		8.199	
Method Detection Limits				
LOD (pg/mg)	1.9		27	
LOQ (pg/mg)	9.2		125	
Accuracy and Precision				
Within session accuracy (%)	6.7		7.0	
Within session repeatability (%)	0.9		3.7	
Inter session repeatability (%)	3.1		3.8	

where S_0 is the solubility of the solute in water, S is the solubility in the presence of salt, γ is the activity coefficient of the solute, K_s is the Setschenow constant and C is the salt concentration. As some Authors showed [36, 37, 38], we noticed that the salt mixture ammonium sulfate (CAS n. 7783-20-2) and sodium dihydrogen phosphate (CAS n. 10049-21-5) (ratio 4/1, 0.7 g) increase the salting out factor of 1.6 rather than the more commonly salt sodium chloride.

In light of what indicated above the authors present the final results. As indicated in **Table 2** the resulting calibration curves for TBC-dimethylether and acetylacetone-PFB-*bis*-oximes were linear in the investigated range, showing a correlation coefficients >0.99 . Accuracy was within 15% of the theoretical concentration, in line with the requirement of US Food and Drug Administration.

The new autosampler platform proposed in this study integrate the MFX device. Several sample preparation steps immediately before sample injection have been automated, allowing just-in-time sample preparation. Following an example to show the advantages of the use of SPME FFA Multi Off-Line Sampler (**Figure 5**), we assume an extraction time of 40 minutes for TBC-*bis*-methylether and acetylacetone-PFB-*bis*-oximes equilibrium in a SPME three phase



Figure 5. SPME 32-position Multi Off-Line Sampler

system and analysis time of 20 minutes. The results are excellent, with reduction of the total analysis time of 725 minutes (30 samples processed) respect to conventional SPME on-line analysis.

CONCLUSIONS

Our data suggest that automated SPME extraction coupled with GC/MS may be a viable alternative for quantitative TBC and acetylacetone analyses. New sample preparation techniques are being increasingly introduced because of the considerable need for information management, the automation of sample preparation, and the integration of data management into the analytical process. As a future perspective, we wish to expand the application of this methodology by carrying out the quantitative TBBC determination.

ACKNOWLEDGEMENTS

We thank Polynt SPA (San Giovanni Valdarno, Arezzo, Italy), one of the world's largest manufacturers and suppliers of polyester gel coats, for allowing us access to the laboratories and the employees, particularly Alessandro Renzi, Giacomo Cipriani and Emanuele Fabbri, for enduring our presence and participating in the study.

REFERENCES

1. Unsaturated Polyester Resin (UPR) Market Analysis By Product (DCPD, Orthophthalic, Isophthalic), By End-Use (Pipes & Tanks, Building & Construction, Electrical, Marine, Transport, Artificial Stones) And Segment Forecasts To 2020. (2014) <http://www.grandviewresearch.com/industry-analysis/unsaturated-polyester-resin-upr-market> (Grand View Research, Inc.)
2. Andrews K, Bingham S, McAninch I, Greer C, Sands JM, La Scala JJ, Geng X, Palmese GM, Crisostomo V, and Suib S (2009) Analysis of Commercial Unsaturated Polyester Repair Resins, ARL-TR-4872. U.S. Army Research Laboratory (ARL).

3. Malik, M., Choudhary, V., & Varma, I. K. (2000). Current status of unsaturated polyester resins. *J. Macromol. Sci.-Rev. Macromol. Chem. Phys.*, 40(2-3), 139.
4. Luce, C. C., Humphrey, E. F., Guild, L. V., Norrish, H. H., Coull, J., & Castor, W. W. (1964). Analysis of Polyester Resins by Gas Chromatography. *Anal. Chem.*, 36(3), 482.
5. Stamatakis, G., Knuutinen, U., Laitinen, K., & Spyros, A. (2010). Analysis and aging of unsaturated polyester resins in contemporary art installations by NMR spectroscopy. *Anal. Bioanal. Chem.*, 398(7-8), 3203.
6. Autran, M., Pauliard, R., Gautier, L., Mortaigne, B., Mazeas, F., & Davies, P. (2002). Influence of mechanical stresses on the hydrolytic aging of standard and low styrene unsaturated polyester composites. *J. Appl. Polym. Sci.*, 84, 2185.
7. Bartelt, R. J. (1997). Calibration of a commercial solid-phase microextraction device for measuring headspace concentrations of organic volatiles. *Anal. Chem.*, 69(3), 364.
8. Bianchi, F., Bisceglie, F., Dugheri, S., Arcangeli, G., Cupelli, V., Del Borrello, E., Sidisky, L., & Careri, M. (2014). Ionic liquid-based solid phase microextraction necklaces for the environmental monitoring of ketamine. *J. Chromatogr. A*, 1331, 1.
9. Kremser, A., Jochmann, M. A., & Schmidt, T. C. (2016). SPME Arrow - Evaluation of a Novel Solid-Phase Microextraction Device for Freely Dissolved PAHs in Water. *Anal. Bioanal. Chem.*, 408(3), 943.
10. Abdel-Rehim, M., Altun, Z., & Blomberg, L. (2011). Microextraction in packed syringe (MEPS) for liquid and gas chromatographic applications. Part II--Determination of ropivacaine and its metabolites in human plasma samples using MEPS with liquid chromatography/tandem mass spectrometry. *J. Mass Spectrom.*, 39(12), 1488.
11. David, F., & Sandra, P. (2007). Stir bar sorptive extraction for trace analysis. *J. Chromatogr. A*, 1152(1-2), 54.
12. Rossbach, B., Kegel, P., & Letzel, S. (2012). Application of headspace solid phase dynamic extraction gas chromatography/mass spectrometry (HS-SPDE-GC/MS) for biomonitoring of n-heptane and its metabolites in blood. *Toxicol. Lett.*, 210(2), 232.
13. Laaks, J., Jochmann, M. A., Schilling, B., & Schmidt, T. C. (2015). Optimization strategies of in-tube extraction (ITEX) methods. *Anal. Bioanal. Chem.*, 407(22), 6827.
14. Singh, D. K., Sanghi, S. K., Gowri, S., Chandra, N., & Sanghi, S. B. (2011). Determination of aliphatic amines by gas chromatography-mass spectrometry after in-syringe derivatization with pentafluorobenzoyl chloride. *J. Chromatogr. A*, 1218(33), 5683.
15. Pedersen-Bjergaard, S., & Rasmussen, K. E. (1999). Liquid-liquid-liquid microextraction for sample preparation of biological fluids prior to capillary electrophoresis. *Anal. Chem.*, 71(14), 2650.
16. Saraji, M., & Ghani, M. (2015). Hollow fiber liquid-liquid-liquid microextraction followed by solid-phase microextraction and in situ derivatization for the determination of chlorophenols by gas chromatography-electron capture detection. *J. Chromatogr. A*, 1418, 45.
17. Rezaee, M., Assadi, Y., Milani Hosseini, M. R., Aghaee, E., Ahmadi, F., & Berijani, S. (2006). Determination of organic compounds in water using dispersive liquid-liquid microextraction. *J. Chromatogr. A*, 1116(1-2), 1.
18. Kamarei, F., Ebrahimzadeh, H., & Yamini, Y. (2010). Optimization of solvent bar microextraction combined with gas chromatography for the analysis of aliphatic amines in water samples. *J. Hazard Mater.*, 178(1-3), 747.
19. Ferreira, A. M., Laespada, M. E., Pavón, J. L., & Cordero, B. M. (2013). In situ aqueous derivatization as sample preparation technique for gas chromatographic determinations. *J. Chromatogr. A*, 1296, 70.
20. Baghdady, Y. Z., & Schug, K. A. (2016). Review of in situ derivatization techniques for enhanced bioanalysis using liquid chromatography with mass spectrometry. *J. Sep. Sci.*, 39(1), 102.

21. Handley, J., & Harris, C. M. (2001). Great ideas of a decade. *Anal. Chem.*, 73(23), 660.
22. Dugheri, S., Bonari, A., Pompilio, I., Mucci, N., Montalti, M., & Arcangeli, G. (2016). Development of new gas chromatography/mass spectrometry procedure for the determination of hexahydrophthalic anhydride in unsaturated polyester resins. *Rasayan J. Chem*, 9(4), 657.
23. Stolwijk, T. B., Sudhölter, E. J. R., & Reinhoudt, D. N. (1989). Effect of crown ether lipophilicity on the facilitated transport of guanidinium thiocyanate through an immobilized liquid membrane. *J. Am. Chem. Soc.*, 111, 6321.
24. Duan, X., Zhong, D., & Chen, X. (2008). Derivatization of β -dicarbonyl compound with 2,4-dinitrophenylhydrazine to enhance mass spectrometric detection, application in quantitative analysis of houttuynin in human plasma. *Journal of Mass Spectrometry*, 43(6), 814.
25. Konidari, C. N., Stalikas, C. D., & Karayannis, M. I. (2001). Gas chromatographic method for the sensitive determination of 2,5-hexanedione using electron capture and mass-selective detection. *Analytica Chimica Acta*, 442(2), 231.
26. Stashenko, E. E., Puertas, M. A., Salgar, W., Delgado, W., & Martínez, J. R. (2000). Solid-phase microextraction with on-fibre derivatization applied to the analysis of volatile carbonyl compounds. In situ aqueous derivatization as sample preparation technique for gas chromatographic determinations. *J. Chromatogr. A*, 886(1-2), 175.
27. Pacenti, M., Dugheri, S., Traldi, P., Degli Esposti, F., Perchiazzi, N., Franchi, E., Calamante, M., Kikic, I., Alessi, P., Bonacchi, A., Salvadori, E., Arcangeli, G., & Cupelli, V. (2010). New automated and high-throughput quantitative analysis of urinary ketones by multifiber exchange-solid phase microextraction coupled to fast gas chromatography/negative chemical-electron ionization/mass spectrometry. *V. J. Autom. Methods. Manag. Chem.*
28. Flores, R. M., & Doskey, P. V. (2015). Evaluation of multistep derivatization methods for identification and quantification of oxygenated species in organic aerosol. *J. Chromatogr. A*, 1418, 1.
29. Middleditch, B. S., & Knights, B. A. (1972). The mass spectra of some O-methyloximes of aliphatic aldehydes and ketones. *Org. Mass Spectrom*, 6, 179.
30. Hussain, H., Specht, S., Sarite, S. R., Saeftel, M., Hoerauf, A., Schulz, B., & Krohn, K. (2011). A New Class of Phenazines with Activity against a Chloroquine Resistant Plasmodium falciparum Strain and Antimicrobial Activity. *J. Med. Chem.*, 54(13) 4913.
31. Mederos, A., Dominguez, S., Hernandez-Molina, R., Sanchiz, J., & Britom F. (1999). Coordinating ability of phenylenediamines. *Coord. Chem. Rev.*, 193-195, 913.
32. Liebich, H. M., & Gesele, E. (1999). Profiling of organic acids by capillary gas chromatography-mass spectrometry after direct methylation in urine using trimethyloxonium tetrafluoroborate. *J. Chromatogr. A*, 843(1-2), 237.
33. Zhang, Z., & Pawliszyn, J. (1993). Headspace solid-phase microextraction. *J. Anal. Chem.*, 65(14), 1843.
34. Pacenti, M., Dugheri, S., Villanelli, F., Bartolucci, G., Calamai, L., Boccalon, P., Arcangeli, G., Vecchione, F., Alessi, P., Kikic, I., & Cupelli, V. (2008). Determination of organic acids in urine by solid-phase microextraction and gas chromatography-ion trap tandem mass spectrometry previous 'in sample' derivatization with trimethyloxonium tetrafluoroborate. *Biomed. Chromatogr.*, 22(10), 1155.
35. Setschenow, J. (1889). Z.Uber die konstitution der salzlosungenauf grund ihres verhaltens zu kohlensaure Z. *Phys. Chem.*, 4, 117- 125.
36. Fiorini, D., Pacetti, D., Gabbianelli, R., Gabrielli, S., & Ballini, R. (2015). A salting out system for improving the efficiency of the headspace solid-phase microextraction of short and medium chain free fatty acids. *J. Chromatogr. A*, 1409, 282.
37. Bretti, C., Crea, F., Foti, C., & Sammartano, S. (2006). Solubility and Activity Coefficients of Acidic and Basic Nonelectrolytes in Aqueous Salt Solutions. 2. Solubility and Activity

- Coefficients of Suberic, Azelaic, and Sebacic Acids in NaCl(aq), (CH₃)₄NCl(aq), and (C₂H₅)₄Nl(aq) at Different Ionic Strengths and at t = 25 °C. *J. Chem. Eng.*, 51(5), 1660.
38. Fiorini, D., Boarelli, M. C., Gabbianelli, R., Ballini, R., & Pacetti, D. (2016). A quantitative headspace-solid-phase microextraction-gas chromatography-flame ionization detector method to analyze short chain free fatty acids in rat feces. *Anal. Biochem.*, 508, 12.

<http://www.eurasianjournals.com>