

**UNIVERSITY OF LEEDS**

This is a repository copy of *Three-well terahertz frequency quantum cascade lasers with a common LO-phonon extraction and injection stage*.

White Rose Research Online URL for this paper:

<http://eprints.whiterose.ac.uk/89955/>

Version: Accepted Version

Conference or Workshop Item:

Han, YJ, Li, LH, Chen, L et al. (9 more authors) Three-well terahertz frequency quantum cascade lasers with a common LO-phonon extraction and injection stage. In: Intersubband Transitions in Quantum Wells (ITQW) 2015, 6 - 11 September 2015, Vienna. (Unpublished)

Reuse

Unless indicated otherwise, fulltext items are protected by copyright with all rights reserved. The copyright exception in section 29 of the Copyright, Designs and Patents Act 1988 allows the making of a single copy solely for the purpose of non-commercial research or private study within the limits of fair dealing. The publisher or other rights-holder may allow further reproduction and re-use of this version - refer to the White Rose Research Online record for this item. Where records identify the publisher as the copyright holder, users can verify any specific terms of use on the publisher's website.

Takedown

If you consider content in White Rose Research Online to be in breach of UK law, please notify us by emailing eprints@whiterose.ac.uk including the URL of the record and the reason for the withdrawal request.



eprints@whiterose.ac.uk
<https://eprints.whiterose.ac.uk/>

Three-well terahertz frequency quantum cascade lasers with a common LO-phonon extraction and injection stage

**Y. J. Han^{1,*}, L. H. Li¹, L. Chen¹, A. Valavanis¹, A. Grier¹, J. Zhu¹, J. R. Freeman¹,
P. Dean¹, N. Isac², R. Colombelli², A. G. Davies¹, and E. H. Linfield¹**

¹ School of Electronic and Electrical Engineering, University of Leeds, Leeds LS2 9JT, United Kingdom

² Institut d'Electronique Fondamentale, Univ. Paris Sud, UMR8622 CNRS, 91405 Orsay, France

*Contact Email: y.han@leeds.ac.uk

1. Introduction

Terahertz-frequency quantum cascade lasers (THz QCLs) are promising sources for many applications including THz spectroscopy, remote sensing and THz imaging.^{1,2} However, cryogenic cooling is needed for THz QCLs, limiting their practical use in many applications outside the laboratory environment. In order to improve the temperature performance, an extraction-controlled design was proposed, based on an indirect pumping scheme, where LO-phonon scattering replaces resonant tunnelling for carrier injection.³ Here, we present a three-well design, in which one diagonal phonon-scattering process is employed to realize both the carrier extraction and injection simultaneously. Its simplicity makes it an ideal platform to investigate the scattering injection process for high temperature operation of THz QCLs.

2. Design of active region

The conduction band profile and the squared moduli of the electronic wavefunctions of two periods of our GaAs/Al_{0.15}Ga_{0.85}As structure at the design bias are shown in Fig. 1. Levels 2 and 1 are the laser states for the emission of THz radiation; level 3 then behaves as the injection level of the same period and simultaneously as the extraction level of the previous period. The energy separation between levels 3 and 2 is designed to be equal to the LO-phonon energy, enabling fast resonant LO-phonon scattering to transport electrons from level 3 to level 2. The electrons in level 1 are extracted rapidly via resonant tunnelling and subsequently by LO-phonon scattering. This leads to a short lifetime for level 1, and hence a population inversion between laser-levels 2 and 1.

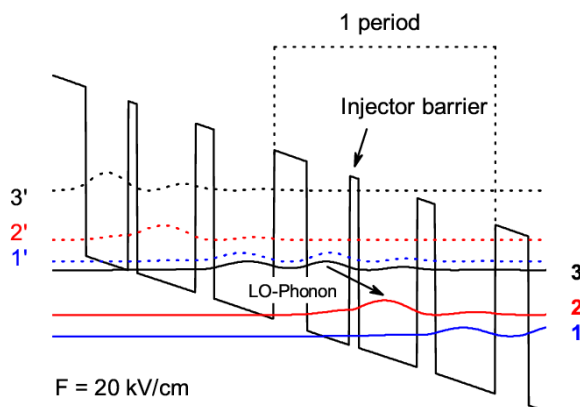


Fig. 1: Calculated conduction band diagram and squared moduli of the electronic wave functions of a three-well design in GaAs/Al_{0.15}Ga_{0.85}As at an electric field of 20 kV/cm.

3. Experimental results

The sample was grown by molecular beam epitaxy. The QCL structure consisted of a 10- μm -thick stack containing the periodic three-well active module, which was embedded between two n^+ -GaAs layers ($n = 5.0 \times 10^{18} \text{ cm}^{-3}$). Devices were fabricated using a gold–gold waveguide configuration, and the laser ridges were defined by wet-chemical etching. For the light intensity–current–voltage (L–I–V) and spectral characterization, the devices were operated in pulsed mode with 2- μs -long pulses at a repetition rate of 10 kHz and the laser emission was detected using a cooled Ge:Ga bolometer. The output power was calibrated with an absolute THz power meter (Thomas–Keating Instruments).

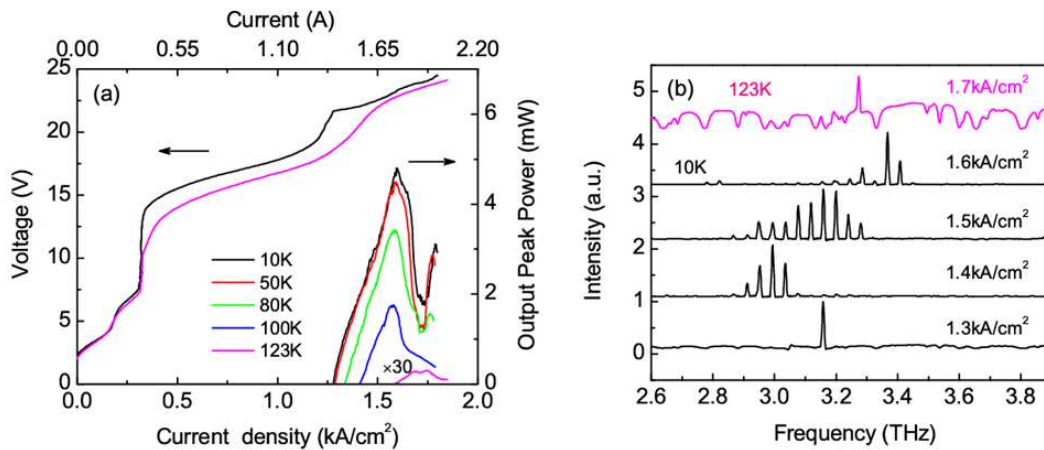


Fig. 2: (a) L–I–V characteristics at various temperatures. (b) Spectra at 10 K and 123 K. The device was 1000 μm long and 110 μm wide, processed into a gold–gold waveguide configuration.

The L–I–V curves and the measured spectra at various biases are shown in Fig. 2(a) and Fig. 2(b), respectively. The device lased up to 123 K in pulsed mode. At a temperature of 10 K, the threshold current density is 1.32 kA/cm^2 and the peak output power is 4.8 mW. The emission frequency was centred at ~ 3.1 THz at biases close to threshold. With increasing bias, the spectra broadened and multi-mode lasing behaviour over the range 2.9 to 3.4 THz was observed. The large threshold current density and the temperature performance will be analysed based on a density matrix model.

We acknowledge financial support from the EPSRC (UK) ‘COTS’ programme, the ERC grant ‘TOSCA’, the European Space Agency, and the CEOI-ST. AGD acknowledges support from the Royal Society and the Wolfson Foundation. RC acknowledges partial support from the ANR projects PHASE-LOCK and the ERC ‘GEM’ grant (Grant Agreement No. 306661). YJH thanks R. Dong for his assistance in the device processing.

References

- [1] R. Köhler, A. Tredicucci, F. Beltram, H. E. Beere, E. H. Linfield, A. G. Davies, D. A. Ritchie, R. C. Iotti, and F. Rossi, “Terahertz semiconductor-heterostructure laser,” *Nature* 417, 156 (2002).
- [2] P. Dean, A. Valavanis, J. Keeley, K. Bertling, Y. L. Lim, R. Alhathloul, A. D. Burnett, L. H. Li, S. P. Khanna, D. Indjin, T. Taimre, A. D. Rakić, E. H. Linfield, and A. G. Davies, “Terahertz imaging using quantum cascade lasers - review of systems and applications,” *J. Phys. D* 47, 374008 (2014).
- [3] A. Wacker, “Extraction-controlled quantum cascade lasers,” *Appl. Phys. Lett.* 97, 081105 (2010).