



Ruthenium indenylidene “1st generation” olefin metathesis catalysts containing triisopropyl phosphite

Stefano Guidone, Fady Nahra, Alexandra M. Z. Slawin and Catherine S. J. Cazin*

Full Research Paper

[Open Access](#)**Address:**

EaStCHEM School of Chemistry, University of St Andrews, St Andrews, UK, KY16 9ST, UK

Email:

Catherine S. J. Cazin* - cc111@st-andrews.ac.uk

* Corresponding author

Keywords:

1st generation; indenylidene; metathesis; phosphite; ruthenium

Beilstein J. Org. Chem. **2015**, *11*, 1520–1527.

doi:10.3762/bjoc.11.166

Received: 16 June 2015

Accepted: 05 August 2015

Published: 01 September 2015

This article is part of the Thematic Series "Progress in metathesis chemistry II".

Guest Editor: K. Grela

© 2015 Guidone et al; licensee Beilstein-Institut.

License and terms: see end of document.

Abstract


The reaction of triisopropyl phosphite with phosphine-based indenylidene pre-catalysts affords “1st generation” *cis*-complexes. These have been used in olefin metathesis reactions. The *cis*-Ru species exhibit noticeable differences with the *trans*-Ru parent complexes in terms of structure, thermal stability and reactivity. Experimental data underline the importance of synergistic effects between phosphites and L-type ligands.

Introduction

The olefin metathesis reaction is a powerful tool for C–C bond formation in the synthesis of highly valuable organic compounds [1-4]. Protocols involving W-, Mo- and Ru-based pre-catalysts can shorten or provide alternative synthetic pathways for the synthesis of natural products displaying complex chemical structures [5-9]. Ru-based pre-catalysts are known to be more air-, moisture- and functional-group tolerant compared to early transition metal complexes [10-13]. In general, the commonly used Ru(II)-based pre-catalysts have five ligands in the metal coordination sphere and adopt a distorted square pyramidal geometry (Figure 1).

The basic components of this structure include two L-type ligands mutually *trans* (e.g., phosphines and *N*-heterocyclic

carbene) and two halides. The apex of the pyramid is occupied by an alkylidene moiety, such as a benzylidene or an indenylidene. Mixed NHC/phosphine complexes (**G-II** and **Ind-II**) known as “2nd generation” pre-catalysts generally display higher catalytic activity than “1st generation” complexes (**G-I** and **Ind-I**) containing two phosphines [14-23]. The most common phosphine, so called “throw-away ligand”, is tricyclohexyl phosphine [10-23]. In other words, such phosphorus donor ligands dissociate from the metal center to afford the 14e⁻ active species [10-13,24]. In order to reduce the cost of the Ru-based pre-catalyst, our group has investigated the use of phosphites as an economical alternative to phosphines. The reaction of triisopropyl phosphite with the pyridine-containing indenylidene complex [RuCl₂(Ind)(SIMes)(py)] (SIMes = *N,N'*-

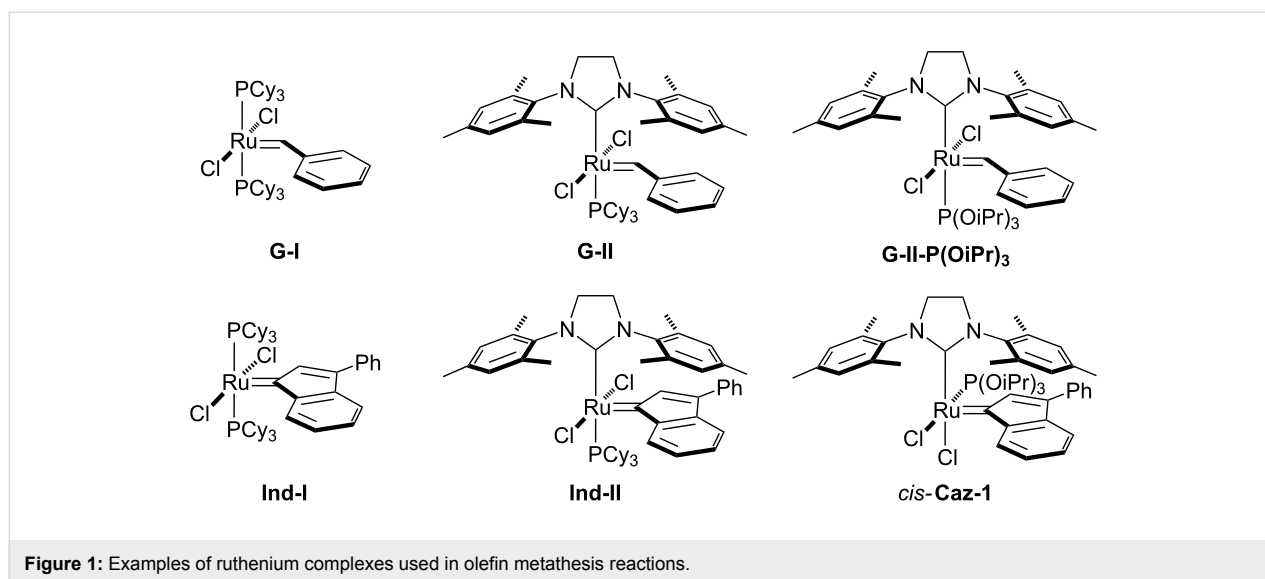

bis[2,4,6-(trimethyl)phenyl]imidazolidin-2-ylidene) afforded a Ru pre-catalyst displaying an unusual *cis*-geometry [25]. *cis-Caz-1*, which is more thermodynamically stable than its *trans*-isomer represents a breakthrough in catalyst-design for metathesis reactions of challenging hindered substrates (Figure 1) [25–34]. The latent behavior exhibited by *cis-Caz-1* can be of interest in fields such as polymer chemistry, where its thermally-switchable properties can be used to inhibit polymerization during the storage of monomer-catalyst mixtures, and/or to initiate polymerization on demand through use of a stimulus [35,36]. The use of this catalyst in the ring-closing metathesis (RCM) reaction gave excellent conversions of challenging substrates, even at low catalyst loadings. The high activity and robustness of *cis-Caz-1* is derived from synergistic effects between the σ -donor ligand NHC and the π -acidic triisopropyl phosphite [25,37]. Subsequently, the benzylidene analogue **G-II-P(OiPr)₃** was also reported. The latter displayed a typical *trans*-configuration, seen in other Ru pre-catalysts, and gave a similar catalytic activity to that of the phosphine-containing parent **G-II** [26].


Because of the recent interest in “1st generation” complexes [9,38–40], previous findings concerning “2nd generation” complexes [25–33] and the desire to further reduce catalyst cost, the aim of this contribution is to replace the phosphine ligands in **Ind-I** with the less expensive triisopropyl phosphite and to study the structural and catalytic properties of these new species.

Results and Discussion

Synthesis of [RuCl₂(Ind)(PCy₃){P(OiPr)₃}] (**1**)

Attempts towards the synthesis of a mixed phosphine/phosphite complex involved the reaction of **Ind-I** with a stoichiometric

amount of triisopropyl phosphite. Complex **1** was isolated in analytically pure form in 85% yield, after recrystallization, using a simple ligand exchange reaction (Scheme 1).

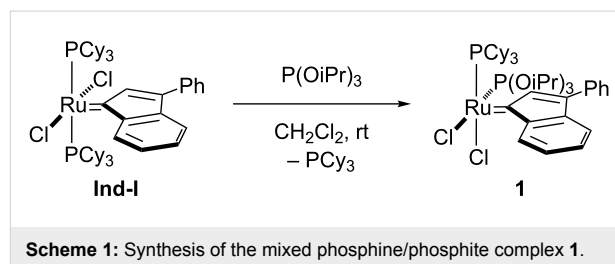

Similarly to the mixed NHC/phosphite species **Caz-1** [25], the *cis*-geometry is the most thermodynamically stable conformation for the phosphine/phosphite complex **1**. The corresponding *trans*-isomer was not isolated due to the fast isomerization occurring under the reaction conditions, although traces of transient species were detected by ³¹P-¹H NMR spectroscopy (see Supporting Information File 1, section 4). The ¹H NMR spectrum of **1** in CD₂Cl₂ showed the typical indenylidene proton system (characteristic doublet at low field, $\delta_{\text{H}} = 8.80$ ppm). Coalescence of the aliphatic protons assigned to the cyclohexyl and the phosphite moieties was also observed at room temperature. These signals were resolved at a lower temperature (193 K). The ¹³C-¹H NMR spectrum showed a doublet of doublets for the carbene carbon at $\delta_{\text{C}} = 290.3$ ppm with two ²J_{CP} of 12.5 and 24.5 Hz (cf., *cis-Caz-1*; 24.7 Hz) [25]. In the ³¹P-¹H NMR spectrum, two doublets at 120.1 and 47.4 ppm with ²J_{PP} of 37.0 Hz were observed, consistent with a *cis*-disposition of the phosphorus donor ligands. This geometry was confirmed by X-ray diffraction analysis on a single crystal (Figure 2).

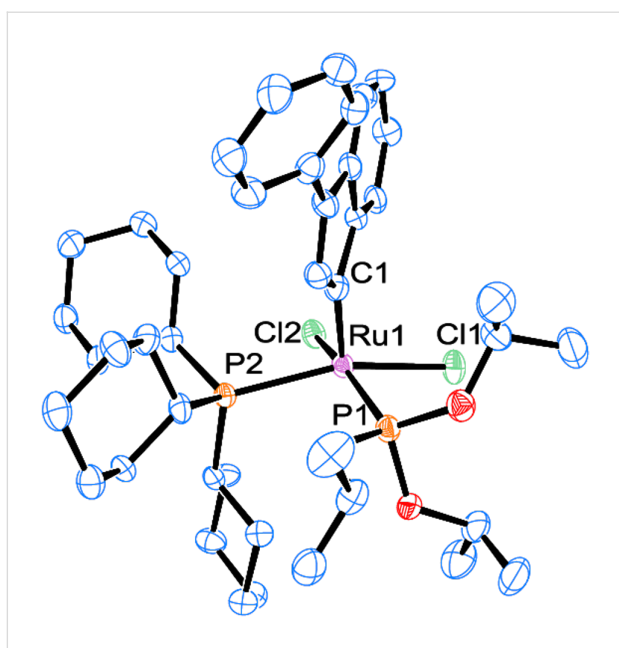


Figure 2: Molecular structure of mixed phosphine/phosphite complex **1**. Hydrogen atoms are omitted for clarity.

Synthesis of $[\text{RuCl}_2(\text{Ind})\{\text{P}(\text{OiPr})_3\}_2]$ (**2**)

The synthesis of the bis-phosphite species **2** was first attempted by the reaction of **Ind-I** with 2.5 equivalents of $\text{P}(\text{OiPr})_3$. Full conversion of the starting material was observed affording complex **2** (Scheme 2). Unfortunately, all attempts to purify **2** failed due to the presence of PCy_3 decomposition products. The PPh_3 adduct **Ind-I⁰** was then employed as alternative starting material for the ligand substitution reaction with the phosphite (Scheme 2) (see Supporting Information File 1, section 4). During the recrystallization from dichloromethane/pentane, compound **3** was detected as a decomposition product [41].

Due to the high solubility of this species and difficulties encountered in the purification process, product **2** was isolated with traces of compound **3** still present. In the ^1H NMR spectrum of **2** in CD_2Cl_2 (with **3** present), the characteristic doublet at $\delta_{\text{H}} = 8.53$ ppm for the indenylidene system was observed.


The $^{13}\text{C}\{-^1\text{H}\}$ NMR spectrum contains a doublet of doublets for the carbene carbon at $\delta_{\text{C}} = 291.1$ ppm with two similar $^2J_{\text{CP}}$ of 22.0 Hz (cf. *cis-Caz-1*, 24.7 Hz) [25]. In the $^{31}\text{P}\{-^1\text{H}\}$ NMR spectrum, two singlets at $\delta_{\text{P}} = 123.0$ ppm and 10.9 ppm corresponding to **2** and **3**, respectively, were detected. Fortunately, we were able to cleanly isolate **3**, which allowed its full characterization and assignment. Crystals suitable for X-ray diffraction studies were grown for both species. These studies confirmed the relative *cis*-disposition of the phosphite ligands in **2** and the structure of **3** (Figure 3).

Complexes **1** and **2** display a rare distorted *cis*-square pyramidal geometry as observed in the case of *cis-Caz-1* [25]. The *cis*-geometry differentiates these species from other “1st generation” complexes that display the more common *trans*-geometry [14–17]. Comparing the details of the three structures in Table 1 (entries 1 to 3), the $\text{Ru}\text{--}\text{C}_{\text{NHC}}$ bond distances are found shorter than $\text{Ru}\text{--}\text{P}_{\text{phosphite}}$, and both of them are shorter than $\text{Ru}\text{--}\text{P}_{\text{phosphine}}$ ($\text{Ru}(1)\text{--}\text{P}(2)$ complex **1**) [34].

From data listed in Table 1, the $\text{Ru}\text{--}\text{P}$ bond appears stronger in the case of the $\text{Ru}\text{--}\text{phosphite}$ than the $\text{Ru}\text{--}\text{phosphine}$ scenario, suggesting the latter as the leaving ligand in catalysis (see Supporting Information File 1, section 5).

Catalytic activity in ring-closing metathesis (RCM)

The reactivity of the mixed phosphine/phosphite complex **1** was first evaluated in the RCM of the easily cyclized diethyl diallylmalonate (**4**) (see Supporting Information File 1, section 2). The need for thermal activation for this pre-catalyst was clearly revealed by the low catalytic activity at 30–50 °C and the high conversion observed at 80 °C in toluene (0.1 mol % of **1**, 94% conv.). Contrary to **1**, the phosphine-based **Ind-I** initiates at 30 °C exhibiting good catalytic activity and undergoes fast decomposition at higher temperature with moderate conversion (see Supporting Information File 1, section 2). This trend was further studied by profiling reactions under catalytic conditions (Figure 4).

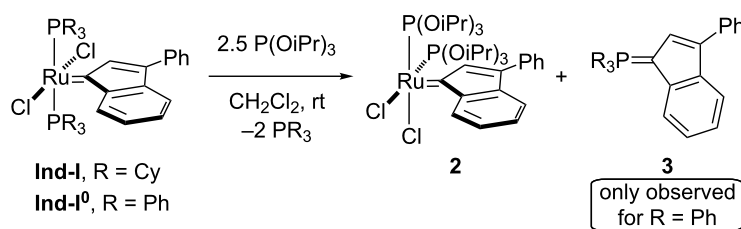

Scheme 2: Synthesis of the bis-phosphite complex **2**.

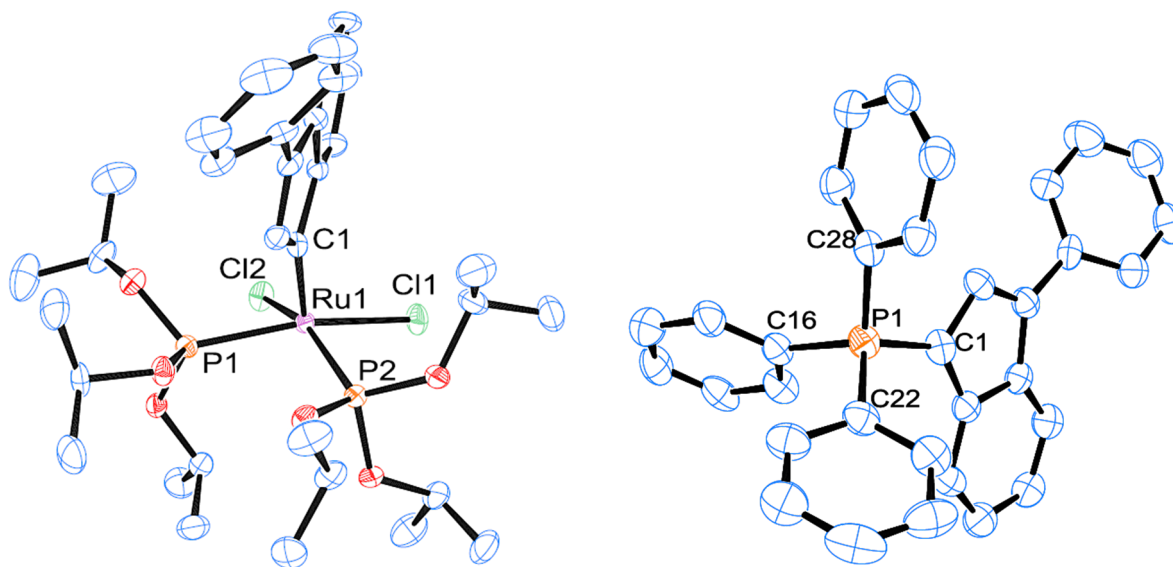


Figure 3: Molecular structure of **2** and the ylide **3**. Hydrogen atoms and solvent molecules are omitted for clarity. Selected bond distances (Å) and angles (°) (ESD) for compound **3**: P(1)–C(1), 1.713(5); P(1)–C(28), 1.795(5); P(1)–C(22), 1.805(5); P(1)–C(16), 1.811(5); C(1)–P(1)–C(28), 106.2(2); C(1)–P(1)–C(22), 113.1(3); C(28)–P(1)–C(22), 109.0(2); C(1)–P(1)–C(16), 113.3(2); C(28)–P(1)–C(16), 109.2(2); C(22)–P(1)–C(16), 105.9(2).

Table 1: Selected bond distances (Å) and angles (°) for **1**, **2** and *cis*-Caz-1.


Entry	Parameter	1	2	<i>cis</i> -Caz-1[25]
1	Ru(1)–C(1)	1.873(14)	1.869(3)	1.881(8)
2	Ru(1)–P(1)	2.239(4)	2.2300(9)	2.249(2)
3	Ru(1)–P(2)	2.387(4)	2.2663(8)	–
4	Ru(1)–C(NHC)	–	–	2.067(7)
5	Ru(1)–Cl(1)	2.398(4)	2.3999(9)	2.4036(18)
6	Ru(1)–Cl(2)	2.369(3)	2.3789(8)	2.3974(19)
7	P(1)–Ru(1)–P(2)	98.74(13)	97.34(3)	–
8	C(NHC)–Ru(1)–P(1)	–	–	100.06(19)
9	C(1)–Ru(1)–P(1)	90.2(5)	90.94(10)	90.5(2)
10	C(1)–Ru(1)–P(2)	94.3(4)	86.41(9)	–
11	C(1)–Ru(1)–C(NHC)	–	–	98.7(3)

An induction period was observed for **1** at the early stage of the catalysis, a behavior similar to *cis*-Caz-1 [25], followed by a fast reaction with full conversion of the substrate at 80 °C in less than 50 min. These features prompted us to hypothesize an isomerization step from the *cis*-pre-catalyst **1** to the corresponding *trans* isomer as reported for *cis*-Caz-1 (see Supporting Information File 1, section 2) [25]. Under the same conditions, instant pre-catalyst initiation and fast decomposition of the active species were observed for the phosphine-based pre-catalyst **Ind-I** (86% conversion after 30 min). When the experiment was performed at 30 °C, **Ind-I** exhibited slower conversion of the substrate, reaching complete conversion after 4 h [22]. The reaction profiles show the importance of synergistic

effects in the case of the mixed phosphine/phosphite system. Complex **1** is a thermally-switchable, latent pre-catalyst displaying higher thermal stability compared to the phosphine-based **Ind-I**.

Consequently, a brief study of the scope of the reaction was investigated employing “1st generation” complexes **1** and **Ind-I** (Table 2).

The diene **6** was poorly converted by mixed PCy₃/P(OR)₃ complex **1**, whereas 94% conversion was obtained with **Ind-I** (Table 2, entries 1–4). In the case of tri-substituted diene **8**, a more challenging substrate compared to **6**, pre-catalyst **1** gave

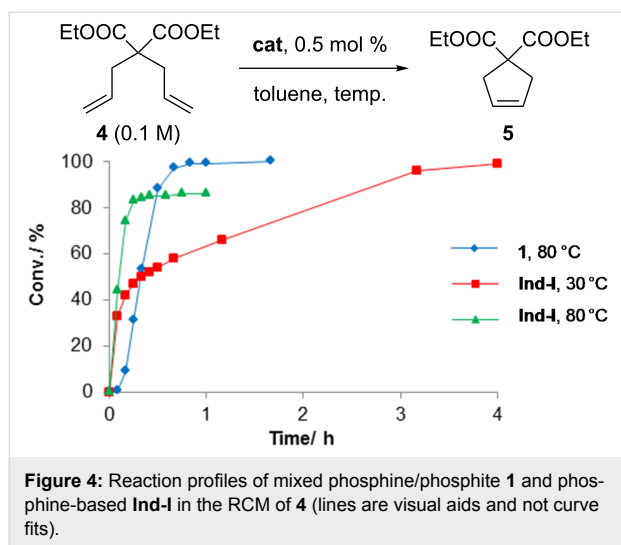

79% conversion while **Ind-I** converted 33% of the substrate at 80 °C and 53% at 30 °C (Table 2, entries 5–7). The tosylamide derivative **10** was converted into product **11** by **1** (1 mol %) with 41% conversion (Table 2, entry 8). When the loading was increased to 2 mol %, no improvement in the conversion was detected (Table 2, entry 9). A higher catalytic activity was observed for **Ind-I** with 77% conversion when using 2 mol % pre-catalyst at 30 °C (Table 2, entry 13). Complex **1** was active in the ring-closing enyne metathesis (RCEYM) with 78% conversion of substrate **12** obtained with 1 mol % catalyst

loading (Table 2, entry 14). A higher conversion of compound **12** was detected with **Ind-I** (98%, Table 2, entry 15).

Conclusion

The influence of triisopropyl phosphite in Ru-based indenylidene “1st generation” complexes has been presented. The mixed phosphine/phosphite complex **1** and the bis-phosphite complex **2** adopt distorted square pyramidal geometries with the P-donor ligands mutually *cis* as the most thermodynamically stable conformation. The isolation of the corresponding *trans*-isomers was not possible due to a fast isomerization process occurring during the synthesis of the complexes. Pre-catalyst **1** was found to be active in olefin metathesis reaction showing similarities with *cis*-**Caz-1** in terms of reactivity. Both pre-catalysts need thermal activation; they display an induction period in the reaction profiling and exhibit higher thermal stability compared to their phosphine-based analogues. In terms of catalytic efficiency, **Ind-I** was found more active than **1** unless higher thermal stability is needed. Indeed, in the case of the malonate derivative **8**, pre-catalyst **1** afforded the tri-substituted ring-closed product in 71% isolated yield. The similar structural and catalytic properties observed in the mixed phosphine/phosphite complex **1** and the mixed NHC/phosphite *cis*-**Caz-1** suggest the importance of synergistic effects involving phosphites, an inexpensive alternative to phosphines for Ru-based pre-catalysts, and the L-type ligands, a concept that can be used to incite further improvements in catalyst design.

Table 2: Scope of the reaction employing **1** and **Ind-I**.^a

Entry	Substrate	Product	Pre-catalyst (mol %)	T (°C)	Conv. (%) ^b
1			1 (0.1)	80	<1
2			1 (1)	80	4
3			Ind-I (0.1)	80	94
4			Ind-I (0.1)	30	94
5			1 (1)	80	79 (71)
6			Ind-I (1)	80	33
7			Ind-I (1)	30	53
8			1 (1)	80	41
9			1 (2)	80	41
10			Ind-I (1)	80	22
11			Ind-I (1)	30	21
12			Ind-I (2)	80	30
13			Ind-I (2)	30	77
14			1 (1)	80	78
15			Ind-I (1)	30	98

^aReaction conditions: substrate (0.25 mmol), pre-catalyst (0.1 to 2 mol %), toluene (0.5 mL), 19 h. ^bConversions were determined by GC analysis. Isolated yields in parentheses.

Experimental

Synthesis and characterization of

[RuCl₂(Ind)(PCy₃)₂]{P(OiPr)₃} (1): Under an inert atmosphere of argon, triisopropyl phosphite (364 μL, 1.53 mmol) was added to a solution of **Ind-I** (1.414 g, 1.53 mmol) in dichloromethane (20 mL). The mixture was stirred for 24 h at room temperature and the solvent was then removed in vacuo. The crude product was recrystallized twice from dichloromethane/pentane. The solid was collected by filtration and washed with pentane (3 × 10, 2 × 15 mL). The product was obtained as a brownish red solid (1.116 g, 85%). During NMR experiments, peaks originating from the decomposition of the PCy₃ were observed. ¹H NMR of the mixture (400 MHz, CD₂Cl₂) δ 1.08–1.33 (m, 6H, PCy₃), 1.11 (d, ³J_{HH} = 6.3 Hz, 9H, CH-CH₃), 1.30 (d, ³J_{HH} = 6.3 Hz, 9H, CH-CH₃), 1.40–1.55 (m, 9H, PCy₃), 1.60–1.85 (m, 15H, PCy₃), 2.50 (m, 3H, CH PCy₃), 4.55 (m, 3H, CH-CH₃), 6.79 (s, 1H, H²), 7.27 (d, ³J_{HH} = 7.1 Hz, 1H, H⁴), 7.43 (dd, ³J_{HH} = 6.7 Hz, ³J_{HH} = 6.3 Hz, 1H, H⁵), 7.44 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 6.3 Hz, 2H, H¹⁰), 7.50 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.7 Hz, 1H, H¹¹), 7.53 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.4 Hz, 1H, H⁶), 7.76 (d, ³J_{HH} = 7.3 Hz, 2H, H⁹), 8.80 (d, ³J_{HH} = 7.3 Hz, 1H, H⁷) ppm; ¹³C-¹H} NMR of the mixture (100.6 MHz, CD₂Cl₂) δ 24.3 (s, CH-CH₃), 24.5 (d, ³J_{CP} = 4 Hz, CH-CH₃), 26.9 (s, CH₂ PCy₃), 28.1 (d, ²J_{CP} = 11 Hz, CH₂ PCy₃), 28.4 (d, ²J_{CP} = 10 Hz, CH₂ PCy₃), 30.1 (s, CH₂ PCy₃), 30.6 (s, CH₂ PCy₃), 35.3 (s, CH PCy₃), 71.4 (s, CH-CH₃), 118.4 (s, C⁴), 127.0 (s, C⁹), 129.6 (s, C¹⁰), 129.7 (s, C¹¹), 130.2 (s, C⁷), 130.3 (s, C⁶), 130.7 (s, C⁵), 135.1 (s, C⁸), 136.5 (s, C³), 140.6 (s, C^{3a}), 141.3 (dd, ³J_{CP} = 5.0 Hz, ³J_{CP} = 14.0 Hz, C²) 147.8 (s, C^{7a}), 290.3 (dd, ³J_{CP} = 12.5 Hz, ²J_{CP} = 24.5 Hz, C¹) ppm; ³¹P-¹H} NMR of the mixture (162 MHz, CD₂Cl₂) δ 120.1 (d, ²J_{PP} = 37.0 Hz, PCy₃), 47.4 (d, ²J_{PP} = 37.0 Hz, P(OiPr)₃) ppm; anal. calcd for C₄₂H₆₄Cl₂O₃P₂Ru: C, 59.29; H, 7.58; found: C, 59.45; H, 7.66. CCDC-889638 contains the supplementary crystallographic data for **1**. These data can be obtained free of charge from the Cambridge Crystallographic Data Centre via http://www.ccdc.cam.ac.uk/data_request/cif.

Synthesis and characterization of [RuCl₂(Ind){P(OiPr)₃}₂]

(2): Under an inert atmosphere of argon, triisopropyl phosphite (65 μL, 0.28 mmol) was added to a solution of **Ind-I⁰** (0.100 g, 0.113 mmol) in dichloromethane (1.2 mL). The mixture was stirred for 24 h at room temperature and the solvent was removed in vacuo. The crude product was recrystallized from dichloromethane/pentane. The solid was collected by filtration and washed with pentane (3 × 3 mL). The product was obtained as a brownish green solid in a mixture with the phosphonium ylide **3** (0.032 g, 35%). ¹H NMR of the mixture (400 MHz, CD₂Cl₂) δ 1.13 (d, ³J_{HH} = 6.3 Hz, 18H, CH-CH₃), 1.31 (d, ³J_{HH} = 6.1 Hz, 18H, CH-CH₃), 4.53 (m, ³J_{HH} = 6.3 Hz, 6H, CH-CH₃), 7.18 (s, 1H, H²), 7.26 (d, ³J_{HH} = 6.9 Hz, 1H, H⁴),

7.40 (dd, ³J_{HH} = 7.1 Hz, ³J_{HH} = 7.1 Hz, 1H, H⁵), 7.43 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.4 Hz, 1H, H⁶), 7.46 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.4 Hz, 2H, H¹⁰), 7.53 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.4 Hz, 1H, H¹¹), 7.77 (d, ³J_{HH} = 7.3 Hz, 2H, H⁹), 8.53 (d, ³J_{HH} = 7.0 Hz, 1H, H⁷) ppm; ¹³C-¹H} NMR of the mixture (100.6 MHz, CD₂Cl₂) δ 24.0 (s, CH-CH₃), 24.4 (s, CH-CH₃), 71.5 (m, CH-CH₃), 119.0 (s, C⁴), 127.1 (s, C⁹), 129.6 (s, C¹¹), 130.0 (s, C¹⁰), 130.2 (s, C⁶), 130.3 (s, C⁷), 131.2 (s, C⁵), 134.8 (s, C⁸), 136.8 (s, C³), 140.3 (s, C^{3a}), 140.7 (dd, ³J_{CP} = 8.5 Hz, C²) 150.2 (s, C^{7a}), 291.1 (dd, ²J_{CP} = 22.0 Hz, ²J_{CP} = 22.0 Hz, C¹) ppm; ³¹P-¹H} NMR (162 MHz, CD₂Cl₂) δ 123.0 (s, P(OiPr)₃) ppm; CCDC-889639 contains the supplementary crystallographic data for **2**. These data can be obtained free of charge from the Cambridge Crystallographic Data Centre via http://www.ccdc.cam.ac.uk/data_request/cif.

Characterization of Ph₃P(Ind) (3): Under an inert atmosphere of argon, compound **3** was obtained as a side product from the reaction of **Ind-I⁰** (0.303 mg, 0.34 mmol, 1 equiv) with triisopropyl phosphite (179 μL, 0.75 mmol, 2.2 equiv) for 24 h. During recrystallization in a dichloromethane/pentane mixture, compound **3** was isolated as a yellow solid (63.4 mg, 41%). ¹H NMR (400 MHz; CD₂Cl₂) δ 6.73 (d, ²J_{HP} = 4.9 Hz, 1H, H²), 6.77 (dd, ³J_{HH} = 7.5 Hz, ³J_{HH} = 7.5 Hz, 1H, H⁶), 6.89 (d, ³J_{HH} = 7.9 Hz, 1H, H⁷), 6.97 (dd, ³J_{HH} = 7.5 Hz, ³J_{HH} = 7.5 Hz, 1H, H⁵), 7.08 (dd, ³J_{HH} = 7.4 Hz, ³J_{HH} = 7.4 Hz, 1H, H¹¹), 7.32 (dd, ³J_{HH} = 7.6 Hz, ³J_{HH} = 7.6 Hz, 2H, H¹⁰), 7.52–7.60 (m, 6H, C₆H₅), 7.61 (d, ³J_{HH} = 7.9 Hz, 2H, H⁹), 7.66–7.75 (m, 9H, C₆H₅), 7.96 (d, ³J_{HH} = 8.1 Hz, 1H, H⁴) ppm; ¹³C-¹H} NMR (100.6 MHz; CD₂Cl₂) δ 68.5 (d, ¹J_{CP} = 121.6 Hz, C¹), 118.2 (s, C⁵), 118.5 (s, C⁶), 118.7 (s, C⁷), 119.4 (s, C⁴), 121.2 (d, ³J_{CP} = 15.8 Hz, C³), 123.8 (s, C¹¹), 125.6 (d, ¹J_{CP} = 90.3 Hz, *i*-C₆H₅), 127.1 (s, C⁹), 127.8 (d, ²J_{CP} = 16.5 Hz, C²), 128.7 (s, C¹⁰), 129.5 (d, ³J_{CP} = 12.3 Hz, *m*-C₆H₅), 133.3 (d, ⁴J_{CP} = 2.7 Hz, *p*-C₆H₅), 134.2 (d, ²J_{CP} = 10.3 Hz, *o*-C₆H₅), 135.0 (d, ³J_{CP} = 13.9 Hz, C^{3a}), 137.1 (d, ²J_{CP} = 13.2 Hz, C^{7a}), 140.5 (s, C⁸) ppm; ³¹P-¹H} NMR (162 MHz; CD₂Cl₂) δ 10.9 (s, Ph₃P(Ind)) ppm; HMRS (APCI): *m/z* calcd for [C₃₃H₂₅P + H] 453.18; found 453.1754. CCDC-889640 contains the supplementary crystallographic data for **3**. These data can be obtained free of charge from the Cambridge Crystallographic Data Centre via http://www.ccdc.cam.ac.uk/data_request/cif.

General procedure for catalysis: Substrates **6** [42], **8** [43], **10** [42], **12** [22], were synthesized following previous reports in the literature. Compound **4** was obtained from a commercial source and its purity confirmed prior to use. ¹H NMR data of product **9** were compared to previously reported analyses [22].

A 5 mL screwcap-vial fitted with a septum equipped with a magnetic stirring bar was charged with the olefin (0.25 mmol)

then purged with nitrogen, closed and introduced in a glovebox. The solvent and pre-catalyst (stock solution for <1 mol %, or weighed in the vial) were added to the reaction mixture (total amount of solvent 0.5 mL). Once out of the glovebox, the reaction mixture was heated at the desired temperature and stirred for 14 or 19 hours. The reaction mixture was then analyzed by GC and/or purified by flash chromatography.

General procedure for kinetic experiments. A Schlenk flask was charged with the olefin (0.5 mmol), then closed, placed under vacuum and introduced in a glovebox. The solvent was added (5 mL) and then the pre-catalyst was weighed and charged into the Schlenk flask. Out of the glovebox, the reaction was performed at the desired temperature. Samples were taken under nitrogen flow and quenched with ethyl vinyl ether. Data were obtained by GC analysis.

Supporting Information

Crystallographic data for complexes **1–3** in CIF format can be obtained free of charge from the Cambridge Crystallographic Data Centre via http://www.ccdc.cam.ac.uk/data_request/cif (CCDC/889638-889640).

Supporting Information File 1

Crystallographic data for compounds **1–3**, NMR spectra of all the complexes, spectroscopic data.
[<http://www.beilstein-journals.org/bjoc/content/supplementary/1860-5397-11-166-S1.pdf>]

Supporting Information File 2

CIF file for complex **2**.
[<http://www.beilstein-journals.org/bjoc/content/supplementary/1860-5397-11-166-S2.cif>]

Supporting Information File 3

CIF file for complex **3**.
[<http://www.beilstein-journals.org/bjoc/content/supplementary/1860-5397-11-166-S3.cif>]

Supporting Information File 4

CIF file for complex **4**.
[<http://www.beilstein-journals.org/bjoc/content/supplementary/1860-5397-11-166-S4.cif>]

Acknowledgements

The authors gratefully acknowledge the Royal Society (University Research Fellowship to CSJC) and the EC (CP-FP 211468-2 EUMET) for funding and the EPSRC National Mass Spec-

trometry Service Centre Swansea University for HMRS analyses.

References

- Hoveyda, A. H.; Zhugralin, A. R. *Nature* **2007**, *450*, 243–251. doi:10.1038/nature06351
- Chauvin, Y. *Angew. Chem., Int. Ed.* **2006**, *45*, 3740–3747. doi:10.1002/anie.200601234
- Schrock, R. R. *Angew. Chem., Int. Ed.* **2006**, *45*, 3748–3759. doi:10.1002/anie.200600085
- Grubbs, R. H. *Angew. Chem., Int. Ed.* **2006**, *45*, 3760–3765. doi:10.1002/anie.200600680
- Fürstner, A. *Angew. Chem., Int. Ed.* **2000**, *39*, 3012–3043. doi:10.1002/1521-3773(20000901)39:17<3012::AID-ANIE3012>3.0.CO;2-G
- Buchmeiser, M. R. *Chem. Rev.* **2000**, *100*, 1565–1604. doi:10.1021/cr990248a
- Connon, S. J.; Blechert, S. *Angew. Chem., Int. Ed.* **2003**, *42*, 1900–1923. doi:10.1002/anie.200200556
- Grubbs, R. H.; Miller, S. J.; Fu, G. C. *Acc. Chem. Res.* **1995**, *28*, 446–452. doi:10.1021/ar00059a002
- Nicolaou, K. C.; Bulger, P. G.; Sarlah, D. *Angew. Chem., Int. Ed.* **2005**, *44*, 4490–4527. doi:10.1002/anie.200500369
- Trnka, T. M.; Grubbs, R. H. *Acc. Chem. Res.* **2001**, *34*, 18–29. doi:10.1021/ar000114f
- Schrock, R. R.; Hoveyda, A. H. *Angew. Chem., Int. Ed.* **2003**, *42*, 4592–4633. doi:10.1002/anie.200300576
- Grubbs, R. H., Ed. *Handbook of Metathesis: Catalyst Development*; Wiley-VCH: Weinheim, Germany, 2003. doi:10.1002/9783527619481
- Grela, K., Ed. *Olefin Metathesis – Theory and Practice*; Wiley-VCH: Weinheim, Germany, 2014.
- Nguyen, S. T.; Johnson, L. K.; Grubbs, R. H.; Ziller, J. W. *J. Am. Chem. Soc.* **1992**, *114*, 3974–3975. doi:10.1021/ja00036a053
- Nguyen, S. T.; Grubbs, R. H.; Ziller, J. W. *J. Am. Chem. Soc.* **1993**, *115*, 9858–9859. doi:10.1021/ja00074a086
- Schwab, P.; Grubbs, R. H.; Ziller, J. W. *J. Am. Chem. Soc.* **1996**, *118*, 100–110. doi:10.1021/ja952676d
- Boeda, F.; Clavier, H.; Nolan, S. P. *Chem. Commun.* **2008**, 2726–2740. doi:10.1039/b718287b
- Weskamp, T.; Kohl, F. J.; Herrmann, W. A. *J. Organomet. Chem.* **1999**, *582*, 362–365. doi:10.1016/S0022-328X(99)00163-1
- Huang, J.; Schanz, H.-J.; Stevens, E. D.; Nolan, S. P. *Organometallics* **1999**, *18*, 5375–5380. doi:10.1021/om990788y
- Scholl, M.; Ding, S.; Lee, C. W.; Grubbs, R. H. *Org. Lett.* **1999**, *1*, 953–956. doi:10.1021/ol990909q
- Sanford, M. S.; Love, J. A.; Grubbs, R. H. *J. Am. Chem. Soc.* **2001**, *123*, 6543–6554. doi:10.1021/ja010624k
- Clavier, H.; Nolan, S. P. *Chem. – Eur. J.* **2007**, *13*, 8029–8036. doi:10.1002/chem.200700256
- Monsaert, S.; Drozdak, R.; Dragutan, V.; Dragutan, I.; Verpoort, F. *Eur. J. Inorg. Chem.* **2008**, 432–440. doi:10.1002/ejic.200700879
- Nelson, D. J.; Manzini, S.; Urbina-Blanco, C. A.; Nolan, S. P. *Chem. Commun.* **2014**, *50*, 10355–10375. doi:10.1039/C4CC02515F
- Bantreil, X.; Schmid, T. E.; Randall, R. A. M.; Slawin, A. M. Z.; Cazin, C. S. J. *Chem. Commun.* **2010**, *46*, 7115–7117. doi:10.1039/c0cc02448a
- Schmid, T. E.; Bantreil, X.; Citadelle, C. A.; Slawin, A. M. Z.; Cazin, C. S. J. *Chem. Commun.* **2011**, *47*, 7060–7062. doi:10.1039/c1cc10825e

27. Songis, O.; Slawin, A. M. Z.; Cazin, C. S. J. *Chem. Commun.* **2012**, *48*, 1266–1268. doi:10.1039/C2CC15903A
28. Bantreil, X.; Poater, A.; Urbina-Blanco, C. A.; Bidal, Y. D.; Falivene, L.; Randall, R. A. M.; Cavallo, L.; Slawin, A. M. Z.; Cazin, C. S. J. *Organometallics* **2012**, *31*, 7415–7426. doi:10.1021/om300703p
29. Urbina-Blanco, C. A.; Bantreil, X.; Wappel, J.; Schmid, T. E.; Slawin, A. M. Z.; Slugovc, C.; Cazin, C. S. J. *Organometallics* **2013**, *32*, 6240–6247. doi:10.1021/om4004362
30. Falivene, L.; Poater, A.; Cazin, C. S. J.; Slugovc, C.; Cavallo, L. *Dalton Trans.* **2013**, *42*, 7312–7317. doi:10.1039/C2DT32277C
31. Guidone, S.; Songis, O.; Nahra, F.; Cazin, C. S. J. *ACS Catal.* **2015**, *5*, 2697–2701. doi:10.1021/acscatal.5b00197
32. Guidone, S.; Songis, O.; Falivene, L.; Nahra, F.; Slawin, A. M. Z.; Jacobsen, H.; Cavallo, L.; Cazin, C. S. J. *ACS Catal.* **2015**, *5*, 3932–3939. doi:10.1021/acscatal.5b00219
33. Bantreil, X.; Cazin, C. S. J. *Monatsh. Chem.* **2015**, *146*, 1043–1052. doi:10.1007/s00706-015-1487-7
34. Cazin, C. S. J., Ed. *N-Heterocyclic Carbenes in Transition Metal Catalysis and Organocatalysis; Catalysis by Metal Complexes*, Vol. 32; Springer: New York, NY, U.S.A., 2011. doi:10.1007/978-90-481-2866-2
35. Ung, T.; Hejl, A.; Grubbs, R. H.; Schrodi, Y. *Organometallics* **2004**, *23*, 5399–5401. doi:10.1021/om0493210
36. Slugovc, C.; Burtscher, D.; Stelzer, F.; Mereiter, K. *Organometallics* **2005**, *24*, 2255–2258. doi:10.1021/om050141f
37. Ho, C.-Y.; Jamison, T. F. *Angew. Chem., Int. Ed.* **2007**, *46*, 782–785. doi:10.1002/anie.200603907
38. Wallace, D. J.; Reamer, R. A. *J. Org. Chem.* **2014**, *79*, 5644–5651. doi:10.1021/jo500815q
39. Chatterjee, S.; Guchhait, S.; Goswami, R. K. *J. Org. Chem.* **2014**, *79*, 7689–7695. doi:10.1021/jo501184t
40. Keck, C. G.; Kendall, J. L.; Caster, K. C. *Adv. Synth. Catal.* **2007**, *349*, 165–174. doi:10.1002/adsc.200600455
41. Hong, S. H.; Day, M. W.; Grubbs, R. H. *J. Am. Chem. Soc.* **2004**, *126*, 7414–7415. doi:10.1021/ja0488380
Phosphorus ylide bearing the alkylidene moiety has already been proposed.
42. Terada, Y.; Arisawa, M.; Nishida, A. *Angew. Chem., Int. Ed.* **2004**, *43*, 4063–4067. doi:10.1002/anie.200454157
43. Kirkland, T. A.; Grubbs, R. H. *J. Org. Chem.* **1997**, *62*, 7310–7318. doi:10.1021/jo970877p

License and Terms

This is an Open Access article under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/2.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

The license is subject to the *Beilstein Journal of Organic Chemistry* terms and conditions: (<http://www.beilstein-journals.org/bjoc>)

The definitive version of this article is the electronic one which can be found at:
[doi:10.3762/bjoc.11.166](https://doi.org/10.3762/bjoc.11.166)