



Aalborg Universitet

AALBORG UNIVERSITY  
DENMARK

## Methodology For The Simulation of Fatigue-Driven Delamination In 3D Composite Structures

Carreras, Laura; Bak, Brian Lau Verndal; Turon, Albert; Lindgaard, Esben; Renart, Jordi ;  
Essa, Yasser; de la Escalera, Federico Martin

*Publication date:*  
2017

[Link to publication from Aalborg University](#)

### *Citation for published version (APA):*

Carreras, L., Bak, B. L. V., Turon, A., Lindgaard, E., Renart, J., Essa, Y., & de la Escalera, F. M. (2017). *Methodology For The Simulation of Fatigue-Driven Delamination In 3D Composite Structures*. Poster presented at 8th International Conference on Composites Testing and Model Identification (CompTest 2017), Leuven, Belgium.

### **General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- ? Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- ? You may not further distribute the material or use it for any profit-making activity or commercial gain
- ? You may freely distribute the URL identifying the publication in the public portal ?

### **Take down policy**

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.

# METHODOLOGY FOR THE SIMULATION OF FATIGUE-DRIVEN DELAMINATION IN 3D COMPOSITE STRUCTURES

L.Carreras<sup>1</sup>, B.L.V. Bak<sup>2</sup>, A. Turon<sup>1</sup>, E. Lindgaard<sup>2</sup>, J. Renart<sup>1</sup>, Y. Essa<sup>3</sup>, F. Martin de la Escalera<sup>3</sup>

<sup>1</sup> AMADE, Universitat de Girona, Dept. of Mechanical Engineering and Industrial Construction. Universitat de Girona 4, E-17003 Girona, Spain

<sup>2</sup> Aalborg University, Dept. of Mechanical and Manufacturing Engineering. Fibigerstraede 16, DK-9220 Aalborg East, Denmark

<sup>3</sup> AERNNOVA Engineering Division SAU. Parque Tecnológico de Álava, Leonardo da Vinci 13, E-01510 Álava, Spain

## Introduction

Fatigue-driven delamination is one of the most common failure mechanisms in real layered composite structures. A reliable design should account for this damage mechanism. Recently, Bak et al. [1] presented a method based on a cohesive zone model approach which does not rely on any fitting parameter. However, due to the lack of applicable formulations of the  $J$ -integral in 3D cohesive interfaces, Mode III was disregarded and the model was only validated in 2D.

In this work, the method is enhanced for its application to 3D structures where the crack front shape can change during fatigue propagation.


## Method for high-cycle fatigue-driven delamination using a cohesive zone model

The method presented in [1] directly links the cohesive zone model approach for quasi-static crack propagation with any variant of the Paris' law describing the crack growth rate.




$$\frac{dD}{dN} = \left( F_{\beta} \frac{\partial \beta}{\partial a} + F_{\lambda} \frac{\partial \lambda}{\partial a} \right) \frac{da}{dN}$$

$\beta$ : local mode mixity  
 $\lambda$ : opening displacement

$$\frac{da}{dN} = f(G_{max}, R, \phi) \quad \phi = \frac{G_{II}}{G_I + G_{II}}$$

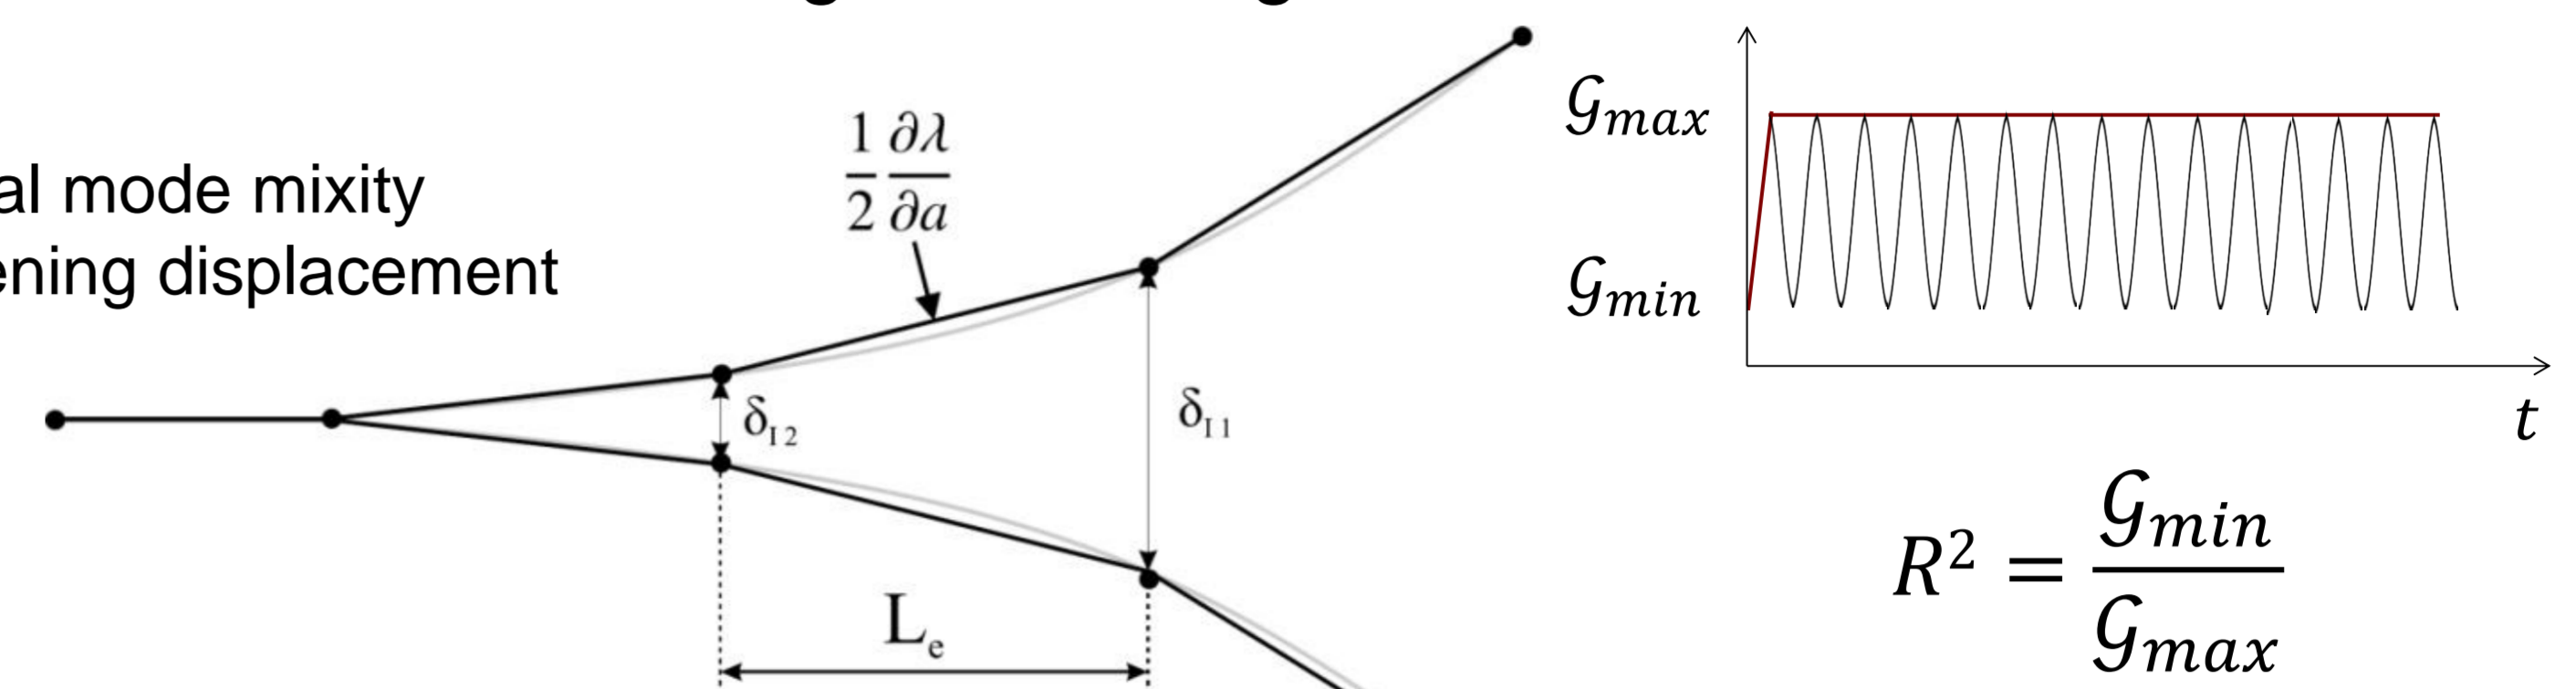



$$R^2 = \frac{G_{min}}{G_{max}}$$

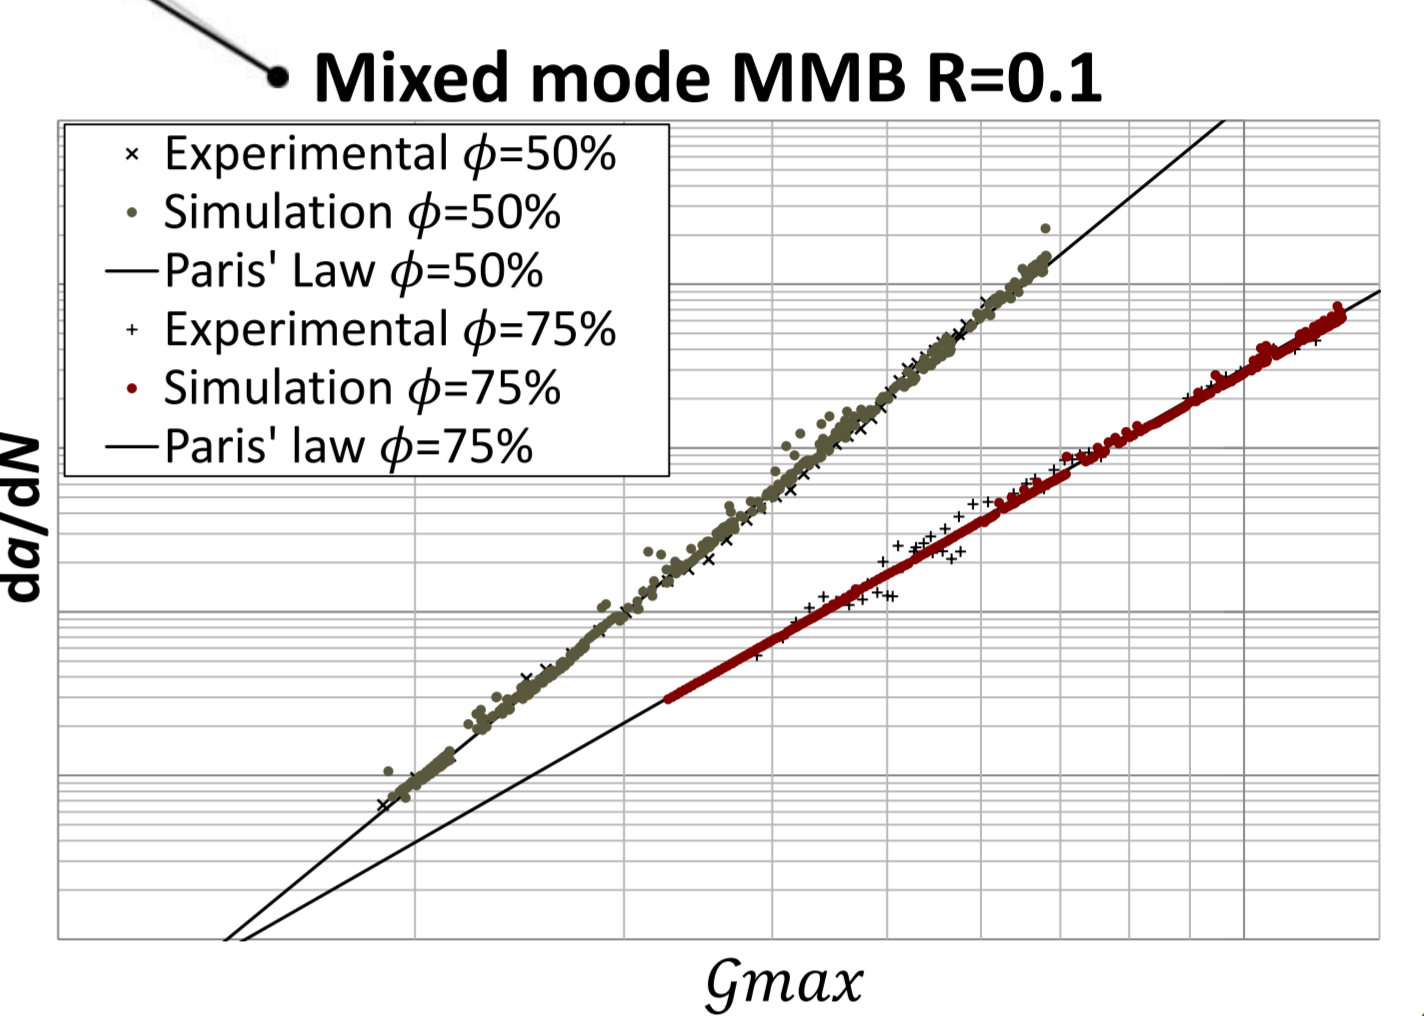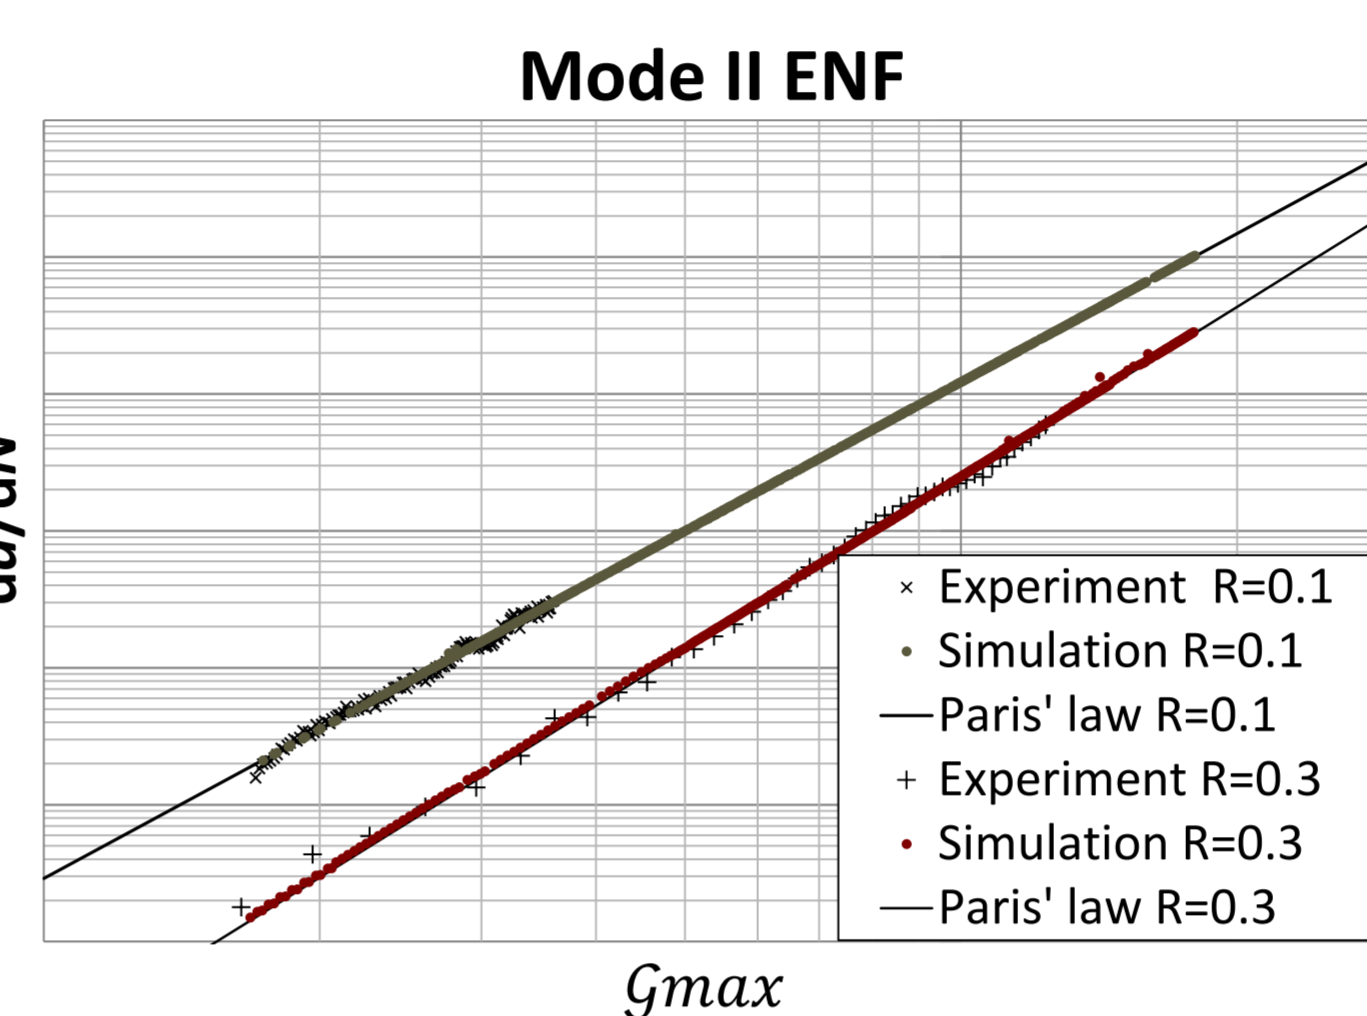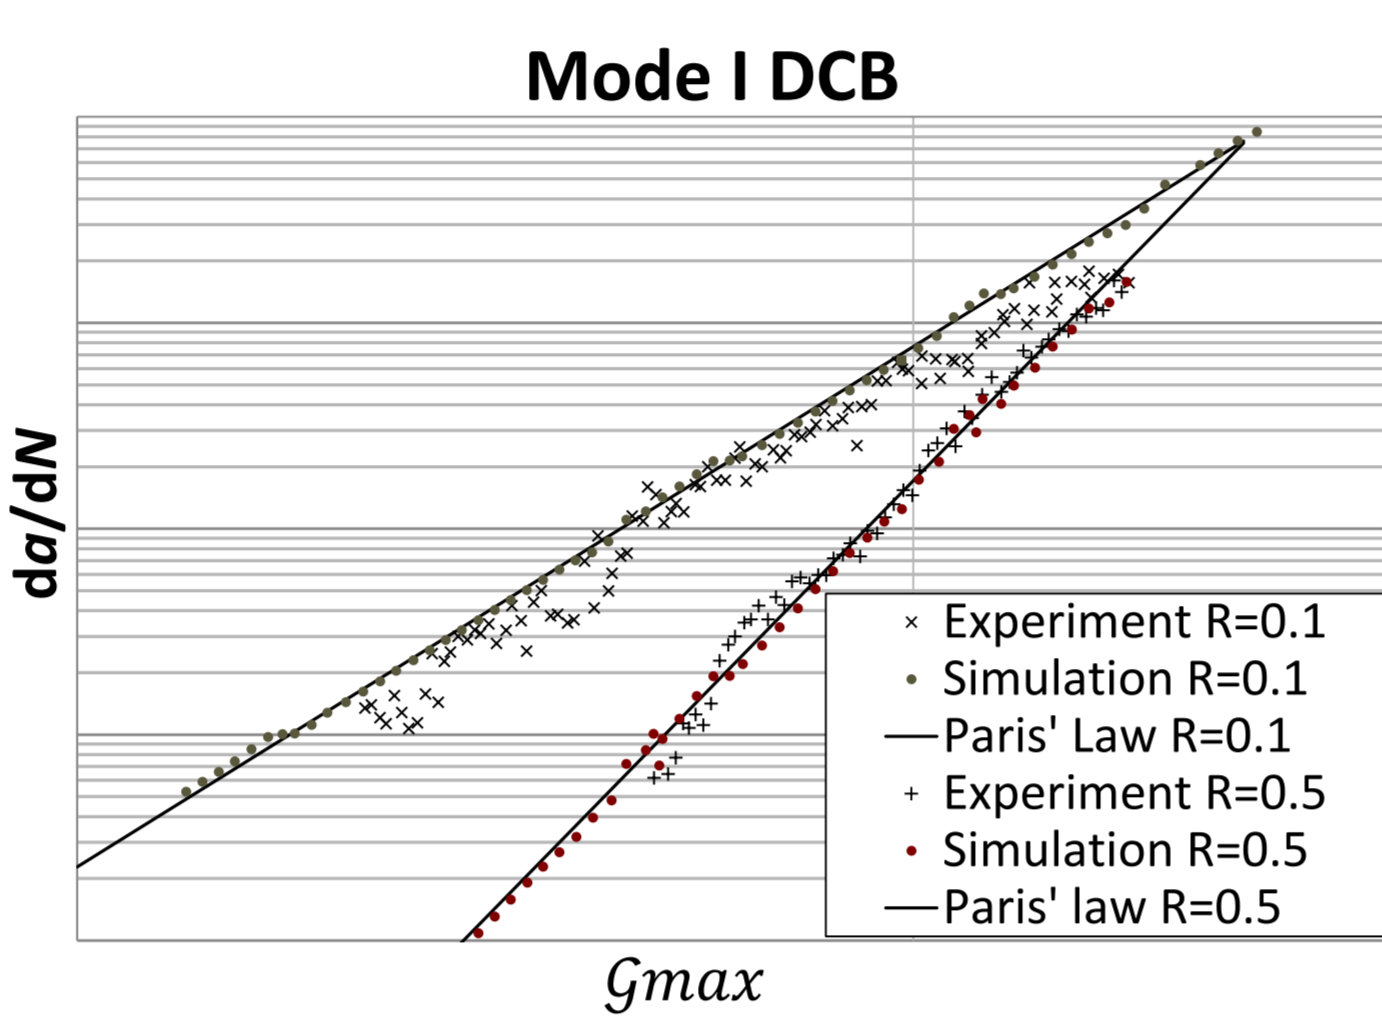

## Extension of the method for 3D application

The  $J$ -integral is used in [1] to determine the mode I and shear components of the energy release rate that feed the Paris' law. The computation of this value requires the proper identification of the crack propagation direction within the cohesive zone which, in a **3D structure**, is not straightforwardly deduced. Moreover, the evaluation of the damage rate also requires the **crack propagation direction** to compute the opening displacement and local mixed-mode ratio slopes along the crack growth coordinate,  $\frac{\partial \lambda}{\partial a}$  and  $\frac{\partial \beta}{\partial a}$  respectively.

These two challenges have been solved with the **pointwise description of the crack front shape** and the **mode-decomposed  $J$ -integral** presented in *Evaluation of the decomposed  $J$ -integral in 3D crack fronts using cohesive elements – PO 43 (COMPTTEST2017)*.

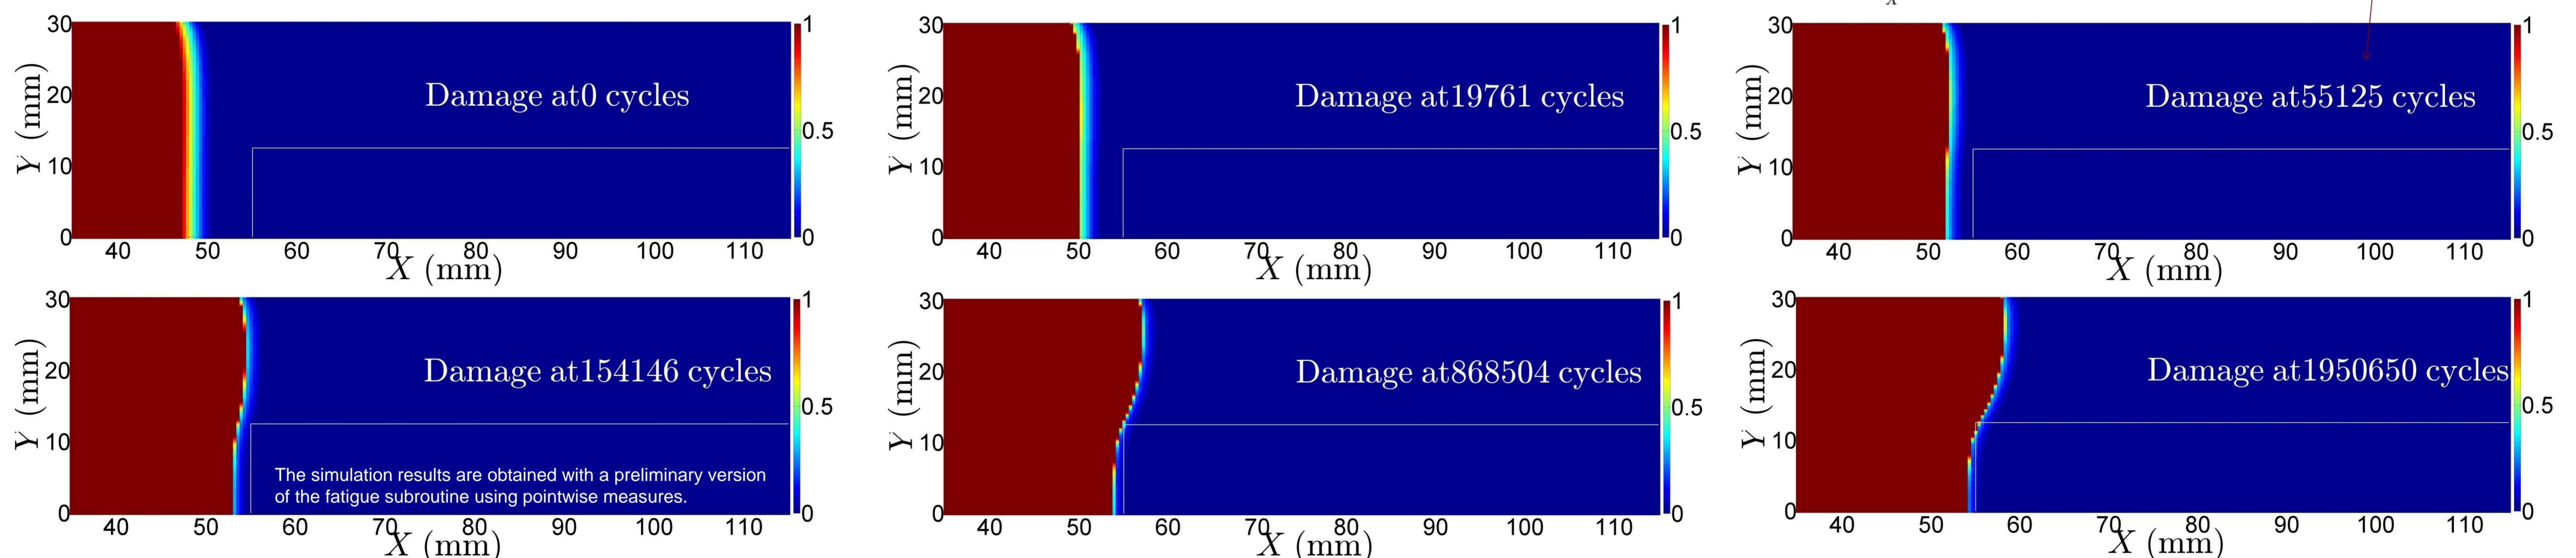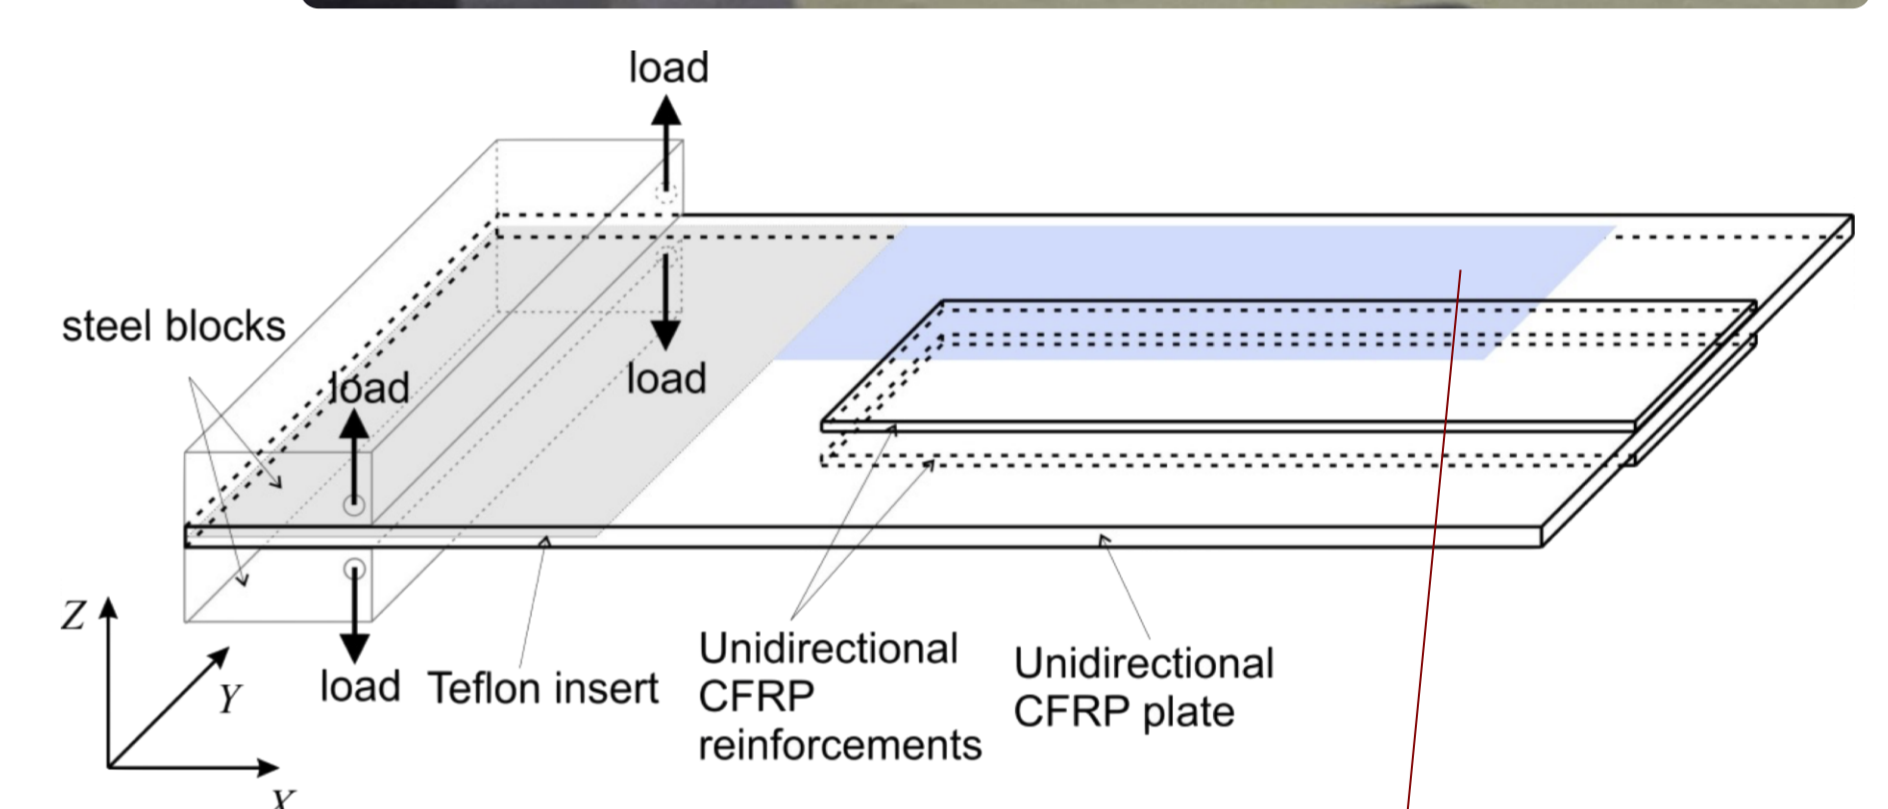

A symmetric run-out specimen with a midplane initial defect has been simulated. The damage state after different number of applied cycles is shown in the Figure. The model inherently captures the change on the crack front shape and on the width of the process zone during fatigue propagation. For the geometry and boundary conditions simulated, crack arrest is predicted when the crack reaches the stiffener.

## Conclusions

A model to simulate fatigue in 3D structures is presented. Two new developments have been introduced: a local crack propagation direction criterion and a 3D expression for the mode decomposed  $J$ -integral. The formulation predicts the crack front shape merely using information available at element level. The method has been implemented in a Finite Element framework. The model predicts crack front shape changes during fatigue growth in 3D structures. The model can be used to predict delamination onset and growth in complex aeronautical components.

## References

[1] Bak BLV, Turon A, Lindgaard E, Lund E, *A Simulation Method for High-Cycle Fatigue-Driven Delamination Using a Cohesive Zone Model*, International Journal for Numerical Methods in Engineering, **106**, 2016, p. 163-191.

## Acknowledgements

This work has been partially funded by the Spanish Government (Ministerio de Economía y competitividad) under contract TRA2015-71491-R and the European Union by the financial support of ERANet AirTN 01/2013 under the project entitled "Methodology to design composite structures resistant to intra- and interlaminar damage (static & fatigue)- MERINDA".