

# Kent Academic Repository

## Full text document (pdf)

### Citation for published version

Williams, George T. and Sedgwick, Adam C. and Sen, S. and Gwynne, Lauren and Gardiner, Jordan E. and Brewster, James T. and Hiscock, Jennifer R. and James, Tony D. and Jenkins, A. Toby A. and Sessler, Jonathan L. (2020) Boronate ester cross-linked PVA hydrogels for the capture and H<sub>2</sub>O<sub>2</sub>-mediated release of active fluorophores. *Chemical Communications*. ISSN 1359-7345.

### DOI

<https://doi.org/10.1039/d0cc01904f>

### Link to record in KAR

<https://kar.kent.ac.uk/80786/>

### Document Version

Author's Accepted Manuscript

#### Copyright & reuse

Content in the Kent Academic Repository is made available for research purposes. Unless otherwise stated all content is protected by copyright and in the absence of an open licence (eg Creative Commons), permissions for further reuse of content should be sought from the publisher, author or other copyright holder.

#### Versions of research

The version in the Kent Academic Repository may differ from the final published version.

Users are advised to check <http://kar.kent.ac.uk> for the status of the paper. **Users should always cite the published version of record.**

#### Enquiries

For any further enquiries regarding the licence status of this document, please contact:

[researchsupport@kent.ac.uk](mailto:researchsupport@kent.ac.uk)

If you believe this document infringes copyright then please contact the KAR admin team with the take-down information provided at <http://kar.kent.ac.uk/contact.html>

## COMMUNICATION

## Boronate ester cross-linked PVA hydrogels for the capture and H<sub>2</sub>O<sub>2</sub>-mediated release of active fluorophores


Received 00th June 2019,  
Accepted 00th Month 20xx

DOI: 10.1039/x0xx00000x

George T. Williams,<sup>a,c†</sup> Adam C. Sedgwick,<sup>b,†</sup> Sajal Sen,<sup>b†</sup> Lauren Gwynne,<sup>a</sup> Jordan E. Gardiner,<sup>a</sup> James T. Brewster II,<sup>b</sup> Jennifer R. Hiscock,<sup>c\*</sup> Tony D. James,<sup>\*,a</sup> A. Toby A. Jenkins,<sup>\*,a</sup> and Jonathan L. Sessler<sup>\*,b</sup>

A new set of PVA hydrogels were formed using the boronate ester fluorescent probe, PF1 and the novel boronate fluorescent probe PT1 as the covalent crosslinkers. Treatment with aqueous H<sub>2</sub>O<sub>2</sub> allowed triggered **release** of the fluorescent dye accompanied by complete dissolution of the hydrogel.

Functional hydrogels have generated widespread interest as so-called intelligent devices wherein a specific stimulus can yield a macroscopic change to the self-supporting material.<sup>1, 2</sup> Such constructs offer promise in the area of drug delivery and design of “smart” wound dressings.<sup>3-6</sup> In addition, these functional hydrogels have demonstrated great potential as fluorescent probes for live cell imaging, disease diagnosis and sensing applications with the controlled release of a fluorophore.<sup>7</sup> These constructs have utilised non-covalent interactions such as aromatic–aromatic, hydrogen bonding, and hydrophobic interactions. Unfortunately, these interactions can result in the unwanted leaching of the active molecule from the hydrogel matrix. Next generation systems comprised of a pro-molecule backbone covalently linked to the hydrogel may address these issues by providing a higher local dose and sustained/controlled release of the bioactive molecule.<sup>8</sup> Here, we demonstrate a new set of controlled release materials wherein hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) is used as a stimulus to release fluorophores from polyvinyl alcohol (PVA) boronate hydrogels.

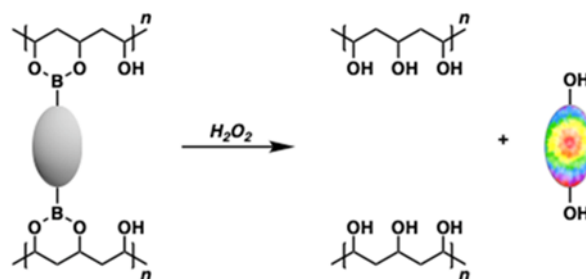

**Scheme 1** - Cartoon representation illustrating the boronate pro-fluorophore encapsulated within a PVA hydrogel being activated by H<sub>2</sub>O<sub>2</sub> to release the active fluorophore.

Boronic acid and boronate esters have found widespread application in material-based applications, in part because of their propensity to bind reversibly with 1,2- and 1,3-diols.<sup>9-19</sup> Such chemistry has been demonstrated *inter alia* using commercially available polyvinyl alcohol (PVA) and diboronic acid crosslinkers to afford functional PVA-boronate hydrogels.<sup>20-25</sup> Boronic acids and boronate esters are well-known to undergo hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>)-mediated oxidative transformations to afford their corresponding phenol functionalities.<sup>26-28</sup> We envisaged that the use of *bis*-boronate-based pro-molecules as cross-linkers would afford a H<sub>2</sub>O<sub>2</sub>-responsive hydrogel platform that would allow the controlled and localised release of an active molecule, such as a fluorophore (Scheme 1). It is important to note the boronate functionality is commonly used to mask active therapeutics.<sup>29, 30</sup> Currently, there is considerable interest in functionalized hydrogels wherein a specific stimulus can yield a macroscopic change to the self-supporting material, including for the stimulus-based release of specific payloads.<sup>31, 32, 33, 34</sup> However, new approaches to achieving such overarching objectives are still needed.

To address the above need, we have now prepared a new class of H<sub>2</sub>O<sub>2</sub>-responsive PVA-boronate hydrogels. These systems rely on covalent cross-linking provide solely by a set of constituent H<sub>2</sub>O<sub>2</sub>-responsive boronate ester fluorescent probes, namely the known fluorophore PF1<sup>26</sup> and the novel fluorescent

<sup>a</sup> Department of Chemistry, University of Bath, Bath, BA2 7AY, UK. Email: t.d.james@bath.ac.uk, a.t.a.jenkins@bath.ac.uk


<sup>b</sup> Department of Chemistry, University of Texas at Austin, 105 E 24th street A5300, Austin, TX 78712-1224, United States. Email: sessler@cm.utexas.edu

<sup>c</sup> School of Physical Sciences, University of Kent, Canterbury, CT2 7NH, U.K. Email: J.R.Hiscock@kent.ac.uk

† These authors contributed equally.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

probe, **PT1** (Figure 1). The resultant hydrogel constructs **Greenment (Gment)** and **Purplement (Pment)** displayed stability over 7 days in both aqueous solution and in the air; however, upon exposure to aqueous  $\text{H}_2\text{O}_2$  the polymers were oxidised thus releasing their constituent fluorophores, fluorescein<sup>26</sup> and thionol<sup>35</sup> (Schemes S1 and S2). Complete dissolution of the hydrogel could be effected depending on the specific choice of conditions as detailed below.

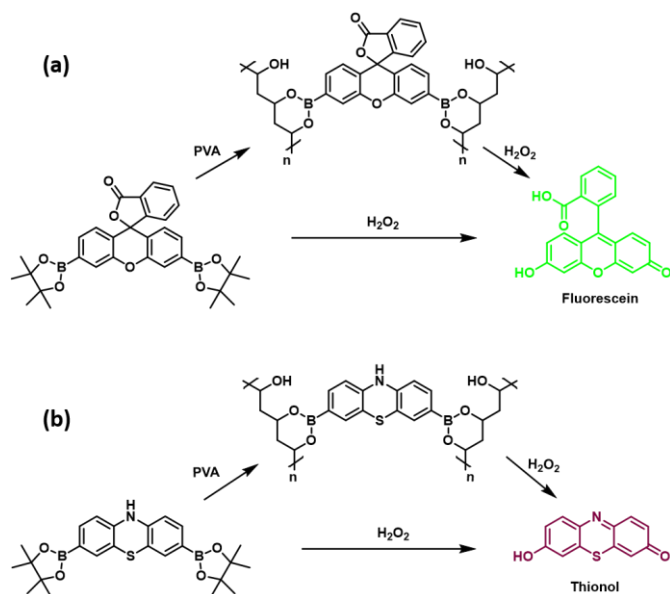

**Figure 1** - (a)  $\text{H}_2\text{O}_2$ -responsive fluorescent probe **PF1** and its corresponding  $\text{H}_2\text{O}_2$ -responsive PVA hydrogel **Gment**. (b)  $\text{H}_2\text{O}_2$ -responsive fluorescent probe **PT1** and its corresponding  $\text{H}_2\text{O}_2$ -responsive PVA hydrogel **Pment**.


**PF1** was prepared following literature procedures.<sup>26</sup> The novel fluorescent probe **PT1** was synthesized through the dibromination of commercially available phenothiazine (**1**) using  $\text{Br}_2$  (5 equiv.) in acetic acid at room temperature, giving the desired product in 74% yield. Subsequent Suzuki-Miyaura borylation using potassium acetate, bis(pinacolato)diboron, and  $\text{Pd}(\text{dppf})\text{Cl}_2$  afforded **PT1** in 43% yield.

With **PF1** and **PT1** in hand, UV and fluorescence analyses were performed. Upon exposure to aqueous  $\text{H}_2\text{O}_2$  at concentrations as low as 125  $\mu\text{M}$ , **PF1** exhibited a colour change from clear to green with an increase in absorption at 490 nm and an increase in fluorescence emission at 520 nm, which corresponded to the release of fluorescein (Fig. S1 and S2). Whereas, exposure of **PT1** to  $\text{H}_2\text{O}_2$  in an analogous manner led to a colour change from clear to purple and a concomitant increase in the absorption intensity at 595 nm and an increase in fluorescence emission at 610 nm. These optical changes reflected the release of free thionol as confirmed by high resolution mass spectrometry, Fig. S3-S5. It is important to note that in this work, we have focused on the use of these boronate-based hydrogels as materials whose controlled release may be triggered by  $\text{H}_2\text{O}_2$ . However, previous reports have demonstrated the greater reactivity of boronate-based fluorescent probes towards peroxynitrite ( $\text{ONOO}^-$ ).<sup>16, 36-39</sup> Therefore, it is likely that if used in cellular applications, both **PF1** and **PT1** could have a role to play in the

fluorescence imaging of both  $\text{ONOO}^-$  and  $\text{H}_2\text{O}_2$ , albeit not necessarily in a species specific manner.

Next, the **Gment** and **Pment** PVA-hydrogels were prepared by mixing a solution of either **PF1** or **PT1** (100 mM) in dimethylsulfoxide (DMSO) with a DMSO solution of 10% PVA (low molecular weight; purchased commercially) in a 1:1 ratio. This solution was then heated to induce gelation, followed by heating at 60  $^\circ\text{C}$  overnight in an oven. The resultant gels were washed with hexanes to remove the displaced pinacol and water to remove excess DMSO. These self-supporting gels proved physically robust and stable in air and could be stored in aqueous media (PBS, pH 7.4) without degradation for 7 days until used (Fig. S6-S8).


The ability of **Gment** or **Pment**-based PVA-hydrogel to release the corresponding dye in the presence of  $\text{H}_2\text{O}_2$  was then evaluated. This was done by submerging the chosen hydrogel ( $200 \pm 10$  mg) in aqueous solutions containing different concentrations of  $\text{H}_2\text{O}_2$ . As shown in Figure 2, exposure of **Gment** gels to  $\text{H}_2\text{O}_2$  (0 – 1 mM) led to a dose-dependent increase in the fluorescence emission intensity. The colorimetric nature of **Gment** was then tested by placing the hydrogel ( $200 \pm 10$  mg samples) in an aqueous solution of  $\text{H}_2\text{O}_2$  (1 mL, 1 mM). A clear change in colour was observed from colourless to green. Analysis of the UV-Vis absorption revealed an increase in two absorption peaks at 450 nm and 490 nm (Fig. S9). The absorption peak at  $\sim 450$  nm is tentatively assigned to the release of monoboronate **PF3**<sup>40</sup> and the absorption peak at 490 nm corresponds to the release of fluorescein. From this result, we believe the oxidation of only one boronate linkage is required to release the molecule from the PVA-hydrogel system (Scheme S3).

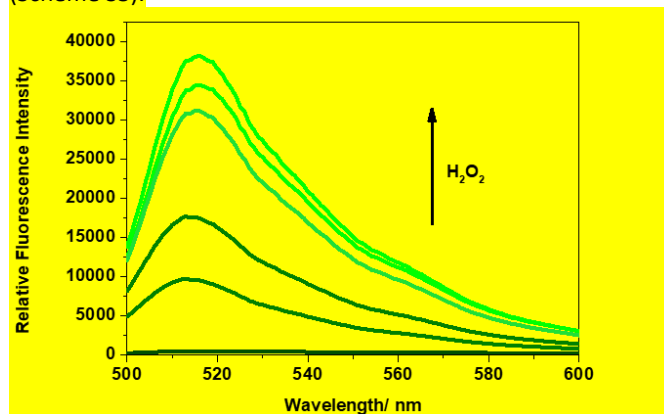

**Figure 2** – Fluorescence spectra of the supernatant of **Gment**-based PVA-hydrogels exposed to various concentrations of  $\text{H}_2\text{O}_2$  (0 – 1 mM) in PBS, pH 7.4. Measurements were taken after 5 min at 25  $^\circ\text{C}$ .  $\lambda_{\text{exc}} = 472$  (bandwidth: 16 nm) on a BMG Labtech CLARIOstar<sup>®</sup> plate reader.


As shown in Figure 3, **Pment** PVA-hydrogels exposed to various concentrations of  $\text{H}_2\text{O}_2$  (0 – 1 mM) also led to a dose-dependent increase in the fluorescence intensity at the emission maximum of 610 nm. The colorimetric nature of **Pment** was then tested by placing the hydrogel ( $200 \pm 10$  mg samples) in an aqueous solution of  $\text{H}_2\text{O}_2$  (1 mL, 1 mM). A readily discernible change in colour was observed from colourless to purple with an increase in the absorption intensity at 595 nm (See ESI - Figs. S9 - S11). In

comparison to one another, **Gment** was found to be more sensitive to  $\text{H}_2\text{O}_2$  than **Pment** (Figs. S12 and S13). This finding is reflected in **Gment** having a lower Limit of Detection ((LoD) - **Gment** = 0.12 mM, LoD **Pment** = 0.33 mM). However, it is important to note, these calculated LoD values are dependent upon incubation times.

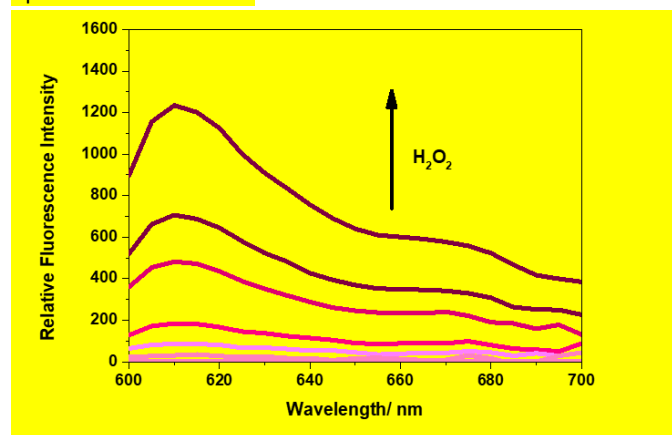

**Figure 3** – Fluorescence spectra of the supernatant of **Pment**-based PVA-hydrogels exposed to various concentrations of  $\text{H}_2\text{O}_2$  (0 – 1 mM) in PBS, pH 7.4. Measurements were taken after 5 min at 25 °C.  $\lambda_{\text{ex}} = 570$  (bandwidth: 16 nm) on a BMG Labtech CLARIOstar® plate reader.

Notably, subjecting the hydrogels to an aqueous solution of  $\text{H}_2\text{O}_2$  (100 mM) resulted in the complete dissolution of the hydrogels into solution, as shown in Figure 4. Of note is that commercially available 3%  $\text{H}_2\text{O}_2$  sold for consumer use is approximately 980 mM. The present work thus demonstrates the potential utility of boronate-based PVA polymers as a smart material for the masking and facile release of easy-to-visualise fluorophores using a readily accessible trigger. Lastly, an MTT assay with A549 cells was carried out using the **Gment** gel. At concentrations up to 50  $\mu\text{g}/\text{mL}$ , A549 cells displayed at least 80% viability, thus demonstrating minimal acute cytotoxicity in this well-studied cell line (Fig. S14). We believe these findings provide further support for the suggestion that the present approach may have a role to play in the controlled delivery of fluorescence-based diagnostics and active pharmacophores.<sup>29</sup>

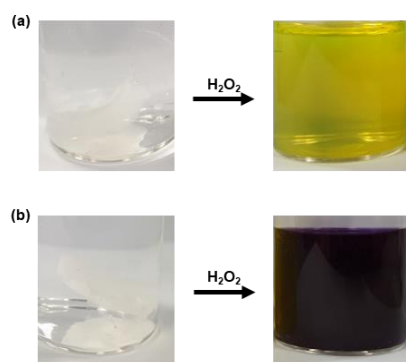

**Figure 4** – (a) **Gment** and (b) **Pment** PVA-hydrogels before and after 1.5 h exposure to 100 mM  $\text{H}_2\text{O}_2$  in PBS, pH 7.4.

In conclusion, we report here the synthesis of a new  $\text{H}_2\text{O}_2$ -responsive *bis*-boronate fluorescent probe, **PT1**, and the

synthesis of the previously reported  $\text{H}_2\text{O}_2$ -responsive fluorescent probe **PF1**. Both **PT1** and **PF1** were successfully used as diboronic acid crosslinkers to form air and aqueous stable PVA-based hydrogels. Exposure of these initially colourless and non-fluorescent systems to aqueous solutions of  $\text{H}_2\text{O}_2$  allowed for the controlled release and activation of the encapsulated fluorophore. We believe these systems represent a masking and delivery strategy that has the potential for the controlled and localised release of boronic acid-based sensors and pro-drugs.<sup>29</sup>

## Acknowledgments

The authors would like to thank the EPSRC for grant EP/R003556/1. GTW would like to thank the EPSRC and Public Health England. GTW and JRH would like to thank the global challenges doctoral centre at the University of Kent for funding. ACS and ATAJ wish to thank the EPSRC for funding on smart-wound plasma – EP/R003939/1. This work was supported in part by grant MR/N0137941/1 for the GW4 BIOMED DTP, awarded to the Universities of Bath, Bristol, Cardiff and Exeter from the Medical Research Council (MRC)/UKRI. TDJ wishes to thank the Royal Society for a Wolfson Research Merit Award. The work in Austin was supported by the National Institutes of Health (R01 GM103790 to J.L.S.) and the Robert A. Welch Foundation (F-0018). ACS would also like to acknowledge use of a Bruker AVIII HD 500 with Prodigy liquid nitrogen cryoprobe supported by NIH grant 1 S10 OD021508. All data supporting this study are provided as supplementary information accompanying this paper (ESI†).

## Conflicts of interest

There are no conflicts to declare.

## Notes and references

- N. N. Ferreira, L. M. B. Ferreira, V. M. O. Cardoso, F. I. Boni, A. L. R. Souza and M. P. D. Gremiao, *Eur. Polym. J.*, 2018, **99**, 117-133.
- K. Wang, Y. T. Hao, Y. N. Wang, J. Y. Chen, L. Z. Mao, Y. D. Deng, J. L. Chen, S. J. Yuan, T. T. Zhang, J. Y. Ren and W. Z. Liao, *Int. J. Polym. Sci.*, 2019. DOI: 10.1155/2019/3160732
- M. M. S. Ebrahimi, M. Laabei, A. T. A. Jenkins and H. Schonherr, *Macromol. Rapid Commun.*, 2015, **36**, 2123-2128.
- N. T. Thet, D. R. Alves, J. E. Bean, S. Booth, J. Nzakizwanayo, A. E. R. Young, B. V. Jones and A. T. A. Jenkins, *ACS Appl. Mater. Interfaces*, 2016, **8**, 14909-14919.
- D. Huber, G. Tegl, A. Mensah, B. Beer, M. Baumann, N. Borth, C. Sygmund, R. Ludwig and G. M. Guebitz, *ACS Appl. Mater. Interfaces*, 2017, **9**, 15307-15316.
- H. Liu, C. Y. Wang, C. Li, Y. G. Qin, Z. H. Wang, F. Yang, Z. H. Li and J. C. Wang, *RSC Adv.*, 2018, **8**, 7533-7549.
- N. Mehewish, X. Q. Dou, Y. Zhao and C. L. Feng, *Mater. Horiz.*, 2019, **6**, 14-44.
- S. Akkad and C. J. Serpell, *Macromol. Rapid Commun.*, 2018, **39**.

9. H. Matsumura, N. Ahmatjan, Y. Ida, R. Imai and K. Wanatabe, *Int. Wound J.*, 2013, **10**, 291-294.
10. A. Matsumoto and Y. Miyahara, *Sci. Technol. Adv. Mater.*, 2017, **19**, 18-30.
11. A. Matsumoto, K. Kataoka and Y. Miyahara, *Polym. J.*, 2014, **46**, 483-491.
12. M. Sanjoh, Y. Miyahara, K. Kataoka and A. Matsumoto, *Anal. Sci.*, 2014, **30**, 111-117.
13. A. Matsumoto, M. Tanaka, H. Matsumoto, K. Ochi, Y. Morooka, H. Kuwata, H. Yamada, I. Shirakawa, T. Miyazawa, H. Ishii, K. Kataoka, Y. Ogawa, Y. Miyahara and T. Suganami, *Sci. Adv.*, 2017, **3**. DOI:10.1126/sciadv.aag0723
14. A. Matsumoto, K. Yamamoto, R. Yoshida, K. Kataoka, T. Aoyagi and Y. Miyahara, *Chem. Commun.*, 2010, **46**, 2203-2205.
15. W. L. A. Brooks and B. S. Sumerlin, *Chem. Rev.*, 2016, **116**, 1375-1397.
16. M. L. Odyneic, A. C. Sedgwick, A. H. Swan, M. Weber, T. M. S. Tang, J. E. Gardiner, M. Zhang, Y. B. Jiang, G. Kociok-Kohn, R. B. P. Elmes, S. D. Bull, X. P. He and T. D. James, *Chem. Commun.*, 2018, **54**, 8466-8469.
17. E. V. Lampard, A. C. Sedgwick, T. Sombuttan, G. T. Williams, B. Wannalorse, A. T. A. Jenkins, S. D. Bull and T. D. James, *Chemistryopen*, 2018, **7**, 266-268.
18. X. L. Sun, M. L. Odyneic, A. C. Sedgwick, K. Lacina, S. Y. Xu, T. T. Qiang, S. D. Bull, F. Marken and T. D. James, *Org. Chem. Front.*, 2017, **4**, 1058-1062.
19. B. L. Patenall, G. T. Williams, L. Gwynne, L. J. Stephens, E. V. Lampard, H. J. Hathaway, N. T. Thet, A. E. Young, M. J. Sutton, R. D. Short, S. D. Bull, T. D. James, A. C. Sedgwick and A. T. A. Jenkins, *Chem. Commun.*, 2019, **55**, 15129-15132.
20. G. M. Peters, X. D. Chi, C. Brockman and J. L. Sessler, *Chem. Commun.*, 2018, **54**, 5407-5409.
21. R. Nishiyabu, S. Ushikubo, Y. Kamiya and Y. Kubo, *J. Mater. Chem. A*, 2014, **2**, 15846-15852.
22. R. Nishiyabu, Y. Takahashi, T. Yabuki, S. Gommori, Y. Yamamoto, H. Kitagishi and Y. Kubo, *RSC Adv.*, 2020, **10**, 86-94.
23. R. Nishiyabu, H. Kobayashi and Y. Kubo, *RSC Adv.*, 2012, **2**, 6555-6561.
24. Y. Guan and Y. J. Zhang, *Chem. Soc. Rev.*, 2013, **42**, 8106-8121.
25. R. W. Guo, Q. Su, J. W. Zhang, A. J. Dong, C. G. Lin and J. H. Zhang, *Biomacromolecules*, 2017, **18**, 1356-1364.
26. E. W. Miller, A. E. Albers, A. Pralle, E. Y. Isacoff and C. J. Chang, *J. Am. Chem. Soc.*, 2005, **127**, 16652-16659.
27. H. Zhu, J. L. Fan, S. L. Zhang, J. F. Cao, K. D. Song, D. Ge, H. J. Dong, J. Y. Wang and X. J. Peng, *Biomater. Sci.*, 2014, **2**, 89-97.
28. J. Chan, S. C. Dodani and C. J. Chang, *Nat. Chem.*, 2012, **4**, 973-984.
29. E. J. Kim, S. Bhuniya, H. Lee, H. M. Kim, C. Cheong, S. Maiti, K. S. Hong and J. S. Kim, *J. Am. Chem. Soc.*, 2014, **136**, 13888-13894.
30. M. L. Odyneic, H. H. Han, J. E. Garidner, A. C. Sedgwick, X. P. He, S. D. Bull and T. D. James, *Frontiers in Chemistry*, 2019, **7**. DOI: 10.3389/fchem.2019.00775
31. Y. Qiu and K. Park, *Adv. Drug Deliv. Rev.*, 2001, **53**, 321-339.
32. Y. Lee, K. H. Choi, K. M. Park, J. M. Lee, B. J. Park and K. D. Park, *ACS Appl. Mater. Interfaces*, 2017, **9**, 16891-16900.
33. C. H. Ren, L. P. Chu, F. Huang, L. J. Yang, H. R. Fan, J. F. Liu and C. H. Yang, *RSC Adv.*, 2017, **7**, 1313-1317.
34. F. Liu, L. B. Bai, H. L. Zhang, H. Z. Song, L. D. Hu, Y. G. Wu and X. W. Ba, *ACS Appl. Mater. Interfaces*, 2017, **9**, 31626-31633.
35. S. Granick and L. Michaelis, *J. Am. Chem. Soc.*, 1947, **69**, 2983-2986.
36. A. Sikora, J. Zielonka, M. Lopez, J. Joseph and B. Kalyanaraman, *Free Radical Biol. Med.*, 2009, **47**, 1401-1407.
37. A. C. Sedgwick, W. T. Dou, J. B. Jiao, L. L. Wu, G. T. Williams, A. T. A. Jenkins, S. D. Bull, J. L. Sessler, X. P. He and T. D. James, *J. Am. Chem. Soc.*, 2018, **140**, 14267-14271.
38. A. C. Sedgwick, H. H. Han, J. E. Gardiner, S. D. Bull, X. P. He and T. D. James, *Chem. Commun.*, 2017, **53**, 12822-12825.
39. H. H. Han, A. C. Sedgwick, Y. Shang, N. Li, T. T. Liu, B. H. Li, K. Q. Yu, Y. Zang, J. T. Brewster, M. L. Odyneic, M. Weber, S. D. Bull, J. Li, J. L. Sessler, T. D. James, X. P. He and H. Tian, *Chem. Sci.*, 2020, **11**, 1107-1113.
40. B. C. Dickinson, C. Huynh and C. J. Chang, *J. Am. Chem. Soc.*, 2010, **132**, 5906-5915.