

# Kent Academic Repository

## Full text document (pdf)

### Citation for published version

Taallah, Ayoub and Xia, JiaChen and Guo, Jian and Shuai, Gao and Odunmbaku, Omololu and Gong, Min and Shang, Hongyan and Corrias, Anna and Boi, Filippo (2020) Magnetic vortex and unsaturated magnetization components in highly oriented pyrolytic graphite. *Materials Research Express* . ISSN 2053-1591.

### DOI

<https://doi.org/10.1088/2053-1591%2Fab8d61>

### Link to record in KAR

<https://kar.kent.ac.uk/81031/>

### Document Version

Author's Accepted Manuscript

#### Copyright & reuse

Content in the Kent Academic Repository is made available for research purposes. Unless otherwise stated all content is protected by copyright and in the absence of an open licence (eg Creative Commons), permissions for further reuse of content should be sought from the publisher, author or other copyright holder.

#### Versions of research

The version in the Kent Academic Repository may differ from the final published version.

Users are advised to check <http://kar.kent.ac.uk> for the status of the paper. **Users should always cite the published version of record.**

#### Enquiries

For any further enquiries regarding the licence status of this document, please contact:

[researchsupport@kent.ac.uk](mailto:researchsupport@kent.ac.uk)

If you believe this document infringes copyright then please contact the KAR admin team with the take-down information provided at <http://kar.kent.ac.uk/contact.html>

ACCEPTED MANUSCRIPT • OPEN ACCESS

## Magnetic vortex and unsaturated magnetization components in highly oriented pyrolytic graphite

To cite this article before publication: Ayoub Taallah *et al* 2020 *Mater. Res. Express* in press <https://doi.org/10.1088/2053-1591/ab8d61>

### Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2020 The Author(s). Published by IOP Publishing Ltd.

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

Everyone is permitted to use all or part of the original content in this article, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions may be required. All third party content is fully copyright protected and is not published on a gold open access basis under a CC BY licence, unless that is specifically stated in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

# Magnetic vortex and unsaturated magnetization components in highly oriented pyrolytic graphite

Ayoub Taallah<sup>a,b</sup>, JiaChen Xia<sup>a,b</sup>, Jian Guo<sup>c</sup>, Gao Shuai<sup>a,b</sup>, Omololu Odunmbaku<sup>a,b</sup>, Min Gong<sup>a,b</sup>, Hongyan Shang<sup>d</sup>, Anna Corrias<sup>e</sup> and Filippo S. Boi<sup>a,b\*</sup>.

a. College of Physics, Sichuan University, Chengdu, China 610064.

b. Sino-British Joint Materials Research Institute, Sichuan University, Chengdu, China 610064.

c. Department of Chemistry, University College London, London, UK WC1E 6BT.

d. College of Chemistry and Materials Science, Sichuan Normal University, Chengdu, China 610066.

e. School of Physical Sciences, University of Kent, Canterbury, UK CT2 7NZ.

email corresponding author: f.boi@scu.edu.cn

## Abstract

Observation of ferromagnetic and granular superconductive features in highly-oriented-pyrolytic-graphite (HOPG) has recently attracted an important attention. We report a novel temperature dependent XRD and SQUID investigation of HOPG in the temperature range from 300.15 to 77.15 K. Unusual hysteresis features indicate the possible presence of vortex states in conditions of magnetic field approximately perpendicular to the HOPG layers. This interpretation is further supported by additional measurements performed on intermediate lamellae extracted by exfoliation. Evidence of a possible structural-transition in the c-axis of HOPG in the temperature range between 77 K and 100K is also provided by using the Rietveld refinement method.

ZFC and FC measurements performed at high field values of 5000-10000 Oe, together with mFC-mZFC subtraction, highlight absence of a sharp depletion of the difference between magnetization signals towards zero. These observations may indicate the possible presence of additional unsaturated weak features, which are ascribed to superconductive signals as previously predicted by Scheike et al. [8].

## 1 Introduction

Understanding the origin of magnetic ordering in pure carbon-based graphitic materials has recently become a crucial focus of research towards translation of these systems into technological applications. Graphite is a layered material with hexagonal symmetry (space group  $P6_3/mmc$ ) characterized by delocalized  $\pi$ -electrons along the graphene layers and Van der Waals forces in between (layers) [1-15]. The stacking between graphene layers and the layer orientation have been shown to play a crucial role towards modifications of band gap and energy dispersion relation characteristics of these materials. In particular, formation of unusual superconductive features in bilayer graphene and highly oriented pyrolytic graphite (HOPG) has been recently reported for specific rotational angle, known as magic angle of rotation [1-15,23,25]. Presence of sequential stacking consisting of Bernal and rhombohedral phases has been also acknowledged as one of the possible factors governing such high temperature superconductive effects [4]. Interestingly, superconductive ordering in HOPG systems was already reported in early 2000 by Kopelevich et al. for certain conditions of annealing [1]. It was shown that formation of superconductive hysteresis could be triggered by high temperature annealing of as grown ferromagnetic HOPG samples [1]. These observations were further supported by the recent works of Scheike T. et al. and Esquinazi et al. [7,8] where existence of room temperature superconductive phenomena was reported in conditions of magnetic field perpendicular to HOPG layers and explained on the basis of the Burgers–Bragg–Read–Shockley (BBRS) dislocation model [5,6]. Existence of possible relationships between second order

1  
2  
3  
4 antiferromagnetic transitions and critical superconductive temperature in such magic  
5  
6 angle Mott insulated superconductive systems has been also recently proposed [12a,  
7  
8 12b, 24]. In typical Mott insulator, the ground state is generally characterized by  
9  
10 antiferromagnetic spin ordering below the Néel temperature [24, 12a, 12b]. In view of  
11  
12 this important theory recently proposed in magic angle superconductivity,  
13  
14 understanding the link between antiferromagnetic correlations and superconducting  
15  
16 ordering is of crucial importance. The presence of temperature induced  
17  
18 antiferromagnetic transitions has been recently reported also in electron paramagnetic  
19  
20 resonance (EPR) studies of nanostructured graphite and multiwalled carbon nanotubes  
21  
22 [17-19]. Possible correlation effects compatible with antiferromagnetic/ferromagnetic  
23  
24 ordering were also shown through EPR studies in pristine HOPG [21]. Possible links  
25  
26 between this magnetic transition and structural rearrangements of the graphitic c-axis  
27  
28 in this type of Bernal systems (with A-B-A stacking) with the decrease of the  
29  
30 temperature remain still unclear.  
31  
32  
33  
34  
35  
36  
37  
38

39  
40 Interestingly, presence of transitions in the c-axis of the graphitic unit-cell has been  
41  
42 reported in multiwalled carbon nanotubes in the range from 300K to 12 K (below room  
43  
44 temperature) [20]. Furthermore, c-axis shifts have been reported in nanostructured  
45  
46 graphite, carbon nanotubes, carbon onions and HOPG at higher temperatures, from 298  
47  
48 K to 673 K [20, 23,25]. However, further studies are needed in order to understand the  
49  
50 possible relationship between such structural transitions and the magnetic correlation  
51  
52 effects recently predicted for these systems at the magic angle. In contrast with those  
53  
54 predictions [12a, 12b], it is also important to mention a recent theory which suggests  
55  
56  
57  
58  
59  
60

1  
2  
3  
4 the absence of Mott insulation characteristics and proximity to Wigner Crystallization  
5  
6 in conditions close to first magic angle of rotation [16]. In addition, anomalous  
7  
8 transitions have been predicted in graphite for large applied magnetic fields [26-29].  
9

10  
11 In this work we report a novel temperature dependent XRD and SQUID investigation  
12  
13 of HOPG from 300.15 down to 77.15 K.  
14  
15

16  
17 Magnetization vs Field measurements revealed the presence of unusual vortex-like  
18  
19 magnetic hysteresis with characteristic sharp magnetization features at 250 K.  
20  
21

22 Interpretation of this unusual type of signal was further supported by magnetization  
23  
24 analysis performed on lamellae exfoliated from internal regions of the sample which  
25  
26 revealed anomalous pinning features possibly attributable to onion and vortex states of  
27  
28 the magnetization [35]. Additionally, zero field cooled (ZFC)-field cooled (FC)  
29  
30 measurements appeared to suggest the possible absence of complete magnetic-moment-  
31  
32 saturation in conditions of high applied magnetic field values of 5000 Oe and 10000  
33  
34 Oe. These observations were further corroborated by calculations performed using the  
35  
36 mFC-mZFC subtraction methods reported in previous works [7,8]. Possible presence  
37  
38 of additional magnetic components (i.e. weak superconductive regions/interfaces) at  
39  
40 the origin of such unsaturated magnetization signal can not be excluded on the basis of  
41  
42 recent experimental reports [7,8].  
43  
44  
45  
46  
47  
48  
49

50 Evidence of a structural-transition in the c-axis of HOPG at temperatures between 100  
51  
52 to 77K is also demonstrated by means of Rietveld refinement. This transition was  
53  
54 further investigated on turbostratic graphite and carbon nanotubes samples for  
55  
56 comparison.  
57  
58  
59  
60

## 2 Experimental

HOPG samples with dimensions of 5 x 5 x 1 mm and mosaic angle of  $0.5^\circ, \pm 0.2^\circ$  and  $0.8^\circ, \pm 0.2^\circ$  were purchased from XFNANO, INC China. Commercial graphite powder was purchased from Xiya Reagents China Cas number 7782-42-5.  $\text{Fe}_5\text{C}_2/\text{Fe}_7\text{C}_3$  filled CNTs were produced by pyrolysis of sulfur/ferrocene mixtures following the method reported in reference [19].

Temperature dependent XRD measurements were performed on a Rigaku Smart-lab powder X-ray diffractometer (Cu K- $\alpha$ ,  $\lambda = 0.15418$  nm) with Bragg- Brentano configuration under vacuum values below 7 Pa in the temperature range from 300.15 down to 77.15 K, with an Anton Paar TTK450 chamber. The HOPG samples were positioned with the c-axis perpendicular to the substrate holder. Additional measurements were performed on thin walled CNT samples on a PANalytical Empyrean powder X-ray diffractometer (Cu K- $\alpha_1$ ,  $\lambda = 0.15406$  nm), equipped with a primary Johansson monochromator, an Oxford Cryosystems PheniX cryostat operating under vacuum below 10-2 Pa, and a X'celerator linear detector, in the temperature range from 12 to 300K. TEM measurements were performed with a 200 kV American FEI Tecnai G2F20. Fourier transform analyses and Moiré pattern analyses were performed with the Digital Micrograph software (see ESI Fig.Supp.1-3). SQUID measurements were performed at maximum fields values of 5000 Oe and 10000 Oe in pristine as purchased samples, with a Quantum Design system.

### 3 Results and Discussion

The layered structure of the HOPG sample was firstly revealed by XRD measurements, as indicated in Fig.1, with the observation of preferred 002 and 004 reflections. Note that no peak features compatible with rhombohedral graphite were detected. By analyzing the temperature dependent XRD diffractograms in Fig.1, it is possible to notice that a significant temperature dependent shift in the position of the 002 and 004 diffraction peaks towards larger values of  $2\theta$  is present as the temperature decreases.

This significant transition can be observed in more detail in Fig.2, where the 002 (Fig.2A) and 004 (Fig.2B) peak-shifts are shown as a function of the temperature. The Rietveld refinement method (see ESI) was used for extracting the corresponding c-axis values for each of the analyzed temperature point. As shown in Fig.2C a significant decrease in the c-axis value with the decrease of the temperature was found. By examining the plot in Fig.2C the presence of a non-linear trend could be observed. On the basis of the calculated c-axis values with tabulated thermal expansion parameters, a shift of -0.0040 nm would be expected [22]. Instead by extracting the c-axis shift in the temperature range from 300 to 77K with Rietveld refinement (see ESI for detailed analyses), our results show a much weaker value of c-axis shift, namely -0.0008 nm (see Fig.2C).

The right part of the plot shown in Fig.2C, could be ascribed to the possible presence of phonon-related thermal contributions (Grüneisen law for a periodic system). Note, this trend significantly deviates from the linear one shown in ref.25 at high temperature for HOPG samples containing rotational characteristics with comparable  $\theta_{\text{misfit}}$  values.



1  
2  
3  
4 Focusing then on the region of the plot comprised from 100K to 77K (Fig.2C), is then  
5  
6 possible to notice a clear change in the step of the c-axis shift and a saturation-like effect  
7  
8 which implies the presence of a transition in the value of thermal expansion parameter  
9  
10 along the c-axis of HOPG. This is shown in Fig.2D where the thermal expansion  $\alpha$ -  
11  
12 parameter is plotted as a function of the temperature. This observation strongly diverges  
13  
14 from the expected linear trend predicted by the tabulated thermal expansion parameter  
15  
16 of nanostructured graphite [22]. Note also that no such saturation effect could be  
17  
18 detected in the values of c-axis extracted in comparable temperature range from other  
19  
20 turbostratic graphite-based samples which are shown in Figs.3 and 4 respectively (see  
21  
22 also ESI for details of Rietveld refinement analyses), namely commercial turbostratic  
23  
24 graphite (see Figs.3-4A) and thin walled carbon nanotubes (see Figs.3-4B). Additional  
25  
26 structural information was then extracted by employing high resolution transmission  
27  
28 electron microscopy (HRTEM). These analyses were performed with the electron beam  
29  
30 parallel to the c-axis of the exfoliated lamellae. Interestingly, existence of Moiré  
31  
32 periodicities was found, as shown in Fig.Supp1-3. By using the equation  $a/2D=\sin(\theta/2)$   
33  
34 where  $a$  is the basal lattice constant (0.25239 nm) of HOPG and  $\theta$  is the misfit angle, a  
35  
36 misfit angle  $\theta_{\text{misfit}}$  of  $\sim 1.5^\circ$  between the graphitic layers was extracted.  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

48 Additional insight was obtained by SQUID magnetometry. As shown in Fig.5, presence  
49  
50 of an unusual hysteresis was found in the magnetization vs field measurements  
51  
52 performed at 250K in conditions of magnetic field approximately perpendicular to the  
53  
54 graphitic layers (see Fig.5A before subtraction and B-C after diamagnetic subtraction  
55  
56 using slightly different  $\chi$ -values; note that due to the sample dimensions, the sample  
57  
58  
59  
60

1  
2  
3  
4 could be accommodated only with a tilted-like orientation within the measurement-  
5  
6 capsule). Presence of unusual sharp magnetization pinning components in this system  
7  
8 could be further detected. Particularly, note the presence of feature 1 and 2 in Fig.5B.  
9  
10 which may imply the possible presence of vortex-like states in the analyzed sample.  
11  
12 The variation of the shape of the magnetization signal after subtraction of a gradually  
13  
14 increasing diamagnetic background is shown in Fig.5B,C. This subtraction evidences  
15  
16 the presence of multiple components in the magnetization signal and therefore of  
17  
18 complexities in the magnetic properties of the analyzed sample.  
19  
20  
21  
22  
23

24 In the attempt to investigate the origin of these signals additional measurements were  
25  
26 performed in lamellae extracted from internal intermediate regions (between surface  
27  
28 and central regions) of the bulk HOPG sample. Note that analyses of lamellae exfoliated  
29  
30 between surface and central regions of the main HOPG sample were not considered in  
31  
32 order to avoid effects from surface-contamination or impurities. Indeed, a previous  
33  
34 work has shown presence of contamination on surface layers of commercially available  
35  
36 HOPG [37].  
37  
38  
39  
40  
41

42 As shown in Fig.6, these investigations revealed the presence of anomalous unsaturated  
43  
44 hysteresis signals with characteristic pinning features which could be ascribed to  
45  
46 presence of onion and vortex magnetization states (see Fig.6A-D before diamagnetic  
47  
48 subtraction and Fig.6E-F after subtraction) [35]. Particularly, the dynamics of vortex  
49  
50 state formation could be described departing from an initial onion state (I) in analogy  
51  
52 with the study reported in ref.35. Namely, onion state (phase I), distorted onion states  
53  
54 (II) and (III), vortex state (IV), distorted vortex states (V) and (VI) and reversed-onion  
55  
56  
57  
58  
59  
60

1  
2  
3  
4 state (VII) [35]. Particularly, note also the possible presence of pair vortices in the phase  
5  
6 IV (see also ref [36] for additional example of onion states and pair vortices).  
7

8  
9 Additional analyses were then sought by means of ZFC and FC in an attempt to  
10  
11 investigate possible presence of multiple magnetic components, see Fig.7. These  
12  
13 measurements were performed in two HOPG samples characterized by comparable  
14  
15 XRD diffractograms. ZFC and FC measurements performed in conditions of high  
16  
17 magnetic field of 5000 Oe (A) and 10000 Oe (B) revealed the presence of a significant  
18  
19 transition as the temperature was decreased from 300K to 10K. The magnetization was  
20  
21 found to be less negative as the temperature decreased to 10K (see Fig.7). Furthermore,  
22  
23 no significant overlap between the FC and ZFC signals was observed, despite the used  
24  
25 high fields values (i.e. significant overlap would be expected for a standard  
26  
27 ferromagnetic component for applied fields above the  $H_{\text{saturation}}$  [32-34]). Additional  
28  
29 evidence was then sought by plotting the difference of the two magnetization signals  
30  
31 (mFC-mZFC) following the method reported by Scheike et al.[7,8]. These analyses  
32  
33 revealed a non-zero trend in conditions of large field values of 5000 Oe and 10000 Oe  
34  
35 [32-34]. This observation seems to confirm the complex nature of the signal shown in  
36  
37 Fig.5. Particularly, saturation would be typically expected to exist for maximum field  
38  
39 values in the order 2000-3000 Oe. Literature reports have further shown that  
40  
41 ferromagnetic saturation can require up 3000 Oe in certain type of pyrolytic graphite  
42  
43 samples [34]. In those conditions, a saturated linear trend in proximity to zero values  
44  
45 of mFC-mZFC is expected [34]. Interestingly in Fig.7B and .8B, the measurements  
46  
47 performed at 10000 Oe do not show a saturated trend; This observation implies the  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4 existence of additional unsaturated magnetic complexities of possible superconductive  
5  
6 origin in agreement with the report of Scheike et al. [7,8]. Further work will be still  
7  
8 necessary for gaining deeper understanding of the nature of the observed multiple  
9  
10 magnetization signals.  
11  
12

## 13 14 **4 Conclusion**

15  
16 In conclusion, we have reported a novel temperature dependent XRD and SQUID  
17  
18 investigation of HOPG from 300.15 to 77.15 K. Presence of unusual vortex states in  
19  
20 the magnetization signals was demonstrated by hysteresis loop measurements  
21  
22 performed on the bulk sample and on lamellae extracted by exfoliation methods. mFC-  
23  
24 mZFC subtractions also revealed presence of unsaturated magnetization features at high  
25  
26 fields of 5000 Oe and 10000 Oe possibly indicating presence of a weak superconductive  
27  
28 component. Comparative measurements of c-axis shifts as a function of the temperature  
29  
30 were further reported in turbostratic graphite and CNTs samples. Evidence of a possible  
31  
32 structural-transition in the c-axis of HOPG in the temperature range between 77 K and  
33  
34 100K was also evidenced by means of Rietveld refinement.  
35

## 36 37 **Acknowledgments**


38  
39 We acknowledge research support from NSFC fund 11750110413 and Sichuan  
40  
41 Province fund 2019YFH0080. We also acknowledge prof. Wang Shanling for the help  
42  
43 in the TEM measurements of the sample.  
44

## 45 46 **References**

- 47  
48 [1] Kopelevich Y., Esquinazi P., Torres J. H. S., Moehlecke S. *Journal of Low*  
49  
50 *Temperature Physics* 2000; 119: 691-702.  
51  
52 [2] Zoraghi, Mahsa, Barzola-Quiquia, José, Stiller Markus, Esquinazi Pablo D., Estrela-  
53  
54 Lópis Irina. *Carbon* 2018; 139: 1074-1084.  
55  
56 [3] Marchenko, D., Evtushinsky, D. V., Golias, E., Varykhalov, A., Seyller, Th., Rader,  
57  
58 O. *Science Advances* 2018; 4: 11  
59  
60 [4] Precker C. E., Esquinazi P. D., Champi A., Barzola-Quiquia J., Zoraghi M., Muiños-  
Landin S., Setzer A., Böhlmann W., Spemann D., Meijer J., Muenster T., Baehre O.,  
Kloess G. and Beth H. *New J. Phys.* 2016;18: 113041

- [5] Esquinazi P., Heikkilä T. T., Lysogorskiy Y. V., Tayurskii D. A., and Volovik G. E. JETP Letters 2014; 100: 336–339.
- [6] Volovik G. E. JETP Letters 2018; 107: 516-517
- [7] Scheike T., Böhlmann W., Esquinazi P., Barzola-Quiquia J., Ballestar A., and Setzer A. Adv. Mater. 2012; 24: 5826.
- [8] Scheike T., Esquinazi P., Setzer A., and Böhlmann W. Carbon 2013; 59:140.
- [9] Saad M., Gilmutdinov I. F., Kiiamov A. G., Tayurskii D. A., Nikitin S. I., Yusupov R. V. JETP Lett. 2018; 107: 37-41.
- [10] Ballestar A., Barzola-Quiquia J., Scheike T. and Esquinazi P. New Journal of Physics 2013 ;15: 023024.
- [11] Brihuega I., Mallet P., González-Herrero H., de Laissardière G. T., Ugeda M. M., Magaud L., Gómez-Rodríguez J. M., Ynduráin F., and Veuillen J.-Y. Phys. Rev. Lett. 2012; 109: 196802.
- [12a] Cao Y., Fatemi V., Fang S., Watanabe K., Taniguchi T., Kaxiras E. and Jarillo-Herrero P. Nature 2018; 556: 43–50.
- [12b] Cao Y., Fatemi V., Demir A., Fang S., Tomarken S. L., Luo J. Y., Sanchez-Yamagishi J. D., Watanabe K., Taniguchi T., Kaxiras E., Ashoori R. C. and Jarillo-Herrero P. Nature 2018; 556: 80–84.
- [13] Flores M., Cisternas E., Correa J., and Vargas P. Chem. Phys. 2013; 423: 49.
- [14] Yin L.-J., Qiao J.-B., Wang W.-X., Chu Z.-D., Zhang K. F., Dou R.-F., Gao C. L., Jia J.-F., Nie J.-C., and He L. Phys. Rev. B 2014; 89: 205410.
- [15] Warner J. H., Römmeli M. H., Gemming T., Büchner B., and Briggs G. A. D. Nano Lett. 2009; 9: 102.
- [16] Padhi B., Setty C., and Phillips P. W. Nanoletters 2018; 18: 6175-6180
- [17] Kausteklis J., Cevc P., Arcon D., Nasi L., Pontiroli D., Mazzani M., et al. Physical Review B 2011; 84: 125406.
- [18] Likodimos V., Glenis S., Guskos N., Lin C. L. Physical Review B 2007; 76: 075420
- [19] Odunmbaku O., Xia J., Borowiec J., Wang S., Taallah A., He Y., and Boi F. S. Journal of Applied Physics 2019; 125: 024302.
- [20] Boi F. S., Zhang X. and Corrias A. Materials Research Express 2018; 5: 025010.
- [21] Liu S., Sakurai M., Zhang W., Asakura K., Iida N., Tona M., Terui T., Sakurai T., Ohta H. Phys. Scr. 2011; T144: 014043.
- [22] Harb M., von Korff Schmising C., Enquist H., Jurgilaitis A., Maximov I., Shvets P. V., Obraztsov A. N., Khakhulin D., Wulff M., and Larsson J. Appl. Phys. Lett. 2012; 101: 233108.
- [23] Boi F. S., Liu M., Xia J., Odunmbaku O., Taallah A. and Wen J. Carbon, 2019; 145: 690-693
- [24] Luo H., Zhang R., Laver M., Yamani Z., Wang M., Lu X., Wang M., Chen Y., Li

- 1  
2  
3 S., Chang S., Lynn J. W., and Dai P. *Physical Review Letters* 2012; 108: 247002.  
4  
5 [25] Boi F. S., Liu M., Xia J., Odunmbaku O., Taallah A., Wen J. *Carbon* 2019; 150: 27-  
6  
7 31.  
8 [26] LeBoeuf D., Rischau C. W., Seyfarth G., K uchler R., Berben M., Wiedmann S.,  
9  
10 Tabis W., Frachet M., Behnia K. and Fauqu e B. *Nature Communications* 2017; 8 1337.  
11 [27] Tanuma, S. et al. in *Physics in High Magnetic Fields* (eds Chikazumi, S. & Miura,  
12  
13 N.) 274–283 (Springer, Berlin, 1981).  
14 [28] Yaguchi, H. and Singleton, J. J. *Phys. Condens. Matter* 2009; 21: 344207.  
15 [29] Fauqu e, B. & Behnia, K. in *Basic Physics of Functionalized Graphite* (ed.  
16  
17 Esquinazi, P. D.) Ch. 4 (Springer, 2016)  
18 [30] Medranda D., Borowiec J., Zhang X., Wang S., Yan K., Zhang J., He Y., Ivaturi  
19  
20 S., Boi F. S.. Ferromagnetically filled carbon nano-onions: the key role of sulfur in  
21  
22 dimensional, structural and electric control. *R. Soc. Open Sci.* 2018; 5: 170981  
23 [31] Boi F. S., Wang J., Ivaturi S., Zhang X., Wang S., Wen J., He Y. and Xiang G.  
24  
25 Micrometre-length continuous single-crystalline nm-thin Fe<sub>3</sub>C-nanowires with  
26  
27 unusual 010 preferred orientation inside radial few-wall carbon nanotube structures:  
28  
29 the key role of sulfur in viscous boundary layer CVS of ferrocene. *RSC Adv.*, 2017; 7:  
30  
31 13272.  
32 [32] P. Esquinazi, *Graphite and its hidden superconductivity*, *Pap. Phys.* 2013; 5:  
33  
34 050007 (2013).  
35 [33] E. M. Forgan. *Commentary on \Graphite and its hidden superconductivity*. *Papers*  
36  
37 *in Physics* 2013; 5: 050008.  
38 [34] P. Esquinazi. *Reply to the Commentary on Graphite and its hidden*  
39  
40 *superconductivity*. *Papers in Physics* 2013; 5: 050009.  
41 [35] F. Montoncello, L. Giovannini, F. Nizzoli, H. Tanigawa, T. Ono, G. Gubbiotti, M.  
42  
43 Madami, S. Tacchi, and G. Carlotti. *Magnetization reversal and soft modes in*  
44  
45 *nanorings: Transitions between onion and vortex states studied by Brillouin light*  
46  
47 *scattering*. *Physical Review B* 2008; 78: 104421.  
48 [36] Mei-Feng Lai, Ying-Jiun Chen, Da-Ren Liu, Chi-Kuen Lo, Chia-Jung Hsu, Chun-  
49  
50 Neng Liao, Chiun-Peng Lee, Yi-Hsun Chiu, and Zung-Hang Wei. *Influence of different*  
51  
52 *onion states on magnetization reversal processes in permalloy rings*. *IEEE Transactions*  
53  
54 *on Magnetics* 2010; 46(2): 179-182.  
55 [37] Spemann D., Esquinazi P., Setzer A., and B ohlmann W. *Trace element content and*  
56  
57 *magnetic properties of commercial HOPG samples studied by ion beam microscopy and*  
58  
59 *SQUID magnetometry*. *AIP Advances* 4, 107142 (2014)  
60

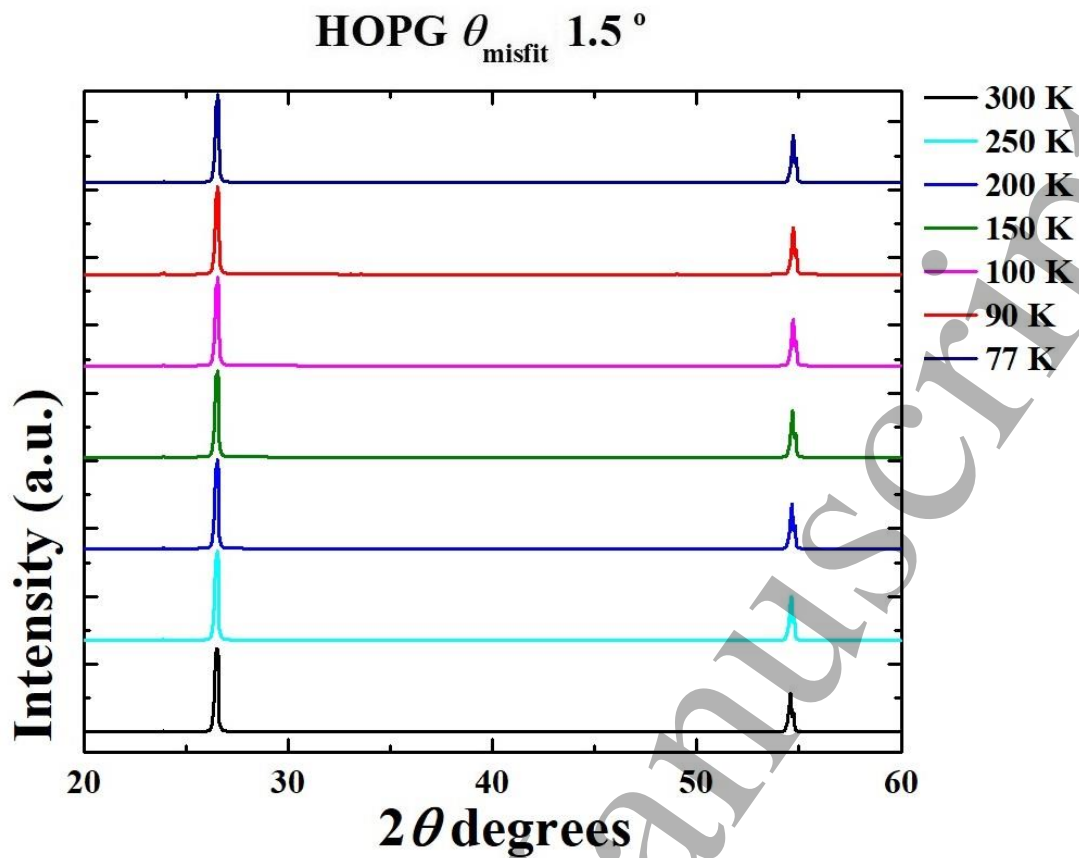

32 Figure 1. XRD diffractograms showing the structural shifts of the 002 and 004 reflections of HOPG  
33 as a function of the temperature from 300.15 to 77.15K.  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

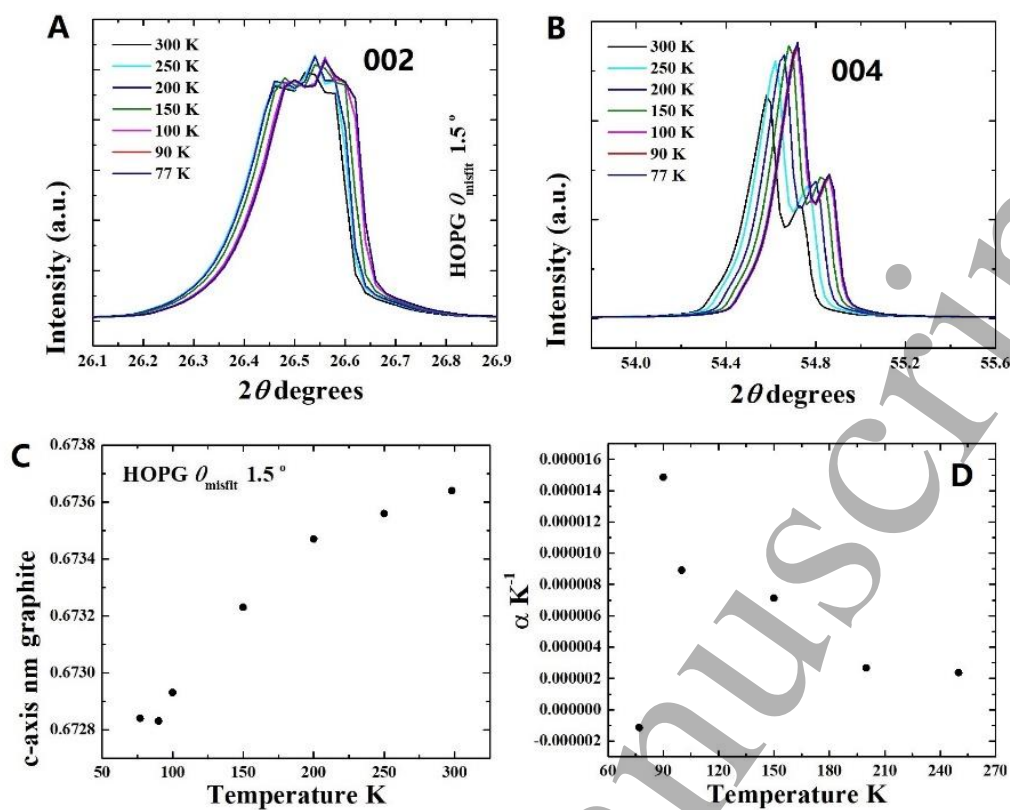


Figure 2. XRD diffractograms showing with a higher detail the structural shifts of the 002 (A) and 004 (B) reflections of HOPG as a function of the temperature from 300.15 to 77.15K. In C, D plots showing the variation of the unit cell c-axis of HOPG as extracted with the Rietveld refinement method (see ESI for detailed analyses) as a function of the temperature from 300.15 to 77.15K. The  $\alpha$ -factor was also plotted as function of the temperature in D. Note the presence of a possible transition at the temperature of 100-77K.



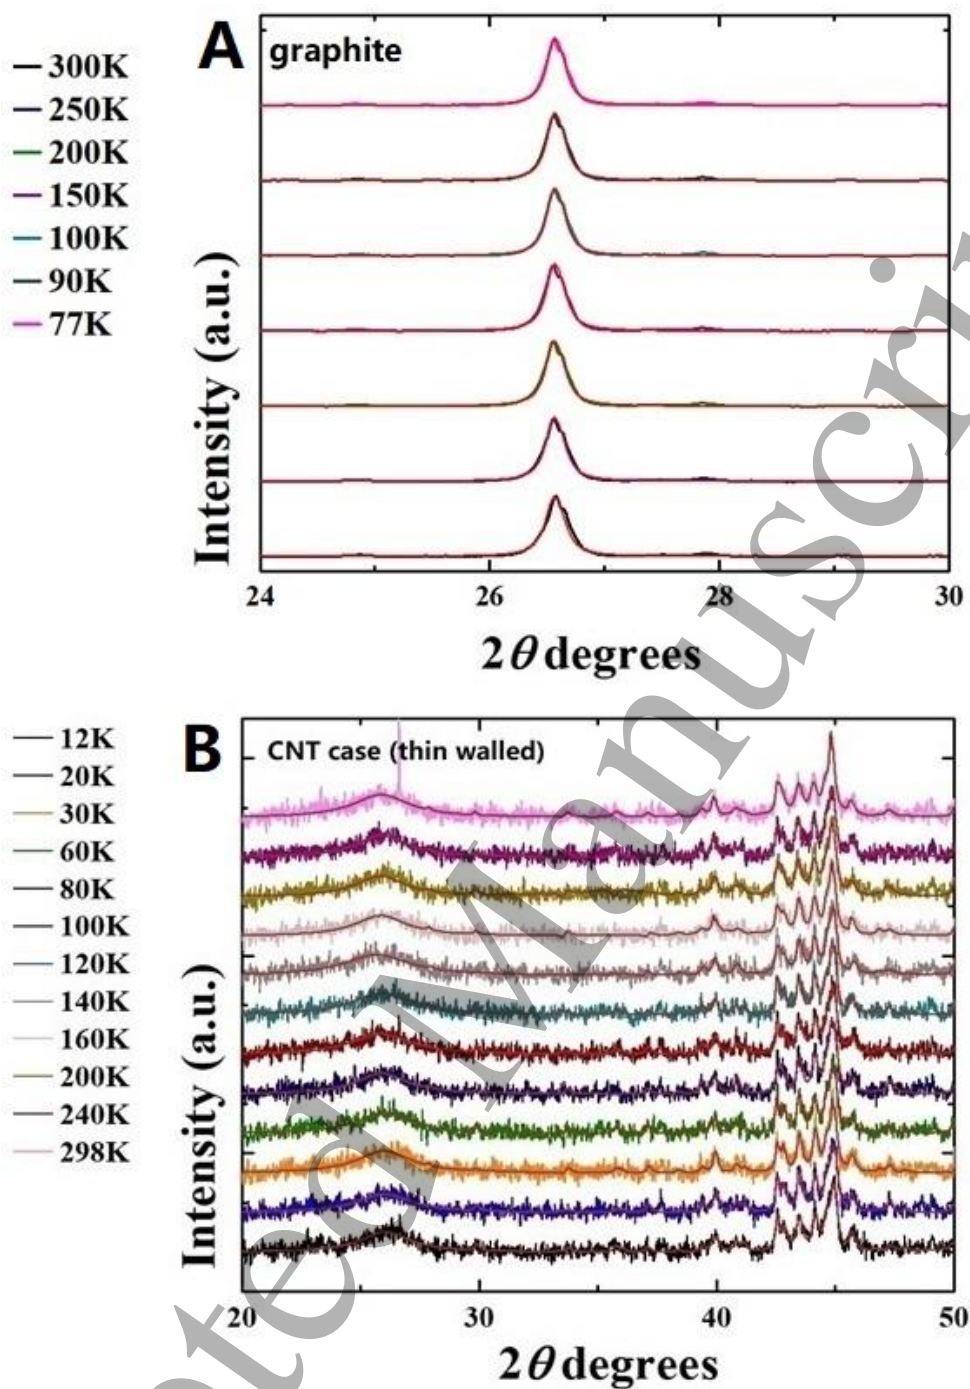


Figure 3: XRD patterns and Rietveld refinement (red line) obtained from a powder of graphite (turbostratic) in A (see experimental section for details of used instrumentation) and a powder of  $\text{Fe}_5\text{C}_2/\text{Fe}_7\text{C}_3$  filled CNTs produced by pyrolysis of sulfur/ferrocene mixtures in B. See reference 30-31 for method of CNT-production and peak phase identification.

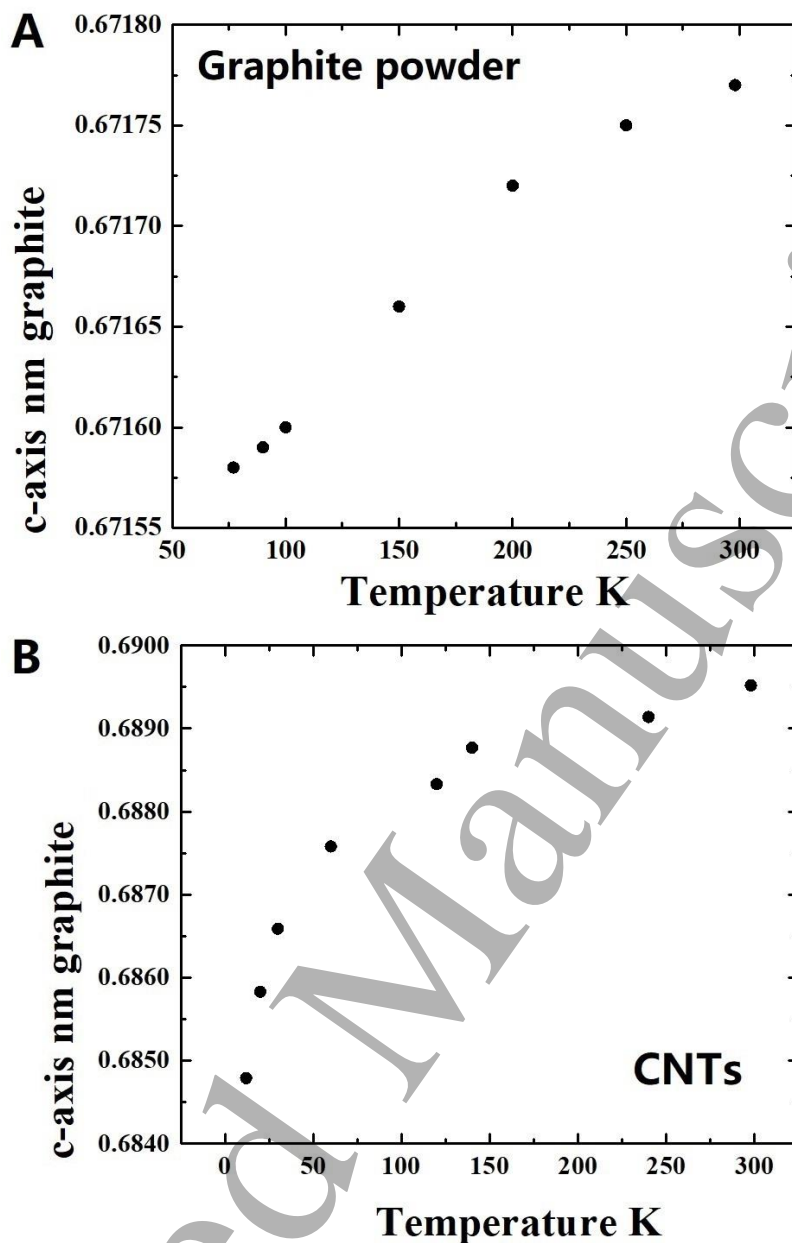


Figure 4. Plots showing the variation of the unit cell c-axis in A) for turbostratic graphite (Fig.3A) and B) for thin walled CNTs (Fig.3B), as extracted with the Rietveld refinement method as a function of the temperature from 300.15 to 77.15 K (graphite case) and from 300 to 12 K (CNT case). See Fig.3 for Rietveld refinement characterization of thin walled CNTs samples.

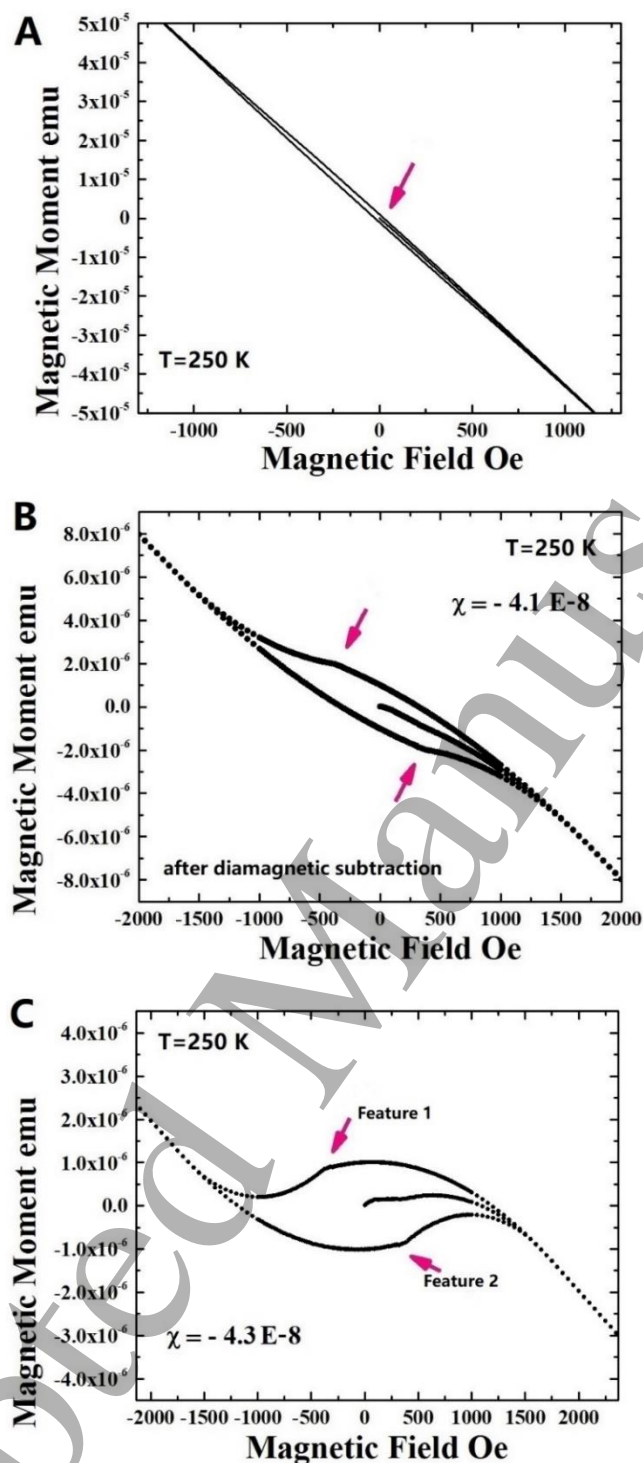


Figure 5. Magnetization vs Field measurements of HOPG at 250K showing the presence of an unusual hysteresis for magnetic field orientation approximately perpendicular (tilted orientation) to the HOPG layers (due to sample dimensions, only a tilted orientation could be achieved in the HOPG sample when encased in the SQUID capsule). In B and C the signal is shown after diamagnetic background subtraction using slightly different slopes obtained by fitting the linear diamagnetic background. Note the presence of two characteristics sharp features, as indicated by the magenta arrows, which can not be explained on the basis of standard ferromagnetic ordering.

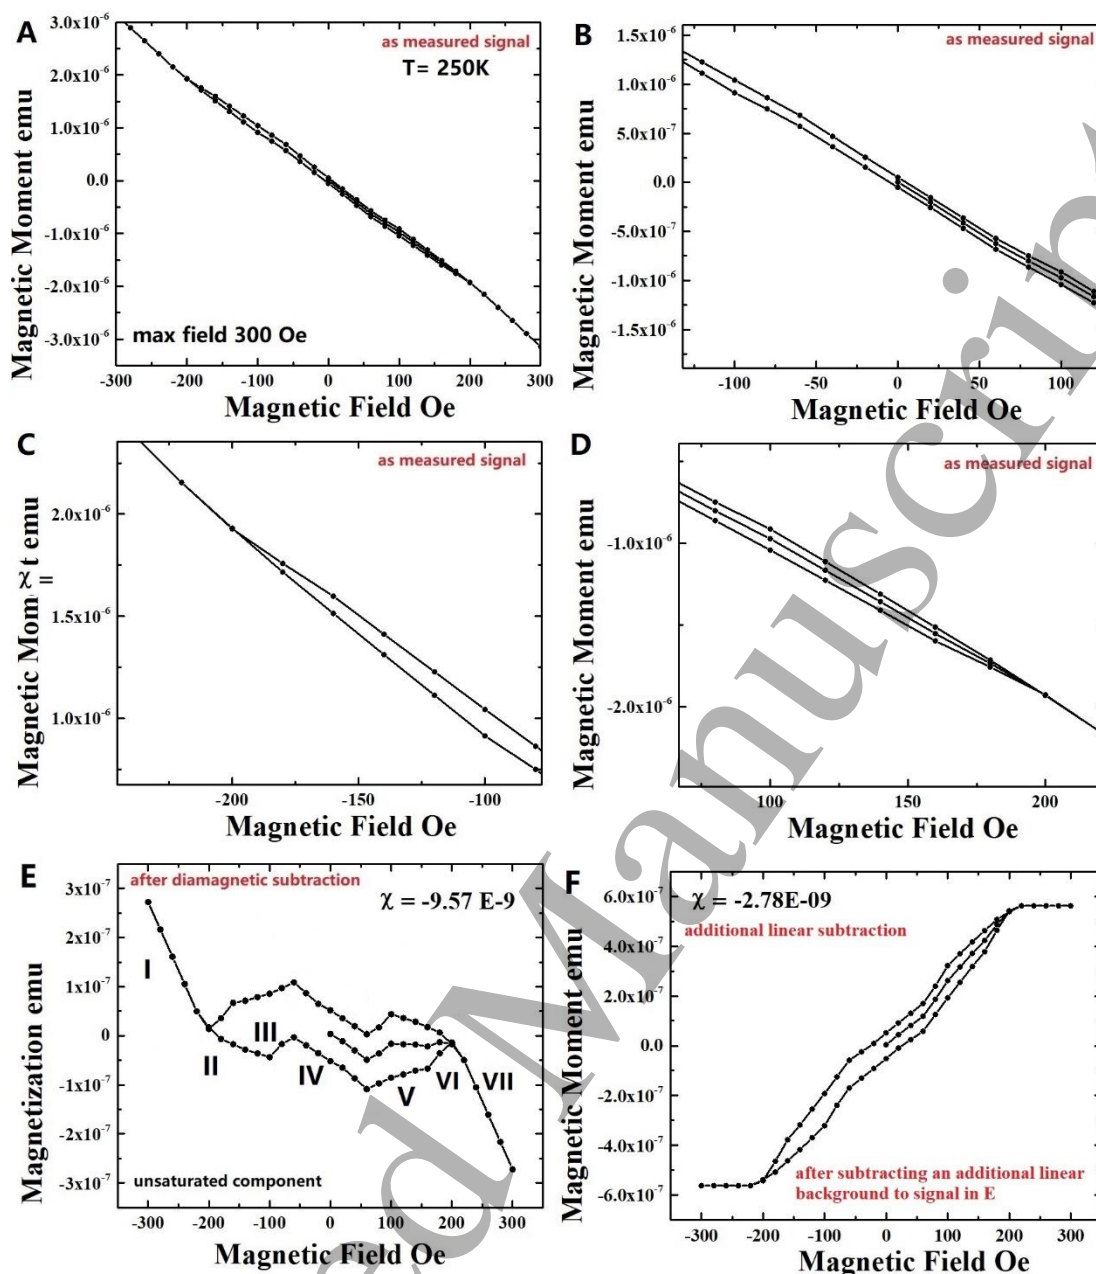


Figure 6. Magnetization vs Field measurements in A-D of a  $\mu\text{m}$ -thin lamellae extracted from the internal regions of the bulk HOPG sample by using tape-based exfoliation methods. The measured signal reveals the presence of an unusual hysteresis in conditions of magnetic field orientation perpendicular to the HOPG layers. Anomalous pinning features, could be clearly observed in E after diamagnetic subtraction (in E the signal is obtained by subtracting a linear diamagnetic background). By applying a second diamagnetic subtraction to the signal in E, an unusual magnetization signal can be found. The observed features indicate the presence of a transition from a onion-like magnetization state to a vortex-like one in conditions of max applied field of 300 Oe. The dynamics of vortex state formation can be described as onion state (phase I), distorted onion states (II) and (III), vortex state (IV), distorted vortex states (V) and (VI) and reversed-onion state (VII) [35] as highlighted in E.

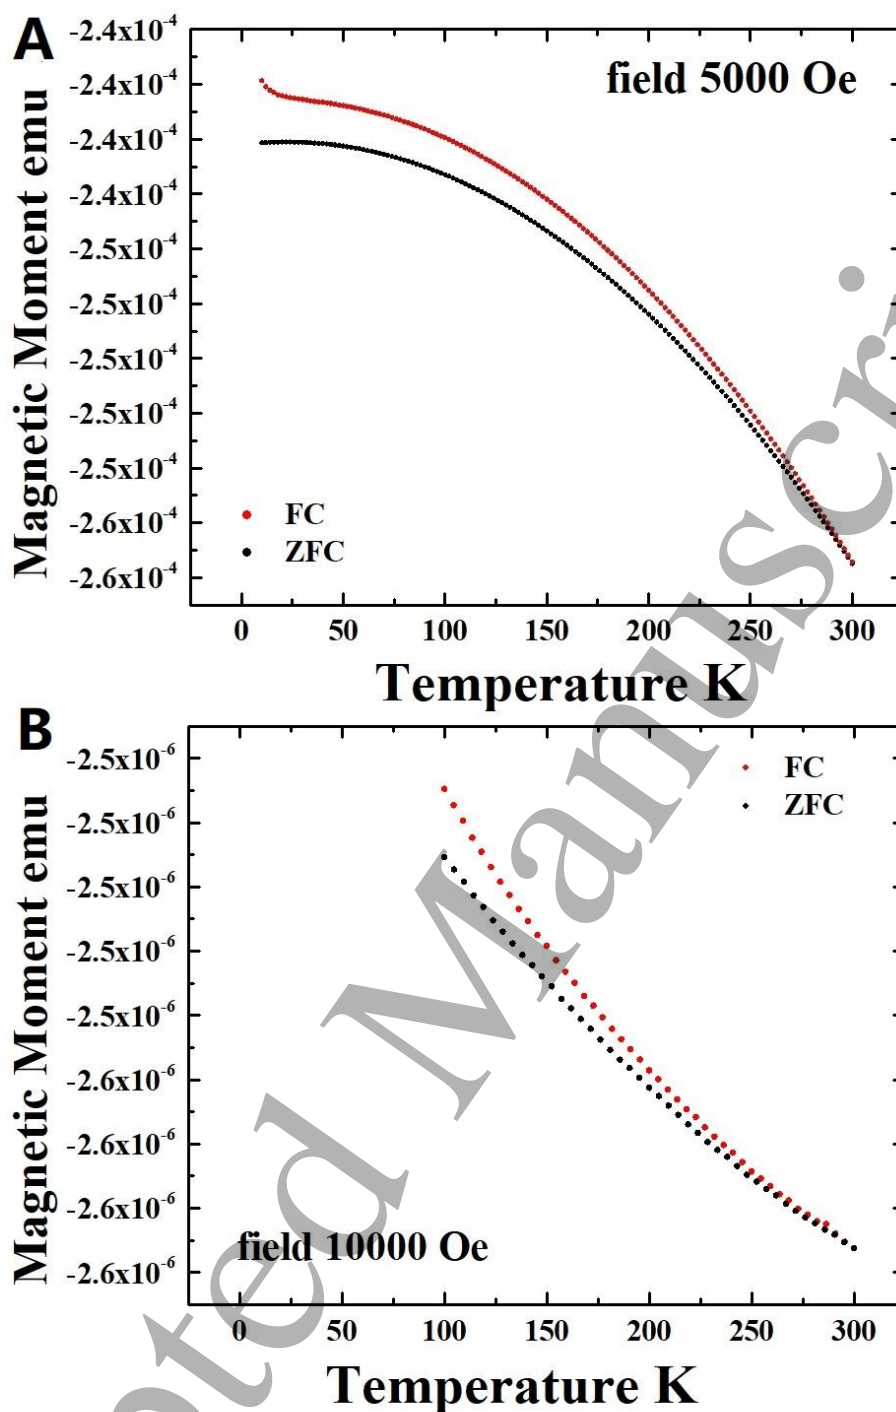


Figure 7. ZFC and FC magnetization plots of two HOPG samples with comparable structural characteristics. Note the presence of a significant transition as temperature approaches to 100 K. The magnetization is found to be less negative as the temperature decreases to 10K. Most importantly note the absence of saturation despite the use of large magnetic field values of 5000 Oe and 10000 Oe.

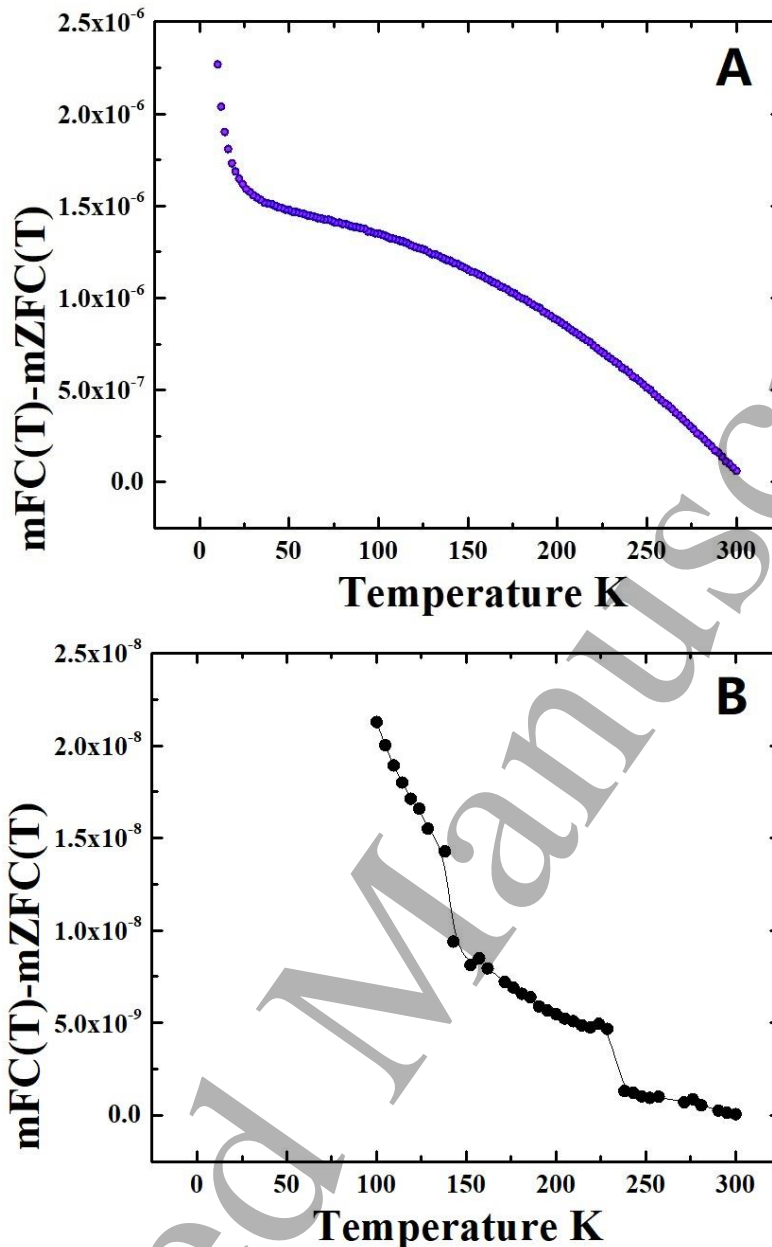


Figure 8. mFC -mZFC plots measured at 5000 Oe (A) and 10000 Oe (B) in two HOPG samples with comparable structural characteristics. Notice the non-zero positive contribution in both samples at large field values of 5000 Oe (A) and 10000 Oe (B) which can not be explained on the basis of the only ferromagnetic-vortex ordering. Previous works [32-34] have shown that a finite positive difference between mFC -mZFC can be possibly attributed as due to pinning of magnetic entities, superconducting vortices or magnetic domains in ferromagnets in conditions of low applied magnetic field values. Such a subtraction would be however expected to sharply decrease to zero in conditions of applied magnetic field larger than saturation-fields for  $H > H_{\text{saturation}}$ . The significant divergence observed below 300K in A and B indicates presence of unusual unsaturated components in agreement with previous observations of Scheike et al.[7,8].