

1 Recommendation of RILEM TC237-SIB on 2 Cohesion Test of Recycled Asphalt

3
4 Method to evaluate the presence of potentially active bitumen in reclaimed asphalt using indirect
5 tension test.

6 Gabriele Tebaldi¹, Eshan Dave², Augusto Cannone Falchetto³, Martin Hugener⁴, Daniel
7 Perraton⁵, Andrea Grilli⁶, Davide Lo Presti⁷, Marco Pasetto⁸, Andreas Loizos⁹, Kim Jenkins¹⁰,
8 Alex Apeagyei¹¹, James Grenfell¹², Maurizio Bocci¹³

9
10 ¹ *University of Parma, Italy - University of Florida, USA*

11 ² *Civil and Environmental Engineering, University of New Hampshire, USA*

12 ³ *Technische Universitat Braunschweig, Germany*

13 ⁴ *EMPA, Swiss Federal Laboratories for Materials Science and Technology, Switzerland*

14 ⁵ *University of Québec, ETS, Québec, Canada*

15 ⁶ *University of San Marino, San Marino*

16 ⁷ *University of Nottingham, United Kingdom*

17 ⁸ *University of Padova, Italy*

18 ⁹ *National Technical University of Athens, Greece*

19 ¹⁰ *Stellenbosch University, South Africa*

20 ¹¹ *University of East London, United Kingdom*

21 ¹² *Australian Road Research Board, Australia*

22 ¹³ *Università Politecnica delle Marche, Ancona, Italy*

23 *Contributors:*

24 *Elie Hajj, Patrick Muraya, Giovanni Giacomello, Di Wang*

25
26 **Abstract** This recommendation describes how to evaluate the presence of potentially active bitumen
27 in Recycled Asphalt (RA) materials through the cohesion test. The experimental protocol is designed
28 according to the research performed by the RILEM Technical Committee 237-SIB “Testing and
29 characterization of sustainable innovative bituminous materials and systems” with the purpose, to
30 develop a new, simple and fast method for the characterization of RA while limiting the need for
31 conventional rheological tests. The guidelines in this recommendation focus on the testing procedure
32 including specimen preparation, data analysis and provide information on the preparation of a tests
33 report.

34 *Keywords: Recycled Asphalt (RA); Cohesion Test, Indirect Tensile Strength (ITS)*

35

1
2 This recommendation was developed by the task group TG6 within RILEM TC 237-SIB
3 consisting of Gabriele Tebaldi, Eshan Dave, Martin Hugener, Augusto Cannone Falchetto, Daniel
4 Perraton, Andrea Grilli, Davide Lo Presti, Marco Pasetto, Andreas Loizos, Kim Jenkins, Alex
5 Apeageyi, James Grenfell, Maurizio Bocci. The draft recommendation was submitted for approval
6 to the full TC and subsequently approved by RILEM TC 237-SIB.
7

8 *TC Chairman:* Manfred N. Partl (EMPA - Swiss Federal Laboratories for Materials Science and
9 Technology, Dubendorf, Switzerland).

10 *TC Secretary:* Emmanuel Chailleux (IFSTTAR – French institute of science and technology for
11 transport, development and networks, Nantes, France).
12

13 *TG6 Group Leader:* Gabriele Tebaldi (University of Parma, Italy - University of Florida, USA).
14

15
16 *TC Members:* Gordon Airey (UK), Alex Apeageyi (UK), Ignacio Artamendi (UK), Hassan Baaj
17 (Canada), Hussain U. Bahia (USA), Wojciech Bankowski (Poland), Davide Broere (The
18 Netherlands), Maurizio Bocci (Italy), Yves Brosseaud (France), Willam G. Buttlar (USA),
19 Francesco Canestrari (Italy), Armelle Chabot (France), Emmanuel Chailleux (France), Eshan
20 Dave (USA), Joëlle De Visscher, (Belgium), Hervé Di Benedetto (France), Augusto Cannone
21 Falchetto (Germany), Gilda Ferrotti (Italy), Tomas Gabet (France), Marcin Gajewski (Poland),
22 Vincent Gaudefroy (France), William Grady (The Netherlands), Andrea Graziani (Italy), James
23 Grenfell (UK), Andrea Grilli (San Marino), Ferhat Hammoum (France), Bernhard Hofko
24 (Austria), Martin Hugener (Switzerland), Illan Ishai (Israel), Kim Jenkins (South Africa), Nicole
25 Kringos (Sweden), Greet A. Leegwater (The Netherlands), Eyal Levenberg (Israel), Andreas Loizos
26 (Greece), Davide Lo Presti (UK), Xiaohu Lu (Sweden), Paul Marsac (France), Anne Millien
27 (France), Konrad Mollenhauer (Germany), Francisco Morea (Argentina), Virginie Mouillet
28 (France), Patrick Muraya (Norway), Marco Pasetto (Italy), Manfred N. Partl (Switzerland),
29 Daniel Perraton (Canada), Christophe Petit (France), Katherine Petros (USA), Laurent Porot
30 (The Netherlands), Simon Pouget (France), Lily D. Poulidakos (Switzerland), Christiane Raab
31 (Switzerland), Safwat Said (Sweden), Cesare Sangiorgi (Italy), Cédric Sauzéat (France), Tom
32 Scarpas (The Netherlands), Hilde Soenen (Belgium), Dariusz Sybilsky (Poland), Gabriele Tebaldi
33 (Italy), Ann Vanelstraete (Belgium), Stefan Vansteenkiste (Belgium), Michael Wistuba (Germany),
34 Ludo Zanzotto (Canada), Adam Zofka (Poland)
35

36 Gabriele Tebaldi (✉)
37 University of Parma, Italy - University of Florida, USA
38 e-mail: gtebaldi@unipr.it

1 Introduction

2 In the pavement industry, the use of reclaimed asphalt (RA) is a common practice, mainly because
3 of its environmental and economical benefits [1]. RA is obtained from pavements which have
4 exceeded their service life and therefore, this material is a product of milling or demolition
5 processes. RA is composite material made of aggregates, bitumen, mastic, and in many instances a
6 conglomerate of multiple aggregate particles. Given the complex characteristics of RA, it is critical
7 to estimate the amount of RA bitumen that may be actively available when producing recycled
8 asphalt mixtures (cold, warm, and hot mixtures for in-situ and plant production). This is especially
9 important to develop reliable mix designs and to control mixture composition during production. In
10 addition, the current experimental procedures to analyze the RA bitumen require time-consuming
11 test procedures (bitumen extraction and recovery) [2, 3] coupled with sophisticated measurement
12 methods and expensive devices (i.e. the dynamic shear rheometer) [4, 5] and complex modeling
13 formulation that are not viable for routine mix design as well as for control of mix composition
14 during production. Together with lack of simple experimental methods, RA consistency and
15 representativeness, also in terms of bitumen, represent a challenge which requires use of test
16 procedure that can provide a “fingerprint” of RA.

17 2 Scope

18 The present recommendation introduces a new experimental procedure capable of evaluating the
19 capacity of bitumen from RA to actively contribute in blending process with virgin binder during
20 the production of recycled asphalt mixture; specifically, the cohesion test is hereafter presented.
21 Details on specimen preparation and test procedure, data analysis and tests reports are provided in
22 the following section of this document.

23 The application of the proposed experimental procedure is part of a larger protocol,
24 developed in different research efforts [6-8] and detailed in an upcoming RILEM recommendation,
25 [9] with the purpose of RA characterization as well as for use in mix design procedures of asphalt
26 mixtures that incorporate RA. The objective is to achieve a final product in field operation and
27 construction site, which is comparable to the design performed in the laboratory. It must be stressed
28 out that currently no alternative practical test procedures are available to easily determine the
29 capacity of RA bitumen that can be reactivated.

30 The proposed procedure includes testing at different temperatures and, hence, the results
31 provide insight on the availability of RA bitumen as function of temperature while also
32 characterizing the influence of temperature on the evolution of particle size distribution. In addition,
33 the cohesion test may contribute in the decision process regarding the selection of the specific
34 recycling technology: hot, warm or cold. The present testing procedure is designed according to the
35 protocol validated by round robin tests (RRT) conducted by the researchers of the TG6 of RILEM
36 TC 237-SIB.

3 Referenced documents

The following section provides a list of international standards and documents linked to the present recommendation.

ASTM Standards

- ASTM D6925-15 (2015) Standard Test Method for Preparation and Determination of the Relative Density of Asphalt Mix Specimens by Means of the Superpave Gyratory Compactor. ASTM International, West Conshohocken, PA
- ASTM D6926-16 (2016) Standard Practice for Preparation of Bituminous Specimens Using Marshall Apparatus. ASTM International, West Conshohocken, PA
- ASTM D6931-17 (2017) Standard Test Method for Indirect Tensile (IDT) Strength of Bituminous Mixtures. ASTM International, West Conshohocken, PA

EN Standards

- EN 12697-23 (2003) Bituminous Mixtures - Test methods for hot mix asphalt - Part 23: Determination of the Indirect Tensile Strength of Bituminous Specimens. European Committee for Standardization, Brussels, Belgium
- EN 12697-30 (2012) Bituminous mixtures - Test methods for hot mix asphalt - Part 30: Specimen preparation by impact compactor. European Committee for Standardization, Brussels, Belgium
- EN 12679-31 (2007) Bituminous mixtures - Test methods for hot mix asphalt - Part 31: Specimen preparation by gyratory compactor. European Committee for Standardization, Brussels, Belgium

RILEM recommendations

- Recommendation of RILEM TC237-SIB: Protocol for Characterization of Recycled Asphalt (RA) Materials for Pavement Applications

4 Definitions


Please refer to "Recommendation of RILEM TC237-SIB: Protocol for Characterization of Recycled Asphalt (RA) Materials for Pavement Applications" for definitions that are relevant to this recommendation.

5 Specimen preparation

RA can be classified as “active” or “inactive”, depending on the capacity of the residual bitumen to glue the particles together after compaction. For this reason, the cohesion test is performed on 100% RA without additional bitumen with a maximum aggregate size to be less than or equal to 1/5th of

1 the smaller mould dimension. Before testing, RA has to be dried at 30°C until the weight loss within
 2 24 hours is less than 1% (Figure 1a). Then, the material is compacted into cylindrical samples
 3 (Figure 1b). For this purpose, a Superpave Gyrotory Compactor (SGC) with a mould having a
 4 150mm diameter can be used to impose 30 gyrations to the RA material according to ASTM D6925-
 5 15 or EN 12697-31 [10, 11]. Quantity of material should be selected to produce specimen of
 6 dimensions required by ASTM D6931-12 or EN 12697-23 [14, 15]. During compaction, the
 7 evolution of the air voids content is recorded. Alternatively, Marshall Compaction according to
 8 ASTM D6926-10 or EN 12697-30 [12, 13] can be used to produce specimens with a diameter of
 9 101.6 mm, however use of gyratory compactor is recommended.

10 Specimens needs to be compacted at three different temperatures: 20, 70 and 140°C. Before
 11 determining the cohesion value through the Indirect Tensile Strength (ITS) [14, 15]. Six replicates
 12 need to be produced for each of the selected testing temperatures. Each of the six samples is divided
 13 into two sub-groups where one is tested in dry condition while the other set is conditioned in water
 14 at 25°C for 24 hours prior to testing.

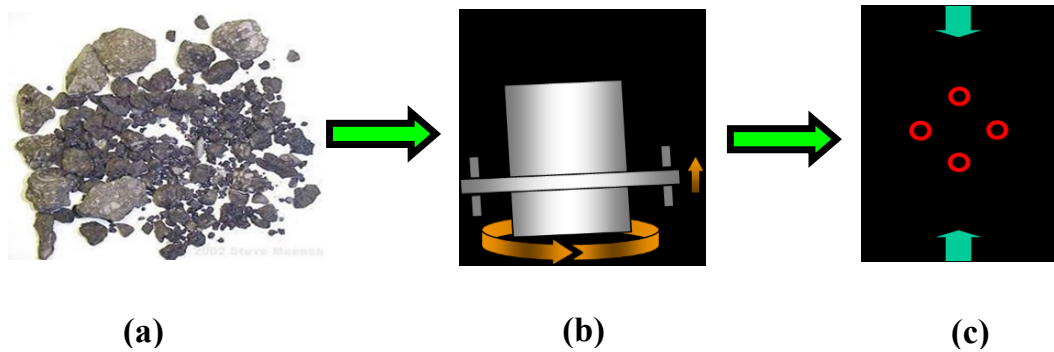

15 (a) (b) (c)
 16 **Fig. 1** Procedure and apparatus used in the cohesion test

17 6 Test procedure

18 The ITS testing procedure detailed in the ASTM D6931-12 or EN 12697-23 [14, 15] is used to
 19 evaluate the degree of cohesion (Figure 1c). Table 1 shows typical cohesion test results obtained
 20 from the RRT conducted by the TG6 of RILEM TC 237-SIB.

21

22 **Table 1** Example of cohesion test results


<i>Source of RAP</i>	A
<i>Temperature 20°C</i>	
<i>ITS at 25°C (dry) [kPa]</i>	<i>N/A</i>
<i>ITS at 25°C (wet) [kPa]</i>	<i>N/A</i>
<i>Air voids level</i>	<i>N/A</i>
<i>Source of RAP</i>	A
<i>Temperature 70°C</i>	
<i>ITS at 25°C (dry) [kPa]</i>	389
<i>ITS at 25°C (wet) [kPa]</i>	61
<i>Air voids level</i>	23.0
<i>Source of RAP</i>	A
<i>Temperature 140°C</i>	

ITS at 25°C (dry) [kPa]	811
ITS at 25°C (wet) [kPa]	765
Air voids level	18.2

1 N/A.: it was not possible to test the compacted specimens, as they fell apart during the demoulding
2 process

3 7 Data analysis


4 This section is based on the analysis performed during the RRT campaign of the TG6 of RILEM TC
5 237-SIB. All the manufactured samples are subjected to ITS test as described in Section 6. Figures
6 2 and 3 provide an overview of the results obtained from the RRT as an example. The average air
7 voids value of each group of tested samples is reported in brackets in the graphs.

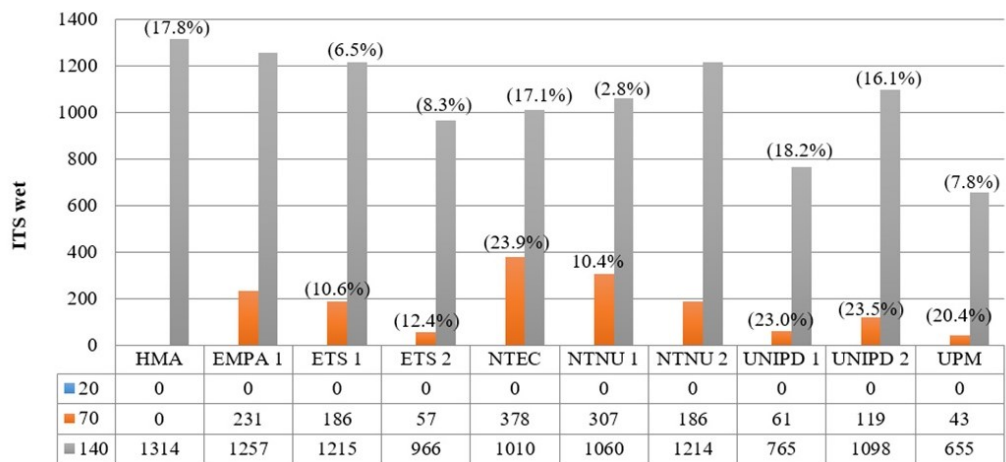

8

9 **Fig. 2** Cohesion test results - WET condition

10

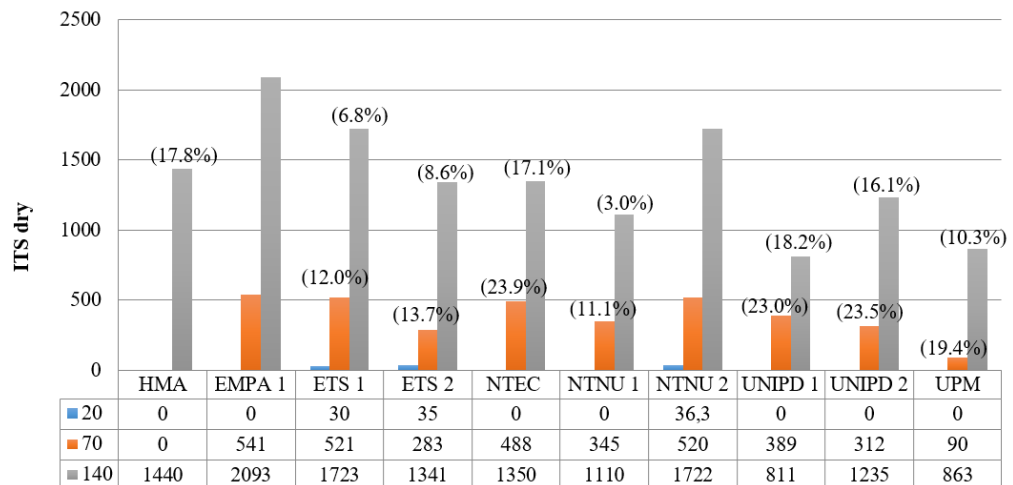

11

12 **Fig. 3** Cohesion test results - DRY condition

13


14

15

16

With respect to the proposed example, RA samples compacted at 20°C did not hold in most of the cases. Nevertheless, in all other cases, regardless if in dry or in wet condition, the values exceeded 100 kPa indicating that all RA can be classified to have bitumen or mastic with potential

1 cohesive contribution. After water bath conditioning, the results of ITS test on 100% RA samples
 2 vary significantly (Figure 4); while differences for hot mixes are less noticeable, using a
 3 classification in wet conditions might be more meaningful for half-warm mix applications.
 4

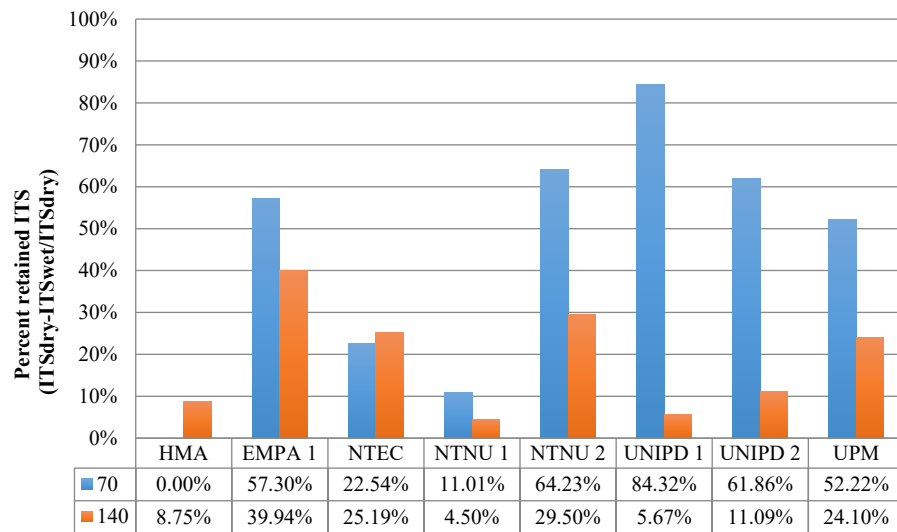

5
 6 **Fig. 4** Reduction of ITS value due to 24h water soaking

7 **8 Closing remark and test report**

8 The cohesion test presented in this RILEM recommendation provide as simple procedure to estimate
 9 the presence of active binder in RA materials. The RA material can be considered to have no
 10 cohesive contribution from bitumen or mastic (inactive) if the tested specimen at 20, 70 or 140°C is
 11 unable to support self-weight and the shape of the compacted specimen is not maintained at the
 12 testing time at designated test temperature, or if the ITS value in wet condition is less than 100kPa
 13 at 70°C. The specimen self-supporting requirement is made in context of gyratory compacted
 14 specimens of 150 mm diameters, while using Marshall procedure for compaction, the 100kPa
 15 strength based limit should be used. The procedure requires equipment which widely used and
 16 commonly available in laboratories and at asphalt plants. Based on the present document the test
 17 report should contain:

- 18 • Relevant information on the tested RA, such as origin, storing, maximum aggregate size
 19 and potential conditioning;
- 20 • The description of the test setup, including: mould size, compaction temperatures and
 21 mode, specimen conditioning;
- 22 • The ITS values measured for each compaction temperature and corresponding air voids
 23 values, for wet and dry conditions as well as the corresponding variation between the two
 24 measured values in percentage.

25 **Compliance with ethical standards**

26 Conflict of interest: The authors declare that they have no conflict of interest.

1 **References**

- 2 1. Kennedy TW, Tam WO, Solaimanian M (1998) Optimizing use of reclaimed asphalt pavement
3 with the Superpave system. *J Assoc Asph Paving Technol*, 67: 311–325
- 4 2. ASTM D1856-09 (2015) Standard Test Method for Recovery of Asphalt from Solution by
5 Absorb Method, ASTM International, West Conshohocken, PA, 2015
- 6 3. EN 12697-3 (2013) Bituminous mixtures. Test methods for hot mix asphalt. Bitumen recovery:
7 Rotary evaporator. European Committee for Standardization, Brussels, Belgium
- 8 4. AASHTO T315 (2012) Standard Method of Test for Determining the Rheological Properties of
9 Asphalt Binder Using a Dynamic Shear Rheometer (DSR). American Association of State
10 Highway and Transportation Officials, Washington.
- 11 5. EN 14770-08 (2012) Bitumen and bituminous binders - Determination of complex shear
12 modulus and phase angle using a Dynamic Shear Rheometer (DSR). European Committee for
13 Standardization, Brussels, Belgium
- 14 6. Tebaldi G, Dave E, Marsac P, Muraya P, Hugener M, Pasetto M et Alt., (2012a).
15 Classification of recycled asphalt (RA) material. 2nd International symposium on asphalt
16 pavements & environment, ISAP TC APE, Fortaleza. Brazil.
- 17 7. Tebaldi G, Dave E, Marsac P, Muraya P, Hugener M, Pasetto M et Alt., (2012b). Synthesis of
18 Specimen Preparation and Curing Processes for Cold Recycled Asphalt Mixes, 2nd
19 International symposium on asphalt pavements & environment, ISAP TC APE, Fortaleza.
20 Brazil.
- 21 8. Tebaldi G, Dave EV, Marsac P, Muraya P, Hugener M, Pasetto M, et alt. (2014) Synthesis of
22 standards and procedures for specimen preparation and in-field evaluation of cold recycled
23 asphalt mixtures, *Road Mater Pavement*, 15(2): 272-299. doi: 10.1080/14680629.2013.866707
- 24 9. Recommendation of RILEM TC237-SIB: Protocol for Characterization of Recycled Asphalt
25 (RA) Materials for Pavement Applications
- 26 10. ASTM D6925-15 (2015) Standard Test Method for Preparation and Determination of the
27 Relative Density of Asphalt Mix Specimens by Means of the Superpave Gyratory Compactor.
28 ASTM International, West Conshohocken, PA
- 29 11. EN 12679-31 (2007) Bituminous mixtures - Test methods for hot mix asphalt - Part 31:
30 Specimen preparation by gyratory compactor. European Committee for Standardization,
31 Brussels, Belgium
- 32 12. ASTM D6926-16 (2016) Standard Practice for Preparation of Bituminous Specimens Using
33 Marshall Apparatus. ASTM International, West Conshohocken, PA
- 34 13. EN 12697-30 (2012) Bituminous mixtures - Test methods for hot mix asphalt - Part 30:
35 Specimen preparation by impact compactor. European Committee for Standardization,
36 Brussels, Belgium
- 37 14. ASTM D6931-17 (2017) Standard Test Method for Indirect Tensile (IDT) Strength of
38 Bituminous Mixtures. ASTM International, West Conshohocken, PA

- 1 15. EN 12697-23 (2003) Bituminous Mixtures - Test methods for hot mix asphalt - Part 23:
- 2 Determination of the Indirect Tensile Strength of Bituminous Specimens. European
- 3 Committee for Standardization, Brussels, Belgium