



## Structural Studies of Aliphatic Substituted Phthalocyanine-Lipid Multilayers

Zarbakhsh, A; Campana, M; Mills, D; Webster, JRP


For additional information about this publication click this link.

<http://qmro.qmul.ac.uk/jspui/handle/123456789/5375>

Information about this research object was correct at the time of download; we occasionally make corrections to records, please therefore check the published record when citing. For more information contact [scholarlycommunications@qmul.ac.uk](mailto:scholarlycommunications@qmul.ac.uk)

**Langmuir**  
Msc: la102876r

The following graphic will be used for the TOC on the ACS website:

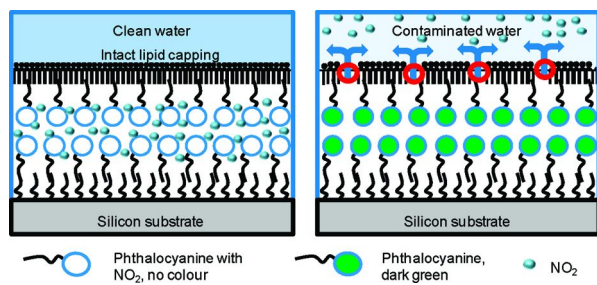

## Structural Studies of Aliphatic Substituted Phthalocyanine–Lipid Multilayers

Ali ZARBAKHSH,<sup>\*,†</sup> Mario Campana,<sup>†</sup> David Mills,<sup>‡</sup> and John R. P. Webster<sup>§</sup>

<sup>†</sup>*School of Biological & Chemical Sciences, Queen Mary, University of London, Joseph Priestley Building, Mile End Road, London E1 4NS, United Kingdom,* <sup>‡</sup>*Department of Physics, Queen Mary, University of London, GO Jones Building, Mile End Road, London, E1 4NS, United Kingdom, and* <sup>§</sup>*ISIS Neutron Facility, Science and Technology Facilities Council, Rutherford Appleton Laboratory, Harwell Science and Innovation Campus, Didcot, OX11 0QX, United Kingdom*

Received July 20, 2010. Revised Manuscript Received August 26, 2010

A Langmuir–Blodgett film of aliphatic substituted phthalocyanines on a C18 silane supporting layer coupled onto a silicon substrate has been investigated using neutron reflectometry. This multilayer structure is seen as a possible candidate for phthalocyanine–lipid biosensor devices. The results show the suitability of the C18 ligands as an anchoring layer for the phthalocyanines. The scattering length density profiles demonstrate the effectiveness of a lipid monolayer in partitioning the composition of phthalocyanine layers from that of the bulk liquid. The effectiveness of this barrier is a critical factor in the efficiency of such devices.

### Introduction

Since the discovery of phthalocyanines (Greek word, rock oil blue) in 1907<sup>1</sup> and their subsequent in-depth structural and chemical study a number of years later,<sup>2</sup> these compounds have shown potential in countless applications. Phthalocyanines are thermally and chemically very stable. They also display intense color and possess catalytic, electrical, as well as photophysical properties.<sup>3</sup> Phthalocyanine derivatives can form Langmuir monolayers at the air–water interface. Their deposition on a solid support using the Langmuir–Blodgett (LB) technique on hydrophobic surfaces has shown that the phthalocyanine ring will exhibit an edge-on orientation.<sup>4</sup> This is thought to be due to the amphiphilic character of these compounds.

The design of integrated optical sensors using aliphatic substituted phthalocyanines for continuous monitoring and spot checks on water quality has been reported.<sup>5</sup> These novel and highly sensitive, integrated optical biosensors are based on detection of change in the refractive index of a sensing layer saturated with nitrous molecules encapsulated between a biomimic membrane (phospholipid) and a solid support. The change in refractive index is measured using a stacked planar waveguide in a dual-polarization interferometer arrangement in these devices. The diffusion of entrapped nitrous molecules through the biomimic encapsulation will change as a function of damage caused by either bioagents (bacteria, viruses) or chemical agents (heavy metal contamination, pesticides) and is detected by change in the refractive index of the sensing layer.

The focus of our project was to study the structure and hence optimization of the design of a disposable version of these sensors, removing the need for optical measurement and the reliance on

the waveguide as a means of detection. This design will involve replacing the optical waveguide part of the sensor by a multilayer of an aliphatic substituted phthalocyanine compound, which can incorporate a color pigment, sensitive to nitrous oxide, which is in turn deposited on a hydrophobically modified silicon substrate using the Langmuir–Blodgett technique. A schematic diagram of such a device is shown in Figure 1. The first step in the commercialization of these devices involves a better understanding of the structure of the interfaces, that is, layer uniformity, the composition, and the effectiveness of a lipid layer as a membrane separating the sensing region from that of the bulk water. We report here a structural study of Langmuir–Blodgett deposited aliphatic (C10) substituted phthalocyanines (Figure 2) and lipid multilayer structures on a hydrophobic solid support using neutron reflectometry technique. We seek to determine the water content of the phthalocyanine multilayers, as this plays an important role in the long term stability of these devices, and also to investigate the interface between the aliphatic (substituted phthalocyanine molecules) and the mimic layer (lipid monolayer). The results will provide a better understanding of the interfaces and will ultimately enable engineering of more robust and reproducible commercial biosensors.

### Experimental Section

**Materials.** *d*-1,2-Dipalmitoyl-*sn*-glycero-3-phosphocholine (DPPC) and functionalized poly(ethylene glycol) (PEG) lipids DSPE-PEG(2000) were purchased from Avanti (Avanti, Polar Lipids, Inc.). The synthesis of the aliphatic substituted phthalocyanine is reported elsewhere.<sup>6</sup> The D<sub>2</sub>O was obtained from Fluorochem (>99 at. D%), and ultrapure H<sub>2</sub>O was produced using an Elgastat water purification unit. The silicon blocks (Crystran Ltd., Poole, U.K.), used as the substrate, were circular in section with a diameter of 100 mm and a thickness of 10 mm and were polished on one (111) face to ca. 6 Å. The silicon surface was initially cleaned using the RCA method.<sup>7</sup> The substrates were then

\*Author to whom correspondence should be addressed. E-mail: a.zarbaksh@qmul.ac.uk.

(1) Braun, A.; Tscherniac, J. *Ber. Dtsch. Chem. Ges.* **1907**, *40*, 2709.

(2) Linstead, R. P. *J. Chem. Soc.* **1934**, 1016.


(3) Torre, G.; Vazquez, P.; Agullo-Lopez, F.; Torres, T. *J. Mater. Chem.* **1998**, *8*, 1671.

(4) Palacin, S. *Adv. Colloid Interface Sci.* **2000**, *87*, 165.


(5) Fan, X.; White, I. M.; Shopova, S. J.; Zhu, H.; Suter, J. D.; Sun, Y. *Anal. Chim. Acta* **2008**, *14*, 8.

(6) Chambrier, I.; Cook, M. J.; Cracknell, S. J.; McMurdo, J. J. *Mater. Chem.* **1993**, *3*, 841.

(7) Kern, W. *J. Electrochem. Soc.* **1990**, *137*, 1887.

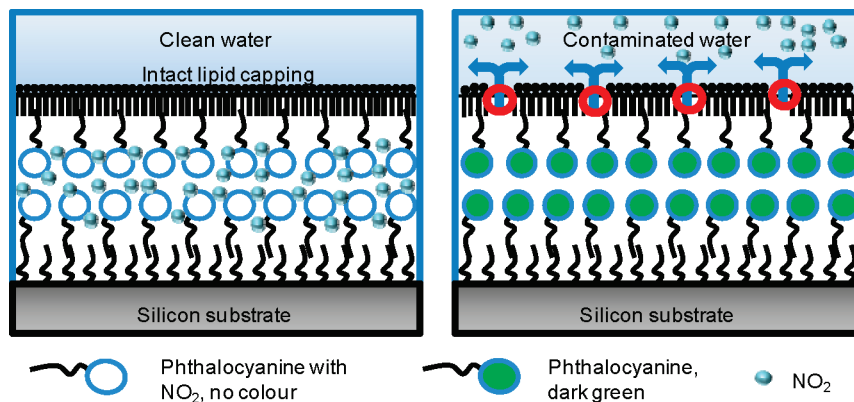

**Figure 1.** Schematic diagram of the phthalocyanine sensor device.

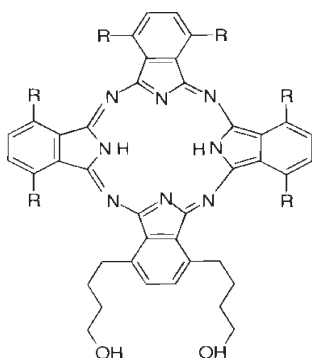

**Figure 2.** Chemical structure of the phthalocyanine ligand. The six R groups are  $C_{10}H_{21}$ .

80 chemically dried prior to treatment with a silane coupling agent  
81 octadecyltrichlorosilane (ACROS, 95%) using established  
82 methods.<sup>8</sup> This has been shown to provide a chemically bound  
83 hydrophobic layer on the silica surface.<sup>9</sup> In our previous work, we  
84 have characterized this layer by measuring the reflectivity from the  
85 Si–water interface using a series of contrasts.<sup>9</sup>

86 **Neutron Reflectometry.** Reflectivity measurements were  
87 carried out using the reflectometer SURF<sup>9</sup> at the ISIS Spallation  
88 Neutron Source, Rutherford Appleton Laboratory, Didcot, U.K.  
89 The neutron beam is polychromatic with wavelengths in the range  
90  $0.53 < \lambda < 6.9$  Å. To obtain the widest amenable momentum  
91 transfer,  $Q$ , range, reflectivity spectra were measured for a series  
92 of grazing incidence angles  $\theta$ , where  $\theta$  is the angle of incidence at  
93 the Si–water interface and  $Q = (4\pi \sin \theta)/\lambda$  is the momentum  
94 transfer at the interface. The nominal incidence angles used were  
95 0.35, 0.8, and 1.8°. The actual angles of incidence were determined  
96 by performing detector angle scans in reflection geometry once the  
97 height alignment of the sample with respect to the neutron beam  
98 has been optimized. The collimating slit settings were varied with  
99 incidence angle in order to measure all reflectivities with a  
100 constant angular resolution ( $\delta\theta/\theta = 3\%$ ). The sample was under-  
101 illuminated with an illuminated length of  $\sim 45$  mm projected on  
102 the sample.

103 The measured reflectivity profiles are normalized relative to the  
104 incidence beam monitor spectrum and corrected for detector  
105 efficiency as per standard reflectivity measurement on a time-of-

flight instrument,<sup>11</sup> and the data were subsequently corrected for  
the wavelength-dependent transmission through the silicon sub-  
strate. The data obtained were then overlapped in  $Q$ .

Neutron reflectivity is a technique sensitive to the average  
neutron refractive index,  $n$ , profile normal to an interface.<sup>8</sup> The  
dispersive refractive index can be written as

$$n(\lambda) \approx 1 - \frac{\lambda^2}{2\pi} Nb + i \frac{\lambda}{4\pi} N\sigma$$

where  $\lambda$  is the neutron wavelength,  $Nb = \sum_i N_i b_i$ , and  $N\sigma = \sum_i N_i \sigma_i$ ,  
with  $N_i$  being the number density,  $b_i$  the coherent scattering  
length, and  $\sigma_i$  the absorption and incoherent cross-section of  
nucleus  $i$ . The multiple  $Nb$  is known as the scattering length  
density of a medium with refractive index  $n$ . According to the  
above equation, the large difference in the scattering lengths of  $^1\text{H}$   
( $b = -3.7406$  fm) and  $^2\text{H}$  ( $b = 6.671$  fm) can be exploited in  
hydrogenous systems. Since  $Nb$  is linearly related to the volume  
fraction composition ( $Nb \approx \sum_j \phi_j Nb_j$ , where  $\phi_j$  is the volume  
fraction and  $Nb_j$  is the scattering length density of species  $j$ ), a  
layer model with discrete strata representing regions with different  
chemical composition can be constructed and the reflectivity from  
such a model can readily be calculated. Each layer,  $i$ , has a  
thickness,  $d_i$ , refractive index,  $n_i$ , scattering length density,  $Nb_i$ ,  
and interfacial roughness,  $\sigma_i$ . The reflectivity can be calculated  
using, among other methods, the standard optical-matrix method,  
and the parameters of the proposed layer model can be optimized  
using nonlinear least-squares fitting.

Two silicon blocks, S1 and S2, were used in these experiments.  
The surfaces of both these substrates were first cleaned and  
then rendered hydrophobic by means of silane coupling. A C-18  
layer was deposited. A series of 2, 4, and 6 layers of substituted  
phthalocyanine were subsequently deposited onto the C18  
coated silicon substrate S1, using Langmuir–Blodgett dipping  
technique.<sup>12</sup> The deposition was performed using a standard  
Teflon Langmuir trough. The trough was filled with ultrapure  
water (Milli-Q). A solution of phthalocyanine in chloroform was  
prepared and then carefully spread at the air–water interface. An  
ordered Langmuir film was then obtained by moving the poly-  
(tetrafluoroethylene) (PTFE) barriers of the trough until a surface  
pressure of  $25 \text{ mN m}^{-1}$  was reached. The surface tension was  
monitored by the Wilhelmy plate method. A sample holder was  
manufactured to dip the silicon block into the water, and while the  
block was immersed, the surface pressure was maintained at  
 $25 \text{ mN m}^{-1}$  by computer controlled motion of the PTFE barriers.  
The sample holder allowed dipping/removing of the block from  
the aqueous phase at a constant speed of 5 mm/min. First, a bilayer  
was deposited. The block with a bilayer was then characterized  
using neutron reflectometry with  $D_2O$  forming the aqueous


(8) Bowers, J.; Manzanera-Papayanopoulos, E.; McLure, I. A.; Cubitt, R. *J. Phys.: Condens. Matter* **1998**, *10*, 8173.

(9) Bowers, J.; Zarbaksh, A.; Christenson, H. K.; McLure, I. A.; Cubitt, R. *J. Chem. Phys.* **2003**, *119*, 11917.


(10) Penfold, J.; Richardson, R. M.; Zarbaksh, A.; Webster, J. R. P.; Bucknall, D. G.; Rennie, A. R.; Jones, R. A. L.; Cosgrove, T.; Thomas, R. K.; Higgins, J. S.; Fletcher, P. D. I.; Dickinson, E.; Roser, S. J.; McLure, I. A.; Hillmann, A. R.; Richards, R. W.; Burgess, A. N.; Simister, E. A.; White, J. W. *J. Chem. Soc., Faraday Trans.* **1997**, *93*, 3899.

(11) Penfold, J. *Phys. B* **1991**, *173*, 1.

(12) Davis, F.; Higson, S. P. *J. Biosens. Bioelectron.* **2005**, *21*(1), 1.

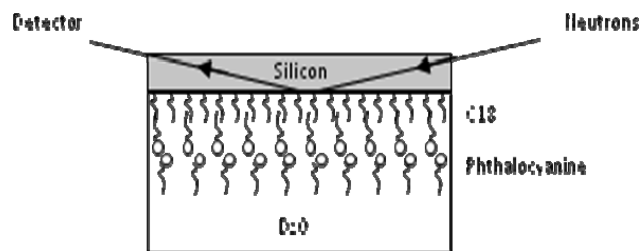

**Figure 3.** Neutron reflectometry experimental arrangement.

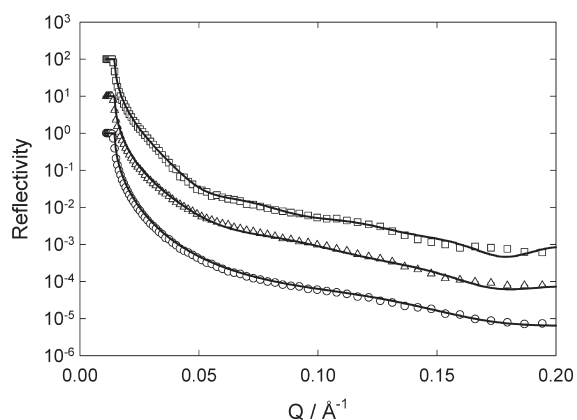

**Figure 4.** Reflectivity profiles for 1× bilayer (○), 2× bilayer (Δ), and 3× bilayer (□) of phthalocyanine at the silicon/D<sub>2</sub>O interface. The solid lines show the best fit to the data. The profiles are shifted by a factor of 10 for the purpose of clarity.


151 subphase. After this first measurement, the block was carefully  
 152 removed from the cell and a second bilayer was deposited using the  
 153 same procedure described above. Now those two bilayers of  
 154 phthalocyanine were again characterized using neutron reflecto-  
 155 metry. The same procedure was followed for the deposition of the  
 156 third bilayer.

157 In a second experiment, a mixture of DPPC and DPPE carrying  
 158 a PEG group (3%w/w) monolayer were transferred on top of the  
 159 second C18 coated second silicon substrate, S2, as a control  
 160 experiment. The deposition of the lipid mixture was also per-  
 161 formed at a constant surface pressure of 25 mN m<sup>-1</sup> and a dipping  
 162 speed of 5 mm/min. As only a monolayer had to be deposited, the  
 163 block was immersed in the aqueous phase, and then the air–water  
 164 interface was carefully cleaned by vacuum suction. Only then the  
 165 block was slowly removed from the trough. The structure of this  
 166 controlled monolayer was then determined. The lipid monolayer  
 167 was then washed away, and a bilayer of phthalocyanine followed  
 168 by a lipid monolayer was then deposited. In actual devices, the  
 169 nitrous oxide would be entrapped below this lipids monolayer.  
 170 A series of neutron reflectivity profiles were then obtained to  
 171 characterize these layers.

172 The C-18 layer has already been characterized using a series of  
 173 solvent contrasts on numerous occasions.<sup>9</sup> The silicon oxide layer  
 174 and the C-18 hydrophobe layer were also characterized using the  
 175 technique of ellipsometry (see the Supporting Information). The  
 176 layer thickness and density of the oxide layer and C18 layer were  
 177 then used as a starting point in our subsequent fitting procedure.  
 178 The neutron reflectometry's experimental arrangement is shown in  
 F3 179 Figure 3.

## 180 Results and Discussion

181 The measured reflectivity data for the C18 coated silicon block  
 182 S1 with 1, 2, and 3 bilayers of aliphatic substituted phthalocyanine  
 F4 183 with D<sub>2</sub>O forming the aqueous subphase are shown in Figure 4.  
 184 The solid lines correspond to modeled reflectivity based on the

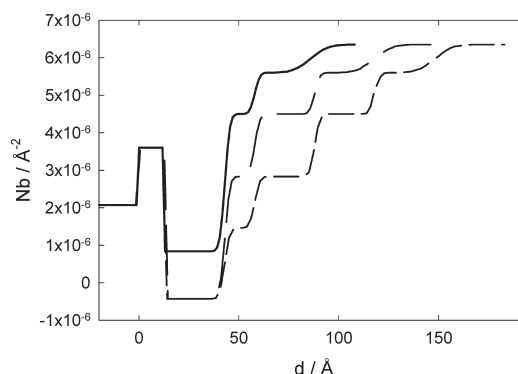


**Figure 5.** Scattering length density profiles for 2 (solid), 4 (long dash), and 6 (short dash) layers of phthalocyanine at the silicon–D<sub>2</sub>O interface.

**Table 1.** Fitted Structural Parameters Obtained from the Fits to the Reflectivity Profiles Shown in Figure 4

Si (S1) substrate			
layer	layer thickness (Å)	NB ( $\times 10^{-6} \text{ \AA}^{-2}$ )	roughness (Å)
1× bilayer phthalocyanine			
	C18	30 ± 2	0.84
1	phthalocyanine	15 ± 2	4.50
2	phthalocyanine	28 ± 2	5.60
2× bilayer phthalocyanine			
	C18	30 ± 2	−0.43
1	phthalocyanine	15 ± 1	2.83
2	phthalocyanine	30 ± 2	4.50
3	phthalocyanine	30 ± 2	5.60
3× bilayer phthalocyanine			
	C18	30 ± 2	−0.43
1	phthalocyanine	15 ± 2	1.46
2	phthalocyanine	30 ± 2	2.83
3	phthalocyanine	30 ± 2	4.50
4	phthalocyanine	30 ± 2	5.60

scattering length density profiles that are shown in Figure 5. In the  
 modeling of the data, the thickness and scattering length density  
 of the oxide film was found to be  $d = 13 \pm 2 \text{ \AA}$ ,  $Nb = 3.6 \times$   
 $10^{-6} \text{ \AA}^{-2}$ . The fitted structural parameters obtained from these  
 fits are given in Table 1.

The C18 layer was found to be  $30 \pm 2 \text{ \AA}$ , which is slightly  
 thicker than the expected value of 24 Å reported previously<sup>9</sup> and  
 a value of  $17 \pm 2 \text{ \AA}$  for a dry C18 layer coupled silicon sample  
 deduced from the ellipsometry data. This indicates an entangle-  
 ment of the C18 chain with the aliphatic tail of the phthalocyanine  
 layer, hence the good anchoring characteristic of the C18 Layer.  
 Neutron reflectometry cannot distinguish between the C18 chain  
 and the aliphatic tail of the phthalocyanine because of the lack of  
 contrast between the protonated C18 and the aliphatic part of the  
 phthalocyanine which is also protonated (similar scattering length  
 density value). One striking feature of these results is the fact that  
 as the number of phthalocyanine bilayers increases, the water  
 (D<sub>2</sub>O) content of the underlying structures decreases. This can be  
 seen in the scattering length density profiles (Figure 5). The total  
 layer thickness for the aliphatic substituted phthalocyanine for  
 the 1 bilayer sample was found to be 43 Å, for the 2 bilayers 75 Å,  
 and for the 3 bilayers 105 Å. This indicates a 13% and an 18%  
 reduction in the overall ideal layer thickness for 2 and 3 bilayer  
 samples which results from the D<sub>2</sub>O expulsion as more layers are

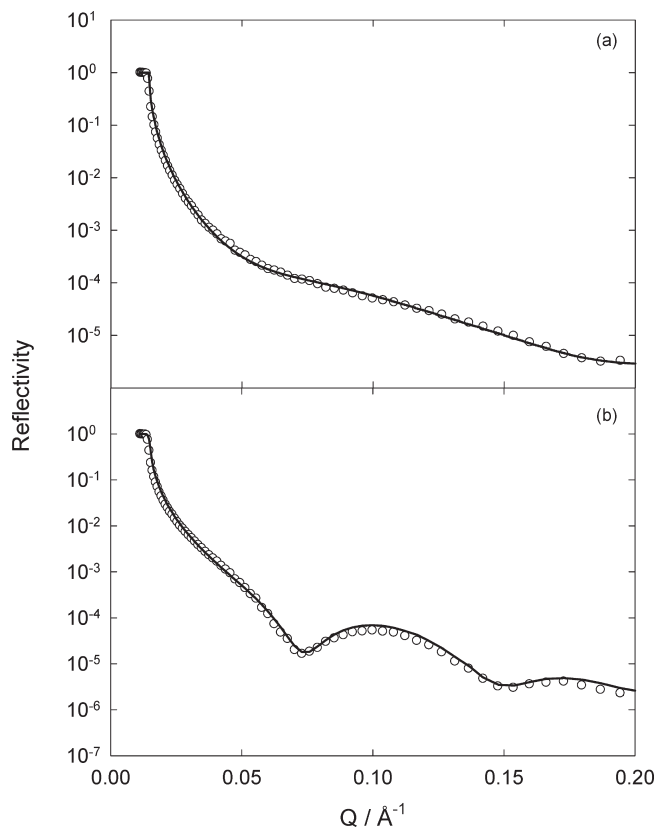


**Figure 6.** (a) Reflectivity profiles for DPPC-DPPE+PEG layer and (b) 2 layers of phthalocyanine covered by DPPC-DPPE+PEG at the silicon–D<sub>2</sub>O interface. The best fits to the data are shown by solid lines.

**Table 2. Fitted Structural Parameters Obtained from the Fits to the Reflectivity Profiles Shown in Figure 6**

Si (S2) substrate				
layer	layer thickness (Å)	NB ( $\times 10^{-6} \text{ Å}^{-2}$ )	roughness (Å)	
C18 + DPPC monolayer				
1	C18 + <i>d</i> -lipid	19 ± 2	0.55	4
2	lipid-chain	16 ± 2	3.30	3
3	lipid head-PEG	60 ± 5	5.83	14
C18 + 1 × bilayer phthalocyanine + DPPC monolayer				
1	C18	30 ± 2	−0.12	2
2	phthalocyanine	15 ± 1	1.22	2
3	phthalocyanine	30 ± 1	2.32	2
4	lipid-chain	16 ± 1	3.48	5
5	lipid head-PEG	60 ± 5	5.83	20

deposited. This is also supported by the scattering length density profiles (Figure 5).

In part one of the second experiment, a mixture of DPPC and DPPE carrying a PEG group (3%w/w) was deposited as a monolayer on a hydrophobic Si (C18 coated) surface (S2). The reflectivity profile is shown in Figure 6a. The fit to the data indicated a mixing of the deuterated tail of DPPC and the protonated C18 chain over a 19 Å region. This confirms the earlier results for the S1 sample (i.e., the interpenetrations of the aliphatic chains) and can now be seen because of better contrast. A three layer model was required to fit this data: a 19 Å layer consisting of a mixture of C18 and DPPC tail, a 16 Å layer representing the DPPC tail region, followed by a 60 Å layer

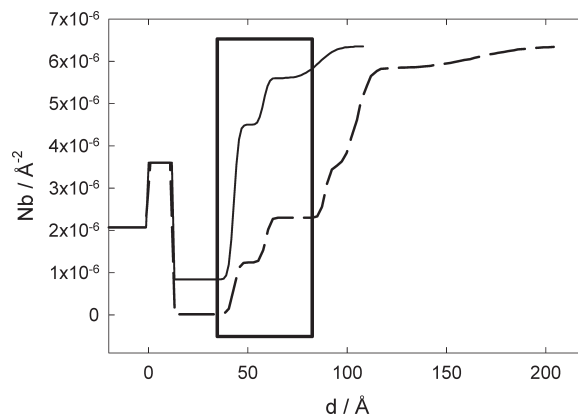

**Figure 7.** Scattering length density profiles for DPPC-DPPE+PEG layer (solid) and 2 layers of phthalocyanine covered by DPPC-DPPE+PEG (long dash) at the silicon–D<sub>2</sub>O interface. The box represents the phthalocyanine layer contribution to the data.

representing the large PEG and DPPC headgroup region. The fitted parameters are given in Table 2.

The lipid monolayer was then washed from the S2, and a bilayer of phthalocyanine was deposited followed by a lipid monolayer. The reflectivity data obtained are shown in Figure 6b. This deposited layer sequence represents an ideal device structure. The water penetration into the phthalocyanine bilayers was found to be less than that in the case of the 1 × bilayer phthalocyanine (S1 sample) with the same overall layer thickness. The water content of the phthalocyanine bilayer is an indication of the ability of the lipid monolayer to form an effective barrier between the D<sub>2</sub>O bulk and the phthalocyanine bilayer beneath. These are ideal characteristics required for these types of devices. The full scattering length density profile for the fit is shown in Figure 7. The fitted structural parameters are given in Table 2.

## Conclusions

In this experiment, we have shown the suitability of the C18 ligands as an anchoring layer for phthalocyanine on a solid support. The thicknesses of multilayers of phthalocyanine at the silicon–air interface measured with ellipsometry (see the Supporting Information) prior to the solid–liquid neutron experiment were 41, 82, and 124 Å, respectively, for 2, 4, and 6 layers, in overall good agreement with the neutron data and those reported in the literature.<sup>13</sup> Although the layer thicknesses reported here for neutron are slightly lower than these because of the interpenetrations of C18 and the aliphatic substituted phthalocyanine and the lack of scattering contrast between these layers.

The data for the phthalocyanine bilayer with the deposited lipid monolayer showed almost a complete depletion of water from the C18 layer in addition to a depletion of water from the phthalocyanine bilayer. This result demonstrates the effectiveness of the lipid layer in partitioning (sealing) the deposited phthalocyanine layers from the bulk water. This is crucial for viability of these systems as the biosensors' operation relies on the entrapment and subsequent release of nitrous oxide gas depending on the integrity of the lipid membrane. However, some trapped water content of these layers is required to maintain the sensing layer saturated with nitrous molecules for effective functioning of these devices. In a future experiment, we plan to use polished quartz as a substrate with color incorporated into the phthalocyanine bilayer. The transparent quartz will allow us to observe the color changes

(13) Velez, M.; Vieira, S.; Chambrier, I.; Cook, M. J. *Langmuir* **1998**, *14*, 4227.

263 in the sensing layer when the lipid membrane is attacked, resulting  
264 in the escape of the nitrous oxide gas, while simultaneously  
265 measuring the changes to the layer structures using neutron  
266 reflectometry.

267 **Acknowledgment.** The authors wish to thank the STFC, UK,  
268 for granting direct-access beam-time on SURF (ISIS) for this

work. The authors also wish to thank Professor Michael J. Cook 269  
group at the University of East Anglia, Norwich, UK for the 270  
provision of aliphatic substituted phthalocyanine ligand. 271

**Supporting Information Available:** Ellipsometry data ob- 272  
tained at the air–water interface. This material is available 273  
free of charge via the Internet at <http://pubs.acs.org>. 274