



# University of HUDDERSFIELD

## University of Huddersfield Repository

Pawlak, W., Kubiak, Krzysztof, Wendler, B.G. and Mathia, T.G.

Wear resistant multilayer nanocomposite WC<sub>1-x</sub>/C coating on Ti-6Al-4V titanium alloy

### Original Citation

Pawlak, W., Kubiak, Krzysztof, Wendler, B.G. and Mathia, T.G. (2015) Wear resistant multilayer nanocomposite WC<sub>1-x</sub>/C coating on Ti-6Al-4V titanium alloy. *Tribology International*, 82 (B). pp. 400-406. ISSN 0301-679X

This version is available at <http://eprints.hud.ac.uk/21616/>

The University Repository is a digital collection of the research output of the University, available on Open Access. Copyright and Moral Rights for the items on this site are retained by the individual author and/or other copyright owners. Users may access full items free of charge; copies of full text items generally can be reproduced, displayed or performed and given to third parties in any format or medium for personal research or study, educational or not-for-profit purposes without prior permission or charge, provided:

- The authors, title and full bibliographic details is credited in any copy;
- A hyperlink and/or URL is included for the original metadata page; and
- The content is not changed in any way.

For more information, including our policy and submission procedure, please contact the Repository Team at: [E.mailbox@hud.ac.uk](mailto:E.mailbox@hud.ac.uk).

<http://eprints.hud.ac.uk/>

## Wear resistant multilayer nanocomposite WC<sub>1-x</sub>/C coating on Ti-6Al-4V titanium alloy

W. Pawlak<sup>1</sup>, K.J. Kubiak<sup>\*2</sup>, B.G. Wendler<sup>1</sup>, T.G. Mathia<sup>3</sup>

<sup>1</sup>*Institute of Materials Science and Engineering, Technical University of Lodz, ul. Stefanowskiego 1/15, 90-924 Lodz, Poland*

<sup>2</sup>*University of Liverpool, School of Engineering, Liverpool L69 3GH, United Kingdom*

<sup>3</sup>*Laboratoire de Tribologie et Dynamiques des systèmes, CNRS, UMR 5513, Ecole Centrale de Lyon, 36 avenue Guy de Collongue, 69134 Ecully, France*

*\*Corresponding author: kris@kubiak.co.uk; k.kubiak@liverpool.ac.uk*

### Abstract

A significant improvement of tribological properties on Ti-6Al-4V has been achieved by developed in this study multilayer treatment method for the titanium alloys. This treatment consists of an intermediate 2 µm thick TiC<sub>x</sub>N<sub>y</sub> layer which has been deposited by the reactive arc evaporation onto a diffusion hardened material with interstitial O or N atoms by glow discharge plasma in the atmosphere of Ar+O<sub>2</sub> or Ar+N<sub>2</sub>. Subsequently, an external 0.3 µm thin nanocomposite carbon-based WC<sub>1-x</sub>/C coating has been deposited by a reactive magnetron sputtering of graphite and tungsten targets. The morphology, microstructure, chemical and phase compositions of the substrate material after treatment and coating deposition have been investigated with use of AFM, SEM, EDX, XRD, 3D profilometry and followed by tribological investigation of wear and friction analysis. An increase of hardness in the diffusion treated near-surface zone of the Ti-6Al-4V substrate has been achieved. In addition, a good adhesion between the intermediate gradient TiC<sub>x</sub>N<sub>y</sub> coating and the Ti-6Al-4V substrate as well as with the external nanocomposite coating has been obtained. Significant increase in wear resistance of up to 94% when compared to uncoated Ti-6Al-4V was reported. The proposed multilayer system deposited on the Ti-6Al-4V substrate is a promising method to significantly increase wear resistance of titanium alloys.

**Keywords:** Nanocomposite coating WC<sub>1-x</sub>/C, Titanium alloy Ti-6Al-4V, Low wear coating, Diffusion hardening.

## 1 Introduction

Titanium alloys due to its low weight, high strength and good biocompatibility are widely used in aerospace, military, chemical and medical industries [1, 2]. However its poor wear resistance and low tribo-corrosion performance has severely limited their use in engineering applications where friction is involved [3, 4]. High coefficient of friction [5] and tendency to seizure and catastrophic wear drastically decrease the reliability of titanium based components. To alleviate the problem several coating systems has been proposed in recent years based on the following treatment and deposition processes: Physical Vapour Deposition (PVD) [6, 7], Chemical Vapour Deposition (CVD) [8], thermal oxidation [9], ion implantation [10, 11] and more recently Micro Arc Oxidation (MAO) [12]. In most cases another problem can arise that due to hard coating deposited on soft substrate will create so called 'eggshell effect' and such coating will have tendency to collapse under the load [13]. Therefore, an intermediate layer or hardened surface is often required to increase the tribological performance of coating system [14]. Attempts to overcome these disadvantages by the surface and near-surface zone hardening with use of interstitial C, N, or O atoms don't improve its tribological properties [15]. Different treatment methods can be used to increase tribological performance [16]. Tribological properties of hard coating deposited on soft substrates has been widely investigated. Ramalho et al. [17, 18] and Zaidi et al. [19] reported the results of tribological investigations of coatings on steel, whereas Schmitt and Paulmier [20] on aluminium alloys.

In this paper new multilayer coating system  $WC_{1-x}/C$  deposited by the reactive magnetron sputtering on a diffusion hardened Ti-6Al-4V alloy is developed and tribological analysis of friction and wear response of such tribosystem under severe fretting loading conditions are presented.

## 2 Experimental procedure

Experimental part of the study consists of two stages. The first one is coating deposition and the second is tribological analysis. New nanocomposite carbon-based  $WC_{1-x}/C$  coating has been deposited on a monocrystalline (100) 7N Si(p) wafer and on a diffusion hardened Ti-6Al-4V substrate coated with an intermediate  $TiC_xN_y$  gradient layer. The basic properties of the nanocomposite coating have been

measured for the coating deposited on the Si substrate. Second stage of the study is devoted to tribological investigation (**Fig. 1**) carried out on nanocomposite coating deposited on the diffusion hardened Ti-6Al-4V titanium alloy.

## 2.1 Studied materials and coating deposition

Diffusion hardening process of the Ti-6Al-4V substrate with interstitial O or N atoms has been carried out with use of the glow discharge plasma in Ar+O<sub>2</sub> and Ar+N<sub>2</sub> atmosphere. Detailed description of this standard process can be found in a previous paper [21]. Increase of the surface micro-hardness, after diffusion hardening process, has been achieved from initial value of 350 HV<sub>0.2</sub> to 1000 HV<sub>0.2</sub>. The intermediate 2 μm thick TiC<sub>x</sub>N<sub>y</sub> coating has been deposited onto the hardened Ti-6Al-4V substrate by the reactive arc evaporation from a pure Ti cathode in the reactor described in [21]. An external nanocomposite carbon-based 0.3 μm thick WC<sub>1-x</sub>/C layer has been deposited by a reactive magnetron sputtering of graphite and tungsten targets in a vacuum chamber equipped with four magnetrons with circular targets (with diameter of 100 mm). Architecture of designed coating is presented in Fig. 1.

### Design of coating system

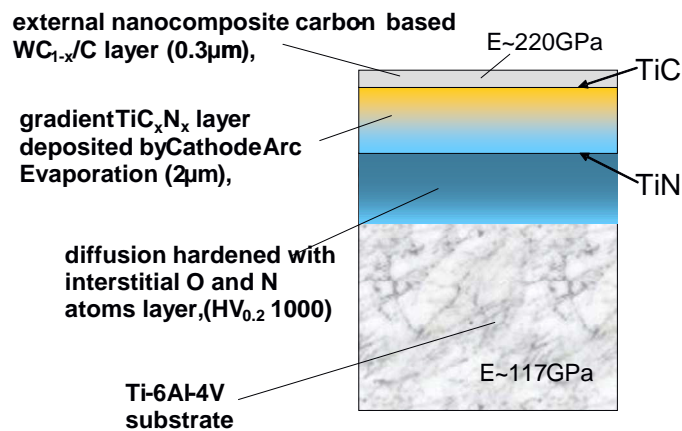


Fig. 1: Schematic diagram of developed multilayer coating system for titanium alloy.

The Ti-6Al-4V substrate has been placed in centre of a rotating table. In order to enhance ionization and increase reactivity of the plasma excited in the pure Ar, an additional electrode powered by 27.12 MHz RF generator and 0.6 kW linear amplifier has been mounted in the centre of the base plate of the vacuum chamber. The microstructure of nanocomposite WC<sub>1-x</sub>/C coating deposited on the Ti-6Al-4V is presented in [22]. More detailed description of the device and process parameters can be found in [23]. As mentioned above, two different materials have been used as

the substrates: pure monocrystalline (100) 7N Si(p) wafer, and a rectangular prism (6x18x18 mm) of Ti-6Al-4V titanium alloy.

Table 1: Parameters of reactive magnetron sputtering deposition process.

Process parameters	Substrate material	
	monocrystalline (100) 7N Si(p) wafer	Diffusion hardened Ti-6Al-4V with 2 $\mu\text{m}$ $\text{TiC}_x\text{N}_y$ intermediate gradient layer
Time of Deposition (ks)	3.8	3.9
Bias - Potential (V)	-50	-50
Bias - Current (A)	0.05	0.04
Ar flow ( $\text{mm}^3\text{s}^{-1}$ )	470	420
Pressure (Pa)	0.03	0.025
Total power of 3 magnetrons with C targets (kW)	3.35	2.83
Power of magnetron with W target (kW)	1.15	0.8

## 2.2 Tribological analysis of friction and wear

Analysis of friction and wear behaviour for all: untreated, hardened and coated tribosystems have been performed on Ti-6Al-4V alloy substrates. The reciprocating tribotester with small amplitude sinusoidal displacements has been used. Tribological tests have been carried out in a configuration sphere/plane, where diameter of the sphere was 12.7 mm. In order to reduce wear of the sphere counterbody, an AISI 52100 sphere was used. The normal load in the contact has been kept constant during the tests and applied normal force was  $P=20$  N. Displacement in the contact have been imposed by an electro-dynamic shaker. Four different amplitude levels of sinusoidal displacement have been used (25, 50, 75 and 100  $\mu\text{m}$ ) and therefore energy wear coefficient ( $\alpha$ ) of the system can be calculated [24]. Advantage of the energy wear approach is that it is quasi-independent of the used contact geometry and therefore more universal when used to predict or compare the wear kinetic on different systems. The test frequency was kept constant at  $F=10\text{Hz}$ . Test duration has been set to last for 10000 cycles. The schematic diagram of experimental device is presented in Fig. 2. During the tests, values of tangential force  $Q$ , normal force  $P$  and relative displacement  $\delta$  have been recorded. All specimens have been ultrasonically cleaned in acetone and ethanol before the tests. Experiments were

performed in laboratory conditions at constant temperature of 23+/-1°C and relative humidity 43+/-5%.

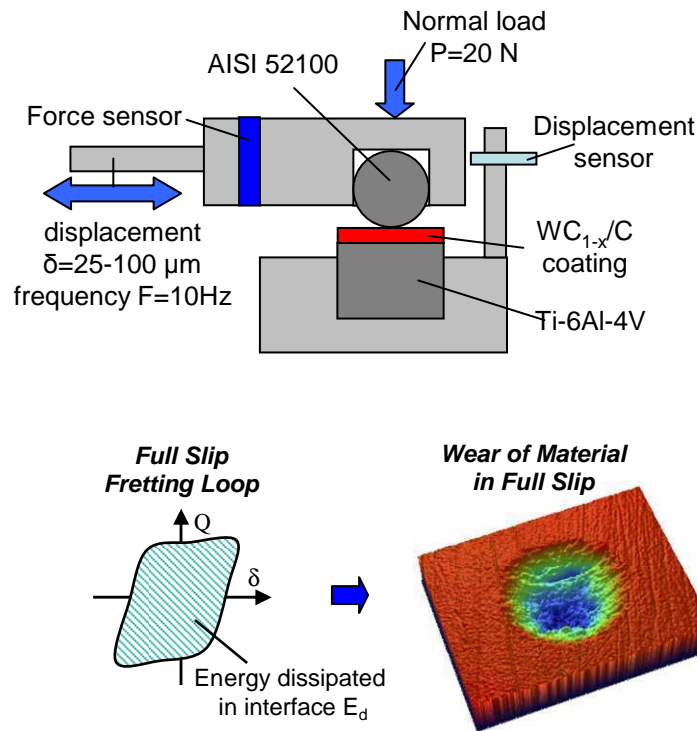


Fig. 2: Schematic diagram of experimental device for sphere/plane configuration, illustration of measured parameters and wear damage observed in gross slip regime [25].

Total amount of dissipated energy ( $E_d$ ) during the test can be calculated by integration of fretting loops area over total number of cycles:  $\sum_1^N E_d(Q, \delta)$ . The wear volume of sphere ( $V_s$ ) and plane ( $V_p$ ) specimens have been measured by a 3D optical interferometer Veeco NT3300. To analyze friction behaviour, coefficient of friction calculated as ratio of tangential force amplitude and normal force ( $\mu=Q^*/P$ ) can be analysed and average value of coefficient of friction for a given test can be calculated as:  $\mu_a = \sum_1^N \frac{1}{N} \cdot \frac{Q^*}{P}$ , where N is the total number of cycles. More detailed description of friction analysis can be found in previous publication [26].

### 3 Results and discussion

Microstructure and mechanical properties of new nanocomposite carbon based WC<sub>1-x</sub>/C coating have been analysed for coating deposited on a silicon substrate used as a reference material and tribological behaviour has been tested on the coating deposited on a diffusion hardened Ti-6Al-4V substrate.

### 3.1 Coating composition

An example of SEM morphology of cross-section fracture of  $WC_{1-x}/C$  coating deposited on the silicon substrate is presented in Fig. 3a. The thickness of coating is homogenous and is in the order of  $0.3 \mu\text{m}$ . The AFM topography is presented in Fig. 3b, measured average roughness was  $R_a=1.35 \text{ nm}$ . AFM analysis confirms that obtained surface is uniform and isotropic. For the coating system deposited onto Ti-6Al-4V substrate polished with 2500 grit abrasive sandpaper, the average roughness measured by 3D interferometer was  $R_a=95.6 \text{ nm}$ . The characteristic "orange skin" surface can be observed only on SEM image presented in Fig. 10. This effect can be caused by an initial surface roughness ( $R_a=86.4 \text{ nm}$ ) and microstructure of the Ti-6Al-4V substrate.

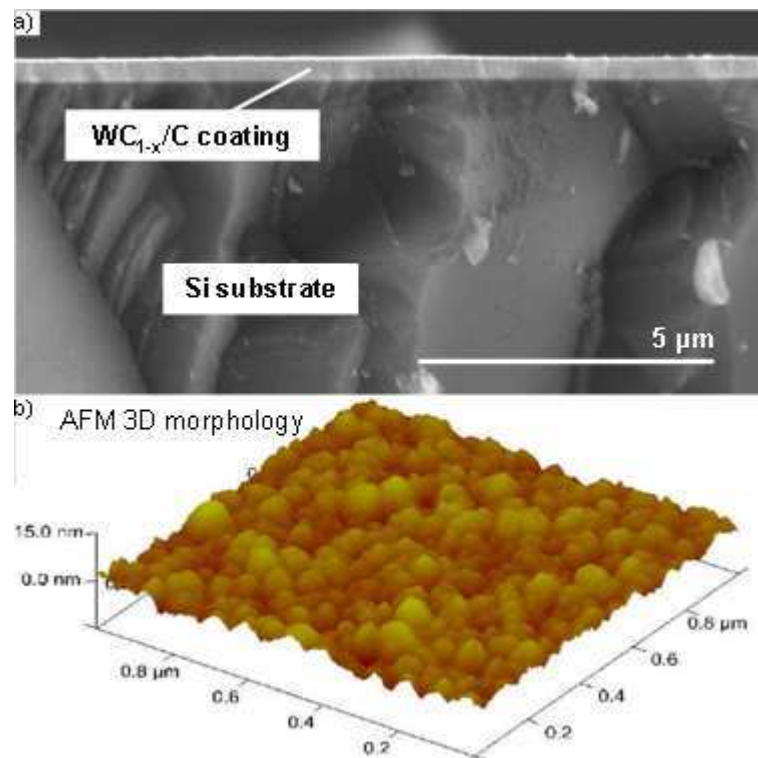


Fig. 3: Characterization of the new  $WC_{1-x}/C$  coating deposited by reactive magnetron sputtering on the silicone substrate, a) SEM image of coating fracture and b) AFM morphology of coating surface [23].

A standard XRD phase analysis of the coating has been carried out and the spectrum of the diffracted beams is plotted in Fig. 4. Chemical compositions of the coatings measured by EDX technique is 53 (at.%) of C and 47 (at.%) of W.

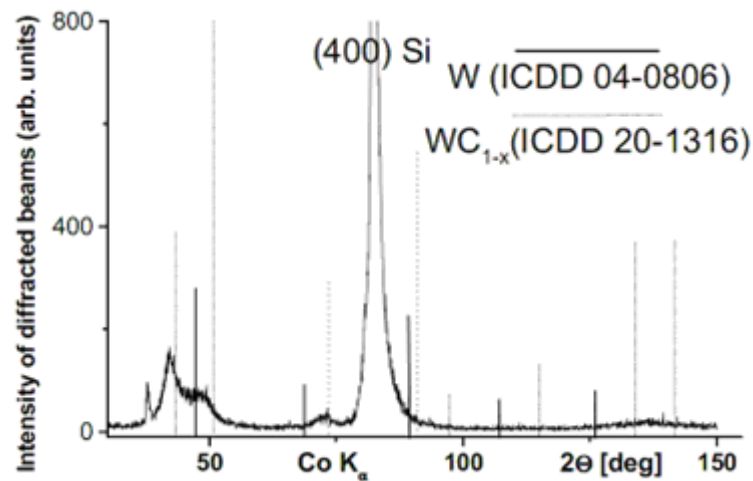


Fig. 4: Results of X-ray phase analysis of  $WC_{1-x}/C$  coating deposited on the silicone substrate, nanocrystalites of  $WC_{1-x}$  phase in an amorphous carbonaceous a-C matrix [23].

### 3.2 Friction and wear resistance analysis

The friction and wear analysis have been performed for classical sphere/plane contact configuration at small displacement amplitudes (25 - 100  $\mu\text{m}$ ). The reciprocating tribotester have been used to carry out tribological experiments. Examples of results for coefficient of friction (COF) evolution during the test are presented in Fig. 5. The highest value can be noted for untreated substrate, slightly lower and very similar evolution can be observed for both the hardened and the coated tribosystems. Proposed multilayer system does not decrease the coefficient of friction significantly, which can be very suitable for many practical applications where the tangential forces or shear stress have to be transmitted through the contact (i.e. screw joints, rotor blades ...). An average value of coefficient of friction  $\mu_a$  for all tested conditions is summarized in Table 2.



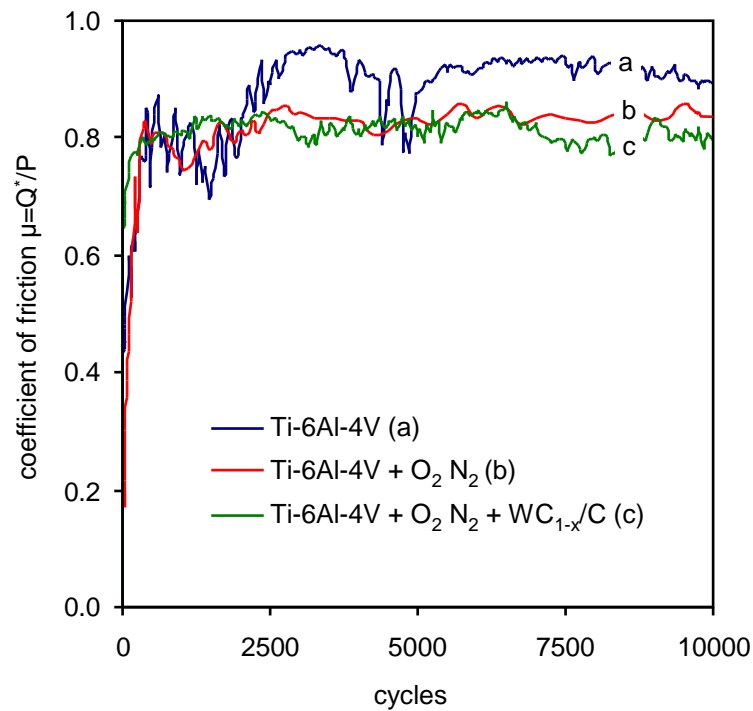


Fig. 5: Analysis of friction evolution for untreated (Ti-6Al-4V), hardened (Ti-6Al-4V + O<sub>2</sub> N<sub>2</sub>) and coated (Ti-6Al-4V + O<sub>2</sub> N<sub>2</sub> + WC<sub>1-x</sub>/C) in sphere/plan contact configuration, displacement amplitude  $\delta^* = 50 \mu\text{m}$ .

In the tribosystems with high value of coefficient of friction, also high wear rate can be expected. Contact between Ti-6Al-4V and 52100 is characterized by high value of coefficient of friction similar to Ti-6Al-4V // Ti-6Al-4V contact with value around ~0.9 [27]. Wear analysis, also was conducted for untreated, hardened and coated contact configurations. In first case, for untreated Ti-6Al-4V // 52100 contact (Fig. 6), severe wear rate and exponential relationship between cumulated dissipated energy  $\Sigma E_d$  and wear volume of the plane  $V_p$  can be observed. These results confirm the investigation and results reported by Fridrici [28], where similar relation in Ti-6Al-4V // Ti-6Al-4V contact has been reported.

For uncoated tribosystem the wear observed on a sphere counterbody is decreasing for higher value of dissipated energy  $E_d$  (higher displacement amplitude  $\delta^*$ ). This effect is related to high adhesion of titanium alloy and material transfer phenomenon from the plane to the sphere specimen. Therefore, adhesive wear mechanism for uncoated system can be confirmed. This hypothesis can be supported by EDX analysis performed on the sphere (Fig. 10, Sphere T15). Titanium (Ti) particles has been detected in the fretting scar on the sphere sample, however on plane specimen (Plane T15) only traces of the iron (Fe) particles has been found. This confirms that transfer of material for an uncoated tribosystem has been observed from plane Ti-

6Al-4V to the sphere 52100 material. This phenomenon leads to a very high wear rate of Ti-6Al-4V substrate.

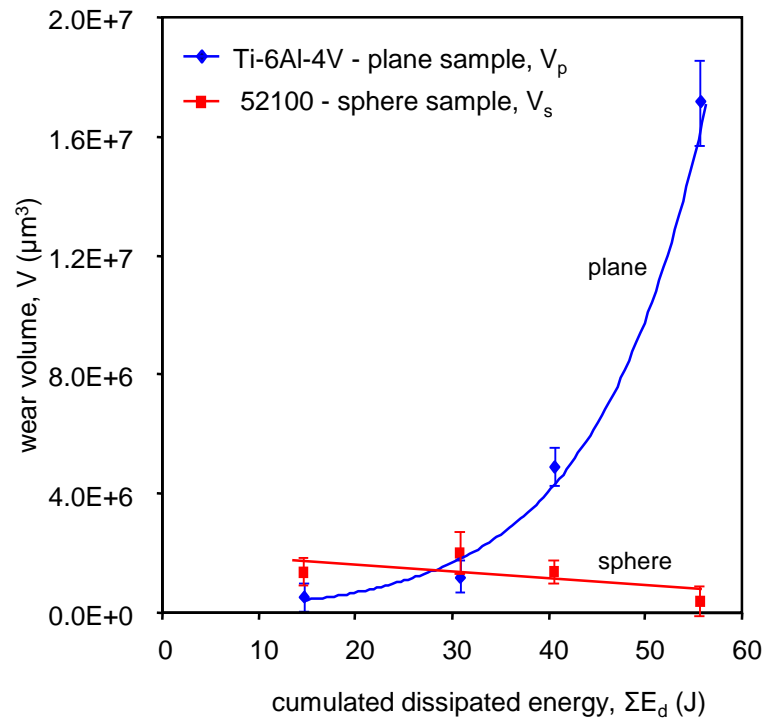


Fig. 6: Evolution of wear volume ( $V$ ) as a function of cumulated energy dissipated in contact during the test  $\Sigma E_d$ , for uncoated Ti-6Al-4V // 52100 tribosystem.

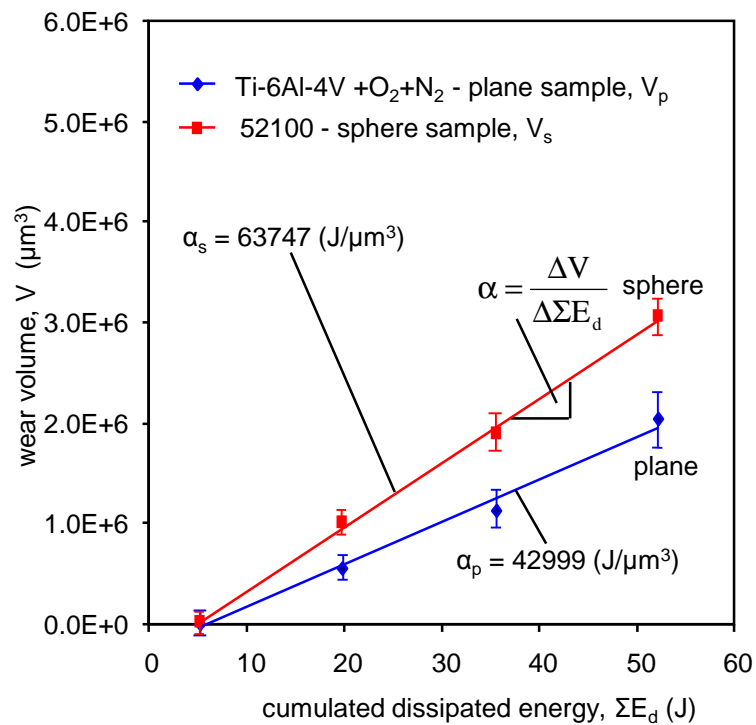


Fig. 7: Linear evolution of wear volume ( $V$ ) as a function of cumulated energy dissipated in contact during the test  $\Sigma E_d$ , for the diffusion hardened Ti-6Al-4V alloy against 52100 sphere.

The results of wear analysis for diffusion hardened titanium alloy (Ti-6Al-4V + O<sub>2</sub> N<sub>2</sub>) is presented in Fig. 7. In this case, linear evolution of wear volume can be observed for both, plane and sphere specimens. The strengthened material presents much better wear resistance, while keeping the coefficient of friction at similar level. Wear mechanism change from adhesive to abrasive, some layer of Fe particles was detected on titanium sample, but there is no transfer of titanium material onto the sphere specimen. For this linear evolution a wear rate coefficient based on energy description can be calculated for the plane  $\alpha_p=42999 \text{ J}/\mu\text{m}^3$  and for the sphere counterbody  $\alpha_s=63747 \text{ J}/\mu\text{m}^3$ . One can note that, evolution of wear for the plane specimen does not intersect the origin of the graph, this phenomenon is related to the energy required to activate the wear degradation process. This phenomenon is relatively common in this kind of tribological test and can be observed for different materials [25] and for different surface treatments [29]. It is usually associated with the tribologically transformed microstructure of material layer, but related physics is still not fully understood and is yet to be unveiled.

The third case is hardened titanium alloy with the transitional gradient coating (TiC<sub>x</sub>N<sub>y</sub>) and an external nanocomposite WC<sub>1-x</sub>/C coating deposited by reactive magnetron sputtering of graphite and tungsten targets. The results of wear analysis are presented in Fig. 8. Significant improvement of more than an order of magnitude in wear rate value, have been achieved for the plane material with energy wear coefficient  $\alpha_p=2393 \text{ J}/\mu\text{m}^3$ . Also further reduction in wear rate of sphere counterbody have been observed with  $\alpha_s=36266 \text{ J}/\mu\text{m}^3$ . This reduction could be attributed to thick layer of Fe atoms adhered on plane specimen (Fig. 10 Plane TW12) which slows down the abrasive wear kinetics. In this case, there is no transfer of Ti particles on the sphere specimen (Fig. 10 Sphere TW12). Wear mode in this case also changed from adhesive to abrasive due to higher hardness (1000 HV<sub>0.2</sub>) of titanium material after hardening treatment and better resistance to shear stress.

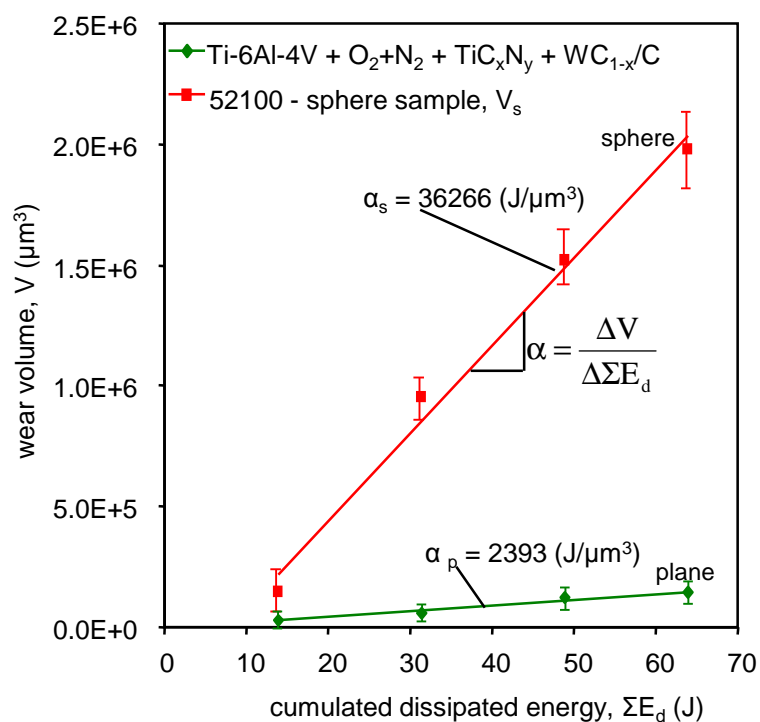


Fig. 8: Linear evolution of wear volume ( $V$ ) as a function of cumulated energy dissipated in contact during the test  $\Sigma E_d$ , for the multilayer system on Ti-6Al-4V alloy with external nanocomposite carbon-based  $WC_{1-x}/C$  layer against 52100 sphere.

For large displacement amplitude ( $\delta^* = 100 \mu\text{m}$ ) the relatively thin coating system of  $0.3 \mu\text{m}$  of  $WC_{1-x}/C$  and  $2 \mu\text{m}$  of  $TiC_xN_y$  have been worn and the Ti-6Al-4V substrate has been reached. However, for the smaller amplitudes of displacement the maximum depth of wear measured on plane surfaces remains lower than  $1.8 \mu\text{m}$  suggesting that only external nanocomposite coating was removed due to very severe contact conditions. Therefore, it is important to note that all three processes: diffusion hardening with interstitial O and N atoms, intermediate  $TiC_xN_y$  gradient coating and top layer of nanocomposite  $WC_{1-x}/C$  coating are required to guarantee such a significant wear resistance improvement as achieved in this study. Results of wear analysis taking into account total wear volume ( $V_t = V_p + V_s$ ) observed on the plane and on the sphere counterparts have been presented in Fig. 9 and summarized in Table 2. For coated tribosystem a significant reduction in the wear rate of 94% in comparison to uncoated Ti-6Al-4V can be observed for  $\delta^* = 25 \mu\text{m}$  displacement amplitude and 99% for  $\delta^* = 100 \mu\text{m}$ . This spectacular wear rate reduction is a result of multilayer treatment combining substrate diffusion hardening, the intermediate  $TiC_xN_y$  coating and the top nanocomposite  $WC_{1-x}/C$  coating deposition.

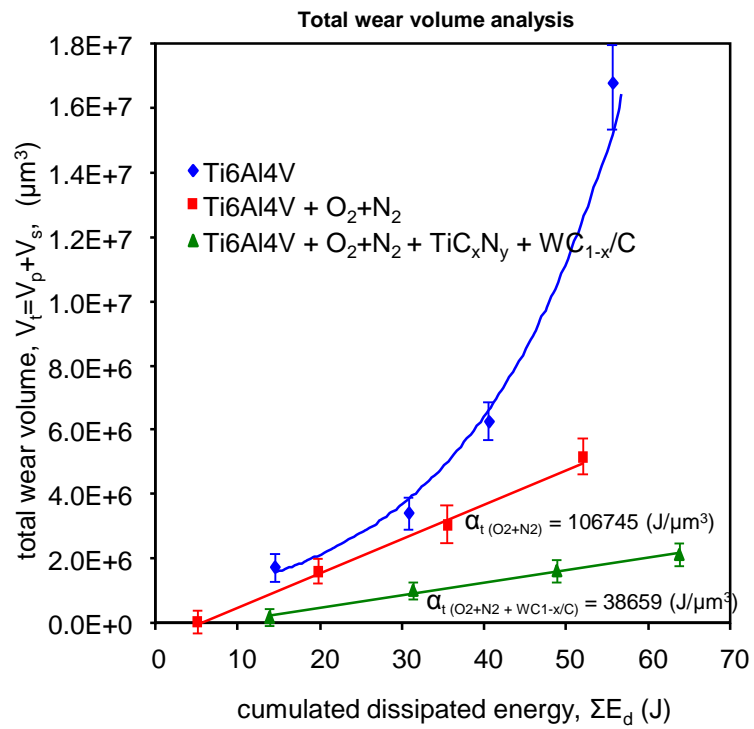


Fig. 9: Evolution of total wear volume ( $V_t = V_p + V_s$ ) as a function of cumulated dissipated energy  $\Sigma E_d$ .

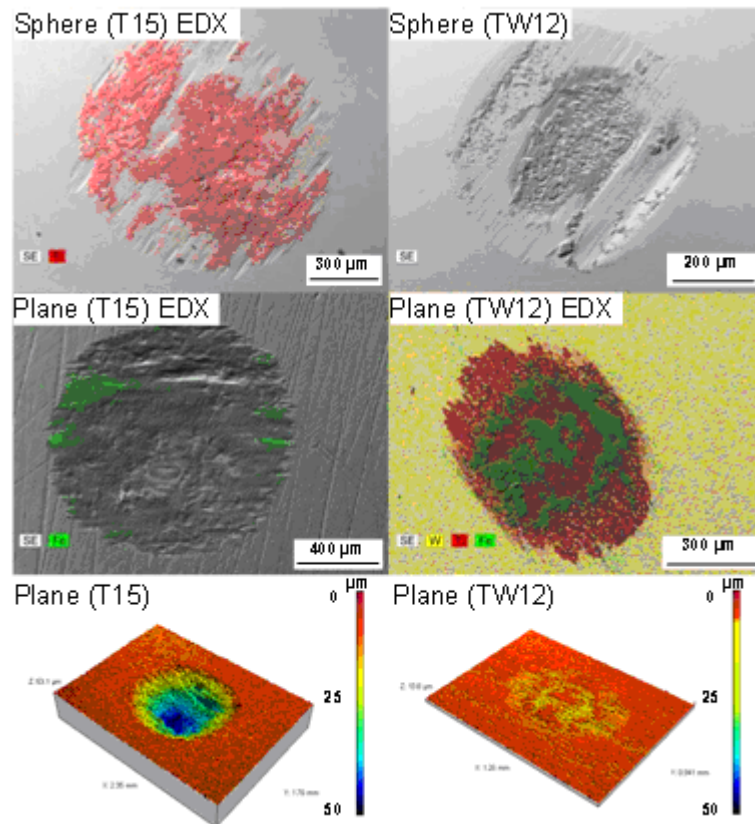


Fig. 10: Wear scar: SEM images and 3D morphologies of uncoated Ti-6Al-4V // 52100 tribosystem and multilayer system on Ti-6Al-4V alloy with an external nanocomposite carbon-based  $\text{WC}_{1-x}/\text{C}$  layer against 52100 sphere (displacement amplitude  $\delta^* = 100 \mu\text{m}$ ).

Table 2: Wear and friction results of experimental tribological analysis.

Sphere material 52100 (D=12.7 mm), Frequency F=10 Hz, Normal force P=20 N							
Test No.	Plane Material	Displ. amplitude	Averaged COF $\mu_a = \sum_{i=1}^N \frac{1}{N} \cdot \frac{Q_i^*}{P}$	Cumulated Dissipated Energy	Wear Volume of sphere ( $V_s$ ) and plane ( $V_p$ ) specimens		Maximum wear depth on plane specimen
		$\delta^*$ ( $\mu\text{m}$ )		$\Sigma E_d$ (J)	$V_s$ ( $\mu\text{m}^3$ )	$V_p$ ( $\mu\text{m}^3$ )	$H_{\text{max}}$ ( $\mu\text{m}$ )
T18	Ti-6Al-4V	25	0.85	14.657	1.212E+06	5.117E+05	6.1
T17		50	0.87	30.939	2.259E+06	1.165E+06	10.7
T16		75	0.85	40.620	1.376E+06	4.891E+06	20.6
T15		100	0.84	55.782	3.695E+05	1.716E+07	36.3
TN43	Ti-6Al-4V +N <sub>2</sub> O <sub>2</sub>	25	0.74	5.216	2.00E+04	1.09E+03	0.59
TN44		50	0.82	19.826	1.00E+06	5.46E+05	3.1
TN45		75	0.89	35.688	1.90E+06	1.09E+06	8.1
TN46		100	0.88	51.175	3.05E+06	2.06E+06	10.0
TW19	Ti-6Al-4V +N <sub>2</sub> O <sub>2</sub> +WC <sub>1-x</sub> /C	25	0.75	13.842	1.456E+05	3.062E+04	1.7
TW14		50	0.81	31.406	9.511E+05	5.842E+04	1.6
TW13		75	0.84	48.969	1.522E+06	1.210E+05	1.8
TW12		100	0.81	63.867	1.976E+06	1.432E+05	1.9

## 4 Conclusions

The new multilayer system of nanocomposite WC<sub>1-x</sub>/C coating deposited on a diffusion hardened Ti-6Al-4V has been developed. Tribological performance of this new system has been investigated under severe fretting contact conditions and the results of friction and wear analysis are reported.

Developed multilayer coating system for titanium alloy consists of the following layers:

- 1) diffusion hardened layer with interstitial O and N atoms obtained by glow discharge plasma in the atmosphere of Ar+O<sub>2</sub> and Ar+N<sub>2</sub>,
- 2) intermediate layer of 2  $\mu\text{m}$  thick TiC<sub>x</sub>N<sub>y</sub> coating deposited by reactive arc evaporation,
- 3) external layer of 0.3  $\mu\text{m}$  thick nanocomposite carbon-based WC<sub>1-x</sub>/C coating deposited by the reactive magnetron sputtering of the graphite and tungsten targets.

Based on the result of experimental analysis, the following conclusions can be formulated:

- Significant reduction of wear rate of titanium material (up to 94% less wear volume observed) has been achieved by developed multilayer coating system,
- Adhesive wear mechanism observed for untreated surface changed to abrasive wear mechanism after diffusion hardening by O<sub>2</sub> and N<sub>2</sub> atoms.
- Similar coefficient of friction was maintained after the coating system deposition and only small drop of about 10% was observed to average value of  $\mu_a=0.8$  for the coated titanium alloy // 52100 system.

## 5 References

---

- [1] ASM Handbook, Titanium and Titanium Alloy Castings, vol. 2, ASM, International, 1998. p. 634 - 646.
- [2] W.F. Brown, H. Mindlin, C.Y. Ho, Aerospace Structural Metals Handbook, vol. 4, CINDAS/USAF Perdue University, 1997, p. 12.
- [3] K.G. Budinski, Tribological properties of titanium alloys, *Wear* 151 (1991) p. 203 - 217.
- [4] L. Ceschini, E. Lanzoni, C. Martini, D. Prandstraller, G. Sambogna, Comparison of dry sliding friction and wear of Ti6Al4V alloy treated by plasma electrolytic oxidation and PVD coating, *Wear* 264 (2008), p. 86 - 95.
- [5] X. Huang, R.W. Neu, High-load fretting of Ti-6Al-4V interfaces in point contact, *Wear* Volume 265, Issues 7-8 (2008) p. 971 - 978.
- [6] C. Martini, L. Ceschini, A comparative study of the tribological behaviour of PVD coatings on the Ti-6Al-4V alloy, *Tribology International* 44 (3) (2011) p. 297-308.
- [7] J.C. Avelar-Batista, E. Spain, G.G. Fuentes, A. Sola, R. Rodriguez, J. Housden, Triode plasma nitriding and PVD coating: A successful pre-treatment combination to improve the wear resistance of DLC coatings on Ti6Al4V alloy, *Surface & Coatings Technology* 201 (2006) p. 4335 - 4340.
- [8] Y. Balcaen, N. Radutoiu, J. Alexis, J.D. Beguin, L. Lacroix, D. Samelot, C. Vahlas, Mechanical and barrier properties of MOCVD processed alumina coatings on Ti6Al4V titanium alloy, *Surface & Coatings Technology* 206 (7) (2011) p. 1684 - 1690.
- [9] E. Arslan, Y. Totik, E. Demirci, A. Alsaran, Influence of Surface Roughness on Corrosion and Tribological Behavior of CP-Ti After Thermal Oxidation Treatment, *Journal of Materials Engineering and Performance*, 19 (3) (2010) p. 428 - 433.
- [10] S.W. Jiang, B. Jiang, Y. Li, Y.R. Li, G.F. Yin, C.Q. Zheng, Friction and wear study of diamond-like carbon gradient coatings on Ti6Al4V substrate prepared by plasma source ion implant-ion beam enhanced deposition, *Applied Surface Science* 236 (1-4) (2004) p. 285 - 291.
- [11] S.M. Johns, T. Bell, M. Samandi, G.A. Collins, Wear resistance of plasma immersion ion implanted Ti6Al4V, *Surface & Coatings Technology* 85 (1-2) (1996) p. 7 - 14.
- [12] A.L. Yerokhin, X. Nie, A. Leyland, A. Matthews, Characterisation of oxide films produced by plasma electrolytic oxidation of a Ti-6Al-4V alloy, *Surface & Coatings Technology* 130 (2-3) (2000) p. 195 - 206.
- [13] T. Grogler, O. Plewa, S.M. Rosiwal, R.F. Singer, CVD diamond films as protective coatings on titanium alloys, *International Journal of Refractory Metals & Hard Materials* 16 (1998) 217-222.
- [14] E. Arslan, Y. Totik, E. E. Demirci, I. Efeoglu, Wear and adhesion resistance of duplex coatings deposited on Ti6Al4V alloy using MAO and CFUBMS, *Surface & Coatings Technology* 214 (2013) p.1-7.

- [15] Bin Tang, Pei-Qiang Wu, Xiu-Yan Li, Ai-Lan Fan, Zhong Xu, J. -P. Celis, Tribological behavior of plasma Mo-N surface modified Ti-6Al-4V alloy, *Surface and Coatings Technology* Volume 179, Issues 2-3 (2004) p. 333-339.
- [16] C. Rapiejko, M. Gazicki-Lipman, L. Klimek, H. Szymanowski, M. Strojek, RF plasma deposition of thin Si x Ge y C z : H films using a combination of organometallic source materials, *Thin Solid Films*, 469–470 (2004) p. 173–177.
- [17] A. Ramalho, A. Cavaleiro, A. S. Miranda, M. T. Vieira, Failure modes observed on worn surfaces of W-C-Co sputtered coatings, *Surface and Coatings Technology*, Volume 62, Issues 1-3 (1993) p. 536-542.
- [18] A. Ramalho, M.T. Vieira, A.S. Miranda, Tribological behaviour of W-C-Co coatings, *Journal of Materials Processing Technology*, Volume 31, Issues 1-2 (1992) p. 225-234.
- [19] H. Zaidi, J. Frene, A. Senouci, M. Schmitt, D. Paulmier, Carbon surface modifications during sliding test and friction behavior of carbon thin films against XC 48 steel, *Surface and Coatings Technology*, Volume 123, Issues 2-3 (2000) p. 185-191.
- [20] M. Schmitt, D. Paulmier, Tribological behaviour of diamond coatings sliding against Al alloys, *Tribology International*, Volume 37, Issue 4 (2004) p. 317-325.
- [21] B.G. Wendler, W. Pawlak: Low friction and wear resistant coating systems on Ti6Al4V alloy. *Journal of Achievements in Materials and Manufacturing Engineering* Volume 26 Issue 2, (2008) p. 207-210.
- [22] T. Moskalewicz, B. Wendler, A. Czyrska-Filemonowicz, Microstructural characterisation of nanocomposite nc-MeC/a-C coatings on oxygen hardened Ti-6Al-4V alloy, *Material Characterization* volume 61 (2010) p. 959-968.
- [23] B.G. Wendler, P. Nolbrzak, W. Pawlak, A. Rylski: Structure and properties of WC<sub>1-x</sub>/C coatings deposited by reactive magnetron sputtering on ASP2023 HSS steel and monocrystalline Si substrates, *Materials Engineering* 6 Volume 166 (2008) p. 640-645, Sigma-Not Publishing House, ISSN 0208-6247.
- [24] S. Fouvry, Ph. Kapsa, H. Zahouani and L. Vincent, Wear analysis in fretting of hard coatings through a dissipated energy concept. *Wear* Volume 203–204 (1997) p. 393-403.
- [25] K.J. Kubiak, T.W. Liskiewicz, T.G. Mathia, Surface morphology in engineering applications: Influence of roughness on sliding and wear in dry fretting, *Tribology International*, vol. 44 (2011) p.1427-1432.
- [26] K.J. Kubiak, T.G. Mathia, Influence of roughness on contact interface in fretting under dry and boundary lubricated sliding regimes, *Wear*, Vol. 267, Issues 1-4 (2009) p. 315-321.
- [27] X. Huang, R.W. Neu, High-load fretting of Ti-6Al-4V interfaces in point contact, *Wear* Volume 265, Issues 7-8 (2008) p. 971-978.
- [28] V. Fridrici, S. Fouvry, Ph. Kapsa, Effect of shot peening on the fretting wear of Ti-6Al-4V, *Wear*, Volume 250, Issues 1-12 (2001) p. 642-649.
- [29] K. Kubiak, S. Fouvry, A.M. Marechal, A practical methodology to select fretting palliatives: Application to shot peening, hard chromium and WC-Co coatings, *Wear*, Volume 259, Issues 1-6 (2005) p. 367-376.