



# University of HUDDERSFIELD

## University of Huddersfield Repository

Yang, H., Zhao, M., Gu, Z.L., Jin, L.W. and Chai, John

A further discussion on the effective thermal conductivity of metal foam: An improved model

### Original Citation

Yang, H., Zhao, M., Gu, Z.L., Jin, L.W. and Chai, John (2015) A further discussion on the effective thermal conductivity of metal foam: An improved model. *International Journal of Heat and Mass Transfer*, 86. pp. 207-211. ISSN 0017-9310

This version is available at <http://eprints.hud.ac.uk/23831/>

The University Repository is a digital collection of the research output of the University, available on Open Access. Copyright and Moral Rights for the items on this site are retained by the individual author and/or other copyright owners. Users may access full items free of charge; copies of full text items generally can be reproduced, displayed or performed and given to third parties in any format or medium for personal research or study, educational or not-for-profit purposes without prior permission or charge, provided:

- The authors, title and full bibliographic details is credited in any copy;
- A hyperlink and/or URL is included for the original metadata page; and
- The content is not changed in any way.

For more information, including our policy and submission procedure, please contact the Repository Team at: [E.mailbox@hud.ac.uk](mailto:E.mailbox@hud.ac.uk).

<http://eprints.hud.ac.uk/>

# A further discussion on the effective thermal conductivity of metal foam: an improved model

H. Yang<sup>a</sup>, M. Zhao<sup>b</sup>, Z.L. Gu<sup>b</sup>, L.W. Jin<sup>b\*</sup>, J.C. Chai<sup>c</sup>

<sup>a</sup>*School of Energy and Power Engineering, Xi'an Jiaotong University, Xi'an, Shaanxi 710049, China*

<sup>b</sup>*School of Human Settlements and Civil Engineering, Xi'an Jiaotong University, Xi'an, Shaanxi 710049, China*

<sup>c</sup>*Department of Engineering and Technology, School of Computing and Engineering, University of Huddersfield, Queensgate, Huddersfield, HD1 3DH, U.K.*

## Abstract

In this study, we explain the causes and effects of the geometrical impossible result encountered in the widely adopted tetrakaidecahedron model (Boomsma and Poulikakos, 2001; Dai et al., 2010) for the effective thermal conductivities (ETCs) of metal foam. The geometrical impossible result is successfully eliminated by accounting for the size variation of the node with porosity. The improved model provides predictions of ETCs that are more precise than available models. For aluminum foams ( $k_s = 218 \text{ W m}^{-1}\text{K}^{-1}$ ) using water and air as fluid media, the relative root-mean-square (RMS) deviation of the present predictions from the experimental data is about 5.3%; for the reticulated vitreous carbon (RVC) foams ( $k_s = 8.5 \text{ W m}^{-1}\text{K}^{-1}$ ), the relative RMS deviation is about 7.4%.

**Key words:** effective thermal conductivity; foam structure; node size; deviation; improved model.

## Nomenclature

a	foam ligament radius (m)	L	ligament length (m)
d	dimensionless foam ligament radius	R	thermal resistance ( $\text{m}^2 \text{ K W}^{-1}$ )
e	dimensionless cubic node length	r	cubic node length (m)
f	function	V	volume ( $\text{m}^3$ )
k	thermal conductivity ( $\text{W m}^{-1} \text{ K}^{-1}$ )		

## Subscripts

A	unit cell layer	D	unit cell layer
B	unit cell layer	eff	effective
C	unit cell layer	f	fluid

i A, B, C, D s solid

21 Greek symbol

$\varepsilon$  porosity

## 22 **1. Introduction**

23 High-porosity metal foams are promising materials for thermal management applications.  
24 Since the effective thermal conductivity (ETC) is one of their most important thermal properties,  
25 an accurate evaluation of it becomes especially important. Studies on modeling the ETC of metal  
26 foams have been carried out numerically [1-3], experimentally [4-6] and analytically [5-12].  
27 Among these approaches, the analytical approaches are less time consuming but more universal,  
28 and have attracted the attention of investigators. A review of the analytical approaches for  
29 prediction of the ETC has been conducted by Coquard and Baillis [13, 14], and Randrianalisoa  
30 and Baillis [15].

31 One of the most widely used analytical approaches was developed by Boomsma and  
32 Poulikakos [10] who first used the idealized three dimensional tetrakaidecahedron model to  
33 predict the metal foam ETC. Predictions were reported to accurately match the experimental data.  
34 However, Dai et al. [11] pointed out a few problems in their work. Dai et al. [11] extended the  
35 model by accounting for the ligament orientation. Predictions of the extended model were  
36 compared with the experimental data [5], and a relative RMS deviation of about 12% was  
37 observed. The deviation indicated that there was still room for improvement. In addition, results  
38 obtained in Ref. [11] showed that, as the porosity decreased, the diameter of the ligament became  
39 longer than the length of the node, which led to a geometrical impossible result. The diameter  
40 of the ligament should be shorter than the length of the node (see Fig. 1), which was a basic  
41 assumption in the development of the model.

42 In this paper, the tetrakaidecahedron model originally proposed by Boomsma and Poulikakos  
43 [10] and later extended by Dai et al. [11] is first discussed. The causes and effects of the  
44 geometrical impossible results are examined and explained. The model is further improved by  
45 accounting for the size variation of the nodes. We then show that the geometrical impossible  
46 results are eliminated. Lastly, predictions of our improved model are compared with several other  
47 analytical solutions as well as experimental data available in literature. It is shown that the current  
48 model has a steadily high precision in predicting the ETC of high porosity foams with a wide  
49 range of phase conductivity ratios ( $k_s / k_f$ ).

## 50 **2. Calculation of the Effective Thermal Conductivity**

51 It is important to note that, for a better understanding of the present discussion, reader should  
52 be familiar with the analytical approaches developed by Boomsma and Poulikakos [10], and Dai  
53 et al. [11]. Therefore, in this part of the discussion, we give a brief review of how the ETC is  
54 calculated using their approaches. For more detailed discussions, reader may refer to Refs. [10,  
55 11].

### 56 **2.1. The Unit Cell of the Tetrakaidecahedron Model**

57 Cubic nodes and cylindrical ligaments were used to represent the actual components of the  
58 foam network, as is shown in Fig. 1(a). As the lump shape at the ligament intersection varies with  
59 the foam porosity, the simplified spherical geometry is adopted for various porosities based on the  
60 fact that the lump volume has more significant effect on ETC than its shape does. The length of  
61 the node is  $r$ , the radius of the ligament is  $a$  and its length is  $L$  (from node center to node  
62 center). Based on the symmetry of the idealized model and one-dimension heat conduction along  
63 the  $z$  axis, a representative unit cell which contains all geometrical characteristics of the

64 tetrakaidecahedron model was selected. The height of the unit cell in the  $z$  direction is  
 65  $L\sqrt{2}/2$ . While the length of the other two sides in the  $x-y$  plane are both  $L\sqrt{2}$ . It can be  
 66 proved that the ETC of the selected unit cell is equal to that of the tetrakaidecahedron model.

## 67 2.2. Effective Thermal Conductivity

68 In order to calculate the ETC, the unit cell is divided into four distinctive vertical layers along  
 69 the  $z$  axis, namely A, B, C and D, as is shown in Fig. 1(b). The heights of the four layers are:

$$70 L_A = a, L_B = r/2 - a, L_C = L\sqrt{2}/2 - r \text{ and } L_D = r/2 .$$

71 According to the extend model (accounting for the ligament orientation) proposed by Dai et al.  
 72 [11], the thermal resistance of each layer is

$$73 R_A = \frac{4dL}{[2e^2 + \pi d(1-e)]k_s + \{4 - [2e^2 + \pi d(1-e)]\}k_f} \quad (1a)$$

$$74 R_B = \frac{(e-2d)L}{e^2k_s + (2-e^2)k_f} \quad (1b)$$

$$75 R_C = \frac{2(\sqrt{2}-2e)L}{\pi d^2k_s\sqrt{2} + 2(2-\pi d^2\sqrt{2})k_f} \quad (1c)$$

$$76 R_D = \frac{2eL}{e^2k_s + (4-e^2)k_f} \quad (1d)$$

77 where  $k_s$  is the thermal conductivity of the solid and  $k_f$  is thermal conductivities of the fluid,

78  $d$  and  $e$  are non-dimensional parameters, defined as:  $d \equiv a/L$  and  $e \equiv r/L$ .

79 The overall thermal conductivity is calculated by assuming that the thermal resistances of the  
 80 layers are connected in series. Based on the Fourier law of heat conduction, the ETC can be  
 81 written as

$$82 k_{\text{eff}} = \frac{L_A + L_B + L_C + L_D}{R_A + R_B + R_C + R_D} \quad (2)$$

83 Eq. (2) can be written as

$$84 k_{\text{eff}} = f_1(d, e) \quad (3)$$

85 here,  $f_1$  is a known function.

86 The porosity  $\varepsilon$ , which is defined as the ratio of the solid volume to the total volume can be

87 calculate based on  $d$  and  $e$  as

$$88 \quad \varepsilon = 1 - \frac{\sqrt{2}}{2} \left[ de^2 + \frac{\pi d^2}{2} (1-e) + \left(\frac{e}{2} - d\right) e^2 + \pi d^2 (1-e\sqrt{2}) + \frac{e^3}{4} \right] \quad (4)$$

89 Solving for  $d$  in Eq. (4) gives

$$90 \quad d = \left[ \frac{\sqrt{2}(2 - 2\varepsilon - \frac{3\sqrt{2}}{4}e^3)}{\pi(3 - e - 2e\sqrt{2})} \right]^{\frac{1}{2}} \quad (5)$$

91 Substituting Eq. (5) into Eq. (3) gives

$$92 \quad k_{\text{eff}} = f_2(\varepsilon, e) \quad (6)$$

93 where  $f_2$  is another known function. Here, once the value of  $e$  is given, the ETC can be

94 calculated purely by porosity.

### 95 **3. Improved Model**

96 We present a discussion on the model of Dai et al. [11]; highlighting the possible area of

97 improvement. We then discuss the reason for the appearance of the geometrical impossible result.

98 Our proposed model is then presented.

#### 99 **3.1. Revisit Dai et al. 's Model**

100 Precision: In order to use Eq. (6) to predict the ETC, the value of  $e$  should first be calibrated.

101 According to Ref. [11], a value of  $e = 0.198$  was found to minimize the relative RMS deviation

102 of predictions from the experimental data [5]. This deviation is about 12%, which indicates that

103 there is still room for improvement.

104 The Geometrical Impossible Result: It should be true that  $r/a > 2$  to ensure that the length of

105 the node is larger than the diameter of the ligament. However, as has been mentioned in Ref. [11],

106 this requirement can hardly be fulfilled with  $e = 0.198$ . The reason for the appearance of this

107 geometrical impossible result is explained next.

### 108 **3.2. Causes and Effects of the geometrical impossible results**

109 According to Eq. (4) or the structure of the tetrakaidecahedron model (see Figs. 1(a), 1(b)), a  
110 decrease in porosity  $\varepsilon$ , is attributed to an increase in  $d$  when  $e$  is held constant and vice-versa.  
111 Here,  $d$  and  $e$  can be considered to represent the diameter of the ligament and the length of the  
112 node. In the model of Boomsma and Poulikakos [10] and Dai et al. [11], the parameter  $e$  was set  
113 as a constant value. Therefore, according to Eq. (4), a decrease in porosity can only be realized by  
114 an increase in the diameter of the ligament  $d$ . As a result, as the porosity decreases, the diameter of  
115 the ligament increases while the length of the node remains constant, and eventually, the former  
116 exceeds the latter, leading to geometrical impossible results. In fact, the smaller the value of  $e$ ,  
117 the more likely the geometrical impossible result occurs. As a result, geometrical impossible  
118 results were encountered more frequently in Ref. [11] than in Ref. [10].

### 119 **3.3. Current Model**

120 We improve on the model of Dai et al. [10] and eliminate the geometrical impossible result  
121 by accounting for the changing foam structure with porosity through the variable  $e$ . Since the  
122 experimental data contains information of the foam structure, using the experimental data, we can  
123 find how  $e$  varies with porosity. For a given porosity, we calibrate the  $e$  value by comparing  
124 the predictions made by Eq. (6) against experimental data (Ref. [5]). As a result, values of  $e$  for  
125 ten given porosities are obtained, as is shown in Fig. 2. The parameter  $e$  can be fitted by a third  
126 order polynomial function of the porosity  $\varepsilon$  (Fig. 2) as

$$127 \quad e = a + b\varepsilon + c\varepsilon^2 + d\varepsilon^3 \quad (7)$$

128 where  $a = 327.25811$ ,  $b = -1075.55645$ ,  $c = 1182.83207$  and  $d = -434.55535$ . The fitting error is

129 less than 1%.

#### 130 **4. Model Validation**

131 After obtaining the function between  $e$  and porosity, the ETC can be predicted as a function of  
132 porosity. Substituting Eq. (7) into Eq. (6), gives:

$$133 k_{\text{eff}} = f(\varepsilon) \quad (8)$$

134 where  $f$  is a known function.

135 When Eq. (8) is used to compute the ETCs for the experimental data in Ref. [5], the relative  
136 RMS deviation is about 5.0% for water-saturated foams, and 5.6% for air-saturated foams. The  
137 ratios of the node length to the ligament radius are also predicted using the current approach. As a  
138 result, within the porosity of 0.905 to 0.978, the  $r/a$  ratios are always  $> 2.0$  (decreasing from 6.33  
139 to 2.71). Thus, the geometrical impossible results are eliminated.

140 Figure 3 shows comparisons of our model with selected models. As a result of the changing  $e$   
141 values with porosity, our model is capable of capturing the non-linear variations in the ETCs as  
142 function of porosity. The relative RMS deviations from water and air experimental data of the  
143 present, Yang's, Dai's and Paek's predictions are 5.3%, 11.7%, 13.2% and 13.3% respectively.  
144 Since the  $e$  value is calibrated from the experimental data in Ref. [5], the high precision against  
145 the experimental data in Ref. [5] is expected. To validate our model, we use Eq. (8) to compute the  
146 ETCs for the experimental data reported by Phanikumar and Mahajan [16]. They reported the  
147 ETCs of air-saturated Al foams with porosity ranging from 0.899 to 0.959. Due to a similar foam  
148 geometry, the present model is capable of accurately predicting the variation trend of the ETCs  
149 with porosity; with a relative RMS deviation of about 12.1%.

150 To further assess the validity of our improved model as well as the fitted  $e$  value (Eq. 7).



151 We use our model to predict the ETCs of high porosity RVC foams (which have similar structure  
152 with high porosity metal foams), and the results are compared with experimental measurements  
153 reported in Ref. [6]. As a result, for water-saturated RVC foams, all the analytical models can  
154 accurately predict the ETCs (RMS deviation < 10%). When it comes to air-saturated RVC foams,  
155 Yang's model and Peak's model are less accurate with a RMS deviation of more than 21.8%. The  
156 relative RMS deviations of the present model are relative small; 7.2% and 7.6% for  
157 water-saturated and air-saturated RVC foams respectively. These results indicate that our  
158 improved model have a wider range of applicability.

## 159 **5. Conclusions**

160 We accounted for the size variation of the node with porosity and successfully eliminate the  
161 geometrical impossible results. The improved model provides more accurate predictions of the  
162 ETCs. Comparisons with other analytical models as well as experimental data validates that our  
163 model has a steadily high precision in predicting ETCs of foams with a wide range of solid phase  
164 to liquid phase conductivity ratios ( $k_s / k_f$ ).

## 165 **Conflict of interest**

166 None.

## 167 **Acknowledgments**


168 This work was supported by Science and Technology Project of Shaanxi Province  
169 (2014JZ2-002). The authors would like to thank sincerely Prof T.J. Lu and Dr X.H. Yang for their  
170 extensive and constructive suggestions on the model analysis.

## 171 **References**


172 [1] M.A. Mendes, S. Ray, D. Trimis, An improved model for the effective thermal conductivity of  
173 open-cell porous foams, International Journal of Heat and Mass Transfer 75 (2014) 224-230.

- 174 [2] M.A. Mendes, S. Ray, D. Trimis, A simple and efficient method for the evaluation of effective  
175 thermal conductivity of open-cell foam-like structures, *International Journal of Heat and Mass*  
176 *Transfer* 66 (2013) 412-422.
- 177 [3] M. Wang, N. Pan, Modeling and prediction of the effective thermal conductivity of random  
178 open-cell porous foams, *International Journal of Heat and Mass Transfer* 51 (5) (2008) 1325-1331.
- 179 [4] N. Dukhan, K.C. Chen, Heat transfer measurements in metal foam subjected to constant heat  
180 flux, *Experimental Thermal and Fluid Science* 32 (2) (2007) 624-631.
- 181 [5] V.V. Calmidi, R.L. Mahajan, The effective thermal conductivity of high porosity fibrous metal  
182 foams, *Journal of Heat Transfer* 121 (2) (1999) 466-471.
- 183 [6] A. Bhattacharya, V.V. Calmidi, R.L. Mahajan, Thermophysical properties of high porosity  
184 metal foams, *International Journal of Heat and Mass Transfer* 45 (5) (2002) 1017-1031.
- 185 [7] J.W. Paek, B.H. Kang, S.Y. Kim, J.M. Hyun, Effective Thermal Conductivity and Permeability  
186 of Aluminum Foam Materials, *International Journal of Thermophysics* 21 (2) (2000) 453-464.
- 187 [8] X. Fu, R. Viskanta, J.P. Gore, Prediction of effective thermal conductivity of cellular  
188 ceramics, *International Communications in Heat and Mass Transfer* 25 (2) (1998) 151-160.
- 189 [9] C.Y. Wang, C. Beckermann, A two-phase mixture model of liquid-gas flow and heat transfer in  
190 capillary porous media-I. Formulation, *International Journal of Heat and Mass Transfer* 36 (1993)  
191 2747-2747.
- 192 [10] K. Boomsma, D. Poulikakos, On the effective thermal conductivity of a three-dimensionally  
193 structured fluid-saturated metal foam, *International Journal of Heat and Mass Transfer* 44 (4)  
194 (2001) 827-836.
- 195 [11] Z. Dai, K. Nawaz, Y.G. Park, J. Bock, A.M. Jacobi, Correcting and extending the  
196 Boomsma-Poulikakos effective thermal conductivity model for three-dimensional, fluid-saturated  
197 metal foams, *International Communications in Heat and Mass Transfer* 37 (6) (2010) 575-580.
- 198 [12] X.H. Yang, J.X. Bai, H.B. Yan, J.J. Kuang, T.J. Lu, T. Kim, An analytical unit cell model for  
199 the effective thermal conductivity of high porosity open-cell metal foams, *Transport in Porous*  
200 *Media* 102 (3) (2014) 403-426.
- 201 [13] R. Coquard, D. Baillis, Numerical investigation of conductive heat transfer in high-porosity  
202 foams, *Acta Materialia* 57 (18) (2009) 5466-5479.
- 203 [14] R. Coquard, D. Rochais, D. Baillis, Conductive and radiative heat transfer in ceramic and  
204 metal foams at fire temperatures, *Fire Technology* 48 (3) (2012) 699-732.
- 205 [15] J. Randrianalisoa, D. Baillis, Thermal conductive and radiative properties of solid foams:  
206 Traditional and recent advanced modelling approaches, *Comptes Rendus Physique*, 2014, in press.
- 207 [16] M.S. Phanikumar, R. L. Mahajan, Non-Darcy natural convection in high porosity metal  
208 foams, *International Journal of Heat and Mass Transfer* 45 (18) (2002) 3781-3793.

209

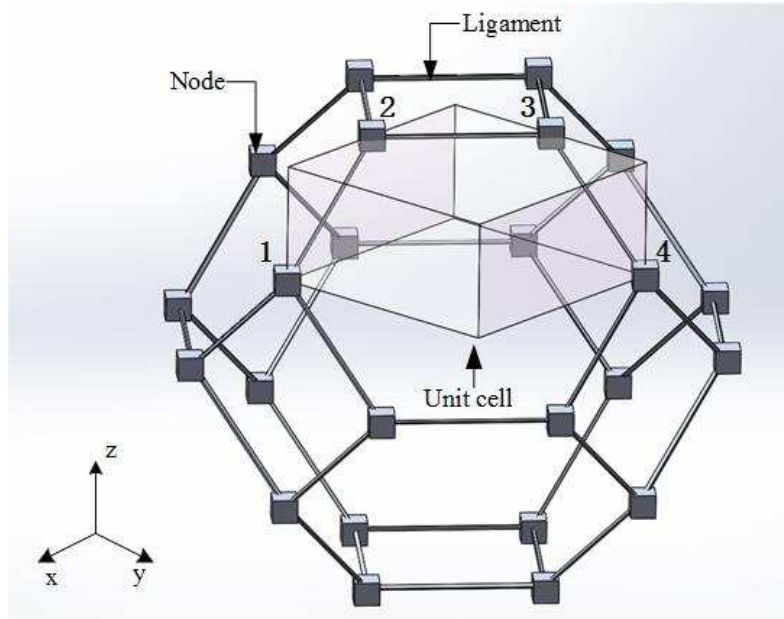

(a)

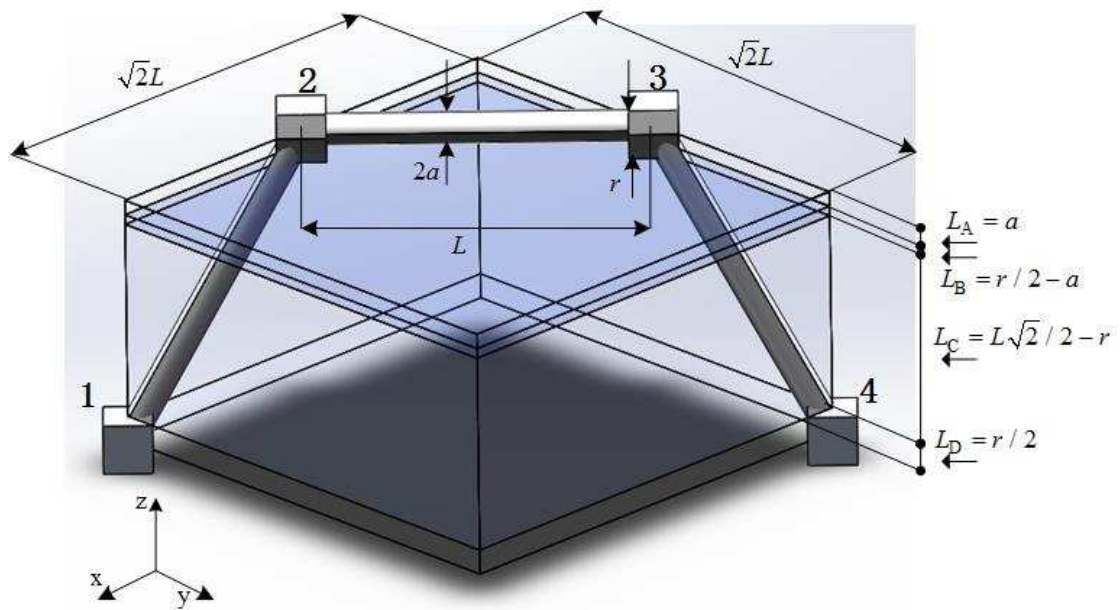

(b)

210

211


Fig. 1 (a) The tetrakaidecahedron model and (b) four distinctive layers for the unit cell

212

213

214

215

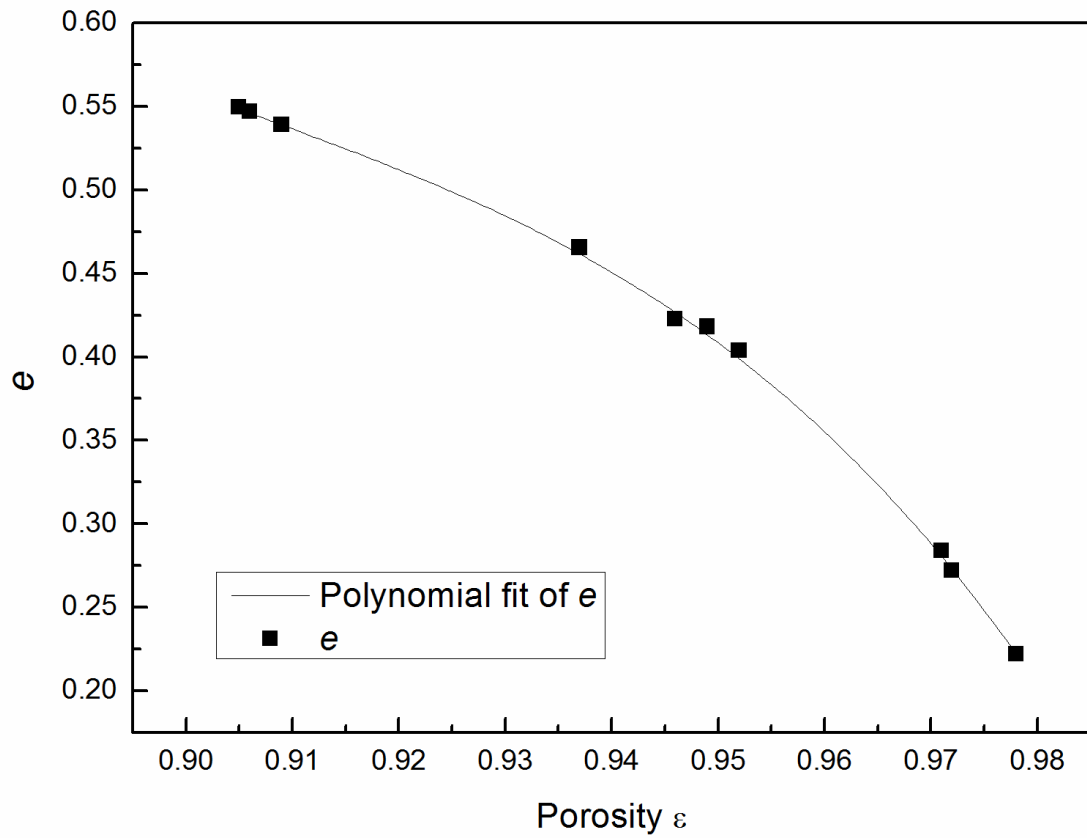

216

217

Fig. 2 Calibrated  $e$  values

218

219

220

221

222

223

224

225


226

227


228

229

230

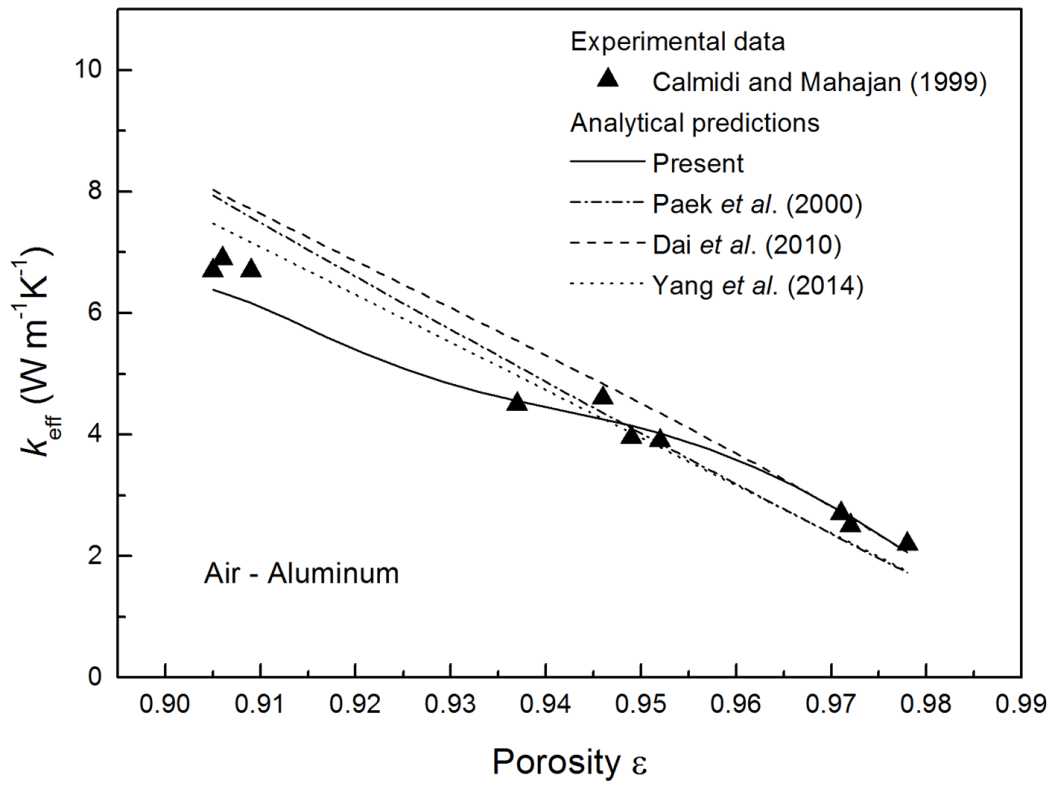

(a)

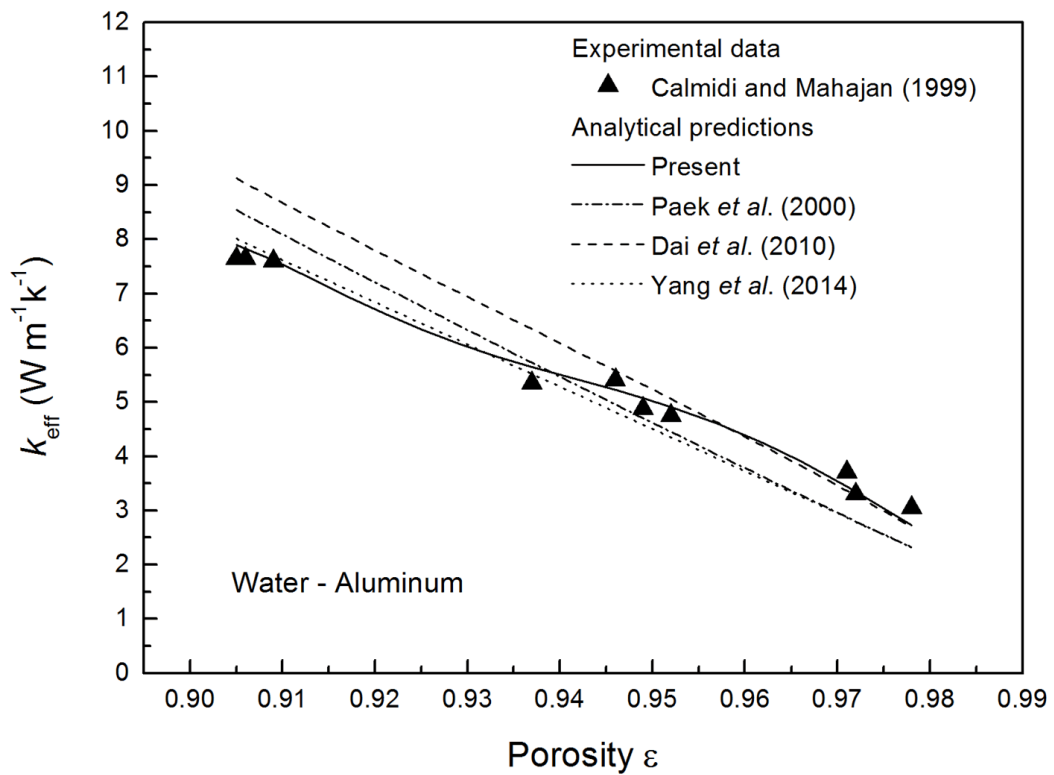

(a)

231

232 Fig. 3 Comparisons between the analytical models and the experimental data of (a) air-aluminum  
 233 and (b) water-aluminum