

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Photoswitchable Ratchet Surface Topographies based on Self-Protonating Spiropyran-NIPAAAM Hydrogels

Jelle E. Stumpel[†], *Bartosz Ziółkowski*[‡], *Larisa Florea*[‡], *Dermot Diamond*[‡], *Dirk J. Broer*^{†, §, *},
and Albertus P. H. J. Schenning^{†, §, *}

[†]Department of Functional Organic Materials and Devices, Chemical Engineering and
Chemistry, Eindhoven University of Technology. Den Dolech 2, 5612 AZ Eindhoven, The
Netherlands. E-mail: d.broer@tue.nl; a.p.h.j.schenning@tue.nl

[‡]The INSIGHT Centre for Data Analytics, National Centre for Sensor Research, School of
Chemical Sciences, Dublin City University, Glasnevin, Dublin 9, Ireland.

[§]Institute for Complex Molecular Systems and Laboratory of Macromolecular and Organic
Chemistry, Eindhoven University of Technology, P.O. Box 513, 5600 MB, Eindhoven, The
Netherlands

KEYWORDS Photoresponsive hydrogel, spiropyran, N-isopropylacrylamide, ratchet, surface
topography.

Abstract

In this work, self-protonating spiropyran based poly(N-isopropylacrylamide) polymer networks are prepared. These photoresponsive hydrogel coatings can change their surface topography upon exposure with visible light in neutral environment. Photoresponsive surface constrained films have been fabricated of which the swelling behavior can be controlled in a reversible manner. In a first step, symmetrical switchable surface topologies with varying cross-link density are obtained by polymerization-induced diffusion. Under light exposure, the areas with low cross-link density swell more than the areas with high crosslink density thus forming a corrugated surface. Asymmetric ratchet-like photoresponsive surfaces have been prepared on pre-structured asymmetric substrates. Due to thickness variation of the surface confined hydrogel layer an asymmetric swelling behavior is obtained. Depending on the cross-link density of the hydrogel it is possible to switch between a ratchet and flat surface topography or even an inverse ratchet surface by light.


Introduction

Responsive surface topographies, manufactured from materials which can change their properties in a reversible fashion, are gaining a lot of attention in recent years.¹⁻² By chemical design, the topographies can become responsive towards various stimuli, such as pH, temperature or light.³⁻⁷ Photoresponsive materials are of particular interest, since they can be operated locally in a non-contact way, without physically changing their chemical environment.⁸ Such materials are attractive as coatings for incorporation in microfluidic devices, in order to provide new approaches for key functions like valving, pumping and mixing.⁹⁻¹¹ These photoswitchable topographies might also be interesting for biological purposes such as

1
2
3 controlled cell growth.¹²⁻¹⁴ So far, most of the research has been focused on symmetric
4 responsive surface topographies, while asymmetric responsive topologies are rare.¹⁵ Such type of
5 coatings is interesting for transport or fluidic control. Especially ratchet-like structures are
6 appealing to induce unidirectional transport of liquids and particles.¹⁶⁻¹⁹
7
8
9

10
11
12 Suitable materials for photoresponsive coatings are hydrogels which can undergo reversible
13 volume changes in aqueous media due to differences in their hydrophilicity. A well-known
14 responsive polymer is poly-*N*-isopropylacrylamide (PNIPAAm).²⁰⁻²² Its thermoresponsive
15 behavior makes the hydrogel more hydrophobic upon increasing the surrounding temperature
16 above the lower critical solution temperature (LCST), resulting in dehydration and collapse of
17 the polymer chains. In case of addition of a crosslinking agent to the polymer backbone, a
18 hydrogel is formed. Dehydration of the polymer chains will lead to shrinkage of the hydrogel.
19
20 Modification of the polymer backbone by hydrophobic functionalities leads to a decrease or
21 disappearance in the ability of the polymer film to absorb water and swell, whilst incorporation
22 of hydrophilic compounds leads to an increase in water uptake. Implementing spiropyran, a
23 photochromic moiety of which the isomers have a high difference in polarity, in the polymer
24 backbone causes the entire polymer gel to change its hydrophilicity upon light irradiation.²³
25
26 Hydrophobic spiropyran causes the hydrogel to shrink, while hydrophilic protonated
27 merocyanine leads to swelling. In order to create hydrogel surface topographies based on
28 spiropyran and NIPAAm which shrink upon light exposure, the spiropyran moiety needs to be in
29 its hydrophilic protonated merocyanine form (Scheme 1).²⁴⁻²⁷ Therefore an acidic environment is
30 required to fabricate responsive surface topologies and up to now, most experiments are carried
31 out in slightly acidic solution. Recently, we have reported the incorporation of a small amount of
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 acrylic acid into the polymer backbone as internal proton source, to make freestanding
4
5 photoresponsive polymer gels that operate in neutral environment.²⁸
6
7

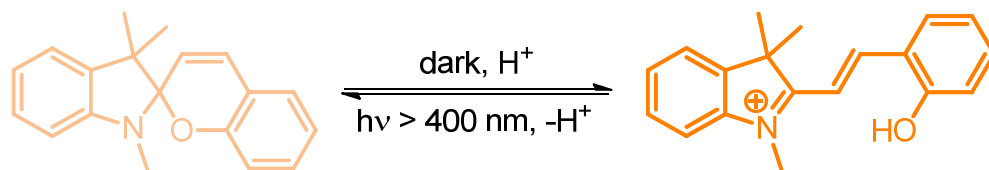

Scheme 1. Photoisomerization behavior of spiropyran into protonated merocyanine under acidic conditions.

In this work, we report on unprecedented asymmetric light responsive topographies based on self-protonating spiropyran-PNIPAAm hydrogels. Initially, we have prepared surface constrained films to study the photoresponsive behavior of our coating at neutral pH. It was found that the response time is similar to hydrogels operating at pH = 2.7 and that the degree of swelling can be controlled by the amount of crosslinker. Subsequently symmetrical switchable surface topographies with varying cross-link density within the polymer network are obtained by polymerization-induced diffusion. Asymmetric surface topographies are prepared by a single photopolymerization step on a pre-structured surface, having a ratchet-like topography.¹⁵ Due to the variable thickness of hydrogel present in different areas, the surface topography changes upon exposure with visible light. A thicker layer will result in a greater degree of swelling of the confined pattern. Depending on the cross-link density in the polymer film asymmetric responsive surfaces can be fabricated that switch between a ratchet and flat surface or mirror image ratchet topographies.

Experimental

Materials

1
2
3 Unless stated otherwise, all reagents and chemicals were obtained from commercial sources,
4
5 UV-photoinitiators 2-hydroxy-2-methyl-1-phenyl-1-propanone (Darocur 1173) and 2-hydroxy-1-
6
7 [4-(2-hydroxyethoxy) phenyl]-2-methyl-1-propanone-1-one (Irgacure 2959) were purchased at
8
9 Ciba Specialty Chemicals, acrylic acid, N-isopropylacrylamide (NIPAAAM), *N,N'*-
10
11 methylenebisacrylamide (MBIS), tripropylene glycol diacrylate (TPGDA), *1H,1H,2H,2H*-
12
13 perfluorodecyl triethoxysilane and 3-(trimethoxysilyl)propyl methacrylate were obtained from
14
15 Sigma Aldrich, and used without further purification. 6-((1',3',3'-Trimethylspiro[chromene-2,2'-
16
17 indolin]-6-yl)oxy)hexyl acrylate (SPA) was prepared as described before.²⁵ Two monomer
18
19 mixtures are used. Mixture 1 consists of NIPAAAM, SPA, acrylic acid, MBIS and Darocur 1173,
20
21 respectively 92, 1, 5, 1, 1 mol%. For mixture 2 the ratio is 91, 1, 5, 2, 1 mol%. Both mixtures are
22
23 dissolved in an equal (weight) amount of anhydrous dioxane.
24
25
26
27
28
29

30 **Substrate preparation**

31
32
33 Glass substrates were cleaned by means of sonication (ethanol, 15 minutes) followed by
34
35 treatment in a UV-ozone photoreactor (Ultra Violet Products, PR-100, 20 minutes). The surface
36
37 of the glass substrates was modified by spincoating 3-(trimethoxysilyl)propyl methacrylate
38
39 solution (1 v/v % solution in a 1:1 water-isopropanol mixture) or *1H,1H,2H,2H*-
40
41 perfluorodecyltriethoxysilane solution (1 v/v % solution in ethanol) on the activated glass
42
43 substrate during 45 seconds at 3000 rpm. After curing for 10 minutes at 100 °C, the substrates
44
45 were ready for use.
46
47
48
49

50 **Preparation of surface constrained coatings**

51
52
53 Substrate attached patterned films were prepared in a home-made cell, which consisted of one
54
55 upper *1H,1H,2H,2H*-perfluorodecyl-triethoxysilane functionalized glass slide and an lower
56
57
58
59
60

1
2
3 propyl methacrylate functionalized glass slide with a spacing of $\sim 55 \mu\text{m}$. The cells were capillary
4 filled with the monomer solution and subsequently exposed to UV light (unfiltered spectrum of a
5
6 collimated EXFO Omnicure S2000 lamp, 300 sec, $48 \text{ mW}/\text{cm}^2$ intensity in the range 320-390
7
8 nm). This dose of UV-exposure leads to full polymerization (Fig. S1).
9
10
11

12 13 **Preparation of symmetric patterned hydrogels coatings by polymerization-induced** 14 15 **diffusion** 16 17

18
19 Similar cells as for surface constrained coatings were capillary filled, before being placed on a
20 black surface. This is required in order to minimize polymerization in non-exposed areas due to
21 optical effects caused by reflection of light that has already passed through the sample. A mask
22 was placed on top of the sample and the sample exposed to UV light (unfiltered spectrum of a
23 collimated EXFO Omnicure S2000 lamp, 45 sec, $13.5 \text{ mW}/\text{cm}^2$ intensity in the range 320-390
24 nm). Afterwards, the mask was removed and the cell was fully exposed for another 300 seconds
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

40 41 42 43 44 45 46 47 48 49 50 51 52 53 54 55 56 57 58 59 60 **Preparation of asymmetric ratchet-like hydrogel coatings by pre-structured substrates**

40 An inverse copy of a Fresnel lens was prepared as follows. A droplet of TPGDA containing 2
41 wt% photoinitiator Irgacure 2959 was placed on a propyl methacrylate functionalized glass slide.
42 The Fresnel lens was placed firmly on top and the sample was mildly exposed to UV light (60
43 sec, $13.5 \text{ mW}/\text{cm}^2$ intensity in the range 320-390 nm) in order to have unreacted acrylates left for
44 covalent bonding between the template and the hydrogel in the next processing step. The Fresnel
45 lens was carefully removed using a razor blade. A droplet of the monomer mixture was placed
46 on the copy and a *1H,1H,2H,2H*-perfluorodecyl-triethoxysilane functionalized glass slide was
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 pressed firmly on top prior to photopolymerization for 300 seconds (48 mW/cm² intensity in the
4 range 320-390 nm).
5
6
7

8 9 **Photoresponse of the films**

10
11
12 For all samples, the upper glass slide of the hydrogel films was removed and the dioxane was
13 allowed to evaporate, before the hydrogel was swollen in deionized water. During the water
14 uptake, the films become colored due to the protonation of merocyanine. Furthermore, the
15 dimensions increase more than 2 times compared to the film in dioxane. After being immersed in
16 water for 1 hour, the film was stable (i.e. both the color of the film and its dimensions were in
17 equilibrium).²⁹ Due to the pre-treatment of the substrate, the film is covalently attached to the
18 surface. This is confirmed by the fact that no detachment of the coating occurs during the
19 swelling procedure. The photoresponse of the material was determined whilst immersed in
20 deionized water. Light irradiation of the films was performed with a DC4100 4-Channel LED
21 driver, equipped with a M455L3-C2 collimated LED (455 nm, FWHM = 18 nm, 0-1000 mA)
22 from Thorlabs, Inc. Photoresponsiveness of surface constrained films was performed at 700 mA
23 for 5 minutes, masked exposures at 700 mA for 1 minute (mixture 1 and 2) or 10 seconds
24 (mixture containing directly acrylated spiropyran, Fig. S5).²⁸ Surface topographies obtained by
25 polymerization-induced diffusion or by pre-structured substrates were exposed at 700 mA for 15
26 minutes.
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48

49 **Characterization of the hydrogels**


50
51
52 UV/Vis experiments were performed on an HR2000+ high resolution spectrometer from Ocean
53 Optics, mounted on a DM6000 M microscope from Leica microsystems. The corresponding light
54 source emits between 400 and 800 nm. Height profiles and 3D-images of patterned films were
55
56
57
58
59
60

1
2
3 recorded using a 3D interferometer (Fogale Nanotech Zoomsurf with a vertical resolution of 0.1
4
5
6 nm).

7 8 9 Results and discussion

10 11 12 Preparation and photoresponse of surface constrained hydrogel films

13
14
15 Initially, the photoresponsive behavior of self-protonating spiropyran hydrogels, covalently
16 attached to a surface, was investigated. For these hydrogels, a similar chemical composition was
17 used as previously reported for the non-constrained polymer films (Scheme 2).²⁸ N-
18 Isopropylacrylamide (NIPAAM) was used as main component (91 and 92% in mixture 1 and 2,
19 respectively). Spiropyran derivative SPA was incorporated as the photochromic unit (1%) and
20 acrylic acid (5%) was added to obtain the self-protonated merocyanine form.^{25, 28} For chemical
21 cross-linking of the network, 1 or 2 mol% of *N,N'*-methylenebisacrylamide (MBIS) was used
22 (mixture 1 or 2).³⁰ Darocur 1173 was utilized as photoinitiator. The monomer mixture was
23 dissolved in anhydrous dioxane prior to use. Unless stated otherwise, mixture 1 was used in all
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60 experiments.

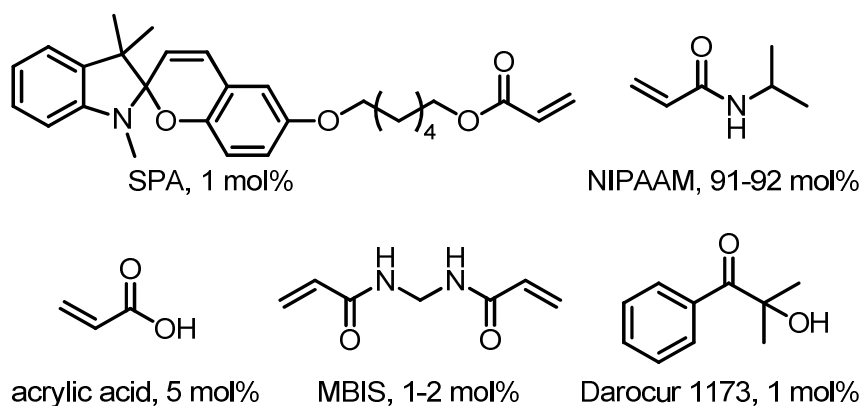

Scheme 2. Materials used for the preparation of the polymer coatings.

1
2
3 The acrylamide based hydrogels were covalently attached to a glass surface by using a propyl
4 methacrylate functionalized glass slide. This results in a surface constrained polymer coating.
5
6 Therefore a glass cell (spacing = 55 μm) with a methacrylate functionalized surface on one side
7
8 was used. This was filled with the dioxane mixture which was subsequently photopolymerized to
9
10 full conversion. The upper glass plate was then removed, and the dioxane was evaporated,
11
12 resulting in a ca. 25 μm thick film. Subsequently, the polymer coating was placed in
13
14 demineralized water leading to swelling of the film. After swelling for at least 1 hour, the
15
16 thickness of the film was increased to roughly 140 μm . This high degree of swelling (5.6 times)
17
18 is probably caused by the fact that the polymer network is prepared in solution leading to a non-
19
20 rigid network. Due to the double amount of crosslinks present, polymer coatings prepared from
21
22 mixture 2 swell slightly less. Here a thickness of 120 μm (4.8 times) was obtained. As the
23
24 swelling occurs mostly in the z-direction, the hydrogel is not able to swell in a unidirectional
25
26 fashion, therefore the swelling behavior is different than for freestanding films.³¹
27
28
29
30
31
32
33
34

35 During swelling of the hydrogels, the slightly off-color hydrogel film changed to a more intense
36
37 orange color (Fig. S2), which indicates that the protonated merocyanine isomer forms
38
39 spontaneously in water due to the carboxylic acid which is incorporated in the polymer
40
41 backbone. Absorption measurements of the film showed an absorption maximum of $\lambda = 470 \text{ nm}$
42
43 which is consistent with the formation of the self-protonated merocyanine hydrogel.^{25, 32} When
44
45 the sample was exposed to visible light ($\lambda = 455 \text{ nm}$) for 5 minutes, the protonated merocyanine
46
47 absorbance at 470 nm almost completely disappears (Fig. 1b), demonstrating complete reversion
48
49 of the protonated merocyanine to the spiropyran form (Scheme 1).
50
51
52
53
54
55
56
57
58
59
60

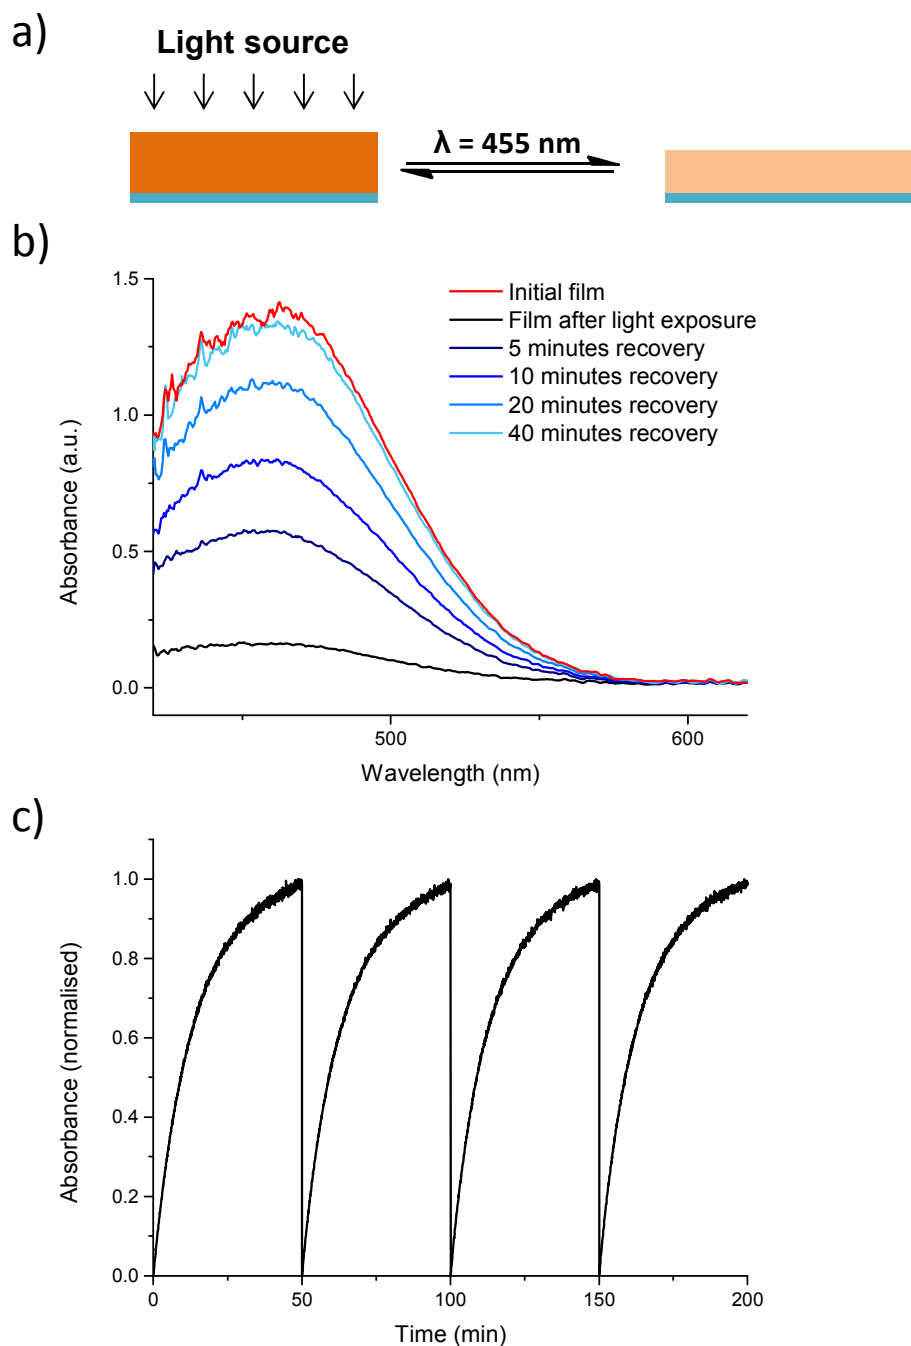


Figure 1. (a) Schematic representation of the photo-induced changes in the hydrogel coating, (b) UV-Vis spectrum showing spontaneous isomerization of spiropyran to protonated merocyanine after exposure to light (455 nm) and (c) Reversible photoresponsive behavior of the hydrogel film, change in absorption at 470 nm is depicted during four successive 5 minute exposure steps.

1
2
3 The back-isomerization of spiropyran into protonated merocyanine was monitored with UV/Vis
4 spectroscopy. After 50 minutes at room temperature, the absorption band at $\lambda = 470$ nm returns
5
6 to its initial intensity (Fig. 1b, c), demonstrating complete recovery. Four successive exposure
7
8 cycles show that this recovery is fully reversible and can be repeated multiple times.³³ The $t_{1/2}$
9
10 value of the recovery is ~ 10 minutes, which is slightly faster than the hydrogels without acrylic
11
12 acid in acidic environment which we reported before.²⁵ When increasing the amount of cross
13
14 linker from 1 to 2 mol%, the same recovery timescale was observed, despite the difference in
15
16 cross-link density (Fig. S3). The faster recovery is most likely related to the use of a different
17
18 cross-linker, rather than the difference between internal or external protonation (Fig. S4
19
20 compares two different cross-linkers). Furthermore, the spiropyran moiety modified with hexyl
21
22 acrylate leads to a faster recovery than its directly acrylated spiropyran analogue (Fig. S5). This
23
24 behavior can be explained due to the stronger electron donating character of the ether group
25
26 versus the ester group on the benzene ring.³²
27
28
29
30
31
32
33
34

35 To measure the swelling behavior of the initially flat hydrogel coating, masked exposure ($\lambda =$
36
37 455 nm) was performed through a line mask with dark lines of 1 mm and a pitch of 2 mm
38
39 (schematic representation in Fig. 2a). After this masked exposure step, the exposed areas lost
40
41 their color, whilst the non-exposed areas remain unchanged (Fig. 2b). Therefore, it can be
42
43 concluded that isomerization only took place in the exposed parts of the film. As with the
44
45 experiments performed without photomask, spiropyran isomerized back into the protonated
46
47 merocyanine isomer in ca. 50 minutes.
48
49
50
51
52
53
54
55
56
57
58
59
60

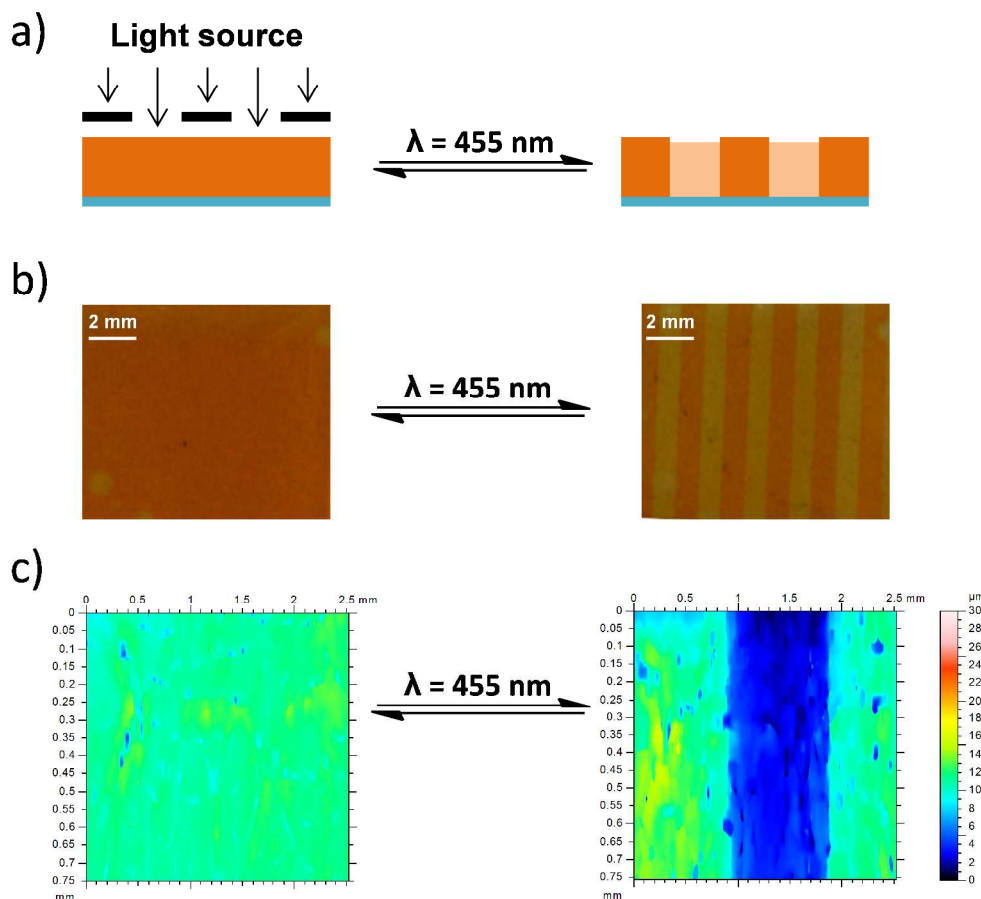


Figure 2. (a) Schematic presentation of masked illumination of the initially flat hydrogel coating, (b) photographs of a hydrogel (mixture 1) before (left) and after (right) masked illumination (455 nm), (c) corresponding height profile, as observed by interferometry. The lowest area is set as zero.

After masked exposure, the surface topography was investigated. Interferometry measurements revealed (Fig. 2c, S6) that the exposed areas were shrunken after masked exposure, leading to a symmetric structured surface topography.³⁴ At the exposed areas, the film thickness decreased by approximately 5 μm , revealing shrinkage of the swollen film by 3.6 %. To investigate the influence of the amount of cross-linker, similar experiments were performed in which the amount of MBIS was doubled (mixture 2, gel thickness is 120 μm , Fig. S7). The structures

1
2
3 obtained using these hydrogels decreased by only 3.2 μm after the masked exposure step, which
4
5 is considerably lower. This lower 2.7 % shrinkage is caused by the higher cross-link density,
6
7 which leads to a lower degree of swelling and shrinkage. The results show that photoresponsive
8
9 surface topography changes can be fine-tuned by varying the cross-link density of the hydrogel.
10
11

12 13 14 **Symmetric photoresponsive surface topographies by polymerization-induced diffusion**

15
16
17 We have first created symmetric photoresponsive surface topographies hydrogels that operate at
18
19 neutral pH. Such films were created via a controlled spatial distribution of the crosslink density
20
21 leading to patterned swelling.³⁵⁻³⁶ Therefore hydrogels were prepared by polymerization-induced
22
23 diffusion in the presence of a solvent (see Fig. S8 for the preparation method).^{3, 25}
24
25

26
27 Polymerization-induced diffusion occurs during patterned light UV-exposure of a monomer
28
29 mixture, due to different diffusion and polymerization rates of the monomers. This leads to a
30
31 patterned cross-link density following the pattern of the mask that is used during the
32
33 photopolymerization step. In previous solvent-free experiments at elevated temperature, the
34
35 polymerization was faster than the diffusion, resulting in accumulation of the diacrylate
36
37 monomers near the edges of the photomask.^{25, 37-38}
38
39
40

41
42 The same type of cells as for the preparation of surface constrained hydrogel films was used, but
43
44 in these experiments, the photopolymerization process consisted of two sequential photo-
45
46 exposure steps at room temperature. The first step was a masked photo-exposure, after which the
47
48 mask was removed and a flood UV-exposure applied to ensure the formation of a polymer film
49
50 over the entire surface area. As these polymerizations were performed in solution, there is a high
51
52 degree of monomer mobility, and diffusion of the monomers during the first exposure step is
53
54
55
56
57
58
59
60

therefore faster than in the solvent-free experiments, resulting in smooth structures instead of accumulation of monomers at the edges of the exposed areas (Fig. S9 and S10).

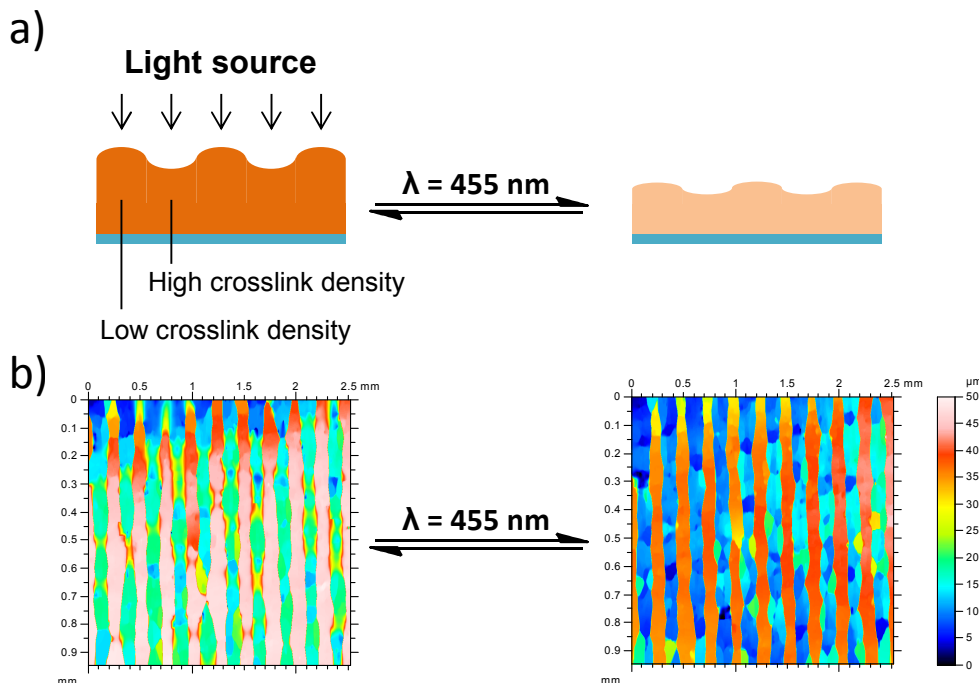



Figure 3. (a) Schematic representation of the hydrogel prepared by polymerization-induced diffusion and (b) height profiles of a hydrogel prepared by polymerization-induced diffusion before and after exposure, as observed by interferometry. The lowest area is set as zero (note: due to smoothing software, the topographies are presented more block-like than their actual shape, however, the minima and maxima were measured accurately).

The coatings prepared by polymerization-induced diffusion had an initial thickness of approximately 30 μm (Fig. S9a and S10a). After swelling, the thickness of areas with a low cross-link density increased to 200 μm (6.6 times swollen). The height of the relief structure is 28 μm in which the twice exposed areas swell less (5.6 times, Fig. 3b). This behavior indicates that these areas contain more cross linker as in the first exposure step the more reactive diacrylate cross linker diffuses to the exposed areas.

1
2
3 After exposure with visible light ($\lambda = 455$ nm), the total thickness of areas with a low cross-link
4 density decreased to $180 \mu\text{m}$ (-10 %) and the relief structure decreased to $23 \mu\text{m}$ (-18 %, Fig. 3b,
5
6 S10). Therefore, it can be concluded that a cross-link density difference throughout the film can
7
8 be obtained with the use of polymerization-induced diffusion for solubilized systems as well. As
9
10 the polymer film is surface-constrained and therefore can only swell in the direction
11
12 perpendicular to the surface. It should be noted that the swelling and light response behavior of
13
14 the coating are larger in comparison with the constrained homogeneous polymer coatings (vide
15
16 supra). This behavior indicates that the areas with low or high cross-link density do not behave
17
18 independently.
19
20
21
22
23
24

25 **Asymmetric photoresponsive surface topographies by pre-structured substrates**

26
27
28
29 In order to fabricate asymmetric photoresponsive surface topographies an asymmetric ratchet
30
31 substrate was used. This approach is based on the fact that a thicker surface constrained hydrogel
32
33 film shows a larger degree of swelling and due to asymmetry in the substrate, asymmetric
34
35 swelling occurs.¹⁵ A copy of a ratchet template was made using tripropylene glycol diacrylate
36
37 (TPGDA), which was partly photopolymerized.³⁹ Due to the incomplete polymerization, pendant
38
39 acrylate groups are still present at the copy. Subsequently, the structure was filled with the
40
41 hydrogel mixture and photopolymerized, leading to hydrogel which is covalently linked to the
42
43 asymmetric substrate. Following evaporation of dioxane after polymerization, the dried film has
44
45 a similar, but less steep, topography as the TPGDA substrate (Scheme 3a-b, Fig. S11).
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

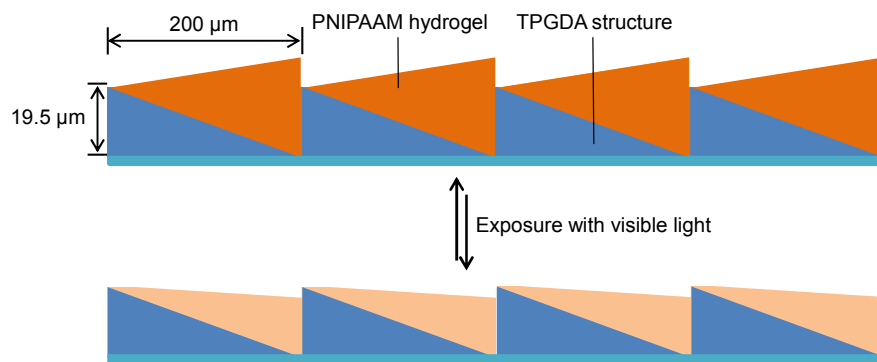

Scheme 3. Working mechanism of the ratchet topography.

In its dry state, the maximum height of the polymer network is $10.7 \mu\text{m}$. The surface, after swelling the film in demineralized water, shows an inverse ratchet topography (Fig. 4, S12 and S13) compared to the dry film. This behavior shows that the thicker surface parts swell more, as expected (Scheme 3). The maximal height difference is around $6 \mu\text{m}$ (total height swollen hydrogel $26 \mu\text{m}$). Upon light exposure, the ratchet slope decreased. The maximum change that could be obtained was a reduction of $3 \mu\text{m}$ in height. Subsequent illumination and reswelling cycles resulted in similar shrinkage and swelling behavior, showing that the hydrogel coating can be reversibly switched between a ratchet and a more flat surface topography.


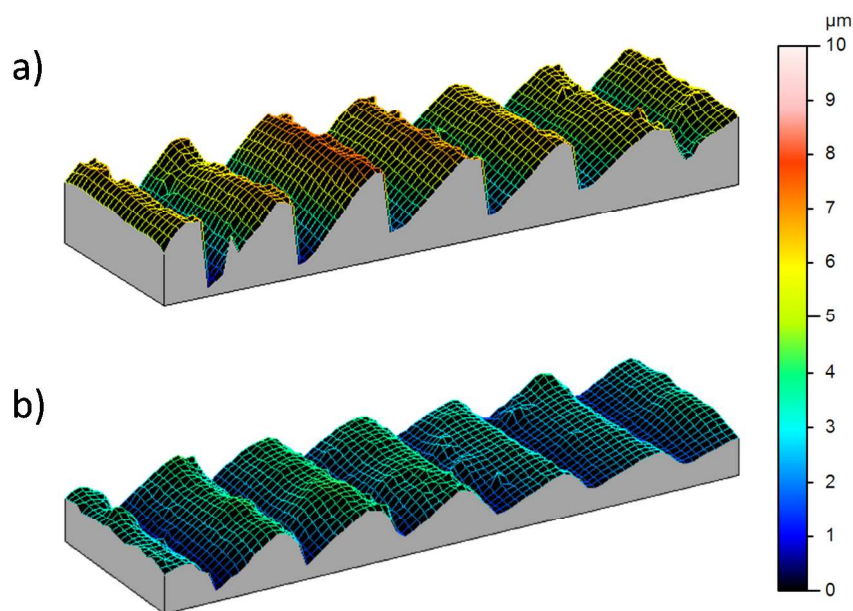


Figure 4. 3D height profiles of a ratchet prepared from mixture 1 before (a) and after (b) light exposure, as observed by interferometry (dimensions of the surface are 379 μm by 1262 μm).

In order to show that surface topography can be controlled by varying the amount of cross-linker, similar ratchet films were prepared from mixture 2 containing 2 wt% cross-linker (Fig. 5, S12 and S14). Due to the higher cross-link density, the obtained hydrogel swells less than the previously discussed hydrogel (initial height is 10.8 μm , height of the swollen hydrogel is 21.3 μm). This results in an asymmetric structure with a difference in height of only 1.8 μm after being swollen in demineralized water, which is comparable with the difference in case of surface-constrained films (vide supra). Upon exposure to visible light, the surface went from ratchet structured to flat and even formed an inverse ratchet structure that had 1 μm height difference. Furthermore, the alteration of the protrusions could be easily controlled, depending on the intensity of the illumination and the exposure time (Fig. S15). Both ratchet structures could be photo-switched many times. After several months of storage in demineralized water, the response of the coating towards light is still present (i.e. there is no decrease in response

1
2
3 compared to fresh samples), showing that it is possible to fabricate durable photoresponsive
4
5
6 topographies.
7
8
9
10
11
12

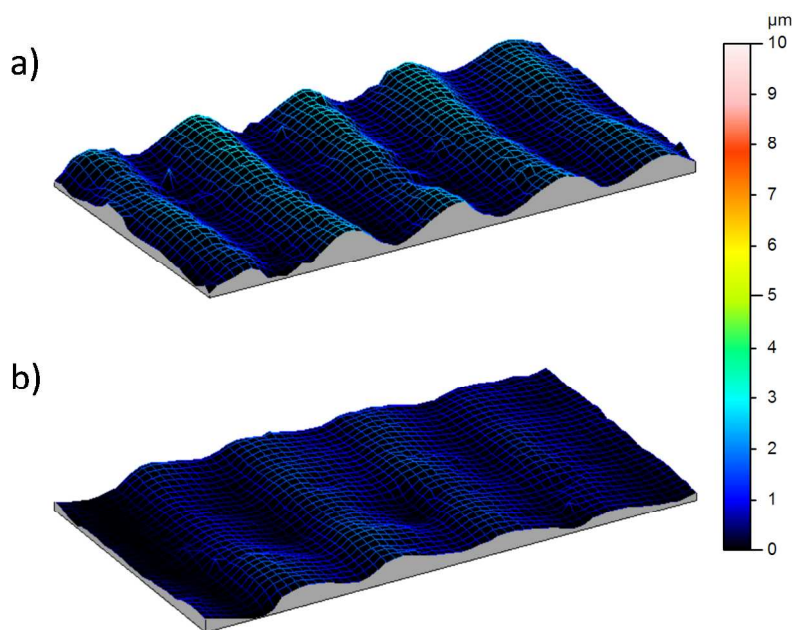

33
34 **Figure 5.** 3D height profiles of a ratchet prepared from mixture 2 before (a) and after (b) light
35 exposure, as observed by interferometry (dimensions of the surface are 505 μm by 946 μm).
36
37

38 39 **Conclusions**

40
41
42 Hydrogels based on polymers of NIPAAm, spiropyran and acrylic acid have been used to
43
44 produce photoresponsive symmetric and asymmetric surface topographies which can operate in
45
46 neutral aqueous environment. By using pre-structured ratchet substrates the light responsive
47
48 asymmetric surface topography can in principle be fully controlled by the chemical composition
49
50 of the mixture. Furthermore one can expect that even more complex surface topographies are
51
52 possible by combining the approaches reported here i.e. local light exposure, polymerization
53
54 induced diffusion and pre-structured substrate approaches. Our results show that dynamic robust
55
56
57
58
59
60

1
2
3 asymmetric hydrogel surfaces can be fabricated that can be useful in microfluidic, biological and
4
5 tribological applications. Currently, we have initiated investigations into the behavior of cell
6
7 growth on these coatings and started to implement the practical incorporation of these
8
9 photoresponsive materials within microfluidic devices.^{8,40}
10
11

12
13 **Supporting Information.** Photoresponsive behavior of different hydrogel films; surface
14
15 topographies, as observed by interferometry. This material is available free of charge via the
16
17 Internet at <http://pubs.acs.org>.
18
19

20 21 22 **Corresponding Author**

23
24 * E-mail: d.broer@tue.nl; a.p.h.j.schenning@tue.nl
25
26

27 28 **Acknowledgment**

29
30 This research has been made possible by a VICI grant of The Netherlands Foundation for
31
32 Scientific Research (NWO). Support from Science Foundation Ireland under INSIGHT award
33
34 SFI/12/RC/2289 is also kindly acknowledged. BZ acknowledges the EU Framework 7 project
35
36 “ATWARM” (Marie Curie ITN, No. 238273). Furthermore, we would like to thank Danqing Liu
37
38 for help with the initial experiments.
39
40

41 42 **REFERENCES**

- 43
44 (1) Spruell, J. M.; Hawker, C. J. Triggered Structural and Property Changes in Polymeric
45
46 Nanomaterials. *Chem. Sci.* **2011**, *2*, 18-26.
47
48 (2) Byrne, R.; Benito-Lopez, F.; Diamond, D. Materials Science and the Sensor Revolution.
49
50 *Mater. Today* **2010**, *13*, 16-23.
51
52 (3) Liu, D.; Bastiaansen, C. W. M.; den Toonder, J. M. J.; Broer, D. J. Single-Composition
53
54 Three-Dimensionally Morphing Hydrogels. *Soft Matter* **2013**, *9*, 588-596.
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (4) Liu, D.; Bastiaansen, C. W. M.; den Toonder, J. M. J.; Broer, D. J. Photo-Switchable Surface Topologies in Chiral Nematic Coatings. *Angew. Chem., Int. Ed.* **2012**, *51*, 892-896.
 - (5) Wei, J.; Yu, Y. Photodeformable Polymer Gels and Crosslinked Liquid-Crystalline Polymers. *Soft Matter* **2012**, *8*, 8050-8059.
 - (6) Pedron, S.; van Lierop, S.; Horstman, P.; Penterman, R.; Broer, D. J.; Peeters, E. Stimuli Responsive Delivery Vehicles for Cardiac Microtissue Transplantation. *Adv. Funct. Mater.* **2011**, *21*, 1624-1630.
 - (7) Beebe, D. J.; Moore, J. S.; Bauer, J. M.; Yu, Q.; Liu, R. H.; Devadoss, C.; Jo, B.-H. Functional Hydrogel Structures for Autonomous Flow Control inside Microfluidic Channels. *Nature* **2000**, *404*, 588-590.
 - (8) Florea, L.; Diamond, D.; Benito-Lopez, F. Photo-Responsive Polymeric Structures Based on Spiropyran. *Macromol. Mater. Eng.* **2012**, *297*, 1148-1159.
 - (9) Benito-Lopez, F.; Byrne, R.; Raduta, A. M.; Vrana, N. E.; McGuinness, G.; Diamond, D. Ionogel-Based Light-Actuated Valves for Controlling Liquid Flow in Micro-Fluidic Manifolds. *Lab Chip* **2010**, *10*, 195-201.
 - (10) Sugiura, S.; Sumaru, K.; Ohi, K.; Hiroki, K.; Takagi, T.; Kanamori, T. Photoresponsive Polymer Gel Microvalves Controlled by Local Light Irradiation. *Sens. Actuators, A* **2007**, *140*, 176-184.
 - (11) Sugiura, S.; Szilagyi, A.; Sumaru, K.; Hattori, K.; Takagi, T.; Filipcsei, G.; Zrinyi, M.; Kanamori, T. On-Demand Microfluidic Control by Micropatterned Light Irradiation of a Photoresponsive Hydrogel Sheet. *Lab Chip* **2009**, *9*, 196-198.


- 1
2
3 (12) Sun, T.; Qing, G. Biomimetic Smart Interface Materials for Biological Applications. *Adv.*
4
5 *Mater.* **2011**, *23*, H57-H77.
6
7
8 (13) Fu, S.-W.; Chien, H.-W.; Tsai, W.-B. Fabrication of Poly(N-Isopropylacrylamide) Films
9
10 Containing Submicrometer Grooves for Constructing Aligned Cell Sheets. *Langmuir*
11
12 **2013**, *29*, 14351-14355.
13
14
15 (14) Schmidt, S.; Zeiser, M.; Hellweg, T.; Duschl, C.; Fery, A.; Möhwald, H. Adhesion and
16
17 Mechanical Properties of Pnipam Microgel Films and Their Potential Use as Switchable
18
19 Cell Culture Substrates. *Adv. Funct. Mater.* **2010**, *20*, 3235-3243.
20
21
22 (15) Liu, D.; Bastiaansen, C. W. M.; den Toonder, J. M. J.; Broer, D. J. (Photo-)Thermally
23
24 Induced Formation of Dynamic Surface Topographies in Polymer Hydrogel Networks.
25
26 *Langmuir* **2013**, *29*, 5622-5629.
27
28
29 (16) Duncombe, T. A.; Erdem, E. Y.; Shastry, A.; Baskaran, R.; Böhringer, K. F. Controlling
30
31 Liquid Drops with Texture Ratchets. *Adv. Mater.* **2012**, *24*, 1545-1550.
32
33
34 (17) Duncombe, T. A.; Parsons, J. F.; Böhringer, K. F. Directed Drop Transport Rectified
35
36 from Orthogonal Vibrations Via a Flat Wetting Barrier Ratchet. *Langmuir* **2012**, *28*,
37
38 13765-13770.
39
40
41 (18) Sekeroglu, K.; Gurkan, U. A.; Demirci, U.; Demirel, M. C. Transport of a Soft Cargo on
42
43 a Nanoscale Ratchet. *Appl. Phys. Lett.* **2011**, *99*, 063703.
44
45
46 (19) Malvadkar, N. A.; Hancock, M. J.; Sekeroglu, K.; Dressick, W. J.; Demirel, M. C. An
47
48 Engineered Anisotropic Nanofilm with Unidirectional Wetting Properties. *Nat Mater*
49
50 **2010**, *9*, 1023-1028.
51
52
53 (20) Schild, H. G. Poly(N-Isopropylacrylamide): Experiment, Theory and Application. *Prog.*
54
55 *Polym. Sci.* **1992**, *17*, 163-249.
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (21) Philipp, M.; Müller, U.; Aleksandrova, R.; Sanctuary, R.; Müller-Buschbaum, P.; Krüger, J. K. On the Elastic Nature of the Demixing Transition of Aqueous Pnipam Solutions. *Soft Matter* **2012**, *8*, 11387-11395.
- (22) Philipp, M.; Müller, U.; Aleksandrova, R.; Sanctuary, R.; Müller-Buschbaum, P.; Krüger, J. K. Immense Elastic Nonlinearities at the Demixing Transition of Aqueous Pnipam Solutions. *Soft Matter* **2013**, *9*, 5034-5041.
- (23) Minkin, V. I. Photo-, Thermo-, Solvato-, and Electrochromic Spiroheterocyclic Compounds. *Chem. Rev.* **2004**, *104*, 2751-2776.
- (24) Satoh, T.; Sumaru, K.; Takagi, T.; Kanamori, T. Fast-Reversible Light-Driven Hydrogels Consisting of Spirobenzopyran-Functionalized Poly(N-Isopropylacrylamide). *Soft Matter* **2011**, *7*, 8030-8034.
- (25) Stumpel, J. E.; Liu, D.; Broer, D. J.; Schenning, A. P. H. J. Photoswitchable Hydrogel Surface Topographies by Polymerisation-Induced Diffusion. *Chem. - Eur. J.* **2013**, *19*, 10922-10927.
- (26) Szilágyi, A.; Sumaru, K.; Sugiura, S.; Takagi, T.; Shinbo, T.; Zrínyi, M.; Kanamori, T. Rewritable Microrelief Formation on Photoresponsive Hydrogel Layers. *Chem. Mater.* **2007**, *19*, 2730-2732.
- (27) Sumaru, K.; Ohi, K.; Takagi, T.; Kanamori, T.; Shinbo, T. Photoresponsive Properties of Poly(N-Isopropylacrylamide) Hydrogel Partly Modified with Spirobenzopyran. *Langmuir* **2006**, *22*, 4353-4356.
- (28) Ziólkowski, B.; Florea, L.; Theobald, J.; Benito-Lopez, F.; Diamond, D. Self-Protonating Spiropyran-Co-Nipam-Co-Acrylic Acid Hydrogel Photoactuators. *Soft Matter* **2013**, *9*, 8754-8760.

- 1
2
3 (29) The actual swelling and coloration of the film is relatively fast, after 5 minutes, no visual
4 changes are observed. The longer swelling time of 1 hour is used to ensure that both
5 hydration and isomerization are equilibrated.
6
7
8
9
10 (30) Incorporation of MBIS as cross-linker leads to slightly faster recovery rates than those of
11 tri(propylene glycol) diacrylate (TPGDA) we reported before (Fig. S4).
12
13 (31) Li, Y.; Tanaka, T. Kinetics of Swelling and Shrinking of Gels. *J. Chem. Phys.* **1990**, *92*,
14 1365-1371.
15
16
17 (32) Satoh, T.; Sumaru, K.; Takagi, T.; Takai, K.; Kanamori, T. Isomerization of
18 Spirobenzopyrans Bearing Electron-Donating and Electron-Withdrawing Groups in
19 Acidic Aqueous Solutions. *Phys. Chem. Chem. Phys.* **2011**, *13*, 7322-7329.
20
21
22 (33) Wang, W.; Metwalli, E.; Perlich, J.; Papadakis, C. M.; Cubitt, R.; Müller-Buschbaum, P.
23 Cyclic Switching of Water Storage in Thin Block Copolymer Films Containing Poly(N-
24 Isopropylacrylamide). *Macromolecules* **2009**, *42*, 9041-9051.
25
26
27 (34) Zhou, S.; Wu, C. In-Situ Interferometry Studies of the Drying and Swelling Kinetics of
28 an Ultrathin Poly(N-Isopropylacrylamide) Gel Film Below and above Its Volume Phase
29 Transition Temperature. *Macromolecules* **1996**, *29*, 4998-5001.
30
31
32 (35) Hashmi, S. M.; Dufresne, E. R. Mechanical Properties of Individual Microgel Particles
33 through the Deswelling Transition. *Soft Matter* **2009**, *5*, 3682-3688.
34
35
36 (36) Radji, S.; Alem, H.; Demoustier-Champagne, S.; Jonas, A. M.; Cuenot, S. p. Variation of
37 Elastic Properties of Responsive Polymer Nanotubes. *J. Phys. Chem. B* **2010**, *114*, 4939-
38 4944.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (37) de Gans, B.-J.; Sánchez, C.; Kozodaev, D.; Wouters, D.; Alexeev, A.; Escuti, M. J.; Bastiaansen, C. W. M.; Broer, D. J.; Schubert, U. S. Optimizing Photo-Embossed Gratings: A Gradient Library Approach. *J. Comb. Chem.* **2006**, *8*, 228-236.
- (38) Leewis, C. M.; de Jong, A. M.; van Ijzendoorn, L. J.; Broer, D. J. Simulations with a Dynamic Reaction--Diffusion Model of the Polymer Grating Preparation by Patterned Ultraviolet Illumination. *J. Appl. Phys.* **2004**, *95*, 8352-8356.
- (39) As substrate, we have made a copy of a Fresnel lens as it possesses a ratchet-like structure.
- (40) Czugala, M.; O'Connell, C.; Blin, C.; Fischer, P.; Fraser, K. J.; Benito-Lopez, F.; Diamond, D. Swelling and Shrinking Behaviour of Photoresponsive Phosphonium-Based Ionogel Microstructures. *Sens. Actuators, B* **2014**, *194*, 105-113.

TOC

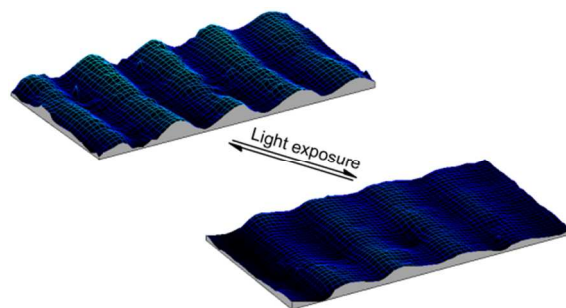

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60