

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)



# Decentralized production of hydrogen for residential PEM fuel cells from piped natural gas by low temperature steam-methane reforming using sorption enhanced reaction concept

Michael G. Beaver and Shivaji Sircar\*  
*Chemical Engineering Department  
Lehigh University, Bethlehem, Pa 18015, U.S.A.*

## Background

Decentralized generation of small-scale stationary power (< 250 KW) for residential or commercial use has been a subject of much interest during the last decade and many corporations around the world have engaged in research and development of fuel cell technology for this application [1-10]. The driver for this technology is rapidly expanding worldwide demand for more heating, cooling and electrical supply by increasing populations and growing economics [1, 2, 4, 8]. Some of the potential benefits include (a) quiet and reliable operation, (b) power on demand, (c) efficiency at low load, (d) higher efficiency vis a vis combustion route of power generation, (e) lower CO<sub>2</sub> production than combustion, (f) absence of transmission line loss, and (f) absence of SO<sub>x</sub> and NO<sub>x</sub> production at the point of operation.

## Proton Exchange Membrane (PEM) Fuel Cell

Proton exchange membrane or polymer electrolyte membrane (PEM) fuel cell technology which transforms the chemical energy liberated during the electrochemical reaction between hydrogen and oxygen to electric energy as opposed to direct combustion of hydrogen and oxygen to produce thermal energy has attracted most attention [11 - 13].

Some of the attractive features of the PEM fuel cells include (a) delivery of high power density, (b) light weight and compactness, (c) relatively low temperature operation (~ 60-80°C), (d) use of non-corrosive electrolyte (e) quick start-up, (f) rapid response to demand changes in power, (g) elimination of storage battery, and (h) durability [2, 12, 13].

---

\* Corresponding author, email: sircar@aol.com

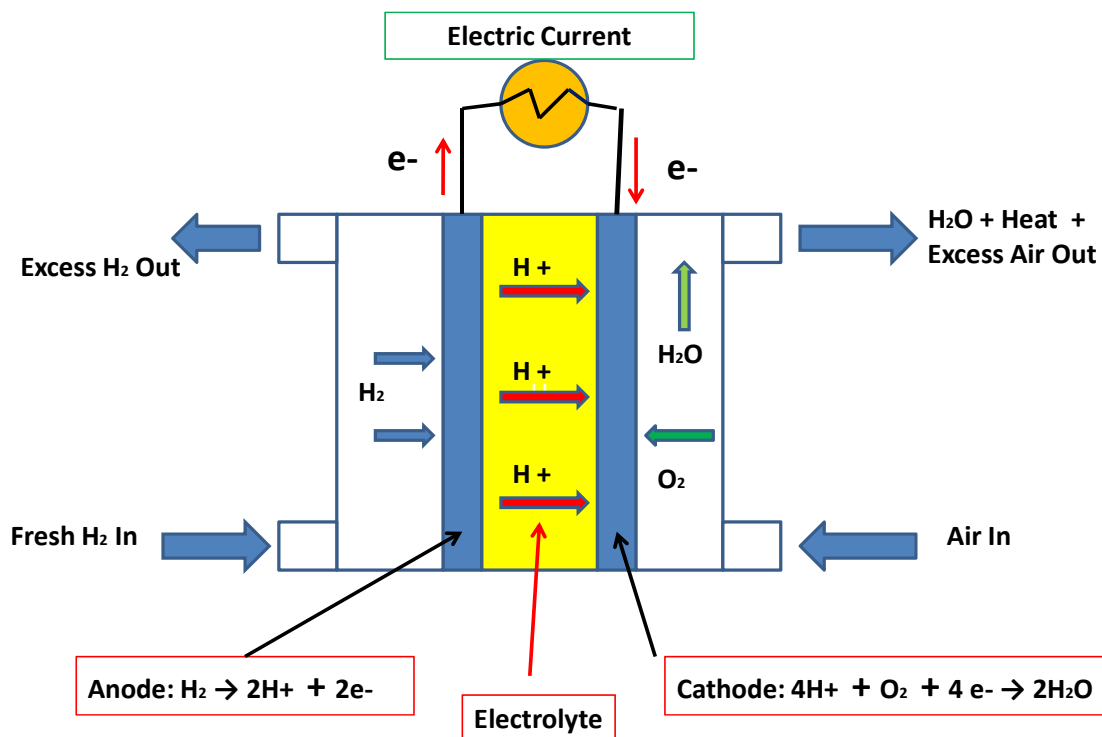


Fig. 1. Cartoon of a hydrogen PEM fuel cell.

Figure 1 is a cartoon depicting the principle of operation of a hydrogen PEM fuel cell [11]. It uses a solid polymer as an electrolyte and porous carbon electrodes containing primarily a platinum catalyst. The most commonly used membrane is humidified Nafion developed by DuPont Corp. The fuel cell needs pure hydrogen, oxygen (from air) and water (to moisten the membrane) for operation. H<sub>2</sub> is catalytically dissociated into a proton and an electron at the anode followed by selective transport of only the proton through the membrane to the cathode, where it reacts with dissociated O<sub>2</sub> to produce H<sub>2</sub>O and heat. The relevant chemical reactions at the electrodes are shown in the figure. The net reaction ( $2H_2 + O_2 \leftrightarrow 2H_2O$ ) is highly exothermic which generates a large amount of heat in the fuel cell. The free electron released at the anode moves to the cathode through an external circuit, thereby, generating electric current.

The purities of H<sub>2</sub> and O<sub>2</sub> used in the PEM hydrogen fuel cell are critical issues. The catalytic activity of the platinum electrodes in a PEM fuel cell is poisoned by the presence of trace amounts of CO, NH<sub>3</sub>, H<sub>2</sub>S and HCN in the H<sub>2</sub> [4, 11, 14], as well as by the presence of trace amounts of SO<sub>2</sub> and H<sub>2</sub>S in the O<sub>2</sub> (air) [15]. Presence of CH<sub>4</sub> in the H<sub>2</sub> is regarded to be inert towards the performance of the electrodes. CO<sub>2</sub> itself is also regarded to be inert, but the formation of trace CO by reverse water gas shift reaction (RWGS) at the anode [ $CO_2 + H_2 \leftrightarrow CO + H_2O$ ] due to the presence of CO<sub>2</sub> in H<sub>2</sub> can have the same detrimental effect as in the presence of trace CO in H<sub>2</sub> [14].

Figure 2 shows thermodynamic estimation of CO formation by reaction between CO<sub>2</sub> and H<sub>2</sub> at different temperatures of operation of a PEM fuel cell [14]. It may be seen that a considerable amount of CO, albeit in parts per million level, is formed at the anode which is sufficient to poison the catalyst by being selectively chemisorbed on the platinum electrode over H<sub>2</sub>.

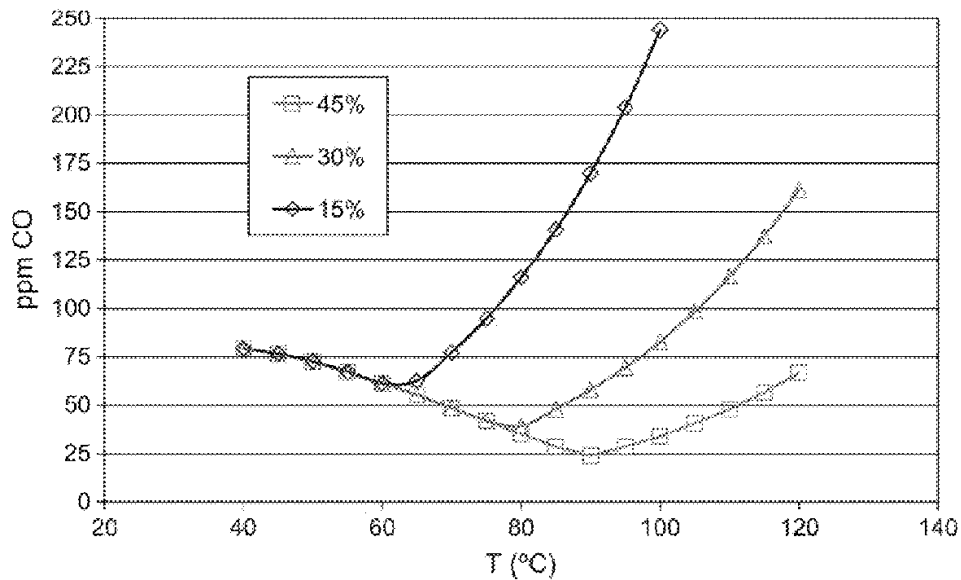


Fig. 2. Equilibrium concentration of CO produced by RWGS reaction from a feed gas containing 3:1 H<sub>2</sub>: CO<sub>2</sub> at 1.5 bar and different temperatures in presence of different concentrations of water. Reprinted from J. Power Sources, 110, 117-124 (2002) with permission from Elsevier.

Figures 3 and 4, respectively, show two sets of experimental data demonstrating the detrimental performance of a PEM fuel cell in presence of bulk CO<sub>2</sub> in H<sub>2</sub> [14] and trace SO<sub>2</sub> in air [15].

Figure 3 shows that the cell voltage for a given current density decreases as the CO<sub>2</sub> concentration in the feed H<sub>2</sub> increases. Figure 4 shows that the normalized output voltage of a fuel cell decreases with operation time when the air introduced at the cathode is contaminated with even a trace amount (<1.5 ppm) of SO<sub>2</sub>. The rate of degradation of the cell performance increases rapidly as the concentration of contaminated SO<sub>2</sub> is increased.

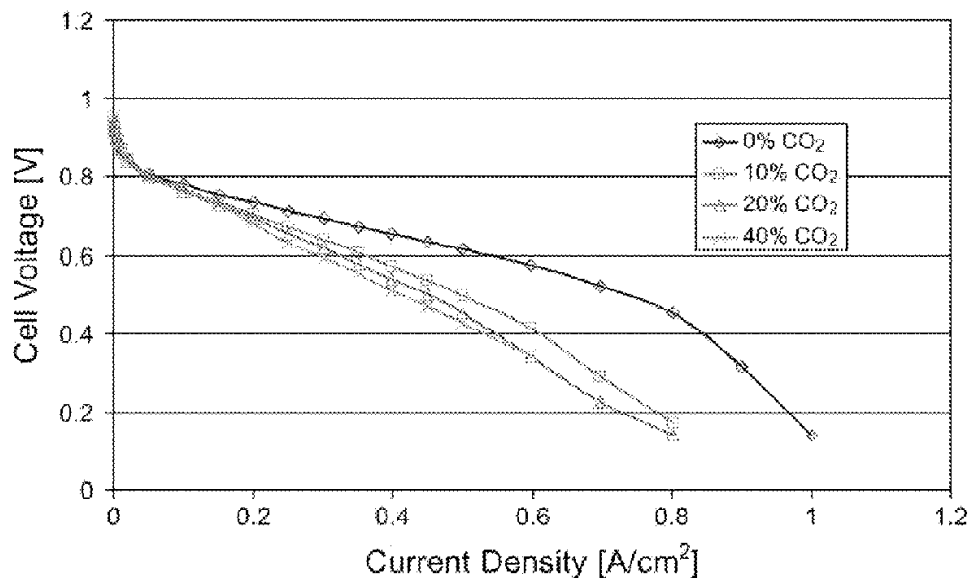


Fig. 3. Polarization curves of a Nafion fuel cell at various CO<sub>2</sub> concentrations in the feed H<sub>2</sub> at 65°C. P = 1.5 atm. Reprinted from J. Power Sources, 110, 117-124 (2002) with permission from Elsevier.

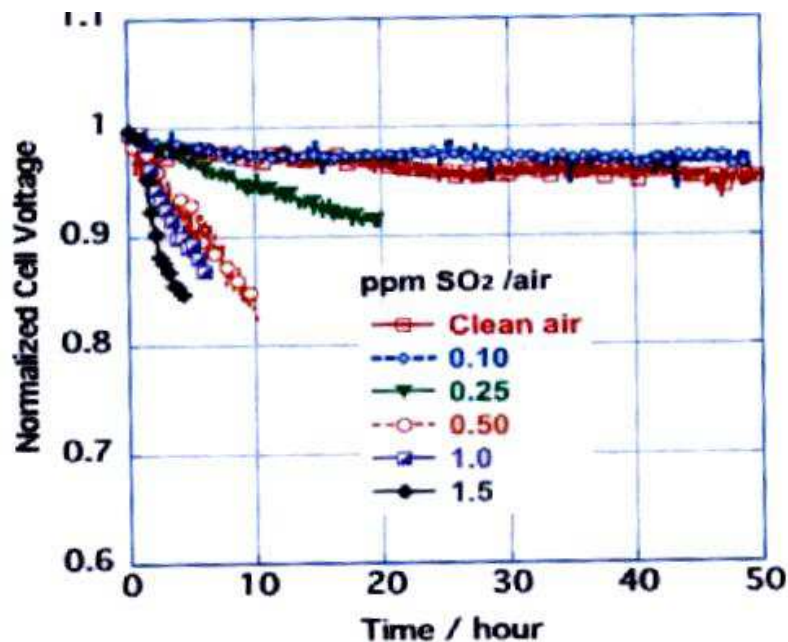


Fig. 4. Effect of the presence of trace  $\text{SO}_2$  in air at the cathode of a PEM fuel cell.

Consequently, essentially  $\text{CO}_x$ , sulfur, and  $\text{NH}_3$  free  $\text{H}_2$  and air streams are needed as feed gases for efficient and durable operation of a PEM fuel cell. A 2005 draft specification of the fuel cell grade hydrogen suggested by the U. S. Department of Energy is provided in Table 1 [15].

Components	Levels
Hydrogen	>99,9 %
CO	~0.1 ppm
$\text{CO}_2$	~5.0 ppm
$\text{NH}_3$	~1 ppm
Non $\text{CH}_4$ hydrocarbons	~100 ppm

Table 1. Suggested specification of  $\text{H}_2$  purity for PEM fuel cell [15].

This requirement of very high purity  $\text{H}_2$  may be a potential limitation of the use of a PEM fuel cell for residential use. It should, however, be noted that a very active R & D effort is being carried out to produce more  $\text{CO}_x$  tolerant anode catalysts by employing platinum-ruthenium catalysts made by different preparation methods as well as by using other catalyst formulations [16 - 21]. The other potential limitations of commercializing residential fuel cells may be (a) high manufacturing costs, (b) complex heat and water management issues, (c) long warm up period, (d) inferior performance when cold, and (e) membrane life and cost of replacement [12].

### Natural Gas as source of Hydrogen

The high purity  $\text{H}_2$  required by a PEM fuel cell must be easily available at the point of location of residential use. One potential solution is to directly produce fuel-cell grade  $\text{H}_2$  at the site of the fuel cell by steam reforming of methane [22]. A network of pipe lines to

supply natural gas for domestic (heating or cooking), and commercial (heating) applications already exists in the infrastructure of many advanced countries. The gas is typically available at a pressure of 2 – 60 psig, and is centrally processed to remove impurities like H<sub>2</sub>O, CO<sub>2</sub>, S, He, and heavy hydrocarbons.

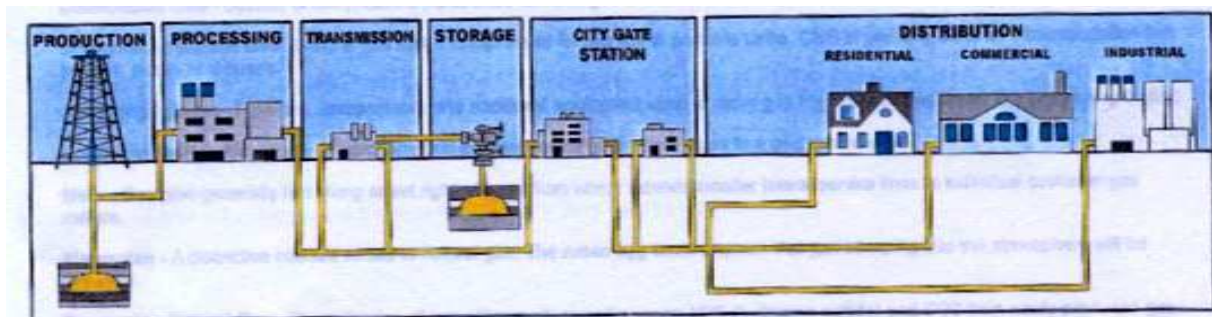


Fig. 5. Lay-out of infrastructure for natural gas supply.

Figure 5 shows a cartoon of a typical infrastructure lay-out for natural gas production, processing (impurity removal), transmission, storage, and distribution [23]. The gas leaves the transmission system and enters the distribution system at the city gate stations where it may be odorized by adding trace amounts of mercaptans as a safety measure for domestic use.

### Production of Fuel Cell Grade H<sub>2</sub> from Natural Gas

Catalytic reformation of CH<sub>4</sub> by reaction with steam is the most efficient and economically viable route of production of H<sub>2</sub> and many commercial processes employing this principle have been developed [24]. The primary reactions in the reforming reactor are:

- Endothermic steam-methane reforming (SMR) reaction :  

$$\text{CH}_4 + \text{H}_2\text{O} \leftrightarrow \text{CO} + 3\text{H}_2; \quad \Delta H_R = +206 \text{ kJ/mole} \quad (1)$$
- Exothermic water gas shift (WGS) reaction :  

$$\text{CO} + \text{H}_2\text{O} \leftrightarrow \text{CO}_2 + \text{H}_2; \quad \Delta H_R = -41 \text{ kJ/mole} \quad (2)$$
- Endothermic net reaction :  

$$\text{CH}_4 + 2 \text{H}_2\text{O} \leftrightarrow \text{CO}_2 + 4\text{H}_2; \quad \Delta H_R = +165 \text{ kJ/mole} \quad (3)$$

These reactions are controlled by the chemical thermodynamic equilibria, which dictate the preferred reaction conditions (pressure, temperature and feed H<sub>2</sub>O:CH<sub>4</sub> ratio), the H<sub>2</sub> conversion, and the composition of the SMR reaction product gas containing H<sub>2</sub> + CO<sub>2</sub> (bulk) + CO (dilute) + CH<sub>4</sub> (dilute) on a dry basis.

Figure 6 shows the equilibrium constants for the reversible SMR ( $K_{\text{SMR}}$ ) and WGS ( $K_{\text{WGS}}$ ) reactions [25], and the estimated thermodynamic conversion of CH<sub>4</sub> to H<sub>2</sub> by SMR as a function of reaction temperature (reactor pressure = 1.5 atm, feed H<sub>2</sub>O/CH<sub>4</sub> ratio = 5:1). It may be seen that the maximum conversion (~90%) of CH<sub>4</sub> to H<sub>2</sub> can be achieved at a reaction temperature of ~700 – 800°C. Such high temperature requires expensive metallurgy for reactor construction, and a rather complex system of heat management. Table 2 shows the equilibrium compositions of the SMR reactor gas at different operating temperatures for a reactor feed gas containing 5:1 H<sub>2</sub>O:CH<sub>4</sub> at 1.5 atm. It shows that the reactor effluent gas must be stringently purified in order to produce a stream of pure H<sub>2</sub>.

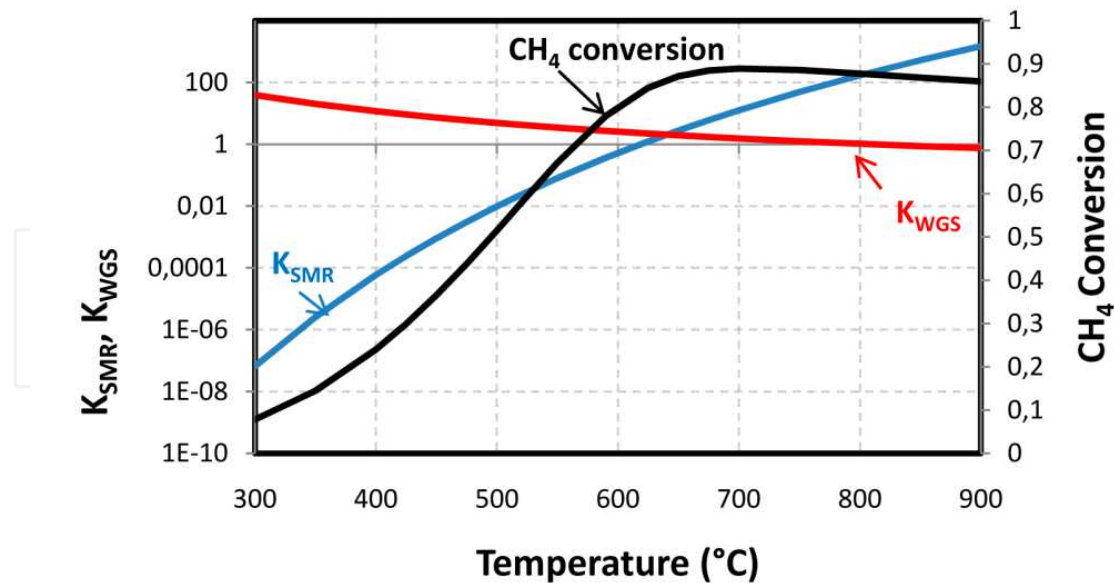


Fig. 6. Reaction equilibrium constants and thermodynamic  $\text{CH}_4$  to  $\text{H}_2$  conversion for SMR reaction.

Reaction Temperature (C)	Reactor effluent gas composition (dry basis) (mole %)			
	$\text{CO}_2$	$\text{CO}$	$\text{CH}_4$	$\text{H}_2$
800	11.39	10.75	0.03	77.83
700	13.18	8.45	0.32	78.06
590	15.41	4.70	4.18	75.71
550	15.87	3.11	8.15	72.87
520	15.89	2.09	12.21	69.82

Table 2. Equilibrium compositions of SMR reactor effluent gases.

### Conventional Process Scheme for $\text{H}_2$ Production by SMR [24]

The most common commercial method for production of high purity  $\text{H}_2$  (99.999+ %) from natural gas for fuel cell use consists of high temperature ( $\sim 800$  -  $900^\circ\text{C}$ ) catalytic steam-methane reforming (SMR), followed by catalytic water gas shifting (WGS) of the reaction products at  $\sim 300$  -  $400^\circ\text{C}$ , and finally purification of the WGS reactor effluent gas to produce pure  $\text{H}_2$  at feed gas pressure by employing a multi-step, multi column, pressure swing adsorption (PSA) process [24]. The feed natural gas to the process is pre-treated to remove trace S and N impurities, if needed. The PSA process is operated at a near ambient temperature ( $20$  -  $40^\circ\text{C}$ ) by employing physi-sorbents like zeolites, aluminas, and activated carbons for removal of the impurities ( $\text{H}_2\text{O}$ ,  $\text{CO}_2$ ,  $\text{CO}$ ,  $\text{CH}_4$ ,  $\text{N}_2$ ) from the  $\text{H}_2$  product gas. The feed gas to the PSA system typically contains 15 - 25 %  $\text{CO}_2$  + 1 - 4 %  $\text{CO}$  + 1 - 5 %  $\text{CH}_4$  + 0.2%  $\text{N}_2$  in  $\text{H}_2$  (dry basis). A waste gas containing all of the carbon impurities and un-recovered hydrogen is also produced by the PSA system which is used as fuel in the SMR furnace.

Figure 7 shows a simplified box diagram of the process for production of ultra pure H<sub>2</sub> from natural gas by the conventional SMR-WGS-PSA route.

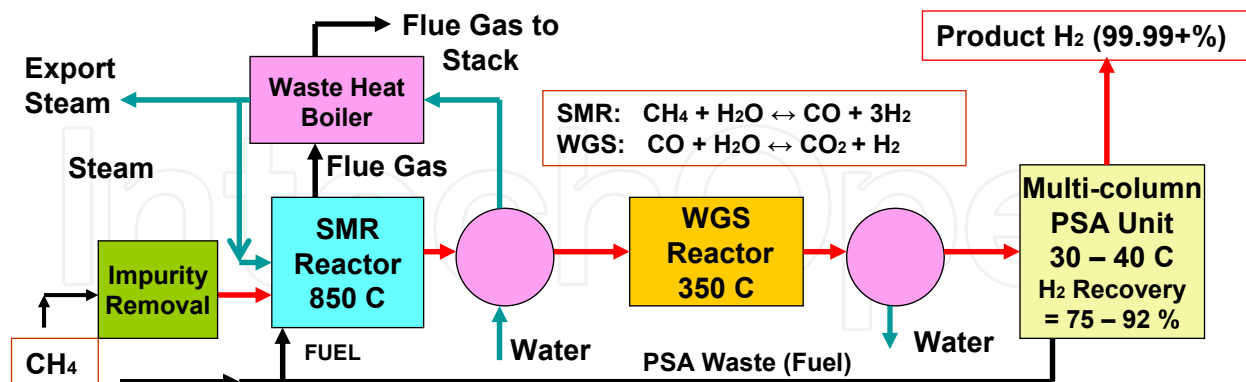


Fig. 7. Conventional steam-methane reforming route of H<sub>2</sub> production from natural gas.

Although the scheme shown by Figure 7 has become the state of the art technology for production of ~ 1 to 150 MMSCFD of H<sub>2</sub> from CH<sub>4</sub>, there are several unattractive but unavoidable features for scaling down the process for residential fuel cell use (H<sub>2</sub> demand for a 250 kW PEM fuel cell is only ~0.15 MMSCFD). These include (a) operation of the SMR reactor at high temperature, (b) use of a part of the purified H<sub>2</sub> product (8 -25%) to regenerate the PSA adsorbents by purge, thereby reducing the over-all recovery of H<sub>2</sub> produced by the SMR and WGS reactions, (c) generation of export steam in order to recover the excess heat required for the operation of the relatively low efficiency SMR reactor, and (d) fairly complex nature of the process using several unit operations which requires large footprint and capital cost.

### Alternative Process Scheme for H<sub>2</sub> production by SMR [1, 26]

An alternative process scheme has been developed for production of fuel cell grade H<sub>2</sub> from CH<sub>4</sub> by SMR [1, 26]. It replaces the PSA purification step of the conventional scheme of Figure 7 by a catalytic PROX /SELOX (Preferential/ Selective Oxidation) reactor which selectively oxidizes the residual CO (~ 1 - 4 %) from the WGS reactor effluent gas to CO<sub>2</sub> (CO + 0.5 O<sub>2</sub> → CO<sub>2</sub>) in presence of excess H<sub>2</sub> at a moderate temperature of 80 - 200°C. A small quantity of air is added to the PROX reactor feed to supply the oxygen needed for this purpose. The CO level can be reduced to ~ 10 ppm by the PROX concept. Figure 8 is a schematic box diagram for this approach.

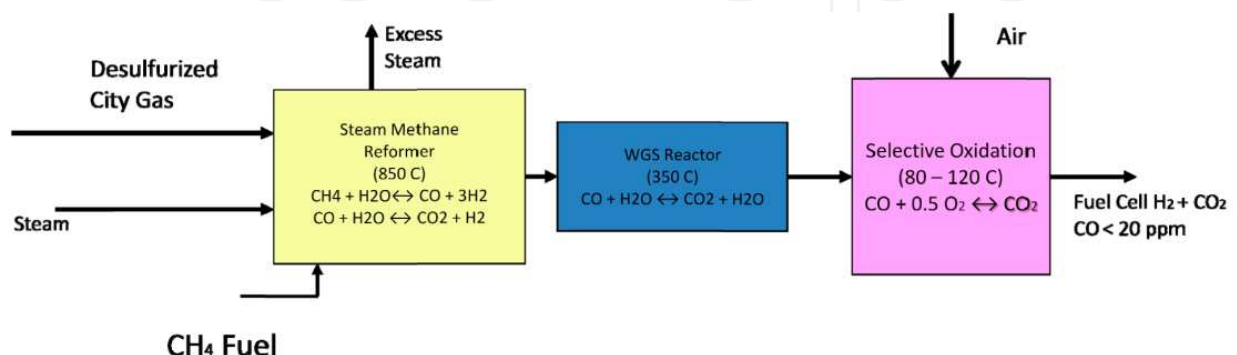


Fig. 8. Alternative steam-methane reforming route of H<sub>2</sub> production from natural gas.



Selectivity of CO oxidation to produce CO<sub>2</sub> vis a vis H<sub>2</sub> oxidation to produce H<sub>2</sub>O, and the absolute conversion of CO to CO<sub>2</sub> are two critical performance markers for the PROX catalyst. A large volume of research on mono- and bi- metallic PROX catalyst formulation, nature of support matrix, and method of preparation has been published, and the subject is an active area of research around the world [27 - 38]. The common catalysts include noble metals (Pt, Ru, Rh, Pd) supported on a porous matrix such as alumina [32, 38]. Some of them offer good catalytic activity (~ 100 % CO conversion with 30 - 50 % selectivity) in the temperature range of 130 - 200°C.

The performance of a PROX catalyst may substantially deteriorate in the presence of H<sub>2</sub>O and CO<sub>2</sub>. Figure 9 shows an example where both the CO conversion (solid lines) and selectivity (dashed lines) of a PROX catalyst [1% (1:1) Pt Au/CeO<sub>2</sub> produced by single step-sol-gel method] decrease substantially in presence of CO<sub>2</sub> in the reactant gas (1% CO, 1% O<sub>2</sub>, 0 - 25 % CO<sub>2</sub>, 40 % H<sub>2</sub> and balance He) at all temperatures [37].

Figure 10 shows another example of the performance of a PROX catalyst (Pt/FAU) at a temperature of 165°C where the CO conversion and selectivity were not affected by the presence of CO<sub>2</sub> and H<sub>2</sub>O in a long term stability test [38]. The reactant for this test contained 1.21 % CO, 2.9 % H<sub>2</sub>O, 25.25 % CO<sub>2</sub> and 70.63 % H<sub>2</sub>.

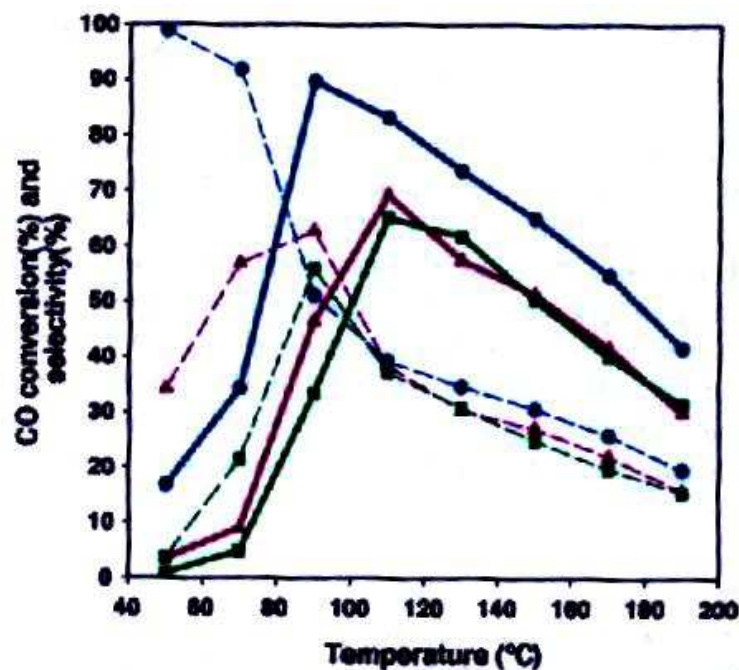


Fig. 9. Effect of CO<sub>2</sub> in feed gas on performance of a PROX catalyst.

● 0 % CO<sub>2</sub>, Δ 5 % CO<sub>2</sub> □ 25 % CO<sub>2</sub>

Reprinted from J. Power Sources, 163, 547-554 (2006) with permission from Elsevier.

Clearly, a practical PROX catalyst for producing an essentially CO free H<sub>2</sub> for fuel cell application must exhibit ~ 100 % CO conversion in presence of CO<sub>2</sub> and H<sub>2</sub>O. Less than 100 % CO oxidation selectivity may be acceptable albeit with the loss of some H<sub>2</sub> produced by SMR. The presence of CO<sub>2</sub> in the effluent gas from a PROX reactor, however, can be the cause of anode deactivation of a PEM fuel cell due to reformation of CO by RWGS reaction as discussed earlier.

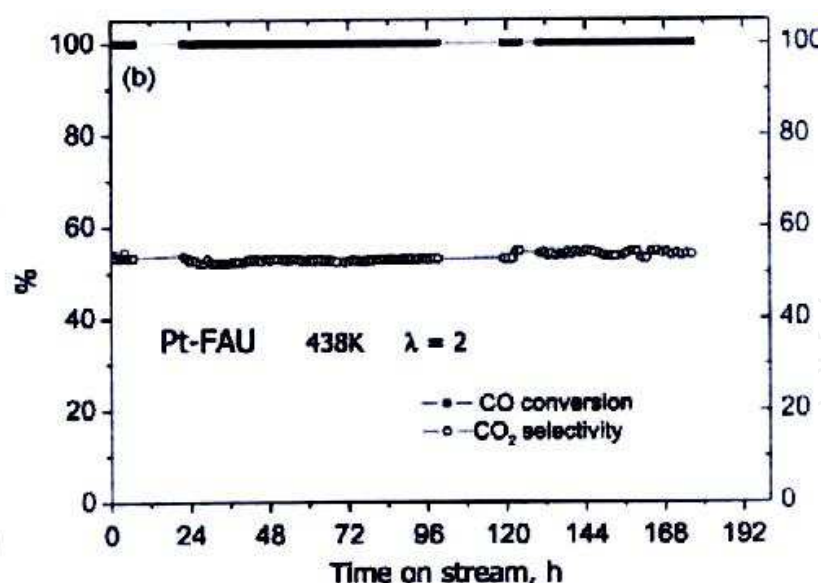


Fig. 10. Performance of Pt/Fau PROX catalyst. Reprinted from Applied Catalysis A; General, 366, 242-251 (2009) with permission from Elsevier.

### Sorption Enhanced Reaction (SER) Concepts for H<sub>2</sub> Production by Low Temperature SMR

Recently, several novel adsorptive process concepts called 'sorption enhanced reaction (SER)' have been designed to substantially enhance the performance of SMR and WGS reactors for production of fuel cell grade H<sub>2</sub> from CH<sub>4</sub> by circumventing the thermodynamic limitations of these reactions. The key benefits include:

- Drastically increase the H<sub>2</sub> product purity and conversion in a single unit operation
- Significantly lower the SMR reaction temperature without sacrificing process performance
- Enhance the kinetics of the forward SMR reaction
- Increase the over-all H<sub>2</sub> recovery from the plant
- Reduce the plant foot print and cost by integration of the reactors (SMR and WGS) and the PSA unit as a single unit operation, and by lowering the temperature of SMR reaction (easier heat management and loss).

These advantages are achieved by applying the Le Chatelier's principle, whereby one of the reaction products, CO<sub>2</sub>, is selectively removed from the reaction zone at the reaction temperature. An admixture of a reversible CO<sub>2</sub> chemisorbent, which can selectively sorb CO<sub>2</sub> in presence of steam at the reaction temperature, and an SMR catalyst is used in the sorber-reactor for this purpose. The chemisorbent is periodically regenerated for re-use by desorbing the CO<sub>2</sub> using the principles of pressure swing adsorption (PSA) or thermal swing adsorption (TSA) processes.

A recent monograph entitled 'Sorption Enhanced Reaction Concepts for Hydrogen Production: Materials and Processes' [39] and a review article entitled 'Reversible Chemisorbents for CO<sub>2</sub> and their Potential Applications' [40] describe the current state of the art on the SER processes for H<sub>2</sub> production by SMR and the CO<sub>2</sub> chemisorbents used in them. Chemisorbents utilizing either bulk (e.g. CaO) or surface (e.g. K<sub>2</sub>CO<sub>3</sub> promoted

hydrotalcite) reactions with  $\text{CO}_2$  have been used in these processes [39, 40]. Fixed bed sorber-reactors using both types of chemisorbents have been considered by most authors [39], while a fluidized bed sorber-reactor using the first type of chemisorbent has been evaluated by Harrison [39, 41].

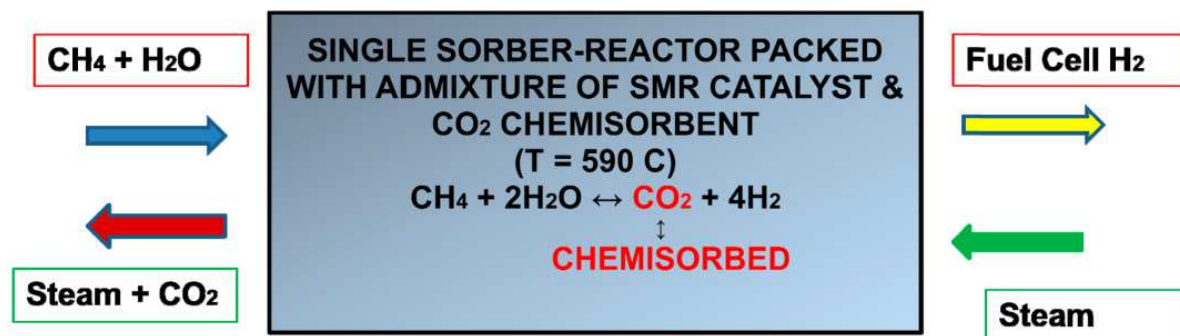


Fig. 11. Conceptual sketch of SER SMR process concepts.

A fixed-bed cyclic SER process employing a  $\text{CO}_2$  chemisorbent utilizing surface reaction may be preferred for the residential fuel cell application because of (a) direct production of high purity  $\text{H}_2$  by SMR with high conversion of  $\text{CH}_4$  to  $\text{H}_2$ , (b) relatively lower temperature of operation, (c) ease of  $\text{CO}_2$  regeneration using conventional principles of pressure or thermal swing adsorption processes, (d) use of steam purge for  $\text{CO}_2$  desorption, (e) process compactness, (f) faster chemisorption kinetics, and (g) absence of sorbent transportation. Figure 11 is a conceptual drawing of a generic fixed-bed SER process concept for directly producing fuel cell grade  $\text{H}_2$  by low temperature SMR.

### Surface reaction based $\text{CO}_2$ chemisorbent used in SER processes for $\text{H}_2$ production by SMR

$\text{K}_2\text{CO}_3$  promoted hydrotalcite has been found to be an acceptable  $\text{CO}_2$  chemisorbent for fixed-bed adsorptive SER processes (PSA or TSA) operated at a temperature of  $400 - 550^\circ\text{C}$  for production of fuel cell grade  $\text{H}_2$  by SMR [40, 42] because it provides (i) a decent cyclic  $\text{CO}_2$  working capacity under a pressure or thermal swing mode of SER process operation, (ii) fast  $\text{CO}_2$  chemisorption kinetics, (iii) moderate isosteric heat of  $\text{CO}_2$  sorption, (iv) nearly infinite selectivity of sorption for  $\text{CO}_2$  in presence of steam,  $\text{CO}$ ,  $\text{CH}_4$  and  $\text{H}_2$ , (v) relatively easy desorption of  $\text{CO}_2$  by purge using steam, and (vi) thermal stability. Some of the key relevant characteristics of  $\text{CO}_2$  chemisorption on the material are described below:

#### Chemisorption Equilibria [40, 42]:

Figure 12 shows the equilibrium  $\text{CO}_2$  chemisorption isotherms on a sample of the promoted hydrotalcite at different temperatures. An analytical isotherm model incorporating simultaneous Langmuirian surface chemisorption and an additional surface reaction between the chemisorbed and gaseous  $\text{CO}_2$  molecules describes the isotherms adequately (lines in Figure 12). The heats of these reactions are moderate, being respectively, 5.0 and 10.1 Kcal/mole.

Mass transfer rate for CO<sub>2</sub> chemisorption [40, 42, 53]:

The conventional linear driving force (LDF) model was found to adequately describe the over-all mass transfer of CO<sub>2</sub> on promoted hydrotalcite [40]. The same LDF mass transfer coefficient (k) described both sorption and desorption of CO<sub>2</sub>. Figure 13 shows the temperature coefficient of k [40, 53]. The activation energy for k was 4.5 Kcal/mole.

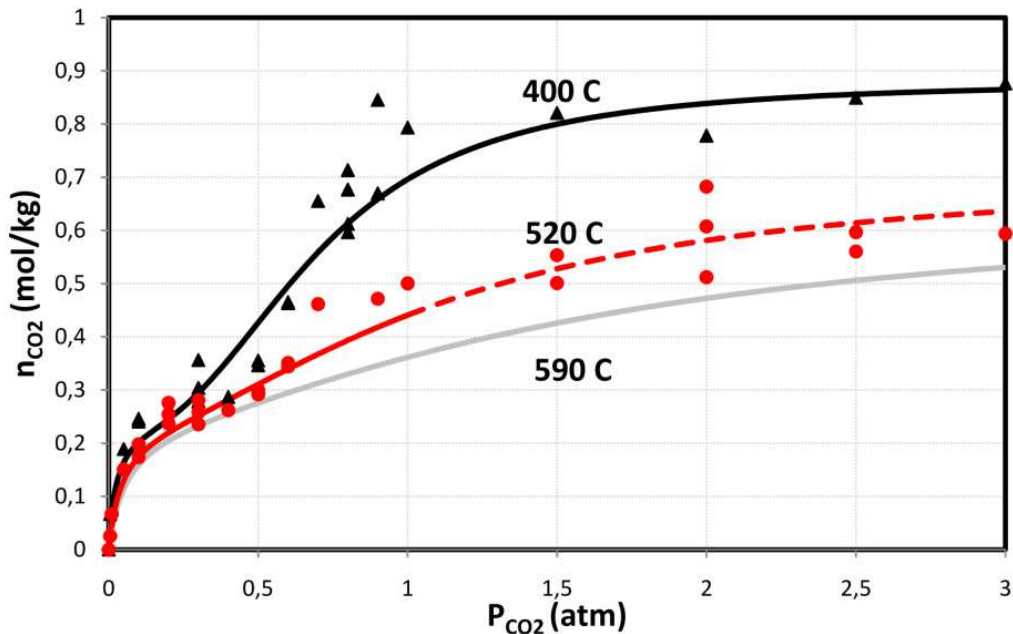


Fig. 12. Chemisorption isotherms of CO<sub>2</sub> on K<sub>2</sub>CO<sub>3</sub> promoted hydrotalcite.

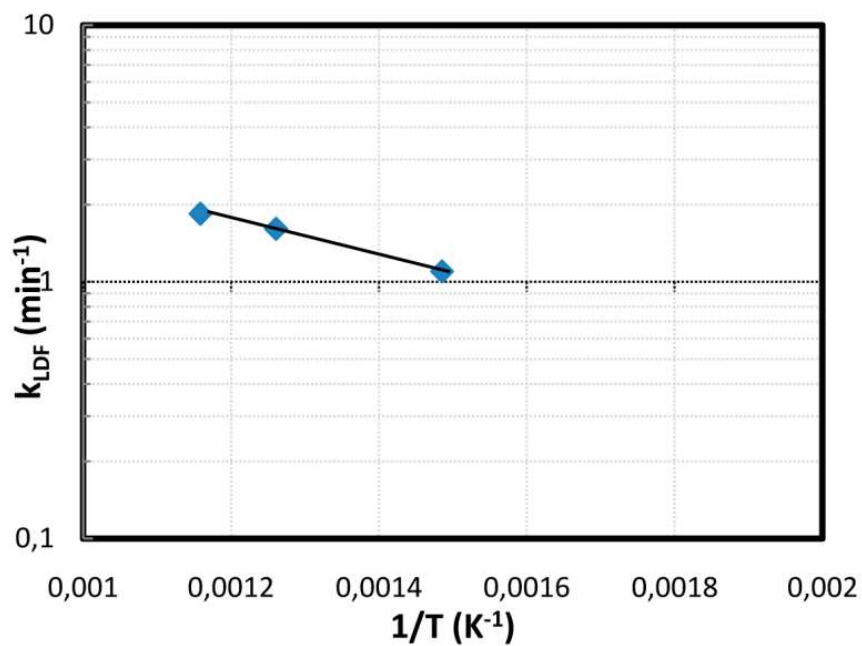


Fig. 13. Temperature dependence of CO<sub>2</sub> mass transfer coefficient on K<sub>2</sub>CO<sub>3</sub> promoted hydrotalcite.

### Experimental demonstration of SER-SMR concept [53]:

Figure 14 experimentally demonstrates the SER concept using a packed column (63.4 cm long) of a 2:1 admixture of  $K_2CO_3$  promoted hydrotalcite and a commercial  $Ni/Al_2O_3$  SMR catalyst (Sud Chemie Corp.). A pre-heated feed gas mixture containing  $\sim 37$  mole %  $H_2O$  + 7.4 mole %  $CH_4$  + Ar was passed through the column at near ambient pressure. The column was initially heated to  $550^\circ C$  and filled with Ar.

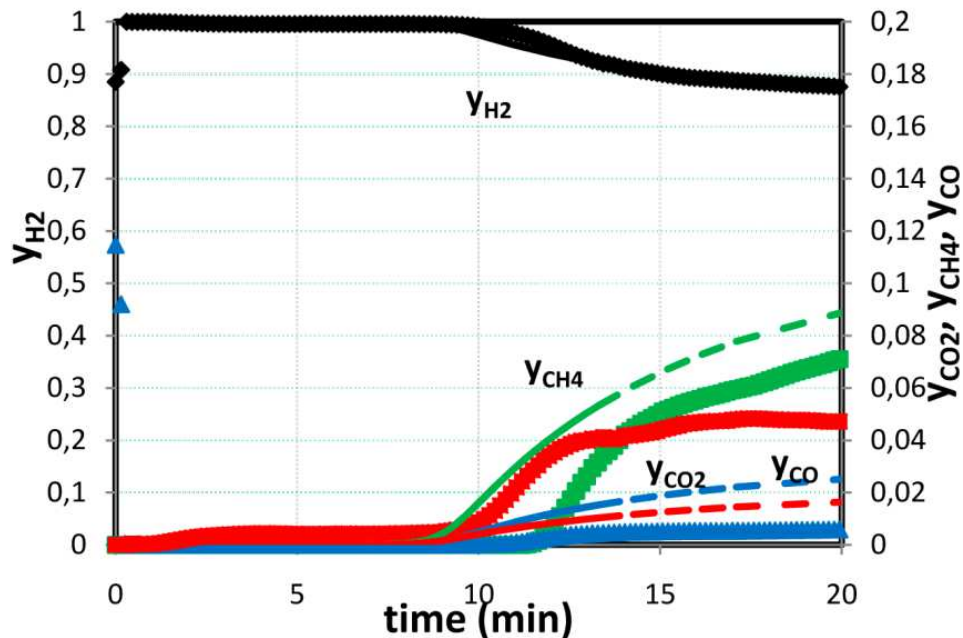


Fig. 14. Experimental demonstration of SER- SMR concept at  $550^\circ C$  using promoted hydrotalcite.

It may be seen from Figure 14 that the effluent gas from the sorber- reactor (solid lines) contained a stream of high purity  $H_2$  ( $CO_x < 20$  ppm) which was suitable for use in a  $H_2$  fuel cell for a period of time. Thereafter,  $CO$ ,  $CH_4$ , and  $CO_2$  simultaneously broke through the sorber-reactor and their mole fractions rapidly rose to different plateau levels which corresponded to the thermodynamic reaction product concentrations of the SMR reaction (without the chemisorbent) at the reaction temperature. The average  $CH_4$  mole fraction of the high purity  $H_2$  product stream was 0.35 mole %. The conversion of feed  $CH_4$  to pure  $H_2$  product was 98.6 %. The dashed lines in the Figure are simulated performance using a model [53].

### Pressure swing sorption enhanced reaction (PSSER) process

A pressure swing sorption enhanced reaction (PSSER) process for low temperature ( $\sim 500^\circ C$ ) SMR was designed by Sircar and coworkers [43, 44]. The process employed a pair of fixed bed sorber-reactors and it could directly produce a fuel-cell grade  $H_2$  using  $K_2CO_3$  promoted hydrotalcite as the  $CO_2$  chemisorbent in the process. The sorbent was periodically regenerated by purging it with steam at the reaction temperature under a sub-atmospheric pressure condition. The cyclic process consisted of four steps: (a) sorption -reaction at a super-ambient pressure to produce the fuel-cell grade  $H_2$  product at feed gas pressure, (b)

counter-current depressurization to near ambient pressure, (c) counter-current steam purge at sub-atmospheric pressure, and (d) counter-current pressurization with steam to feed pressure. These PSSER process steps were operated under a nearly isothermal condition.

A shell and tube reactor design was suggested for the above-described PSSER process. Two different types of indirect heat transfer methods were also proposed for supplying the endothermic heat of SMR reaction and heat for CO<sub>2</sub> desorption. They consisted of (a) flowing a vaporized heat transfer liquid through the shell side of the reactor so that the condensing vapor would supply the heat of reaction in the reactor and maintain a constant reactor temperature during all steps of the process, and (b) indirect gas heating (IGH) by flowing a hot flue gas through the shell side of the reactor with finned tubes to supply the heat of reaction [43].

Figure 15 is a schematic flow diagram of a two column PSSER system for production of H<sub>2</sub>. An example of the cyclic steady state performance of the PSSER process from a pilot scale test apparatus is given in Table 3 which shows that fuel-cell grade H<sub>2</sub> with high CH<sub>4</sub> to H<sub>2</sub> conversion can be achieved by the process. Sircar and co-workers also proposed that the performance of the PSSER process could be improved by (a) use of a catalyst only section in the feed end of the sorber-reactor, (b) using a dilute amount of H<sub>2</sub> with the purge steam, and (c) imposing a moderately increasing temperature gradient from the feed to the product end of the sorber-reactor [45].

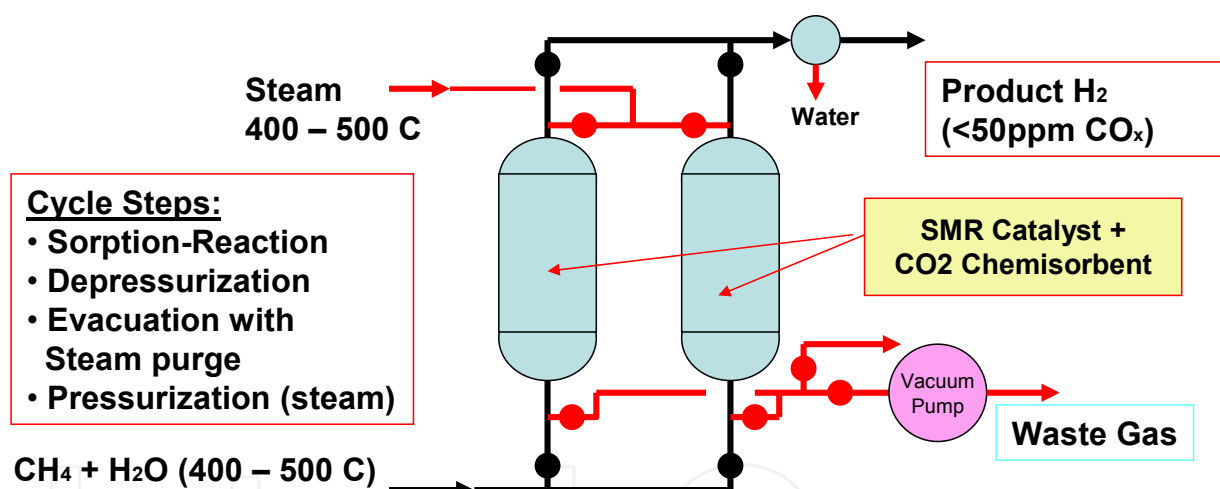


Fig. 15. Schematic flow sheet of a PSSER system.

Process	H <sub>2</sub> Product Purity (dry basis)	H <sub>2</sub> Productivity (mol/kg)	CH <sub>4</sub> to H <sub>2</sub> Conversion (net)	Steam Purge Duty (mol. steam per mol. of H <sub>2</sub> Product)
PSSER [Experimental] 6:1 H <sub>2</sub> O:CH <sub>4</sub> Feed P = 1.78 bar; T = 490°C Catalyst = 33%	H <sub>2</sub> = 94.4 % CH <sub>4</sub> = 5.6 % CO = <30 ppm CO <sub>2</sub> = 40 ppm	0.25	73 %	7.5 (Needs Vacuum)
TSSER [Simulated] 4:1 H <sub>2</sub> O: CH <sub>4</sub> Feed P = 1.5 bar; T = 490°C Catalyst = 10 %	H <sub>2</sub> = 99.99 % CH <sub>4</sub> = 60 ppm CO = 10 ppm CO <sub>2</sub> = 13 ppm	0.39	96.4 %	5.8

Table 3. Performance of PSSER and TSSER processes

Rodrigues and co-workers [46-50] developed a detailed mathematical model of the above-described PSSER process to simulate its performance for producing fuel-cell grade hydrogen. The model simulations were also used to investigate several new operational schemes for improving the performance of the PSSER process (higher conversion and purer H<sub>2</sub>). They included (a) introduction of a purge step with a mixture of N<sub>2</sub> and H<sub>2</sub> prior to steam purge, and (b) packing different sections (three) of the sorber-reactor using different catalyst-sorbent ratios, the sections at the feed and the product ends being lean in sorbent, and operating the sections at different temperatures, the product -end section having a lower temperature.

### Thermal swing sorption enhanced reaction (TSSER) process

A rapid thermal swing sorption enhanced reaction (TSSER) process for low temperature (~ 520 - 590°C) SMR was recently designed by Sircar and co-workers [51 - 53]. The process employed a pair of fixed bed sorber-reactors and it could directly produce fuel-cell grade H<sub>2</sub> using K<sub>2</sub>CO<sub>3</sub> promoted hydrotalcite as the CO<sub>2</sub> chemisorbent in the process. The process uses two cyclic steps:

(a) **sorption-reaction step** where a mixture of H<sub>2</sub>O and CH<sub>4</sub> is fed at a pressure of ~ 1.5-2.0 bar and a temperature of ~ 490°C into a fixed-bed reactor, which is packed with an admixture of the SMR catalyst and the chemisorbent, and which is pre-heated to ~ 520 - 590°C. The effluent from the reactor is fuel-cell grade H<sub>2</sub> at feed pressure.

(b) **thermal regeneration step** where the reactor is simultaneously depressurized to near-ambient pressure and counter-currently purged with superheated steam at ambient pressure and at ~ 520 - 590°C, followed by counter-current pressurization of the reactor with steam at ~520 - 590°C to the feed pressure. The reactor effluent for this step is a CO<sub>2</sub> rich waste gas.

The key advantages of the proposed TSSER concept over the above-described PSSER process are (a) elimination of the usually expensive, sub-atmospheric steam purge step for desorption of CO<sub>2</sub> and, consequently absence of a rotating machine (vacuum pump) in the process, (b) direct supply of the heat of endothermic SMR reaction from the sensible heat stored in the reactor at the start of step (a), (c) higher utilization of the specific CO<sub>2</sub> capacity of the chemisorbent in the cycle due to more stringent regeneration, (d) higher conversion of CH<sub>4</sub> to H<sub>2</sub>, (e) higher purity of H<sub>2</sub> product, and (f) lower steam purge requirement per unit amount of H<sub>2</sub> product.

Figure 16 is a schematic drawing of a two-column embodiment of the concept using a shell and tube design of the sorber-reactors. The tubes will be packed with an admixture of the SMR catalyst and the CO<sub>2</sub> chemisorbent. The outside walls of the tubes will be maintained at a constant temperature by cross-flowing super-heated steam in the shell side. Figure 16 clearly exhibits the compactness of the proposed idea compared with the rather involved flow sheet for the conventional SMR-WGS-PSA route of Figure 7.

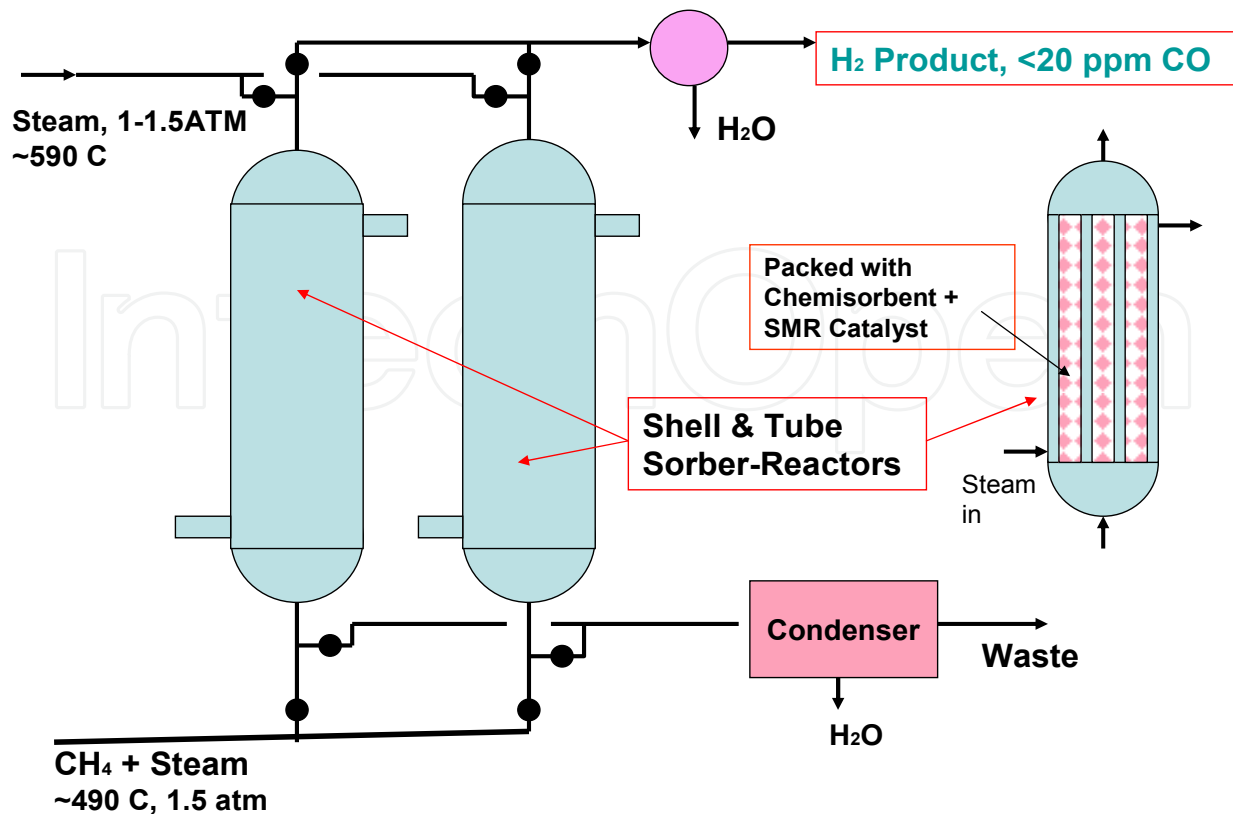


Fig. 16. Schematic drawing of the TSSER concept.

The performance of a TSSER process design [sorber-reactor tubes (I.D = 2.54 cm, length,  $L_c = 250$  cm) packed with an admixture of a commercial SMR catalyst (10 %) and promoted hydrotalcite (90 %)] was estimated using a mathematical model which simulated the operation of the individual steps (10 minutes each) of the process. A detailed description of the model can be found elsewhere [51]. The thermodynamic and kinetic properties of the SMR reaction were obtained from the published literature [25, 54], and those for chemisorption of  $\text{CO}_2$  are given by Figures 12 and 13. The feed gas ( $\text{H}_2\text{O}:\text{CH}_4 = 5:1$ ,  $P = 1.5$  atm,  $T = 450$  C) was introduced to the sorber-reactor which was preheated to 520, 550, or 590 C.

Figure 17 shows an example of the simulation results. The profiles of  $\text{CO}_2$  loadings are plotted as a function of dimensionless distance ( $L/L_c$ ) in the sorber-reactor at the ends of steps (a) and (b) of the TSSER process at three different reaction temperatures [53]. The superior performance of the process at higher reaction temperatures is self evident.



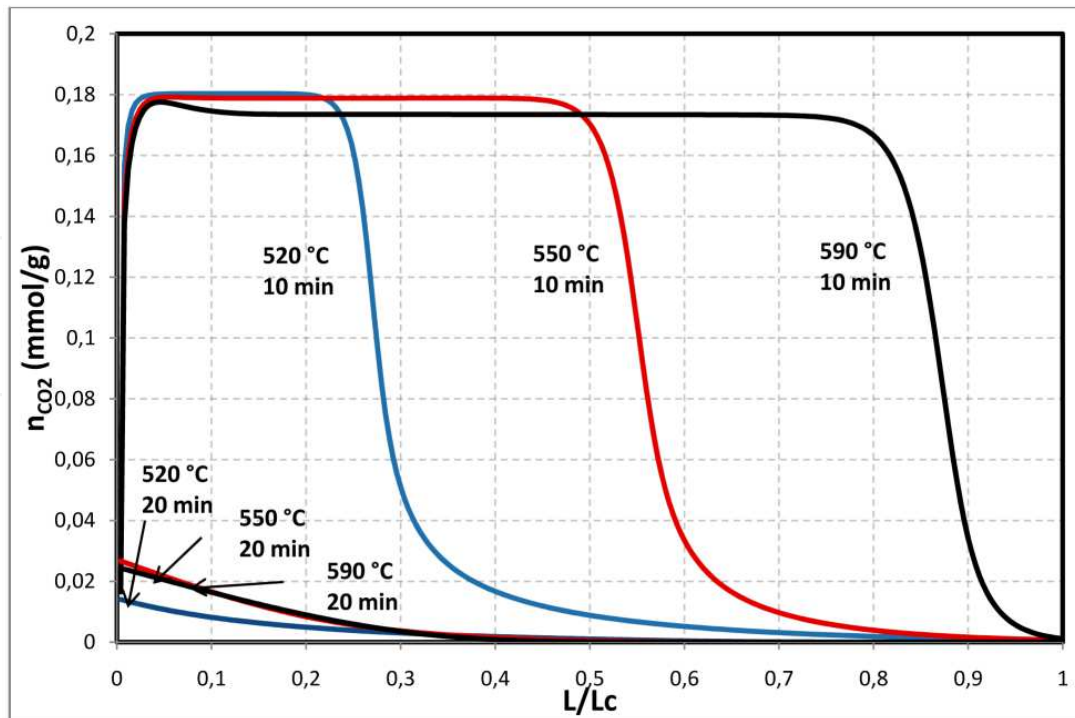


Fig. 17. Simulated profiles of CO<sub>2</sub> loadings in sorber-reactor: End of step (a) – solid lines (10 min); end of step (b) – dashed lines (20 min).

Table 4 summarizes the simulation results. It may be seen that the TSSER concept produces fuel cell grade H<sub>2</sub> by low temperature SMR with very high CH<sub>4</sub> to H<sub>2</sub> conversion at all temperatures. The specific H<sub>2</sub> productivity (mol. kg<sup>-1</sup> of total solid in sorber reactor) however increases and the steam purge duty by the process decreases as the reaction T is increased from 520 to 590°C.

It may also be seen from Table 4 that the conversion of CH<sub>4</sub> to H<sub>2</sub> and the purity of H<sub>2</sub> product achieved by the TSSER concept far exceed those governed by the thermodynamics of catalyst-only SMR reaction (Figure 6 and Table 2) at any given temperature. Consequently, the concept permits operation of the SMR reaction at a much reduced temperature without sacrificing product H<sub>2</sub> conversion and purity.

Reactor Feed		Reactor T (°C)	H <sub>2</sub> Product Purity (ppm)	H <sub>2</sub> Productivity (moles/kg of total solid)	Feed CH <sub>4</sub> to Product H <sub>2</sub> Conversion (%)	Steam purge duty for regeneration in step (b) (moles/mole of H <sub>2</sub> product)
CH <sub>4</sub> : H <sub>2</sub> O	Pressure (Bar)					
1:5	1.5	590	CO = 10 CO <sub>2</sub> = 13 CH <sub>4</sub> = 60	0.440	99.8%	7.2
1:5	1.5	550	CO = 10 CO <sub>2</sub> = 23 CH <sub>4</sub> = 129	0.296	99.5%	8.2
1:5	1.5	520	CO = 10 CO <sub>2</sub> = 31 CH <sub>4</sub> = 480	0.157	99.1%	13.3

Table 4. Simulated performances of the TSSER concept

The model was also used to evaluate the performance of the TSSER process under conditions identical to that used for the PSSER process reported in Table 3. The comparative results given in Table 3 demonstrate the superiority of the TSSER concept (higher H<sub>2</sub> purity, higher specific H<sub>2</sub> productivity by the catalyst-chemisorbent admixture, and higher CH<sub>4</sub> to H<sub>2</sub> conversion).

It should be mentioned here that the model was also used to simulate the performance of another rapid TSSER process designed for simultaneous production of fuel cell grade H<sub>2</sub> and a compressed CO<sub>2</sub> by-product stream to facilitate its sequestration from a synthesis gas produced by gasification of coal [55].

### Thermal efficiency of the TSSER concept

A thermal efficiency for this process was defined as

$$\eta_{Th} = \frac{LHV_{H_2 \text{ Product}}}{LHV_{NG \text{ feed}} + LHV_{NG \text{ fuel}}} \quad (4)$$

where  $LHV_{NG \text{ feed}}$  = heating value of the natural gas fed into the TSSER unit,  $LHV_{NG \text{ fuel}}$  = heating value of supplemental fuel for (a) supplying additional heat of SMR reaction, (b) adding additional heat to feed and desorption gas streams, and (c) supplying heat of desorption to the bed for regeneration of the sorbent. Assuming LHV values of 120.1 MJ/kg and 47.1 MJ/kg for H<sub>2</sub> and natural gas, respectively, the thermal efficiency of the TSSER process was calculated to be 79.6%. This shows that the process is highly efficient for production of H<sub>2</sub> from CH<sub>4</sub>.

**The TSSER process will potentially provide an efficient but relatively simple and compact alternative for direct production of fuel-cell grade hydrogen by low temperature SMR without producing export steam.**

Figure 18 is a heat integrated flow diagram of a TSSER concept designed for production of hydrogen for a 250 KW residential PEM fuel cell which requires ~ 3 kilo liters of H<sub>2</sub> per minute. The system contains two shell and tube sorber-reactors, heat exchangers, make-up heaters and blowers. Each sorber-reactor contains 2665 tubes [2.54 cm ID x 250 cm long, intra tube void fraction = 0.25, each packed with ~ 1.1 kg of an admixture of the SMR catalyst (10%) and CO<sub>2</sub> chemisorbent]. The feed (5:1 steam: methane) to the reactor was at 450°C and at a pressure of 1.5 bar. The reaction temperature was 590°C. The cycle time for each step was 10 minutes. The design was based on the simulated performance data of Table 4.

A first pass estimation of the capital and operating costs (\$/kg of H<sub>2</sub>) of the TSSER process for H<sub>2</sub> production for a 250 KW residential fuel cell is given in Table 5 which indicates that the cost is very competitive (cost of distributed production from natural gas ~ \$ 2.5- 3.5 /kg of H<sub>2</sub>)[56].

### Design & Cost of a TSSER Process for a Residential Fuel Cell

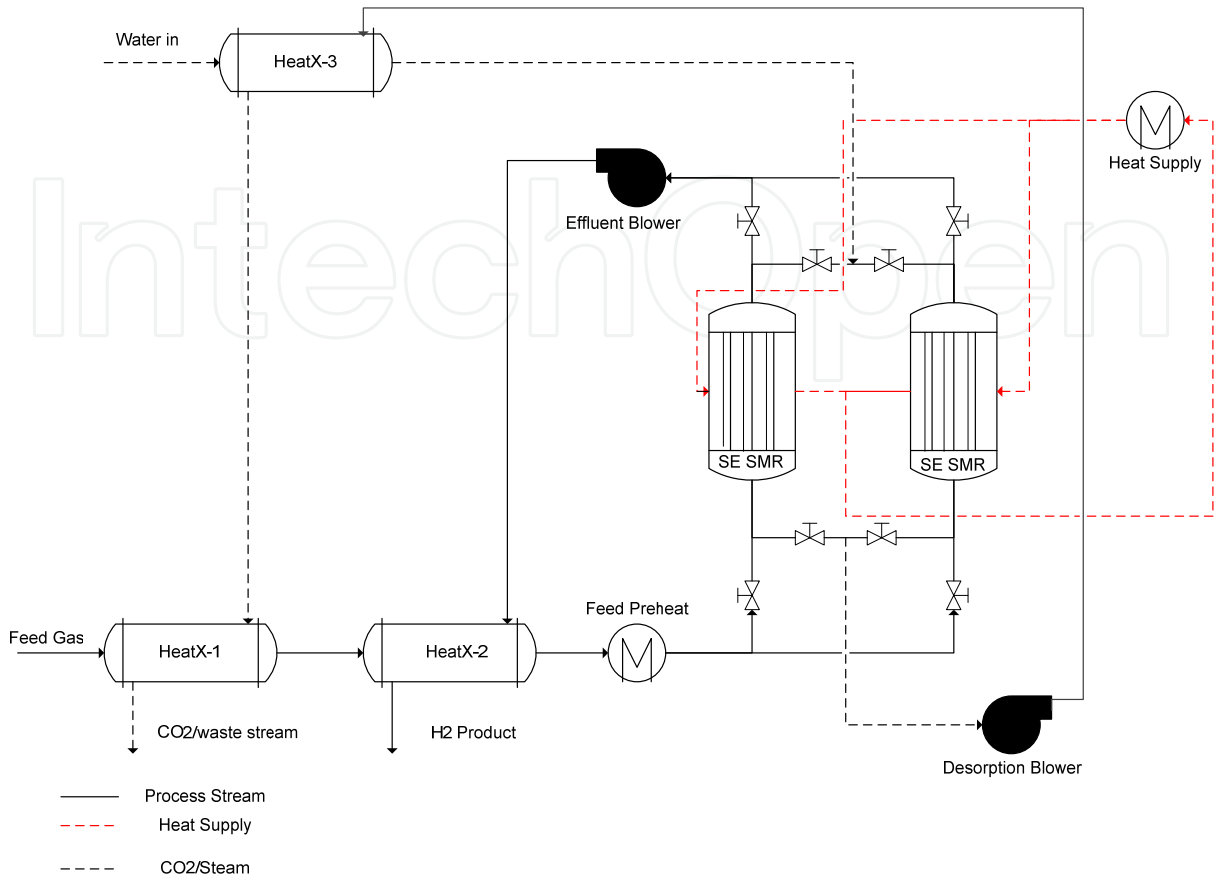


Fig. 18. Tentative flow sheet for a TSSER system supplying  $H_2$  to a 250 kW residential PEM fuel cell.

<b>Capital Costs, \$/kg <math>H_2</math></b>	250 kW
SER-SMR vessels	0.13
Over all Vessel dimensions	5.0' Dia. 8.2' High
Blowers	0.11
Heat Exchangers	0.02
Sorbent/catalyst	0.01
<b>Total</b>	<b>0.27</b>
<b>Operating costs, (\$/kg <math>H_2</math>)</b>	
Electricity for blowers	0.65
Steam consumption	0.02
Supplemental heat	0.14
<b>Total</b>	<b>0.71</b>

Table 5. First pass cost estimation of TSSER process.

## Summary

Decentralized residential power generation employing a H<sub>2</sub> PEM fuel cell requires that essentially CO<sub>x</sub> free H<sub>2</sub> be produced on site by catalytic steam reforming of piped natural gas and then purifying the product H<sub>2</sub> (removal of bulk CO<sub>2</sub> and dilute CO impurities). Currently, it may be achieved by subjecting the reformed gas to water gas shift reaction followed by (a) removal of all impurities by a PSA process or (b) selective oxidation in a catalytic PROX reactor to reduce only the CO impurity below ~ 10 ppm for use in the fuel cell. The latter approach assumes that the detrimental effect of CO<sub>2</sub> on the performance of the fuel cell is minimum. This assumption may not be valid.

A recently developed thermal swing sorption enhanced reaction (TSSER) process scheme can be used to combine reformation, shifting, and purification in a compact, single unit operation for this application. The process permits circumvention of the thermodynamic limits of the SMR reaction and permits direct production of fuel cell grade H<sub>2</sub> with high recovery and purity, yet operating the SMR reaction at a lower temperature. Simulated performance of the process, preliminary process design for supplying H<sub>2</sub> to a 250 KW fuel cell, and first pass costs are described.

## References

1. Okoda, O., Yokoyama, K, Development of polymer electrolyte fuel cell cogeneration systems for residential applications, *Fuel Cells*, 1, 72 (2001)
2. Jackson, C., Dudfield, C., Moore, J, PEM Fuel cell technology feature- for small scale stationary power, Intelligent Energy Ltd., Loughborough, UK.
3. Walsh, B., Wichert, R, Fuel cell technology, [wbdg.org/resources/fuelcell.php](http://wbdg.org/resources/fuelcell.php)
4. Lasher, S., Zogg, R., Carlson, E., Couch, P., Hooks, M., Roth, K., Brodrick, J, PEM fuel cells for distributed generation, *ASHRAE J.*, pp45-46, (2006).
5. Sinyak, Yu. V., Prospects for hydrogen use in decentralized power and heat supply, *Studies on Russian Economic Development*, Springer Science, 18, 264-275 (2007).
6. Jean, G. V, Hydrogen fuel cells to power homes, vehicles in Japan, [nationaldefensemagazine.org/archive/2008](http://nationaldefensemagazine.org/archive/2008)
7. Residential fuel cell heat & power system, [Acumentrics.com/products-fuel-cell-home-energy.htm](http://Acumentrics.com/products-fuel-cell-home-energy.htm)
8. Home power hydrogen fuel cells, [absak.com/library/small-hydrogen-fuel-cell-generators](http://absak.com/library/small-hydrogen-fuel-cell-generators) (2008).
9. Fuel cells come home. [Homeenergy.org/archive/hem.dis.anl.gov](http://Homeenergy.org/archive/hem.dis.anl.gov) (1998).
10. Residential PEM fuel cell system, [e1ps.tripod.com/fuelcellfuture/id4.html](http://e1ps.tripod.com/fuelcellfuture/id4.html)
11. Proton exchange membrane fuel cell, [en.wikipedia.org/wiki/Proton\\_exchange\\_membrane\\_fuel\\_cell](http://en.wikipedia.org/wiki/Proton_exchange_membrane_fuel_cell)
12. The fuel cell, [batteryuniversity.com/parttwo-52.htm](http://batteryuniversity.com/parttwo-52.htm)
13. Types of fuel cells, Department of energy, [1.eere.energy.gov/hydrogenandfuelcells/fuelcells/fc\\_types.html](http://1.eere.energy.gov/hydrogenandfuelcells/fuelcells/fc_types.html)
14. Bruijn, F. A., Papageorgopoulos, D. C., Sitters, E. F., Janssen, G. J. M, The influence of carbon dioxide on PEM fuel cell anodes, *J. Power Sources*, 110, 117-124 (2002).

15. Uribe, F., Brosha, E., Garzon, F., Mikkola, M., Pivovar, B., Rockward, T., Valerio, J., Wilson, M, Effect of fuel and air impurities on PEM fuel cell performance, DOE Hydrogen Program Project Report (2005).
16. Auer, E., Freund, A., Lehmann, T, CO-tolerant anode catalyst for PEM fuel cells and a process for its preparation, U.S. Patent 6,007,934 (1999)
17. Lee, S. J., Mukerjee, S., Ticianelli, E. A., McBreen, J, Electrocatalysis of CO tolerance in hydrogen oxidation reaction in PEM fuel cells, *Electrochimica Acta.*, 44, 3283-3293 (1999)
18. Yu, H., Hou, Z., Yi, B., Lin, Z, Composite anode for CO tolerance PEM fuel cells, *J. Power Sources*, 105, 52-57 (2002).
19. Divisek, J., Oetjen, H. F., Peinecke, V., Schmidt, V. M., Stimming, U, Components for PEM fuel cell systems using hydrogen and CO containing fuels, *Electrochimica Acta.*, 43, 3811-3815 (1998).
20. Bayrakceken, A., Turker, L., Eroglu, I, Improvement of carbon dioxide tolerance of PEMFC electrocatalyst by using microwave irradiation technique, *Int. J. Hydrogen Energy*, 33, 7527-7537 (2008).
21. Tanaka, K. I., Shou, M., He, H., Zhang, C., Lu, D, A CO-tolerant hydrogen fuel cell system designed by combining with an extremely active Pt/CNT catalyst, *Catalyst Letters*, 127, 148-151 (2009).
22. Farrauto, R., Hwang, S., Shore, L., Ruettinger, W., Lampert, J., Giroux, T., Liu, Y., Iloinich, O, New material needs for hydrocarbon fuel processing: Generating hydrogen for the PEM fuel cell, *Annual Review of Materials Research*, 33, 1 - 27 (2003).
23. Why natural gas? Learn about natural gas, [foodtechinfo.com/Why\\_Gas/Learn\\_About\\_Natural\\_Gas.htm](http://foodtechinfo.com/Why_Gas/Learn_About_Natural_Gas.htm)
24. Leiby, S. M, Options for refinery hydrogen, PEP Report No. 212, Process Economics Program, SRI International, Menlo Park, CA. (Feb. 1994).
25. Twigg, M. V., ed, *Catalyst Handbook*, Wolfe, London (1989).
26. Ghencu, A. F, Review of fuel processing catalysts for hydrogen production in PEM fuel cell systems, *Current Opinion in Solid State and Material Science*, 6, 389-399 (2002).
27. Avgouropoulos, G., Ioannides, T., Papadopoulos, Ch., Batista, J., Hocevar, S., Matralis, H. K, A comparative study of PtY-Al<sub>2</sub>O<sub>3</sub>, Au/ $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> and CuO-CeO<sub>2</sub> catalysts for the selective oxidation of carbon monoxide in excess hydrogen, *Catalysis Today*, 75, 157-167 (2002).
28. Snytnikov, P. V., Sobyenin, V. A., Belyaev, P., Tsyruinikov, G., Shitova, N. B., Shiyapin, D. A, Selective oxidation of carbon monoxide in excess hydrogen over Pt-, Ru- and Pd supported catalysts, *Applied Catalysis A: General*, 239, 149-156 (2003).
29. Roh, H. S., Potdar, H. S., Jun, K. W., Han, S. Y., Kim, J. W, Low temperature selective CO oxidation in excess of H<sub>2</sub> over Pt/Ce-ZrO<sub>2</sub> catalysts, *Catalysis Letters*, 93, Nos 3 - 4 (2004).
30. Rosso, I, Antonini, M, Galletti, C, Saracco, G., Specchia, V, Selective CO-oxidation over Ru-based catalysts in H<sub>2</sub> rich gas for Fuel cell applications, *Topics in Catalysis*, 30-31, No 1, (2004).
31. Kwak, C., Park, T. J., Suh, D. J, Preferential oxidation of carbon Monoxide in hydrogen rich gas over platinum-cobalt-alumina aerogel catalysts, *Chem. Eng. Sci.*, 60, 1211-1217 (2005).

32. Cominos, V., Hessel, V., Hofmann, C, Kolb, G, Ziogas, A, Delsman, E. R, Schouten, J. C, Selective oxidation of carbon monoxide in a Hydrogen-rich fuel cell feed using a catalyst coated, microstructured reactor, *Catalysis Today*, 110, 140-153 (2005).
33. Suh, D. j., Kwak, C., Kim, J. H., Kwon, S. M., Park, T. J, Removal of carbon monoxide from hydrogen rich fuels by selective low-temperature oxidation over base metal added platinum catalysts, *J. Power Sources*, 142, 70-74 (2004).
34. Caputo, T., Lisi, L., Pirone, R., Russo, G, Kinetics of preferential oxidation of CO over CuO/CeO<sub>2</sub> catalysts in H<sub>2</sub>- rich gases, *Ind. Eng. Chem. Res.*, 46, 6793-6800 (2007).
35. Chen, Z. Y., Liaw, B. J., Chang, W. C., Huang, C. T, Selective oxidation of CO in excess hydrogen over CuO/Ce<sub>x</sub>Zr<sub>1-x</sub>O<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> catalysts, *Int. J. Hydrogen Energy*, 32, 4550-4558 (2007).
36. Siri, G. J., Bertolini, G. R., Ferretti, O. A, Preferential oxidation of CO in presence of H<sub>2</sub>-behavior of PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts modified by K or Ba, *Lat. Am. Appl. Res.*, 37No 4 (2007).
37. Monyanon, S., Pongstabodee, S., Luengnaruemitchai, A, Catalytic activity of Pt-Au/CeO<sub>2</sub> catalyst for the preferential oxidation of CO in H<sub>2</sub>-rich stream, *Journal of Power Sources*, 163, 547 - 554 (2006)
38. Sebastian, V., Irusta, S., Mallads, R., Santamaria, J, Selective Oxidation of CO in presence of H<sub>2</sub>, CO<sub>2</sub> and H<sub>2</sub>O on different zeolite-supported Pt catalysts, *Applied Catalysis A; General*, 366, 242-251 (2009).
39. Sircar, S., Lee, K.B, (Eds), 'Sorption Enhanced Reaction Concepts for Hydrogen Production: Materials & Processes', Research Signpost, Trivandrum, Kerala, India (2010).
40. Lee, K. B., Beaver, M. G., Caram, H. S., Sircar, S, Reversible chemisorbents for carbon dioxide and their potential applications, *I & EC Res.*, 47, 8048-8062 (2008).
41. Harrison, D. P, Sorption Enhanced Hydrogen Production: A review, *I & EC Res.*, 47, 6486-6501 (2008).
42. Lee, K. B., Verdooren, A., Caram, H.S., Sircar, S, Chemisorption of carbon dioxide on potassium carbonate promoted hydrotalcite, *J. Coll. Interface Sci.*, 308, 30 - 39 (2007).
43. Hufton, J. R., Mayorga, S., Sircar, S, Sorption enhanced reaction process for hydrogen production, *AIChE J.*, 45, 248-256 (1999).
44. Waldron, W. E., Hufton, J. R., Sircar, S, Production of hydrogen by cyclic sorption enhanced reaction process, *AIChE J.*, 47, 1477 - 1479 (2001).
45. Sircar, S., Hufton, J. R., Nataraj, S, Process and apparatus for the production of hydrogen by steam reforming of hydrocarbon, U. S. Patent, 6,103,143 (2000).
46. Xiu, G.H., Soares, J. L., Li, P., Rodrigues, A. E, Simulation of five step one-bed sorption enhanced reaction process, *AIChE, J.*, 48, 2817-2832 (2002).
47. Xiu, G.H., Li, P., Rodrigues, A. E, Sorption enhanced reaction process with reactive regeneration, *Chem. Eng. Sci.*, 57, 3893-3908 (2002).
48. Xiu, G.H., Li, P., Rodrigues, A. E, Adsorption-enhanced steam methane reforming with intra-particle diffusion limitations, *Chem. Eng. J.*, 95, 83-93 (2003).
49. Xiu, G.H., Li, P., Rodrigues, A. E, New generalized strategy for improving sorption enhanced reaction process, *Chem. Eng. Sci.*, 58, 3425-3437 (2003)
50. Xiu, G.H., Li, P., Rodrigues, A. E, Subsection-controlling strategy for improving sorption enhanced reaction process, *Chem. Eng. Res. Des.*, 82, 192-202 (2004).

51. Lee, K. B., Beaver, M. G., Caram, H. S., Sircar, S, Novel thermal swing sorption enhanced reaction process for hydrogen production by low temperature steam-methane reforming, *I & EC Res.*, 46,5003-5014 (2007).
52. Lee, K. B., Beaver, M. G., Caram, H. S., Sircar, S, Production of fuel-cell grade hydrogen by thermal swing sorption enhanced reaction concept, *Int. J. Hydrogen Energy*, 33, 781-790 (2008).
53. Beaver, M. B., Caram, H. S., Sircar, S, Sorption enhanced reaction process for direct production of fuel-cell grade hydrogen by low temperature catalytic steam-methane reforming, *J. Power Sources*, 195, 1998-2002 (2010)
54. Xu, J. G., Froment, G. F, Methane steam reforming, methanation, and water gas shift: I. Intrinsic kinetics, *AIChE J.*, 35, 88-96 (1989).
55. Lee, K. B., Beaver, M. G., Caram, H. S, Sircar, S, Reversible chemisorptions of CO<sub>2</sub>: simultaneous production of fuel-cell grade H<sub>2</sub> and compressed CO<sub>2</sub> from synthesis gas. *Adsorption*, 13, 385-397 (2007).
56. Agrawal, R., Offutt, M., Ramage, M. P, Hydrogen economy- an opportunity for chemical engineers? *AIChE J.*, 51, 1582- 1589 (2005).

IntechOpen



## **Clean Energy Systems and Experiences**

Edited by Kei Eguchi

ISBN 978-953-307-147-3

Hard cover, 178 pages

**Publisher** Sciyo

**Published online** 05, October, 2010

**Published in print edition** October, 2010

This book reports the latest developments and trends in "clean energy systems and experiences". The contributors to each chapter are energy scientists and engineers with strong expertise in their respective fields. This book offers a forum for exchanging state of the art scientific information and knowledge. As a whole, the studies presented here reveal important new directions toward the realization of a sustainable society.

### **How to reference**

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Michael Beaver and Shivaji Sircar (2010). Decentralized Production of Hydrogen for Residential PEM Fuel Cell from Piped Natural Gas by Low Temperature Steam - Methane Reforming Using a Novel Sorption Enhanced Reaction Concept, Clean Energy Systems and Experiences, Kei Eguchi (Ed.), ISBN: 978-953-307-147-3, InTech, Available from: <http://www.intechopen.com/books/clean-energy-systems-and-experiences/decentralized-production-of-hydrogen-for-residential-fuel-cell-from-piped-natural-gas-by-low-tempera>

**INTECH**  
open science | open minds

### **InTech Europe**

University Campus STeP Ri  
Slavka Krautzeka 83/A  
51000 Rijeka, Croatia  
Phone: +385 (51) 770 447  
Fax: +385 (51) 686 166  
[www.intechopen.com](http://www.intechopen.com)

### **InTech China**

Unit 405, Office Block, Hotel Equatorial Shanghai  
No.65, Yan An Road (West), Shanghai, 200040, China  
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元  
Phone: +86-21-62489820  
Fax: +86-21-62489821



© 2010 The Author(s). Licensee IntechOpen. This chapter is distributed under the terms of the [Creative Commons Attribution-NonCommercial-ShareAlike-3.0 License](#), which permits use, distribution and reproduction for non-commercial purposes, provided the original is properly cited and derivative works building on this content are distributed under the same license.

IntechOpen

IntechOpen