

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.

For more information visit www.intechopen.com



Electrosynthesis and Characterization of Polypyrrole in the Presence of 2,5-di-(2-thienyl)-Pyrrole (SNS)

Nasser Arsalani¹, Amir Mohammad Goganian¹, Gholam Reza Kiani³,
Mir Ghasem Hosseini² and Ali Akbar Entezami¹

¹*Polymer Research Laboratory, Department of Organic Chemistry,
Faculty of Chemistry, University of Tabriz, Tabriz,*

²*Electrochemistry Research Laboratory, Department of Physical Chemistry,
Faculty of Chemistry, University of Tabriz, Tabriz,*

³*School of Engineering-Emerging Technologies, University of Tabriz, Tabriz
Iran*

1. Introduction

Electronically conducting polymers are a very popular research field among the chemists due to their use in a wide variety of marketable applications such as electrochromic devices [Mortimer et al., 2006; Sahin et al., 2005], polymer light-emitting diodes (LEDs) [Kraft et al., 1998], artificial muscles [Cortes & Moreno, 2003], gas sensors [Nicolas-Debarnot & Poncin-Epaillard, 2003], bio sensors [Geetha et al., 2006; Malinauskas et al., 2004] and corrosion protection of metals [Hosseini et al., 2007, 2008; Oco'n et al., 2005]. The preparation, characterization and application of electrochemically active, electronically conjugated polymeric systems are in the foreground of research activities in electrochemistry [Heinze et al., 2010]. Among the conducting polymers, polypyrrole has attracted a lot more interests [Jang & Oh, 2004; Zhang et al., 2006; Chang et al., 2009]. This polymer is easy to synthesize both chemically and electrochemically, exhibiting good electrical conductivity and relatively good stability under ambient conditions, but lacking good electroactivity and redoxability.

In order to improve the electroactivity and redoxability of the electro-synthesized polypyrrole, another molecule containing conjugated system can be used during the electropolymerization of pyrrole. 2,5-di-(2-thienyl)-pyrrole (SNS) is one of the molecules containing conjugated system and have been studied by various electrochemical methods such as cyclic voltammetry, chronopotentiometry, and chronoamperometry under different conditions (changing the electrolyte, electrode, electrochemical potential range and etc) [Otero et al., 1998; Brillas et al., 2000; McLeod et al., 1986].

Entezami et al. have studied the electropolymerization of pyrrole and *N*-methyl pyrrole in the presence of 1-(2-pyrrolyl)-2(2-thienyl) ethylene (PTE) and 2-(2-thienyl) pyrrole (TP) by cyclic voltammetry in different conditions [Kiani et al., 2001]. Recently, we have studied the electropolymerization of thiophene and 3-Methyl thiophene in the presence of small amount

of 1-(2-pyrrolyl)-2-(2-thienyl) ethylene (PTE). It was found that the conductivity, electroactivity and redoxability of polythiophene and poly(3-methyl thiophene) are improved in the presence of PTE [Kiani et al., 2008a, 2008b].

In this work, the effects of conjugated molecule (SNS) on the electropolymerization and electrochemical behaviour of pyrrole was investigated. Firstly, the electropolymerization of pyrrole and SNS were carried out separately by CV method. Secondly, the electropolymerization of pyrrole in the presence of small amount of SNS was carried out and then the influence of SNS on the electropolymerization and electrochemical behaviour of pyrrole was investigated. In addition, the effect of SNS addition on the electron transfer reaction of ferro/ferricyanide redox system on the polypyrrole film was studied and finally the conductivity of poly(Py-SNS) was determined by electrochemical impedance spectroscopy (EIS) method.

2. Experimental

2.1 Materials

Solvents were purified and dried according to the common procedures in the literature [Perin & Armarego, 1998]. Acetic anhydride, ammonium acetate, ferro/ferricyanide were purchased from Merck and lithium perchlorate were bought from Fluka and all of them were used directly.

2.2 Preparation of 2,5-di-(2-thienyl)-pyrrole (SNS)

2,5-di-(2-thienyl)-pyrrole (SNS) was prepared by the method described by Wynberg and Metselaar [Wynberg & Metselaar, 1984]. The yield was improved by refluxing the solution of the intermediate 1,4-di-(2-thienyl)-1,4-butanedione (3 g) with ammonium acetate (40.3 g), glacial acetic acid (120 ml) and acetic anhydride (24 ml) overnight under a nitrogen atmosphere. The reaction mixture was then poured into 250 ml of distilled water and the resulting dark-green solid was chromatographed over a silica gel column with dichloromethane: hexane (3:2) elution to give SNS with 75% yield, as pale yellow crystals of melting point 82-83 °C.

IR(KBr): 3490 cm^{-1} (N-H); $^1\text{H NMR}(\text{CDCl}_3)$: δ : 6.2(2H,d), 6.8(6H,m), 8.0(1H,s).

2.3 Electropolymerization method and conductivity measurements

The electropolymerization was carried out using digital potentiostat/galvanostat (Autolab PGSTAT 30). A glassy carbon (GC) disk (2 mm diameter) as working electrode, a platinum wire as a counter electrode and Ag/AgCl as a reference electrode were used. Acetonitrile was distilled over P_2O_5 and lithium perchlorate was used as an electrolyte in 0.1 M concentration. The electropolymerization of pyrrole (0.5 ml, 7.4 mmole) and SNS (16 mg, 0.074 mmole) in 0.1 M LiClO_4 /acetonitrile electrolyte were performed separately in two different potential ranges vs. Ag/AgCl at the scan rate of 50 $\text{mV}\cdot\text{s}^{-1}$. Similar conditions were adopted for the electropolymerization of pyrrole in the presence of SNS (7.4 mmole: 0.074 mmole). In the study of the cyclic voltammetry experiment of electron transfer, 1 mM ferro/ferricyanide in the 1 M H_2SO_4 media at 50 $\text{mV}\cdot\text{s}^{-1}$ scan rate was used.

For the EIS measurements, the AC frequency range extended from 100 kHz to 10 mHz, a 10 mV peak-to-peak sine wave was as the excitation signal. Both real and imaginary

components of the EIS in the complex plane were analyzed using the Zview(II) software to estimate the parameters of the equivalent electrical circuit. A computer-controlled potentiostat (PARSTATE 2263 EG&G) was used for EIS measurements.

3. Results and discussion

3.1 Electrochemical synthesis of polymers

The electropolymerization of pyrrole was performed by cyclic voltammetry in the potential range of -100 to 900 mV through 15 scans. As shown in figure 1, at the first scan, there is an anodic peak at ca. 800 mV. By continuing electropolymerization through second scan, another anodic peak was observed at 550 mV indicating formation of polypyrrole. After the formation of black colored polymer film on the GC electrode surface, the electrode was taken out from electrochemical cell and was washed with acetonitrile. For the resulted polymer, the cyclic voltammograms at various scan rates were shown in figure 2 indicating a quasi-reversible behaviour.

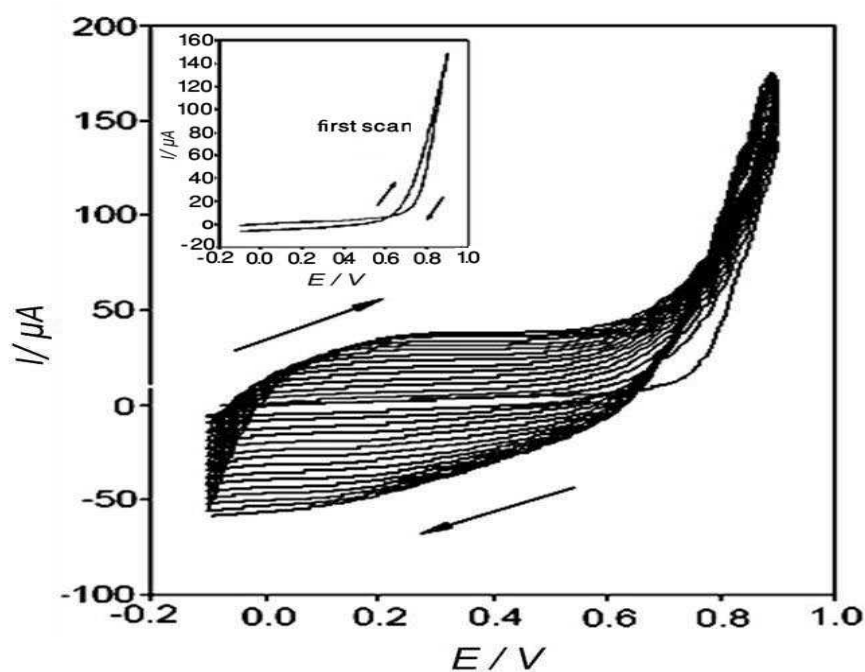


Fig. 1. Cyclic voltammograms of 7.4×10^{-3} M pyrrole in 0.1 M $\text{LiClO}_4 / \text{CH}_3\text{CN}$ electrolyte at scan rate 50 mV/s vs. Ag/AgCl

The cyclic voltammetry investigations of SNS were carried out in the potential range of -400 to 1500 mV (Fig. 3). At the first scan two anodic peaks at ca. 570 and 1300 mV were observed resulting from the oxidation of SNS. In the backward scan from 1500 to -400 mV, there is one peak indicating a quasi-reversible reaction. At the second scan, a new anodic peak current was observed indicating formation of the electroactive poly(SNS) with an ionic structure. As shown in figure 3, after 7 scans, the second anodic peak at 1300 mV was eliminated. The cyclic voltammogram of poly(SNS) in the potential ranges between -400 to 1000 mV at various scan rates was shown in figure 4.

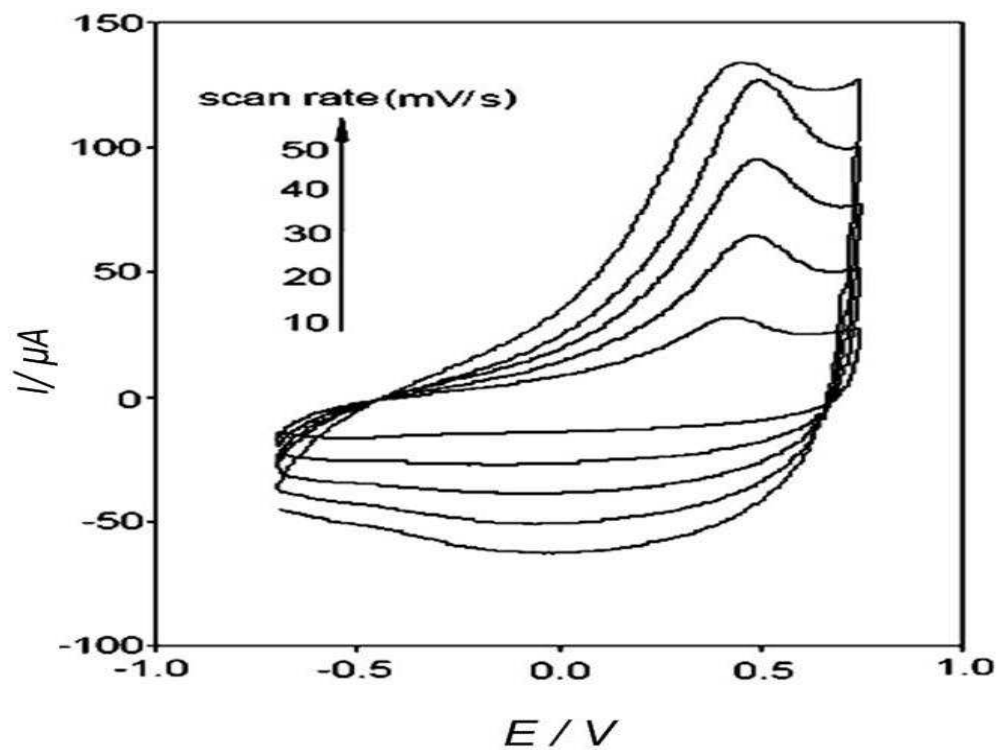


Fig. 2. Cyclic voltammograms of poly(Py) in 0.1 M LiClO₄ / CH₃CN electrolyte at various scan rates

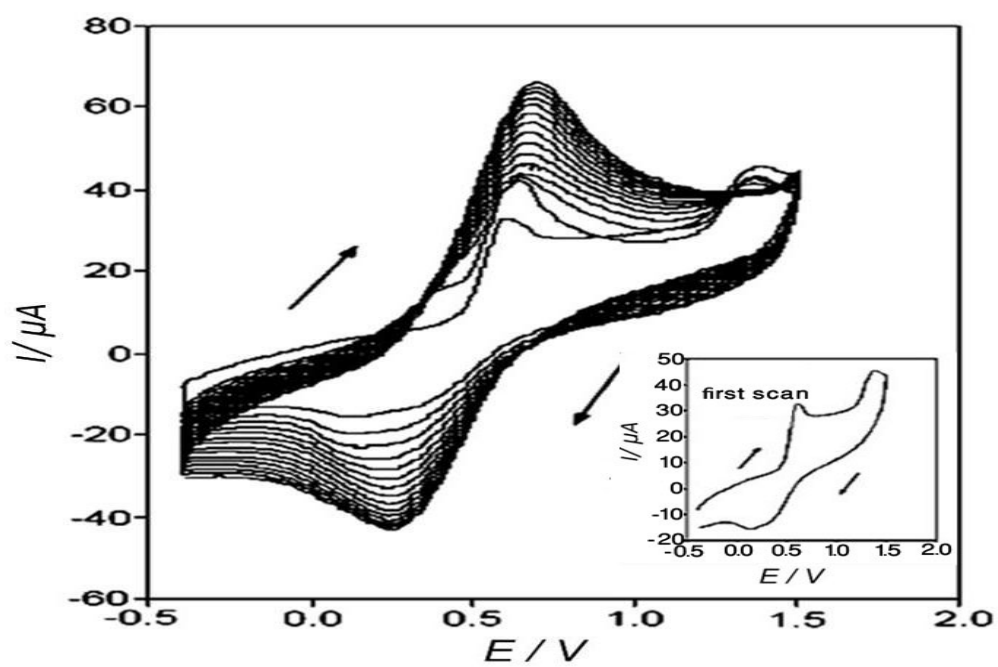


Fig. 3. Cyclic voltammograms of 7.4 × 10⁻⁵ M SNS in 0.1 M LiClO₄ / CH₃CN electrolyte at scan rate 50 mV/s vs. Ag/AgCl

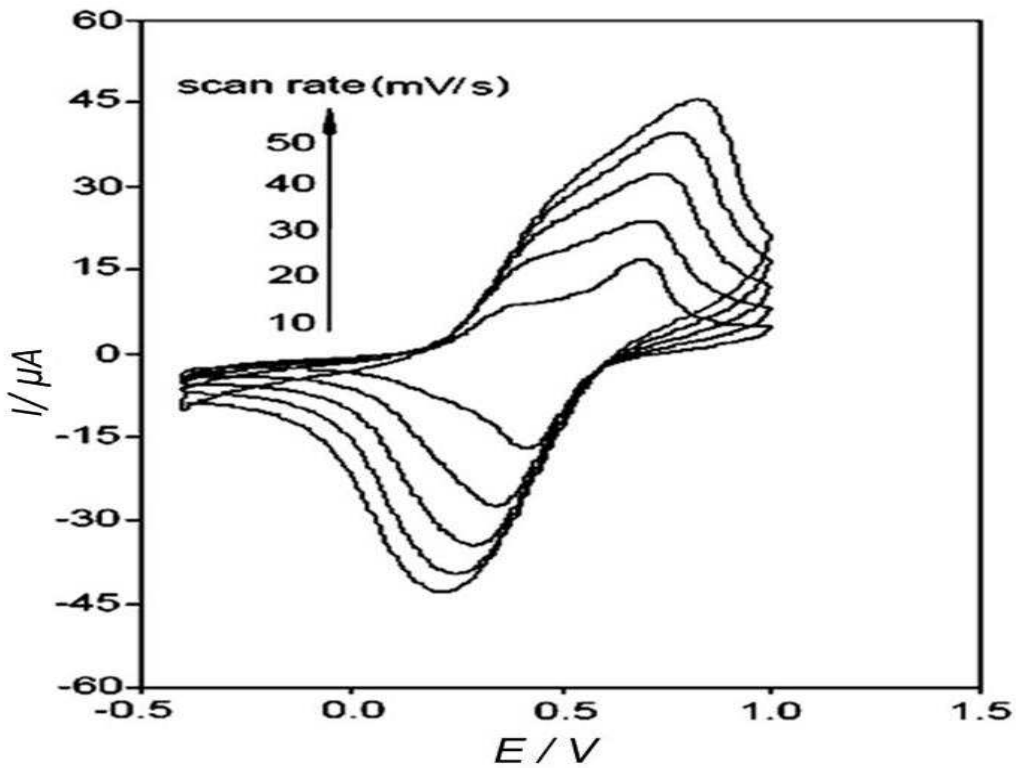


Fig. 4. Cyclic voltammograms of poly(SNS) in 0.1 M LiClO₄ / CH₃CN electrolyte at various scan rates

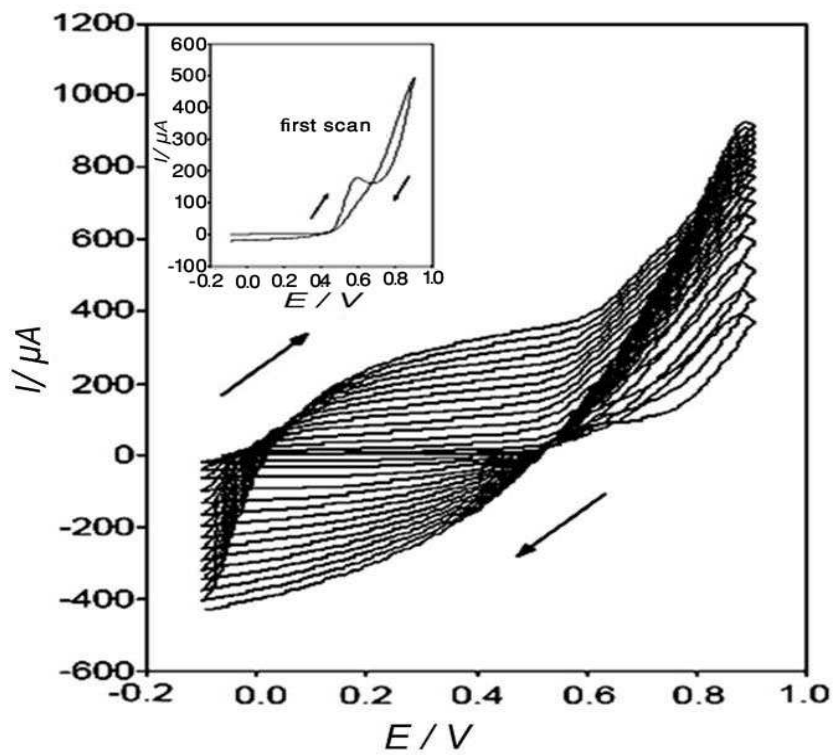


Fig. 5. Cyclic voltammograms of Py-SNS (100:1 mole ratio) in 0.1 M LiClO₄ / CH₃CN electrolyte at scan rate 50 mV/s vs. Ag/AgCl

During the electropolymerization of pyrrole in the presence of the SNS (7.4 *mmole*: 0.074 *mmole*) two anodic peaks appeared at 570 and 800 *mV*. These peaks are due to the oxidation of SNS and pyrrole, respectively. In addition, the anodic peak at 570 *mV* was absent during electropolymerization of pyrrole without SNS (Fig. 5). Because of conjugated backbone of SNS, the oxidation potential of this monomer is less than pyrrole. The cyclic voltammogram for the resulted polymer in various scan rates showed a relatively reversible behaviour (Fig. 6).

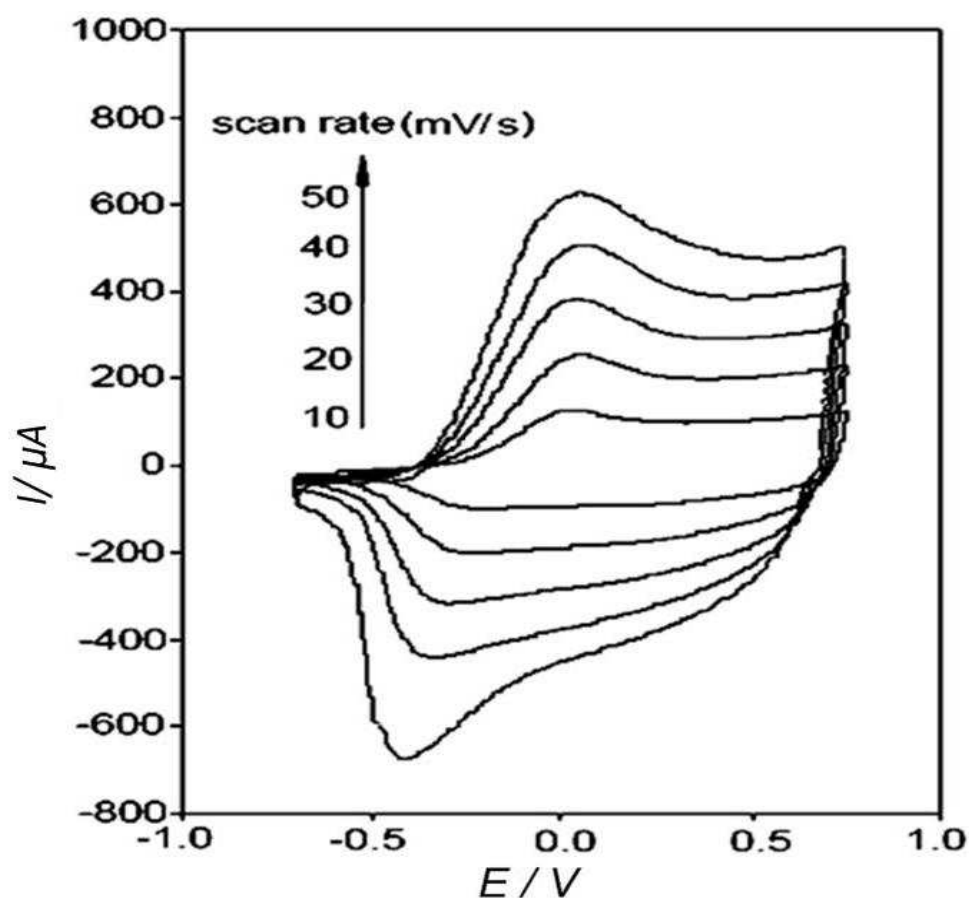
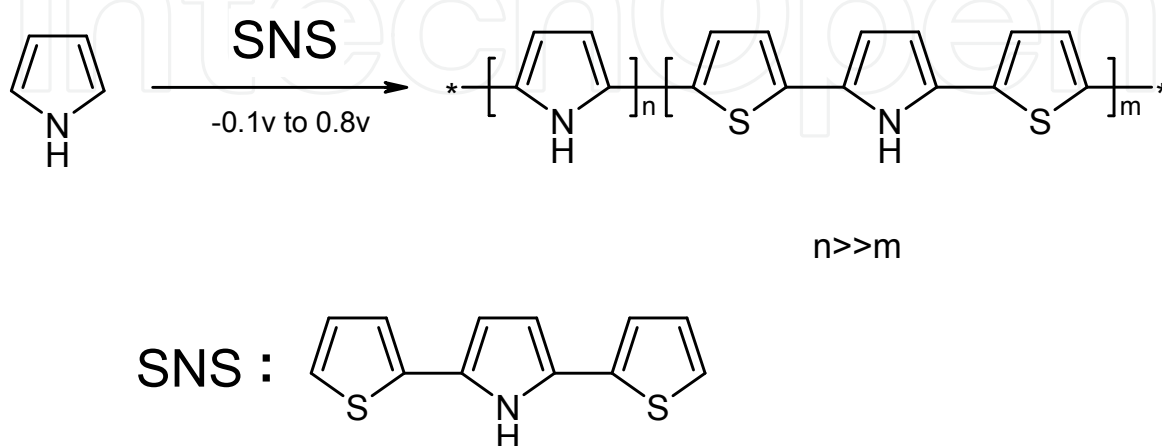


Fig. 6. Cyclic voltammograms of poly(Py-SNS) in 0.1 M LiClO₄ / CH₃CN electrolyte at various scan rates

Figure 7 presents the plot of anodic peak currents vs. different scan rates for obtained polymers. These curves show that the slope for poly(Py) and poly(Py-SNS) increases from 2.83 to 12.37 $mAs.mV^{-1}$. These results indicated considerable increase in the electroactivity and rate of electropolymerization of polypyrrole in the presence of a small amount of SNS compared to the those of polypyrrole and poly(SNS). According to extracted data from cyclic voltammeteries of polymers (see Table1), it can be seen that at various scan rates, E_{pa} for poly(Py-SNS) is less than those two for other polymers, but i_{pa} for former polymer is more than those for two others. In other words, the conductivity of SNS included polypyrrole is better than polypyrrole alone and poly(SNS). Also, it is evident that at scan rates of less than 50 $mV.s^{-1}$, ΔE_p for poly(Py-SNS) is lower those for than two others, indicating improvement of redoxability for poly(Py-SNS) in comparison with poly(Py) and poly(SNS). At scan rate of 50 $mV.s^{-1}$ the redoxability of poly(Py-SNS) is relatively similar to that of poly(Py).

The overall scheme of electrosynthesis of polypyrrole in the presence of SNS as shown Fig. 6.

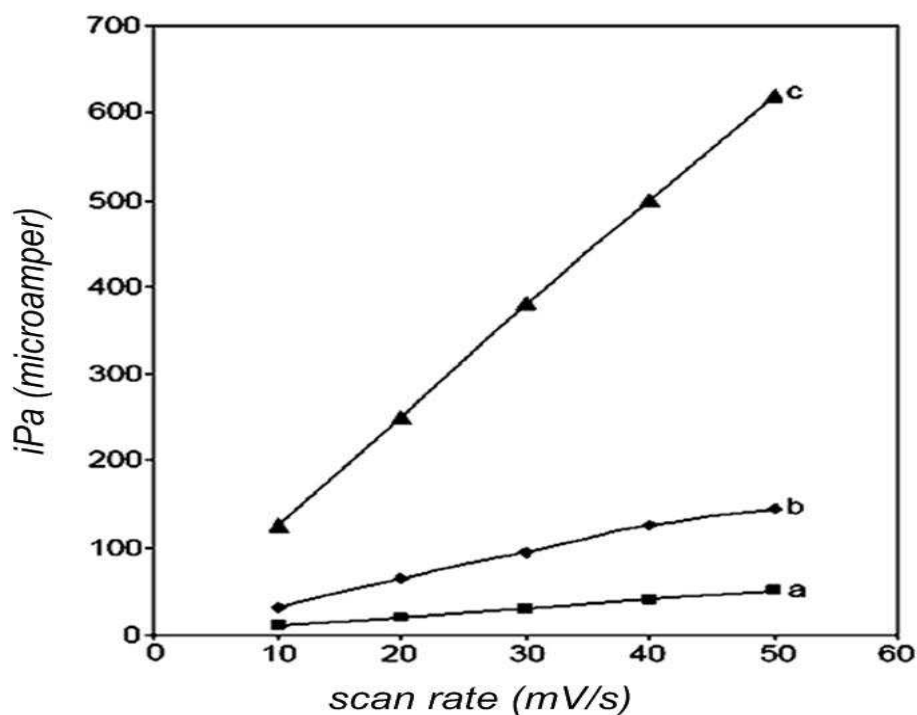


Fig. 7. Plots of anodic peak currents vs. scan rates for (a) poly(SNS), (b) poly(Py), (c) poly(Py-SNS)

Scan	rates	Poly(Py)	Poly(SNS)	Poly(Py-SNS)
$E_{pa}(V)$	10	0.450	0.715	0.052
	30	0.500	0.750	0.075
	50	0.460	0.841	0.132
$E_{pc}(V)$	10	-0.123	0.405	-0.240
	30	-0.070	0.277	-0.329
	50	-0.050	0.201	-0.431
$\Delta E_p(V)$	10	0.573	0.310	0.292
	30	0.570	0.473	0.404
	50	0.510	0.640	0.563
$i_{pa}(\mu A)$	10	32	19	120
	30	94	33	380
	50	103	47	620

E_{pa} : potential of anodic peak

E_{pc} : potential of cathodic peak

i_{pa} : anodic peak currents

Table 1. Obtained data for poly(Py), poly(SNS) and poly(Py-SNS) at scan rates 10 and 50 mV/s

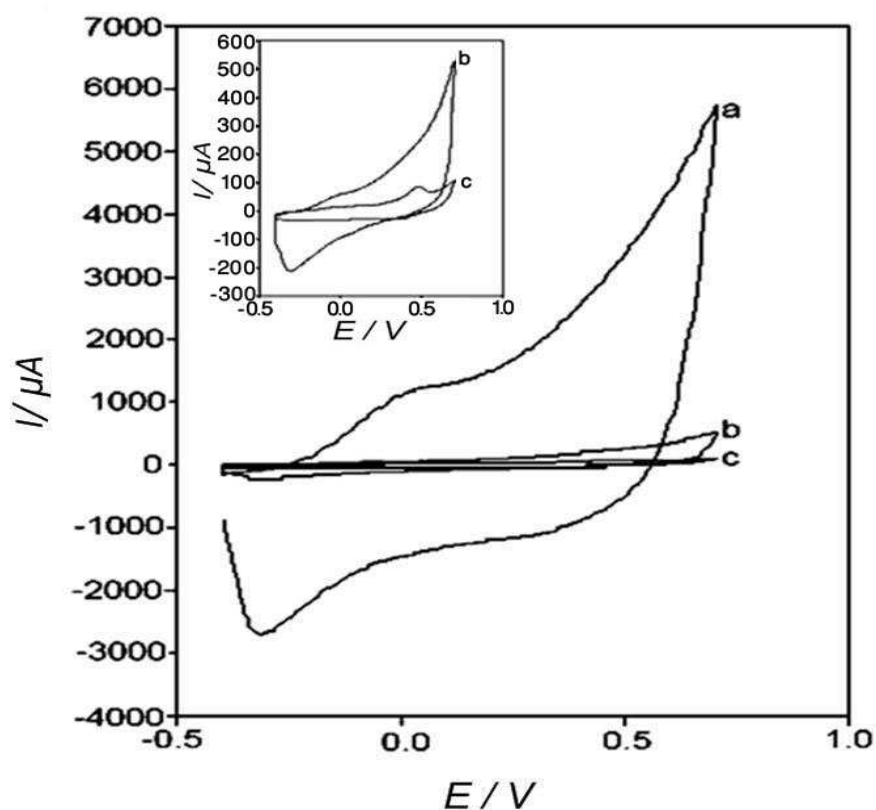


Fig. 8. Cyclic voltammograms of (a) poly(Py-SNS), (b) poly(SNS), and (c) poly(Py) on the GC electrode in 1 M H_2SO_4 and 1 mM $Fe(CN)_6^{4-/3-}$ redox system at 50 mV/s scan rate

The CV experiments were performed to study the effect of SNS in the polypyrrole film in the electron transfer of ferro/ferricyanide redox system. Figure 8 shows the CV of electron transfer ferro/ferricyanide redox on different modified GC electrodes with poly(Py), poly(SNS), and poly(Py-SNS). This figure indicates that the electron transfer of ferro/ferricyanide on polypyrrole in the presence of the SNS is more feasible than that of polypyrrole alone, because the conductivity of polypyrrole increases in the presence of SNS.

3.2 Evaluation of conductivity and electrochemical behaviour by electrochemical impedance spectroscopy (EIS)

Electrochemical impedance spectroscopy (EIS) is a measurement technique which allows for a wide variety of coating evaluations. EIS is an effective method to probe the interfacial properties of surface-modified electrodes. EIS has been used to characterize the electrical properties of the electropolymerized films [Kiani et al., 2008a, 2008b]. The electrochemical behaviour of polypyrrole changes in the presence of SNS. In order to choose a suitable electrical equivalent circuit for EIS experimental data fitting, one must take in consideration the physicochemical picture of the system under study. In other words, each element of the equivalent circuit should have a physicochemical aspect attributable to it. In the model circuit chosen, R_s presents the uncompensated resistance of the solution between working and reference electrode. CPE_1 and R_1 stand for the dielectric and resistive characteristics of the conductive polymer on the GC electrode, respectively. In this case R_1 is a reverse measure of polymer conductivity. CPE_2 and R_2 show the capacitance and resistance of the polymer/GC interface. As is evident from the high values of R_2 for all as well as the Nyquist plot of studied polymers, due to the fact that polymer layer is impermeable to the ionic charge carrier species, low frequency behaviour of the polymer/GC interface tends to be of capacitive nature. Again more evidence for this fact is reflected in the values of n_{CPE2} which for all studied samples is not very far than unity. Our main aim by EIS studies was to determine the polymer layer bulk resistivity (or its reciprocal i.e conductivity). In the selected equivalent circuit R_1 corresponds to this parameter. The studied electrical parameters were calculated using Zview(II) software. All fitting results are presented in Table 2.

Sample	$R_s(\Omega)$	$R_1(\Omega.cm^2)$	$R_2(\Omega.cm^2)$ Y_0	CPE_1 n	$CPE_1 Y_0$	CPE_2 n	CPE_2
Poly(Py)	43.86	5.81	2.5E4	8.0E-4	0.64	8.3E-4	0.98
Poly(SNS)	38.94	2282	7.2E4	1.3E-4	0.72	1E-4	1.00
Poly(Py-SNS)	30.50	1.46	7.2E4	0.67	0.58	0.01	0.98

R_s : uncompensated resistance of the solution

R_1 and CPE_1 : dielectric and resistive characteristics of the conductive polymer

R_2 and CPE_2 : capacitance and resistance of the polymer/ GC interface

Y_0 : CPE Admittance

n : CPE exponent

Table 2. Impedance parameters obtained by fitting the EIS data of poly(Py), poly(SNS) and poly(Py-SNS) on the GC electrode in 3.5% NaCl

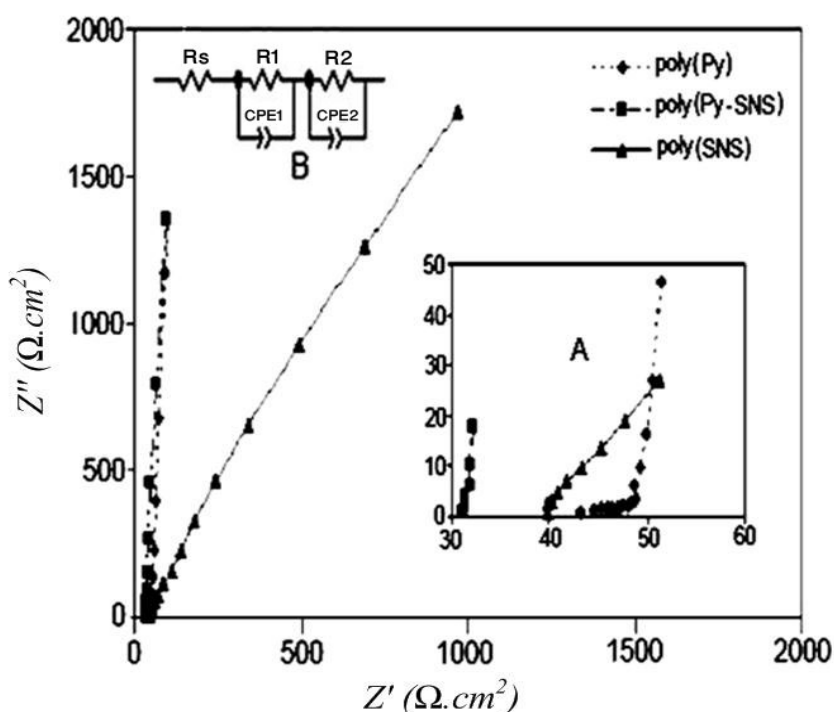


Fig. 9. Nyquist plots for poly(Py), poly(Py-SNS)(100:1 mole ratio) and poly(SNS) in 3.5% (W/V) NaCl solution: A) Exploded view in the high frequency range, B) Proposed equivalent circuit

According to these results (Table 2), we can notice a decrease in the charge transfer resistance value in the case of the polypyrrole in the presence of SNS systems as compared to polypyrrole alone. The R_{ct} (R_{ct} : charge transfer resistance) values obtained for polypyrrole and poly(SNS) are 5.81 and 2282 $\Omega.cm^2$ respectively. This value decreases in the presence of SNS to 1.46 $\Omega.cm^2$. The polypyrrole film formed in the presence of SNS is more conductive. On the other hand, in the presence of SNS, value of the capacitance of the double layer, CPE_1 , rises from 8.0E-4 to 0.67 $\mu F.cm^2$ which can be attributed to an increase in the electrode surface area. This change in the capacitance strongly supports the hypothesis of the incorporation of SNS in the polypyrrole film. Also, these results support the results of CV in the Figure 9. In the presence of SNS, the conductivity of polypyrrole is improved. Increased value of CPE_1 for polypyrrole in the presence of SNS compared to pure polypyrrole confirmed the easy electron transfer of ferro/ferricyanide redox system for poly(Py-SNS) (Fig. 8). Improvement of the conductivity, electroactivity and redoxability of polypyrrole containing SNS leads it to extensive applications in many fields.

4. Conclusions

The resulted poly(Py-SNS)(100:1 mole ratio) showed a considerable increase in the electroactivity, redoxability, and the rate of polymerization in comparison to polypyrrole alone. The cyclic voltammograms of electron transfer ferro/ferricyanide redox system on different modified GC electrode showed that the rate of charge transfer for polypyrrole in the presence of SNS increased in comparison to pure polypyrrole. In addition, the conductivity of polypyrrole was studied by electrochemical impedance spectroscopy. The obtained R_{ct} value for polypyrrole is 5.81 $\Omega.cm^2$, whereas the value decreases to 1.46 $\Omega.cm^2$ in

the presence of SNS. By considering the fact that decreasing the R_{ct} leads to an increase in conductivity, it is predictable that the film of polypyrrole formed in the presence of SNS will be more conductive. In the presence of SNS, value of electrical double layer capacitance (CPE_1) rises, indicating a probable increase in the electrode surface area. There is a good complementary agreement between the results of CV and EIS measurements. From these results it can be concluded that the produced polypyrrole containing small amount of SNS has better performance compared to polypyrrole alone for production of batteries, capacitors, diodes, electrochromic devices, sensors and etc.

5. Acknowledgment


The authors acknowledge Mr. I. Ahadzadeh, for his kind help in EIS measurements.

6. References

- Brillas, E. Carrasco, J. Oliver, R. Estrany, F. Vilar, J. & Morlans, J.M. (2000). Electropolymerization of 2,5-di-(2-thienyl)-pyrrole in ethanolic medium. Effect of solution stirring on doping with perchlorate and chloride ions. *Electrochimica Acta*, Vol. 45, pp. 4049-4057.
- Chang, C.H. Son, P.S. Yang, G.H. & Choi, S.H. (2009). Electrochemical Synthesis of the Functionalized Poly(pyrrole) Conducting Polymers. *Journal of the Korean Chemical Society*, Vol. 53, No.2, pp. 111-117.
- Cortés, M.T. & Moreno, J.C. (2003). Artificial muscles based on conducting polymers. *e-Polymers*, No. 041, pp. 1-42.
- Geetha, S. Chepuri, R.K.R. Vijayan, M. & Trivedi, D.C. (2006). Biosensing and drug delivery by polypyrrole. *Analytica Chimica Acta*, Vol. 568, pp. 119-125.
- Heinze, J. Frontana-Uribe, B.A. & Ludwigs, S. (2010). Electrochemistry of Conducting Polymers – Persistent Models and New Concepts. *Chemical Reviews*, Vol. 110, No.8, pp. 4724-4771.
- Hosseini, M.G. Sabouri, M. & Shahrabi, T. (2007). Corrosion protection of mild steel by polypyrrole phosphate composite coating. *Progress in Organic Coatings*, Vol. 60, pp. 178-185.
- Hosseini, M.G. Sabouri, M. & Shahrabi, T. (2008). Comparison of the corrosion protection of mild steel by polypyrrole-phosphate and polypyrrole-tungstenate coatings. *Journal of Applied Polymer Science*. Vol. 110, No. 5, pp. 2733-2741.
- Jang, J. & Oh, J.H. (2004). Morphogenesis of Evaporation-Induced Self-Assemblies of Polypyrrole Nanoparticles Dispersed in a Liquid Medium. *Langmuir*, Vol. 20, pp. 8419-8422.
- Kiani, G.R. Arsalani, N. & Entezami, A.A. (2001). The Influence of the Catalytic Amount of 1-(2-Pyrrolyl)-2-(2-Thienyl) Ethylene and 2-(2-Thienyl) Pyrrole on Electropolymerization of Pyrrole and N-Methylpyrrole. *Iranian Polymer Journal*, Vol. 10, pp. 135-142.
- Kiani, G.R. Arsalani, N. & Entezami, A.A. (2008). Synthesis of Poly(3-methylthiophene) in the Presence of 1-(2-Pyrrolyl)-2-(2-thienyl) Ethylene by Electropolymerization. *Journal of Iranian Chemical Society*, Vol. 5, pp. 559-565.
- Kiani, G.R. Arsalani, N. Hosseini, M.G. & Entezami, A.A. (2008). Improvement of the conductivity, electroactivity, and redoxability of polythiophene by

- electropolymerization of thiophene in the presence of catalytic amount of 1-(2-pyrrolyl)-2-(2-thienyl) ethylene (PTE). *Journal of Applied Polymer Science*, Vol. 108, No. 4, pp. 2700-2706.
- Kraft, A. Grimsdale, A.C. & Holmes, A.B. (1998). Electroluminescent Conjugated Polymers-Seeing Polymers in a New Light. *Angewandte Chemie International Edition*, Vol. 37, No.4, pp. 402-428, ISSN 14337851
- Malinauskas, A. Garjonyte, R. Mazeikiene, R. & Jureviciute, I. (2004). Electrochemical response of ascorbic acid at conducting and electrogenerated polymer modified electrodes for electroanalytical applications: a review. *Talanta*, Vol. 64, pp. 121-129.
- McLeod, G.G. Mahboubian-Jones, M.G.B. Pethrick, R.A. Watson, S.D. Truong, N.D. Galin, G.C. & Francois, J. (1986). Synthesis, electrochemical polymerization and properties of poly(2,5-di-(2-thienyl)-pyrrole). *Polymer*, Vol. 27, pp. 455-458.
- Mortimer, R.J. Dyer, A.L. & Reynolds, J.R. (2006). Electrochromic organic and polymeric materials for display applications. *Displays*, Vol. 27, No.1, pp. 2-18.
- Nicolas-Debarnot, D. & Poncin-Epaillard, F. (2003). Polyaniline as a new sensitive layer for gas sensors. *Analytica Chimica Acta*, Vol. 475, pp. 1-15.
- Oco'n, P. Cristobal, A.B. Herrasti, P. & Fatas, E. (2005). Corrosion performance of conducting polymer coatings applied on mild steel. *Corrosion Science*, Vol. 47, pp. 649-662.
- Otero, T.F. Villanueva, S. Brillas, E. & Carrasco, J. (1998). Electrochemical processing of the conducting polymer poly(SNS). *Acta Polymerica*, Vol. 49, pp. 433-438. ISSN 0323-7648
- Perin, D.D. & Armarego, W.L.F. (1998). Purification of Laboratory Chemicals, Edition, Pergamon publisher, Oxford.
- Sahin, E. Camurlu, P. Toppare, L. Mercore, V.M. Cianga, I. & Yagci, Y.J. (2005). Conducting copolymers of thiophene functionalized polystyrenes with thiophene. *Journal of Electroanalytical Chemistry*, Vol. 579, pp. 189-197.
- Wynberg, H. & Metselaar, J. (1984). A Convenient Route To Polythiophenes. *Synthetic Communications*, Vol. 14, pp. 1-9.
- Zhang, X. Zhang, J. Song, W. & Liu, Z. (2006). Controllable Synthesis of Conducting Polypyrrole Nanostructures. *Journal of Physical Chemistry B*, Vol. 110, pp. 1158-1165, ISSN 16471658.

IntechOpen

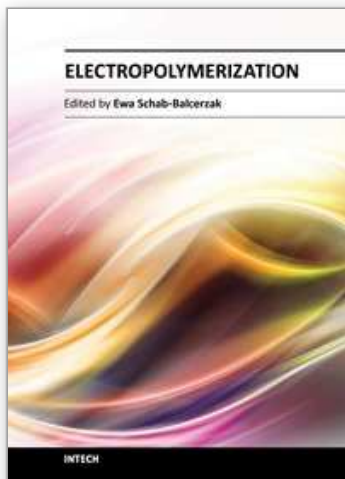

Electropolymerization

Edited by Dr. Ewa Schab-Balcerzak

ISBN 978-953-307-693-5

Hard cover, 214 pages

Publisher InTech

Published online 22, December, 2011

Published in print edition December, 2011

In recent years, great focus has been placed upon polymer thin films. These polymer thin films are important in many technological applications, ranging from coatings and adhesives to organic electronic devices, including sensors and detectors. Electrochemical polymerization is preferable, especially if the polymeric product is intended for use as polymer thin films, because electrogeneration allows fine control over the film thickness, an important parameter for fabrication of devices. Moreover, it was demonstrated that it is possible to modify the material properties by parameter control of the electrodeposition process. Electrochemistry is an excellent tool, not only for synthesis, but also for characterization and application of various types of materials. This book provides a timely overview of a current state of knowledge regarding the use of electropolymerization for new materials preparation, including conducting polymers and various possibilities of applications.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Nasser Arsalani, Amir Mohammad Goganian, Gholam Reza Kiani, Mir Ghasem Hosseini and Ali Akbar Entezami (2011). Electrosynthesis and Characterization of Polypyrrole in the Presence of 2,5-di-(2-thienyl)-Pyrrole (SNS), *Electropolymerization*, Dr. Ewa Schab-Balcerzak (Ed.), ISBN: 978-953-307-693-5, InTech, Available from: <http://www.intechopen.com/books/electropolymerization/electrosynthesis-and-characterization-of-polypyrrole-in-the-presence-of-2-5-di-2-thienyl-pyrrole-sns>

INTECH
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2011 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen