

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities

**WEB OF SCIENCE™**Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com



Potential Applications for Solar Photocatalysis: From Environmental Remediation to Energy Conversion

Antonio Eduardo Hora Machado^{1,*}, Lidiaine Maria dos Santos¹,
Karen Araújo Borges¹, Paulo dos Santos Batista²,
Vinicius Alexandre Borges de Paiva¹, Paulo Souza Müller Jr.¹,
Danielle Fernanda de Melo Oliveira¹ and Marcela Dias França¹

¹*Universidade Federal de Uberlândia, Instituto de Química,
Laboratório de Fotoquímica, Uberlândia, Minas Gerais,*

²*Universidade Federal de Goiás, Campus Catalão, Departamento de Química, Catalão, Goiás,
Brazil*

1. Introduction

Taking into consideration the impacts of increasing concern as a result of human activity on the environment in recent decades, different approaches have been developed and proposed to minimize the persistence of organic and inorganic pollutants, not only the dangerous or biorecalcitrant. Industrial waste discharges, those from domestic sewage, and so-called emerging contaminants (pesticides, hormones and drugs), among others, have caused numerous problems for the sustainability of ecosystems (Amat et al., 2011).

In general, environmental problems are largely associated with the disposal of waste into sewers, rivers and eventually into the ocean. The damage caused to biota by these discharges is incalculable (Hermann & Guillard, 2002; Corcoran et al., 2010).

New and effective forms of wastewater treatment are essential to enable a responsible economic development of the planet ensuring its sustainability for future generations (Amat et al., 2011). These processes need to be environmentally safe, providing the elimination of contaminants and not just promoting a phase transfer, ensuring the reuse of water (Hermann & Guillard, 2002; Machado et al., 2003a; Sattler et al., 2004; Wojnárovits et al., 2007).

Besides the application in order to minimize the environmental impacts of human action, via photocatalytic processes, semiconductor oxides have also been employed in producing chemical raw materials through specific chemical reactions (Kanai et al., 2001; Murata et al., 2003; Amano et al., 2006; Denmark & Venkatraman, 2006; Hakki et al., 2009; Swaminathan & Selvam, 2011; Swaminathan & Krishnakumar, 2011), in the conversion of solar energy into electricity (Prashant, 2007; Patrocínio et al., 2010; Huang et al., 2011; Zhou et al., 2011) and

* During his leave as Visiting Professor in the Departamento de Química at the Campus Catalão of Universidade Federal de Goiás.

production of hydrogen for subsequent generation of energy (Jing et al., 2010; Kim & Choi, 2010; Melo & Silva, 2011).

2. Advanced Oxidation Processes (AOP)

Advanced Oxidation Processes (or Advanced Oxidative Technologies) stand out among the new technologies potentially useful for the minimization of environmental impacts to biota (Ismail et al., 2009), and, among these technologies, are the photocatalytic degradation of contaminants in the environment, especially using solar radiation (Martin et al., 1995; Zioli & Jardim, 1998; Machado et al., 2003a; Duarte et al., 2005; Augugliaro et al., 2007; Machado et al., 2008). They are characterized by being able to degrade a wide range of organic contaminants into carbon dioxide, water and inorganic anions through reactions involving oxidizing species, particularly hydroxyl radicals which have a high oxidizing power ($E^{\circ}=2.8$ V) (Nogueira & Jardim, 1998; Machado et al., 2003a; Machado et al., 2008; Kumar & Devi, 2011).

Among the AOP can be cited processes involving the use of ozone, hydrogen peroxide, catalytic decomposition of hydrogen peroxide in acid medium (Fenton or/and photo-Fenton reactions), and semiconductors such as titanium dioxide (heterogeneous photocatalysis) (Nogueira & Jardim, 1998; Kumar & Devi, 2011). The heterogeneous photocatalysis is considered one of the most promising advanced oxidation technologies. In heterogeneous photocatalytic processes, highly oxidizing reactive oxygen species (ie hydroxyl radicals, superoxide radical-ions, etc.) are generated from interaction between the semiconductor electronically excited, oxygenated species and other substrates (Andreozzi et al., 1999; Fujishima et al., 2007; Machado et al., 2008; Kumar & Devi, 2011).


The solar photocatalysis deserves special attention, since the sun is a virtually inexhaustible source of energy at no cost (Machado et al., 2008; Amat et al., 2011).

2.1 Heterogeneous photocatalysis

The great potential of heterogeneous photocatalysis has been demonstrated mainly in the treatment of industrial effluents and wastewater through the degradation of contaminants (Malato et al., 1997; Andreozzi et al., 1999; Malato et al., 2002; Sattler et al., 2004a, 2004b; Duarte et al., 2005; Pons et al., 2007; Palmisano et al., 2007a; Machado et al., 2008). A significant number of these studies have focused on the photocatalytic properties of TiO_2 , suggesting a promising use of this material in heterogeneous photocatalysis (Mills & Hunte, 1997; Malato et al., 2002; Mills et al., 2002; Machado et al., 2003a; Machado et al., 2003b; Sattler et al., 2004a, 2004b; Duarte et al., 2005; Palmisano et al., 2007a; Pons et al., 2007; Machado et al., 2008; Oliveira et al., 2012).

The potential of heterogeneous photocatalysis has been demonstrated in studies originally reported by Fujishima and Honda (Fujishima & Honda, 1971, 1972). The photoactivation of a semiconductor is based on its electronic excitation by photons with energy greater than the band gap energy. This tends to generate vacancies in the valence band - VB (holes, h^+) and regions with high electron density (e^-) in the conduction band - CB (Hoffmann et al., 1995; Nogueira & Jardim, 1998; Kumar & Devi, 2011). These holes have pH dependent and strongly positive electrochemical potentials, in the range between +2.0 and +3.5 V, measured against a saturated calomel electrode (Khataee et al., 2011). This potential is sufficiently positive to generate hydroxyl radicals ($\text{HO}\cdot$) from water molecules adsorbed on the surface of the

semiconductor (eqs. 1-3). The photocatalytic efficiency depends on the competition between the formation of pairs of electrons and holes in semiconductor surface and the recombination of these pairs (eq.4) (Nogueira & Jardim, 1998; Ziolli & Jardim, 1998; Ni et al., 2011).



The electrons transferred to the conduction band are responsible for reducing reactions, such as the formation of gaseous hydrogen and the generation of other important oxidizing species such as superoxide anion radical. In the case of TiO_2 , the band gap energy, E_g , is between 3.00 and 3.20 eV (Hoffmann et al., 1995; Palmisano et al., 2007a; Jin et al., 2010; Kumar & Devi, 2011). This process can be viewed schematically in Fig. 1.

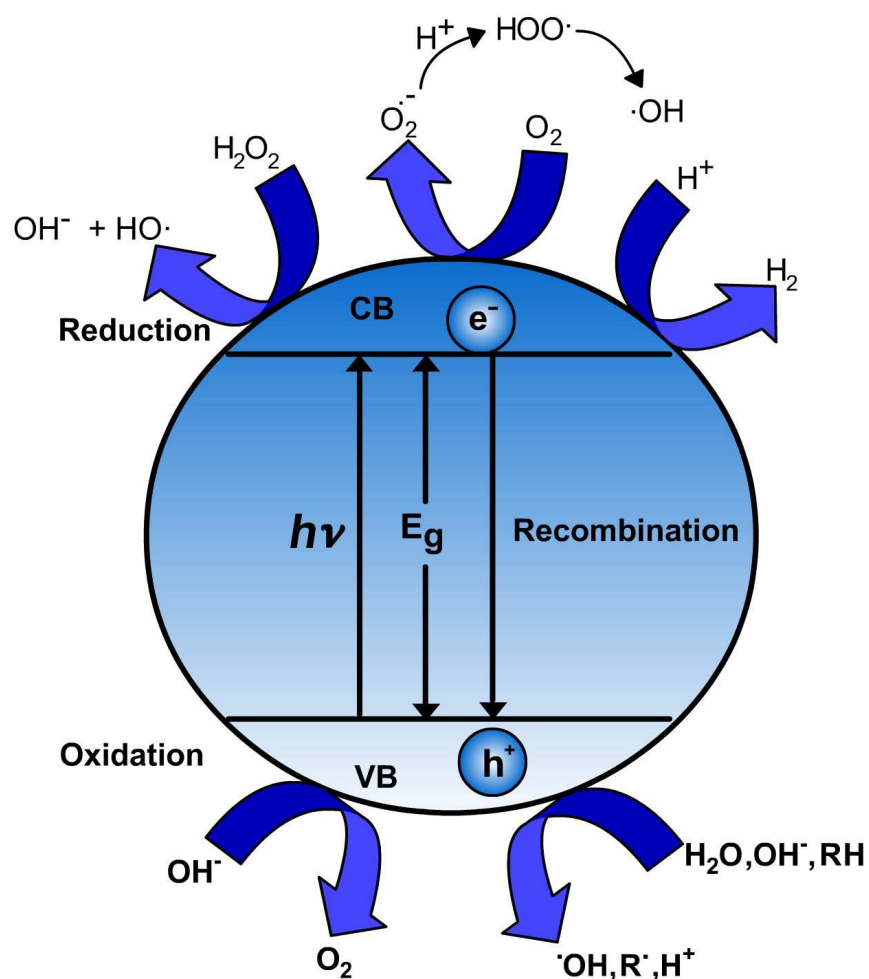


Fig. 1. General scheme for some primary processes that occur after photoactivation of a semiconductor and for photocatalytical production of gaseous hydrogen by decomposition of water.

The production of reactive species by a TiO₂ photocatalyst is influenced by a series of factors, such as surface acidity and pH of the reaction medium, control of the kinetic of recombination of charge carriers, interfacial electron-transfer rate, optical absorption of the semiconductor, phase distribution, morphology, specific surface area and porosity (Hoffmann et al., 1995; Furube et al., 2001; Diebold, 2003; Carp et al., 2004; Kumar & Devi (2011).

The reactions (1) to (4) combined with other (Hoffmann et al., 1995; Machado et al., 2008; Kumar & Devi, 2011) give an approximate view of the chain reactions that compose a heterogeneous photocatalytic process.

Different semiconductors are able to trigger the heterogeneous photocatalytic processes. Other in addition to TiO₂ are: CdS, ZnO, ZnS, and Fe₂O₃ (Nogueira & Jardim, 1998).

TiO₂ stands in front of others for its abundance, low toxicity, good chemical stability over a wide pH range, photosensitivity, photostability, insolubility in water, low cost, chemical inertness, biological and chemical inertness, and stability to corrosion and photocorrosion (Martin et al., 1995; Augugliaro et al., 2007). However, its band gap energy limits, in principle, its application in photocatalytic processes induced by solar radiation, since the radiation incident on the biosphere consists of approximately 5 % UV, 43 % visible and 52 %, harvesting infrared (Kumar & Devi, 2011).

The introduction of changes in the crystalline structure of TiO₂ through the introduction of dopant ions and/or modifying ions and associations between TiO₂ and other semiconductor oxides in order to expand the use of incident radiation, is particularly important if the aim is to use solar radiation in photocatalytic processes. The synthesis of new materials based on TiO₂ has resulted in substantial progress towards the improvement of the photocatalytic activity of this semiconductor (Imhof & Pine, 1997; Cavaleiro et al., 2008; Eguchi et al., 2001; Agostiano et al., 2004; Machado et al., 2008; Zaleska et al., 2010; Batista, 2010; Machado et al., 2011b).

Titanium dioxide can be found in nature in the form of three different polymorphs: Anatase, Rutile and Brookite (Hanaor & Sorrell, 2011; Khataee et al., 2011; Kumar & Devi, 2011). Among these polymorphs, the thermodynamically more stable is the rutile, which can be obtained from the conversion of anatase, which in turn is the most photoactive polymorph (Hoffmann et al., 1995; Khataee et al., 2011).

Technological applications of titanium oxide are quite large. In addition to the previously described, TiO₂ has been used in filters to absorb ultraviolet radiation (sunscreens, for example), pigments, in chemical sensors for gases (Pichat et al., 2000), as constituents of ceramic materials for bone and dental implants (Chen et al., 2008), among others.

2.2 Changes in the structure and surface of titanium dioxide

Strong light absorption and suitable redox potential are prerequisites for photocatalytic reactions. Growing interest has focused on doped TiO₂ catalysts (Ohno et al., 2003; Luo et al., 2004; Li et al., 2005; Labat et al., 2008; Yang et al., 2008; Long et al., 2009; Zhang et al., 2010; Zaleska et al., 2010; Iwaszuk & Nolan, 2011; Long & English, 2011; Spadavecchia et al., 2011; Kumar & Devi, 2011;), however current achievements are still far from the ideal goal.

In order to extend the photocatalytic activity in the region of visible light, and in order to achieve a better use of solar radiation, several approaches have been proposed for tuning the band gap response of titania to the visible region. Doping or incorporate trace impurities in the structure of TiO₂ in order to obtain materials with photocatalytic activity maximized in the visible region are strategies widely used (Ohno et al., 2003; Li et al., 2005; Zaleska et al., 2010). These strategies include doping with transition metals (Nogueira & Jardim, 1998; Yamashita et al., 2001; Cavaleiro et al., 2008; Zaleska et al., 2010), nonmetals (Ohno et al., 2003; Li et al., 2005), and the inclusion of low-valence ions on the surface of the semiconductor (for example, Ag⁺, Ni³⁺, V³⁺ e Sc³⁺). Certain metals, when incorporated to titanium dioxide, are able to decrease the band gap, making possible in some cases its application in solar photocatalysis. Furthermore, they can contribute to minimize the electron-hole recombination, increasing the photocatalytic efficiency of the semiconductor (Zaleska et al., 2010).

Coupling of two photocatalysts has also been considered effective for improvement of photocatalytic efficiency. As example, nitrogen doped TiO₂ coupled with WO₃ and after loaded with noble metal, resulted in a material with improved photocatalytic efficiency (Yang et al., 2006).

2.2.1 Synthesis of TiO₂

We have performed the synthesis of titanium dioxide using different methodologies (Batista, 2010; Oliveira, 2011). A modification was introduced in the methodology of the synthesis by precipitation of TiO₂ using titanium tetraisopropoxide as precursor suggested by Batista (Batista, 2010). It consists in making the whole process, since the solubilization of the precursor in 2-propanol, always under the action of ultrasound. The solid obtained was dried at 60 ° C and subjected to heat treatment at 400 ° C. This new photocatalyst has been adopted in our most recent studies since it has shown impressive photocatalytic activity in the mineralization of different organic substrates (Machado et al., 2011b). As a result, we have studied the introduction of modifications in order to enlarge it, especially expanding it to the visible.

After annealing, the semiconductor was highly crystalline, being only anatase with average crystallite size around 12 nm, estimated from the line width obtained for the peak of greatest intensity in XRD (**Fig.2**). For a semiconductor synthesized according to a similar methodology adopted by Batista, the minimum crystallite size obtained was equal to 22 nm (Batista, 2010).

From the curves of diffuse reflectance, the band gap of the synthesized TiO₂ and TiO₂ P25 Degussa were estimated. For this, we used Tauc's method (Wood & Tauc, 1972). For the synthesized TiO₂ was obtained a value equal to 3.18 eV while for TiO₂ P25 Degussa the estimated band gap was equal to 3.20 eV, in agreement with the value described by many authors (Hoffmann et al., 1995; Machado et al., 2008; Batista, 2010). The earlier versions obtained by precipitation, reported by Batista in his DSc Thesis (Batista, 2010) showed no photocatalytic activity due to its proper degree of aggregation and in some cases limited surface area. Most likely, due to the significant aggregation observed in semiconductor synthesized by Batista (2010), the recombination of charge carriers was more favored at the expense of photocatalytic reactions. It is very likely that the introduction of ultrasound in

the synthesis process resulted in significant increase in the dispersion of the particles formed during the formation of critical nuclei, resulting in the precipitation of particles with minimal or no aggregation. Morphological characterization of this new photocatalyst is ongoing.

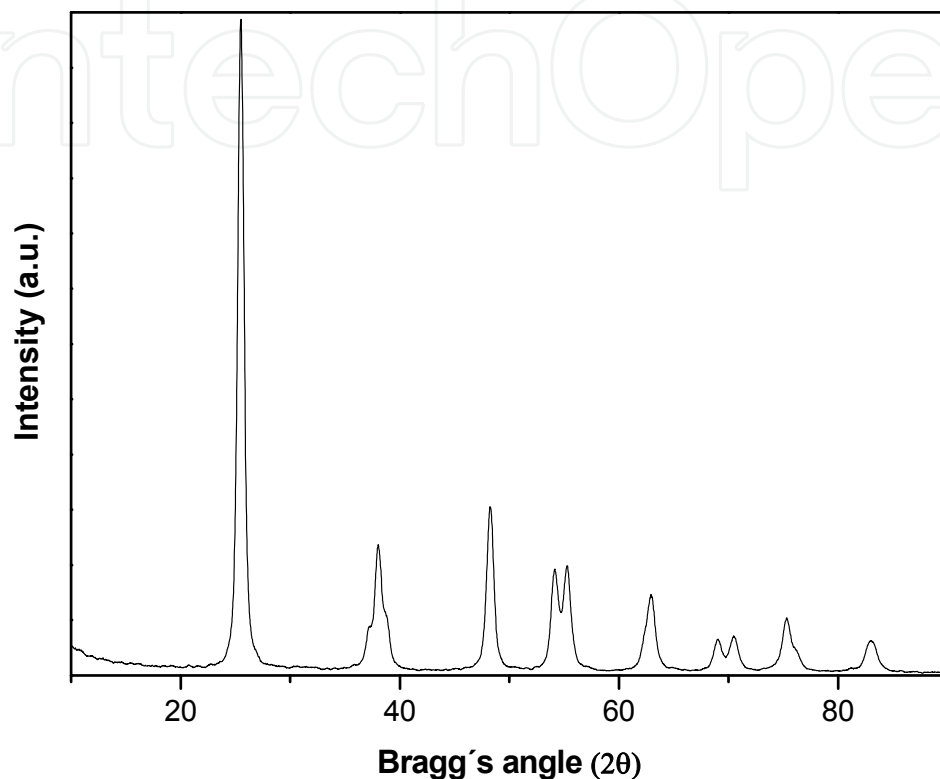


Fig. 2. X-ray diffraction patterns of TiO_2 synthesized by solubilization of titanium tetraisopropoxide in 2-propanol and subsequent hydrolysis and precipitation by slow addition of ultrapure water.

The mineralization of food dye tartrazine, C.I. 19140, mediated by this new photocatalyst is presented as an example. It was promoted at pH 3, using 100 mg/L of photocatalyst, in experiments on laboratory scale, using as radiation source a 400 W high pressure mercury vapor lamp. 4 L of the model effluent were used per experiment. Hydrogen peroxide (166 mg/L) was added as an extra font of radicals (Machado et al., 2003a). The results were compared to the obtained under the same conditions using TiO_2 P25 Degussa as photocatalyst. Additionally, all photolysed samples underwent the following tests: pH monitoring, spectrophotometric measurements through the use of a UV/VIS dual beam Shimadzu UV-1650PC spectrophotometer. The aliquots collected in the experiments in the presence of the photocatalyst were filtered using Millipore filters (0.45 μm of mean pore size) to remove suspended TiO_2 before the measurements. The experimental setup is similar to that described in previous studies (Machado, 2003; Oliveira, 2012).

After 120 minutes of reaction, 52% of mineralization was reached with the use of the synthesized TiO_2 . For TiO_2 P25-mediated degradation, the mineralization was 84% under

the same conditions. In the absence of H_2O_2 , the levels of mineralization were respectively 24 and 38% for the synthesized TiO_2 and TiO_2 P25 (Fig. 3). The mineralization was estimated from measurements of dissolved organic carbon using a Shimadzu TOC-VCPH Total Organic Carbon Analyzer.

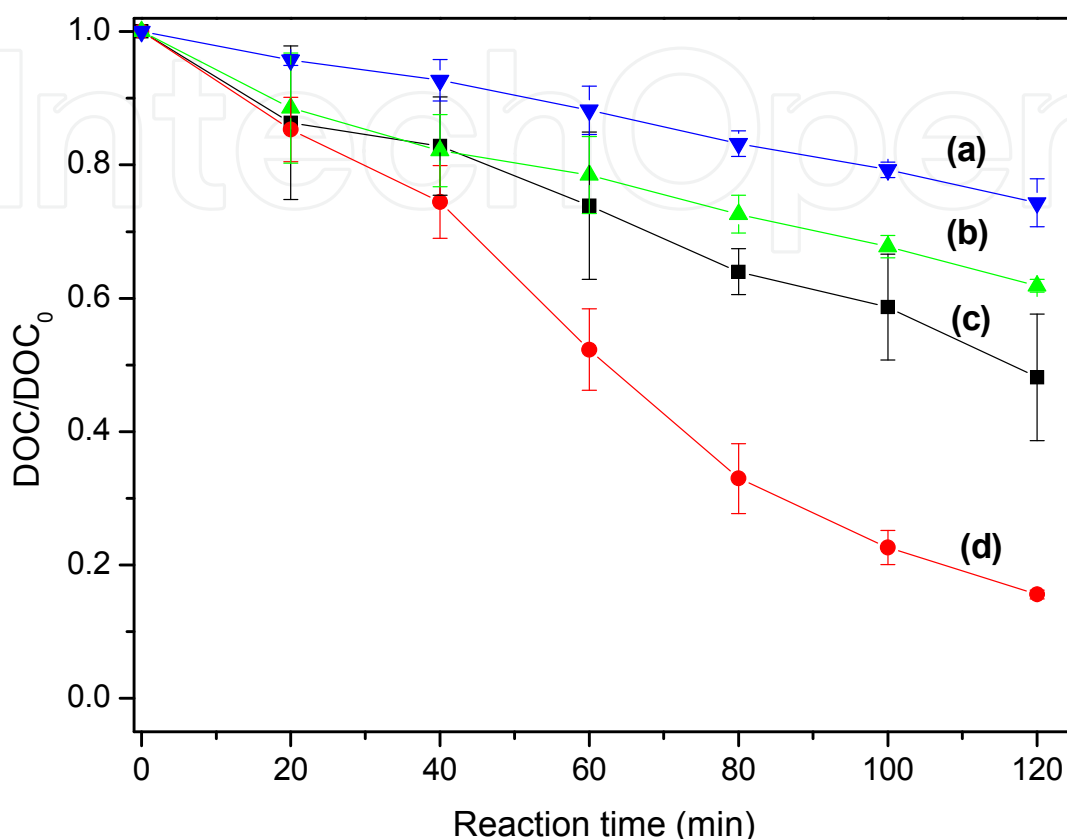


Fig. 3. Mineralization of tartrazine by heterogeneous photocatalysis using: (a) TiO_2 synthesized in reaction in the absence of H_2O_2 ; (b) TiO_2 P25 in reaction in the absence of H_2O_2 ; (c) TiO_2 synthesized, in reaction in the presence of H_2O_2 , and (d) TiO_2 P25 reaction in the presence of H_2O_2 .

The changes introduced during the solubilization and synthesis process itself should have been enough to guarantee a level of ordering of the particles formed. The final product after thermal treatment of the oxide formed proved to be 100% anatase.

2.2.2 Photocatalysts based on the association between a photosensitizing dye and a semiconductor oxide

Electron transfer at the interface between a photoactive species and the semiconductor surface is a fundamental aspect for organic semiconductor devices (Grätzel, 2001; Ino et al., 2005). Certain photoactive compounds has proven to be able, when electronically excited, to inject electrons in the conduction band of semiconductors (Grätzel, 2001; Ino et al., 2005; Rehm et al., 1996; Nazeeruddin et al., 1993; Asbury et al., 2001; Krüger et al., 2001; Argazzi et al., 1998; Xargas et al., 2000; Tennakone et al., 1997; Sharma et al., 1991; Hao et al., 1998; Chen et al., 1997; Wu et al., 2000), increasing the performance of dye-sensitized solar cells. In

particular, ultrafast charge separation led by electron injection from electronically excited photoactive molecules to the conduction band of a wide-gap metal oxide, and a good electronic coupling between dye molecules and surface of the substrate are key steps for improving the performance of these materials (Rehm et al., 1996; Nazeeruddin et al., 1993; Asbury et al., 2001). In the dye sensitization process, dye gets excited rather than the TiO₂ particles to appropriate singlet and triplet states, being subsequently converted to cationic dye radicals after electron injection to TiO₂ CB (Benko et al., 2002). The electrons injected to TiO₂ CB react with the preadsorbed O₂ to form oxidizing species (superoxide, hydroperoxyl and hydroxyl radicals) which combined to the species produced from photoexcited TiO₂, induce oxidative reactions (Wu et al., 1998). Thus TiO₂ plays an important role in electron-transfer mediation, even though TiO₂ itself is not excited. A photodegradation mechanism of dyes under visible irradiation without TiO₂ photoexcitation was recently presented by Kumar & Devi (2011). The formation of singlet oxygen has been reported in some cases (Stylidi et al., 2004).

The association between photosensitizing dyes and oxides semiconductors with photocatalytic activity constitutes a strategy for obtaining more efficient photocatalysts for a wider range of applications. These photosensitizing dyes, when excited by photons of lower energy, allow the injection of electrons from these species to the conduction band of the semiconductor increasing the concentration of charge carriers (Benkő et al., 2002; Sharma et al., 2006; Machado et al., 2008; Shang et al., 2011; Kumar & Devi, 2011). The electrons, in turn, can be transferred to reduce organic acceptors adsorbed on the catalyst surface (Machado et al., 2008). Thus, the photocatalyst composites containing a photosensitizing dye associated with the photoactive semiconductor have, in general, improved photocatalytic activity. The possibility of utilization of solar radiation, because they have the range of absorption expanded to the visible, makes it possible to achieve important contributions in solving problems concerning effluent treatment (Machado et al., 2008). Machado and coworkers (2003b; 2008; 2011; Duarte et al., 2005) have studied composites prepared by the association between zinc phthalocyanine (ZnPc) and titanium dioxide, obtained by coating TiO₂ particles using a solution of zinc phthalocyanine followed by controlled drying of the organic suspension (Machado et al., 2008). These materials have been intensively characterized (Machado et al., 2008; Batista et al., 2011). A decrease between 20 and 30% in the specific surface area (SSA) is verified for the composites when compared to the TiO₂ P25 (Machado et al., 2008; Oliveira et al., 2011; Batista et al., 2011). This difference should be as a result of the incorporation of ZnPc aggregates on the surface of the semiconductor. The changes in the specific area caused by the incorporation of zinc phthalocyanine do not imply distortions in the crystal structure (Machado et al., 2008). Scanning tunneling microscopy of different metal phthalocyanines confirm that the above mentioned aggregates are adsorbed onto the semiconductor surface (Qiu et al., 2004).

For these composites, the surface sensitization by electron transfer via physisorbed ZnPc should compensate the decrease in surface area, increasing the efficiency of the photocatalytic process. It should be emphasized that the extended range of wavelengths shifted to the visible region of the electromagnetic spectrum, which is capable of positively influencing the electron transfer between the excited dye and the semiconductor conduction band tends to improve electron-hole separation (Machado et al., 2008; Carp et al., 2004;

Wang et al., 1997; Shourong et al., 1997; Zhang et al., 1997; Zhang et al., 1998). These composites have shown to be better photocatalysts for wastewater decontamination, mainly mediated by visible light, than pure TiO₂ (Machado et al., 2003b; Duarte et al., 2005; Machado et al., 2008; França, 2011; Oliveira et al., 2012), performance that remains even when reused (Machado et al., 2008).

The zero point charge pH (pH_{ZPC}) was estimated for TiO₂ P25 and a composite containing 1.6% m/m of ZnPc by zeta potential measurements, carried out in a disperse suspension using a Zetasizer Nano ZS90. The estimated value for the composite, pH_{ZPC} = 5.50, lower than the one for P25 (pH_{ZPC} = 6.25) suggests a differentiated behavior for the composite since its surface is negatively charged in a pH range in which P25 is still with the surface positively charged. The value measured for TiO₂ P25 agrees with the reported in the literature (Hoffmann et al., 1995). The morphological characteristics of both samples were investigated by SEM, carried out in a Philips XL-30 microscope coupled to a field emission gun and a EDX analytical setup. The micrographs show the occurrence of macro-aggregates in the composite and spherical particles around 25 nm in P25. The estimated concentration of ZnPc on P25 surface is around 1.6%, confirmed by EDX measurements (Batista et al., 2011). Also, the thickness of ZnPc coating, homogeneity, and aggregation on the TiO₂ composite surface were evaluated by TEM using a Philips CM-120 microscope. The improvement of visible light absorption in TiO₂/ZnPc and electronic surface properties of this composite (Machado et al., 2008) are responsible for an almost three times faster mineralization of Ponceau 4R (C.I. 16255), an azo dye employed in the food industry, when compared with the result obtained using only TiO₂ P25, and still much higher than the presented by the other TiO₂-based photocatalysts (Oliveira et al., 2012). This dye is classified as a carcinogen in some countries and is currently listed as a banned substance by U.S. Food and Drug Administration (FDA).

The highest photocatalytic activity of TiO₂/ZnPc 1.6% seems to be the result of synergism between the photocatalytic characteristics inherent to TiO₂ P25 with the redox properties and charge transport of ZnPc Frenkel's "J" aggregates on the semiconductor surface (Fidder et al., 1991; Kim et al., 2006; Machado et al., 2008; Machado et al., 2011a). The sensitization of TiO₂ P25, induced by zinc phthalocyanine aggregates was effective in producing more active photocatalysts.

Fig. 4 presents the diffuse reflectance spectra (DRS) of ZnPc, TiO₂ and some of the studied TiO₂/ZnPc composites.

Unlike what occurs with TiO₂ (**Fig. 4a**), for composite materials obtained by the association between TiO₂ and ZnPc there is a significant electronic absorption for wavelengths above 390 nm. Comparison between the graphs presented in As can be seen in **Fig. 4 (a to e)**, the UV-Vis absorption spectrum (DRS) of these composites is not the result of an additive effect between the absorption spectra of the precursors. The absorption spectra of the composites are quite different from the typical absorption profiles of TiO₂ (**Fig. 4a**) and pure ZnPc in the solid state (**Fig. 4f**) or even in very dilute liquid solutions (Miranda et al., 2002).

The absorption spectrum of these composites is characterized by an intense absorption band below 460 nm, and a large, intense and non structured absorption band above 475 nm. Both bands are most probably the result of superposition of electronic states of TiO₂ and ZnPc aggregates.

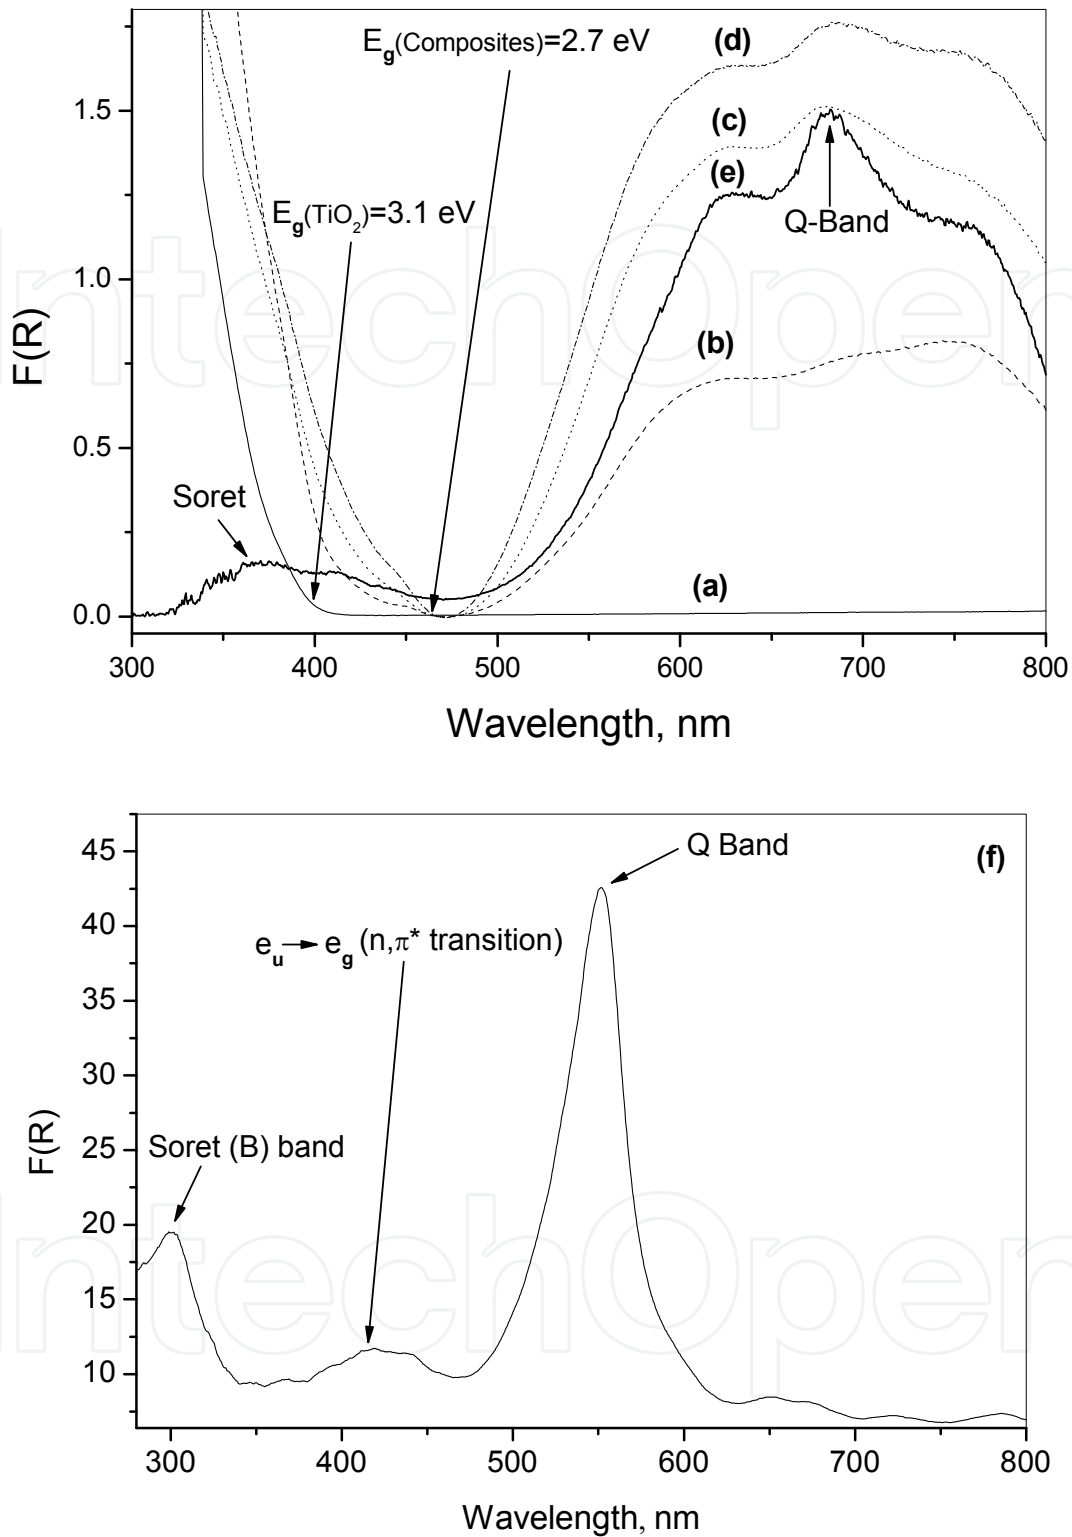


Fig. 4. Diffuse reflectance spectra (DRS) of TiO₂ and TiO₂/ZnPc composites, prepared with different percent in mass of ZnPc. TiO₂ P25 (a) and composite containing: 1.0% of ZnPc (b); 2.5% of ZnPc (c); 5.0% of ZnPc (d); composite containing 2.5% of ZnPc, using TiO₂ P25 as reference (e) and DRS of pure ZnPc (f). Barium sulphate was used as reference for (a) to (d) (Machado et al., 2008).

In **Fig. 4e** the shape of the bands in the ultraviolet and visible portions of the electronic spectrum of the composite containing 2.5% m/m of ZnPc, obtained using TiO₂ as reference, is very different from that observed for pure ZnPc in the solid state, **Fig. 4f**. In the visible, it presents a large and intense three peak band centered by a red shifted Q band, with maximum at 683 nm. The bathochromic shift of the absorption maximum associated to Q band, suggests the occurrence of Frenkel's J aggregates of ZnPc (**Fig. 5**) in the composites (Köhler & Schmid, 1996; Einfeld & Briggs, 2006; Chen, Z. et al., 2008), which agrees with results of a theoretical study employing methods of Density Functional Theory on the formation of aggregates of zinc phthalocyanine (Machado et al., 2011a). The bathochromic shift of the absorption maximum of the Q band highlights the differentiated nature of these compounds against pure TiO₂ and ZnPc. The Soret (B) band also presents a different shape compared to its equivalent in pure ZnPc in the solid state (**Fig. 4f**), and is red shifted. The spectrum of **Fig. 4e** is very similar to the absorption spectrum for a flash-evaporated ZnPc thin film deposited on a glass substrate (Senthilarasu et al., 2003), in which the two energy bands characteristic of phthalocyanines are evident, one in the region between 500 and 900 nm, with an absorption peak at 690 nm, related to the Q band, and the other, very intense, at 330 nm, attributed to Soret (B) band (Meissner & Rostalski, 2001), similar to that reported for the absorption spectrum for thin films of Magnesium Phthalocyanine (Mi et al., 2003). The unstructured band in the visible and the red shifted Q band of these composites can be attributed to the strong intermolecular interactions due to ZnPc aggregation (ZnPc_{agg}), resulting in coupling effects of excitons on the allowed transitions, with significant effects on the mobility of charge carriers (Hoffmann, 2000).

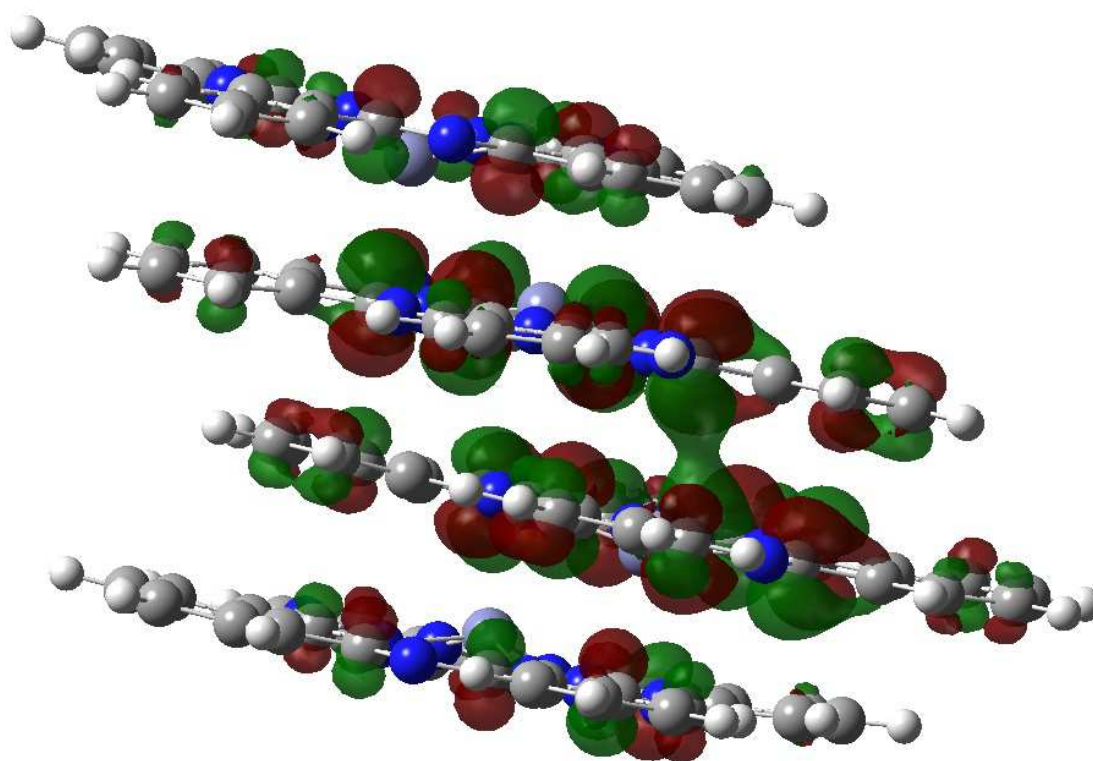


Fig. 5. Representation of the molecular structure of a Frenkel's J aggregate of ZnPc formed by four grouped individual molecules, indicating the sharing the same ligand MO between the ZnPc 2 and 3, in the HOMO (Machado et al., 2011a).

Fig. 4f presents the diffuse reflectance spectrum of pure ZnPc. The intense absorption peak at 552 nm, is related to the Q band and is attributed to very intense $\pi \rightarrow \pi^*$ transitions (Leznoff & Lever, 1990). The Soret band presents an absorption maximum at 301 nm. A low intensity and non structured absorption band with the absorption peak centered at 416 nm, is related to an $n \rightarrow \pi^*$ transition involving the e_u azanitrogen lone pair orbital with the e_g LUMO (Ricciardi et al., 2001). A set of three very small intensity low energy bands, above the Q band, can also be observed.

The E_g value for the TiO_2/ZnPc composites, 2.7 eV, lower than the estimated for pure TiO_2 (Hoffmann et al., 1995), has a value similar to the estimated for iron (II) phthalocyanine excitons (2.6 eV) in TiO_2/FePc blends (Sharma et al., 2006) and other metal phthalocyanine associated to semiconductor oxides (Iliev et al., 2003). For ZnPc thin films, Senthilarasu et al. assigned an E_g of 1.97 eV (Senthilarasu et al., 2003) with a directly allowed optical transition, near the value estimated for the peak absorption Q-band (2.25 eV) of pure ZnPc in the solid state (**Fig. 4f**). The E_g for the composites might be related to the coupling between TiO_2 and ZnPc electronic states and their positive implications. Similar to TiO_2/FePc blends (Sharma et al., 2006) and ZnPc thin films (Ino et al., 2005; Senthilarasu et al., 2003), the photoexcitation of ZnPc aggregates should result in the formation of e^-/ZnPc^+ pairs, followed by electron transfer from ZnPc excitons to the conduction band of bulk TiO_2 , which explains at least in part the improved photocatalytic activity observed for some of the ZnPc/TiO_2 composites (Machado et al., 2008; Oliveira et al., 2012). Sharma et al. reported charge separation after photo-excitation of TiO_2/FePc composite film due to charge transfer from FePc to TiO_2 resulting in $\text{FePc}(h^+)$ and $\text{TiO}_2(e^-)$ (Sharma et al., 2006). Additionally, they reported that the charge transport and the current leakage through FePc films and the photo-generation are due to the efficient dissociation of exciton at the donor-acceptor interface of the bulk, and that the higher holes mobility in the organic material layer, combined with lower conductance leakage, leads to the more efficient collection of photo-generated carriers. Thus, the electronic coupling strength between donor and acceptor is one of the critical conditions to ensure the occurrence of such electron transfer (Ino et al., 2005; Rehm et al., 1996; Senthilarasu et al., 2003; Meissner & Rostalski, 2001).

The spectrum presented in **Fig. 4e** is very similar to the absorption spectrum for a flash-evaporated ZnPc thin film deposited on a glass substrate (Senthilarasu et al., 2003), in which the two energy bands characteristic of phthalocyanines are evident, one in the region between 500 and 900 nm, with an absorption peak at 690 nm, related to the Q band, and the other, very intense, at 330 nm, attributed to Soret (B) band (Meissner & Rostalski, 2001), similar to that reported for the absorption spectrum for thin films of Magnesium Phthalocyanine (Mi et al., 2003).

2.3 Solar photocatalysis using a compound parabolic concentrator (CPC) reactor

2.3.1 Design and construction of a CPC reactor

The study of new technologies has now focused on decontamination methods feasible alternatives that are environmentally friendly, and allow its application in large scale, with easy operation and low cost.

The economic use of AOPs based on the use of solar radiation in the treatment of wastewater has been proposed for their low cost, especially in regions with high insolation

(Malato et al., 2002; Machado et al., 2003; Sattler et al., 2004a, 2004b; Machado et al., 2004; Palmisano et al., 2007; Machado et al., 2008; Torres et al., 2008; Li et al., 2009). Literature reports suggest that the reactors most suitable for application in solar photocatalysis are CPC type (Malato et al., 1997; Malato et al., 2002; Sattler et al., 2003a, 2003b; Machado et al., 2004; Duarte et al., 2005; Machado et al., 2008).

CPC reactors are static collectors of solar radiation with reflective surfaces in the form of involute positioned around cylindrical tubes, **Fig. 6**. Reflectors with this geometry allows the pock up of solar radiation, either by direct incidence, as the diffuse radiation, directing it to a glass tube through which circulates the effluent to be treated (Duarte et al., 2005).

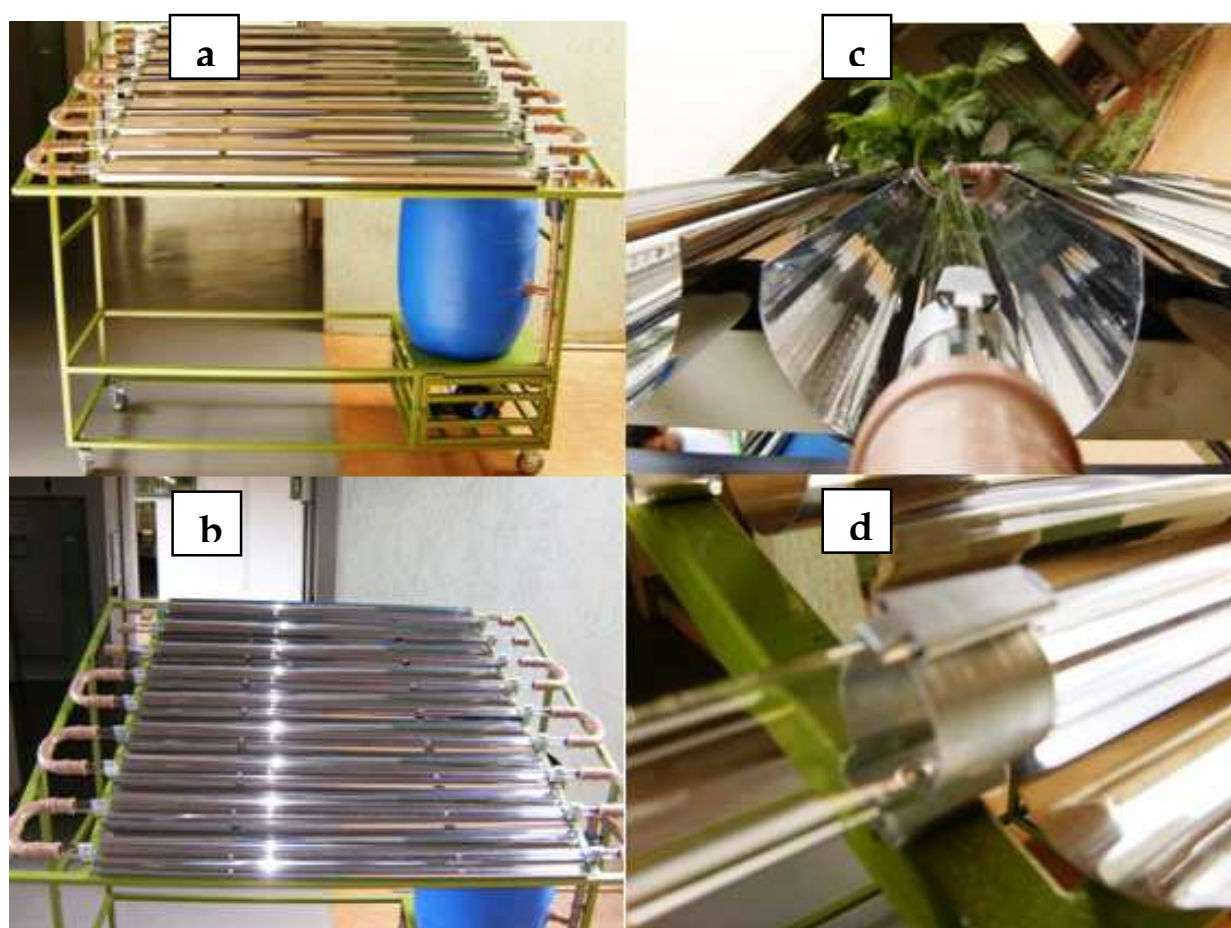


Fig. 6. Representation in two angles (a and b) of a CPC reactor, detailing one of the reflectors in the form of involute (c), and pipes the fixed to the body of the reactor (d).

Our CPC reactor was designed to process up to 150 L of effluent, This reactor consists in a module with an aperture of about 1.62 m², elevation angle adjusted to the latitude of Uberlândia, Brazil (19° S), ensuring a better use of incident radiation. The reflecting surface contains 10 borosilicate glass tubes (external diameter 32 mm, wall thickness of 1.4 mm, and length of 1500 mm), mounted in parallel and connected in series, each on double parabolic shaped inox steel reflector surfaces (Duarte et al., 2005). A centrifugal pump of 0.50 HP with rotor and housing made in inert material has been used to ensure a flow of 2 m³/h.

The flow of effluent in tubular reactors is usually turbulent, which may cause loss of efficiency in the capture of solar radiation. However, this difficulty can be minimized during the design of the reactor, and the use of balanced amounts of the catalyst, in the case of heterogeneous photocatalysis, so as to guarantee a uniform flow and a good dispersion of the photocatalyst in the effluent to be treated, minimizing possible effects of co-absorption of the incident radiation (Duarte et al., 2005). Non-uniform flows implies in non uniform residence times that can lower efficiency compared to the ideal conditions (Koca & Sahin, 2002). In the case of the heterogeneous processes with photocatalyst powder in suspension, sedimentation and depositing of the catalyst along the hydraulic circuit should be avoided and turbulent flow in the reactor needs be guaranteed. Reynolds's number varying between 10 000–50 000 ensures fully turbulent flow and avoids the settlement of the photocatalyst particles in the tubes (Malato et al., 2002). In our project, the Reynolds' number were defined as being $Re_{\text{glass}} = 34,855.4$ and $Re_{\text{PVC}} = 40,070.0$, for glass and PVC, the materials where the effluent with the photocatalyst in suspension circulate.

Details of the project of a CPC reactor similar to the built in our laboratory are available in Duarte et al., 2005.

2.3.2 Photocatalytic degradation of organic substrates using solar radiation

2.3.2.1 Degradation of organic matter present in a model-effluent simulating the wastewater produced by a pulp and paper industry, using TiO₂ P25 and the composite TiO₂/ZnPc 2.5% m/m

The performance of the studied composites to degrade organic matter present in wastewaters, in reactions mediated by solar irradiation, and the possibility of reuse of such photocatalysts, was evaluated monitoring the consumption of the organic matter content during the treatment of three 50 L batches of a model effluent (an aqueous solutions containing 160 mg L⁻¹ of a sodium salt of lignosulphonic acid (Sigma-Aldrich), possessing a mean molecular mass of 52,000 D. The reactions were done at pH 3, with the addition of hydrogen peroxide (30 mg L⁻¹), used as additional source of reactive species (Machado et al., 2003a), and monitored by chemical oxygen demand (COD) analysis of aliquots of effluent samples collected at different accumulated doses of UV-A radiation (this option was due to operational limitations. However, the spectral pattern of the visible light does not change significantly during the execution of the experiments). To evaluate the observed (global) reaction kinetics, the temporal variations were substituted by the UVA accumulated dose, which warrants the reproducibility of these experiments under different latitude and weather conditions. The incident UV-A radiation was monitored using a Solar Light PMA-2100 radiometer. All reactions were stopped when the accumulated dose of UVA reached 900 kJ m⁻² (Machado et al., 2008). This corresponds to about 3 hours of sunlight on a sunny day, or 5 to 6 hours during a cloudy day with moderate to high nebulosity in Uberlândia, MG, Brasil (Duarte et al., 2005).

The COD measurements considered the Environmental Protection Agency (EPA) recommended method (Jirka & Carter, 1975).

A same sample of the photocatalyst (100 mg per liter of effluent), containing initially 2.5% of ZnPc, was used to treat the three effluent batches. The treatment of each batch was performed using a CPC (Compound Parabolic Concentrator) reactor (Duarte et al., 2005).

As reference, an additional effluent batch was treated under similar conditions using pure TiO₂ P25 as photocatalyst.

The degradation of the sodium salt of lignosulphonic acid (LSA) suggests higher photocatalytic efficiency for the TiO₂/ZnPc composite. Fig. 7 shows a more effective LSA degradation under the action of TiO₂/ZnPc, which increases with reuse, with significant changes in the degradation profile due to the use of the recovered composite. While under the action of TiO₂ P25 was reached 60% degradation, under the same conditions, with the unused composite, the degradation reached 96%. For the composite in both the first and second reuse, the degradation of the LSA was about 90%. The change in profile suggests that other processes, less likely to occur before, became important for the overall reaction (Machado et al., 2008). The production of singlet oxygen by photosensitization from ³ZnPc*, for example, is an event plausible if the level of aggregation of ZnPc is reduced. The formation of singlet oxygen has been reported in some cases (Stylidi et al., 2004).

On the other hand, the better hydration of the surface of the composite due to the increasing number of cycles of use, should favor reactions from the valence band.

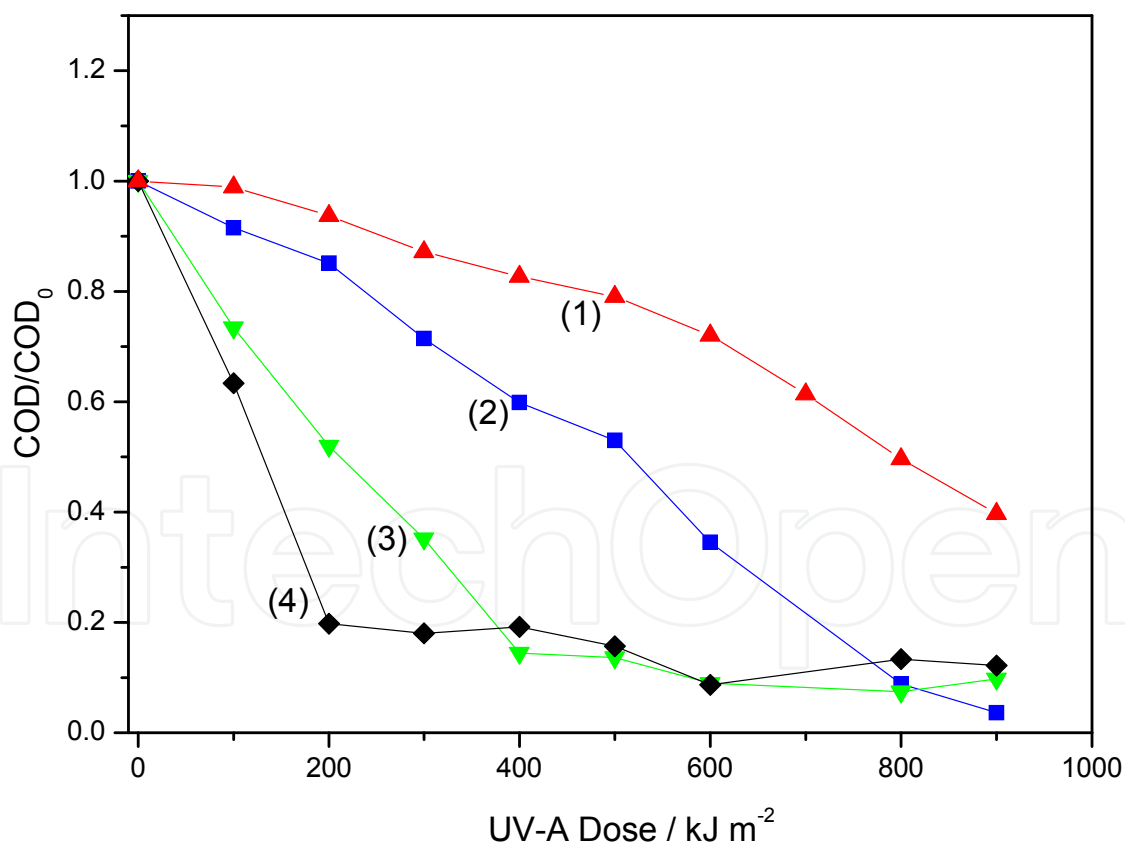


Fig. 7. Degradation of the organic load present in 50 L of a model waste water containing LSA monitored in terms of relative chemical oxygen demand (COD/COD₀), induced by: (1) TiO₂ P25; (2) TiO₂/ZnPc 2.5%; (3) TiO₂/ZnPc 2.5% in the first recycling; (4) TiO₂/ZnPc 2.5% in the second recycling.

Despite the fact that part of ZnPc adsorbed to the surface of TiO₂ P25 may have been degraded during the photocatalytic process, surprisingly, the photocatalytic efficiency of the composite did not decrease when reused. Results suggest that the composite can be reused at least five times before making any significant loss of photocatalytic efficiency.

2.3.2.2 Photocatalytic degradation of paracetamol using solar photocatalysis

Conditions were evaluated to promote the mineralization of paracetamol (or acetaminophen), a known emerging contaminant (Daughton, C. G. & Ternes, T. A., 1999; Bound, J. P. & Voulvoulis, N., 2004; Jones, O. A. H., Voulvoulis, N. et al., 2007; Nikolaou, A., Meric, S. et al., 2007; Zhang, X. et al., 2008; Bartha, B. et al., 2010), employing heterogeneous photocatalysis mediated by TiO₂/ZnPc 2.5% m/m, under the action of solar radiation. The results were compared with process under similar conditions, using TiO₂ P25 as photocatalyst.

Firstly, to find the best experimental conditions, the influence of hydrogen peroxide concentration and pH was evaluated in the photocatalytic reactions mediated by 100 mg L⁻¹ of photocatalyst, on a laboratory scale using an experimental setup already described (Machado et al., 2003a; Oliveira et al., 2012). The best conditions for the reactions in laboratory scale were obtained at pH 6.80 using 33.00 mg L⁻¹ of hydrogen peroxide for the degradation and mineralization of aqueous solutions containing 10 mg L⁻¹ of paracetamol (França, 2011). Under these conditions, the substrate was completely oxidized after 40 minutes of reaction using TiO₂ P25, while 78% of mineralization with this same photocatalyst was reached after 120 minutes of reaction. Using the TiO₂/ZnPc composite, the substrate was completely oxidized after 60 minutes of reaction, and 63% was mineralized after 2 hours of reaction.

In the photocatalytic tests using a CPC reactor and solar radiation (**Fig. 8**), the experiments were done preferentially at pH 3.00 (França, 2011), using 50 L of an aqueous solution containing 10 mg L⁻¹ of paracetamol and 100 mg L⁻¹ of photocatalyst. Hydrogen peroxide, used as additional radical source (Machado et al., 2003a), was employed at the same concentration as defined in studies on laboratory scale.

Although the mineralization of paracetamol under the action of solar radiation has been equivalent in both cases (56%), after the accumulation of an UVA dose equal to 700 kJ m⁻², comparing the results obtained on laboratory scale and induced by solar radiation, it was observed that the increase in mineralization obtained with the use of the composite, 33%, was higher than that obtained using the commercial photocatalyst, equal to 25%, suggesting a better utilization of solar radiation by TiO₂/ZnPc composite.

In terms of degradation, monitored by high performance liquid chromatography (HPLC), the commercial photocatalyst required the accumulation of less UVA radiation (200 kJ m⁻²) to oxidize 96% of paracetamol, whereas for the composite this level of degradation was achieved when the dose reached 350 kJ m⁻² (**Fig. 9**).

The results obtained by Zhang et al (2010) indicated that TiO₂ photocatalytic degradation is an effective way to remove paracetamol from wastewater and drinking water without any generation of more toxic products. Although we have not analyzed the intermediates and products obtained, our results also point to the efficiency of heterogeneous photocatalysis in the treatment of acetaminophen, even if present in high concentrations in wastewater and drinking water.

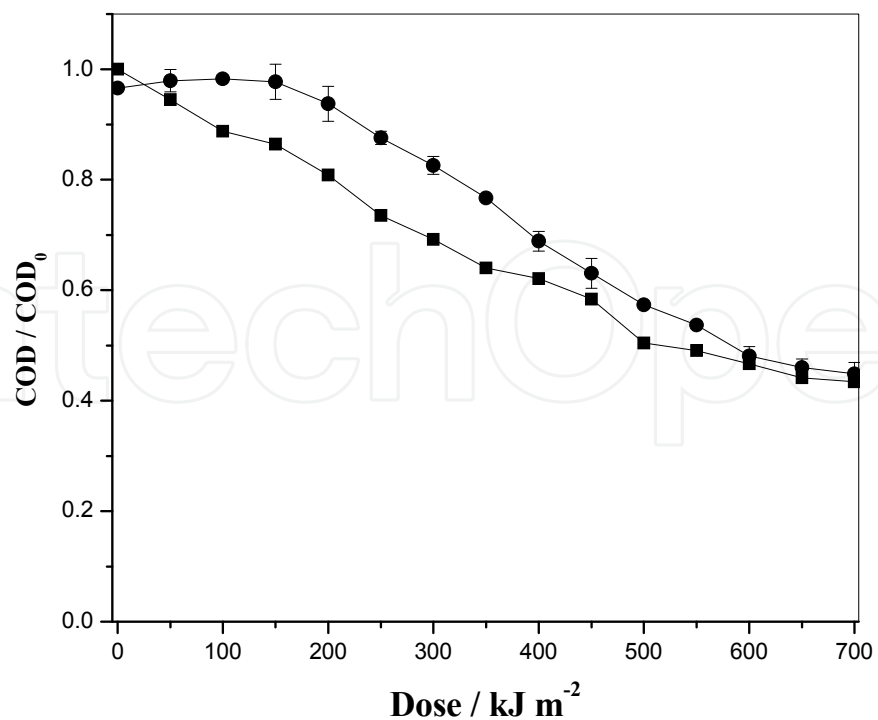


Fig. 8. Variation of dissolved organic carbon (DOC) as a function of cumulative dose of UVA, during the photocatalytic degradation of paracetamol mediated by solar radiation: TiO₂/ZnPc 2.5% m/m (●); TiO₂ P25 (■).

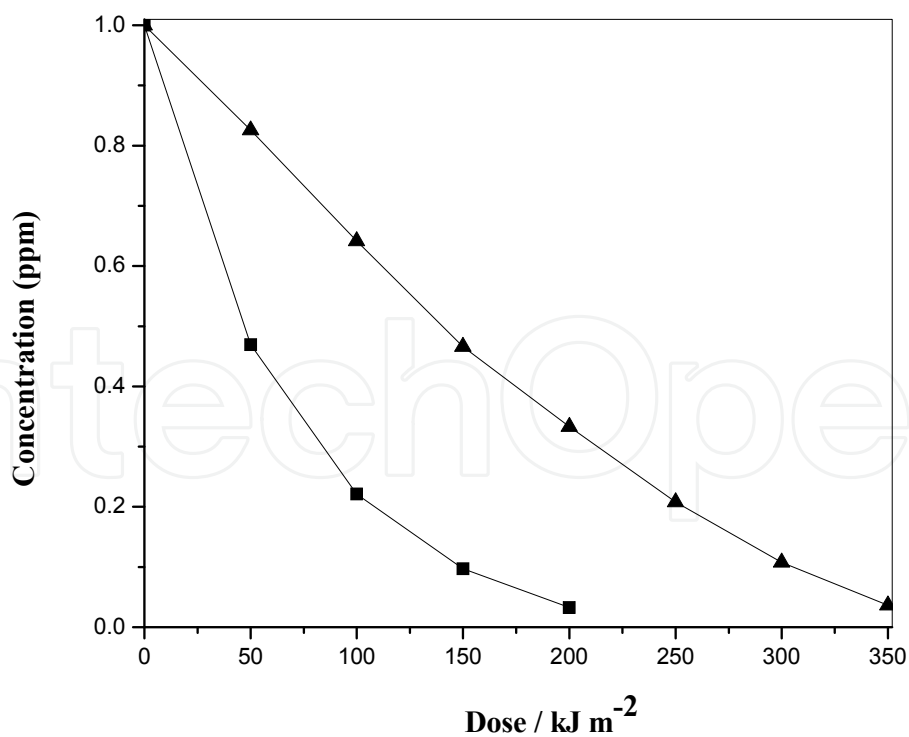


Fig. 9. Variation in the concentration of paracetamol measured by HPLC during photodegradation experiments mediated by TiO₂ P25 (■) and TiO₂/ZnPc 2.5% m/m (▲) and induced by solar radiation.

3. Obtention of gaseous hydrogen for energy production

The International Energy Agency (IEA) estimates that world demand for energy should suffer an increase of 45% by 2030 (Biroi, 2008). Based on the projections presented, one can expect a worsening of global warming, if no measures are taken that result in significant reduction of CO₂ emissions. In addition, we expect a worrying shortage of fossil fuels, if alternative sources of energy are not being widely used.

Among the alternative energy sources, H₂ is a very attractive option, as it concentrates high energy per unit mass - 1.0 kg of hydrogen contains approximately the same energy furnished by 2.7 kg of gasoline, which facilitates the portability of energy (Smith & Shantha, 2007). Besides, its combustion generates no contaminants.

Experts have pointed out three major obstacles to the expansion of consumption of hydrogen taking into consideration the technology available at the moment: clean production, low cost, storage and transportation. As a result, most efforts to expand the use of hydrogen as a source of cheap energy has been based on the development of new materials and processes of production.

Among the technologies for hydrogen production, biomass gasification (Albertazzi et al., 2005; Smith & Shantha, 2007), photocatalysis (Ni et al. 2007; Patsoura et al., 2007; Jing et al., 2010), and biological processes (Peixoto, 2008), have been focus of many studies for being routes clean and renewable. The heterogeneous photocatalysis and hydrogen generation by decomposition of water using concentrated solar radiation as primary source energy are between the most promising having gain attention due to their potential.

The great expectation of the global market for the use of hydrogen gas as an important input in the production of energy has been driven by the sectors of energy generation and distribution, which moves large numbers of capital around the world, and is in frank expansion, due to the enormous demand for energy by all sectors (Steinfeld, 2005; Preguer et al., 2009; Pagliaro et al., 2010). Most efforts to expand the use of hydrogen as a renewable energy source has been based on the development of fuel cell technology, both for expansion of its service life, by minimizing costs. Volumes of hydrogen gas have already been produced, both in EU-funded projects, such as the United States.

3.1 Hydrogen production using heterogeneous photocatalysis

In recent decades, research has been conducted on the possibility of using hydrogen as energy vector with low carbon emissions. The policy guidance for reducing the emission of greenhouse gases, and the prospect of decline in oil and other fossil fuels, has brought to light again the discussion about the use of hydrogen and technologies related to it. However, it is clear that large-scale use of hydrogen will only be possible if renewable sources are used in its production (Preguer et al., 2009). Currently, renewables contribute only about 5% of the commercial production of hydrogen, while the remaining 95% are derived from fossil fuels, given the still high cost of production from renewable sources.

The photocatalytic degradation of water to produce hydrogen, under the action of solar energy, offers a promising way to produce hydrogen cleanly, inexpensive and environmentally friendly. While great progress in photocatalysis using radiation in the ultraviolet region has occurred in recent decades, it has been extended with some difficulty,

considering the use of visible radiation as a trigger for photocatalytic processes. Particularly, we have achieved some progress in this direction, involving the association between a photosensitizer dye and a semiconductor oxide.

The development of semiconductor oxides capable to be excited by radiation in the visible region became one of the most important topics in photocatalysis research, since the visible light represents a significant fraction of solar energy usable (Hwang et al., 2004). However, finding another photocatalyst than TiO_2 , which has good chemical stability, corrosion resistance, be able to efficiently absorb radiation in the visible, and is environmentally friendly, has proved an arduous task. However, no semiconductor material capable of catalyzing the overall water splitting under action of visible radiation around 600 nm, with a quantum efficiency high enough to make possible the commercial application (Maeda & Domen, 2007; Jing et al., 2010). Besides, many of the photocatalysts capable to induce hydrogen production with commercially acceptable quantum efficiency, with excitation between 300 and 450 nm, are expensive and inadequate from the environmental point of view (Zeug et al., 1985; Maeda et al., 2006; Bao et al., 2008).

The low efficiency for the hydrogen production by semiconductor photocatalysis already with appropriate band gap should be due to the following reasons: 1) quick electron/hole recombination in the bulk or on the surface of semiconductor particles; 2) quick back reaction of oxygen and hydrogen to form water on the surface of catalyst; and 3) inability to promote efficient use of visible radiation. It is known that photogenerated electrons easily recombine with holes in the semiconductor (Hoffmann et al., 1995; Li et al., 2010; Kumar & Devi, 2011), compromising the quantum efficiency of the photocatalytic process (Kudo, 2006). Noble metal loading can suppress to some extent the charge recombination by forming a Schottky barrier (Chand & Bala, 2007; Fu et al., 2008). Often, sacrificial reagents has been added to the reaction media for the elimination of photo-generated holes, minimizing the electron/hole recombination, improving the quantum efficiency (Liu et al., 2006; Zaleska, 2008a; Jing et al., 2010). Methanol, ethanol and acetic acid have usually been employed as agents of sacrifice. Toxic organic substrates can also be a good option of sacrificial reagent (Jing et al., 2010).

Much progress has been made in photocatalytic water splitting since the Fujishima-Honda effect was reported (Fujishima & Honda, 1971, 1972). Thermodynamically, water splitting into H_2 and O_2 can be seen as an unfavorable reaction ($\Delta G = +238 \text{ kJ/mol}$) (Jing et al., 2010; Melo & Silva, 2011). However, the efficiency of water splitting is determined by the band gap, band structure of the semiconductor and the electron transfer process (Linsebigler et al., 1995; Hagfeldt & Grätzel, 1995; Melo & Silva, 2011).

Generally for efficient H_2 production using visible light-driven semiconductor the band gap should be less than 3.00 eV (ca. 420 nm) and higher than 1.23 eV (ca. 1000 nm), corresponding to the water splitting potential (Jing et al., 2010; Melo & Silva, 2011). Moreover CB and VB levels should satisfy the energy requirements set by the reduction and oxidation potentials for H_2O , respectively: the bottom of the conduction band must be located at a more negative potential than the H^+/H_2 reduction potential ($E_0 = 0 \text{ V vs. NHE}$ at pH 0), while the top of the valence band must be more positively positioned than the $\text{H}_2\text{O}/\text{O}_2$ oxidation potential ($E_0 = 1.23 \text{ V vs. NHE}$) (Melo & Silva, 2011). Band engineering is thus necessary for the design of new semiconductors with the combined properties (Jing et al., 2010).

Oxides as $\text{HPb}_2\text{Nb}_3\text{O}_{10}$, MgWO_x and NiInTaO_4 among others, active under the action of ultraviolet radiation, were also active in the visible region after doping using C, N and S (TiO_2N_x , TiO_2C_x , TaON and $\text{Sm}_2\text{Ti}_2\text{O}_5\text{S}$) (Hwang et al., 2004), as well as certain perovskite-type photocatalysts, with significant absorption in the visible. Zhang & Zhang (2009) reported the synthesis of a photocatalyst based on BiVO_4 which showed high photocatalytic activity in the visible region. However, most of these catalysts are not environmentally friendly as TiO_2 .

Photocatalytic induced water-splitting technology involving nanosized TiO_2 , despite the considerable variety of semiconductor photocatalysts capable to split water using solar energy and other photocatalytic processes has great potential to support an economy based on low-cost and environmentally friendly hydrogen production using solar radiation (Ashokkumar, 1998; Ni et al., 2007).

The photocatalytic hydrogen production using TiO_2 as photocatalyst can be schematized through **Figs. 1 and 10**.


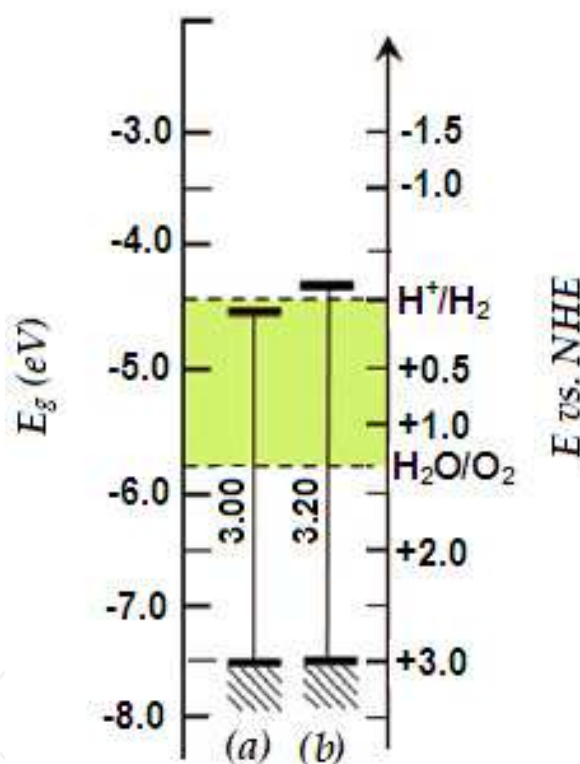


Fig. 10. Band gap of (a) Rutile and (b) Anatase compared to the redox potential of water at pH 1.

For an efficient production of H_2 , the energy level of the CB should be more negative than the energy level of the reduction of hydrogen, while the energy level of VB should be more positive than the energy level of the oxidation of water to formation of O_2 (**Fig.10**) (Ashokkumar, 1998; Ni et al., 2007), eqs 5 to 7. As outlined in **Fig. 1**, the vacancies photogenerated in the VB oxidize water into oxygen and hydrogen cations. These cations are reduced to molecular hydrogen in the conduction band. In other words, the separated electrons and holes act as reducer and oxidizer, respectively, in the water splitting reaction to produce hydrogen and oxygen. However, for this to happen effectively, it is necessary to

ensure the fast transportation of the photogenerated carriers, avoiding bulk electron/hole recombination. Separation of hydrogen gas is also required as oxygen and hydrogen are produced simultaneously.



Having the adequate semiconductor, capable to induce water splitting when photoexcited by solar radiation, a key issue concerns the efficient utilization of the solar energy itself. Two major drawbacks of solar energy must be considered: (1) the intermittent and variable manner in which it arrives at the earth's surface (2) efficient collection of solar light on a useful scale. The first drawback can be solved by converting solar energy into storable hydrogen energy. For the second, the solution could be the use of solar concentrators (Jing et al., 2010).

For photocatalytic hydrogen production, it is imperative the use of visible radiation, especially if the goal is the storage of the energy supplied by the sun. Thus, photocatalysts able to mediate reactions through the use of visible radiation are more than desirable. Amplify the sensitivity of photocatalysts through the introduction of dopants, impurities and / or association between semiconductor and photosensitizers capable of shifting the absorption of the resulting composite to visible, are alternatives to a more efficient water photolysis (Hwang et al., 2004; Machado et al., 2008; Zaleska, 2008a, 2008b; Zhang & Zhang, 2009).

When a metal (eg platinum) is deposited on a semiconductor, the excited electrons migrate from the semiconductor to the metal until the Fermi levels of both species are aligned. The Schottky's barrier (Chand & Bala, 2007; Fu et al., 2008) formed at the metal/semiconductor interface can serve as a trap for electrons, efficient enough to minimize electron-hole recombination, increasing the efficiency of the photocatalytic process. At the same time, the metal is important for its own catalytic activity. Metals deposited on a semiconductor serve as active sites for the production of H₂, in which the trapped electrons are transferred to photogenerated protons to produce H₂ (**Fig. 11**) (Melo & Silva, 2011).

Research on photocatalytic hydrogen production in our laboratory is very recent. Our primary aim is the development of highly efficient, stable and low-cost visible-light-driven photocatalyst using different modification methods, such as doping, sensitization, supporting and coupling methods to extend the light response and performance of the photocatalyst aiming its application in environmental photocatalysis and photocatalytic hydrogen production. Despite a considerable variety of semiconductor photocatalysts capable to split water using solar energy and mediate other photocatalytic processes (Ashokkumar, 1998; Kim et al., 2010; Jing et al., 2010; Kumar & Devi, 2011), our studies have focused on improving the photocatalytic activity of TiO₂ through its synthesis by different procedures, their use and of hybrid variants, doped or not, and composites involving TiO₂ and photosensitizing dyes, especially considering issues related to the environment. In particular, we have studied photocatalytic reactions using solar radiation, with the photocatalyst in aqueous suspensions, with methodologies based on CPC reactor.

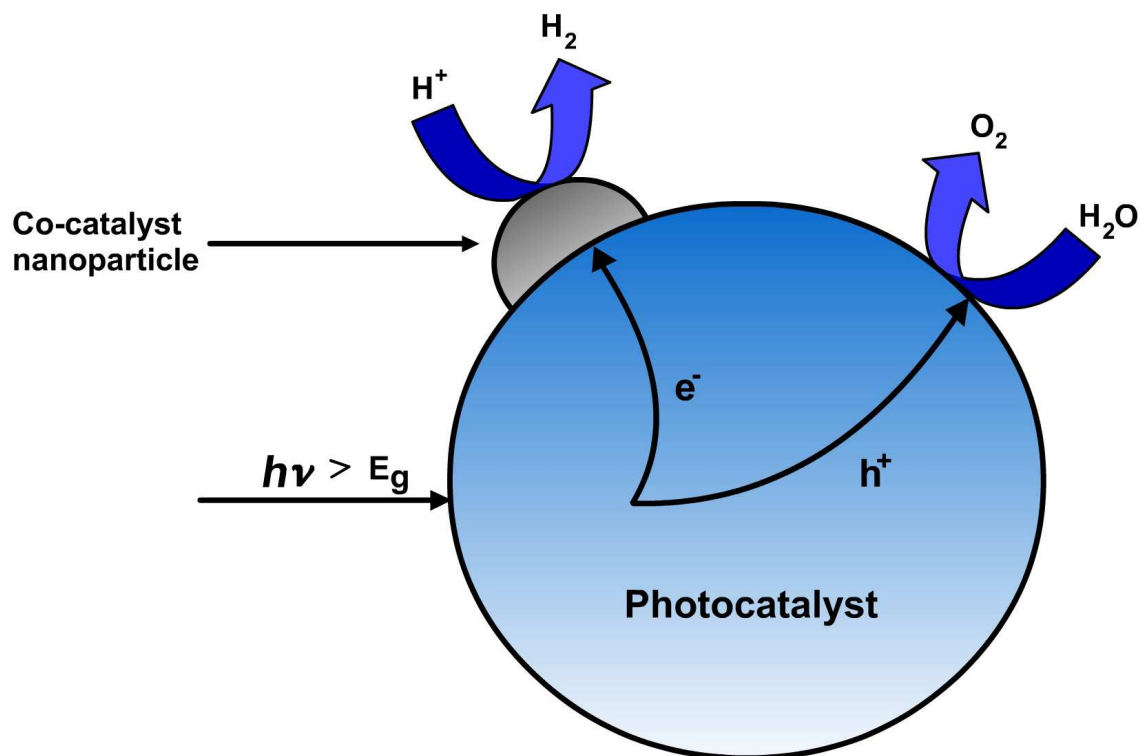


Fig. 11. Schematic representation of the photocatalytic water splitting on a platinized semiconductor powder particle.

We have developed small closed circulation reactor for bench-scale tests. These reactors ensure the evaluation of the developed photocatalyst from lab scale to out-door scale, in a batch mode.

The object of these studies is to improve hydrogen production and its storage under low pressure.

4. Solar cells

Photovoltaic cells are a good example of an alternative energy source, converting sunlight into electricity. Research in this field is quite intense given the importance of solar cells as sources of sustainable energy, as well as due to their reduced cost, low environmental impact, and fair efficiency for conversion of solar energy into electricity (O'Regan & Grätzel, 1991; Grätzel, 2003; Brennaman et al., 2011).

The efficiencies obtained for a silicon solar cell is about 24%, although at a very high manufacturing cost. Therefore, other materials have been studied in order to facilitate the conversion of solar energy into electrical energy (Zhao et al, 1998; Jayaweera et al., 2008; Cao et al., 2009; Patrocínio et al., 2010; Brennaman et al., 2011).

New developed devices such as dye solar cells, capable of converting solar energy into electrical (dye solar cells - DSCs), have been presented as alternatives for power generation (Hagfeldt & Grätzel, 1995; Grätzel & Hagfeldt, 2000; Jayaweera et al., 2008). Despite its efficiency is still lower than that of silicon cells, the DSCs have been particularly interesting

because they have a much lower production cost than devices based on silicon. In addition, the resulting material can be extremely thin as well as flexible and can be applied to almost any surface (Brabec et al., 2001; Kippelen & Bredas, 2009). Technically they are known as dye-sensitized solar cells, or DSSCs.

4.1 Dye-sensitized solar cells (DSSCs)

The use of solar cells based on a combination of dyes and photosensitizers oxide semiconductor (DSCs) have attracted great attention since the pioneering work of Grätzel and collaborators (O'Regan & Gratzel, 1991; Grätzel, 2005). The most efficient sensitizers for wide band gap semiconductors are the well-known metallo-organic ruthenium complexes (Grätzel & O'Regan, 1991). Certain Ru(II) complexes have shown to be excellent photosensitizers for TiO₂ in DSSCs, having gained the attention because of the high efficiencies achieved ($\eta \approx 11\%$) in converting sunlight into electricity (Nazeeruddin et al., 2005; Gao et al., 2008a, 2008b; Cao et al., 2009). In dye-sensitized solar cells, the conversion of visible light to electricity is achieved through the spectral sensitization of wide band gap semiconductors. Light is absorbed by the dye molecules, which are adsorbed on the surface of the semiconductor, thus inducing charge separation. Excitation of the dye molecules results in electron injection into the conduction band of the semiconductor. For electron injection to occur, the excited electrons must be at higher energy level than the semiconductor conduction band. An electrolyte of high ionic strength is also used in dye-sensitized solar cells to facilitate charge transfer across the device.

DSSCs have emerged as one of the most promising devices for sustainable photovoltaics due to their usually reduced cost, low environmental impact, and fair efficiency of conversion of solar energy into electricity (Grätzel, 2003; Polo et al., 2004; Brennaman et al., 2011).

Research in this field has been intense, given the growing worldwide demand for new energy sources (Kamat, 2007; Jacobson, 2009), either with focus on new materials and components or on cell assemblies for development of more efficient and environmentally friendly devices (Garcia et al., 2003; Prochazka et al., 2009; Zakeeruddin & Grätzel, 2009; Snaith, 2010). It is increasingly urgent the need to diversify energy matrices in order to rely on truly renewable energy sources, cleaner and environmentally friendly, if the goal is to build an ecologically sustainable society (Kamat, 2007; Herrero et al., 2011).

However, the high cost of dyes based on Ru (II), due to the low abundance of this metal and use restrictions from the environmental point of view are aspects that restricts its application on a large scale, which has stimulated efforts to use photosensitizing dyes with good features, safe and low cost (Hamann et al., 2008; Mishra et al 2009; Imahori et al., 2009).

Several simple organic dyes, and especially xanthene dyes (Eosin Y, Rose Bengal, etc.), yield efficiencies comparable to those achieved with ruthenium complexes, especially when used to sensitize ZnO films (Guillén et al., 2008; Plank et al., 2009; Pradhan et al., 2007). Organic dyes such as these are inexpensive (Kroon et al., 2007), can be easily recycled (Lee et al., 2006) and do not rely on the availability of precious metals such as ruthenium. They also have high extinction coefficients and their molecular structures contain adequate anchoring groups to be adsorbed onto the oxide surface. However, solar cells sensitized with such dyes tend to have low stability. The development and optimization of solar cells is of great interest, both commercially and scientifically. However, dye sensitized devices are still not

commercially available in large volumes. Disadvantages such as the low efficiency and stability of these cells pose a hindrance to their commercialization.

A considerable increase in conversion efficiency of components of solar radiation into electrical energy by other photosensitizing dyes has been achieved in recent years. Macrocyclic systems such as porphyrins, phthalocyanines and derivatives have been shown to be capable of application in solar cells (Lu et al., 2009a).

Special attention has been given to the electron recombination processes that limit the DSC efficiency (Wang et al., 2006; Peter, 2007a; Zhao et al., 2008). Experimental and theoretical studies have been carried out in order to better understand and control these processes (Kruger et al., 2003; Cameron & Peter, 2005; Peter, 2007b; Xia et al., 2007a), typical interface phenomena. Strategies have been proposed to prepare efficient blocking layers in DSCs by using different techniques, such as spray pyrolysis, sputtering or by immersion in oxide precursor solutions (Xia et al., 2007a; Xia et al., 2007b; Wang et al., 2003; Handa et al., 2007). For example, the application of a compact layer onto the FTO glass before the mesoporous oxide film can prevent electron recombination at the FTO/TiO₂ interface. This blocking layer physically avoids the contact between the electrolyte and the FTO surface, decreasing the occurrence of triiodine reduction by photoinjected electrons (Patrocínio et al., 2010; Lei et al., 2010). Efficient layer-by-layer (LbL) TiO₂ compact films is considered one of the most effective blocking layers to avoid recombination processes at FTO surface in DSCs (Patrocínio et al., 2009). Although not previously reported as blocking layers, LbL metal oxide films have been applied in several devices (Krogman et al., 2008; Srivastava & Kotov, 2008; Jia et al., 2008; Lu et al., 2009b), including DSCs (Tsuge et al., 2006; Agrios et al., 2006). Iha and coworkers have shown that an LbL film based on TiO₂ nanoparticles and sodium sulphonated polystyrene, PSS, applied onto the FTO substrate before the mesoporous TiO₂ layer improved the overall conversion efficiency of DSCs by 28% (Patrocínio et al., 2009). Other complementary effects of the compact LbL TiO₂ layer in DSCs and the role of the polyelectrolyte itself were still under investigation.

LbL films using polyelectrolytes with good thermal stability at the electrode sintering temperature (450° C), such as sodium sulphonated polystyrene and sulphonated lignin, SL, maintain the compact morphology, and act as effective contact and blocking layers in DSCs. TiO₂ LbL films with poly(acrylic acid) as a polyanion presented similar morphology to that exhibited by TiO₂/PSS and TiO₂/SL films before sintering (Patrocínio et al., 2010). The best performance so far achieved is through the use of the TiO₂/PSS compact layer that increases the overall efficiency of DSCs to 30%, from 5.6 to 7.3%. The LbL TiO₂/PSS film imposes a longer time for a charge exchange at the electrode surface decreasing the electron recombination. The TiO₂/SL films (23% improvement) can be a cost effective option if a commercial application is considered.

5. Organic synthesis mediated by heterogeneous photocatalysis

Despite the widespread use of titanium dioxide, modified or not, or even other semiconductors with photocatalytic activity in photodegradation and mineralization of organic matter (Agostiano et al., 2003; Mrowetz et al., 2004; Machado et al., 2008; Hoffmann et al., 2010; Gupta et al., 2011), and its other capabilities (Mrowetz et al., 2004; Zaleska, 2008a, 2008b), these semiconductors have been little explored in the synthesis of compounds of interest, although it is recognized that the photocatalytic synthesis should enable the

efficient production of chemicals through combined fotoredox reactions with significant advantages compared to other methods (Swaminathan & Krishnakumar, 2011).

Synthetic methods based on photocatalytic processes have been reported for the preparation of different organic substrates (Amano et al., 2006; Palmisano et al., 2007b; Denmark & Venkatraman, 2006; Hakki et al., 2009; Swaminathan & Selvam, 2011; Swaminathan & Krishnakumar, 2011). Although the production of chemicals of industrial interest using heterogeneous photocatalysis has been shown to be a viable process, there is still little research on the use of photocatalysis for this purpose, and about the performance of these photocatalytic processes (Kanai et al., 2001; Murata et al., 2003; Amano et al., 2006; Denmark & Venkatraman, 2006; Hakki et al., 2009; Swaminathan & Selvam, 2011; Swaminathan & Krishnakumar, 2011). Apparently, the reason for this is that, in general, these methods are not yet fully satisfactory with regard to operational simplicity, cost of reagents and performance.

The stimulus for research in this field is necessary so that new and viable methodologies can be established.

6. Conclusion

In this chapter we combined a fast literature review about the different applications of heterogeneous photocatalysis, involving environmental photocatalysis, Hydrogen production for power generation, solar energy conversion into electricity using dye/semiconductor oxide cells and organic synthesis, with some experimental results obtained in our research group.

7. Acknowledgement

To Conselho Nacional de Desenvolvimento Científico e Tecnológico (CNPq), Coordenação de Aperfeiçoamento de Pessoal de Nível Superior (CAPES) and Fundação de Amparo à Pesquisa do Estado de Minas Gerais (FAPEMIG), Brazilian agencies for research funding and grants, and to Deutsches Zentrum für Luft- und Raumfahrt/Köln (DLR) and Bundesministerium für Bildung und Forschung (BMBF), Germany, by the support and funding.

8. References

- Agostiano, A.; Cozzoli, P. D.; Comparelli, R.; Fanizza, E.; Curri, M. L. & Laub, D. (2004). Photocatalytic synthesis of silver nanoparticles stabilized by TiO₂ nanorods: A semiconductor/metal nanocomposite in homogeneous nonpolar solution. *Journal of the American Chemical Society*, Vol.126, No.12, (March 2004), pp. 3868-3879, ISSN 0002-7863
- Agostiano, A.; Curri, M. L.; Comparelli, R.; Cozzoli, P. D. & Mascolo G. (2003). Colloidal oxide nanoparticles for the photocatalytic degradation of organic dye. *Materials Science & Engineering C-Biomimetic and Supramolecular Systems*, Vol.23, No.1-2, (January 2003), pp. 285-289, ISSN 0928-4931
- Agrios, A. G.; Cesar, I.; Comte, P.; Nazeeruddin, M. K. & Grätzel, M. (2006). Nanostructured composite films for dye-sensitized solar cells by electrostatic layer-by-layer

- deposition. *Chemistry of Materials*, Vol.18, No.23, (November 2006), pp. 5395–5397, ISSN 0897-4756
- Albertazzi, S.; Basile, E.; Brandin, J.; Einvall, J.; Hulteberg, C.; Fornasari, G.; Rosetti, V.; Sanati, M.; Trifiro, F. & Vaccari, A. (2005). The technical feasibility of biomass gasification for hydrogen production. *Catalysis Today*, Vol.106, No.1-4, (October 2005), pp. 297-300, ISSN 0920-5861
- Amano, F.; Yamaguchi, T. & Tanaka, T. Photocatalytic Oxidation of Propylene with Molecular Oxygen over Highly Dispersed Titanium, Vanadium, and Chromium Oxides on Silica. *The Journal of Physical Chemistry B*, Vol.110, No.1, (January 2006), pp. 281-288, ISSN 1520-6106
- Amat, A. M.; Bernabeu, A.; Vercher, R. F.; Santos-Juanes, L.; Simon, P. J.; Lardin, C.; Martinez, M. A.; Vicente, J. A.; Gonzalez, R.; Llosa, C. & Arques, A. (2011). Solar photocatalysis as a tertiary treatment to remove emerging pollutants from wastewater treatment plant effluents. *Catalysis Today*, Vol.161, No.1, (March 2011), pp. 235-240, ISSN 0920-5861
- Andreozzi, R.; Caprio, V.; Insola, A. & Marotta, R. (1999). Advanced oxidation processes (AOP) for water purification and recovery. *Catalysis Today*, Vol.53, No.1, (October 1999), pp. 51-59, ISSN 0920-5861
- Argazzi, R.; Bignozzi, C. A.; Hasselmann, G. M. & Meyer, G. J. (1998). Efficient Light-to-Electrical Energy Conversion with Dithiocarbamate-Ruthenium Polypyridyl Sensitizers. *Inorganic Chemistry*, Vol. 37, No.18, (September 1998), pp. 4533-4537, ISSN 0020-1669
- Asbury, J. B.; Hao, E.; Wang, Y. Q.; Ghosh, H. N. & Lian, T. (2001). Ultrafast Electron Transfer Dynamics from Molecular Adsorbates to Semiconductor Nanocrystalline Thin Films. *Journal of Physical Chemistry B*, Vol. 105, No.20, (May 2001), pp. 4545-4557, ISSN 1089-5647
- Ashokkumar, M. (1998). An overview on semiconductor particulate systems for production of hydrogen. *International Journal of Hydrogen Energy*, Vol.23, No.6, (June 1998), pp. 427-438, ISSN 0360-3199
- Augugliaro, V.; Palmisano, G.; Pagliaro, M. & Palmisano, L. (2007). Photocatalysis: a promising route for 21st century organic chemistry. *Chemical Communications*, Vol.33, No.33, (April 2007), pp. 3425-3437, ISSN 1359-7345
- Bao, N. Z.; Shen, L. M.; Takata, T. & Domen, K. (2008). Self-templated synthesis of nanoporous CdS nanostructures for highly efficient photocatalytic hydrogen production under visible light. *Chemistry of Materials*, Vol.20, No.1, (January 2008), pp. 110-117, ISSN 0897-4756
- Bartha, B.; Huber, C.; Harpaintner, R. & Schroder, P. (2010). Effects of acetaminophen in *Brassica juncea* L. Czern.: investigation of uptake, translocation, detoxification, and the induced defense pathways. *Environmental Science and Pollution Research*, Vol.17, No.9, (November 2010), pp. 1553-1562, ISSN 0944-1344
- Batista, P. S. (2010). *Síntese e caracterização de novos fotocatalisadores de dióxido de titânio*. D.Sc. Thesis. Instituto de Química, Universidade Federal de Uberlândia, Uberlândia - MG, Brazil
- Batista, P. S.; Santos, M. R. C.; de Souza, D. R.; Oliveira, D. F. M.; França, M. D.; Müller Jr, P. S. & Machado, A. E. H. (2011). Synthesis, characterization and photocatalytic activity of composites of TiO₂ and Zinc Phthalocyanine. X Brazilian Materials

- Research Society Meeting. Symposium F: Nanostructured Functional Materials for Advanced Energy and Environmental Applications. Gramado, RS, Brazil. September, 2011
- Benkő, G.; Kallioinen, J.; Tommola, J. E. I. K.; Yarstev, A. P. & Sundstrom, V. J. (2002). Photoinduced Ultrafast Dye-to-Semiconductor Electron Injection from Nonthermalized and Thermalized Donor States. *Journal of the American Chemical Society*, Vol.124, No.3, (January 2002), pp. 489-493, ISSN 1520-5126
- Biol, F. (2008). *World Energy Outlook* London, UK: International Energy Agency (IEA)
- Brabec, C. J.; Cravino, A.; Meissner, D.; Sariciftci, N. S.; Fromherz, T.; Rispen, M. T.; Sanchez, L. & Hummelen, J. C. (2001). Origin of the open circuit voltage of plastic solar cells. *Advanced Functional Materials*, Vol.11, No.5, (October 2001), pp. 374-380, ISSN 1616-301X
- Bound, J. P. & Voulvoulis, N. Pharmaceuticals in the aquatic environment a comparison of risk assessment strategies. *Chemosphere*, Vol.56, No.11, (September 2004), pp. 1143-1155, ISSN 0045-6535
- Brennaman, M. K.; Patrocinio, A. O. T.; Song, W.; Jurss, J. W.; Concepcion, J. J.; Hoertz, P. G.; Traub, M. C.; Murakami Iha, N. Y. & Meyer, T. J. (2011). Interfacial Electron Transfer Dynamics Following Laser Flash Photolysis of $[\text{Ru}(\text{bpy})_2((4,4'\text{-PO}_3\text{H}_2)_2\text{bpy})]^{2+}$ in TiO_2 Nanoparticle Films in Aqueous Environments, *ChemSusChem*, Vol.4, No.2, (February 2011), pp. 216 - 227, ISSN 1864-5631
- Cameron, P. J. & Peter, L. M. (2005). How Does Back-Reaction at the Conducting Glass Substrate Influence the Dynamic Photovoltage Response of Nanocrystalline Dye-Sensitized Solar Cells? (2005), Vol.109, No.15, (March 2005), pp. 7392-7398, ISSN 1864-5631
- Cao, Y. M.; Bai, Y.; Yu, Q. J.; Cheng, Y. M.; Liu, S.; Shi, D.; Gao, F.F. & Wang, P. (2009). Dye-Sensitized Solar Cells with a High Absorptivity Ruthenium Sensitizer Featuring a 2-(Hexylthio)thiophene Conjugated Bipyridine. *Journal of Physical Chemistry C*, Vol.113, No.15, (March 2009), pp. 6290-6297, ISSN 1932-7447
- Carp, O.; Huisman, C. L. & Reller, A. (2004). Photoinduced reactivity of titanium dioxide. *Progress in Solid State Chemistry*, Vol.32, No.1-2, (November 2004), pp. 33-177, ISSN 0079-6786
- Cavalheiro, A. A.; Bruno, J. C.; Saeki, M. J.; Valente, J. P. S. & Florentino, A. O. (2008). Effect of scandium on the structural and photocatalytic properties of titanium dioxide thin films. *Journal of Materials Science*, Vol.43, No.2, (January 2008), pp. 602-608, ISSN 0022-2461
- Chand, S. & Bala, S. (2007). Simulation studies of current transport in metal-insulator-semiconductor Schottky barrier diodes. *Physica B-Condensed Matter*, Vol.390, No.1-2, (March 2007), pp. 179-184, ISSN 0921-4526
- Chen, C.; Qi, X. & Zhou, B. (1997). Photosensitization of colloidal TiO_2 with a cyanine dye. *Journal of Photochemistry and Photobiology A: Chemistry*, Vol. 109, No.2, (September 1997), pp. 155-158, ISSN 1010-6030
- Chen, Z.; Zhong, C.; Zhang, Z.; Li, Z.; Niu, L.; Bin, Y. & Zhang, F. (2008a). Photoresponsive J-Aggregation Behavior of a Novel Azobenzene-Phthalocyanine Dyad and Its Third-Order Optical Nonlinearity. *The Journal of Physical Chemistry B*, Vol. 112, No. 25, (June 2008), pp. 7387-7394, ISSN 1520-5207

- Chen, C. Z.; Shi, J. Z.; Yu, H. J. & Zhang, S. J. (2008b). Application of magnetron sputtering for producing bioactive ceramic coatings on implant materials. *Bulletin of Materials Science*, Vol.31, No.6, (November 2008), pp. 877-884, ISSN 0250-4707
- Corcoran, E.; Nellesmann, C.; Baker, E.; Bos, R.; Osborn, D. & Savelli, H. (eds). 2010. *Sick Water? The central role of wastewater management in sustainable development*. A Rapid Response Assessment. United Nations Environment Programme, UN-HABITAT, GRID-Arendal. www.grida.no, ISBN: 978-82-7701-075-5, Norway
- Daughton, C. G. & Ternes, T. A. (1999). Pharmaceuticals and personal care products in the environment: agents of subtle change. *Environmental Health Perspectives*, Vol.107, No.6, (December, 1999), pp. 907-942, ISSN 0091-6765
- Denmark, S. E. & Venkatraman, S. (2006). On the mechanism of the Skraup-Doebner-Von Miller quinoline synthesis. *Journal of Organic Chemistry*, Vol.71, No.4, (February 2006), pp. 1668-1676, ISSN 0022-3263
- Diebold, U. (2003). The surface science of titanium dioxide surface. *Surface Science Reports*, Vol.48, No. 5-8, (January 2003), pp. 53 - 229, ISSN 0167-5729
- Duarte, E. T. F. M., Xavier, T. P., De Souza, D. R., De Miranda, J. A., Machado, A. E. D., Jung, C., De Oliveira, L. & Sattler C. (2005). Construção e estudos de performance de um reator fotoquímico tipo CPC ("Compound Parabolic Concentrator). *Química Nova*, Vol.28, No.5, (Junho 2005), pp. 921-926, ISSN 0100-4042
- Eguchi, K.; Fujii, H., Inata, K.; Ohtaki, M. & Arai, H. (2001). Synthesis of TiO₂/CdS nanocomposite via TiO₂ coating on CdS nanoparticles by compartmentalized hydrolysis of Ti alkoxide. *Journal of Materials Science*, Vol.36, No.2 (January 2001), pp.527-532, ISSN 0022-2461
- Eisfeld, A. & Briggs J.S. (2006). The J- and H- bands of organic dye aggregates. *Chemical Physics*, Vol. 324, No. 2-3, (May 2006), pp. 376-384, ISSN 0301-0104
- FDA, Compliance Program Guidance Manual, p. 10,
<http://www.fda.gov/downloads/Food/GuidanceComplianceRegulatoryInformation/ComplianceEnforcement/ucm073305.pdf>
- Fidder, H.; Knoester, J. & Wiersma, D. A. (1991). Optical properties of disordered molecular aggregates: A numerical study. *Journal of Chemical Physics*, Vol.95, No.11 (December 1991), pp. 7880-7891, ISSN 0021-9606
- França, M. D. (2011). *Degradação de paracetamol empregando Tecnologia Oxidativa Avançada baseada em fotocatalise heterogênea, usando irradiação artificial e solar*. M.Sc. Dissertation. Universidade Federal de Uberlândia. Uberlândia, MG, Brazil
- Fu, X.; Long, J.; Wang, X.; Leung, D. Y. C.; Ding, Z.; Wu, L.; Zhang, Z.; Li, Z. & Fu, X. (2008). Photocatalytic reforming of biomass: A systematic study of hydrogen evolution from glucose solution. *International Journal of Hydrogen Energy*, Vol. 33, No. 22, (November 2008), pp. 6484-6491, ISSN 0360-3199
- Fujishima, A. & Honda K. (1971). Electrochemical evidence for mechanism of the primary stage of photosynthesis. *Bulletin of the Chemical Society of Japan*, Vol.44, No. 4, (April 1971), pp. 1148-1150, ISSN 1348-0634
- Fujishima, A. & Honda, K. (1972). Electrochemical Photolysis of Water at a Semiconductor Electrode. *Nature*, Vol.238, No.5358, (July 1972), pp. 37-38, ISSN 0028-836
- Fujishima, A.; Zhang, X. & Tryk, D. A. (2007). Heterogeneous photocatalysis: From water photolysis to applications in environmental cleanup. *International Journal of Hydrogen Energy*, Vol.32, No.14, (September 2007), pp. 2664-2672, ISSN 0360-3199

- Furube, A.; Asahi, T.; Masuhara, H.; Yamashita, H. & Anpo, M. (2001). Direct observation of a picosecond charge separation process in photoexcited platinum-loaded TiO₂ particles by femtosecond diffuse reflectance spectroscopy. *Chemical Physics Letters*, Vol.336, No.5-6, (September 2000), pp. 424-430, ISSN 0009-2614
- Gao, F.; Wang, Y.; Shi, D.; Zhang, J.; Wang, M. K.; Jing, X. Y.; Humphry-Baker, R.; Wang, P., Zakeeruddin, S. M. & Grätzel, M. (2008a). Enhance the optical absorptivity of nanocrystalline TiO₂ film with high molar extinction coefficient ruthenium sensitizers for high performance dye-sensitized solar cells. *Journal of the American Chemical Society*, Vol.130, No.32, (July 2008), pp. 10720-10728, ISSN 0002-7863
- Gao, F.; Wang, Y.; Zhang, J.; Shi, D.; Wang, M.; Humphry-Baker, R.; Wang, P.; Zakeeruddin, S. & Grätzel, M. (2008b). A new heteroleptic ruthenium sensitizer enhances the absorptivity of mesoporous titania film for a high efficiency dye-sensitized solar cell. *Chemical Communications*, Vol.23, No.23, (June 2008), pp. 2635-2637, ISSN 1359-7345
- Garcia, C. G.; Polo, A. S. & Iha, N. Y. M. (2003). Fruit extracts and ruthenium polypyridinic dyes for sensitization of TiO₂ in photoelectrochemical solar cells. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.160, No.1-2, (August 2003), pp. 87-91, ISSN 1010-6030
- Grätzel, M. & O'Regan, B. (1991). A Low-Cost, High-Efficiency Solar-Cell Based on Dye-Sensitized Colloidal TiO₂ Films. *Nature*, Vol.353, No.6346, (October 1991), pp. 737-740, ISSN 0028-0836
- Grätzel, M. (2001). Photoelectrochemical cells. *Nature*, Vol.414, No.6861, pp. 338-344, ISSN 0028-0836
- Grätzel, M. (2003). Dye-sensitized solar cells. *Journal of Photochemistry and Photobiology C-Photochemistry Reviews*, Vol.4, No.2, (October 2003), pp. 145-153, ISSN 1389-5567
- Grätzel, M. (2005). Solar energy conversion by dye-sensitized photovoltaic cells. *Inorganic Chemistry*, Vol.44, No.20, (October 2005), pp. 6841-6851, ISSN 0020-1669
- Guillén, E.; Casanueva, F.; Anta, J.; Vega-Poot, A.; Oskam, G.; Alcántara, R.; Fernández-Lorenzo, C. & Martín-Calleja, J. (2008). Photovoltaic performance of nanostructured zinc oxide sensitised with xanthenes dyes. *Journal of Photochemistry and Photobiology A: Chemistry*, Vol.200, No.2-3, (September 2008), pp. 364-370, ISSN 1010-6030
- Gupta, V. K.; Jain, R.; Nayak, A.; Agarwal, S. & Shrivastava, M. (2011). Removal of the hazardous dye-Tartrazine by photodegradation on titanium dioxide surface. *Materials Science & Engineering C-Materials for Biological Applications*, Vol.31, No.5, (July 2011), pp. 1062-1067, ISSN 0928-4931
- Hagfeldt, A. & Grätzel, M. (1995). Light-Induced redox reactions in nanocrystalline systems. *Chemical Reviews*, Vol.95, No.1, (January 1995), pp. 49-68, ISSN 0928-4931
- Hagfeldt, A. & Grätzel, M. (2000). Molecular photovoltaics. *Accounts of Chemical Research*, Vol.33, No.5, (May 2000), pp. 269-277, ISSN 0001-4842
- Hakki, A.; Dillert, R. & Bahnemann, D. (2009). Photocatalytic conversion of nitroaromatic compounds in the presence of TiO₂. *Catalysis Today*, Vol.144, No.1-2, (June 2009), pp. 154-159, ISSN 0920-5861
- Hamann, T. W.; Jensen, R. A.; Martinson, A. B. F.; Ryswyk, H. V. & Hupp, J. T. (2008). Advancing beyond current generation dye-sensitized solar cells. *Energy & Environmental Science*, Vol.1, No.1, (June 2008), pp. 66-78, ISSN 1754-5692

- Hanaor, D. A. H. & Sorrell C. C. (2011). Review of the anatase to rutile phase transformation. *Journal of Materials Science*, Vol.46, No.4, (February 2011), pp. 855-874, ISSN 0022-2461
- Handa, S.; Haque, S. A. & Durrant, J. R. (2007). Saccharide Blocking Layers in Solid State Dye Sensitized Solar Cells. *Advanced Functional Materials*, Vol.17, No.15, (October 2007), pp. 2878-2883, ISSN 1616-3028
- Hao, Y.; Yang, M.; Yu, C.; Cai, S.; Liu, M.; Fan, L. & Li, Y. (1998). Photoelectrochemical studies on acid-doped polyaniline as sensitizer for TiO₂ nanoporous film. *Solar Energy Materials & Solar Cells*, Vol.56, No.1, (January 1998), pp. 75-84, ISSN 0927-0248
- Herrmann, J. M. & Guillard, C. (2002). New industrial titania photocatalysts for the solar detoxification of water containing various pollutants. *Applied Catalysis B: Environmental*, Vol.35, No.4, (January 2002), pp. 281-294, ISSN 0926-3373
- Herrero, C.; Quaranta, A.; Leibl, W.; Rutherford, A. W. & Aukauloo, A. (2011). Artificial photosynthetic systems. Using light and water to provide electrons and protons for the synthesis of a fuel. *Energy & Environmental Science*, Vol.4, No.7, (February 2011), pp. 2353-2365, ISSN 1754-5692
- Hoffmann, M. R.; Martin, T.; Choi W. & Bahnemann, D. W. (1995). Environmental applications of semiconductor photocatalysis. *Chemical Reviews*, Vol.95, No.1, (January 1995), pp. 69-96, ISSN 1520-6890
- Hoffmann, M. (2000). Frenkel and charge-transfer excitons in quasi-one-dimensional molecular crystals with strong intermolecular overlap. in Doktor der Naturwissenschaften Dissertation; Technischen Universität Dresden, 2000
- Hoffmann, M. R.; Choi J. & Park, H. (2010). Effects of Single Metal-Ion Doping on the Visible-Light Photoreactivity of TiO₂. *Journal of Physical Chemistry C*, Vol.114, No.2, (December 2010), pp. 783-792, ISSN 1932-7455
- Huang, S.; Guo, X.; Huang, X.; Zhang, Q.; Sun, H.; Li, D.; Luo, Y. & Meng, Q. (2011). Highly efficient fibrous dye-sensitized solar cells based on TiO₂ nanotube arrays. *Nanotechnology*, Vol.22, No.31, (July 2011), pp. 315401- 315407, ISSN 1361-6528
- Hwang, D. W.; Kim H. G.; Jang, J. S.; Bae, S. W.; Ji, S. M. & Lee, J. S. (2004). Photocatalytic decomposition of water-methanol solution over metal-doped layered perovskites under visible light irradiation. *Catalysis Today*, Vol.93-95, (September 2004), pp. 845-850, ISSN 0920-5861
- Iliev, V.; Tomova, D.; Bilyarska, L.; Prahov, L. & Petrov, L. (2003). Phthalocyanine modified TiO₂ or WO₃-catalysts for photooxidation of sulfide and thiosulfate ions upon irradiation with visible light. *Journal of Photochemistry and Photobiology, A: Chemistry*, Vol.159, (July 2003), No. 3, pp. 281-287, ISSN 1010-6030
- Imahori H.; Umeyama T. & Ito S. (2009). Large pi-Aromatic Molecules as Potential Sensitizers for Highly Efficient Dye-Sensitized Solar Cells. *Accounts of Chemical Research*, Vol.42, No.11, (November 2009), pp. 1809-1818, ISSN 1520-4928
- Imhof, A. & Pine, D. J. (1997). Ordered macroporous materials by emulsion templating. *Nature*, Vol.389, No.6654, (October 1997), pp. 948-951, ISSN 0028-0836
- Ino, D.; Watanabe, K.; Takagi, N. & Matsumoto, Y. (2005). Electron Transfer Dynamics from Organic Adsorbate to a Semiconductor Surface: Zinc Phthalocyanine on TiO₂(110), *The Journal of Physical Chemistry B*, Vol.109, No.38, (June 2005), pp. 18018-18024, ISSN 1520-5207

- Ismail, A. F.; Bolong, N.; Salim, M. R. & Matsuura, T. (2009). A review of the effects of emerging contaminants in wastewater and options for their removal. *Desalination*, Vol.239, No.1-3, (March 2009), pp. 229-246, ISSN 0011-9164
- Iwaszuk, A. & Nolan, M. (2011). Charge compensation in trivalent cation doped bulk rutile TiO₂. *Journal of Physics: Condensed Matter*, Vol.23, No.334307,(August 2009), pp. 1-11, ISSN 0953-8984
- Jacobson, M. Z. (2009). Review of solutions to global warming, air pollution, and energy security. *Energy & Environmental Science*, Vol.2, No.2, (December 2008), pp. 148-173, ISSN 1754-5692
- Jayaweera, P. V. V.; Perera, A. G. U. & Tennakone, K. (2008). Why Gratzel's cell works so well. *Inorganica Chimica Acta*, Vol. 361, No.3, (February 2008), pp. 707-711, ISSN 0020-1693
- Jia, Y.; Han, W.; Xiong, G. & Yang, W. (2008). Layer-by-layer assembly of TiO₂ colloids onto diatomite to build hierarchical porous materials, *Journal of Colloid and Interface Science*, Vol.323, No.2, (April 2008), pp. 326-331, ISSN 1095-7103
- Jin, B.; Chong, M. N.; Chow, C. W. K. & Saint, C. (2010). Recent developments in photocatalytic water treatment technology: A review. *Water Research*, Vol. 44, No.10, (February 2010), pp. 2997-3027, ISSN 0043-1354
- Jing, D., Guo, L., Zhao, L., Zhang, X., Liu, H., Li, M., Shen, S., Liu, G., Hu, X., Zhang, X., Zhang, K., Ma, L. & Guo, P. (2010). Efficient solar hydrogen production by photocatalytic water splitting: From fundamental study to pilot demonstration, *International Journal of Hydrogen Energy*, Vol.35, No.13, (July 2010), pp. 7087-7097, ISSN 0360-3199
- Jirka, A. M. & Carter, M. J. (1975). Micro semi-automated analysis of surface and wastewaters for chemical oxygen demand. *Analytical Chemistry*, Vol.47, No.8, (July 1975), pp. 1397-1402, ISSN 0003-2700
- Jones, O. A. H.; Voulvoulis, N. & Lester, J. N. Aquatic environmental assessment of the top 25 English prescription pharmaceuticals. *Water Research*, Vol.36, No.20, (December 2007), pp. 5013-5022, ISSN 0043-1354
- Kamat, P.V. (2007). Meeting the Clean Energy Demand: Nanostructure Architectures for Solar Energy Conversion. *The Journal of Physical Chemistry C*, Vol. 111, (February 2007), No. 7, pp. 2834 - 2860, ISSN 1932-7455
- Kanai, H.; Shono, M.; Hamada, K. & Imamura, S. (2001). Photooxidation of propylene with oxygen over TiO₂-SiO₂ composite oxides prepared by rapid hydrolysis. *Journal of Molecular Catalysis A:Chem*, Vol.172, No.1-2, (July 2001), pp. 25-31, ISSN 1381-1169
- Khataee, A. R.; Zarei, M. & Ordikhani-Seyedlar, R. (2011). Heterogeneous photocatalysis of a dye solution using supported TiO₂ nanoparticles combined with homogeneous photoelectrochemical process: Molecular degradation products. *Journal of Molecular Catalysis a-Chemical*, Vol.338, No.1-2, (March 2011), pp. 84-91, ISSN 1381-1169
- Kim, O.-K., Je, J., Jernigan, G., Buckley, L. & Whitten, D. (2006). Super-helix formation induced by cyanine J-aggregates onto random-coil carboxymethyl amylose as template. *Journal of the American Chemical Society*, Vol.128, No.2, (January 2006), pp. 510-516, ISSN 0002-7863
- Kim, J. & Choi, W. (2010). Hydrogen producing water treatment through solar photocatalysis. *Energy & Environmental Science*, Vol.3, No.8, (May 2010), pp. 1042-1045, ISSN 1754-5692

- Kippelen, B. & Bredas, J. L. (2009). Organic photovoltaics. *Energy & Environmental Science*, Vol.2, No.3, (December 2009), pp. 251-261, ISSN 1754-5692
- Koca, A. & Sahin M. (2002). Photocatalytic hydrogen production by direct sun light from sulfide/sulfite solution. *International Journal of Hydrogen Energy*, Vol.27, No.4, (April 2002), pp. 363-367, ISSN 0360-3199
- Köhler, J. & Schmid, D. (1996). Frenkel excitons in NaNO₂: excitation energy transfer and exciton coherence. *Journal of Physics: Condensed Matter*, Vol. 8, No. 2, (January 1996), pp. 115-141, ISSN 1361-648X
- Krogman, K. C.; Zacharia, N. S.; Grillo, D. M. & Hammond, P. T. (2008). Photocatalytic layer-by-layer coatings for degradation of acutely toxic agents. *Chemistry of Materials*, Vol.20, No.5, (March 2008), pp. 1924-1930, ISSN 0897-4756
- Kroon, J.; Bakker, N.; Smit, H.; Liska, P.; Thampi, K.; Wang, P.; Zakeerudin, S.; Grätzel, M.; Hinsch, A.; Hore, S.; Würfel, U.; Sastrawan, R.; Durrant, J.; Palomares, E.; Pettersson, H.; Gruszecki, T.; Walter, J.; Skupien, K. & Tulloch, G. (2007). Nanocrystalline dye-sensitized solar cells having maximum performance. *Progress in Photovoltaics*, Vol.15, No.1,(January 2007), pp. 1-18, ISSN 1062-7995
- Krüger, J.; Bach, U. & Grätzel, M. (2001). High efficiency solid-state photovoltaic device due to inhibition of interface charge recombination. *Applied Physics Letters*, Vol.79, No.13, (September 2001), pp. 2085-2087, ISSN 0003-6951
- Krüger, J.; Plass, R.; Grätzel, M.; Cameron, P. J. & Peter, L. M. (2003). Charge transport and back reaction in solid-state dye-sensitized solar cells: A study using intensity-modulated photovoltage and photocurrent spectroscopy. *The Journal of Physical Chemistry B*, Vol.107, No.31, (August 2003), pp. 7536-7539, ISSN 1520-6106
- Kudo, A. (2006). Development of photocatalyst materials for water splitting. *International Journal of Hydrogen Energy*, Vol.31, No.2, (February,2006), pp. 197-202, ISSN 0360-3199
- Kumar, S. G. & Devi, L. G. (2011). A review on modified TiO₂ photocatalysis under VU/visible light: selected results and related mechanisms on interfacial charge carrier transfer dynamics. *The Journal of Physical Chemistry A*. DOI: 10.1021/jp204364a, ISSN 1089-5639
- Labat, F.; Baranek, P. & Adamo, C (2008). Structural and electronic properties of selected rutile and anatase TiO₂ surfaces: An ab initio investigation. *Journal of Chemical Theory and Computation*, Vol.4, No.2, (February 2008), pp. 341- 352, ISSN 1549-9618
- Lee, W.; Okada, H.; Wakahara, A. & Yoshida, A. (2006). Structural and photoelectrochemical characteristics of nanocrystalline ZnO electrode with Eosin-Y. *Ceramics International*, Vol. 32, No. 5, (March 2006), pp. 495-498, ISSN 0272-8842
- Lei, B. X.; Liao, J. Y.; Zhang, R.; Wang, J.; Su, C. Y. & Kuang, D. B. (2010). Ordered Crystalline TiO₂ Nanotube Arrays on Transparent FTO Glass for Efficient Dye-Sensitized Solar Cells. *The Journal of Physical Chemistry C*, Vol. 114, No.35, (December 2010), pp. 15228-15233, ISSN 1932-7455
- Leznoff, C. C. & Lever, A. B. P. (1990). Phthalocyanines: Properties and Applications, VCH Publishers, ISBN 978-0-471-18720-2, New York, United States
- Li, J.; Liu, Y.; Chen, X. & Burda, C. (2005). Photocatalytic degradation of azo dyes by nitrogen-doped TiO₂ nanocatalysts. *Chemosphere*, Vol.61, No.1, (March 2005), pp. 11-18, ISSN 0045-6535

- Li, J.; Wang, C.; Yang, G. M.; Mele, G.; Slota, A R.; Broda, M. A.; Duan, M. Y.; Vasapollo, G.; Zhang, X. & Zhang, F. X. (2009). Novel meso-substituted porphyrins: Synthesis, characterization and photocatalytic activity of their TiO₂-based composites. *Dyes and Pigments*, Vol.80, No.3, (March 2009), pp. 321-328, ISSN 0143-7208
- Linsebigler, A. L; Lu, G. Q. & Yates, J. T. (1995). Photocatalysis on TiO₂ surfaces: principles, mechanisms, and selected results. *Chemical Reviews*, Vol.95, No.3, (May 1995), pp. 735-758, ISSN 0009-2665
- Liu, H.; Yuan, J. & Shangguan, W. F. (2006). Photochemical reduction and oxidation of water including sacrificial reagents and Pt/TiO₂ catalyst. *Energy & Fuels*, Vol.20, No.6, (November 2006), pp. 2289-2292. ISSN 1520-5029
- Long, R.; Dai, Y.; Meng, G. & Huang, B. B. (2009). Energetic and electronic properties of X- (Si, Ge, Sn, Pb) doped TiO₂ from first-principle. *Physical Chemistry Chemical Physics*, Vol. 11, No. 37, (June 2009), pp. 8165-817, ISSN 1463-9076
- Long, R. & English, N. J. (2011). Band gap engineering of double-cation-impurity-doped anatase-titania for visible-light photocatalysts: a hybrid density functional theory approach. *Physical Chemistry Chemical Physics*, Vol. 13, No. 30, (June 2011), pp. 13698-13703, ISSN 1463-9076
- Lu, H. P.; Mai, C. L.; Tsia, C. Y.; Hsu, S. J.; Hsieh C. P.; Chiu C. L.; Yeh C. Y. & Diau, E. W. G. (2009a). Design and characterization of highly efficient porphyrin sensitizers for green see-through dye-sensitized solar cells. *Physical Chemistry Chemical Physics*, Vol.11, No.44, (September 2009), pp. 10270-10274, ISSN 1463-9076.
- Lu, Y.; Lee, W. H.; Lee, H. S.; Jang, Y. & Cho, K. (2009b). Low-voltage organic transistors with titanium oxide/polystyrene bilayer dielectrics. *Applied Physics Letters*, Vol.94, No.11, (March 2009), pp. 1133031-1133033, ISSN 0003-6951
- Luo, H. M.; Takata, T.; Lee, Y. G.; Zhao, J. F., Domen, K. & Yan, Y. S. Photocatalytic activity enhancing for titanium dioxide by co-doping with bromine and chlorine. *Chemistry of Materials*, Vol.16, No.5, (March 2004), pp. 846-849, ISSN 0897-4756
- Machado, A. E. H.; de Miranda, J. A.; de Freitas, R. F.; Duarte, E. T. F. M.; Ferreira, L. F.; Albuquerque, Y. D. T.; Ruggiero, R.; Sattler, C. & de Oliveira, L. (2003a). Destruction of the organic matter present in effluent from a cellulose and paper industry using photocatalysis. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.155, No.1-3, (February 2003), pp. 231-241, ISSN 1010-6030.
- Machado, A. E. H.; Miranda, J. A.; Sattler, C. & Oliveira, L. (2003b). Compósitos de ftalocianina de zinco e óxido de titânio, para emprego em processos fotocatalíticos e método para sua obtenção. Brazilian Patent, PI 03009203-3 A2, 2003.
- Machado, A. E. H.; Xavier, T. P.; de Souza, D. R.; de Miranda, J. A.; Duarte, E. T. F. M.; Ruggiero, R.; de Oliveira, L. & Sattler, C. (2004). Solar photo-Fenton treatment of chip board production waste water. *Solar Energy*, Vol.77, No.5, (March 2004), pp. 583-589, ISSN 0038-092X.
- Machado, A. E. H.; França, M. D.; Velani, V.; Magnino, G. A.; Velani, H. M. M.; Freitas, F. S.; Muller, P. S.; Sattler, C. & Schmucker, A. (2008). Characterization and evaluation of the efficiency of TiO₂/zinc phthalocyanine nanocomposites as photocatalysts for wastewater treatment using solar irradiation. *International Journal of Photoenergy*, Vol.2008, (March 2008), pp. 1-12, ISSN 1687-529X.

- Machado, A. E. H., Menezes da Silva, V. H. & Ueno, L. T. (2011a). "Formation of Frenkel's J aggregates from zinc phthalocyanine: a m06 approach". XVI Simpósio Brasileiro de Química Teórica. (November 2011). Ouro Preto, MG, Brazil
- Machado, A. E. H., França, M. D., Müller Jr, P. S., Borges, K.A. & dos Santos, L.M. (2011b). Synthesis of new photocatalysts based on TiO₂. Unpublished results.
- Maeda, K.; Teramura, K.; Lu, D. L.; Takata, T.; Saito, N.; Inoue, Y. & Domen, K. (2006). Photocatalyst releasing hydrogen from water. *Nature*, Vol.440, No.7082, (March 2006), pp. 295-295, ISSN 0028-0836
- Maeda, K. & Domen, K. (2007). New non-oxide photocatalysts designed for overall water splitting under visible light. *Journal of Physical Chemistry C*, Vol.111, No.22, (June 2007), pp. 7851-7861, ISSN 1932-7447
- Malato, S.; Blanco, J.; Richter, C.; Curcó, D. & Giménez, J. (1997). Low-concentrating CPC collectors for photocatalytic water detoxification: comparison with a medium concentrating solar collector. *Water Science and Technology*, Vol.35, No.4, (January 1997), pp. 157-164, ISSN 0273-1223
- Malato, S.; Blanco, J.; Vidal, A. & Richter, C. (2002). Photocatalysis with solar energy at a pilot-plant scale: an overview. *Applied Catalysis B*, Vol.37, No.1, (April 2002), pp. 1-15, ISSN 0926-3373
- Martin, S. T.; Lee, A. T. & Hoffmann M. R. (1995). Chemical Mechanism of Inorganic Oxidants in the TiO₂/Uv Process - Increased Rates of Degradation of Chlorinated Hydrocarbons. *Environmental Science & Technology*, Vol.29, No.10, (October 1995), pp. 2567-2573, ISSN 0013-936X
- Meissner, D. & Rostalski, J. (2001). "Photovoltaics of interconnected networks," *Synthetic Metals*, Vol.121, No.1-3, (March 2001), pp. 1551-1552, ISSN 0379-6776
- Melo, M. D. & Silva L. A. (2011). Photocatalytic Production of Hydrogen: an Innovative Use for Biomass Derivatives. *Journal of the Brazilian Chemical Society*, Vol.22, No.8, (August 2011), pp. 1399-1406, ISSN 0103-5053
- Mi, J.; Guo, L.; Liu, Y.; Liu, W.; You, G. & Qian, S. (2003). Excited-state dynamics of magnesium phthalocyanine thin film. *Physics Letters A*, Vol.310, No.5-6, (April 2003), pp. 486-492, ISSN 0375-9601
- Mills A.; Elliott N.; Parkin I. P.; O'Neill S. A. & Clark R. J. H. (2002). Novel TiO₂ CVD films for semiconductor photocatalysis. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.151, No.1-3, (August 2002), pp. 171-179, ISSN 1010-6030
- Mills A. & Hunte S. L. (1997). An overview of semiconductor photocatalysis. *Journal of Photochemistry and Photobiology A:Chemistry*, Vol.108, No.1, (July 1997), pp. 1-35, ISSN 1010-6030
- Miranda, J. A.; Machado, A. E. H. & Oliveira, C. A. (2002). Comparison of the photodynamic action of methylene blue and zinc phthalocyanine on TG-180 tumoral cells. *Journal of Porphyrins and Phthalocyanines*, Vol. 6, No. 1, (2002), pp. 43-49, ISSN 1088-4246
- Mishra A.; Bauerle P. & Fischer M. K. R. (2009). Metal-Free Organic Dyes for Dye-Sensitized Solar Cells: From Structure: Property Relationships to Design Rules. *Angewandte Chemie-International Edition*, Vol.48, No.14, (March 2009), pp. 2474-2499, ISSN 1422-0067
- Mrowetz, M.; Balcerski, W.; Colussi, A. J. & Hoffmann, M. R. (2004). Oxidative power of nitrogen-doped TiO₂ photocatalysts under visible illumination. *Journal of Physical Chemistry B*, Vol.108, No.45, (October 2004), pp. 17269-17273, ISSN 1520-6106

- Murata, C.; Yoshida, H.; Kumagai, J. & Hattori, T. (2003). Active sites and active oxygen species for photocatalytic epoxidation of propene by molecular oxygen over TiO₂-SiO₂ binary oxides. *The Journal of Physical Chemistry B*, Vol.107, No.18, (May 2003), pp. 4364-4373, ISSN 1520-6106
- Nazeeruddin, M. K.; Kay, A.; Rodicio, I.; Humphry-Baker, R.; Müller, E.; Liska, P.; Vlachopoulos, N. & Grätzel, M. (1993). Conversion of light to electricity by cis-X₂bis(2,2'-bipyridyl-4,4'-dicarboxylate)ruthenium(II) charge-transfer sensitizers (X = Cl-, Br-, I-, CN-, and SCN-) on nanocrystalline titanium dioxide electrodes. *Journal of the American Chemical Society*, Vol.115, No. 14, (July 1993), pp. 6382-6390, ISSN 0002-7863
- Nazeeruddin, M. K.; Angelis, F. D.; Fantacci, S.; Selloni, A.; Viscardi, G.; Liska, P.; Ito, S.; Takeru, B. & Grätzel, M. (2005). Combined experimental and DFT-TDDFT computational study of photoelectrochemical cell ruthenium sensitizers. *Journal of the American Chemical Society*, Vol.127, No.48, (December 2005), pp. 16835-16847, ISSN 0002-7863
- Ni, M.; Leung, M. K. H.; Leung, D. Y. C. & Sumathy, K. (2007). A review and recent developments in photocatalytic water-splitting using TiO₂ for hydrogen production. *Renewable & Sustainable Energy Reviews*, Vol.11, No.3, (April 2007), pp. 401-425, ISSN 1364-0321
- Ni, J. R.; Xiong, L.; Sun, W. L.; Yang, Y. & Chen, C. (2011). Heterogeneous photocatalysis of methylene blue over titanate nanotubes: Effect of adsorption. *Journal of Colloid and Interface Science*, Vol.356, No.1, (April 2011), pp. 211-216, ISSN 0021-9797
- Nikolaou, A.; Meric, S. & Fatta, D.(2007) Occurrence patterns of pharmaceuticals in water and wastewater environments. *Analytical Bioanalytical Chemistry*, Vol.387, No.4, (February 2007), pp. 1225-1234, ISSN 1618-2642
- Nogueira R. F. P. & Jardim W. F. (1998). Fotocatálise heterogênea e sua aplicação ambiental. *Química Nova*, Vol.21, No.1, (July,1998), pp. 69-72, ISSN 0100-4042
- Ohno, T., Mitsui, T. & Matsumura, M. (2003). Photocatalytic activity of S-doped TiO₂ photocatalyst under visible light. *Chemistry Letters*, Vol.32, No.4, (April 2003), pp. 364-365, ISSN 0366-7022
- Oliveira, D. F. M.; Batista, P. S.; Muller Jr, P. S.; Velani, V.; França, M. D., de Souza, D. R. & Machado, A. E. H. (2012). Evaluating the effectiveness of photocatalysts based on titanium dioxide in the degradation of the dye Ponceau 4R. *Dyes and Pigments*, Vol. 92, No. 1, (January 2012), pp. 563-572, ISSN 0143-7208
- O'regan, B. & Gratzel, M. (1991). A Low-Cost, High-Efficiency Solar-Cell Based on Dye-Sensitized Colloidal TiO₂ Films. *Nature*, Vol.353, No.6346, (October 1991), pp. 737-740, ISSN 0028-0836
- Pagliari, M.; Konstandopoulos, A. G.; Ciriminna, R. & Palmisano, G. (2010). Solar hydrogen: fuel of the near future. *Energy & Environmental Science*, Vol.3, No.3, (January 2010), pp. 279-287, ISSN 1754-5706
- Palmisano, G.; Augugliaro, V.; Pagliaro, M. & Palmisano, L. (2007a). Photocatalysis: a promising route for 21st century organic chemistry. *Chemical Communications*, No.33, (April 2007), pp. 3425-3437, ISSN 1359-7345
- Palmisano, L.; Palmisano, G.; Yurdakal, S.; Augugliaro, V. & Loddo, V. (2007b). Photocatalytic selective oxidation of 4-methoxybenzyl alcohol to aldehyde in

- aqueous suspension of home-prepared titanium dioxide catalyst. *Advanced Synthesis & Catalysis*, Vol.349, No.6, (April 2007), pp. 964-970, ISSN 1615-4150
- Patrocínio, A. O. T.; Paterno, L. G. & Murakami Iha, N. Y. (2009). Layer-by-layer TiO₂ films as efficient blocking layers in dye-sensitized solar cells. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.205, No.1, (June 2009), pp. 23-27, ISSN 1010-6030
- Patrocínio, A. O. T.; Paterno, L. G. & Murakami Iha, N. Y. (2010). Role of Polyelectrolyte for Layer-by-Layer Compact TiO₂ Films in Efficiency Enhanced Dye-Sensitized Solar Cells. *The Journal of Physical Chemistry C*, Vol.114, No.41, (October 2010), pp. 17954-17959, ISSN 1932-7447
- Patsoura, A.; Kondarides, D. I. & Verykios, X. E. (2007). Photocatalytic degradation of organic pollutants with simultaneous production of hydrogen. *Catalysis Today*, Vol.124, No.3-4, (June 2007), pp.94-102, ISSN 0920-5861
- Peixoto G. (2008). *Produção de hidrogênio em reator anaeróbico de leito fixo ascendente a partir de água residuária de indústria de refrigerantes*. M.Sc. Dissertation. Universidade Federal de São Carlos. São Carlos, SP, Brazil
- Peter, L. M. (2007a). Characterization and Modeling of Dye-Sensitized Solar Cells. *The Journal of Physical Chemistry C*, Vol. 111, No. 18, (May 2007), pp. 6601-6612, ISSN 1932-7447
- Peter, L. (2007b). Transport, trapping and interfacial transfer of electrons in dye-sensitized nanocrystalline solar cells. *Journal of Electroanalytical Chemistry*, Vol.599, No.2, (January 2007), pp. 233-240, ISSN 0022-0728
- Pichat, P.; Disdier, J.; Hoang-Van, C.; Mas, D.; Goutailler, G. & Gaysse, C. (2000). Purification/deodorization of indoor air and gaseous effluents by TiO₂ photocatalysis. *Catalysis Today*, Vol.63, No.2-4, (December 2000), pp. 363-369, ISSN 0920-5861
- Plank, N.; Howard, I.; Rao, A.; Wilson, M.; Ducati, C.; Mane, R.; Bendall, J.; Louca, R.; Greenham, N.; Miura, H.; Friend, R.; Snaith, H. & Welland, M. (2009). Efficient ZnO Nanowire Solid-State Dye-Sensitized Solar Cells Using Organic Dyes and Core-shell Nanostructures. *The Journal of Physical Chemistry C*, Vol.43, No.113, (October 2009), pp. 18515-18522, ISSN 1932-7447
- Polo, A. S.; Itokazu, M. K. & Murakami Iha, N. Y. (2004). Metal complex sensitizers in dye-sensitized solar cells. *Coordination Chemistry Reviews*, Vol.248, No.13-14, (July 2004), pp. 1343-1361, ISSN 0010-8545
- Pons, M. N.; Alinsafi, A.; Evenou, F.; Abdulkarim, E. M.; Zahraa, O.; Benhammou, A.; Yaacoubi, A. & Nejmeddine, A. (2007). Treatment of textile industry wastewater by supported photocatalysis. *Dyes and Pigments*, Vol.74, No.2, (April 2006), pp. 439-445, ISSN 0143-7208
- Pradhan, B.; Batabyal, S. & Pal, A. (2007). Vertically aligned ZnO nanowire arrays in Rose Bengal-based dye-sensitized solar cells. *Solar Energy Materials & Solar Cells*, Vol.91, No.9, (May 2007), pp. 769-773, ISSN 0927-0248
- Prashant V. K. (2007) Meeting the Clean Energy Demand: Nanostructure Architectures for Solar Energy Conversion. *J. Phys. Chem. C*, Vol.111, No.7, (February 2007), pp. 2834-2860, ISSN 1932-7447
- Pregger, T.; Graf, D.; Krewitt, W.; Sattler, C.; Roeb, M. & Möller, S. (2009). Prospects of solar thermal hydrogen production processes. *International Journal of Hydrogen Energy*, Vol.34, No.10, (May 2009), pp.4256-4267, ISSN 0360-3199


- Prochazka, J.; Kavan, L.; Zukalova, M.; Frank, O.; Kalbac, M.; Zukal, A.; Klementova, M.; Carbone, D. & Grätzel, M. (2009). Novel synthesis of the TiO₂(B) multilayer templated films. *Journal of Materials Chemistry.*, Vol.21, No.8, (2009), pp. 1457–1464, ISSN 0897-4756
- Qiu, X. H.; Nazin, G. V. & Ho, W. (2004). Mechanisms of reversible conformational transitions in a single molecule. *Physical Review Letters*, Vol.93, No.19, (November 2004), pp. 196806-1-196806-4, ISSN 1079-7114
- Rehm, J. M.; McLendon, G. L.; Nagasawa, Y.; Yoshihara, K.; Moser, J. & Grätzel, M. (1996). Femtosecond Electron-Transfer Dynamics at a Sensitizing Dye-Semiconductor (TiO₂) Interface. *The Journal of Physical Chemistry*, Vol.100, No. 23 , (January 1996), pp. 9577-9578, ISSN 1932-7447
- Ricciardi, G.; Rosa, A. & Baerends, E. J. (2001). Ground and Excited States of Zinc Phthalocyanine Studied by Density Functional Methods. *The Journal of Physical Chemistry A*, Vol. 105, No 21, (May 2001), pp. 5242-5254, ISBN 1520-5215
- Sattler, C.; Oliveira, L.; Tzschirner, M. & Machado, A. E. H.(2004a). Solar photocatalytic water detoxification of paper mill effluents. *Energy*, V. 29, No. 5-6, (April-May 2004), pp. 835-843, ISSN 0360-5442
- Sattler, C.; Funken, K. H.; Oliveira, L.; Tzschirner, M. & Machado, A. E. H. (2004b). Paper mill wastewater detoxification by solar photocatalysis. *Water Science and Technology*, V. 49, No. 4, pp. 189-193, ISSN 0273-1223
- Senthilarasu, S.; Velumani, S.; Sathyamoorthy, R.; Subbarayan, A.; Ascencio, J.A.; Canizal, G.; Sebastian, P.J.; Chavez, J.A. & Perez, R. (2003). Characterization of zinc phthalocyanine (ZnPc) for photovoltaic applications. *Applied Physics A: Materials Science & Processing*, Vol. 77, No. 3-4, (August 2003), pp. 383–389, ISBN 1432-0630
- Shang, J.; Zhao, F.; W., Zhu, T. & Li, J. (2011). Photocatalytic degradation of rhodamine B by dye-sensitized TiO₂ under visible-light irradiation. *Science China-Chemistry*, Vol.54, No.1, (January 2011), pp. 167-172, ISSN 1674-7291
- Sharma, G. D.; Mathur, S. C. & Dube, D. C. (1991). Organic photovoltaic solar cells based on some pure and sensitized dyes. *Journal of Materials Science.*, Vol.26, No.24, (1991), pp. 6547-6552, ISSN 0022-2461
- Sharma, G. D.; Kumar, R. & Roy, M. S. (2006). "Investigation of charge transport, photogenerated electron transfer and photovoltaic response of iron phthalocyanine (FePc):TiO₂ thin films," *Solar Energy Materials & Solar Cells*, Vol. 90, No. 1, (January 2006), pp. 32-45, 0927-0248
- Shourong, Z.; Qingguo, H.; Jun, Z. & Bingkun, W. (1997). A study on dye photoremoval in TiO₂ suspension solution. *Journal of Photochemistry and Photobiology A: Chemistry*, Vol.108, No.2, (August 1997), pp. 235 - 238, ISSN 1010-6030
- Smith, B. & Shanta, M. S. (2007). Membrane reactor based hydrogen separation from biomass gas - a review of technical advancements and prospects. *International Journal of Chemical Reactor Engineering*, Vol.5, (November 2007), pp. 1-10, ISSN 1542-6580
- Snaith, H. J. (2010). Estimating the Maximum Attainable Efficiency in Dye-Sensitized Solar Cells. *Advanced Functional Materials*, Vol.20, No.1, (January 2010), pp. 13–19, ISSN 1616-3028
- Spadavecchia, F.; Cappelletti, G.; Ardizzone, S.; Ceotto, M. & Falciola, L. (2011). Electronic Structure of Pure and N-Doped TiO₂ Nanocrystals by Electrochemical Experiments

- and First Principles Calculations. *The Journal of Physical Chemistry C*, 2011, Vol.115, No.14, (March 2011), pp. 6381-6391, ISSN 1932-7447
- Srivastava, S. & Kotov, N. A. (2008). Composite Layer-by-Layer (LBL) Assembly with Inorganic Nanoparticles and Nanowires. *Accounts in Chemical Research*, Vol.41, No.12, (November 2008), pp. 1831-1841, ISSN 0001-4842
- Steinfeld, A. (2005). Solar thermochemical production of hydrogen - a review. *Solar Energy*, Vol.78, No.5, (December 2005) pp. 603-615, ISSN 0038-092X
- Stylidi, M.; Kondarides, D. I. & Verykios, X. E. (2004). Visible light-Induced Photocatalytic Degradation of Acid Orange 7 in Aqueous TiO₂ Suspensions. *Applied Catalysis B: Environmental*, Vol.47, No.3, (February 2004), pp. 189-201, ISSN 0926-3373
- Swaminathan, M. & Krishnakumar, B. (2011). A convenient method for the N-formylation of amines at room temperature using TiO₂-P25 or sulfated titania. *Journal of Molecular Catalysis A-Chemical*, Vol.334, No.1-2, (January 2011), pp. 98-102, ISSN 1381-1169
- Swaminathan, M. & Selvam, K. (2011). One-pot photocatalytic synthesis of quinaldines from nitroarenes with Au loaded TiO₂ nanoparticles. *Catalysis Communications*, Vol.12, No.6, (February 2011), pp. 389-393, ISSN 1566-7367.
- Tennakone, K.; Kumarasinghe, A. P.; Kumara, G. R. R. A.; Wijayantha, K. G. U. & Sirimanne, P. M. (1997). Nanoporous TiO₂ photoanode sensitized with the flower pigment cyanidin. *Journal of Photochemistry and Photobiology A: Chemistry*, Vol.108, No.2-3, (August 1997), pp. 193-195, ISSN 1010-6030
- Torres, T.; Claessens, C. G. & Hahn, U. (2008). Phthalocyanines: From outstanding electronic properties to emerging applications. *Chemical Record*, Vol.8, No.2, pp. 75-97, ISSN 1527-8999
- Tsuge, Y.; Inokuchi, K.; Onozuka, K.; Shingo, O.; Sugi, S.; Yoshikawa, M. & Shiratori, S. (2006). Fabrication of porous TiO₂ films using a spongy replica prepared by layer-by-layer self-assembly method: Application to dye-sensitized solar cells. *Thin Solid Films*, Vol.499, No.1-2, (March 2006), pp. 396-401, ISSN 0040-6090
- Wang, C. Y., Liu, C. Y., Wang, W. Q. & Shen, T. (1997). Photochemical events during the photosensitization of colloidal TiO₂ particles by a squaraine dye. *Journal of Photochemistry and Photobiology A: Chemistry*, Vol.109, No.2, (September 15 1997), pp. 159-164, ISSN 1010-6030
- Wang, P., Zakeeruddin, S. M., Moser, J. E. & Grätzel, M. J. (2003). A new ionic liquid electrolyte enhances the conversion efficiency of dye-sensitized solar cells. *Journal of Physical Chemistry B*, Vol.107, No.48, (December 4 2003), pp. 13280-13285, ISSN 1520-6106
- Wang, Z. S., Yanagida, M., Sayama, K. & Sugihara, H. (2006). Electronic-insulating coating of CaCO₃ on TiO₂ electrode in dye-sensitized solar cells: Improvement of electron lifetime and efficiency. *Chemistry of Materials*, Vol.18, No.12, (June 13 2006), pp. 2912-2916, ISSN 0897-4756
- Wojnárovits, L., Palfi, T. & Takacs, E. (2007). Kinetics and mechanism of azo dye destruction in advanced oxidation processes. *Radiation Physics and Chemistry*, Vol.76, No.8-9, (August-September 2007), pp. 497-501, ISSN 0969-806X
- Wood, J. & Tauc, D. L. (1972). Weak Absorption Tails in Amorphous Semiconductors. *Physical Review B*, Vol.5, No.8, (April 1972); pp. 3144-3151, ISSN 0163-1829
- Wu, T., Liu, G., Zhao, J., Hidaka, H. & Serpone, N. (1998). Photoassisted degradation of dye pollutants. V. Self-photosensitized oxidative transformation of Rhodamine B under

- visible light irradiation in aqueous TiO₂ dispersions. *Journal of Physical Chemistry B*, Vol.102, No.30, (July 23 1998), pp. 5845-5851, ISSN 1089-5647
- Wu, T., Xu, S. J., Shen, J. Q., Chen, S., Zhang, M. H. & Shen, T. (2000). Photosensitization of TiO₂ colloid by hypocrellin B in ethanol. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.137, No.2-3, (December 2000), pp. 191-196, ISSN 1010-6030
- Xagas, A. P., Bernard, M. C., Hugot-Le Goff, A., Spyrellis, N., Loizos, Z. & Falaras, P. (2000). Surface modification and photosensitisation of TiO₂ nanocrystalline films with ascorbic acid. *Journal of Photochemistry and Photobiology a-Chemistry*, Vol.132, No.1-2, (March 20 2000), pp. 115-120, ISSN 1010-6030
- Xia, J. B., Masaki, N., Jiang, K. J. & Yanagida, S. (2007a). Sputtered Nb₂O₅ as an effective blocking layer at conducting glass and TiO₂ interfaces in ionic liquid-based dye-sensitized solar cells. *Chemical Communications*, No.2, pp. 138-140, ISSN 1359-7345
- Xia, J. B., Masaki, N., Jiang, K. J. & Yanagida, S. (2007b). Sputtered Nb₂O₅ as a novel blocking layer at conducting Glass/TiO₂ interfaces in dye-sensitized ionic liquid solar cells. *Journal of Physical Chemistry C*, Vol.111, No.22, (June 7 2007), pp. 8092-8097, ISSN 1932-7447
- Yamashita, H., Harada, M., Misaka, J., Takeuchi, M., Ichihashi, Y., Goto, F., Ishida, M., Sasaki, T. & Anpo, M. (2001). Application of ion beam techniques for preparation of metal ion-implanted TiO₂ thin film photocatalyst available under visible light irradiation: Metal ion-implantation and ionized cluster beam method. *Journal of Synchrotron Radiation*, Vol.8, (March 2001), pp. 569-571, ISSN 0909-0495
- Yang, H. H., Guo, L. J., Yan, W. & Liu, H. T. (2006). A novel composite photocatalyst for water splitting hydrogen production. *Journal of Power Sources*, Vol.159, No.2, (September 22 2006), pp. 1305-1309, ISSN 0378-7753
- Yang, K. S., Dai, Y., Huang, B. B. & Whangbo, M. H. (2008). Density Functional Characterization of the Band Edges, the Band Gap States, and the Preferred Doping Sites of Halogen-Doped TiO₂. *Chemistry of Materials*, Vol.20, No.20, (October 28 2008), pp. 6528-6534, ISSN 0897-4756
- Zakeeruddin, S. M. & Grätzel, M. (2009). Solvent-Free Ionic Liquid Electrolytes for Mesoscopic Dye-Sensitized Solar Cells. *Advanced Functional Materials*, Vol.19, No.14, (July 24 2009), pp. 2187-2202, ISSN 1616-301X
- Zaleska, A. (2008a). Characteristics of Doped-TiO₂ Photocatalysts. *Physicochemical Problems of Mineral Processing*, No.42, (July 2008), pp. 211-221, ISSN 1643-1049
- Zaleska, A. (2008b). Doped-TiO₂: A Review. *Recent Patents on Engineering*, Vol.2, (July 2008), pp. 157-164, ISSN 1872-2121
- Zaleska, A., Zielinska, A., Kowalska, E., Sobczak, J. W., Lacka, I., Gazda, M., Ohtani, B. & Hupka, J. (2010). Silver-doped TiO₂ prepared by microemulsion method: Surface properties, bio- and photoactivity. *Separation and Purification Technology*, Vol.72, No.3, (May 2010), pp. 309-318, ISSN 1383-5866
- Zhang, X.; Wu, F.; Wu, X.; Chen, P. & Deng, N. (2008). Photodegradation of acetaminophen in TiO₂ suspended solution. *Journal of Hazardous Materials*, Vol.157, No.2-3, (September 2008), pp. 300 - 307. ISSN 0304-3894
- Zeug, N., Bücheler, J. & Kisch, H. (1985). Catalytic formation of hydrogen and carbon-carbon bonds on illuminated zinc sulfide generated from zinc dithiolenes. *Journal of the American Chemical Society*, Vol.107, No.6, pp. 1459-1465, ISSN 0002-7863

- Zhang, F., Zhao, J., Zang, L., Shen, T., Hidaka, H., Pelizzetti, E. & Serpone, N. (1998). TiO₂-assisted photodegradation of dye pollutants II. Adsorption and degradation kinetics of eosin in TiO₂ dispersions under visible light irradiation. *Applied Catalysis B-Environmental*, Vol.15, No.1-2, (January 15 1998), pp. 147-156, ISSN 0926-3373
- Zhang, A. & Zhang, J. (2009). Characterization of visible-light-driven BiVO₄ photocatalysts synthesized via a surfactant-assisted hydrothermal method. *Spectrochimica Acta Part A*, Vol.73, (March 2009), pp. 336-341, ISSN 1386-1425
- Zhang, H., Lv, X. J., Li, Y. M., Wang, Y. & Li, J. H. (2010). P25-Graphene Composite as a High Performance Photocatalyst. *ACS Nano*, Vol.4, No.1, (January 2010), pp. 380-386, ISSN 1936-0851
- Zhao, J. H., Wang, A., Green, M. A. & Ferrazza, F. (1998). 19.8% efficient "honeycomb" textured multicrystalline and 24.4% monocrystalline silicon solar cells. *Applied Physics Letters*, Vol.73, No.14, (October 1998), pp. 1991-1993, ISSN 0003-6951
- Zhao, Y., Zhai, J., He, J. L., Chen, X., Chen, L., Zhang, L. B., Tian, Y. X., Jiang, L. & Zhu, D. B. (2008). High-Performance All-Solid-State Dye-Sensitized Solar Cells Utilizing Imidazolium-Type Ionic Crystal as Charge Transfer Layer. *Chemistry of Materials*, Vol.20, No.19, (October 14 2008), pp. 6022-6028, ISSN 0897-4756
- Zhou, Y., Dang, M., Li, H. & Lu, C. (2011). Preparation of high-aspect-ratio TiO₂ nanotube arrays and applications for dye-sensitized solar cells. *Optoelectronics and Advanced Materials-Rapid Communications*, Vol.5, No.5-6, (May 2011), pp. 523-526, ISSN 1842-6573
- Zioli, R. L. & Jardim, W. F. (1998). Mechanism reactions of photodegradation of organic compounds catalyzed by TiO₂. *Quimica Nova*, Vol.21, No.3, (May-June 1998), pp. 319-325, ISSN 0100-4042

IntechOpen

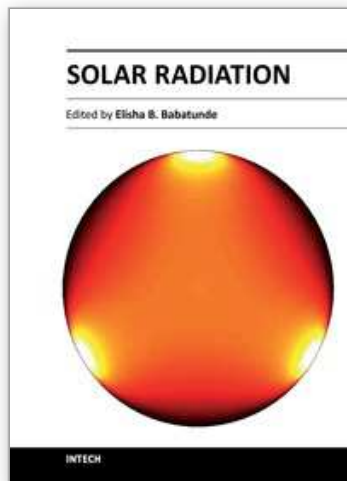

Solar Radiation

Edited by Prof. Elisha B. Babatunde

ISBN 978-953-51-0384-4

Hard cover, 484 pages

Publisher InTech

Published online 21, March, 2012

Published in print edition March, 2012

The book contains fundamentals of solar radiation, its ecological impacts, applications, especially in agriculture, architecture, thermal and electric energy. Chapters are written by numerous experienced scientists in the field from various parts of the world. Apart from chapter one which is the introductory chapter of the book, that gives a general topic insight of the book, there are 24 more chapters that cover various fields of solar radiation. These fields include: Measurements and Analysis of Solar Radiation, Agricultural Application / Bio-effect, Architectural Application, Electricity Generation Application and Thermal Energy Application. This book aims to provide a clear scientific insight on Solar Radiation to scientist and students.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Antonio Eduardo Hora Machado, Lidiaine Maria dos Santos, Karen Araújo Borges, Paulo dos Santos Batista, Vinicius Alexandre Borges de Paiva, Paulo Souza Müller Jr., Danielle Fernanda de Melo Oliveira and Marcela Dias França (2012). Potential Applications for Solar Photocatalysis: From Environmental Remediation to Energy Conversion, Solar Radiation, Prof. Elisha B. Babatunde (Ed.), ISBN: 978-953-51-0384-4, InTech, Available from: <http://www.intechopen.com/books/solar-radiation/potential-applications-for-solar-photocatalysis-from-environmental-remediation-to-energy-conversion>

INTECH
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2012 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen