

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

**4,800**

Open access books available

**122,000**

International authors and editors

**135M**

Downloads

Our authors are among the

**154**

Countries delivered to

**TOP 1%**

most cited scientists

**12.2%**

Contributors from top 500 universities



**WEB OF SCIENCE™**

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.

For more information visit [www.intechopen.com](http://www.intechopen.com)



---

# Hydrogen Economy: Modern Concepts, Challenges and Perspectives

---

Vladimir A. Blagojević, Dejan G. Minić,  
Jasmina Grbović Novaković and Dragica M. Minić

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/46098>

---

## 1. Introduction

Identifying and building a sustainable energy system are two of the most critical issues for any modern society. Ideally, current energy system, based mostly on fossil fuels, which have limited supply and considerable negative environmental impact, would be replaced with a system based on a renewable fuel. Hydrogen, as an energy carrier primarily derived from water, can address the issues of sustainability, environmental emissions and energy security. If one assumes a full hydrogen economy the size of United States, the amount of hydrogen for just purposes of transportation would be about 150 million tons per year, which would amount to consuming, with current production efficiency, between 2 and 5 billion tons of water. As a comparison, current water consumption in United States for purpose of thermoelectric power generation in power plants is around 300 billion tons, with another 1.2 billion tons consumed for gasoline production. Therefore, rather than consume, a hydrogen economy would most likely significantly reduce water consumption for purposes of energy generation (Turner, 2004).

Hydrogen is the most abundant element in the universe, burns clean, producing only water and has the highest energy density per unit mass. This is why hydrogen is considered most suitable to replace fossil fuels as the primary energy material for the mobile industry (Šušić, 1997c). However, hydrogen is not an energy source, only an energy carrier, and it is not freely available in nature and needs to be produced, either from water or other compounds. If it is produced from water, it costs more energy to produce it than one would recover burning it. This is why, ideally, a hydrogen cycle would include hydrogen produced by splitting water using electrolysis with solar energy and stored reversibly in a solid. However, there are considerable difficulties associated with efficient hydrogen production, storage and use in fuel cells. Among them, hydrogen storage for mobile applications is currently the most difficult obstacle.

Gasoline has very high energy density of 31.6 MJ/L, compared to 4.4 MJ/L of compressed hydrogen and 8.8 MJ/L of liquid hydrogen. In addition, gasoline tank has extremely short filling time, is capable of providing energy at low temperatures and provides excellent control of energy discharge, allowing rapid acceleration, high sustained speed and considerable range. These are the challenges that a successful hydrogen tank has to meet, too. US Department of Energy (DOE) target requirements for a hydrogen tank require hydrogen gravimetric density of 7.5 mass% and volumetric density of 70g/L, operating temperature between 233 and 358K, minimum delivery pressure of 12bar (1.2MPa) and fueling time of 3min. In addition, the storage system should be safe, durable (1500 operational cycle life) and cost effective. None of the existing systems meet these requirements.

In order to achieve the hydrogen economy, there are some obstacles that need to be overcome to make hydrogen a viable energy carrier. They are characterized by four main aspects of hydrogen use and some of these will be addressed here:

1. Production – since hydrogen needs to be produced, ideally from water, it is necessary to develop production methods that would consume the least amount of energy and provide ability to produce hydrogen renewably on a large scale.
2. Storage – fuel needs to be easily stored for use and transport, where one of the main requirements is that it is readily available, which requires not just short charge/discharge times, but also excellent control of charge/discharge process coupled with sufficient energy and gravimetric/volumetric density.
3. Power generation – once hydrogen is ready to be consumed, it is necessary to do so in the most effective way: the power generation system that uses hydrogen needs to be both efficient and, for mobile application, lightweight.
4. Safety – hydrogen use and storage comes with some risks (flammability) which necessitate certain precautions and safety measures; another aspect related to this is environmental impact of the hydrogen cycle, which depends on the methods used to produce, store and use it.

Since hydrogen is thought to be a renewable fuel for the future, it is only appropriate that, when we consider all the challenges associated with its production, storage and use, we keep in mind that when we consider proposed systems, efficiency is only one of the factors that will determine the success of these systems. Other important aspects are production cost (both financial and in resource), durability, stability of operation and safety, and these can, more than efficiency, determine the success or failure of any of the proposed solutions for a part of the hydrogen cycle.

## 2. Hydrogen production

There are several potential sources of hydrogen on our planet, although these are exclusively hydrogen compounds, necessitating extraction of hydrogen at energy cost. The most abundant is water, while hydrogen can also be obtained from hydrocarbons, either fossil fuels or biomass. While production from water is clean and renewable, with no CO<sub>2</sub>

emission, production from fossil fuels generates similar or even higher levels of CO<sub>2</sub> emissions as burning of coal and gasoline. Hydrogen production from biomass is carbon-neutral, since plants and organisms used during the process sequester approximately the same amount of CO<sub>2</sub> during their growth as it is emitted during the process of extraction of hydrogen from them. However, their negative environmental impact is considerable due to the fact that they require large land surfaces for growth.

*From water.* Although many technologies have been explored for production of hydrogen by splitting water into hydrogen and oxygen, these processes have yet to achieve the necessary efficiency and scalability for industrial application. The main advantage of hydrogen production from water is that it is clean, renewable and has little or no negative environmental impact, although the energy cost of its production is currently too high. There are several processes of interest, like electrolysis, catalytic thermolysis, photocatalytic water splitting and sulfur-iodine cycle.

Electrolysis of water is used today to produce around 5% of all industrial hydrogen. There are several types of cells in use: solid oxide electrolysis cell, alkaline electrolysis cell and polymer electrolyte membrane cell. These cells operate at elevated temperatures (350-570K) and contain high electrolyte concentrations and catalysts (typically yttrium-stabilized zirconium oxide mixed with nickel). Efficiency of typical electrolysis processes is usually between 50-80%, when inefficiencies of production of power used for electrolysis are not taken into account. With these taken into account, the energy efficiency would decrease to 30-45% for a typical nuclear or thermal power plant used as the power source, or even lower for a typical solar cell or array (Hauch et al., 2008).

Water thermolysis is thermal dissociation of water, which occurs spontaneously around 2800K. Although this temperature is too high for practical applications, significant effort has been invested into research of catalysts to reduce water thermolysis temperature and make it an industrially viable process. The goal is to use water thermolysis either in solar concentrators or in nuclear power plants to produce hydrogen directly using thermal energy. Solar concentrators can produce very high temperatures (over 1800K) by concentrating sunlight using a system of mirrors. Next generation nuclear power plants will be operating at lower temperatures (1000-1300K), but it is hoped that new catalysts will make it possible to use them for direct hydrogen generation using water thermolysis.

Photocatalytic water splitting is a process of directly producing hydrogen using solar energy. It relies on use of photocatalyst to capture the solar energy and use for water dissociation (Ni et al., 2007). There are two principal types of catalysts: photoelectrochemical and photobiological (discussed in biohydrogen production section). Photoelectrochemical (PEC) systems can be divided further into four groups:

- Type 1 – a single electrolyte-filled reactor containing a colloidal suspension of PEC nanoparticles producing a mixture of H<sub>2</sub> and O<sub>2</sub> gas;
- Type 2 – dual electrolyte-filled reactor beds containing a colloidal suspension of PEC nanoparticles, each carrying out half of the reaction process (one producing oxygen, the other hydrogen from H<sup>+</sup> produced in the first reactor bed);

- Type 3 – fixed PEC planar array using multi-junction photovoltaic/PEC cells immersed in electrolyte reservoir;
- Type 4 – PEC solar concentrator system, using reflectors to focus the solar flux at 10:1 intensity onto multi-junction photovoltaic/PEC cell receivers immersed in electrolyte reservoir and pressurized to 2MPa.

Estimated hydrogen production costs for these systems are: 1.63-10.36\$/kgH<sub>2</sub> depending on the type of system. DOE target for 2015 price of hydrogen was originally set at 1.50\$/kgH<sub>2</sub>, but it was increased in 2005 to 2-3\$ per kgH<sub>2</sub>, which means that some of these systems already meet that modified requirement. The main issues in these systems remain separation of O<sub>2</sub> and H<sub>2</sub> from the product for Type 1, ionic conduction (through ionic bridge) between two reactor beds for Type 2, improvement of PEC cell structure to reduce cost for Type 3 and new composite concentrator structure and high pressure PEC operation for Type 4. Potential benefits are clean and renewable direct hydrogen production with relatively low cost, although efficiency, depending on the system, is in range of 5-25% for the entire system.

Sulfur-iodine cycle is a thermochemical process which produces hydrogen from hydrogen iodide at much higher efficiency than water splitting, and at lower temperature (700K). One of its advantages is that sulfur and iodine are recovered and reused during the process and not consumed. It is usually coupled with concentrating solar power systems to produce hydrogen using solar energy, providing clean and renewable source of energy.

*From fossil fuels.* Fossil fuels are the dominant source of industrial hydrogen today. Hydrogen can be produced from natural gas with efficiency of around 80% and from other hydrocarbon sources with a varying degree of efficiency.

Most widely used method of hydrogen production today is steam reforming of methane or natural gas. At high temperatures (1000-1300K), water vapor reacts with methane to yield syngas (mixture of hydrogen and carbon monoxide), which can be used to produce more hydrogen through reaction of water and carbon monoxide (also known as water gas shift reaction, performed around 400K). The drawback of this process is that it produces CO<sub>2</sub> waste (Lee & Lee, 2001).

Other methods of hydrogen production from fossil fuels are partial oxidation of hydrocarbons, which includes partial combustion of fuel-air mixture at high temperatures or in a presence of a catalyst, plasma reforming (Kvaerner process), which produces hydrogen and carbon black from hydrocarbons (no CO<sub>2</sub> waste), and coal gasification, where coal is converted to syngas and methane.

*Biohydrogen production.* Biological H<sub>2</sub> production represents an effort to harness biological processes to generate hydrogen on the industrial scale. Although they have found no industrial application, there are a number of processes for conversion of biomass and waste streams into biohydrogen. Some of them are the same as the ones described above for fossil fuels, except they use biomass in place of fossil fuel (biomass gasification, steam reforming), while others use biological conversion of solar energy (Tao et al., 2007). Biological

conversion is process where biological organisms (usually plants) convert sunlight into hydrogen through their metabolic processes (Melis, 2002).

There are variety of pathways for biological conversion that include unicellular green algae, cyanobacteria, photosynthetic bacteria and dark fermentative bacteria. Photobiological production of hydrogen offers a perspective of operating with solar energy conversion efficiency to H<sub>2</sub> as high as 10%, if some of the barriers could be overcome, like slow H<sub>2</sub> production rate, or discontinuity of H<sub>2</sub> production due to co-generation of O<sub>2</sub> (Maness, 2002). Another challenge represents system engineering for cost-effective photobiological H<sub>2</sub> production. Because of an excellent variety of different bacteria, which absorb light in different spectral regions, it is hoped that, ultimately, a mixture of bacteria tailored to maximize sunlight absorption would be used to improve efficiency. This level of adaptability is one of the advantages of photobiological hydrogen production. There are no photobiological hydrogen production systems that are even close to being competitive with other methods of hydrogen generation, while relatively low overall efficiency would require large surface areas for harvesting and conversion of sunlight. On the other hand, biological production would probably have positive impact on environmental pollution and potentially serve as a source of high value bio-products, which could be useful in the food and synthetic chemistry industries. However, the main limitation of biological production is that it ultimately depends on availability of land for biomass production. This means that it cannot provide the amounts of hydrogen needed by an entire civilization, especially taking into account the fact that we live in a food-limited world with increasing population.

### 3. Hydrogen storage

Hydrogen storage is a problem that has been a focus of scientific research for decades (Minić & Šušić, 2002). During this time a variety of methods have been investigated, although, none of these have accomplished the required performance level so far. Current methods for hydrogen storage can be broadly separated into:

- mechanical storage: storage in a tank of compressed gas or liquid hydrogen;
- physisorption: storage in a solid material through physisorption; includes:
  - graphene and other carbon structures
  - metals and metallic nanocrystals and composites
  - metal-organic frameworks, zeolites;
- hydrogen: storage in solid or liquid material of chemically bound hydrogen that is released on decomposition; includes:
  - light metal hydrides (e.g. alkaline hydrides, alanates, alane)
  - borohydrides
  - amines and imides
  - amino borane.

Each of these methods has its advantages and disadvantages, but all on-board storage technologies have to meet the following requirements:

- safety

- performance
- cost
- technical adaptation for the infrastructure
- scalability (application in both small and large vehicles).


### 3.1. Mechanical storage

Low-pressure gaseous form of hydrogen is preferable in terms of efficiency. However, since vehicles cannot store enough hydrogen in this form, compression or liquefaction of hydrogen represents a relatively straightforward way of increasing vehicle on-board capacity. Mechanical storage methods store hydrogen by confining its gas or liquid form in a mechanical tank, similar to how gasoline is stored. The advantages are relatively good charge/discharge time and durability, but the capacity of the tanks is limited by relatively low energy density of hydrogen gas and liquid. In addition, the weight of tank is considerably larger than the gasoline tank due to demands of safe hydrogen storage.

There are currently three broad methods of mechanical hydrogen storage:

- high-pressure tank systems
- hydrogen-absorbing alloy tank system
- liquid hydrogen tanks.

Most current vehicles using hydrogen are equipped with a composite high-pressure tank, due to its simple structure and ease of charge-discharge cycle. Standard high-pressure tanks store hydrogen at 35MPa (350bar) pressure, which provides vehicle autonomy of 300-350km. Tanks have been developed recently to store hydrogen at 70MPa (700bar) pressure.

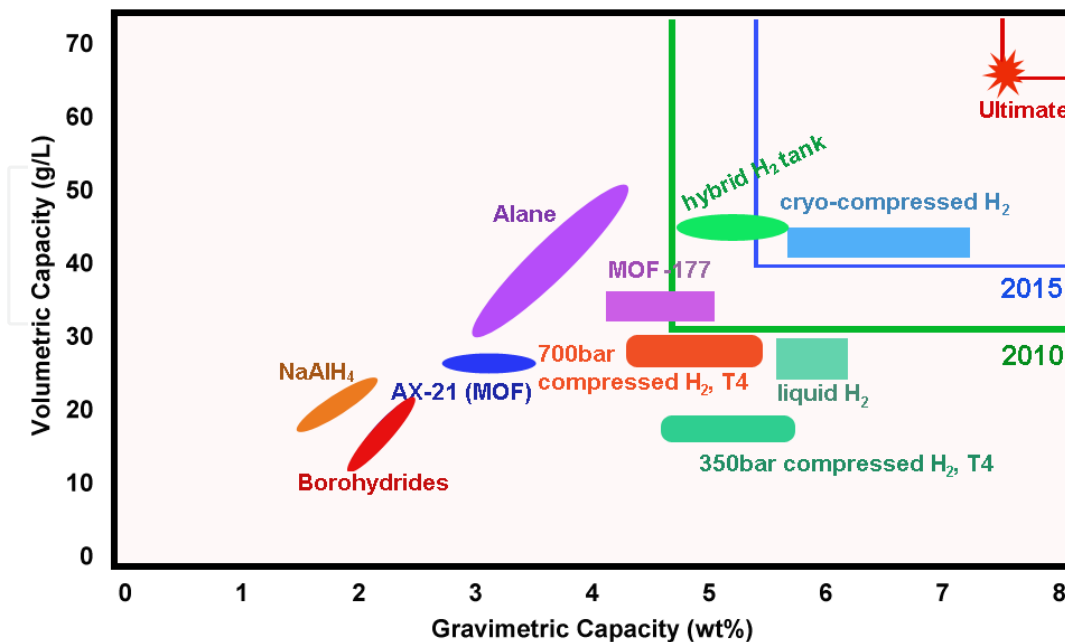

**Figure 1.** DOE set requirements (solid lines) and overview of existing developed hydrogen storage methods with respect to those requirements

However, pressure in this range makes the relationship between hydrogen pressure and amount non-linear. Therefore, doubling of pressure only leads to an increase of 40-60% more hydrogen, increasing vehicle autonomy to around 500km (Mori & Hirose, 2009).

Tank type	Type 1	Type 2	Type 3	Type 4
composition	all metal (carbon steel)	metal liner + GFRP layer	metal liner + CFRP layer	plastic liner + CFRP layer
thickness ratio (cylinder part)	1.0	0.7	0.32	0.28

**Table 1.** Different high-pressure (35MPa) tank types for hydrogen storage (GFRP – glass fiber reinforced polymer, CFRP – carbon fiber reinforced polymer)

In order to improve storage capacity of a high-pressure tank, hydrogen absorbing metal alloy is added to the tank to produce a hybrid high-pressure hydrogen absorbing tank system. The alloy increases capacity of the tank from around 3kg per 180L tank to 7-10kg per 180L tank, but hydrogen absorption on charging releases considerable amount of heat, requiring heat exchanger and radiator to be fitted with the tank, resulting in an increase in tank weight from around 100kg to over 400kg. High-pressure (35MPa) hydrogen environment helps metal alloy absorb hydrogen quickly (around 80% charge in 5min) and improves discharge speed, which is a common difficulty of classical metal hydrides, although high hydrogen pressure means that this system has the same safety issues as a regular high-pressure tank system. This system is also capable of operating at temperatures as low as 243K, which is not possible with low-pressure metal hydride systems. These hybrid systems offer a lot of promise offering good charge/discharge performance, but they still don't achieve the required hydrogen capacity and they retain the same safety issues associated with conventional high-pressure systems.

Another improvement of high-pressure system represents the use of cryo-compressed storage, where hybrid high-pressure tank is equipped with heat-transfer system, allowing it to maintain hydrogen gas at temperature around 50K and 0.4MPa pressure (around 6mass%). As the tank is emptied during use, temperature is gradually increased using the heat released during discharge to maintain a minimum 0.4MPa pressure. Figure 2 shows a comparison of gravimetric and volumetric densities of hydrogen for different high-pressure tank systems. Projected capacity of cryo-compressed hybrid system would meet DOE interim requirements for 2015, the first system so far to achieve this. However, this system is still well short of ultimate goals set by DOE.

Liquid hydrogen exists at atmospheric pressure at temperatures below 20K and its density is much higher than compressed gas. From the point of use in vehicles and infrastructure, liquid hydrogen is very attractive, because it offers an opportunity to easily transport and store large amounts of hydrogen. Some studies show that the extra energy consumption of liquefaction process can be compensated by the ease of delivery and storage. However, due to low temperatures involved, liquid hydrogen tanks require double wall construction for



thermal insulation, minimizing heat conductivity with vacuum multi-layer insulation. This consists of a thin metal layer on the spacer material which prevents both radiation and thermal irradiation between individual layers and heat intrusion from irradiation and gaseous convection. The most advanced liquid hydrogen tanks have limited heat flow to a few watts per second, which results in hydrogen evaporation and, therefore, loss of a few percent per day. Further developments in thermal insulation, advanced liquefaction and charge/discharge strategy are necessary in order to make liquid hydrogen a viable commercial alternative to a gasoline tank.

### 3.2. Carbon materials

There have been a number of studies of use of different carbon materials for hydrogen storage. Although initial reports suggested high hydrogen storage capacity of carbon nanotubes and other related nanostructures, more recent results have shown that the maximum sorption capacity of carbon nanostructures is around 2mass% (Zuettel et al., 2004) and that it is dependent only on the surface area of individual carbon nanostructure. Of those nanostructures, graphene sheets have exhibited the highest surface area and represent the most promising carbon material for hydrogen storage. However, since its capacity in pure form is about 2mass%, recent work has been focused on improving both performance and capacity of graphene. One of the issues that need to be overcome is that binding energy of atomistic hydrogen to carbon is 0.8eV, much lower than the energy of H-H bond in H<sub>2</sub> molecule (2.3eV per hydrogen atom). That is why recent research has been focused on catalyst assisted hydrogen sorption on carbon through spillover effect. Hydrogen spillover refers to transport of an active species generated on one substance (activator) to another (receptor) that would not normally adsorb it. In this case, activator is commonly a metal or a metal oxide, while carbon acts as a receptor, overcoming the energy barrier associated with dissociation of hydrogen molecule. Enhancement of hydrogen adsorption via spillover effect is much more pronounced at lower hydrogen pressure (below 0.5MPa), while it saturates at high pressures. This suggests existence of two distinct mechanisms corresponding to different spillover behavior, which can be controlled by activation of catalyst (Tsao et al., 2010).

Recent first-principle calculations have suggested that use of graphene double-layer and multi-layer structures could increase capacity for hydrogen storage (3-4mass%) (Patchkovskii et al., 2005), while recent experiments of Pd-loaded single-wall carbon nanotubes show improved performance after Pd-loading and thermal treatment at temperatures around 700K (Kocabas et al., 2008). Additional theoretical calculations of spillover on graphene suggests that hydrogen atoms on graphene surface should create compact clusters so that the lowest-energy cluster is composed of closed six-hydrogen rings, which would correspond, if entire surface area of graphene is used, to hydrogen storage capacity of about 7.7mass% (Lin et al., 2008). However, recent studies of kinetics of hydrogen adsorption/desorption kinetics in Pd/Pt/Ni/Ru doped ordered mesoporous carbon indicated that there is no difference in the kinetics of doped and pure carbon (Saha & Deng, 2009), suggesting that doping of carbon materials using transition metals might not be able to achieve significant increase in capacity and charge/discharge rates.

Although work on carbon materials is ongoing, it is unlikely that carbon materials will, in the foreseeable future, achieve the necessary performance levels required to replace fossil fuels. These types of materials have exhibited encouraging hydrogen capacity at low temperatures (20-80K), but their performance has regularly diminished at room temperature and this remains the biggest challenge in research of carbon materials for hydrogen storage.

### 3.3. Zeolites and metal-organic frameworks

Zeolites are crystalline microporous materials, usually aluminosilicates or aluminophosphates. They consist of microporous framework, which, in principle, appears highly suitable for hydrogen adsorption, as the adsorption energies in the narrow pores are very low, allowing thermal cycling to be used for adsorption and desorption of hydrogen. Initial reports of their storage capacities (Weitkamp et al., 1992, 1995, 1997) indicated very low capacities at room temperature, but these substantially increased at 77K, to 1.5mass% (Jhung et al., 2007). However, these fall well short of technical requirements. Projected maximum capacities for zeolite systems (assuming hydrogen packing density equal to liquid hydrogen) are a maximal 2.5 mass%, indicating that the currently known systems would not be able to meet the requirements to serve as hydrogen storage materials in mobile applications, although new materials might offer better performance.


Metal-organic framework (MOF) materials are composed of metal ions as vertices connected by organic molecules, often polyvalent carboxylic acids, to create a porous material of exceedingly high surface area (Rowsell & Yaghi, 2005). Reported hydrogen storage capacities of these materials have been encouraging: material MOF-177 was reported to have saturation uptake of 7.5 mass% at 77K and atmospheric pressure (Wong-Foy et al., 2006), although this declines to 1.62 mass% at 0.1MPa pressure (Rowsell et al., 2004). These materials exhibit an interesting feature, which could be of great importance for hydrogen adsorption – the so-called gated adsorption (Kitaura et al., 2003; Zhao et al., 2004). This process relies on flexibility of the framework of some MOFs allowing the structure to expand upon adsorption of guest species and shrink back upon desorption. This leads to a pronounced hysteresis, which can be exploited to load the materials at high pressure and still be able to capture hydrogen at lower pressures or higher temperature. However, these materials have some disadvantages as the loading of the material has to be performed at low temperatures, which consumes additional energy, and the binding of hydrogen to MOF materials is stronger than in carbon materials like graphite and carbon nanotubes (Rosi et al., 2003). However, this is still a new class of materials and most of them have yet to be investigated as hydrogen storage materials. In addition, in the foreseeable future, there should be many more new materials of this type, therefore, this class of materials shows great promise when it comes to hydrogen storage capabilities and offers genuine prospect of a hydrogen storage system that could meet all the requirements necessary for mobile applications.

### 3.4. Metal hydrides

Many metals and alloys are capable of absorbing considerable amounts of hydrogen according to the reaction (1):




Here  $Me$  is a metal, a solid solution, or an intermetallic compound and  $MeH_x$  is a hydride ( $x$  is the ratio of hydrogen to metal  $H/Me$ ). In most cases this reaction is exothermic and reversible. Heating of the hydride causes hydrogen desorption. Charging can be done using molecular hydrogen gas or hydrogen ions from an electrolyte. If hydrogen is loaded from gas phase, several reaction stages of hydrogen with metal would occur, as shown in Fig.2. The metal is usually in form of powder, and can be amorphous or crystalline (Minić et al., 1996). Repeated thermal treatment during hydrogen absorption and desorption causes structural changes in amorphous metals and intermetallic compounds, leading to crystallization (Minić et al., 1995; Šušić et al., 1996).

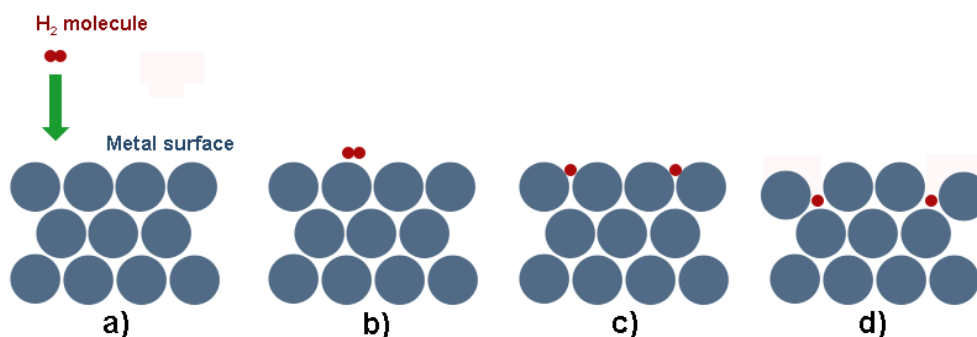


**Figure 2.** Reaction of  $H_2$  molecule with metal surface: a)  $H_2$  molecule move toward the metal surface. b) physisorption of  $H_2$  molecule through Van der Waals interaction with metal surface c) chemisorption of hydrogen after dissociation d) occupation of subsurface sites and diffusion into bulk.

Most of the known metal hydrides exhibit unsatisfactory charge/discharge kinetics, which led to devotion of significant research effort on improving it using surface catalysts and taking advantage of spillover mechanism of hydrogen absorption (Fig. 3). This mechanism includes adsorption and subsequent dissociation of hydrogen molecule on surface catalyst, and migration and subsequent diffusion of adsorbed hydrogen atoms from surface catalyst into the metal (Minić et al., 1997). Since catalyst is a metal or intermetallic compound with superior hydrogen adsorption, it serves as a gateway for hydrogen absorption. This improves charging kinetics of the metal, while using relatively small amounts of catalyst (most commonly Pd) (Šušić, 1997a, 1997b).

The reaction of hydrogen gas with a metal can be described by one-dimensional Lennard-Jones potential curve, Figure 4 (Lennard-Jones, 1932). Far from the metal surface, the potential energy difference of a hydrogen molecule and that of 2 individual hydrogen atoms is equal to dissociation energy ( $H_2 \rightarrow 2H$ ,  $E_D = 435.99 \text{ kJ/molH}_2$ ). The molecular hydrogen initially exhibits Van der Waals attractive interaction during approach to metal surface, leading to the physisorbed state ( $E_{\text{phys}} \approx -5 \text{ kJ/molH}$ ) at a distance from the metal surface approximately equal to hydrogen molecule radius ( $\approx 0.2 \text{ nm}$ ).

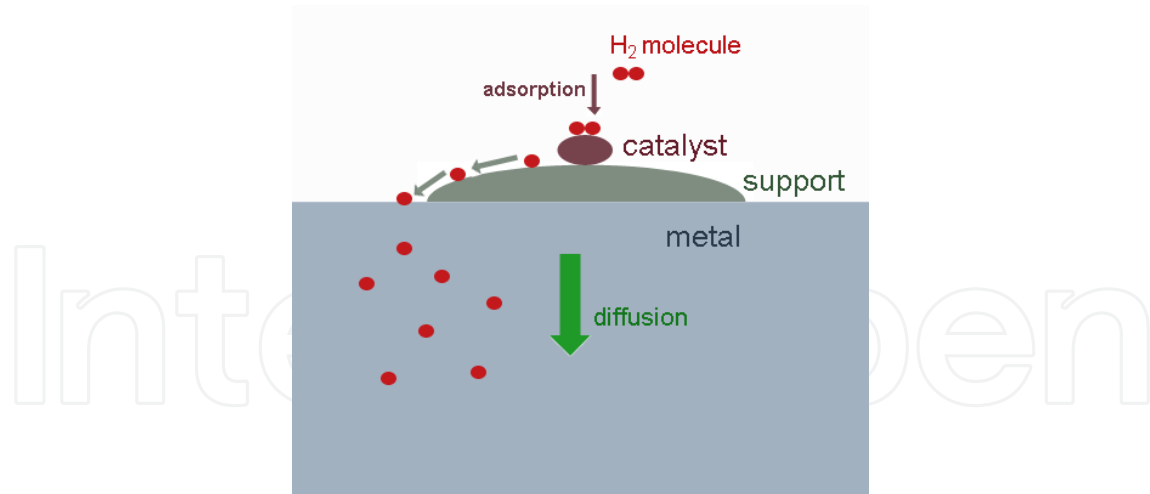

**Figure 3.** Illustration of spillover mechanism of absorption of hydrogen into a metal using a catalyst

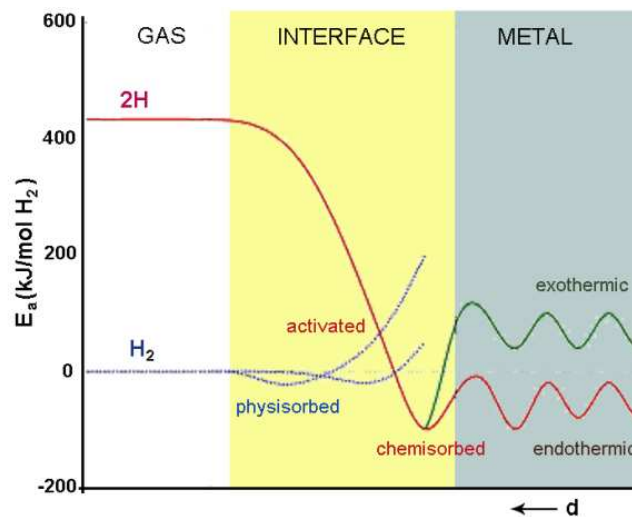


**Figure 4.** One-dimensional potential energy curve (one-dimensional Lennard-Jones potential) for a hydrogen metal system.

Closer to the metal surface, hydrogen has to overcome an activation barrier for dissociation and formation of the hydrogen-metal bond (crossing point of dashed blue and solid red line). The height of the activation barrier depends on the chemical composition of the surface. When hydrogen atom becomes chemisorbed ( $E_{\text{chem}} \approx -50$  kJ/mol $H_2$ ) it shares its electron with the metal atoms at the surface. These hydrogen atoms have high surface mobility, interacting with each other and forming surface phases. In the next step chemisorbed hydrogen atom can migrate into the subsurface layer and, finally, diffuse into the interstitial sites through the host metal lattice, contributing their electrons to the band structure of the metal (Zuettel, 2003).

After dissociation on the metal surface, the H atoms generally diffuse rapidly through the bulk metal even at room temperature to form Me-H solid solution or  $\alpha$ -phase. The thermodynamic aspects of hydride formation from gaseous hydrogen are described by pressure-composition isotherms (Fig. 5). After the maximum solubility of hydrogen in the

$\alpha$ -phase is reached, hydride phase ( $\beta$ -phase) will begin to form. Further increase in hydrogen pressure will result in substantial increase in the amount of absorbed hydrogen. This phenomenon can be explained using the Gibbs phase rule (2)

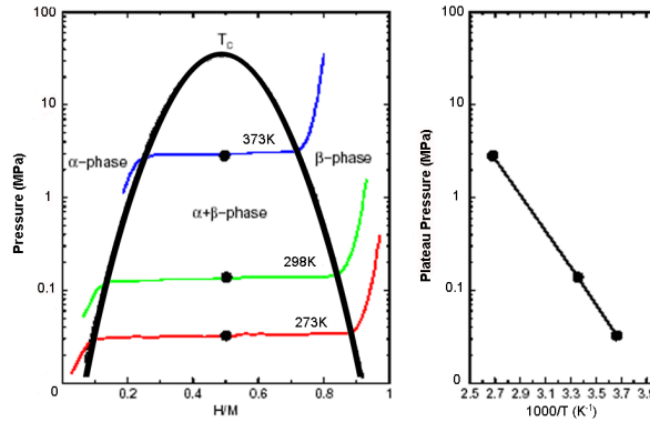

**Figure 5.** Left: Pressure-Composition-Isotherms (PCI) for a hypothetical metal hydride. Right: Van't Hoff plot for a hypothetical metal hydride derived from the measured pressures at plateau midpoints from the PCI's.

$$F = 2 - \pi + N \quad (2)$$

where  $F$  is the degree of freedom,  $\pi$  is the number of phases and  $N$  is the number of components.

Hydrogen pressure at which this transformation takes place is called the plateau pressure, where  $\alpha$ - and  $\beta$ -phase co-exist. When the stoichiometric hydride is formed, completely depleting the  $\alpha$ -phase, an additional degree of freedom is regained and the additional absorption of hydrogen would now require a substantial pressure increase, corresponding to the solid solution of hydrogen in  $\beta$ -phase.

The plateau pressure, described by Van't Hoff equation (3), gives us valuable information about reversible storage capacity. Width of the plateau and the position of the plateau at a given temperature give us a sense of the stability of the hydrides. Stable hydrides (enthalpy of formation,  $H_f \ll 0$ ) would require higher temperatures than less stable hydrides ( $H_f < 0$ ) to achieve a certain plateau pressure. Recording a series of PCI's at different temperatures makes it possible to construct a phase diagram from the end points of the plateaus in the individual PCI's.

$$\ln p = \frac{\Delta H}{RT} - \frac{\Delta S}{R} \quad (3)$$

where  $\Delta H$  is enthalpy,  $\Delta S$  is entropy,  $R$  is the gas constant and  $T$  is temperature.

Figure 6 represents a Van't Hoff diagram showing the dissociation pressures and temperatures of a number of hydrides. Light elements, such as Mg, have shown promising levels of stored hydrogen (about 7 wt% hydrogen), but require higher temperature for

dehydrogenation. Conventional metal hydrides, which have been well characterized and their capacity for interstitial hydrogen storage is well-established, include type AB, AB<sub>2</sub>, AB<sub>5</sub>, A<sub>2</sub>B (TiFe, ZrMn<sub>2</sub>, LaNi<sub>5</sub>, and Mg<sub>2</sub>Ni) intermetallic compounds, and body-centered cubic metals. These materials typically store between 1.4 and 3.6 wt% hydrogen. (Table 2). However, the requirements for gravimetric capacity, fast kinetic and high storage capacity is barely satisfied, so development of new lightweight materials presents many scientific and technical challenges. Among metal hydrides, magnesium hydride appears to be the most promising, because of its high storage capacity and relatively low cost.


Type	Intermetallic compound	H/M	H <sub>2</sub> capacity (mass%)	Temperature (K) for 0.1MPa P <sub>desorption</sub>
A <sub>2</sub> B	Mg <sub>2</sub> Ni	1.33	3.6	528
AB	TiFe	0.975	1.86	265
AB	ZrNi	1.4	1.85	565
AB <sub>2</sub>	ZrMn <sub>2</sub>	1.2	1.77	440
AB <sub>5</sub>	LaNi <sub>5</sub>	1.08	1.49	285
AB <sub>2</sub>	TiV <sub>0.62</sub> Mn <sub>1.5</sub>	1.14	2.15	267

**Table 2.** Hydrogen storage properties of some intermetallic compounds


### 3.5. Magnesium hydride

High gravimetric (7.6 wt.%) (Hanada et al., 2004) and volumetric density (130 kg H<sub>2</sub>/m<sup>3</sup>) and relatively low price make magnesium hydride (MgH<sub>2</sub>) an attractive hydrogen storage material. However the wide industrial application is still not feasible, due to its high enthalpy of formation ( $\Delta H^\circ = -75$  kJ/molH<sub>2</sub>) and dehydrogenation temperature (720 K), as well as slow kinetics of hydrogenation reactions/dehydrogenation reaction. For example, there is no detectable hydrogen desorption at temperature of 573 K, while at 623 K it takes more than 3000s for complete decomposition of MgH<sub>2</sub> (Varin et al., 2009). Furthermore, in order to allow for the formation of MgH<sub>2</sub>, it is necessary to perform an activation process of Mg metal by consecutive heating and cooling of metal in vacuum and in hydrogen atmosphere, which makes the material permeable to hydrogen. The efforts to overcome these deficiencies have made MgH<sub>2</sub> one of the most investigated materials in last two decades.

At moderate hydrogen pressure the only hydride phase existing in equilibrium with Mg is magnesium hydride,  $\beta$ -MgH<sub>2</sub>. Pure Mg has a hexagonal crystal structure, while its hydride has a tetragonal lattice unit cell (rutile type) (Zeng et al., 1999; Yu & Lam, 1988). Figure 7 shows the crystal structure of  $\beta$ -MgH<sub>2</sub> (P4<sub>2</sub>/mnm space group), where each Mg atom is coordinated with six H atoms forming an irregular slightly distorted octahedron (Noritake et al., 2003). Each H atom is coordinated with three planar Mg atoms. Synchrotron X-ray diffraction gives the parameters of crystal  $a = 0.45180(6)$  nm and  $c = 0.30211(4)$  nm (Lide, 2006; Lide, 2007) while the powder diffraction file (JCPDS 12-0697) provides similar values for  $a = 0.4517$  nm and  $c = 0.30205$  nm. Density of MgH<sub>2</sub> is 1.45 g/cm<sup>3</sup> (Bastide, 1980).

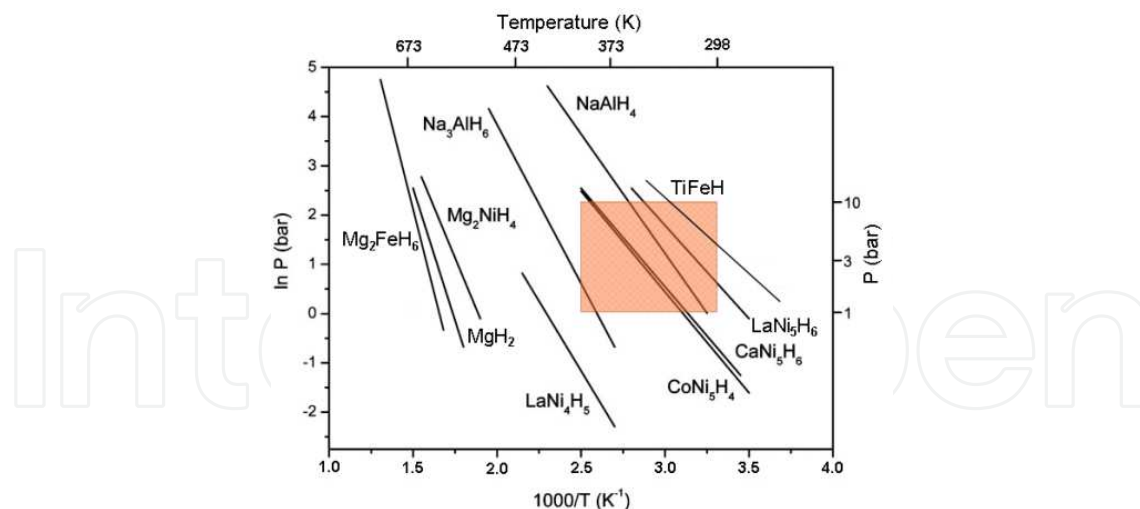

**Figure 6.** Van't Hoff plots of various metal hydrides, showing hydrogen dissociation pressures and temperatures (red shaded area represents desirable operating conditions).

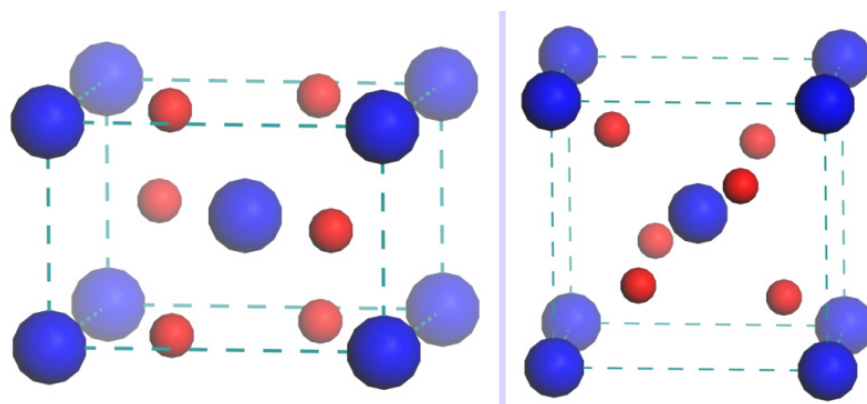

**Figure 7.** Two perspectives of crystal structure of  $\beta$ -MgH<sub>2</sub> showing the positions of Mg (blue) and H atoms (red)

Although there is considerable literature dealing with structure and properties (Novaković et al., 2009; Schimmel et al., 2004, 2005; Kelkar & Pal, 2009; Bassetti et al., 2005) of MgH<sub>2</sub>, there are still some uncertainties about H-desorption kinetics, since the Mg–H interaction strongly depends on method of synthesis and presence of additives. For instance, ball milling causes mechanical deformation, surface modification, and metastable phase formation which generally promote the solid–gas reaction. It also introduces defect zones which may accelerate the diffusion of hydrogen (Shan et al., 2004; Jensen et al., 2006; Bobet et al., 2001; Montone et al., 2006, 2007; Aguey-Zinsou et al., 2007). Addition of transition metals, metal oxides or ternary hydrides to mechanically milled MgH<sub>2</sub> decreases its thermal stability and decomposition temperature. It has also been established that nanosized powders provide a possible solution for the problem of hydrogen desorption kinetics (Varin et al., 2006). *Ab initio* DFT calculations (Kurko et al., 2011) have been used to determine possible ways of improving the performance of MgH<sub>2</sub>. They have shown that destabilization temperature of MgH<sub>2</sub> reduces with decreasing cluster size, and that a crystallite size of 0.9 nm could result in a desorption temperature below 500 K (Wagemans et al., 2005). However

ball milling can also cause agglomeration and cold welding of particles (Montone et al., 2005), therefore experimentally obtained decrease in hydrogen adsorption temperature in ball-milled samples is relatively low, keeping MgH<sub>2</sub> far from practical application (Milovanović et al., 2008). Based on *ab initio* calculations, Novakovic *et al.* (Novaković et al., 2009) examined the possible pathways for adsorption/desorption of hydrogen from MgH<sub>2</sub>, showing that different H-filling patterns influence initial hcp-Mg structure in different ways, qualifying wurtzite MgH as a probable intermediate phase between the hcp-Mg and MgH<sub>2</sub> at 1:1 stoichiometry. Du et al. suggested that surface desorption is rate-determining since the activation barrier computed for H-vacancy diffusion from the surface into sublayer is less than 0.70 eV, much smaller than the activation energy for desorption of hydrogen on the MgH<sub>2</sub>(110) surface (1.78-2.80 eV/H<sub>2</sub>) (Du et al., 2007). Furthermore, the first principle calculations of MgH<sub>2</sub>-TM (TM=Al, Ti, Fe, Ni, Cu, Nb, Co) were carried out to investigate their influence on the stability of the magnesium hydride (Novaković et al., 2010; Song et al., 2004). It was found that TM-H bonding is stronger than the Mg-H bond, but at the same time it weakens other bonds in the second and third coordination around TM atom, which leads to overall destabilization of the MgH<sub>2</sub> compound. Due to a higher number of d-electrons, this effect is more pronounced in late transition metals. In case of Co doping, spin polarization has an additional stabilizing influence on the compound structure.

### 3.6. Alanates

Alanates, or aluminohydrides, are a family of compounds containing aluminum and hydrogen, with NaAlH<sub>4</sub> being the most popular material in this family (Bogdanović & Schwickardi, 1997; Downs & Pulham, 1994; Fichter et al., 2003; Jain et al., 2010). One of the attractive features of alanates is their easy accessibility, since sodium and lithium alanate are commercially available and magnesium alanate can be easily synthesized. They have relatively high gravimetric hydrogen capacity (5-9 mass%), however, these materials usually undergo multi-step thermal decomposition (Eq. 4) to release hydrogen and these reactions require relatively high temperatures and considerable reaction time (NaAlH<sub>4</sub> releases 3.7 mass% H<sub>2</sub> in 3h at 483K).



Additionally, some of the alanates are meta-stable, making their first decomposition (dehydrogenation) step exothermic and irreversible. This makes their direct rehydrogenation impossible, which would rule them out as candidates for on-board hydrogen storage applications.

In order to improve their charge/discharge performance and reduce decomposition temperatures, alanates have been doped with transition metals, with Ti- and Ni-doping exhibiting promising results thus far in improving kinetics and dehydrogenation rates, while preserving very high hydrogen capacity.



Material	H <sub>2</sub> capacity (mass%)	Dehydrogenation temperature (K)	Dissociation enthalpy (kJ/mol H <sub>2</sub> )
NaAlH <sub>4</sub>	5.6	480-490 (I step) >525 (II step)	37 (I step, 3.7 mass% H <sub>2</sub> ) 42 (II step, 1.9 mass% H <sub>2</sub> )
LiAlH <sub>4</sub>	7.9	430-450 (I step) 450-490 (II step)	-10 (I step, 5.3 mass% H <sub>2</sub> ) 25 (II step, 2.6 mass% H <sub>2</sub> )
Mg(AlH <sub>4</sub> ) <sub>2</sub>	9.3	380-470 (I step) 510-650 (II step)	41 (I step, 7 mass% H <sub>2</sub> ) 76 (II step, 2.3 mass% H <sub>2</sub> )
KAlH <sub>4</sub>	5.7	570 (I step) 610 (II step) 650 (III step)	55 (I step, 2.9 mass% H <sub>2</sub> ) 70 (II step, 1.4 mass% H <sub>2</sub> )
Ca(AlH <sub>4</sub> ) <sub>2</sub>	5.9	400 (I step) 520 (II step)	-7 (I step, 2.9 mass% H <sub>2</sub> ) 28 (II step, 2.9 mass% H <sub>2</sub> )

**Table 3.** Overview of characteristics of some of the alanates for hydrogen storage [18]

Alanates exhibit very high hydrogen storage capacity, although they cannot be charged and discharged easily and their working temperatures are too high. There is some hope that doping could alleviate some of these difficulties, but it is clear that if these materials become utilized for hydrogen storage, it will probably be in a hybrid high-pressure system, which could additionally improve their charge/discharge performance and be adapted to account for relatively slow discharge rates, while taking advantage of high hydrogen capacities.

### 3.7. Borohydrides

Borohydride, or tetrahydroborate, refers to a group of complex hydride compounds in which hydrogen is covalently bonded to the central atom in [BH<sub>4</sub>]<sup>-</sup> complex anion (Eq. 5).



They exhibit high gravimetric and volumetric hydrogen capacity, making the materials of interest for hydrogen storage research (Schlesinger et al., 1953). One of the issues that would have to be resolved is the fact that they exhibit exothermic desorption reactions (30-300 kJ/mol), making their rehydrogenation more difficult than that of other materials and making direct rehydrogenation thermodynamically impossible. In addition, they exhibit high dehydrogenation temperatures (520-670°C), which practically means that only part of their hydrogen capacity is accessible at normal working temperatures.

Material	H <sub>2</sub> capacity (mass%)	Dehydrogenation temperature (K)	Dissociation enthalpy (kJ/mol H <sub>2</sub> )
NaBH <sub>4</sub>	10.8	670	-217 to -270
LiBH <sub>4</sub>	13.4	650	-177
Mg(BH <sub>4</sub> ) <sub>2</sub>	13.7	530-670	-39.3 to -50
Ca(BH <sub>4</sub> ) <sub>2</sub>	9.6	620	32

**Table 4.** Overview of characteristics of some of the borohydrides for hydrogen storage [18]

Therefore, most of the work associated with borohydrides is focused on use of doping and catalysts to improve charge/discharge kinetics, lower dehydrogenation temperature and increase hydrogen discharge capacity and cycling ability of these materials (Soler et al., 2007, Pena-Alonso et al., 2007; Lee et al., 2008; Demirci et al., 2009).

### 3.8. Amides and imides

Amides and imides have attracted a lot of interest, due to their high hydrogen capacity and relatively low operating temperature (Chen et al., 2003; Hu et al., 2003). However, their poor absorption kinetics limits their current practical application (Eq. 6). Therefore there has been a lot of focus on overcoming this by doping with a catalyst, usually through mechanical ball milling (Liu et al., 2008).




Another direction of research has been combining alkaline metal amides with other hydride materials using ball milling. Although  $LiNH_2$  and  $LiAlH_4$  mixture released approximately 4 atom equivalents of hydrogen, its rehydrogenation was unsuccessful at  $H_2$  pressures up to 80bar (8MPa) (Xiong et al., 2006).

Metal ion of amide/imide system	$H_2$ capacity (mass%)	Dehydrogenation temperature (K)	Dissociation enthalpy (kJ/mol $H_2$ )
Li	5.4	550	148
	6.5		45
Mg	7.4	470	3.5
Ca	3.5	620	
	2.1	770	
Li-Mg	4.5	470	39
Li-Al	4	360	
	2	440	
	2.1	470	

**Table 5.** Overview of characteristics of some of the amida/imide systems for hydrogen storage [18]

### 3.9. Amino borane

Ammonium borane,  $NH_3BH_3$ , is considered a promising candidate for chemical storage of hydrogen, due to its low molecular weight and high hydrogen content of 19.6 mass%. Its thermal decomposition occurs in three stages (Eqs. 7 and 8), around 363, 420 and 970K, respectively, with one molar equivalent (6.5 mass%) of hydrogen released during each step (Gutowska et al. 2005; Baitalow et al., 2002).



Dehydrogenation rates are very slow due to long induction period (around 200min at 353K) (Chandra & Xu, 2006a, 2006b). The enthalpy is -21 kJ/mol, which is in the range that is suitable for on-board application. Therefore, most of the scientific effort has been focused on overcoming the slow reaction kinetics using additives like silica scaffolds, metal catalysts and ionic liquids (Umegaki et al., 2009).

### 3.10. Alane

Aluminum hydride (alane,  $\text{AlH}_3$ ) has an average enthalpy of formation of -11.4 kJ/mol and freshly synthesized non-solvated alane is reported to desorb around 10 mass% of  $\text{H}_2$  at temperatures below 373K (Graetz & Reilly, 2006). However, while the dehydrogenation reaction occurs readily (Eq. 9), the reverse process does not, requiring 2.5GPa pressure of  $\text{H}_2$  to rehydride (Baranowski & Tkacz, 1983).



In addition, dehydrogenation kinetics is too slow for practical applications, as it is limited by nucleation and growth of aluminum particles. Therefore, research has been focused on decreasing the dehydrogenation temperature and improving its kinetics using additives like alkali metal hydride (Sandrock et al., 2006) and particle size reduction using ball milling (Orimo et al., 2006). Best results have been achieved by doping  $\text{AlH}_3$  with small amounts of LiH, NaH or KH.

## 4. Hydrogen power generation – Fuel cells

As early as 1839, William Grove discovered the basic operating principle of a fuel cell by reversing the electrolysis of water to generate electricity from hydrogen and oxygen. This principle remains unchanged today, that a fuel cell is an electrochemical device which continuously converts chemical energy into electric energy (and heat) for as long as fuel and oxidant are supplied. A fuel cell does not need recharging, operates quietly and efficiently and, with hydrogen as fuel, generates only power and water. This is why it is called a zero-emission engine. Unlike thermal engines, it is not limited by the Carnot efficiency; therefore, while thermal engines typically achieve efficiency of 24-32%, fuel cells achieve efficiencies of 35-60% (Minh & Takahashi, 1995).

One of the major obstacles in fuel cell application so far has been their insufficient lifetime: most fuel cells exhibit major performance decay after 1000 hours of operation, while DOE target for 2015 is 5000 hours of operation at 60% efficiency for mobile applications. Additionally, their price per kW is almost twice that of an internal combustion engine (Hoogers, 2003). There is a wide variety of fuel cell types, which can be distinguished by the electrolyte used, but they all function in the same basic way. At the anode a fuel (usually hydrogen) is oxidized into electrons and protons, and at the cathode, oxygen is reduced to

Fuel Cell Type	Electrolyte	Charge Carrier	Operating temperature (K)	Fuel	Electric Efficiency (system)	Power Range (kW)
Alkaline	KOH	OH <sup>-</sup>	330-390	H <sub>2</sub>	35-55%	<5kW
Proton Exchange Membrane	Solid polymer	H <sup>+</sup>	320-373	H <sub>2</sub> (tolerates CO <sub>2</sub> )	35-45%	5-250
Phosphoric acid	Phosphoric acid	H <sup>+</sup>	~590	H <sub>2</sub> (tolerates CO <sub>2</sub> )	40%	200
Molten carbonate	Li and K carbonate	CO <sub>3</sub> <sup>2-</sup>	~1020	H <sub>2</sub> , CO, CH <sub>4</sub> (tolerates CO <sub>2</sub> )	>50%	200-1000
Solid oxide	Solid oxide electrolyte (Y, Zr)	O <sup>2-</sup>	~1270	H <sub>2</sub> , CO, CH <sub>4</sub> (tolerates CO <sub>2</sub> )	>50%	2-1000

**Table 6.** Overview of different types of fuel cells and their characteristics

oxide species. Depending on the electrolyte, either protons or oxide ions are transported through the electrolyte (ion-conducting, but electronically insulating) to combine with oxide species or protons, respectively, to generate water and electric power. Alkaline fuel cells do not tolerate presence of CO<sub>2</sub> in the system, which forms alkaline carbonates, meaning that they can only use carbon-free fuel.

Of the currently developed types of fuel cells, proton exchange membrane fuel cells (PEMFC) and alkaline fuel cells (AFC) satisfy the required range of operating temperature and provide sufficient current density for mobile applications, although the power range for AFC is sufficient only for specialty applications (like power generation of space crafts). PEMFC, also known as solid polymer fuel cell, takes its name from the special plastic membrane it uses for electrolyte, combining all the key parts (anode, cathode, electrolyte) in a very compact unit, not thicker than few hundreds microns. The membrane requires presence of liquid water, limiting its operating temperature to below 373K, which means that, to achieve a good performance, this fuel cell requires a good catalyst (Wang et al., 2011).

Two high-temperature types of fuel cells (molten carbonate and solid oxide) are mainly considered for large scale stationary power generation. They achieve higher efficiencies than low-temperature systems and high operating temperatures allow for direct internal processing of fuels like natural gas, reducing the system's complexity (Tucker, 2010). However, this also means that they cannot easily be turned off.

In addition to using pure hydrogen or hydrocarbons and carbon monoxide as fuel, in recent times, fuel cells have been coupled with biomass-derived fuel processors. This makes it possible to use biomass-derived fuels, such as ethanol, methanol, biodiesel or biogas, and feed them to a fuel processor as a raw fuel, which would, after reforming, be used by a fuel cell (Xuan et al., 2009).

Although all of types of fuel cells described above operate on gas fuel, recently, PEM fuel cells have been constructed to operate using liquid fuel – methanol (Ismail et al., 2011). This has advantages for mobile applications and fuel transportation, but these direct methanol fuel cells are not yet advanced enough to generate high enough current and power density to compete with gas fuel cells.

## 5. Conclusion

The limitations of our world's natural resources mean that our civilization has to find an alternative energy source and energy carrier to replace fossil fuels. Taking into account available fossil fuel reserves and that such a conversion of energy source/carrier historically takes 75-100 years, it is clear that this is crucial time for alternative energy research. Hydrogen is the obvious candidate for the renewable energy carrier for the future, due to its availability in form of water, high energy density and lack of negative environmental impact. However, current state of technology is such that significant advances are needed in the next decade in order to make hydrogen economy viable. There is still lack of an effective large-scale hydrogen production process from water, while hydrogen storage still falls well behind the requirements set by gasoline. When it comes to power generation, hydrogen fuel cells are still lagging behind internal combustion engines and conventional batteries in performance and power/weight ratio. On the other hand, significant strides have been made in recent times, which give hope that hydrogen will, in the foreseeable future, be able to challenge fossil fuels as the primary energy carrier, but only through a sustained and focused effort.

## Author details

Vladimir A. Blagojević and Dragica M. Minić  
*University of Belgrade, Faculty for Physical Chemistry, Serbia*

Dejan G. Minić  
*Kontrola LLC, Austin, TX, USA*

Jasmina Grbović Novaković  
*Laboratory for Material Sciences, Institute for Nuclear Science Vinča, University of Belgrade, Belgrade, Serbia*

## Acknowledgement

The research has been supported by the by the Serbian Ministry of Education and Science under grants 172015 and III45012.

## 6. References

Aguey-Zinsou K-F., Ares Fernandez J.R., Klassen T. & Bormann R. (2007), *Effect of Nb<sub>2</sub>O<sub>5</sub> on MgH<sub>2</sub> properties during mechanical milling*, International Journal of Hydrogen Energy, vol. 32, No. 13, pp. 2400-2407

- Baitalow F., Baumann J., Wolf G., Jaenicke-Rößler K. & Leitner G., *Thermal decomposition of B–N–H compounds investigated by using combined thermoanalytical methods*, *Thermochimica Acta*, vol. 391, pp. 159–168
- Baranowski B. & Tkacz M. (1983), *The Equilibrium Between Solid Aluminium Hydride and Gaseous Hydrogen*, *Zeitschrift für Physikalische Chemie N.F.*, vol. 135, pp. 27–38
- Bassetti A., Bonetti E., Pasquini L., Montone A., Grbovic J. & Vittori Antisari M. (2005), *Hydrogen desorption from ball milled MgH<sub>2</sub> catalyzed with Fe*, *European Physics Journal B*, vol. 43, No. 1, pp. 19–28
- Bastide J.P., Bonnetot B., Letoffe J.M. & Claudy P. (1980), *Materials Research Bulletin*, vol. 15, pp. 1215
- Bobet J-L., Akiba E. & Darriet B. (2001), *Study of Mg-M (M=Co, Ni and Fe) mixture elaborated by reactive mechanical alloying: hydrogen sorption properties*, *International Journal of Hydrogen Energy*, vol. 26, No. 5, pp. 493–501
- Bogdanovic B. & Schwickardi M. (1997), *Ti-doped alkali metal aluminium hydrides as potential novel reversible hydrogen storage materials*, *Journal of Alloys and Compounds*, vol. 253–254, pp. 1–9.
- Demirci U.B., Akdim O. & Miele P. (2009), *Aluminum chloride for accelerating hydrogen generation from sodium borohydride*, *Journal of Power Sources*, vol. 192, No. 2, pp. 310–315.
- Chandra M. & Xu Q. (2006), *A high-performance hydrogen generation system: Transition metal-catalyzed dissociation and hydrolysis of ammonia–borane*, *Journal of Power Sources*, vol. 156, No. 2, pp. 190–194.
- Chandra M. & Xu Q. (2006), *Dissociation and hydrolysis of ammonia-borane with solid acids and carbon dioxide: An efficient hydrogen generation system*, *Journal of Power Sources*, vol. 159, No. 2, pp. 855–860.
- Chen P., Xiong Z., Luo J.Z., Lin J.Y. & Tan K.L. (2003), *Interaction between Lithium Amide and Lithium Hydride*, *Journal of Physical Chemistry B*, vol. 107, pp. 10967–10970.
- Downs A.J. & Pulham C.R. (1994), *The hydrides of aluminium, gallium, indium, and thallium: a re-evaluation*, *Chemical Society Review*, vol. 23, No. 3, pp. 175–184.
- Du A.J., Smith S.C. & Lu G.Q. (2007), *First-Principle Studies of the Formation and Diffusion of Hydrogen Vacancies in Magnesium Hydride*, *Journal of Physical Chemistry C*, vol. 111, No. 23, pp. 8360–8365
- Fichtner M., Fuhr O. & Kircher O. (2003), *Magnesium alanate—a material for reversible hydrogen storage?*, *Journal of Alloys and Compounds*, vol. 356–357, pp. 418–422.
- Gutowska A., Li L., Shin Y., Wang C.M, Li X.S., Linehan J.C., Smith R.S., Kay B.D., Schmid B., Shaw W., Gutowski M. & Autrey T. (2005), *Nanoscaffold Mediates Hydrogen Release and the Reactivity of Ammonia Borane*, *Angewandte Chemie. International Edition*, vol. 44, No. 23, pp. 3578–3582.
- Graetz J., Reilly J.J. (2006), *Thermodynamics of the  $\alpha$ ,  $\beta$  and  $\gamma$  polymorphs of AlH<sub>3</sub>*, *Journal of Alloys and Compounds*, vol. 424, pp. 262–265.
- Hanada N., Ichikawa T., Orimo S-I. & Fujii H. (2004), *Correlation between hydrogen storage properties and structural characteristics in mechanically milled magnesium hydride MgH<sub>2</sub>*, *Journal of Alloys and Compounds*, vol. 366, pp. 269–273

- Hauch A., Ebbesen S. D., Jensen S.H. & Mogensen M. (2008), *Highly Efficient High Temperature Electrolysis*, Journal of Materials Chemistry, vol. 18, pp. 2331-2340
- Hoogers G. (editor), *Fuel Cell Technology Handbook*, CRC Press, New York, U.S.A., 2003
- Jain I.P., Jain P. & Jain A. (2010), *Novel hydrogen storage materials: A review of lightweight complex hydrides*, Journal of Alloys and Compounds, vol. 503, pp. 303–339
- Hu Y.H. & Ruckenstein E. (2003), *Ultrafast Reaction between LiH and NH<sub>3</sub> during H<sub>2</sub> Storage in Li<sub>3</sub>N*, Journal of Physical Chemistry A, vol. 107, No. 46, pp. 9737–9739.
- Ismail A., Kamarudin S.K., Daud W.R.W., Masdar S. & Yosfiah M.R. (2011), *Mass and heat transport in direct methanol fuel cells*, Journal of Power Sources, vol. 196, pp. 9847– 9855
- Jensen T.R., Andreasen A., Vegge T., Andreasen J.W., Ståhl K., Pedersen A.S., Nielsen M.M., Molenbroek A.M. & Besenbacher F. (2006), *Dehydrogenation kinetics of pure and nickel-doped magnesium hydride investigated by in situ time-resolved powder X-ray diffraction*, International Journal of Hydrogen Energy, vol. 31, No. 14, pp. 2052-2062
- Jhung S.H., Yoon J.W., Lee J.S. & Chang J.S. (2007), *Low-Temperature Adsorption/Storage of Hydrogen on FAU, MFI, and MOR Zeolites with Various Si/Al Ratios: Effect of Electrostatic Fields and Pore Structures*, Chemistry A European Journal, vol. 13 No. 22, pp. 6502 – 6507
- Kelkar T. & Pal S. (2009), *A computational study of electronic structure, thermodynamics and kinetics of hydrogen desorption from Al- and Si-doped  $\alpha$ -,  $\gamma$ -, and  $\beta$ -MgH<sub>2</sub>*, Journal of Materials Chemistry, vol. 19, No. 25, pp. 4348-4355
- Kitaura R., Seki K., Akiyama G. & Kitagawa S. (2003), *Porous Coordination-Polymer Crystals with Gated Channels Specific for Supercritical Gases*, Angewandte Chemie International Edition, vol. 42, No. 4, pp. 428 – 431.
- Kocabas S., Kopac T., Dogu G. & Dogu T. (2008), *Effect of thermal treatments and palladium loading on hydrogen sorption characteristics of single-walled carbon nanotubes*, International Journal of Hydrogen Energy vol. 33, pp. 1693 – 1699
- Kurko S., Paskaš Mamula B., Matovic Lj., Grbovic Novakovic J., Novakovic N. (2011), *The Influence of Boron Doping Concentration on MgH<sub>2</sub> Electronic Structure*, Acta Physica Polonica A, vol. 120, No. 2, pp. 238-241
- Lee W-J. & Lee Y-K. (2001), *Internal Gas Pressure Characteristics Generated during Coal Carbonization in a Coke Oven*, Energy & Fuels, vol. 15, No. 3, pp. 618-623
- Lee Y., Kim Y., Jeong H. & Kang M. (2008), *Hydrogen production from the photocatalytic hydrolysis of sodium borohydride in the presence of In-, Sn-, and Sb-TiO<sub>2</sub>s*, Journal of Industrial Engineering and Chemistry, vol. 14, No. 5, pp. 655–660.
- Lennard-Jones J.E. (1932), *Processes of adsorption and diffusion on solid surfaces*, Transactions of Faraday Society, vol. 28, pp. 333
- Lide D.R. (editor), *Physical constants of inorganic compounds*, CRC Handbook of Chemistry and Physics, Editor: 87th on-line edition (2006-2007), CRC Press, New York, USA
- Lin Y., Ding F. & Yakobson B.I. (2008), *Hydrogen storage by spillover on graphene as a phase nucleation process*, Physical Review B vol. 78, pp. 041402(R)
- Liu Y., Zhong K., Gao M., Wang J., Pan H. & Wang Q. (2008), *Chemistry of Materials*, vol. 20, pp. 3521–3527

- Maness P-C., Smolinski S., Dillon A.C., Heben M.J. & Weaver P.F. (2002) *Characterization of the oxygen tolerance of a hydrogenase linked to a carbon monoxide oxidation pathway in Rubrivivax gelatinosus*, Applied Environmental Microbiology, vol. 68, pp. 2636-2636.03
- Melis A. (2002), *Green alga hydrogen production: progress, challenges and prospects*. International Journal of Hydrogen Energy, vol. 27, pp. 1217-1228
- Milovanović S., Matović Lj., Drvendžija M. & Grbović Novaković J. (2008), *Hydrogen storage properties of MgH<sub>2</sub> - diatomite composites obtained by high energy ball milling*, Journal of Microscopy, vol. 232, No. 3, pp. 522-525
- Minh N. & Takahashi T. (1995), *Science and Technology of Ceramic Fuel Cells*, Elsevier, The Netherlands
- Minić D. & Šušić M. (1995), *Thermal Behaviour of 82Ni-18P Amorphous Powder Alloy in Hydrogen atmosphere*, Materials Chemistry and Physics, vol. 40, pp. 281-284.
- Minić D., Šušić M. & Maričić A. (1996), *Absorption of Hydrogen by Amorphous and Crystalline 89Fe-11P Powder. Deformation of the Powder under Pressure and Relaxation on Heating*, Materials Chemistry and Physics, vol. 45, pp. 280-283.
- Minić D., Šušić M., Tešić Ž. & Dimitrijević R. (1997), *Investigation of the Thermal Behaviour of Ag-Pd Intermetallic Compounds in Hydrogen Atmosphere*, Studies in surface and catalysis, vol. 112, pp. 447-456.
- Minić D., Šušić M.V. (2002), *Modern Concepts of Conversion and Storage of Energy by Disperse Material Absorption*, Science of Sintering, vol. 34, pp. 247-259
- Montone A., Grbović J., Bassetti A., Mirengghi L., Rotolo P., Bonetti E., Pasquini L. & Vittori Antisari M. (2005), *Role of Organic Additives in Hydriding Properties of Mg-C Nanocomposites*, Materials Science Forum, vol. 494, pp. 137-142
- Montone A., Grbović J., Stamenković Lj., Fiorini A.L., Pasquini L., Bonetti E. & Vittori Antisari M. (2006), *Desorption Behaviour in Nanostructured MgH<sub>2</sub>-Co*, Materials Science Forum, vol. 518, pp. 79-84
- Montone A., Grbović Novaković J., Vittori Antisari M., Bassetti A., Bonetti E., Fiorini A.L., Pasquini L., Mirengghi L. & Rotolo P. (2007), *Nano-micro MgH<sub>2</sub>-Mg<sub>2</sub>NiH<sub>4</sub> composites: Tailoring a multichannel system with selected hydrogen sorption properties*, International Journal of Hydrogen Energy, vol. 32, No. 14, pp. 2926-2934
- Mori D. & Hirose K. (2009), *Recent challenges of hydrogen storage technologies for fuel cell vehicles*, International Journal of Hydrogen Energy vol. 34, pp. 4569 – 4574
- Ni M., Leung M.K.H., Leung D.Y.C. & Sumathy K. (2007), *A review and recent developments in photocatalytic water-splitting using TiO<sub>2</sub> for hydrogen production*, Renewable and Sustainable Energy Reviews, vol. 11, pp. 401-425
- Noritake T., Towata S., Aoki M., Seno Y., Hirose Y., Nishibori E., Takata M. & Sakata M. (2003), *Charge density measurement in MgH<sub>2</sub> by synchrotron X-ray diffraction*, Journal of Alloys and Compounds vol. 356-357, pp. 84-86
- Novaković N., Matović Lj., Grbović Novaković J., Manasijević M. & Ivanović N. (2009), *Ab initio study of MgH<sub>2</sub> formation*, Materials Science and Engineering B, vol. 165, No. 3, pp. 235-238



- Novaković N., Grbović Novaković J., Matović Lj., Manasijević M., Radisavljević I., Paskas Mamula B. & Ivanović N. (2010), *Ab initio calculations of MgH<sub>2</sub>, MgH<sub>2</sub>:Ti and MgH<sub>2</sub>:Co compounds*, International Journal of Hydrogen Energy, vol. 35, No. 2, pp. 598-608
- Orimo S., Nakamori Y., Kato T., Brown C. & Jensen C.M. (2006), *Intrinsic and mechanically modified thermal stabilities of  $\alpha$ -,  $\beta$ - and  $\gamma$ -aluminum trihydrides AlH<sub>3</sub>*, Applied Physics A, vol. 83, No. 1, pp. 5-8.
- Patchkovskii S., Tse J.S., Yurchenko S.N., Zhechkov L., Heine T. & Seifert G. (2005), *Graphene nanostructures as tunable storage media for molecular hydrogen*, Proceedings of National Academy of Sciences, vol. 102 No. 30 pp. 10439-10444
- Pena-Alonso R., Sicurelli A., Callone E., Carturan G. & Raj R. (2007), *A picoscale catalyst for hydrogen generation from NaBH<sub>4</sub> for fuel cells*, Journal of Power Sources, vol. 165, No. 1, pp. 315–323.
- Rosi N.L., Eckert J., Eddaoudi M., Vodak D.T., Kim J., O’Keeffe M. & Yaghi O.M. (2003), *Hydrogen Storage in Microporous Metal-Organic Frameworks*, Science, vol. 300, No. 5622, pp. 1127-1129.
- Rowsell J.L.C., Millward A.R., Park K.S. & Yaghi O.M. (2004), *Hydrogen Sorption in Functionalized Metal–Organic Frameworks*, Journal of the American Chemical Society vol. 126, No. 18, pp. 5666 – 5667
- Rowsell J.L.C. & Yaghi O.M. (2005), *Strategies for Hydrogen Storage in Metal–Organic Frameworks*, Angewandte Chemie International Edition, vol. 44 No. 30, pp. 4670 – 4679
- Saha D. & Deng S. (2009), *Hydrogen Adsorption on Ordered Mesoporous Carbons Doped with Pd, Pt, Ni, and Ru*, Langmuir vol. 25, No. 21, pp. 12550-12560
- Sandrock G., Reilly J.J., Graetz J., Zhou W-M., Johnson J. & Wegrzyn J. (2006), *Alkali metal hydride doping of  $\alpha$ -AlH<sub>3</sub> for enhanced H<sub>2</sub> desorption kinetics*, Journal of Alloys and Compounds, vol. 421, pp. 185–189.
- Schimmel H.G., Johnson M.R., Kearley G.J., Ramirez-Cuesta A.J., Huot J. & Mulder F.M. (2004), *The vibrational spectrum of magnesium hydride from inelastic neutron scattering and density functional theory*, Materials Science and Engineering B, vol. 108, No. 1-2, pp. 38-41
- Schimmel H.G., Johnson M.R., Kearley G.J., Ramirez-Cuesta A.J., Huot J. & Mulder F.M. (2005), *Structural information on ball milled magnesium hydride from vibrational spectroscopy and ab-initio calculations*, Journal of Alloys and Compounds, vol. 393, pp. 1-4
- Schlesinger H.I., Brown C.H., Finholt A.E., Gilbreath J.R., Hoekstra H.R. & Hyde E.K. (1953), *Sodium Borohydride, Its Hydrolysis and its Use as a Reducing Agent and in the Generation of Hydrogen*, Journal of the American Chemical Society, vol. 75, No. 1, pp. 215-219
- Shan C.X., Bououdina M., Song Y., Guo Z.X. (2004), *Mechanical alloying and electronic simulations of (MgH<sub>2</sub>+M) systems (M=Al, Ti, Fe, Ni, Cu and Nb) for hydrogen storage*, International Journal of Hydrogen Energy, vol. 29, No. 1, pp. 73-80
- Soler L., Macanás J., Munoz M. & Casado J. (2007), *Synergistic hydrogen generation from aluminum, aluminum alloys and sodium borohydride in aqueous solutions*, International Journal of Hydrogen Energy, vol. 32, No. 18, pp. 4702–4710.
- Song Y., Guo Z.X. & Yang R. (2004), *Influence of selected alloying elements on the stability of magnesium dihydride for hydrogen storage applications: A first-principles investigation*, Physical Review B, vol. 69, No. 9, pp. 094205

- Šušić M., Minić D., Maričić A., Jordović B. & Krsmanović D. (1996), *Structural Changes During Heating a Cold Sintered Amorphous Powder of 82Ni and 18P Alloy*, *Science of Sintering*, vol. 28, pp. 105-110.
- Šušić M.V. (1997), *Hydriding and dehydriding of a graphite powder doped with palladium*, *Journal of Serbian Chemical Society*, vol. 62, No. 12, pp. 1183-1186.
- Šušić M.V. (1997), *Hydriding and dehydriding of palladium-doped charcoal*, *Journal of Serbian Chemical Society*, vol. 62, No. 8, pp. 631-634.
- Šušić M.V. (1997), *Kinetics of the process of isothermal hydriding and dehydriding of hydrogen absorbers*, *International Journal of Hydrogen Energy*, vol. 22, No. 6, pp. 585-589.
- Tao Y., Chen Y., Wu Y., He, Y. & Zhou Z. (2007). *High hydrogen yield from a two-step process of dark- and photo-fermentation of sucrose*, *International Journal of Hydrogen Energy*, vol. 32, No. 2, pp. 200-206
- Tsao C.S., Tzeng Y.R., Yu M.S., Wang C.Y., Tseng H.H., Chung T.Y., Wu H.C., Yamamoto T., Kaneko K. & Chen S.H. (2010), *Effect of Catalyst Size on Hydrogen Storage Capacity of Pt-Impregnated Active Carbon via Spillover*, *Journal of Physical Chemistry Letters*, vol. 1, pp. 1060-1063
- Turner J. (2004), *Sustainable hydrogen production*, *Science* vol. 305, pp. 972-974
- Tucker M.C. (2010), *Progress in metal-supported solid oxide fuel cells: A review*, *Journal of Power Sources*, vol. 195, pp. 4570-4582
- Umegaki T., Yan J.M., Zhang X.B., Shioyama H., Kuriyama N. & Xu Q. (2009), *Boron- and nitrogen-based chemical hydrogen storage materials*, *International Journal of Hydrogen Energy*, vol. 34, No. 5, pp. 2303-2311
- Varin R.A., Czujko T. & Wronski Z. (2006), *Particle size, grain size and  $\gamma$ -MgH<sub>2</sub> effects on the desorption properties of nanocrystalline commercial magnesium hydride processed by controlled mechanical milling*, *Nanotechnology*, vol. 17, No. 15, pp. 3856-3865
- Varin R.A., Czujko T. & Wronski Z.S. (2009), *Nanomaterials for Solid State Hydrogen Storage*, Springer Science+Business Media, LLC, ISBN 978-0-387-77711-5
- Wagemans R.W.P., van Lenthe J.H., de Jongh P.E., van Dillen A.J. & de Jong K. P. (2005), *Hydrogen Storage in Magnesium Clusters: Quantum Chemical Study*, *Journal of the American Chemical Society*, vol. 127, No. 47, pp. 16675-16680
- Wang Y., Chen K.S., Mishler J., Cho S.C. & Adroher X.C. (2011), *A review of polymer electrolyte membrane fuel cells: Technology, applications, and needs on fundamental research*, *Applied Energy*, vol. 88, pp. 981-1007
- Weitkamp J., Fritz M. & Ernst S. (1992), *Zeolithe als Speichermaterialien für Wasserstoff*, *Chemie Ingenieur Technik*, vol. 64, No. 12, pp. 1106 - 1109.
- Weitkamp J., Fritz M. & Ernst S. (1995), *Zeolites as media for hydrogen storage*, *International Journal of Hydrogen Energy*, vol. 20, No. 12, pp. 967 - 970.
- Weitkamp J., Ernst S., Cubero F., Wester F. & Schnick W. (1999), *Nitrido-sodalite Zn<sub>6</sub>[P<sub>12</sub>N<sub>24</sub>] as a material for reversible hydrogen encapsulation*, *Advanced Materials* vol. 9, No. 3, pp. 247 - 248.
- Wong-Foy A.G., Matzger A.J. & Yaghi O.M. (2006), *Exceptional H<sub>2</sub> Saturation Uptake in Microporous Metal-Organic Frameworks*, *Journal of the American Chemical Society* vol. 128, No. 11, pp. 3494 - 3495.
- Xiong Z.T., Wu G.T., Hu J.J. & Chen P. (2006), *Investigation*

- on chemical reaction between  $\text{LiAlH}_4$  and  $\text{LiNH}_2$* , Journal of Power Sources, vol. 159, No. 1, pp. 167-170
- Xuan J., Leung M.K.H., Leung D.Y.C. & Ni M. (2009), *A review of biomass-derived fuel processors for fuel cell systems*, Renewable and Sustainable Energy Reviews, vol. 13, pp. 1301–1313
- Yu R. & Lam P (1988), *Electronic and structural properties of  $\text{MgH}_2$* , Physical Review B vol. 37, No. 15, pp. 8730-8737
- Zhao X., Xiao B., Fletcher A.J., Thomas K.M., Bradshaw D. & Rosseinsky M.J. (2004), *Hysteretic Adsorption and Desorption of Hydrogen by Nanoporous Metal-Organic Frameworks*, Science vol. 306, No. 5698, pp. 1012 – 1015.
- Zeng K., Klassen T., Oelerich W. & Bormann R. (1999), *Critical assessment and thermodynamic modeling of the Mg–H system*, International Journal of Hydrogen Energy, vol. 24, No. 10, pp. 989-1004
- Zuettel A. (2003), *Materials for hydrogen storage*, Materials Today, vol. 6, No. 9, pp. 24-33
- Zuettel A., Wenger P., Sudan P., Mauron P. & Orimo S. (2004), *Hydrogen density in nanostructured carbon, metals and complex materials*, Materials Science and Engineering B vol. 108, pp. 9–18