

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,800

Open access books available

122,000

International authors and editors

135M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)



---

# Physicochemical Properties and Catalytic Applications of Iron Porphyrazines and Phthalocyanines

---

Tomasz Koczorowski, Wojciech Szczolko and  
Tomasz Goslinski

Additional information is available at the end of the chapter

<http://dx.doi.org/10.5772/68071>

---

## Abstract


Porphyrazines and phthalocyanines belong to porphyrinoids, which are macrocyclic compounds consisting of four pyrrole or indole rings, respectively. The aromatic rings of porphyrazines and phthalocyanines are fused together by azamethine bridges (meso nitrogen atoms) in place of methine bridges present in porphyrins. The physicochemical properties of these macrocycles can be modified in two ways. The first is by substitution of metal cation in the core, whereas the second relies on peripheral modification with various substituents. Porphyrazines and phthalocyanines can be modified inside the macrocyclic core with various transition metal cations, including iron(II/III), which impacts their electrochemical properties and influences potential applications in redox reactions. Due to their unique optical and electrochemical properties, porphyrazines and phthalocyanines found many potential and practical applications in medicine and technology. They were mainly researched as photosensitizers in photodynamic therapy, as sensors in biomedical and analytical applications or as building blocks for materials chemistry. This chapter presents physicochemical properties and catalytic applications of iron porphyrazines and phthalocyanines. The first part summarizes the influence of peripheral and axial substituents of iron(II/III) porphyrazines and phthalocyanines on their spectral properties, whereas the second focuses on the electrochemical properties of these molecules. The third part covers the activity of selected iron(II/III) porphyrazines and phthalocyanines of potential value for diverse applications including catalytic reactions.

**Keywords:** catalytic properties, electrochemistry, iron, porphyrazines, phthalocyanines

---

## 1. Introduction to porphyrinoids

Porphyrinoids are macrocyclic compounds consisting of four pyrrole rings usually linked together through methine or azamethine bridges. Porphyrins (Ps) are planar and aromatic with nominally  $22\pi$ -electrons of which  $18\pi$ -electrons are engaged in a conjugative path. Porphyrins can be substituted at the peripheral  $\beta$  and methine meso positions. Chlorins and bacterichlorins possess similar structure to porphyrins, and they are defined as dihydro or tetrahydro derivatives of porphyrins. Corrole macrocycle constitutes an  $18\pi$ -electron system with the characteristic feature being the lack of a methine bridge between the A and D pyrrole rings. In addition, corroles carry inside the macrocyclic core three NH protons, which is different from porphyrins and chlorins, which carry two NH protons. It is worth noting that structurally related corrins with the key natural product cobalamine (vitamin  $B_{12}$ ) are not aromatic and contain only one NH proton inside the macrocyclic core. Porphyrazines (Pzs) and phthalocyanines (Pcs) commonly known as tetraazaporphyrins belong to synthetic porphyrinoids. Methine bridges are replaced by azamethine (with nitrogen atoms) as the most notable feature of their structure. In addition, Pcs are tetrabenzo tetraazaporphyrins, which have annulated benzene rings in comparison with the Pz core. Formally, in phthalocyanines, unlike in porphyrazines, the azamethine bridges combine four indole instead of pyrrole rings, respectively (**Figure 1**). The derivatives of Pcs can be obtained by substitution of fused benzene rings at peripheral (2,3 or  $\beta$ ) and nonperipheral positions (1,4 or  $\alpha$ ). The tetraazaporphyrins possess unique physicochemical properties due to the presence of a conjugated system of

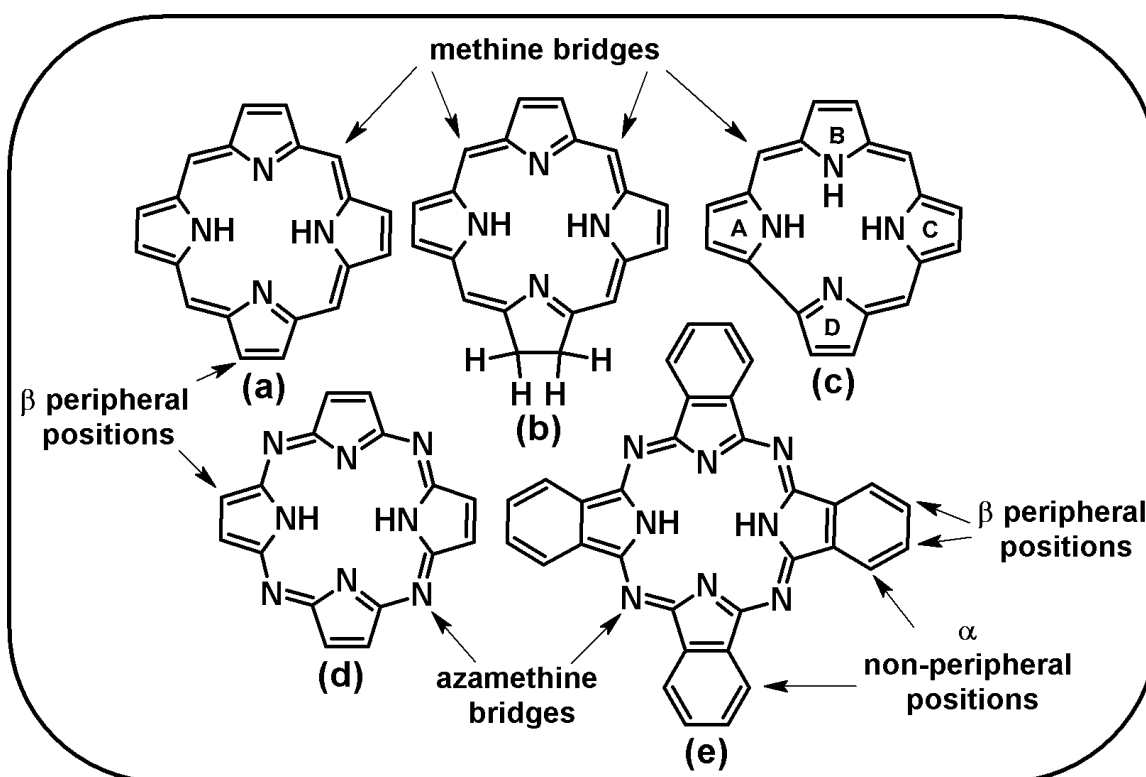


**Figure 1.** Structures of porphyrins (a), chlorins (b), corroles (c), porphyrazines (d), and phthalocyanines (e).

$\pi$  electrons, bulky periphery and an ability to coordinate various metal cations inside macrocyclic core. The chelation reaction of the inner NH protons with various metal ions leads to metal chelates, which is a common feature for all porphyrinoids [1–6].

Many natural porphyrins and chlorins, for example, heme in hemoglobin and chlorophyll, reveal various vital functions and are responsible for many biochemical processes. Nowadays, porphyrinoids possess potential applications in science and technology, for example, synthetic derivatives of porphyrins as well as phthalocyanines found many applications in the dye industry and revealed potential for medicine (photodynamic therapy and photodynamic diagnosis) and technology (artificial enzymes, catalysts). Many tetraazaporphyrins have also been studied as analytical indicators, structural elements in materials chemistry, in optical data drivers and microchips, as well as photovoltaic cells. In addition, there is a possibility to utilize porphyrines and phthalocyanines as catalysts in various organic synthesis reactions due to their ability to coordinate transition metal cations inside macrocyclic core or in the periphery. Lately, tetraazaporphyrins have also been considered as building blocks in nanotechnology due to their self-assembly and self-organization ability (**Figure 2**) [3, 6–19].

Tetraazaporphyrins can be modified using two approaches. The first relies on the introduction of various alkyl and/or aryl substituents with sulfur, nitrogen or oxygen atoms into porphyrine  $\beta$  peripheral positions of pyrrole rings and phthalocyanine  $\alpha$  nonperipheral and/or  $\beta$  peripheral positions of indole rings. The second concerns removal or exchange of central metal cation present in macrocyclic core. By using all of these modification approaches, there is a possibility to obtain macrocyclic compounds of altered physicochemical properties, for example, extended thermal and photochemical stability, increased solubility in organic solvents, improved luminescence and spectroscopic, magnetic, electrochemical properties, photoconductivity and surface activity [1, 2]. Incorporation of iron(II/III) cations into the porphyrinoid core allowed the application of these compounds as catalysts in redox reactions. There is a great interest in the catalytic properties of iron(II/III) tetraazaporphyrins, which dates back to the 1980s. These macrocyclic systems were considered as potential electron

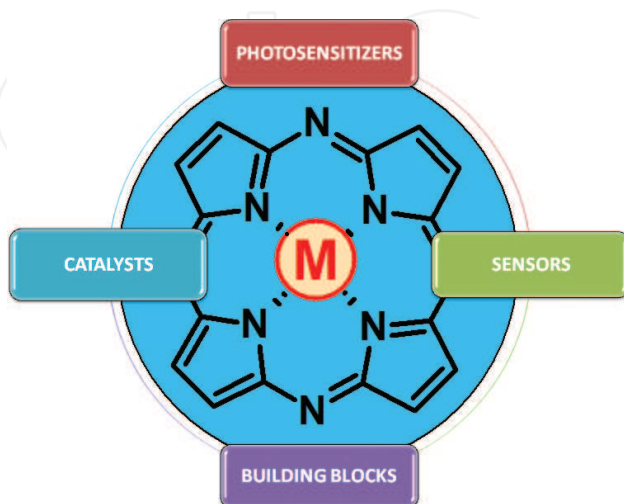

**Figure 2.** The main practical and potential applications of tetraazaporphyrins, M—metal ion.

and/or molecule carriers. For example, iron(III) octaphenylporphyrazine pyridine adduct developed by Stuzhin was found to be a molecular oxygen carrier [20]. Theoretical calculations using density functional theory (DFT) and experimental studies indicated that there are significant differences between metalated tetraazaporphyrins and porphyrins. The difference in the core size and shape of the macrocycle has a substantial effect on the electronic structure and properties of the overall system. DFT calculations indicated on differences in bond lengths between pyrrole/indole nitrogen atoms and coordinated iron(II) cation in porphyrins, phthalocyanines and porphyrazines, which were 1.98; 1.93 and 1.90 Å, respectively. The smaller coordination cavity results in a stronger ligand field in Pzs than in porphyrins. However, the benzo annulation in phthalocyanines produces a surprisingly strong destabilizing effect on the metal-macrocycle bonding [21, 22]. The calculations also showed how the differences in porphyrinoid (Ps, Pcs and Pzs) structures influence the axial ligand coordination of pyridine and CO to the iron(II) complexes [22].


## 2. Physicochemical properties of iron porphyrazines and phthalocyanines

### 2.1. Low solubility and tendency to form aggregates hampering utilization

Applications of porphyrazines and phthalocyanines in science and technology are limited by their low solubility in water and organic solvents and their tendency to form aggregates. These unwelcome features are the result of their likelihood to molecular interactions based on  $\pi$ - $\pi$  stacking. Unfavorable common feature of iron(II/III) porphyrazines and phthalocyanines to form aggregates is mainly related to their conjugated, extended system of  $\pi$ -electrons and an ability of iron cation to coordinate compounds with heteroatoms. Annulation of a porphyrazine macrocyclic system with four benzene rings leads to a phthalocyanine with four indole rings of enhanced aggregation properties. Most of the iron(II/III) tetraazaporphyrins form two types of aggregates: *J*-type aggregates (*head to tail*) or *H*-type aggregates (*face to face*) [23, 24]. In addition, it was also observed that an incorporation of bulky substituents into iron(II) porphyrazine ring, which resulted in the separation of molecules at the distance of ca. 11 Å in the X-ray structure, did not prevent its tendency to form aggregates in solution [25].

Generally, the unsubstituted tetraazaporphyrins possess low solubility. For this reason, the most effective method applied for increasing their solubility is peripheral functionalization. Peripheral functionalization of these compounds with ester groups is able to increase their solubility in many organic solvents. For example, magnesium(II) porphyrazine with 4-hydroxybutylthio substituents was subjected to esterification reaction with 4-biphenylcarboxylic acid and further metalated with Fe<sup>2+</sup> salt toward **1** (Figure 3). Unlike the parent demetalated porphyrazine, the metalated porphyrazines functionalized with eight ester groups were soluble in common organic solvents, such as chloroform, dichloromethane, tetrahydrofuran, acetone, and toluene and were insoluble in water and *n*-hexane [23].

Peripheral functionalization of iron(II/III) porphyrazines and phthalocyanines with halogen electron withdrawing groups (like -F or -CF<sub>3</sub>) was found to improve their solubility in polar solvents like methanol or ethanol, ionization potential and their stability in catalytic

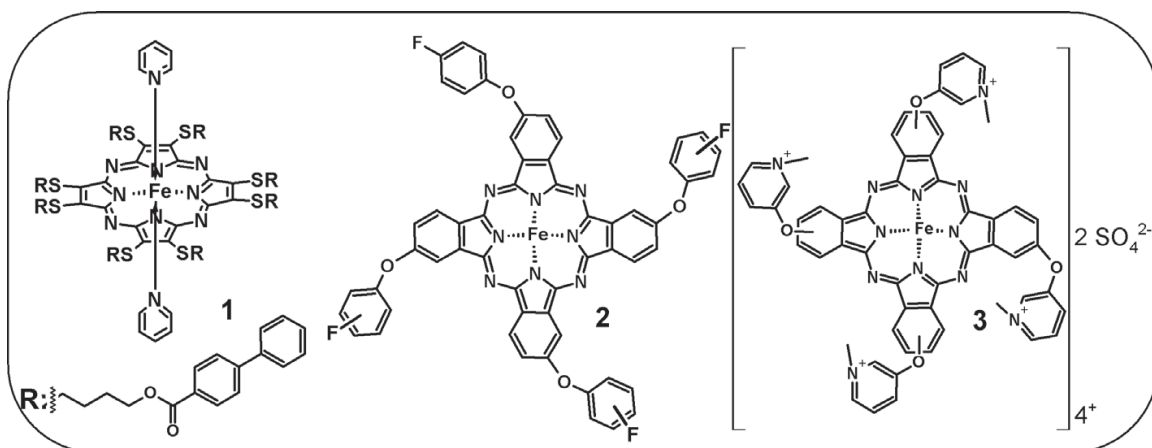

**Figure 3.** Structures of porphyrazine **1** and phthalocyanines **2** and **3**.

oxidation reactions [24, 26]. For example, iron(II) phthalocyanine with peripheral 4-fluorophenoxy groups **2** (**Figure 3**), which was synthesized using microwave-assisted cyclotetramerization (much faster in comparison to classical method), revealed very good solubility in various organic solvents, thus allowing solvatochromic measurements. Unfortunately, this phthalocyanine formed *H*-aggregates as compared to demetalated phthalocyanine and other metalated phthalocyanines (CuPc, Li<sub>2</sub>Pc), especially in polar solvents [24].

Over the years, many methods have been developed in order to obtain soluble tetraazaporphyrins and to utilize them in aqueous media. This was a big challenge because as presented above these macrocycles are known for their aggregation properties. For this reason, a study was performed aiming to incorporate macrocycles into larger structures like  $\beta$ -cyclodextrines ( $\beta$ -CDs). For example, such complexes of  $\beta$ -CDs and iron(II) phthalocyanine **3** with peripheral quaternary pyridinium salt substituents were obtained in Kobayashi group (**Figure 3**) [27]. It is worth noting that the quaternization reaction was performed to enhance water solubility. The addition of  $\beta$ -CD to the aqueous solution of **3** disturbed the monomer-dimer equilibrium, as was seen by an increase in the monomer band and a decrease in the dimer band absorbance in the UV-Vis spectrum. This inclusion complex was deposited on a glassy carbon electrode. In the cyclic voltammetry studies in aqueous solution, **3** revealed very good ability toward oxygen reduction reaction (ORR) at low potential values. It indicates that the “host” compound ( $\beta$ -cyclodextrine) has no influence on physicochemical properties of the “guest” compound (macrocycle).


## 2.2. Advanced physicochemical features

Iron cation coordinated inside a macrocyclic core of porphyrazines and phthalocyanines can be involved in redox reactions and influence their electrochemical properties. By changing the valence of central iron(II/III) metal cation in tetraazaporphyrins, it is possible to transfer electrons on diverse molecules. This feature concerns also axially coordinated compounds, which form enhanced complexes and can be divided into two types. To the first group belong small ions or molecules with heteroatoms in their structure, like pyridine, pyrazine or hydroxyl and bisulfate anions. The obtained complexes are formally named as the axial

complexes. To the second group belong dimers with single atom bridging groups between two iron macrocycles. In both cases, the obtained molecules have modified optical and electrochemical properties [28, 29].

A coordination of iron cation with proper ligand results in the formation of five- or six-coordinated macrocyclic complexes, which were subjected to broad study by Stuzhin et al. [28]. The coordination of iron(II) tetraazaporphyrins with axial ligands leads to the oxidation of iron(II) to iron(III). In this way, iron(II) octaphenylporphyrazine coordinated axially with  $F^-$ ,  $Cl^-$ ,  $Br^-$ ,  $I^-$  and  $HSO_4^-$  anions was transformed to five-coordinated iron(III) complex **4** (Figure 4) [28, 30]. The spin state of the iron in this type of complex, which was evidenced for chloride complex, depended mainly on the nature of both the macrocyclic and axial ligands. In addition, when iron porphyrazine was coordinated with pyridine, the macrocyclic ligand adopted an intermediate structure between common porphyrins and phthalocyanines [30]. Iron(II) porphyrazines reversibly bind a variety of neutral ligands such as THF, nitrogenous bases, and carbon monoxide. This fact can be related to the higher  $\pi$  acidity of the porphyrazine ligand as compared to the porphyrin ligand. Iron(II) porphyrazine demonstrates no affinity for molecular oxygen, which can be a result of positively shifted III/II redox couple potential [31].

Another group of complexes, six-coordinated iron(II) complexes called bisaxial complexes also constitute a large group of compounds. DMSO, pyridine and pyrazine are one of the most often utilized molecules for coordination of iron cation, thus forming adducts as it was studied for iron(II) tetrakis(thiadiazole)porphyrazine **5** in Ercolani and Stuzhin groups (Figure 4) [32]. Coordinated bidentate molecules, for example, pyrazine, can be used as linkers between two or more macrocycles forming bridged complexes. What is more, the axial ligation of metalated Pz derivative with chloride influenced the Q-band absorption, which was the result of change in the symmetry from  $D_{4h}$  to  $C_{4v}$  [23]. FT-IR studies of iron(II) porphyrazine complex **5** axially coordinated with DMSO showed that two Fe-O coordination bonds

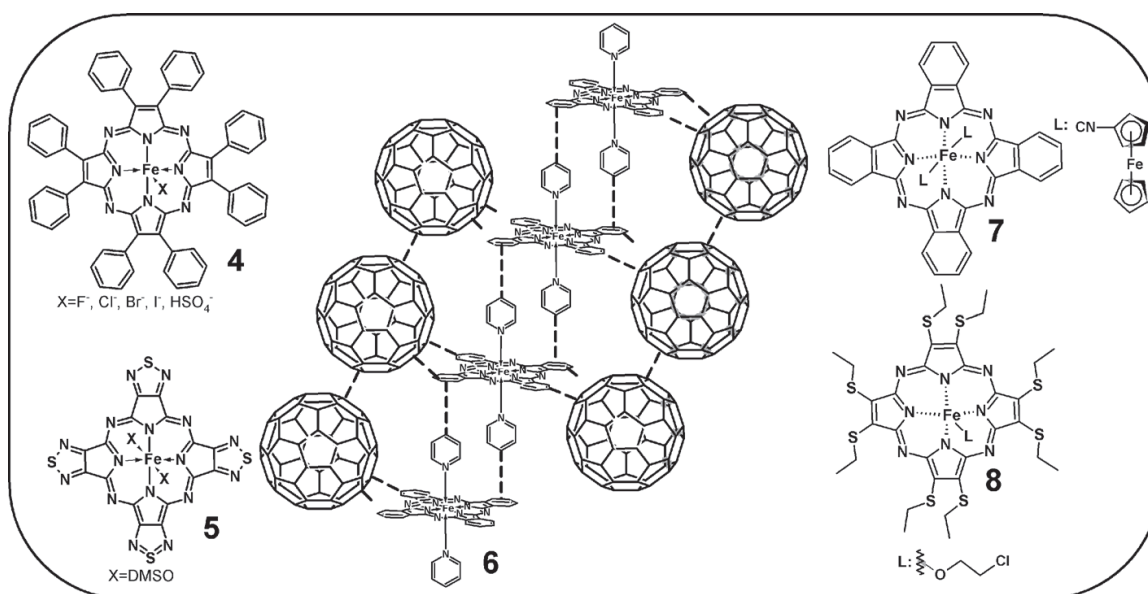

**Figure 4.** Chemical structures of iron(III) octaphenylporphyrazine **4**, iron(II) tetrakis(thiadiazole)porphyrazine **5**, crystal structure of **6**, phthalocyanine trinuclear molecular wire **7** and iron(III) porphyrazine **8**.


were formed. However, in phthalocyanines, analogical process was based on Fe-S coordination bond formation. It indicates that porphyrine **5** is stronger  $\pi$ -acceptor [32].

Iron(II) phthalocyanines demonstrate the ability to form coordination assemblies with large structures like neutral and negatively charged fullerenes. An interesting example is crystal of **6** (**Figure 4**) obtained by cocrystallization from *n*-hexane and composed of fullerenes C<sub>60</sub> and unsubstituted iron(II) phthalocyanines axially ligated with pyridines. In the structure of **6**, there are  $\pi$ - $\pi$  stacking interactions, which do not affect the geometry of iron(II) phthalocyanine [33]. Thus, metal phthalocyanines can be involved simultaneously in molecular complexes with fullerenes as coordination assemblies and with the addition of axial ligands. Another example is trinuclear complex **7** (**Figure 4**) involving two isocyanoferrrocene ligands axially coordinated to iron(II) phthalocyanine. The structure **7** forms a molecular wire between iron cation from phthalocyanine and two iron ions from ferrocenes. However, there is weak electronic communication present between two iron centers of the ferrocene ligands despite a relatively large distance (11.5 Å) [34].

An improvement in synthetic methods from the late 1980s allowed the obtaining of iron(II/III) porphyrine and phthalocyanine complexes able to form dimers of macrocycles bridged by oxygen, nitrogen or carbon atoms ( $\mu$ -oxo,  $\mu$ -nitrido and  $\mu$ -carbido dimers, respectively). Electrochemical studies demonstrated that macrocyclic ligand can influence the redox behavior of the binuclear complex. According to Colomban et al., dimer consisting of two porphyrines possesses intermediate properties between corresponding porphyrin and phthalocyanine dimers [29]. This statement is based on the observation that the values of half-waved oxidation potentials of porphyrine dimer were in the middle between similar phthalocyanine and porphyrin potentials, and for this reason, oxidation potentials in porphyrine-based complexes are closer to phthalocyanines than porphyrins. Cyclic voltammetry of monomeric iron(III) porphyrine axially ligated with 2-chloroethoxy substituent **8** (**Figure 4**) and its  $\mu$ -oxo dimer demonstrated in DMF/TBAP three and six redox processes, respectively. Thus, the redox behavior of  $\mu$ -oxoporphyrine dimer differs significantly not only from that of the small ring system of  $\mu$ -oxoporphyrin dimer, but also from that of the large-ring based  $\mu$ -oxo dimer of phthalocyanine [35]. Compound **8** was also used for thin film formation utilizing Langmuir-Schaefer (LS) technique (horizontal lifting) following the study presented by Garramone et al. [36]. In aqueous solution, the  $\mu$ -oxo dimer was formed as a predominant component (prevalent molecular building block) of LS films. The obtained LS-Fe films showed remarkable changes in the UV-Vis spectra, which are consistent with a significant  $\mu$ -oxo dimer to monomer conversion [36]. The studies on  $\mu$ -oxo iron phthalocyanine dimer demonstrated that according to the reaction conditions, it is possible to obtain bent or linear Fe-O-Fe structures (with Fe-O-Fe angle up to 300°). These two forms were identified by FT-IR signals from Fe-O antisymmetric stretching vibration. Moreover, it was possible to transform bent into linear form by applying the following reaction conditions: (i) by adding of 2-propylamine to compound suspended in chloronaphthalene or (ii) by the mixing the compound in the saturated H<sub>2</sub>SO<sub>4</sub> solution in the presence of oxygen [37].

In comparison with well-known classic alone atop the other dimer structures, there is an example of significantly different "side-by-side" dimer structure **9** (**Figure 5**), which was considered as a novel molecular QCA (*quantum-dot cellular automata*) cell [38]. This dimer has



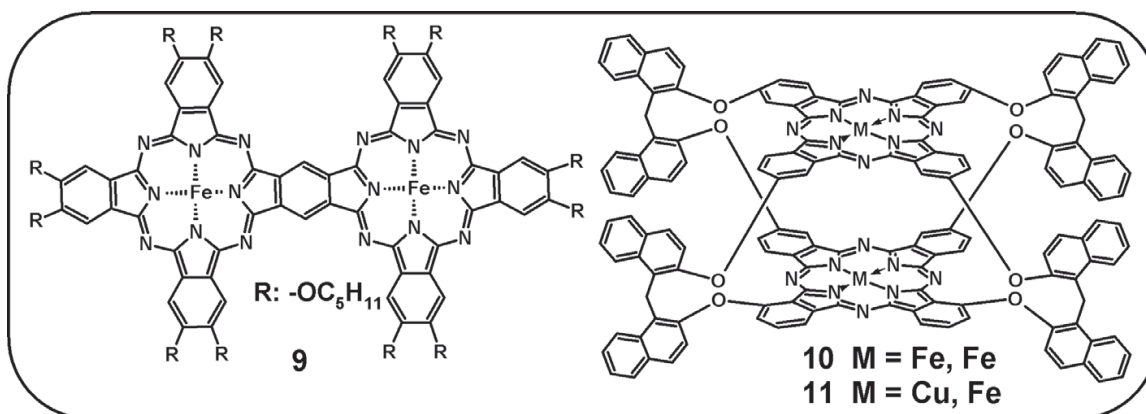

**Figure 5.** Structure of side-by-side dimer **9** and homonuclear and heteronuclear dimers **10** and **11**.


pentylloxy substituents in the periphery, which results in its high solubility in organic solvents. The investigation of the redox properties of **9** in electrochemical study indicated that its oxidized and reduced mixed-valence complexes were stable [38]. Another of two tetraazaporphyrin macrocycles conjugated peripherally by 4,4'-[1,1'-methylenebis-(naphthalene-2,1-diyl)] bis(oxy)diphthalonitrile linker constitutes homonuclear (Fe-Fe) **10** and heteronuclear (Fe-Cu) **11** ball-type compounds (**Figure 5**). In both compounds, two phthalocyanine units were rigidly bound at two sides with four linking arms to form intramolecular cofacial coupling in which the splitting of the classical monophthalocyanine redox processes was observed in a cyclic voltammetry study. Moreover, the nature of the metal centers affected the distance between two Pc units in both ball-type complexes and thus the extent of the mentioned intramolecular cofacial interactions between them [39, 40].

### 3. Catalytic activity and electrochemical properties of iron porphyrines and phthalocyanines

The presence of iron(II/III) cation in the coordination center of porphyrine and phthalocyanine macrocycles determines the possibility of using them as catalysts of the oxidation-reduction reactions. Research studies carried out for several years showed that the iron tetraazaporphyrins are efficient catalysts as compared to the structurally similar porphyrin compounds. Porphyrinoid catalysts, also called biomimetic catalysts, are also more effective in carrying out the oxidation reactions of organic compounds, in comparison with other catalysts. It is related to the increased influence of the electron-donor effect of the ferric cation, which is conjugated to the  $\pi$ -electron system of the macrocyclic ring. The advantages of iron(II/III) porphyrines and phthalocyanines as catalysts include high selectivity, mild and environmentally friendly reaction conditions and low energy consumption during catalysis [41]. In an early 1990s, Fitzgerald et al. provided various studies indicating significant differences in physicochemical properties of Ps, Pcs and Pzs possessing the same peripheral substituents and iron(III) cation inside a macrocyclic core [42]. It was suggested that porphyrines are stronger  $\sigma$ -donors and  $\pi$ -acceptors than porphyrins. The electrochemical

studies indicated that similarly to phthalocyanines, porphyrazines have positively shifted redox potential of 400 mV in comparison with their porphyrin analogues. Moreover, Pzs are more soluble in organic solvents than structurally relevant Pcs and can split the d orbitals of coordinated metal to a greater extent than Ps. In conclusion, it was suggested that, due to the high solubility in organic solvents, accompanied by coordination of metal ions with unusual spin states, and positively shifted redox potentials, Pzs can be considered as more efficient catalysts in comparison with Ps and Pcs [42]. Taking all this into account, iron(II/III) tetraaza-porphyrins became an object of intense studies aimed at obtaining macrostructures with increased catalytic abilities. For instance, large structures like porphyrin-phthalocyanine pentads composed of five fused macrocyclic compounds **12** were even synthesized by Kobayashi et al. (**Figure 6**) [43]. Noteworthy is that the bimetallic Fe-Cu complexes, like metal-linked face-to-face porphyrazine dimer **13** with an increased strong metal-metal spin coupling, were obtained by Barrett, Hoffman and their coworkers [44].

Iron(II/III) porphyrazines and phthalocyanines are active in redox reactions and, therefore, reveal high electrochemical activity. This feature was confirmed by cyclic voltammetry (CV) and square wave voltammetry (SWV) studies, which show, in most cases, four reversible or quasi-reversible oxidation and reduction peaks. The origin of the two peaks was attributed to reactions associated with the presence of iron cation, whereas the other two are the

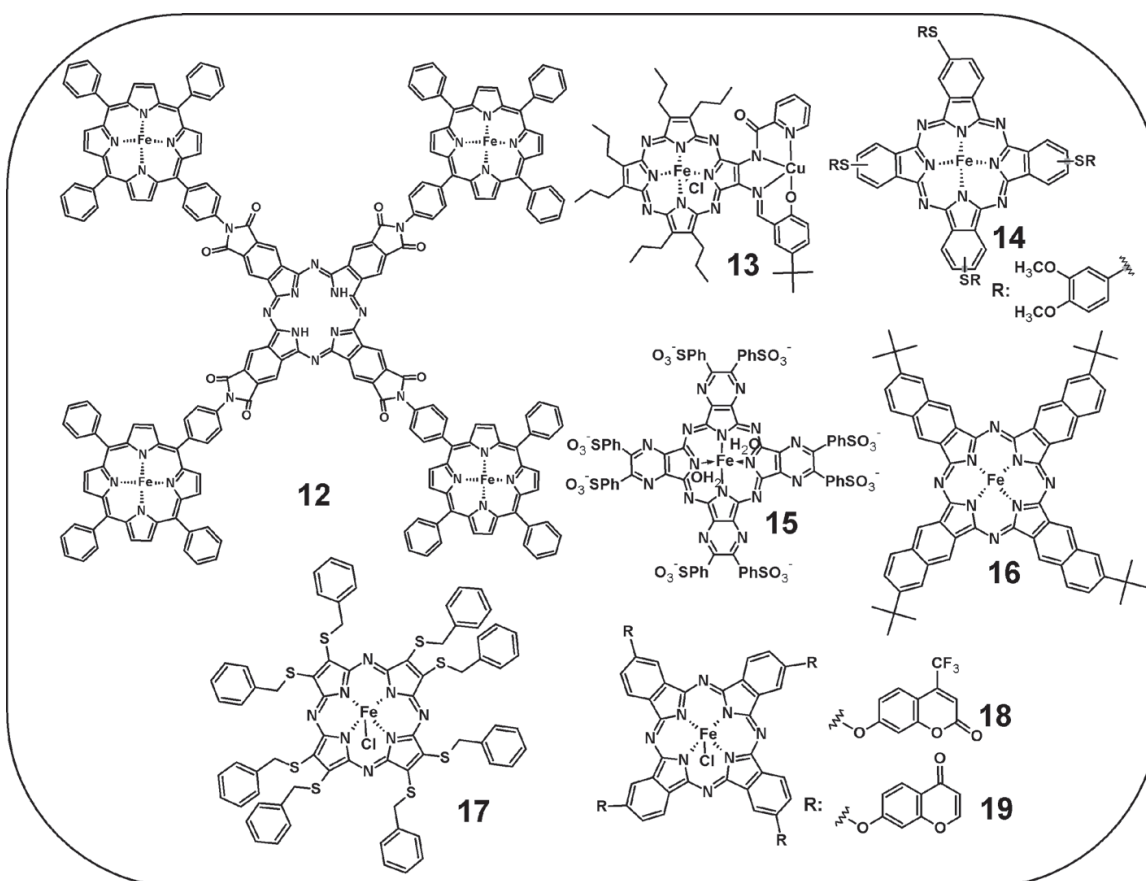

**Figure 6.** Structures of pentad **12**, bimetallic complex **13**, iron(II) phthalocyanine **14** and porphyrazine **15**, iron(II) naphthalocyanine **16**, iron(III) porphyrazine **17** and iron(III) phthalocyanines **18** and **19**.

result of the electronic processes within the macrocyclic ring [45]. However, there are some exceptions to this rule. For example, in the CV study performed in organic solvents for iron(II) phthalocyanine **14** (Figure 6), the presence of six oxidation-reduction processes was observed. Two of them were identified as reversible and irreversible reductions, while the other two were found to be quasi-reversible oxidation reactions [46]. In contrast to other iron porphyrazines, cyclic voltammetry study of water-soluble iron(II) porphyrazine **15** revealed no peaks observed for the  $\text{Fe}^{\text{II}}/\text{Fe}^{\text{I}}$  couple, probably as a result of slow heterogeneous electron transfer kinetics for this couple. Moreover, replacing of water in the coordination sphere of **15** by N-donor ligands increases the extinction coefficients of both the Q and Soret bands with a blue shift of the first one [47].

Electrochemical properties of iron(II/III) porphyrazine and phthalocyanine complexes are influenced by the periphery of the macrocycle, which can lead to an increase or a decrease of their electrochemical activity. An increase in activity is related to the presence of the peripheral substituents with lone pairs of electrons or  $\pi$ -electron systems, which are able to increase the coupling of electrons around the macrocycle. The decrease in activity is observed in the presence of electrochemically inactive substituents, for example, *tert*-butyl groups, as was found for iron(II) naphthalocyanine **16** (Figure 6) [48].

An axial coordination of molecules to the central metal ion can cause a shift of the oxidation potential of the macrocycle or a split of peaks belonging to oxidation process. The rationale for this may be connected with the coordination of solvent molecules to  $\text{Fe}^{3+}$  cation in the center of the oxidized macrocyclic compound [49]. It is known from the literature that there are differences in the values of oxidation-reduction potentials of iron phthalocyanines, when one or two solvent molecules are attached or released from the iron(II/III) cation [50].

Electrochemical studies with iron porphyrazines and phthalocyanines were also carried out using the modified electrodes with tetraazaporphyrins deposited on their surface. One example is the use of iron(III) porphyrazine **17** (Figure 6) as an azide and nitrate(III) anions sensor [51]. This porphyrazine was deposited onto a matrix with PVC, and the selective electrode membrane revealed a shorter electrode response time, greater tolerance within a wide range of pH at high analyte concentration and a high selectivity toward the targeted ions [51]. Another example is iron(III) phthalocyanine with four peripheral coumarin **18** or chromone **19** substituents (Figure 6) deposited by the electropolymerization on the Pt-working electrodes and applied as electron mediators in the electrocatalytic oxidation of nitrates(III) [52].

Studies concerning catalytic properties of iron porphyrazines and phthalocyanines have been conducted over the last 20 years, and they concerned mostly the potential applications in oxidation reactions of linear and cyclic alkenes as well as photocatalytic degradation of organic dyes. However, unsubstituted iron(III) phthalocyanine was widely used to catalyze the reaction of both the incorporation of amino substituents and the hydroxylation of aryl and alkyl molecules [53, 54]. Moreover, this compound was also used as a catalyst in the oxygen reduction reactions and revealed good stability for potential use in fuel cells or batteries [55, 56]. Some studies assessed the ability of iron(II/III) tetraazaporphyrins and their dimers in decomposition and removal of organic pollutants from industrial wastes. So far the most successfully applied photocatalytic reaction was the degradation of Rhodamine B,

which was considered as a model compound in studies on environmental contamination with organic substances. The most commonly used catalysts applied were symmetrical iron sulfanylporphyrazines **20**, **21** and **22**, as well as unsymmetrical **23** (Figure 7). They were used either as homogeneous or heterogeneous catalysts, after deposition on the carrier, which was very often ion exchange resin (e.g., Amberlite CG400). It was shown that the deposition of the catalyst on this kind of support increases the efficiency of catalytic reactions due to an increase in the concentration of catalysts on the resin surface. Therefore, the molecules of the substrate are present in high concentration in the vicinity of the catalyst, facilitating the oxidation and reduction reactions. In addition, it was shown that the iron(II) porphyrazine–resin system is active even in the dark, without activation of macrocycle by irradiation with proper wavelength [57]. Noteworthy, some oxygen atom donors (OAD) like molecular oxygen and hydrogen peroxide were added to the reaction mixture to form an active oxygen species, which allowed the oxidative degradation of substrates. The highest reaction rate and yield were achieved with H<sub>2</sub>O<sub>2</sub> [58]. It was also noticed that the modification of peripheral groups of the macrocycle by introducing hydroxymethyl substituents demonstrated an increased solubility of the catalyst in water and in organic solvents [41]. In order to improve the catalytic properties, the structure of the macrocycle was equipped with electron donor methyl moieties [59].

Another sulfur iron(II) porphyrazine **24** (Figure 7) was used in the catalytic oxidation reaction of organic compound, that is, X3B dye (*Reactive Brilliant Red*). The reaction was provided with hydrogen peroxide as OAD and with simultaneous exposure to light. The catalyst was active in a broad temperature and pH range, with the best yield at pH = 2, and at the higher


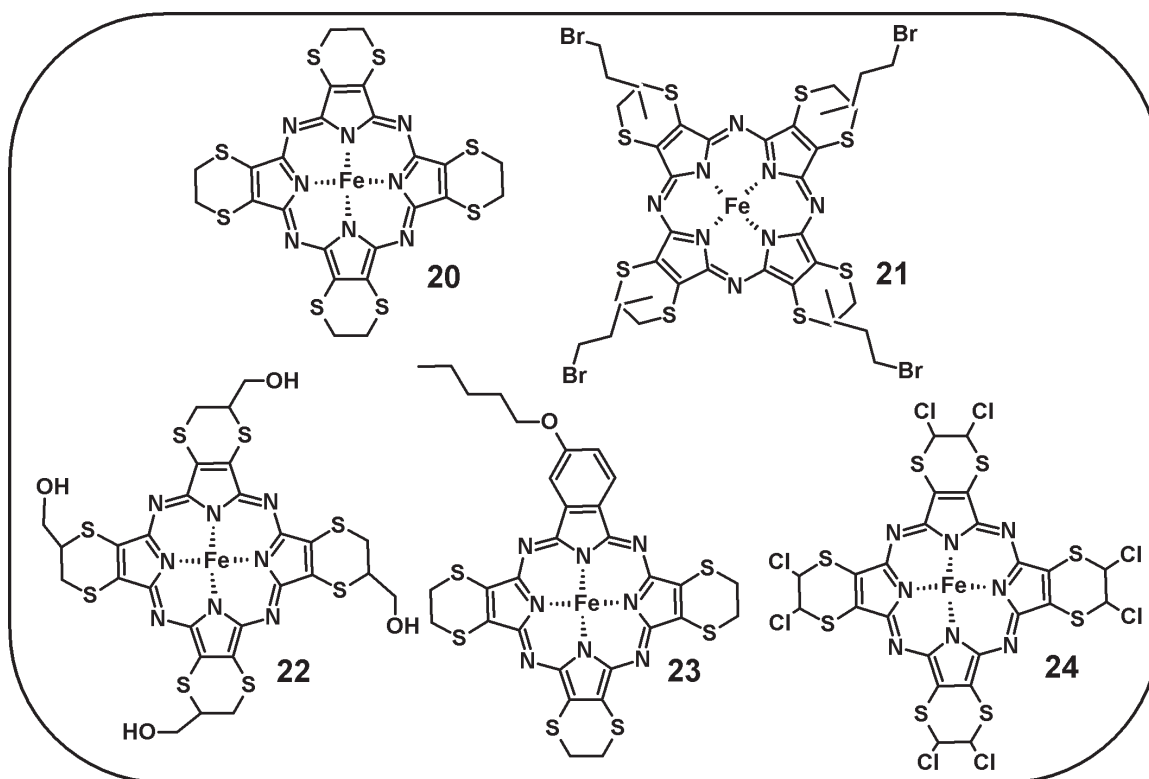



Figure 7. Chemical structure of iron(II) sulfanylporphyrazines 20–24.

temperature. Lower catalytic ability was observed in the absence of light. It has been shown that the use of  $\text{H}_2\text{O}_2$  as a source of oxygen resulted in the production of hydroxyl radicals as reactive oxygen species responsible for degradation of the substrate in the catalytic reaction. This process was called catalytic wet hydrogen peroxide oxidation (CWPO) and has potential for treatment of waste water [60]. As a result of research by Su et al. [61] and Theodoridis et al. [62], it was found that for the application of  $\text{H}_2\text{O}_2$  as a commonly used oxygen atom donor in oxidation reactions catalyzed by iron(II) porphyrazine results in the hydroperoxo complex of iron(III) Pz formation. According to the reaction conditions there are two competitive redox routes: heterolysis (involving transfer of 2 electrons) and homolysis (1 electron transfer) leading to O–O bond cleavage (**Figure 8**). At acidic conditions, proton is utilized in heterolysis of O–O bond and transient high-valence iron-centered oxidizing species  $\text{Pz}^+\text{Fe}^{\text{IV}}=\text{O}$  is generated as the reactive oxygen species (ROS). Of note is that the electronic structure of N4-ligand complexes allows for the stabilization of transient high-valent intermediates. For this reason, high-valence state iron species are often identified as ROS in biomimetic catalysis. On the other hand, homolysis of O–O bond in neutral and alkaline pH conditions leads to hydroxyl radical species formation as ROS, whereas the hydroperoxo complex of porphyrazine is transformed to porphyrazine radical  $\text{Fe}^{\text{III}}=\text{O}^\bullet$  [61].

Another important objective for the application of iron phthalocyanines and porphyrazines as catalysts of the oxidation reactions of organic compounds is their use in chemical synthesis, which leads to new derivatives without using classical synthetic routes. The presence of Fe(II/III) tetraazaporphyrins with the use of suitable oxygen donors permits one or two electron oxidation reactions. As the result, various derivatives containing epoxy groups or hydroxyl, carbonyl and carboxyl substituents can be obtained. In the study aiming to assess catalytic properties of iron porphyrazines and phthalocyanines, cyclohexane was considered as a reference compound. In various studies, there were applied iron(II) phthalocyanine derivatives **25–27** and iron(III) phthalocyanine **28** as catalysts (**Figure 9**) and also diverse sources of oxygen: *tert*-butylhydroperoxide (TBHP), hydrogen peroxide, chloro-peroxybenzoic acid (m-CPBA), molecular oxygen and oxone. It was concluded that with an increase in temperature and catalyst concentration, an increase in reaction yield was observed. The source of

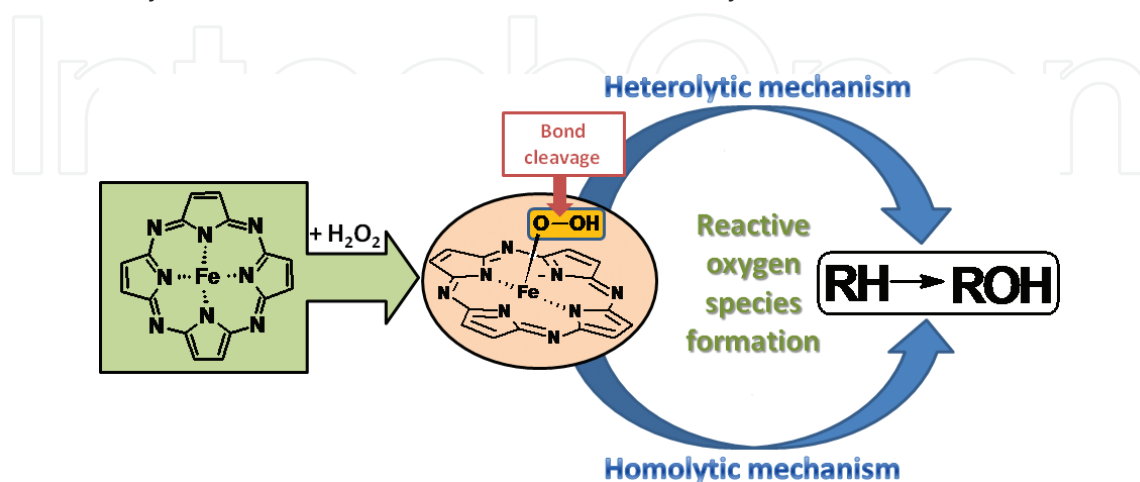

**Figure 8.** The heterolytic and homolytic mechanisms of O–O bond cleavage in the hydroperoxo complex of iron(III) porphyrazine following [61].

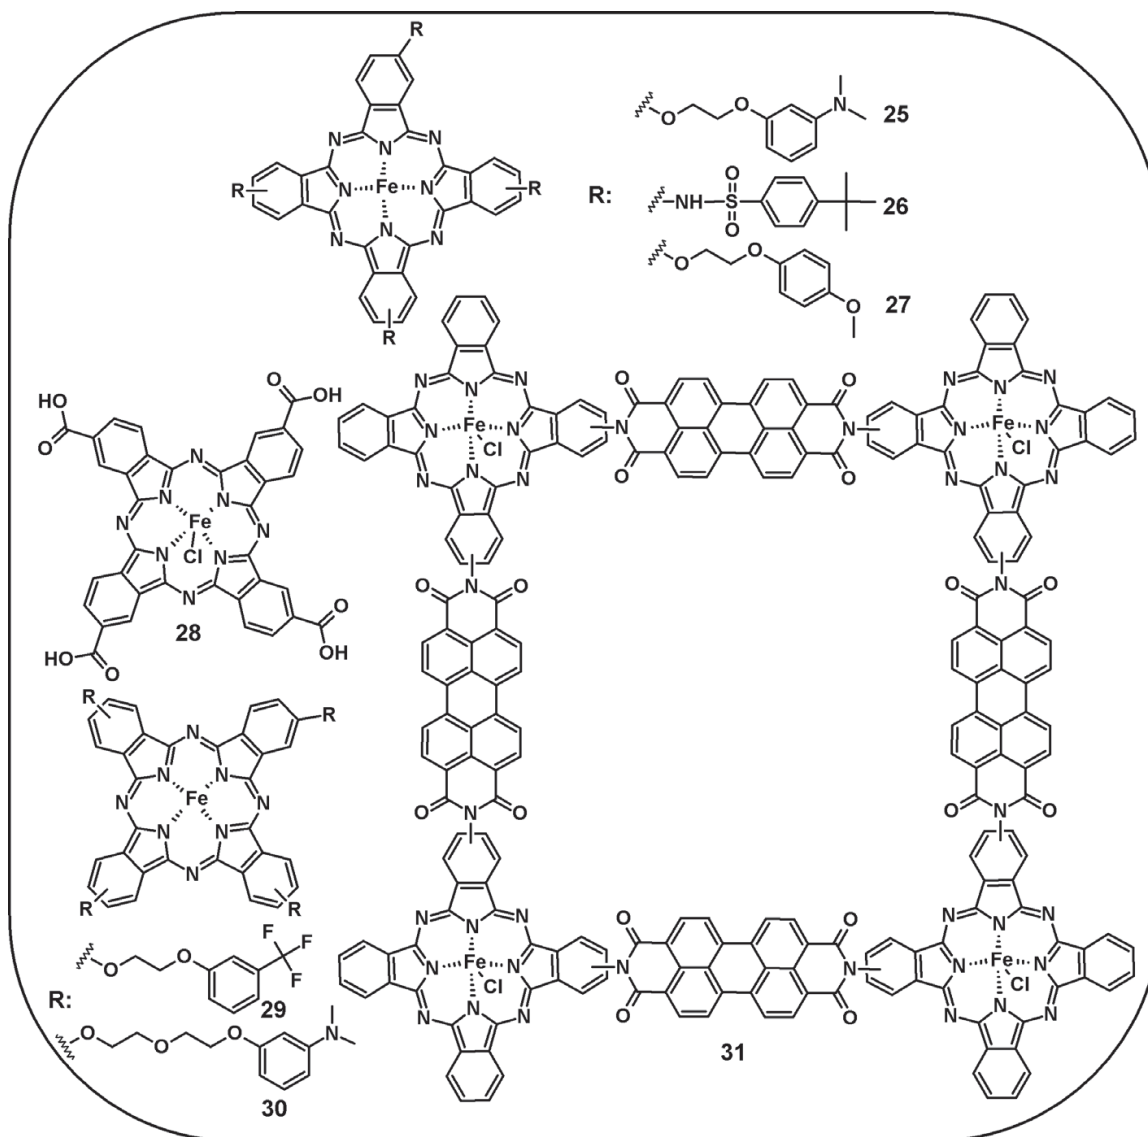

**Figure 9.** Structures of iron(II/III) phthalocyanine derivatives 25–30, and cyclic tetramer 31.

oxygen influenced the structures of obtained products. In all experiments monitored by the UV-Vis spectra, the degradation of the catalysts, manifested by a decrease of their Q-band absorption, was observed. However, in most cases, the catalytic processes proceeded, even after catalyst degradation, which can indicate the influence of other oxidation mechanisms, for example, Fenton reaction [63–66].

Lately performed study with iron(II) phthalocyanine, **29**, **30**, and the cyclic tetramer consisting of iron(III) phthalocyanine linked to 3,4,9,10-perylenetetracarboxylate, tentatively named FePPOP **31** (**Figure 9**) indicate the possibility to use these compounds toward catalytic oxidation reaction of benzyl alcohol. In the case of tetramer, it was found that **31** exhibited high stability and also exhibited the large turnover number of the reaction reaching the value of 960 [67–69]. However, in the initial phase of the experiment, the catalyst **31** acted much slower in comparison with the other compounds [69]. In addition, heterogeneous catalysts consisting

of unsubstituted iron(II) phthalocyanines deposited on the electrodes by electropolymerization were applied in oxidation reactions of organic compounds. Such reactions were carried out in two kinds of systems: (i) phenolic resin/unsubstituted iron(II) phthalocyanine or (ii) the phenolic resin/structurally branched iron(II) phthalocyanine [70, 71]. In another study, various thiol derivatives (e.g., 2-mercaptoethanol) were applied as substrates in electrooxidation reaction toward disulfides. Transparent indium tin oxide electrodes were modified with iron(II) tetraaminophthalocyanine [72, 73].

#### 4. Summary

The iron(II/III) porphyrines and phthalocyanines have interesting electrochemical properties, which were demonstrated in many valuable studies performed during the last 30 years. Moreover, many applications of these macrocycles were presented in medicine, in biomedical and analytical fields, in materials chemistry as well as in chemical synthesis. It clarifies why catalytic abilities of iron(II/III) tetraazaporphyrins became an object of intense studies. This chapter aimed to summarize the influence of peripheral substituents of iron(II/III) porphyrines and phthalocyanines on their spectral and electrochemical properties. Electrochemical properties of iron(II/III) porphyrine and phthalocyanine complexes are significantly influenced by the periphery of the macrocycle, which can lead to an increase or a decrease of their electrochemical activity. Similarly, an axial coordination of molecules to the central metal ion causes a shift of the oxidation potential of the macrocycle or splits peaks belonging to oxidation processes. Selected studies on iron(II/III) porphyrines and phthalocyanines were found not only to present their interesting physicochemical features but also further perspective applications, and thus, they were discussed in more detail. What is of immense value for further applications of these molecules in materials chemistry and nanotechnology is that some macrocycles demonstrated an ability to form coordination assemblies alone or with nanostructures, including fullerenes, and molecular wires. Especially interesting are binuclear complexes based on iron(II/III) porphyrine and phthalocyanine bridged by oxygen, nitrogen or carbon atoms. Interesting modification of classical redox processes was observed in novel potential molecular quantum-dot cellular automata cells in which phthalocyanines were connected "side-by-side" or by forming ball-type dimers in which there were utilized sophisticated linkers binding two phthalocyanine units at two sides rigidly with four linking arms. Porphyrinoid catalysts also have the designation by biomimetic catalysts, this being because they are more effective in carrying out the oxidation reactions of organic compounds to other catalysts. It is related to the increased electron-donor effect of the ferric cation, which is conjugated to the  $\pi$ -electron system of the macrocyclic ring. The advantages of iron(II/III) porphyrines and phthalocyanines as catalysts include high selectivity, mild and environmentally friendly reaction conditions and low energy consumption during catalysis. Studies of catalytic properties of iron(II/III) Pzs and Pcs concerned mostly with their potential applications in oxidation reactions of linear and cyclic alkenes as well as photocatalytic degradation of organic dyes. Some studies assessed the ability of iron(II/III) tetraazaporphyrins and their dimers in decomposition and removal of organic pollutants from industrial wastes. A huge

area for further application of these macrocycles results from the electrochemical studies in which iron Pzs and Pcs were deposited on the surface of electrodes and further applied as selective anions sensors. To sum up, iron(II/III) tetraazaporphyrins appear to present many interesting perspectives for biomedical and technological applications.

## Acknowledgements

Authors thank the National Science Centre, Poland, for funding (grant no. 2015/17/N/NZ7/009 43).

## Author details

Tomasz Koczorowski, Wojciech Szczolko and Tomasz Goslinski\*

\*Address all correspondence to: [tomasz.goslinski@ump.edu.pl](mailto:tomasz.goslinski@ump.edu.pl)

Department of Chemical Technology of Drugs, Faculty of Pharmacy, Poznan University of Medical Sciences, Poznan, Poland

## References

- [1] Michel SLJ, Hoffman BM, Baum SM, Barrett AGM. Peripherally functionalized porphyrines: novel metallomacrocycles with broad, untapped potential. In Karlin KD ed. *Prog. Inorg. Chem. J. Wiley & Sons.* 2001;50:473-590. doi:10.1002/0471227110.ch8
- [2] Rodríguez-Morgade MS, Stuzhin PA. The chemistry of porphyrines: an overview. *J. Porphyr. Phthalocya.* 2004;8:1129-1165. doi:10.1142/S1088424604000490
- [3] Smith KM. *Comprehensive heterocyclic chemistry.* In: Katritzky AR, Rees CW (Eds.). Pergamon, Oxford. 1984;4:377-442.
- [4] Aviv-Harel I, Gross Z. Coordination chemistry of corroles with focus on main group elements. *Coord. Chem. Rev.* 2011;255:717-736. doi:10.1016/j.ccr.2010.09.013
- [5] Ishii K. Functional singlet oxygen generators based on phthalocyanines. *Coord. Chem. Rev.* 2012;256:1556-1568. doi:10.1016/j.ccr.2012.03.022
- [6] Kryjewski M, Goslinski T, Mielcarek J. Functionality stored in the structures of cyclodextrin-porphyrinoid systems. *Coord. Chem. Rev.* 2015;300:101-120. doi:10.1016/j.ccr.2015.04.009
- [7] Piskorz J, Goslinski T, Mielcarek J. Research in the field of azaanalogues of porphyrins and their application in pigment industry. *Przem. Chem.* 2014;93:1855-1858. doi:10.12916/przemchem.2014.1855



- [8] Zhong C, Zhao M, Goslinski T, Stern C, Barrett AGM, Hoffman BM. Porphyrazines peripherally functionalized with hybrid ligands as molecular scaffolds for bimetallic metal-ion coordination. *Inorg. Chem.* 2006;45:3983-3989. doi:10.1021/ic052169p
- [9] Wierzchowski M, Sobotta L, Skupin-Mrugalska P, Kruk J, Jusiak W, Michael Yee M, Konopka K, Düzgünes N, Tykarska E, Gdaniec M, Mielcarek J, Goslinski T. Phthalocyanines functionalized with 2-methyl-5-nitro-1H-imidazolylethoxy and 1,4,7-trioxanonyl moieties and the effect of metronidazole substitution on photocytotoxicity. *J. Inorg. Biochem.* 2013;127:62-72. doi:10.1016/j.jinorgbio.2013.06.012
- [10] Yano S, Hirohara S, Obata M, Hagiya Y, Ogura S-i, Ikeda A, Kataoka H, Tanaka M, Joh T. Current states and future views in photodynamic therapy. *J. Photochem. Photobiol. C Photochem. Rev.* 2011;12:46-67. doi:10.1016/j.jphotochemrev.2011.06.001
- [11] Sobotta L, Skupin-Mrugalska P, Mielcarek J, Goslinski T, Balzarini J. Photosensitizers mediated photodynamic inactivation against virus particles. *Mini-Rev. Med. Chem.* 2015;15:503-521. doi:10.2174/1389557515666150415151505
- [12] Piskorz J, Skupin P, Lijewski S, Korpusinski M, Sciepora M, Konopka K, Sobiak S, Goslinski T, Mielcarek J. Synthesis, physical-chemical properties and in vitro photodynamic activity against oral cancer cells of novel porphyrazines possessing fluoroalkylthio and dietherthio substituents. *J. Fluorine Chem.* 2012;135:265-271. doi:10.1016/j.jfluchem.2011.12.003
- [13] Kryjewski M, Smigielska A, Goslinski T. Porphyrinoid macrocycles as building blocks for nanoarrays construction. *Przem. Chem.* 2010;89:727-733.
- [14] Shultz AM, Farha OK, Hupp JT, Nguyen ST. A catalytically active, permanently microporous MOF with metalloporphyrin struts. *J. Am. Chem. Soc.* 2009;131:4204-4205. doi:10.1021/ja900203f
- [15] Wöhrle D, Schnurpfeil G, Makarov SG, Kazarin A, Suvorova ON. Practical applications of phthalocyanines—from dyes and pigments to materials for optical, electronic and photoelectronic devices. *Macroheterocycles.* 2012;5:191-202. doi:10.6060/mhc2012.120990w
- [16] Jiang Z, Shao J, Yang T, Wang J, Jia L. Pharmaceutical development, composition and quantitative analysis of phthalocyanine as the photosensitizer for cancer photodynamic therapy. *J. Pharm. Biomed. Anal.* 2014;87:98-104. doi:10.1016/j.jpba.2013.05.014
- [17] Calvete M, Yang GY, Hanack M. Porphyrins and phthalocyanines as materials for optical limiting. *Synth. Met.* 2004;141:231-243. doi:10.1016/S0379-6779(03)00407-7
- [18] Collman JP, Boulatov R, Sunderland CJ, Fu L. Functional analogues of cytochrome c oxidase, myoglobin, and hemoglobin. *Chem. Rev.* 2004;104:561-588. doi:10.1021/cr0206059
- [19] Kocki T, Czarczynska-Goslinska B, Kocka K, Stolarska M, Wachowska D, Lijewski S, Koczorowski T, Goslinski T. Nurses and pharmacists in interdisciplinary team of health care providers in photodynamic therapy. In: Tanaka Y. (Ed.). *Photomedicine*. Intech. 2017.

- [20] Stuzhin PA, Latos-Grazynski L, Jezierski A. Synthesis and properties of binuclear nitride-bridged iron octaphenyltetraazaporphyrin. EPR studies of dioxygen adduct formation. *Transit. Met. Chem.* 1989;14:341-346. doi:10.1007/BF01032506
- [21] Liao M-S, Scheiner S. Comparative study of metal-porphyrins, -porphyrines, and -phthalocyanines. *J. Comput. Chem.* 2002;23:1391-403. doi:10.1002/jcc.10142
- [22] Liao M, Watts JD, Huang M, Box PO, State J, Uni V. FeII in different macrocycles: electronic structures and properties. *J. Phys. Chem. A.* 2005;109:7988-8000. doi:10.1021/jp0581476
- [23] Gonca E. Metal-free, metallo-porphyrines, monomeric bisaxial complex [FePz(py)<sub>2</sub>] and the bridged complex [FePz(py)<sub>2</sub>]<sub>n</sub> with eight (4-thiobutyl-4-biphenylcarboxylate) groups. *J. Coord. Chem.* 2014;67:162-175. doi:10.1080/00958972.2013.867036
- [24] Jung C, Beak B, Kakimoto M. Synthesis of phthalocyanines functionalized by 4-fluorophenoxy moieties and their linear optical properties. *J. Ind. Eng. Chem.* 2014;20:234-237. doi:10.1016/j.jiec.2013.03.042
- [25] Koczorowski T, Szczolko W, Burda K, Nowak M, Dawidowska M, Teubert A, Sobotta L, Gdaniec M, Korecki J, Mielcarek J, Tykarska E, Goslinski T. Influence of bulky pyrrolyl substituent on the physicochemical properties of porphyrines. *Dyes Pigm.* 2015;112:138-144. doi:10.1016/j.dyepig.2014.06.033
- [26] Sugimori T, Horike S, Handa M, Kasuga K. Preparation and some properties of perfluoroalkoxy-substituted phthalocyanine complexes of iron(III), nickel(II) and zinc(II). *Inorg. Chim. Acta.* 1998;278:253-255. doi:10.1016/S0020-1693(98)00104-2
- [27] Tasso TT, Furuyama T, Kobayashi N. Absorption and electrochemical properties of cobalt and iron phthalocyanines and their quaternized derivatives: aggregation equilibrium and oxygen reduction electrocatalysis. *Inorg. Chem.* 2013;52:9206-9215. doi:10.1021/ic4002048
- [28] Stuzhin PA, Mahmud H, Ulrich Z, Iron octaphenyltetraazaporphyrins: synthesis and characterization of the five-coordinate complexes of iron(III) (XFe<sup>III</sup>OPTAP; X=F, Cl, Br, I, HSO<sub>4</sub>). *Inorg. Chim. Acta.* 1995;236:131-139. doi:10.1016/0020-1693(95)04633-K
- [29] Colomban C, Kudrik EV, Tyurin DV, Albrieux F, Nefedov SE, Afanasiev P, Sorokin AB. Synthesis and characterization of  $\mu$ -nitrido,  $\mu$ -carbido and  $\mu$ -oxo dimers of iron octapropylporphyrine. *Dalt. Trans.* 2015;44:2240-2251. doi:10.1039/C4DT03207A
- [30] Stuzhin PA, Mal'chugina OV, Wolowiec S, Latos-Grazynski L, Berezin BD. Formation of stable  $\sigma$ -aryliron(III) complexes from the reaction of chloroiron(III) octaphenyltetraazaporphyrinate with aryl Grignard reagents. *Mendeleev Commun.* 1998;8:143-145. doi:10.1070/MC1998v008n04ABEH000974
- [31] Fitzgerald JP, Lebson JR, Wang G, Yee GT, Noll BC, Sommer RD. Iron tetraanthracenotetraazaporphyrins: synthesis, structural characterization, ligand binding properties, and unexpected selectivity of a bis-"bowl" tetraazaporphyrin. *Inorg. Chem.* 2008;47:4520-4530. doi:10.1021/ic702149z

- [32] Bauer EM, Cardarilli D, Ercolani C, Stuzhin PA, Russo U. Tetrakis(thiadiazole)porphyrazines. 2. Metal complexes with Mn(II), Fe(II), Co(II), Ni(II), and Zn(II). *Inorg. Chem.* 1999;2:6114-6120. doi:10.1021/ic990855g
- [33] Konarev DV, Khasanov SS, Lyubovskaya RN. Fullerene complexes with coordination assemblies of metalloporphyrins and metal phthalocyanines. *Coord. Chem. Rev.* 2014;262:16-36. doi:10.1016/j.ccr.2013.10.021
- [34] Nemykin VN, Purchel A, Spaeth AD, Barybin MV. Probing the electronic properties of a trinuclear molecular wire involving isocyanoferrrocene and iron(II) phthalocyanine motifs. *Inorg. Chem.* 2013;52:11004-11012. doi:10.1021/ic4011423
- [35] Pietrangeli D, Garramone G, Guascito MR, Pepe A, Rosa A, Ricciardi G. Synthesis, coordination chemistry, and physico-chemical properties of the 2-chloroethoxy-iron(III)(ethylthio)porphyrazine. *J. Porphyr. Phthalocya.* 2013;17:870-880. doi:10.1142/S1088424613500685
- [36] Garramone G, Pietrangeli D, Ricciardi G, Conoci S, Guascito MR, Malitesta C, Cesari D, Casilli S, Giotta L, Giancane G, Valli L. Electrochemical and spectroscopic behavior of iron(III) porphyrazines in Langmuir-Schaefer films. *J. Phys. Chem. B.* 2008;112:11517-11528. doi:10.1021/jp803418b
- [37] Kobayashi N. Dimers, trimers and oligomers of phthalocyanines and related compounds. *Coord. Chem. Rev.* 2002;227:129-152. doi:10.1016/S0010-8545(02)00010-3
- [38] He W, Lieberman M. The synthesis and characterization of a side-by-side iron phthalocyanine dimer. *J. Porphyr. Phthalocya.* 2011;15:277-292. doi:10.1142/S1088424611003264
- [39] Odabas Z, Dumludağ F, Özkaya AR, Yamauchi S, Kobayashi N, Bekaroğlu Ö. Novel homo- and heterobinuclear ball-type phthalocyanines: synthesis and electrochemical, electrical, EPR and MCD spectral properties. *Dalt. Trans.* 2010;39:8143-8152. doi:10.1039/c0dt00398k
- [40] Odabas Z, Altindal A, Özkaya AR, Salih B, Bekarolu Ö. Novel ball-type homo- and hetero-dinuclear phthalocyanines with four 1,1'-methylenedipthalen-2-ol bridges: synthesis and characterization, electrical and gas sensing properties and electrocatalytic performance towards oxygen reduction. *Sens. Actuators, B Chem.* 2010;145:355-366. doi:10.1016/j.snb.2009.12.016
- [41] Chen L, Zhang Z, Wang Y, Guan Y, Deng K, Lv K, Sun J, Li Z, Li M. Photocatalytic properties and electrochemical characteristic of a novel biomimetic oxygenase enzyme photocatalyst iron(II) tetrahydroxymethyl tetra(1,4-dithiin) porphyrazine for the degradation of organic pollutants. *J. Mol. Catal. A Chem.* 2013;372:114-120. doi:10.1016/j.molcata.2013.02.013
- [42] Fitzgerald JP, Haggerty BS, Rheingold AL, May L, Brewer GA. Iron octaethyltetraaza-porphyrins—synthesis, characterization, coordination chemistry, and comparisons to related iron porphyrins and phthalocyanines. *Inorg. Chem.* 1992;31:2006-2013. doi:10.1021/ic00037a007

- [43] Kobayashi N, Nishiyama Y, Ohya T, Sato M. Symmetrically tetra-substituted phthalocyanines. *J. Chem. Soc. Chem. Commun.* 1987;390-392. doi:10.1039/C39870000390
- [44] Goslinski T, Zhong C, Fuchter MJ, Stern CL, White AJP, Barrett AGM, Hoffman BM. Porphyrines as molecular scaffolds: flexible syntheses of novel multimetallic complexes. *Inorg. Chem.* 2006;45:3686-3694. doi:10.1021/ic060176n
- [45] Adebayo AI, Nyokong T. Synthesis, spectroscopic and electrochemical properties of manganese, nickel and iron octakis-(2-diethylaminoethanethiol)-phthalocyanine. *Polyhedron.* 2009;28:2831-2838. doi:10.1016/j.poly.2009.06.073
- [46] Arıcı M, Arıcan D, Uğur AL, Erdoğan A, Koca A. Electrochemical and spectroelectrochemical characterization of newly synthesized manganese, cobalt, iron and copper phthalocyanines. *Electrochim. Acta.* 2013;87:554-566. doi:10.1016/j.electacta.2012.09.045
- [47] Kudrik EV, van Eldik R, Makarov SV. Kinetics and mechanism of water substitution in the low-spin Fe(II) complex of 4-octasulfophenylpyrazinoporphyrazine. *Dalt. Trans.* 2004;429-435. doi:10.1039/B311695F
- [48] Baker R, Wilkinson DP, Zhang J. Facile synthesis, spectroscopy and electrochemical activity of two substituted iron phthalocyanines as oxygen reduction catalysts in an acidic environment. *Electrochim. Acta.* 2009;54:3098-3102. doi:10.1016/j.electacta.2008.12.003
- [49] Demirbas Ü, Akyüz D, Barut B, Bayrak R, Koca A, Kantekin H. Electrochemical and spectroelectrochemical properties of thiadiazole substituted metallo-phthalocyanines. *Spectrochim. Acta Part A Mol. Biomol. Spectrosc.* 2016;153:71-78. doi:10.1016/j.saa.2015.07.105
- [50] Yu B, Lever BP, Swaddle TW. Electrochemistry of metal phthalocyanines in organic solvents at variable pressure. *Inorg. Chem.* 2004;43:4496-4504. doi:10.1021/ic040032d
- [51] Prasad R, Gupta VK, Kumar A. Metallo-tetraazaporphyrin based anion sensors: regulation of sensor characteristics through central metal ion coordination. *Anal. Chim. Acta.* 2004;508:61-70. doi:10.1016/j.aca.2003.11.056
- [52] Chohan S, Booysen IN, Mambanda A, Akerman MP. Synthesis, characterization and electrocatalytic behavior of cobalt and iron phthalocyanines bearing chromone or coumarin substituents. *J. Coord. Chem.* 2015;68:1829-1846. doi:10.1080/00958972.2015.1023196
- [53] Paradine SM, White MC, Iron-catalyzed intramolecular allylic C-H amination. *J. Am. Chem. Soc.* 2012;134:2036-2039. doi:10.1021/ja211600g
- [54] Bolm C, Legros J, Le Pailh J, Zani L. Iron-catalyzed reactions in organic synthesis. *Chem. Rev.* 2004;104:6217-6254. doi:10.1021/cr040664h
- [55] Li W, Wu J, Higgins D, Choi J, Chen Z. Determination of iron active sites in pyrolyzed iron-based catalysts for the oxygen reduction reaction. *ACS Catal.* 2012;2:2761-2768. doi:10.1021/cs300579b
- [56] Johansson M, Jorgensen KA, Iron-catalyzed allylic amination, *J. Org. Chem.* 1994;59:214-216. doi:10.1021/jo00080a034

- [57] Lei Y, Sun J, Yang C, Deng K, Wang D. Preparation and properties of sulfur-containing tetraazaporphyrin iron supported on anion-exchange resin. *J. Porphyrins Phthalocya.* 2005;9:537-543. doi:10.1142/S1088424605000654
- [58] Tang J, Chen L, Sun J, Lv K, Deng K. Synthesis and properties of iron(II) tetra(1,4-dithiin) porphyrazine bearing peripheral long-chain alkyl group of active end-bromine. *Inorg. Chem. Commun.* 2010;13:236-239. doi:10.1016/j.inoche.2009.11.020
- [59] Yang C, Sun J, Deng K, Wang D. Synthesis and photocatalytic properties of iron(II) tetramethyl-tetra(1,4-dithiin)porphyrazine. *Catal. Commun.* 2008;9:321-326. doi:10.1016/j.catcom.2007.07.020
- [60] Zhang Z, Peng Q, Sun J, Fang L, Deng K. Enhancement of catalytic activities of a biomimetic catalyst  $\text{FePz}(\text{dtnCl}_2)_4$  for the wet oxidation of Brilliant Red X3B through the synergetic effect of heat and light irradiation. *Ind. Eng. Chem. Res.* 2013;52:13342-13349. doi:10.1021/ie4016842
- [61] Su R, Sun J, Sun Y, Deng K, Cha D, Wang D. Oxidative degradation of dye pollutants over a broad pH range using hydrogen peroxide catalyzed by  $\text{FePz}(\text{dtnCl}_2)_4$ . *Chemosphere.* 2009;77:1146-51. doi:10.1016/j.chemosphere.2009.08.005
- [62] Theodoridis A, Maigut J, Puchta R, Kudrik EV, van Eldik R. Novel iron(III) porphyrazine complex. Complex speciation and reactions with NO and  $\text{H}_2\text{O}_2$ . *Inorg. Chem.* 2008;47:2994-3013. doi:10.1021/ic702041g
- [63] Bıyıklıođlu Z, Saka ET, Gökçe S, Kantekin H. Synthesis, characterization and investigation of homogeneous oxidation activities of peripherally tetra-substituted Co(II) and Fe(II) phthalocyanines: oxidation of cyclohexene. *J. Mol. Catal. A Chem.* 2013;378:156-163. doi:10.1016/j.molcata.2013.06.009
- [64] İsci Ü, Caner C, Zorlu Y, Gürek AG, Dumoulin F, Ahsen V. Sulfonamide-substituted iron phthalocyanine: design, solubility range, stability and oxidation of olefins. *Dalt. Trans.* 2014;43:17916-17919. doi:10.1039/C4DT02412E
- [65] Saka ET, Bıyıklıođlu Z. Co(II) and Fe(II) phthalocyanines: synthesis, characterization and catalytic activity on cyclohexene oxidation with different oxygen source. *J. Organomet. Chem.* 2013;745-746:50-56. doi:10.1016/j.jorganchem.2013.07.018
- [66] Sun X, Wang L, Tan Z. Improved synthesis of soluble metal-free/metal phthalocyanine tetracarboxylic acids and their application in the catalytic epoxidation of cyclohexene. *Catal. Lett.* 2015;145:1094-1102. doi:10.1007/s10562-015-1500-0
- [67] Aktas A, Acar İ, Bıyıklıođlu Z, Saka ET, Kantekin H. Synthesis, electrochemistry of metal-free, copper, titanium phthalocyanines and investigation of catalytic activity of cobalt, iron phthalocyanines on benzyl alcohol oxidation bearing 4-{2-[3-trifluoromethyl]phenoxy}ethoxy} groups. *Synth. Met.* 2014;198:212-220. doi:10.1016/j.synthmet.2014.10.022
- [68] Çakır V, Saka ET, Bıyıklıođlu Z, Kantekin H. Highly selective oxidation of benzyl alcohol catalyzed by new peripherally tetra-substituted Fe(II) and Co(II) phthalocyanines. *Synth. Met.* 2014;197:233-239. doi:10.1016/j.synthmet.2014.09.022

- [69] Ma P, Lv L, Zhang M, Yuan Q, Cao J, Zhu C. Synthesis of catalytically active porous organic polymer from iron phthalocyanine and diimide building blocks. *J. Porous Mater.* 2015;22:1567-1571. doi:10.1007/s10934-015-0039-1
- [70] Hiraike Y, Saito M, Niwa H, Kobayashi M, Harada Y, Oshima M, Kim J, Nabaie Y, Kakimoto M. Active site formation mechanism of carbon-based oxygen reduction catalysts derived from a hyperbranched iron phthalocyanine polymer. *Nanoscale Res. Lett.* 2015;10:179-190. doi:10.1186/s11671-015-0881-8
- [71] Isaacs M, Armijo F, Ramírez G, Trollund E, Biaggio SR, Costamagna J, Aguirre MJ. Electrochemical reduction of CO<sub>2</sub> mediated by poly-M-aminophthalocyanines (M=Co, Ni, Fe): poly-Co-tetraaminophthalocyanine, a selective catalyst. *J. Mol. Catal. A Chem.* 2005;229:249-257. doi:10.1016/j.molcata.2004.11.026
- [72] Zagal JH, Gulppi M, Isaacs M, Cárdenas-Jirón G, Jesús Aguirre M. Linear versus volcano correlations between electrocatalytic activity and redox and electronic properties of metallophthalocyanines. *Electrochim. Acta.* 1998;44:1349-1357. doi:10.1016/S0013-4686(98)00257-6
- [73] Zagal JH, Griveau S, Silva JF, Nyokong T, Bedioui F. Metallophthalocyanine-based molecular materials as catalysts for electrochemical reactions. *Coord. Chem. Rev.* 2010;254:2755-2791. doi:10.1016/j.ccr.2010.05.001

IntechOpen

